

ORNL/CP--94923
CONF-9709119--

Note: This is a preprint of a paper being submitted for publication. Contents of this paper should not be quoted nor referred to without permission of the author(s).

To be published in:

ORNL/CP-94923

Proceedings of the International Conference on
Inorganic Scintillators and Their Applications

Shanghai, China
Sept. 22-25, 1997

RECEIVED

NOV 04 1997

OSTI

Recent Results in a Search for Inorganic Scintillators for X- and Gamma-Ray Detection

W.W. Moses¹, M.J. Weber¹, S.E. Derenzo¹, D. Perry¹,
P. Berahl¹, L. Schwarz², U. Sasum², and L.A. Boatner³

¹Lawrence Berkeley National Laboratory, U. of Calif., Berkeley, CA 94720

²Ernst-Moritz-Arndt- Universitat, D-17489 Greifswald, Germany

³Oak Ridge National Laboratory, MS-6056, Building 3150, Oak Ridge, TN 37831

October 1997

"The submitted manuscript has been authored by a contractor of the U.S. Government under contract DE-AC05-96OR22464. Accordingly, the U.S. Government retains a nonexclusive, royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for U.S. Government purposes."

Prepared by
Solid State Division
Oak Ridge National Laboratory
P.O. Box 2008
Oak Ridge, Tennessee 37831-6056
managed by
LOCKHEED MARTIN ENERGY RESEARCH CORP.
for the
U.S. DEPARTMENT OF ENERGY
under contract DE-AC05-96OR22464

This research was sponsored by the Oak Ridge National Laboratory, managed by Lockheed Martin Energy Research Corp., for the U.S. Department of Energy, under contract DE-AC05-96OR22464.

MASTER

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, make any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

DISCLAIMER

**Portions of this document may be illegible
in electronic image products. Images are
produced from the best available original
document.**

Recent Results in a Search for Inorganic Scintillators for X- and Gamma Ray Detection*

W. W. Moses, M. J. Weber, S. E. Derenzo, D. Perry, P. Berdahl, L. Schwarz[†], U. Sasum[†], and L. A. Boatner[‡]

Lawrence Berkeley National Laboratory, University of California, Berkeley, CA 94720 USA

[†]Ernst-Moritz-Arndt-Universität, D-17489 Greifswald, Germany

[‡]Oak Ridge National Laboratory, Oak Ridge, TN 37831 USA

Abstract

We present recent results from an ongoing search for inorganic scintillators for gamma ray detection in which we measure the scintillation properties (luminous efficiency, decay time, and emission wavelength) of powdered samples excited by brief x-ray pulses. Recent promising candidates include cerium doped lutetium borate (LuBO_3) and the lutetium double phosphates $\text{K}_3\text{Lu}(\text{PO}_4)_2$ and $\text{Rb}_3\text{Lu}(\text{PO}_4)_2$, which have luminous intensities above 25,000 photons/MeV. In order to find scintillators that are compatible with silicon photodetectors, we have tested over 1,100 samples using a photomultiplier tube with a GaAs:Cs photocathode, which is sensitive to emissions from 200–950 nm. While many samples exhibited strong emissions in the 600–900 nm range, all had decay times that were larger than 10 μs .

I. INTRODUCTION

We have previously described [1, 2] a method for finding new scintillators by measuring the scintillation properties (luminous efficiency, decay time, and emission wavelength) of powdered samples when excited with brief x-ray pulses [3, 4, 5]. By synthesizing and testing candidate compounds as powders, the difficult task of obtaining large, optically clear samples need only be performed for the most promising compounds. To date, over 1,100 powdered samples have been measured, including both intrinsic and doped compounds. This search method has yielded several candidate materials, including cerium fluoride [6], lead tungstate [1], $\text{LuAlO}_3\text{:Ce}$ [7], and the materials described herein. We are continuing this search to find materials with properties suited for gamma ray detection, which include short attenuation length, high effective atomic number, short fluorescent decay time, high luminous efficiency, and the ability to be economically formed into large, transparent pieces. We are also extending our search to cover longer emission wavelengths, as applications that utilize silicon photodiodes as optical detectors would benefit from scintillators that emit in the 550–1050 nm wavelength region. Many potentially useful materials may have been missed in previous searches because conventional alkali photomultiplier tubes that are insensitive to emissions in this wavelength range were used.

II. METHODS

Powdered samples are measured by exciting them with 20 to 30 keV, 90 ps wide x-ray pulses from the table top pulsed

x-ray unit shown in figure 1 and observing their emission intensity with a sapphire windowed microchannel plate photomultiplier tube. The powdered samples are placed in a quartz cuvette 50 mm long, 5.0 mm outer diameter, with 0.37 mm wall thickness, and sealed with a plastic cap. The cuvette is placed in a holder in a light-tight box in the x-ray beam. A thin aluminum window allows the 20–30 keV x-rays to penetrate the box and excite the sample. Some of the potential fluorescent photons from the sample reach a photomultiplier tube, and its subsequent output measured. Comparison of this photomultiplier tube output to that from powders of a known, well-established scintillator (BGO) is then used to derive the emission intensity. Some samples have individual grains that are not powdered, but are small (0.5 mm typical dimension) crystals. This reduces their optical attenuation (as compared to a powder), and so artificially increases their measured luminosity, typically by a factor of 2–5 [2]. By recording the time difference between the x-ray pulse and the scintillation signal with the delayed coincidence method [8] (with an instrumental response time of 120 ps fwhm), the fluorescent lifetime is measured. By inserting a computer controlled monochromator between the sample and the photomultiplier tube, the emission spectrum is measured [5]. This spectrum is corrected for the wavelength dependent efficiency of the monochromator, but not of the photomultiplier tube, which has a relatively flat response (70 mA/W) between 300 and 850 nm.

To study emissions with >500 nm wavelength, we use a Hamamatsu R 943-02 photomultiplier tube with a GaAs:Cs photocathode, which has high sensitivity to emissions from 200–900 nm. The quantum efficiency and dark current (when cooled to -20°C) of this photomultiplier tube are comparable

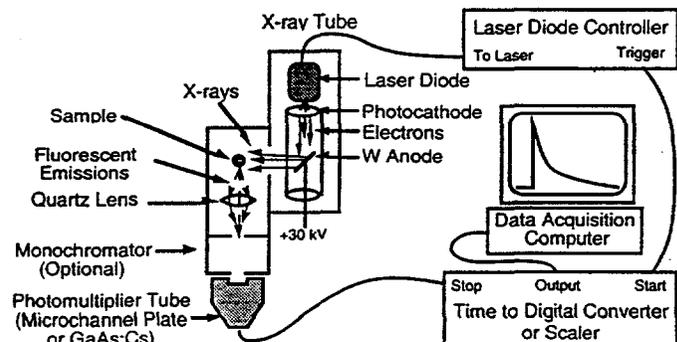


Figure 1. Measurement Apparatus. X-rays from the pulsed x-ray tube impinge on a powdered sample in a quartz cuvette, and the resulting fluorescent emissions (if any) are detected by a photomultiplier tube. The photomultiplier tube count rate measures fluorescent intensity and the delayed coincidence method is used to measure the fluorescent decay time. By inserting a monochromator into the optical path, the emission spectrum is measured.

* This work was supported in part by the U.S. Department of Energy under Contract No. DE-AC03-76SF00098, and in part by Public Health Service Grant No. P01-CA48002 from the National Cancer Institute of the National Institutes of Health.

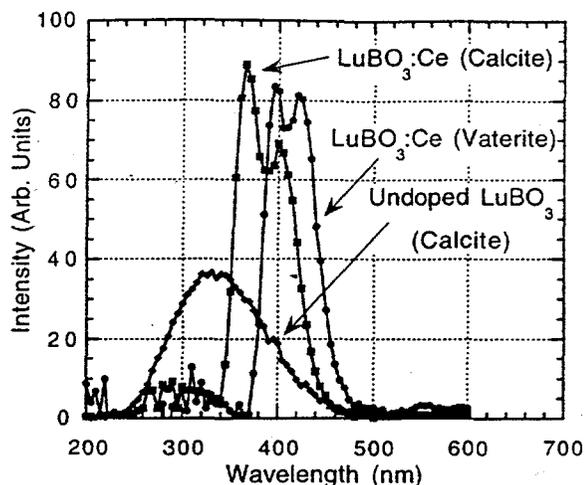


Figure 2. Emission spectra (not to scale) of lutetium borate compounds, corrected for wavelength dependence of monochromator (but not PMT) efficiency.

to a bialkali photomultiplier tube at room temperature, but because of the electron optics in this design (it is a "side-on" photomultiplier tube in an "end-on" package), the single photoelectron transit time jitter is approximately 4 ns fwhm. To restrict our sensitivity to the 600–900 nm range, a pair of filters (Hoya O-54 and R-62) are placed in the optical path. A pair (rather than a single filter) was used to reduce filter fluorescence [9], and the filters were kept in the dark for a day before data collection to minimize phosphorescence.

III. LUTETIUM BORATE

One potentially interesting compound is cerium activated lutetium borate ($\text{LuBO}_3:\text{Ce}$) [10]. This compound exists in two phases: the low temperature calcite phase ($\rho=6.9 \text{ g/cm}^3$, stable below 1310°C) and the high temperature vaterite phase ($\rho=7.4 \text{ g/cm}^3$, stable above 1310°C) [11]. This implies an attenuation length for 511 keV photons of 1.3 cm for the calcite phase, 1.2 cm for the vaterite phase, and a photoelectric fraction of 34% for either phase. For the vaterite phase (with 0.1% Ce), the luminous intensity is 26,000 photons per MeV, the emission spectrum has overlapping peaks centered at 395 and 425 nm (2000 cm^{-1} Stokes shift), and the decay time is fit by a single exponential components with a 39 ns decay constant. For the calcite phase (with 0.5% Ce), the luminous intensity is 27,000 photons per MeV, the emission spectrum has overlapping peaks centered at 365 and 400 nm (2750 cm^{-1} Stokes shift), and the decay time is fit by the sum of four exponential components — 10% at 9.4 ns, 69% at 23 ns, 10% at 245 ns, and 6% at 1640 ns. While the vaterite phase shows no emissions without cerium doping, undoped calcite phase material has an emission intensity of 11,000 photons per MeV, a single, broad emission peak centered at 330 nm, and a decay time that is fit by the sum of two exponential — 60% at 30 ns and 40% at 1400 ns. Figures 2&3 show the emission spectra and decay times of these samples.

While this combination of properties is nearly ideal for gamma ray detection, LuBO_3 may prove difficult to produce economically in large, transparent pieces. The phase transition occurs at 1310°C (at atmospheric pressure), more than 300°C below its 1650°C melting point. Since the two

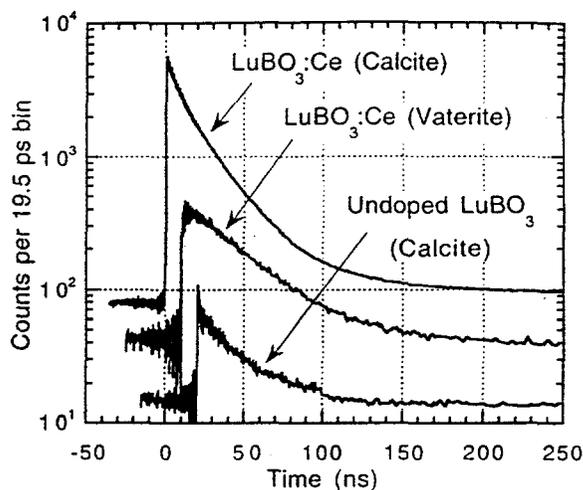


Figure 3. Decay of the lutetium borate compounds ($t=0$ displaced for clarity), measured with a microchannel plate photomultiplier tube.

phases have significantly different densities and structures, common melt-based crystal growth techniques (such as Czochralski or Bridgeman) are unlikely to be successful in producing clear, single crystals without the addition of phase stabilizing dopants. Flux growth might be used to produce good quality calcite phase crystals, but materials with the calcite structure often cleave easily, which is not desirable.

IV. LUTETIUM DOUBLE PHOSPHATES

Lutetium potassium phosphate [$\text{K}_3\text{Lu}(\text{PO}_4)_2:\text{Ce}$] and lutetium rubidium phosphate [$\text{Rb}_3\text{Lu}(\text{PO}_4)_2:\text{Ce}$] are also interesting cerium activated compounds. These compounds are not listed in powder x-ray diffraction databases, and so their densities are not known. Their densities can be approximated by taking the density of a similar compound and multiplying by the formula weight ratio. Such compounds are $\text{K}_3\text{La}(\text{PO}_4)_2$ ($\rho=3.63 \text{ g/cc}$), $\text{K}_3\text{Ce}(\text{PO}_4)_2$ ($\rho=3.71 \text{ g/cc}$), $\text{K}_3\text{Tb}(\text{PO}_4)_2$ ($\rho=3.96 \text{ g/cc}$) and $\text{Rb}_3\text{La}(\text{PO}_4)_2$ ($\rho=4.39 \text{ g/cc}$). This predicts a density of 4.0 g/cc for $\text{K}_3\text{Lu}(\text{PO}_4)_2$ and 4.66 g/cc for $\text{Rb}_3\text{Lu}(\text{PO}_4)_2$, but x-ray analysis shows that the lutetium double phosphate compounds have a different unit cell, so this method is unlikely to be accurate. If, however, we assume that both compounds have a density $\rho=4.0 \text{ g/cc}$, they would have a photoelectric fraction of 19% for the potassium compound, 18% for the rubidium compound, and an attenuation length for 511 keV photons of 2.7 cm for either compound.

These compounds are very luminous — 52,500 photons / MeV for the potassium compound and 28,200 photons / MeV for the rubidium compound. Both the decay time and emission wavelength are typical of cerium (40 ns decay time, 410 nm emission wavelength). Table 1 provides a more complete list of the scintillation properties for samples with various cerium concentrations, while figures 4&5 show the emission spectra and decay times of sample with "optimal" (0.5%) cerium concentration. The emission wavelength is centered at 410 nm, independent of compound type or dopant concentration. The emission in the undoped compounds may be due to cerium impurities in the lutetium oxide starting material.

Table 1. Properties of Double Phosphate Compounds. The measured luminous intensity (in photons per MeV) and decay times of $K_3Lu(PO_4)_2$ and $Rb_3Lu(PO_4)_2$ as a function of cerium concentration.

Compound	Cerium Fraction			
	Undoped	0.1%	0.5%	1.0%
$K_3Lu(PO_4)_2$	14,500 phot/MeV 75% @ 44 ns 25% @ 1350 ns	46,400 phot/MeV 86% @ 39 ns 14% @ 1250 ns	52,500 phot/MeV 86% @ 37 ns 14% @ 1080 ns	19,400 phot/MeV 74% @ 40 ns 26% @ 1060ns
$Rb_3Lu(PO_4)_2$	7,400 phot/MeV 95% @ 44 ns 5% @ 1290 ns	24,600 phot/MeV 89% @ 40 ns 11% @ 1190 ns	27,100 phot/MeV 91% @ 36 ns 9% @ 920 ns	28,200 phot/MeV 84% @ 34 ns 16% @ 990 ns

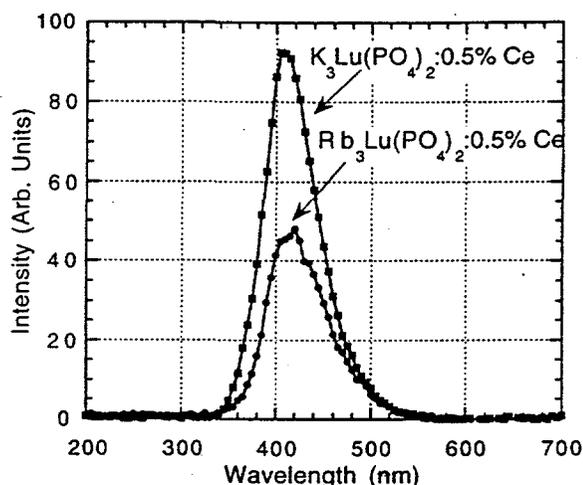


Figure 4. Emission spectra of double phosphate compounds, corrected for wavelength dependence of monochromator (but not PMT) efficiency.

Despite the relatively low density, these compounds have properties that are well suited for gamma ray detection. However, they may prove difficult to produce economically in large, transparent pieces. The compounds do not melt congruently, but decompose before they melt. This again makes growth by common crystal growth techniques from the melt (such as Czochralski or Bridgeman) unlikely to be successful, although flux growth may be possible.

V. LONG WAVELENGTH SCINTILLATORS

Several lanthanide and transition metal ions are known to emit at wavelengths >500 nm in suitable hosts. While most have decay lifetimes of hundreds of microseconds to many milliseconds, there are some (e.g. Eu^{2+} , Ce^{3+} , Fe^{3+} , and Ti^{3+}) with decay times of a few microseconds or less. We have tested all of our compounds for scintillation, and observed emission intensities comparable to commercial phosphors in the 600–900 nm range for Eu and Sm doped $LuPO_4$, $ScPO_4$, and YPO_4 . Significant emissions are also observed in Tb, Dy, Er, Pr, and Tm doped phosphates, as well as several intrinsic compounds. Unfortunately, none of the compounds measured had a major scintillation decay component of 10 μs or less. The Appendix lists the luminous intensity of those compounds with a light output (in the 600–900 nm range) of ≥ 500 photons / MeV. Note that data for all compounds is

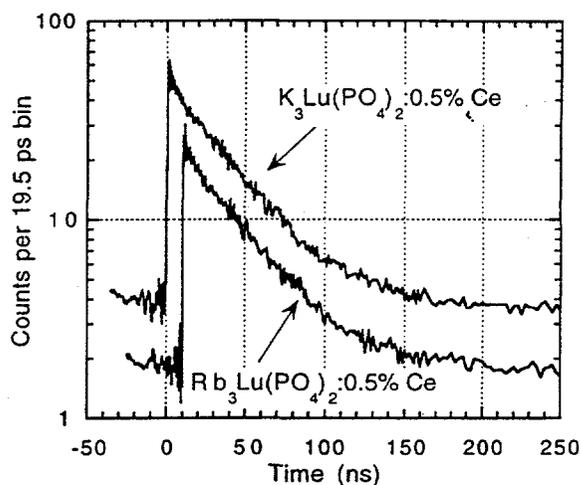


Figure 5. Decay time of the double phosphate compounds, measured with a microchannel plate photomultiplier tube (120 ps fwhm system response).

available electronically in the red_luminosity.dat file via anonymous FTP to scint.lbl.gov [12].

VI. CONCLUSION

Several cerium activated, lutetium based scintillators that possess attractive properties for gamma ray detection have been identified. The vaterite phase of lutetium borate ($LuBO_3:0.2\% Ce$) has a density of 7.4 g/cc, a luminous intensity of 26,000 photons / MeV, a decay time of 39 ns, and overlapping emission peaks at wavelengths of 395 and 425 nm. Cerium activated lutetium potassium phosphate ($K_3Lu(PO_4)_2:0.5\% Ce$) has a density of ~ 4 g/cc, a luminous intensity of 52,500 photons / MeV, a decay time of 40 ns, and an emission wavelength of 410 nm. Despite these attractive properties, both compounds may prove difficult to fabricate in large, optically transparent pieces. Over 1,100 compounds have been examined for emissions in the 600–900 nm range, which are appropriate for readout with silicon photodiodes. While emission intensities comparable to commercial phosphors are measured in Eu and Sm doped $LuPO_4$, $ScPO_4$, and YPO_4 , none of the compounds measured had a major scintillation decay component of 10 μs or less.

Table 2. Long Wavelength Luminosities. The measured luminous intensity (in photons per MeV) of the 600–900 nm emissions. Samples marked with an asterisk (*) contain (0.5 mm typical dimension) crystals and thus have less optical attenuation than powdered samples, yielding high estimates (typical factor 2–5) for the luminosity.

Photon / MeV	Compound	Phot. / MeV	Compound
123171 *	LuPO ₄ :20% Eu	2571 *	YPO ₄ :5% Nd
103244 *	LuPO ₄ :30% Eu	2497	Eu ₂ O ₃
76099 *	LuPO ₄ :~5% Eu	2468 *	LuPO ₄ :0.7% Fe
61072 *	ScPO ₄ :~1% Eu	2427	EuF ₃
60316 *	LuPO ₄ :5%Eu, 1%Gd	2418 *	BaLuYF ₃ :0.2% Pr
44302 *	ScPO ₄ :10% Sm	2401 *	Na _{0.4} Lu _{0.6} F ₂ : 1% Nd
35728	YVO ₄ :Eu	2296	Bi ₂ Al ₄ O ₉ : 0.5% Ce
31543 *	ScPO ₄ :3% Sm	2271 *	ScPO ₄ :2% Dy
31294 *	YPO ₄ :2% Sm	2232	CaMoO ₄
22095 *	YPO ₄ :?% Eu	2201	LaF ₃ :1% Pr, 1% Ba
15728 *	LuPO ₄ :2% Sm	2157	Y ₂ O ₃ :2% Tb
14589 *	ScPO ₄ :~5% Eu	2089 *	ScPO ₄ :1.7% Ni
14288 *	LuPO ₄ :10 % Sm	1806 *	BaF ₂ :8.4% Ho
13067	GdTaO ₄ :Tb	1799	LaF ₃ :0.5% Pr
13053 *	ScPO ₄ :2.9% Dy	1743 *	PbHPO ₄ :5.8% Tb
12101 *	YPO ₄ :1% Dy	1651 *	ScPO ₄ :0.7% Fe
10914 *	ScPO ₄ :0.7% Er	1609 *	TbPO ₄ :25% Gd
10304	BaF ₂ :10% Eu	1526	Y ₂ O ₃ :2% Tb, 2% Eu
9316 *	LuPO ₄ :10% Tb	1514	TbF ₃
9280 *	ScPO ₄ :10% Pr	1514	Lu ₃ Al ₅ O ₁₂ :Ce
9242 *	YPO ₄ :2% Tm	1506 *	LaPO ₄ :?% Eu
7824 *	LaF ₃ :0.5% Pr	1444 *	LuPO ₄ :2% Tm
7658 *	ScPO ₄ :2.6% Pr	1427	CdF ₂ :1% Er
7125	HfTiO ₄	1425	LaF ₃ :1% Pr
7057 *	ZnS:Ag	1389	Al ₂ O ₃
6748 *	ScPO ₄ :1.7% Nd	1378	TbCl ₃
6539	LuTaO ₄ :Tb	1304	ZnO:0.3 % Al
5284 *	ScPO ₄ :0.7% V	1288	3(Zn(OH) ₂)·2(ZnCO ₃)
4776	BaF ₂ :5% Eu	1137	SnSO ₄
4449 *	ScPO ₄ :1% Tb	1133 *	BaF ₂ :10% Er
4399	TiO ₂	1128	BaF ₂ :3% Gd
4293 *	BaNb ₂ O ₆ · SrNb ₂ O ₆	1088	LuAlO ₃ : 1.5% Ce
4143 *	LuPO ₄ :0.63% Dy	1079 *	LuPO ₄ :3.1% Nd
4029 *	CdS	1073 *	SbI ₃
3856	Bi ₂ Al ₄ O ₉	1069	BaF ₂ :1% Eu
3786	SrI ₂	1054	ThCl ₄
3446 *	ScPO ₄ :2% Nd	1040	Eu ₂ (CO ₃) ₃ · x(H ₂ O)
3388 *	Y _{0.5} Gd _{0.5} PO ₄	1025 *	ZnO: 0.6% In
3216 *	ZnO	1017	LuAlO ₃ : 0.5% Ce
3211 *	SrTiO ₃	1011	Bi ₄ Ge ₃ O ₁₂
3202	BaF ₂ :6%Gd, 0.5%Pr	1009	GdF ₃ :15% Ca, <1%Pr
3190 *	ScPO ₄ :1.7% Yb	994	CdF ₂ :10% Tb
3110 *	BaF ₂ :6%Gd, 0.2%Pr	960	ZrO ₂
3060 *	YPO ₄ :0.5% Fe	959	GdF ₃ :17% Sr, <1% Pr
3013 *	YPO ₄ :1% Tb	952 *	YPO ₄ :25% Pr
2942 *	Na _{0.4} Y _{0.6} F ₂ : 1% Nd	939 *	LuPO ₄ :40% Pr
2825 *	LuPO ₄ :0.26% Dy	933 *	LuPO ₄ :25% Pr
2823 *	BaF ₂ :3% Gd,0.2% Pr	932	ErF ₃
2713 *	BaF ₂ :2% Gd,0.2% Pr	930	TbF ₃ :0.5% Ce
2690	CsI	917	Mg ₂ P ₂ O ₇ · 3(H ₂ O)

VII. ACKNOWLEDGMENT

This work was supported in part by the Director, Office of Energy Research, Office of Biological and Environmental Research, Medical Applications and Biophysical Research Division of the U.S. Department of Energy under contract No. DE-AC03-76SF00098 and in part by the National Institutes of Health, National Cancer Institute under grant No. R01-CA48002. Reference to a company or product name does not imply approval or recommendation by the University of California or the U.S. Department of Energy to the exclusion of others that may be suitable.

REFERENCES

- [1] Derenzo SE, Moses WW, Cahoon JL, et al. Prospects for new inorganic scintillators. *IEEE Trans. Nucl. Sci.* NS-37: pp. 203-208, 1990.
- [2] Derenzo SE, Moses WW, Cahoon JL, et al. X-ray fluorescence measurements of 412 inorganic compounds. *Proceedings of The IEEE Nuclear Science Symposium*, pp. 143-147, (Edited by G. T. Baldwin), Santa Fe, NM, 1991.
- [3] Derenzo SE, Moses WW, Blankespoor SC, et al. Design of a pulsed x-ray system for fluorescent lifetime measurements with a timing resolution of 109 ps. *IEEE Trans. Nucl. Sci.* NS-41: pp. 629-631, 1994.
- [4] Blankespoor SC, Derenzo SE, Moses WW, et al. Characterization of a pulsed x-ray source for fluorescent lifetime measurements. *IEEE Trans. Nucl. Sci.* NS-41: pp. 698-702, 1994.
- [5] Moses WW, Derenzo SE, Weber MJ, et al. Scintillator characterization using the LBL pulsed x-ray facility. *Rad. Meas.* 24: pp. 337-341, 1995.
- [6] Moses WW and Derenzo SE. Cerium fluoride, a new, heavy fast scintillator. *IEEE Trans. Nucl. Sci.* NS-36: pp. 173-176, 1989.
- [7] Moses WW, Derenzo SE, Fyodorov A, et al. LuAlO₃:Ce – a high density, high speed scintillator for gamma detection. *IEEE Trans. Nucl. Sci.* NS-42: pp. 275-279, 1995.
- [8] Bollinger LM and Thomas GE. Measurement of the time dependence of scintillation intensity by a delayed-coincidence method. *Rev. Sci. Instr.* 32: pp. 1044-1050, 1961.
- [9] Turner WH. Photoluminescence of color filter glass. *Appl. Optics* 12: pp. 480-486, 1973.
- [10] Weber MJ, Derenzo SE, Dujardin C, et al. Dense Ce³⁺-activated scintillator materials. *Proceedings of Scint '95*, pp. 325-328, (Edited by P. Dorenbos and C. W. E. van Eijk), Delft, The Netherlands, 1996.
- [11] Levin E, Roth RS and Martin JB. Polymorphism of ABO₃ type rare earth borates. *Am. Mineral* 46: pp. 1030-1055, 1961.
- [12] Moses WW, West AC, Derenzo SE, et al. Internet access to data for scintillation compounds. *Proceedings of Scint '95*, pp. 525-527, (Edited by P. Dorenbos and C. W. E. van Eijk), Delft, The Netherlands, 1996.