

CERN 98-01
Technical Inspection
and Safety Commission
18 May 1998

ORGANISATION EUROPÉENNE POUR LA RECHERCHE NUCLÉAIRE
CERN EUROPEAN ORGANIZATION FOR NUCLEAR RESEARCH

**COMPILATION OF RADIATION
DAMAGE TEST DATA**

PART II, 2nd edition:
Thermoset and thermoplastic resins, composite materials

**INDEX DES RÉSULTATS D'ESSAIS
DE RADIORÉSISTANCE**

II^e PARTIE, 2^e édition :
Résines thermodurcies et thermoplastiques, matériaux composites

M. Tavlet, A. Fontaine and H. Schönbacher
CERN, 1211 Geneva 23, Switzerland

L

30 - 03

GENEVA
1998

© Copyright CERN, Genève, 1998

Propriété littéraire et scientifique réservée pour tous les pays du monde. Ce document ne peut être reproduit ou traduit en tout ou en partie sans l'autorisation écrite du Directeur général du CERN, titulaire du droit d'auteur. Dans les cas appropriés, et s'il s'agit d'utiliser le document à des fins non commerciales, cette autorisation sera volontiers accordée.

Le CERN ne revendique pas la propriété des inventions brevetables et dessins ou modèles susceptibles de dépôt qui pourraient être décrits dans le présent document; ceux-ci peuvent être librement utilisés par les instituts de recherche, les industriels et autres intéressés. Cependant, le CERN se réserve le droit de s'opposer à toute revendication qu'un usager pourrait faire de la propriété scientifique ou industrielle de toute invention et tout dessin ou modèle décrits dans le présent document.

Literary and scientific copyrights reserved in all countries of the world. This report, or any part of it, may not be reprinted or translated without written permission of the copyright holder, the Director-General of CERN. However, permission will be freely granted for appropriate non-commercial use.

If any patentable invention or registrable design is described in the report, CERN makes no claim to property rights in it but offers it for the free use of research institutions, manufacturers and others. CERN, however, may oppose any attempt by a user to claim any proprietary or patent rights in such inventions or designs as may be described in the present document.

ISSN 0007-8328

ISBN 92-9083-126-X

ABSTRACT

This catalogue summarizes radiation damage test data on thermoplastic and thermoset resins and composites. Most of them are epoxy resins used as insulator for magnet coils. Many results are also given for new engineering thermoplastics which can be used either for their electrical properties or for their mechanical properties.

The materials have been irradiated either in a ^{60}Co source, up to integrated absorbed doses between 200 kGy and a few megagrays, at dose rates of the order of 1 Gy/s, or in a nuclear reactor at dose rates of the order of 50 Gy/s, up to doses of 100 MGy.

The flexural strength, the deformation and the modulus of elasticity have been measured on irradiated and non-irradiated samples, according to the recommendations of the International Electrotechnical Commission. The results are presented in the form of tables and graphs to show the effect of the absorbed dose on the measured properties.

RÉSUMÉ

Ce catalogue donne les résultats d'essais sur la résistance aux rayonnements ionisants de résines thermodurcies et thermoplastiques, et de composites. Pour la plupart, il s'agit de résines époxydes utilisées comme isolant de bobines d'électro-aimants. De nombreux résultats sont aussi donnés sur des thermoplastiques d'engineering récents pouvant être utilisés soit pour leurs propriétés électriques, soit pour leurs propriétés mécaniques.

Les matériaux ont été irradiés soit en source de ^{60}Co , à des doses comprises entre 200 kGy et quelques mégagrays, à un débit de dose de l'ordre de 1 Gy/s, soit en réacteur nucléaire à un débit de dose de 50 Gy/s, jusqu'à des doses de 100 MGy.

La résistance en flexion, la déformation et le module d'élasticité sont mesurés sur des échantillons irradiés et non irradiés, conformément aux recommandations de la Commission Electrotechnique Internationale. Les résultats sont présentés sous forme de tableaux et de graphiques qui montrent l'effet de la dose absorbée sur ces propriétés.

**NEXT PAGE(S)
left BLANK**

CONTENTS

1.	Introduction	1
	Introduction	1
2.	Materials, characteristic properties, and end-point criteria	2
	Les matériaux, leurs propriétés caractéristiques et les critères de dégradation de ces propriétés	2
3.	Tests and test methods	3
	Essais et méthodes d'essais	3
4.	Irradiation conditions and dosimetry	4
	Conditions d'irradiation et dosimétrie	4
5.	Presentation of the data	5
	Présentation des résultats	5
6.	Classification of materials	6
	Classification des matériaux	6
	Acknowledgements	7
	Remerciements	7
	References	8
APPENDIX 1		15
	List of materials presented in the previous volumes	
APPENDIX 2		18
	Chemical structures of some commercial products	
APPENDIX 3		23
	Alphabetic compilation of data	
APPENDIX 4		171
	List of abbreviations used in the present volume	
APPENDIX 5		173
	List of suppliers of base materials, of transformers, and of some users who gave samples to CERN	

1. INTRODUCTION

Investigations into the degradation of materials and components which are exposed to ionizing radiation have been carried out in many applications, such as nuclear reactors, fusion reactors, high-energy accelerators, medical and industrial irradiation facilities, space projects, etc. At the European Organization for Nuclear Research (CERN), radiation damage test studies have been centred on organic and inorganic materials, electronic and optical components and devices, and other materials that are used in the construction and operation of high-energy accelerators and particle detectors.

Apart from electronic and optical devices, the organic materials are the ones most sensitive to radiation. As a consequence of this, a large number of radiation tests have been made on these materials and the results are extensively documented [e.g. 1–23]. Design engineers are, however, often faced with the problem of finding the desired information quickly within the available literature. We therefore decided to publish our radiation damage test results on organic materials in the form of catalogues.

The first catalogue, published more than fifteen years ago, concerned organic materials used as insulation and sheathing for electric cables [24].

The second dealt with thermosetting and thermoplastic resins, the majority being epoxies used for magnet coil insulations [25].

The third contained information on miscellaneous materials and components used around high-energy accelerators [26].

A second edition of the first catalogue was published in 1989 and concerns halogen-free cable-insulating materials [27].

The present volume is the second edition of the second part and concerns result of thermoset and thermoplastic resins and composite materials which were tested in the meantime.

As in the previous editions, the materials are presented in alphabetical order.

1. INTRODUCTION

Des essais sur la dégradation des matériaux due aux rayonnements ionisants ont été effectués dans plusieurs domaines d'application, par exemple autour des réacteurs nucléaires et de fusion, des accélérateurs à haute énergie, dans les installations industrielles ou médicales, dans les centres d'études spatiales, etc. A l'Organisation Européenne pour la Recherche Nucléaire (CERN), les essais de radiorésistance ont été concentrés sur des matériaux organiques et inorganiques, des composants électroniques et optiques, et d'autres matériaux qui sont utilisés pour la construction et l'opération des accélérateurs à haute énergie et les détecteurs de particules.

A part les composants électroniques et optiques, les matériaux organiques sont parmi les plus sensibles aux rayonnements ionisants. Par conséquent, une grande quantité de ces matériaux ont été soumis à des essais d'irradiation, et les résultats peuvent être trouvés dans de nombreuses publications [par exemple 1–23]. Toutefois, les ingénieurs rencontrent souvent des difficultés pour trouver, dans la littérature, l'information voulue. C'est pour cette raison que nous avons décidé de publier nos résultats d'essais de radiorésistance des matériaux organiques sous forme de catalogues.

Le premier catalogue, paru il y a plus de quinze ans, concernait les matériaux utilisés comme isolants, ainsi que pour les gaines de câbles électriques [24].

Le deuxième concernait des résines thermodurcies et thermoplastiques dont la plupart sont des époxydes utilisées dans l'isolation de bobines d'aimants [25].

Le troisième concernait divers matériaux et composants utilisés autour des accélérateurs de particules [26].

Une seconde édition du premier catalogue, publiée en 1989 portait sur les matériaux pour isolations et gaines de câbles exempts d'halogène [27].

Le présent volume est une seconde édition du deuxième ; il contient des informations sur des résines thermoplastiques et thermodurcies, ainsi que sur des matériaux composites.

Comme dans chaque édition, les matériaux sont présentés dans l'ordre alphabétique suivant leur nom anglais.

We first present some characteristic properties of the materials, and define our end-point criteria for the selection of radiation-resistant materials. We then list the tests and test methods, and give the irradiation conditions. In Section 5 we explain the presentation of the data. It should be noted that most of the data have been obtained from tests after accelerated irradiations, and that all tests were made at ambient temperature. After long exposures and ageing in other environments, a variation in the data presented may be expected; this is mainly the case for thermoplastic materials [9, 12, 18–23]. Test results at cryogenic temperatures can be found in Refs. [30–35].

2. MATERIALS, CHARACTERISTIC PROPERTIES, AND END-POINT CRITERIA

With a few exceptions, which are marked in the catalogue, all the test data given here have been obtained, over the past fifteen years, from commercially-available materials. Some of these materials may no longer be available and this is indicated in the tables when known. The most common materials that are dealt with here are:

- epoxy resins,
- polyester resins,
- polyurethanes,
- rigid and high performance thermoplastics.

The materials were usually supplied by European manufacturers involved in submitting offers and/or supplying components for the construction at CERN of the Large Electron–Positron storage ring (LEP), and for the Large Hadron Collider (LHC) project.

Some characteristic physical, mechanical, and electrical properties of thermoset resins are summarized in Table 1. These values are only a general indication since they depend on numerous parameters such as the composition and quantity of the base resin, the hardener, the accelerator, the filler, and other additives, as well as on the curing conditions, etc.

Most of the materials presented in this catalogue and all of the thermoplastics unless

Nous commençons par exposer quelques propriétés caractéristiques des matériaux présentés dans ce catalogue ; nous définissons les critères de dégradation de ces propriétés, qui servent à sélectionner les matériaux radiorésistants. Nous décrivons ensuite les méthodes d’essais, ainsi que les conditions d’irradiation. Dans la Section 5 nous expliquons la présentation des données. Il faut noter que les résultats ont généralement été obtenus par des irradiations accélérées, et que tous les essais ont été faits à température ambiante. Après une longue période d’irradiation et un vieillissement sous d’autres conditions, on peut s’attendre à un changement dans les résultats que nous avons obtenus, surtout pour les thermoplastiques [9, 12, 18–23]. Des résultats de tests à température cryogénique peuvent être trouvés aux références [30–35].

2. LES MATÉRIAUX, LEURS PROPRIÉTÉS CARACTÉRISTIQUES ET LES CRITÈRES DE DÉGRADATION DE CES PROPRIÉTÉS

A part quelques exceptions, qui sont indiquées dans le catalogue, tous les résultats donnés ont été obtenus, au cours des quinze dernières années, sur des matériaux disponibles dans le commerce. Il est possible que quelques-uns ne soient plus sur le marché, et nous l’avons noté dans les tableaux, pour les cas où nous l’avons su. Les plus courants de ces matériaux sont :

- résines époxydes
- résines polyestères
- polyuréthanes
- thermoplastiques rigides et hautes performance.

En général, les matériaux ont été fournis par des fournisseurs européens qui ont été engagés dans des offres ou des fournitures de matériels pour la construction au CERN du Large Electron-Positron Collider (LEP), ou pour le projet LHC (Large Hadron Collider), grand collisionneur de protons, supraconducteur.

Le tableau 1 donne un résumé des quelques propriétés mécaniques, électriques et physiques des résines thermodurcies. Ces valeurs peuvent seulement servir d’indication générale, puisqu’elles dépendent de nombreux paramètres tels que la composition et la quantité de la résine de base, du durcisseur et de l’accélérateur, ainsi que les charges et d’autres additifs.

otherwise stated, are halogen-free and contain little or no sulphur and phosphorus. They have passed the IEC 754–2 test which defines the maximum acidity and the maximum conductivity of combustion gases [28].

It is clear that when selecting and classifying materials according to their radiation resistance, not all of the properties listed in Table 1 could be tested, and we had to restrict ourselves to a few of the most characteristic and representative ones. For our purposes the mechanical properties were chosen. This choice can be justified by our own experience and that of others [10, 22, 29]. In general the mechanical degradation of plastic insulating materials due to ionizing radiation occurs before the degradation of the electrical and physical properties. Also, no important change in flammability was observed with radiation.

It should be noted that the mechanical properties of polymeric materials depend strongly on the temperature; at cryogenic temperature the stiffness and the brittleness are increased, and the plasticity and the impact strength are reduced. Irradiation of these materials either at low temperature or at room temperature does not influence their degradation: the mechanical properties of polymer-based materials are more influenced by the test temperature than by the irradiation temperature. A characteristic case is that of materials sensitive to oxido-degradation: the degradation is lower if they are irradiated in a cryogenic fluid rather than in air [30–35].

3. TESTS AND TEST METHODS

Whenever possible, the tests were carried out according to international norms [29]. Sometimes exceptions had to be made for practical or technical reasons, e.g. sample size, dose rate during irradiation, etc. The test samples, usually five per test, were cut from 2–6 mm thick plates molded from the respective materials.

Flexion tests were performed on an Instron testing machine to determine the breaking-strength and deflection at the breaking point.

Soulignons que la plupart des matériaux présentés dans ce catalogue, et en tout cas les thermoplastiques, sauf mention contraire sont exempts d'halogène et ne contiennent que peu ou pas de soufre ou de phosphore. Ils passent le test IEC 754–2 qui définit une acidité et une conductivité maximales des gaz de combustion [28].

Il est évident que, pour la sélection et la classification des matériaux selon leur résistance aux rayonnements, on ne peut pas tester toutes les propriétés citées dans le tableau 1, il faut se limiter à quelques-unes des plus représentatives. Dans le cas présent, nous avons choisi les propriétés mécaniques. Ce choix se justifie par notre propre expérience, et celle d'autres auteurs, qui nous a appris que la dégradation, due à l'irradiation, des propriétés mécaniques des isolants plastiques intervient généralement avant celle de leurs propriétés électriques et physiques [10, 22, 29]. D'autre part, les rayonnements n'ont que peu d'effet sur l'inflammabilité de ces matériaux.

Remarquons que les propriétés mécaniques des matériaux polymériques dépendent fortement de la température d'utilisation ; à température cryogénique la rigidité et la fragilité sont accrues, la plasticité et la résistance au chocs sont diminuées. Le fait d'irradier ces matériaux à basse température ou à température ambiante n'influe pas sur leur dégradation : les propriétés mécaniques des matériaux polymériques sont plus influencées par la température de test que par la température d'irradiation. Un cas particulier est celui des matériaux sensibles à l'oxydo-dégradation : lorsqu'ils sont irradiés dans un fluide cryogénique, leur dégradation est moindre que lorsqu'ils sont irradiés dans l'air [30–35].

3. ESSAIS ET MÉTHODES D'ESSAIS

Nous avons exécuté nos essais selon les normes internationales [29] dans tous les cas où cela était possible. Pour des raisons pratiques ou techniques, quelques exceptions étaient inévitables, par exemple dimension d'échantillons, débit de dose pendant l'irradiation, etc.

Les matériaux ont été fournis sous forme de plaques de 2 à 6 mm d'épaisseur, dans lesquelles, en général, cinq échantillons ont été coupés pour chaque essai.

From these measurements, the ultimate flexural strength, the deformation at break and the modulus of elasticity were calculated.

The testing method was a three-point loading system utilizing a centre load on the supported sample according to ASTM norm D790. The distance between the two supports was 67.0 mm and the speed of the central point was 2 mm/min for most of the materials. It was 5 mm/min for some very supple materials which undergo an important deformation. Some of these latter materials did not break during the test (the maximum value of the deformation appears in the tables). In this case, the flexural strength is the maximum recorded value, and not at the breaking point.

According to the recommendations of the International Electrotechnical Commission (IEC) [29], the most radiation-sensitive property is chosen as the reference critical property. For most of the thermoset resins and composites this critical property is the flexural strength, while for most of the thermoplastics it is the deflection [36]. The end-point criterion is 50% of the initial value of the critical property.

The Radiation Index (RI) is defined in IEC 544-4 as the logarithm, base 10, of the absorbed dose in grays (rounded down to two significant digits) at which the critical property is reduced to 50% of its initial value, under specified conditions of irradiation and tests.

4. IRRADIATION CONDITIONS AND DOSIMETRY

Most of the samples were irradiated in the ASTRA reactor at Seibersdorf (Austria) to doses between 5×10^6 Gy and 10^8 Gy, at dose rates of about 2×10^5 Gy/h.

In this 7 MW pool reactor, the irradiation position 'Ebene 1' is in the pool about 26 cm away from the reactor core. The neutron dose is less than 5% of the total dose to the samples. The irradiation medium is air, and the temperature is kept below 60°C.

More sensitive samples were irradiated with a ^{60}Co source, at Ionisos in Dagneux (France),

Des essais de flexion ont été effectués sur une machine Instron qui ont permis de déterminer la force ainsi que la déflexion à la rupture. Ensuite nous avons calculé la résistance à la flexion, la déformation et le module d'élasticité.

La méthode d'essai était un système d'appui à trois points : la force est appliquée sur le point central, selon la norme ASTM D790. La distance entre les deux points d'appui était de 67,0 mm, et la vitesse d'avancement du point central était de 2 mm/min pour la plupart des matériaux, elle était de 5 mm/min pour certains matériaux particulièrement souples à forte déformation. Certains de ces derniers n'ont pas subi de rupture lors des tests. La valeur maximale de la déformation apparaît dans les tables. Dans ce cas, la résistance à la flexion n'est pas calculée à la rupture, mais est la valeur maximale enregistrée au cours de l'essai.

Conformément aux recommandations de la Commission Electrotechnique Internationale (CEI) [29], on choisit comme propriété critique de référence celle qui est la plus sensible aux radiations. Pour les thermodurcies et les composites, il s'agit en général de la résistance à la flexion ; pour les thermoplastiques, il s'agit plutôt de la déflexion [36]. Le critère de fin de vie est 50 % de la valeur initiale de la propriété critique.

La publication CEI 544-4 définit un indice de rayonnement (RI) déterminé par le logarithme, en base 10, de la dose absorbée en grays (arrondi à deux chiffres significatifs) au-dessus de laquelle la valeur de la propriété critique a atteint 50 % de sa valeur initiale, dans les conditions spécifiques d'irradiation et de test.

4. CONDITIONS D'IRRADIATION ET DOSIMÉTRIE

La plupart des échantillons ont été irradiés au réacteur ASTRA, à Seibersdorf (Autriche), à des doses de 5×10^5 Gy à 10^8 Gy, où le débit de dose est de l'ordre de 2×10^5 Gy/h.

Dans ce réacteur-piscine de 7 MW, la position "Ebene 1" se trouve à 26 cm du coeur ; la dose en neutrons intégrée par les échantillons est inférieure à 5 % de la dose totale. Le milieu d'irradiation est l'air, et la température maximale est de 60°C.

Les échantillons plus sensibles ont été irradiés par une source de ^{60}Co , à la société Ionisos à

with doses of 2×10^5 Gy, 5×10^5 Gy, and 10^6 Gy, at a dose rate of about 4000 Gy/h. In a cobalt source, the radiation comes from pure gamma rays of 1.17 and 1.25 MeV.

Some samples were irradiated in the CERN accelerators, either close to the magnet coils which are insulated with the material concerned (we call this 'live irradiation'), or around converting targets. Under these conditions, the neutron dose may be of the order of several tens of per cents of the total dose.

More details about irradiation conditions and dosimetry in the ASTRA reactor are given in Ref. [37] and for other sources in Ref. [38]. (Note that 1 Gy = 1 gray = 1 J/kg = 100 rad.)

5. PRESENTATION OF THE DATA

The lists of the materials that are presented in this catalogue and in the preceding volumes are given in Appendix 1.

Appendix 2 gives the chemical structures of some commercial products.

Appendix 3 is the alphabetical compilation of data where the materials are sorted according to their chemical name. Under each letter, the following information can be found:

- A generic page with the chemical names of the materials, as well as their usual and commercial names (with as many cross-references as possible). If specific results are not given in this volume, an indication of the radiation resistance is given by the value of the radiation index.
- On the verso of this generic page, the list of the materials classified under the given letter, together with their CERN identification number.
- In the individual pages of results, a header gives the TIS reference number, the description of the material and the name of the supplier (Appendix 5). If available, an indication of the fire behaviour is also given. The results are presented in the form of a table and graph. The mean values (and the standard deviation) of the mechanical properties, flexural strength (S), deformation at break (ϵ) and flexural modulus (M) appear in the table

Dagneux, France, à des doses de 2×10^5 Gy, 5×10^5 Gy et 10^6 Gy, à un débit de dose de l'ordre de 4000 Gy/h. Dans une source cobalt, l'irradiation est purement électromagnétique, avec des gammas de 1,17 et 1,25 MeV.

Certains échantillons ont été irradiés dans des accélérateurs du CERN, soit près des bobines d'aimants dont les bobines sont isolées avec le matériau concerné (test avec irradiation à long terme). Dans ces conditions, la dose-neutron peut atteindre plusieurs dizaines de pourcents de la dose totale.

Plus de détails sur les conditions d'irradiation et de dosimétrie peuvent être trouvés dans les références [37] pour le réacteur ASTRA et [38] pour les autres sources. (Pour mémoire : 1 Gy = 1 gray = 1 J/kg = 100 rad.)

5. PRÉSENTATION DES RÉSULTATS

Les listes des matériaux pour lesquels nous donnons des résultats ainsi que ceux présentés dans les volumes précédents constituent l'appendice 1.

L'appendice 2 donne les structures chimiques de quelques composés commerciaux.

L'appendice 3 est la compilation alphabétique des résultats où les matériaux sont classés suivant leurs noms chimiques en Anglais. Sous chaque lettre on peut trouver les informations suivantes :

- La page générique avec les noms chimiques des matériaux, mais aussi leurs noms usuels ou commerciaux (nous avons fait autant de recoupements que possible). Si des résultats spécifiques ne sont pas présentés dans ce volume, une indication de la radiorésistance est donnée par l'indice de rayonnement.
- Au verso de cette page générique, la liste avec les numéros d'identification CERN des matériaux classés sous cette lettre.
- Viennent ensuite les pages individuelles de résultats, sur lesquelles on trouve en entête le numéro d'identification TIS, la description du matériaux et le nom du fournisseur (Annexe 5), ainsi qu'une éventuelle indication sur son comportement au feu. Les résultats sont présentés sous forme de tableau et de graphique. Dans le tableau apparaissent les doses absorbées avec les débits de dose correspondants, puis les valeurs moyennes (et l'écart type) des propriétés mécaniques, la

together with the absorbed doses and the corresponding dose rates. (The formulae for the calculation of these properties are given in Appendix 4. In some cases, the samples are too flexible to break during the test, the values given are then the maximum flexural strength and the maximum possible deformation in the cage.) Below the table are given the critical property for the calculation of the radiation index (RI) and its value for the corresponding dose rate. The graph presents the evolution of the flexural strength and of the deformation with respect to the absorbed dose.

Appendix 4 gives the main abbreviations used in the tables of results.

Appendix 5 is a list of the suppliers of the materials and/or components who contributed to this catalogue.

6. CLASSIFICATION OF MATERIALS

Tables 2a and 2b are a classification of the material in decreasing order of their radiation resistance. We have separated the thermoplastics from the thermosets because their conditions of use are usually different, though high-performance thermoplastics have properties as good as the ones of thermosets today.

This classification gives an order of magnitude of the maximum dose of usability of the materials; it corresponds to long-term irradiations. In particular, thermoplastics (Table 2a) may be very sensitive to oxidation and hence to dose-rate effect; during long-term irradiation in the presence of oxygen, their degradation starts at much lower doses [17–23]. An indication of this appears as a longer ‘mild to moderate’ zone on the bar graph.

All of these materials may be reinforced with fibres, long or short, oriented (1D, 2D, 3D) or not, woven or not, etc. The fibres usually increase the radiation resistance of the materials. The properties of some composites reinforced with glass fibres or carbon fibres may be kept up to doses above 100 MGy. A laminate will undergo degradation following delamination, showing the higher sensitivity of the matrix.

résistance en flexion (S), la déformation à la rupture (ϵ) et le module de flexion (M) (Les formules de calcul de ces grandeurs sont données en appendice 4. Dans certains cas, les échantillons sont trop flexibles pour subir une rupture, la valeur maximale de la déformation atteinte dans la cage est alors donnée, ainsi que la valeur maximale mesurée pour la résistance.) Sous le tableau sont données la propriétés de référence pour le calcul de l’indice de rayonnement (RI) et la valeur de celui-ci au débit de dose correspondant. Le graphique présente l’évolution de la résistance et de la déformation en fonction de la dose absorbée.

L’appendice 4 explique les principales abréviations utilisées dans les tableau de résultats.

L’appendice 5 est une liste des fournisseurs des matériaux de base et/ou de composants qui ont collaboré à ce catalogue.

6. CLASSIFICATION DES MATÉRIAUX

Les tableaux 2a et 2b sont un classement des matériaux par ordre décroissant de leur résistance aux radiations. Nous avons séparé les thermoplastiques des thermosets, car ils ont en général des conditions d’utilisation différentes, bien que les thermoplastiques à hautes performances aient aujourd’hui des propriétés comparables à celles des thermosets.

Ce classement donne un ordre de grandeur de la dose limite d’utilisation d’un matériau, il correspond à des irradiations accélérées. En particulier, les thermoplastiques (Tableau 2a) peuvent être très sensible à l’oxydation et donc à l’effet du débit de dose ; en irradiation à long terme en présence d’oxygène, leur dégradation intervient pour des doses nettement plus faibles [17–23]. Une indication de ceci apparaît comme une zone de “dégradation modérée” plus longue sur le graphique.

Tous ces matériaux peuvent être renforcés par des fibres, courtes ou longues, orientées (1D, 2D ou 3D) ou non, tissées ou non, etc. Les fibres ont en général un effet bénéfique sur la résistance aux radiation d’un matériaux. Les propriétés de certains composites renforcés aux fibres de verre ou de carbone peuvent être conservées à des doses de plus de 100 MGy. Un composite laminé subira une dégradation par délamination, mettant ainsi en évidence la plus grande sensibilité de la matrice.

Acknowledgements

This data compilation was carried out within the framework of an IAEA Research Coordination Programme on Radiation Degradation of Polymers (Contract No. 4319, 1985 to 1989).

Our particular thanks are due to K. Goebel, K. Potter and B. de Raad at CERN who throughout the years have supported radiation-damage studies.

Most of the materials tested were used or proposed for the SPS and LEP, as well as for the LHC project at CERN. We thank the European manufacturers who supplied the test samples, both for their interest in the subject and for the useful discussions that we had with many of them.

The irradiations were carried out in the ASTRA reactor of the Forschungszentrum Seibersdorf in Austria, where the collaboration of A. Burtscher and J. Casta was greatly appreciated. We would also like to thank Mrs M-A. Mirvault and Mrs M.-O. Bachelier from Ionisos in Dagneux, France.

Finally, we would like to thank the CERN Desktop Publishing Service for their help in preparing this report.

Remerciements

Cette compilation de résultats s'inscrit dans le cadre d'un programme de recherche sur la dégradation des polymères par irradiation, coordonné avec l'AIEA (contrat No. 4329, 1985 à 1989).

Nous remercions particulièrement K. Goebel, K. Potter and B. de Raad, du CERN, qui, au long des années ont soutenu les études de dégradation des matériaux due aux rayonnements.

La plus grande partie des matériaux testés ont été utilisés ou proposés pour le SPS et pour le LEP, ainsi que pour le projet LHC du CERN. Nous remercions les fabricants européens qui ont fourni des échantillons d'essais ; nous avons eu des discussions utiles avec les représentants de nombreuses firmes.

Les irradiations ont été effectuées au réacteur ASTRA du Forschungszentrum Seibersdorf en Autriche, où nous avons apprécié la collaboration que nous ont offerte J. Casta et F. Böheim, et à Ionisos, à Dagneux, France où nous remercions Mmes M.A. Mirvault et M.-O. Bachelier.

Nous voudrions enfin exprimer notre appréciation de l'aide et l'attention du Service de publication assistée par ordinateur du CERN.

References

- [1] M.H. Van de Voorde, The effect of nuclear radiation on the electrical properties of epoxy resins, CERN 68-13 (1968).
- [2] M.H. Van de Voorde, Effects of radiation on materials and components, CERN 70-5 (1970).
- [3] M.H. Van de Voorde, Action des radiations sur les résines époxydes, CERN 70-10 (1970).
- [4] M.H. Van de Voorde and C. Restat, Selection guide to organic materials for nuclear engineering, CERN 72-7 (1972).
- [5] H. Schönbacher, Anwendung von Kabel und Magnet-isolationen im nucklearen Strahlungsfeld von über 1 Megagray, Bull. Assoc. Suisse Electr. **69** (1977) 72.
- [6] D.C. Phillips, The effects of radiation on electrical insulators in fusion reactors, AERE-R8923 (UK Atomic Energy Authority, Harwell, 1978).
- [7] D.C. Phillips et al., The selection and properties of epoxide resins used for the insulation of magnet systems in radiation enviroments, CERN 81-05 (1981).
- [8] R.I. Keiser and M. Mottier, Radiation resistant magnets, CERN 82-05 (1982).
- [9] R.L. Clough et al., Accelerated aging tests for predicting radiation degradation of organic materials, Nucl. Saf. **25** No. 2 (1984) 238.
- [10] G. Lipták et al., Radiation tests on selected electrical insulating materials for high-power and high-voltage application, CERN 85-02 (1985).
- [11] H. Schönbacher et al., Strahlenbeständigkeit von Epoxidhormasse, Kunstst.-Berat. **76** (1986) 14.
- [12] P. Beynel, H. Schönbacher, G. Tartaglia, Results of long-term irradiation of epoxy resins used for magnet-coil insulation, CERN-TIS-RP/IR/86-37.
- [13] H. Schönbacher, Life experience with aging of organic electrical insulating materials in nuclear radiation environment, Proc. ANS/ENS Int. Topical Meeting on Operability of Nuclear Power Systems in Adverse Environments, LaGrange Park, 1987, p. 516.
- [14] R.L. Clough, Radiation resistant polymers, in Encyclopedia of Polymer Science and Engineering (John Wiley & Sons, New York, 1988).
- [15] Proc. Research Coordination Meeting on Radiation Damage to Organic Materials in Nuclear Reactor and Radiation Environment, Takaseki, 1989 (IAEA Tech. Rep. Ser., Vienna, 1990).
- [16] Radiation damage to organic materials in nuclear reactors and radiation environments, IAEA-TECDOC-551 (1990).
- [17] M. Tavlet and H. Schönbacher, Radiation resistance of insulators and structural materials, Proc. ECFA Large Hadron Collider Workshop, Aachen, 1990, Eds. G. Jarlskog and D. Rein, CERN 90-10, Vol. 3 (1990) p. 743-8.
- [18] D.W. Clegg and A.A. Collyer, Irradiation effects on polymers (Elsevier Appl. Sci., London and New York, 1991).
- [19] R.L. Clough and S.W. Shalaby, Radiation effects on polymers (ACS Symposium Series 475, 1991).
- [20] R.L. Clough and S.W. Shalaby, Irradiation of polymers (ACS Symposium Series No. 620, 1996).
- [21] Proc. Int. Workshop on Advanced Materials for High Precision Detectors, Archamps, 1994, Eds. B. Niquevert and C. Hauviller, CERN 94-07, Part IV (1994).
- [22] H. Mitsui et al., Synchrotron radiation damage test on insulating materials in the Tristan MR, Part. Accel. **52** (1996) 31-44.

- [23] M. Tavlet, Aging of organic materials around high-energy particle accelerators, *Nucl. Instrum. Methods Phys. Res. B* **131** (1997) 239–244.
- [24] H. Schönbacher and A. Stolarz-Izicka, Compilation of radiation damage test data, Part I: Cable-insulating materials, CERN 79–04 (1979).
- [25] H. Schönbacher and A. Stolarz-Izicka, Compilation of radiation damage test data, Part II: Thermosetting and thermoplastic resins, CERN 79–08 (1979).
- [26] P. Beynel, P. Maier and H. Schönbacher, Compilation of radiation damage test data, Part III: Materials used around high-energy accelerators, CERN 82–10 (1982).
- [27] H. Schönbacher and M. Tavlet, Compilation of radiation damage test data, Part I, 2nd edition: Halogen-free cable-insulating materials, CERN 89–12 (1989).
- [28] CERN Safety Instructions IS23 and IS41, TIS Commission 1993 and 1995.
- [29] International Electrotechnical Commission, Geneva, Publication No. 544: Guide for determining the effects of ionizing radiation on insulating materials, Part I: Radiation interaction, Ref. 544–1 (1977); Part 2: Procedures for irradiation, Ref. 544–2 (1979); Part 3: Test procedures for permanent effects, Ref. 544–3 (1979); Part 4: Classification system for service in radiation environments, Ref. 544–4 (1985).
- [30] M. Van de Voorde, Low temperature irradiation effects on materials and components for superconducting magnets for high-energy physics applications, CERN 77–03 (1977).
- [31] D. Evans and J.T. Morgan, A review of the effects of ionizing radiation on plastics materials at low temperature, *Adv. Cryog. Eng.* **28** (1982) 147–164.
- [32] A. Spindel, Report on the program of 4 K irradiation of insulating materials for the SSC, SSCL–635 (1993).
- [33] K. Humer et al., Tensile strength of fiber reinforced plastics at 77 K irradiated by various radiation sources, *J. Nucl. Mater.* **212–215** (1994) 849–853.
- [34] S. Egusa, Irradiation effects on the mechanical properties of polymer matrix composites at low temperature, *Adv. Cryog. Eng.* **36** (1990) 861–868.
- [35] H. Schönbacher et al., Results of radiation tests at cryogenic temperatures on some selected organic materials for the LHC, CERN 96–05 (1996).
- [36] M. Tavlet and A.-S. Boullin, End-of-Life criteria for rigid plastics undergoing radiation degradation, CERN–TIS–CFM/IR/95–05, presented at the Working Group of IEC Subcommittee 15 B, Milan, June 1995.
- [37] H. Schönbacher et al., Study on radiation damage to high-energy accelerator components by irradiation in a nuclear reactor, *Kerntechnik* **17** (1975) 268.
- [38] E. Leon Florian, H. Schönbacher and M. Tavlet, Data compilation of dosimetry methods and radiation sources for material testing, CERN/TIS–CFM/IR/93–03 (1993).

Table 1
Characteristic properties of thermoset and thermoplastic materials

Polymers Properties		EPOXY RESINS						PEEK	
		BISPHENOL A			EPOXY NOVOLAC				
		No filler	Glass	Mineral	No filler	Glass	Mineral	Unfilled	30% G.F.
Specific gravity (g/cm ³)	ISO 1183	1.15	2.0–2.1	1.8–2.0	1.2	1.97	1.7	1.32	1.48
Water absorption (%)	ISO 62	0.1–0.2	0.02–0.8	0.30–0.80	–	0.04–0.06	0.11–0.20	0.06–0.2	0.14
Thermal conductivity (k cal/m.h. °C)	ASTM D325	0.15–0.45	1	–	–	–	–	–	–
Thermal coefficient of expansion (10 ^{–5} /°C)	ASTM D 696	6	0.6	–	3	–	–	5	2.5
Tensile strength (MPa)	ISO R37	70–80	350–400	70	70	350–400	38	95	170
Elongation (%)	ISO R37	4.4	–	–	2–5	–	–	>25	2
Tensile modulus (GPa)	ISO R37	3.5	30	10–15	3.5	21–22	–	3.6	9.7
Flexural strength (MPa)	ISO 178	80–130	360	150–170	60–100	390	70–80	180	–
Impact strength (notched) (kg cm/cm)	ASTM D 256	1.1–2.7	6.4–8.2	2.2–2.7	2.7	7.0–9.2	2.2–2.7	–	–
Volume resistivity (Ω cm)	IEC 93	6.1 × 10 ¹⁵	–	1.5 × 10 ¹⁵	2.1–10 ¹⁴	–	1.4–5.5 × 10 ¹⁴	10 ¹⁶	–
Dielectric strength (kV/mm)	IEC 243	> 16	18–22	15–16	–	–	12–16	30	–
Power factor (tg) at 10 ⁶ Hz	IEC 250	0.032	0.024	0.013	0.029	0.015	–	0.003	–
Dielectric constant at 10 ⁶ Hz	IEC 250	3.4	4.7–4.8	4.1–4.6	3.5	5.1	4.3–4.8	3.3	–
Heat distortion temperature (°C)	ISO 75	110	–	–	150–200	–	–	340	340

Table 1 (cont.)


Polymers		PHENOLICS						POLYIMIDES	
Properties		No filler	Wood flour	Asbestos	Fibre and fabric	Mineral	Nylon	Unfilled	Glass
Specific gravity (g/cm ³)	ISO 1183	1.30–1.32	1.29–1.51	1.78–2.00	1.3–1.4	1.5–1.9	1.2–1.5	1.47	1.90
Water absorption (%)	ISO 62	0.30–0.40	0.70–1.20	0.03–0.30	0.50–1.6	0.04–0.25	0.25–0.4	0.68	0.20
Thermal conductivity (k cal/m.h. °C)	ASTM D325	–	0.15–0.45	0.15–0.25	0.3	0.3	–	0.60	–
Thermal coefficient of expansion (10 ⁻⁵ /°C)	ASTM D 696	4.3	3.6	–	3	1.8	–	5.4	1.5
Tensile strength (MPa)	ISO R37	14–63	38–63	21–49	31–63	14–59	31–63	74	210
Elongation (%)	ISO R37	~ 5	~ 5	~ 5	~ 5	4–9	–	< 1.5	< 1
Tensile modulus (GPa)	ISO R37	1.4–3.1	4.9–14.0	11–20.0	5.6–10.0	9.5–21.0	2.8–14.0	3.2	28–30
Flexural strength (MPa)	ISO 178	84–100	60	45–77	49–110	56–84	42–91	100	350
Impact strength (notched) (kg cm/cm)	ASTM D 256	2.7–4.3	1–2.8	0.8–16	2–36	0.97–3.9	1.4–2.8	5	17
Volume resistivity (Ω cm)	IEC 93	2.5×10^{10} – 10^{12}	10^9 – 10^{13}	10^8 – 10^{13}	10^8 – 10^{12}	10^{10} – 10^{14}	10^{11} – 10^{14}	10^{16} – 10^{17}	9.2×10^{15}
Dielectric strength (kV/mm)	IEC 243	10–16	0.6–10	0.4–10	0.4–7	3–16	1–11	22	–
Power factor (tg) at 10 ⁶ Hz	IEC 250	0.04–0.05	0.015–0.06	0.03–0.25	0.03–0.08	0.007–0.08	0.15–0.2	0.005	0.0055
Dielectric constant at 10 ⁶ Hz	IEC 250	4–9.7 (10 ³ c/s)	3.9–6.5	5–6	4.8–7	4–6	3.7–4.5	3.4	4.7
Heat distortion temperature (°C)	ISO 75	150–180	130–180	–	250	180–200	–	300	350

Table 1 (cont.)

Polymers		POLYESTERS				POLYURETHANES	SILICONES	
Properties		α Cellulose	Mineral	Glass	No filler		Glass	Mineral
Specific gravity (g/cm ³)	ISO 1183	1.35–1.40	1.70–2.20	1.20–2.00	1.20–1.40	1.21	1.88	1.88–2.8
Water absorption (%)	ISO 62	0.01–1	–	0.1–2	0.03–0.4	0.30–0.90	0.10–0.30	0.05–0.22
Thermal conductivity (k cal/m.h. °C)	ASTM D325	–	–	1.8–2.2	0.15	–	0.27	0.50
Thermal coefficient of expansion (10 ⁻⁵ /°C)	ASTM D 696	–	–	2	7	–	6	5
Tensile strength (MPa)	ISO R37	42–50	21–46	42–90	35–81	45–60	28–56	17–31
Elongation (%)	ISO R37	–	–	0.3–0.5	1.7–2.6	>	< 3	< 3
Tensile modulus (GPa)	ISO R37	–	9.8–19.0	4.2–12.0	2.8–4.6	3.3–8.4	14.7–17.5	8.7–15.9
Flexural strength (MPa)	ISO 178	70–84	17–63	84–150	45–91	–	91 133	49 70
Impact strength (notched) (kg cm/cm)	ASTM D 256	1.6–2.5	1–4	40–54	1.6–10	> 5.4	50	2
Volume resistivity (Ω cm)	IEC 93	> 10 ¹⁴	> 10 ¹⁴	10 ¹² –10 ¹⁵	2.7×10^{14} 2×10^{15}	6×10^{12} –10 ¹⁴	3×10^{14}	10 ¹⁴
Dielectric strength (kV/mm)	IEC 243	10–14	10–17	6–14	10–17	20	10–11	11–16
Power factor (tg) at 10 ⁶ Hz	IEC 250	0.03–0.05	0.013–0.04	1.1–0.04	0.01–0.03	0.03–0.05	0.003–0.02	0.002–0.01
Dielectric constant at 10 ⁶ Hz	IEC 250	3.5–5.5	4.5–6.0	4.5–6.0	3.0–4.01	3.3–3.9	4.35	3.4–4.5
Heat distortion temperature (°C)	ISO 75	–	–	200	50–200	–	> 450	270–450

Table 2a

General classification of rigid thermoplastics with respect to their radiation resistance

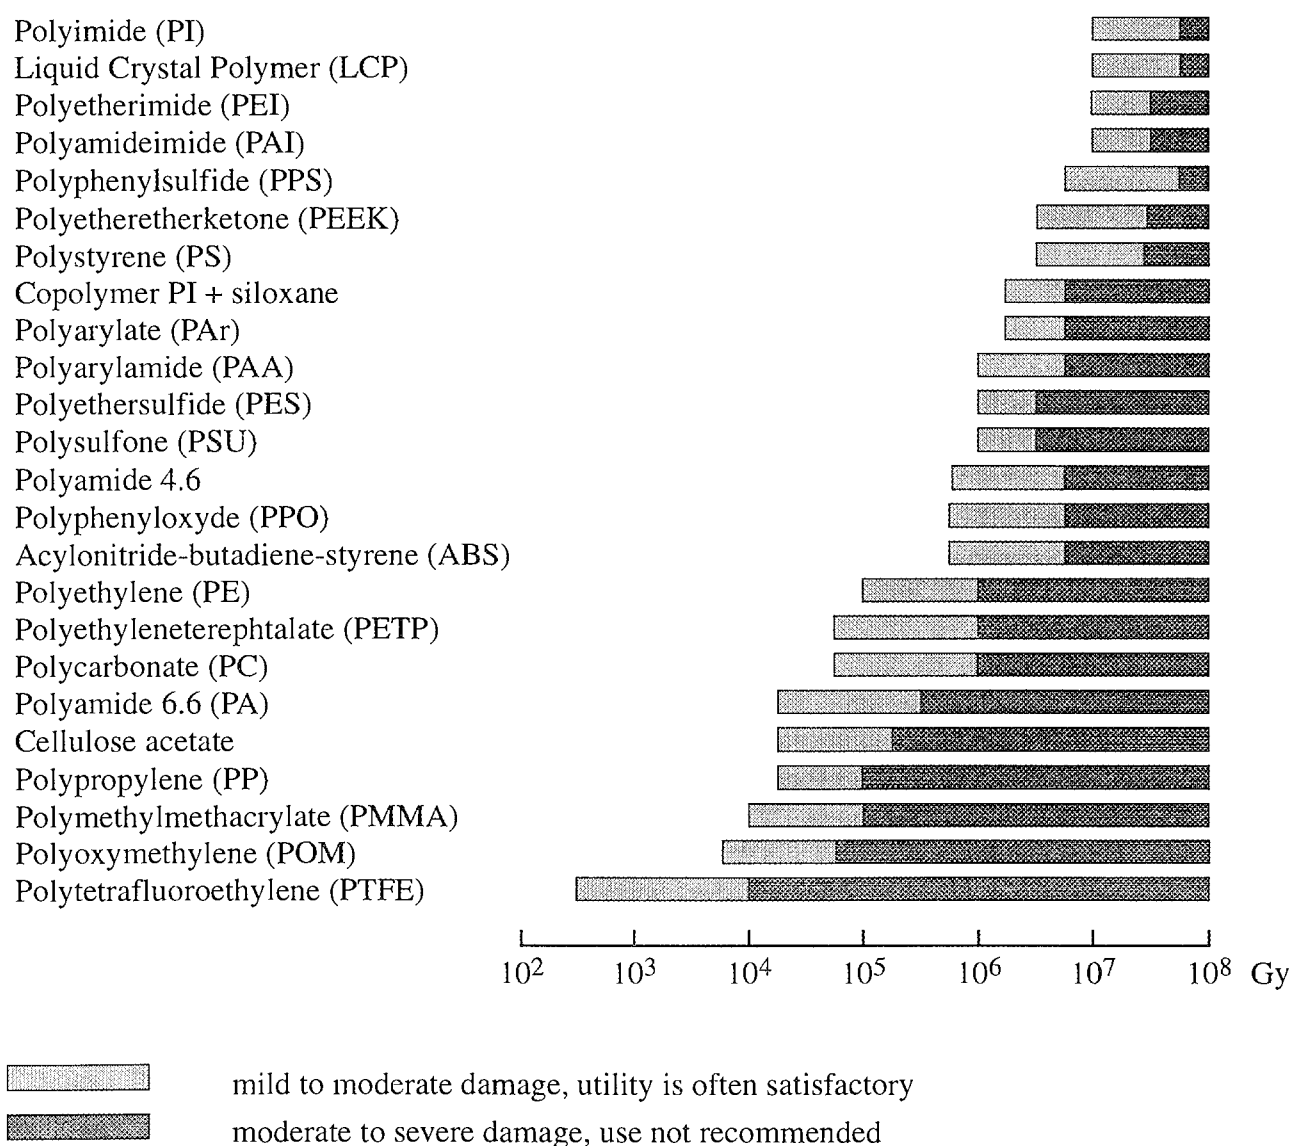


These appreciations can only serve as a general guideline; environmental conditions such as temperature, humidity and dose rate, as well as additives influence the radiation behaviour of materials.

Fibre reinforced composites based on these resins can be at least one order of magnitude better.

Table 2b

General classification of thermoset resins and composites with respect to their radiation resistance

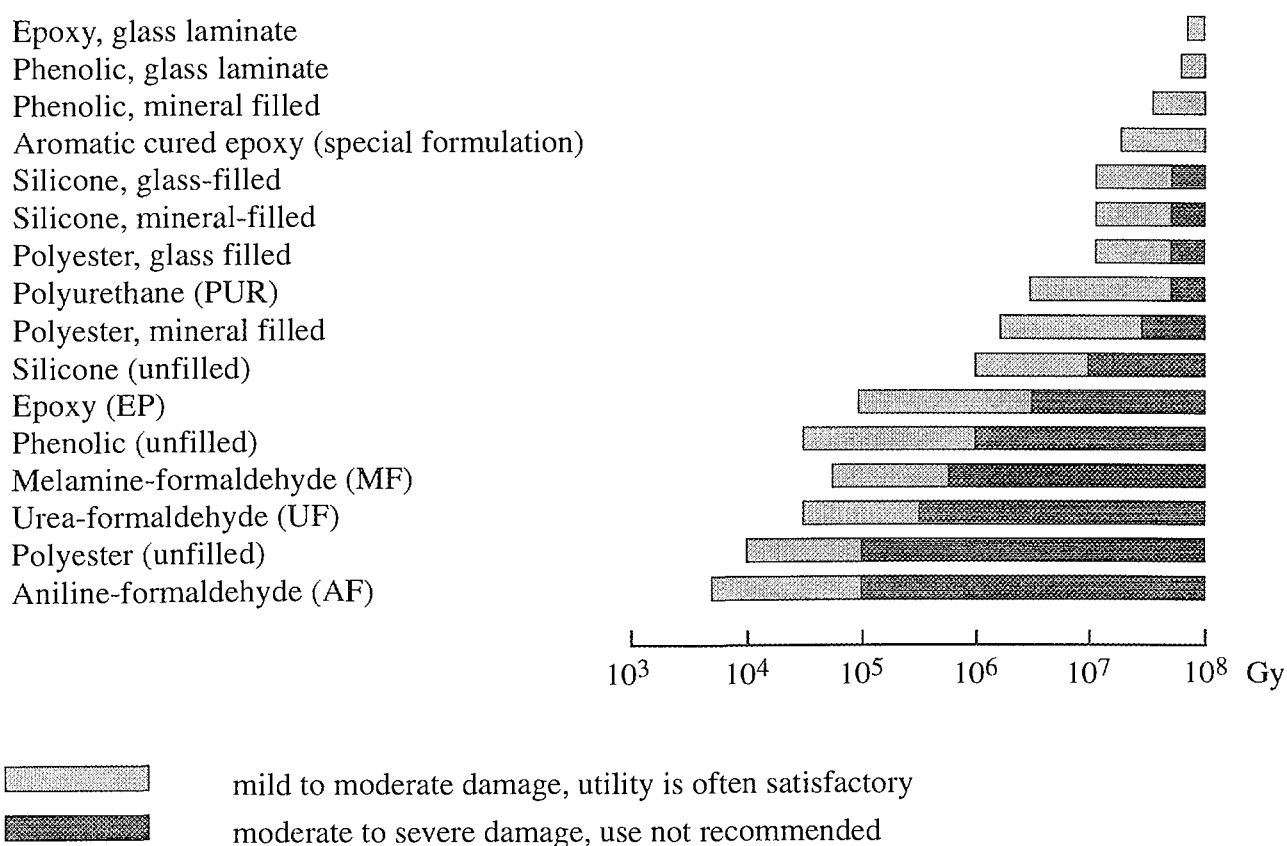

These appreciations can only serve as a general guideline; environmental conditions such as temperature, humidity and dose rate, as well as additives influence the radiation behaviour of materials.

Fibre reinforced composites based on these resins can be at least one order of magnitude better (see Appendix 3).

APPENDIX 1

List of materials presented in the previous volumes (Trade names in italics)

Volume I: Cable insulating materials (Ref. [24])

Butyl rubber	<i>Neoprene</i>
<i>Chlorostop</i>	<i>Nordel</i>
Chlorosulfonated polyethylene (CSP)	Polychloroprene
Cross-linked polyethylene (XLPE)	Polyethylene (PE)
<i>Desmopan</i>	Polyurethane (PUR)
Ethyl-acrylate rubber (EAR)	Polyvinyl chloride (PVC)
Ethylene-propylene diene rubber (EPDM)	<i>Pyrofil</i>
Ethylene-propylene rubber (EPR)	<i>Radox</i>
Ethylene vinyl acetate (EVA)	Semiconducting polyethylene
<i>Flamtrol</i>	Silicone rubber
Fluoropolymer	<i>Silythene</i>
<i>Halar</i>	<i>Stilan</i>
<i>Hypalon</i>	<i>Teflon</i>
<i>Hytrel</i>	<i>Tefzel</i>
<i>Kapton</i>	<i>Viton</i>
<i>Lupolen</i>	XLPE

Volume I, 2nd edition: Halogen-free cable-insulating materials (Ref. [27])

<i>Acorad</i>	Polyurethane (PUR)
<i>Afumex</i>	<i>Radox</i>
<i>Cogegum</i>	<i>Rheychalon</i>
<i>Elastollan</i>	Semiconducting PE
Ethyl acrylate rubber (EAR)	<i>Silanpex</i>
Ethylene ethyl acrylate (EEA)	Silicone rubber (SiR)
Ethylene-propylene diene monomer rubber (EPDM)	<i>Silythene</i>
Ethylene-propylene rubber (EPR)	<i>Sioplas</i>
Ethylene-vinyl acetate copolymer (EVA)	Thermoplastic rubber (TPR)
<i>Lupolen</i>	<i>Toxfree</i>
<i>Megolon</i>	VAC
Polyethylene (PE)	<i>Vamac</i>
Polyolefin (PO)	XLPE

Volume II: Thermoplastic and thermosetting resins (Ref. [25])

Araldite B
Araldite D
Araldite F and other *Araldite* resins
Araldite F + epoxy *Novolac*
Birakrit
Cevolit
Crystic
Dobeckan IF
Dobeckot
Epikote
Epoxy resins
Epoxy resins + epoxy *Novolac*
Etronax
Isoval
Kerimid
Kinel

Makrolon
Novolac
Orlitherm
Phenolic resins
Polycarbonate resins
Polyimide resins
Polylite
Polyurethane resins
Resofil
Ryton
Samicanit
Samicatherm
Silicone resins
Veridur
Vetresit
Vetronite

Volume III: Accelerator engineering materials and components (Ref. [26])

Adhesive tape
Aluminium oxide
Araldite
Asbestos cement
Askarel
Buna
Cable insulation
Cable tie
Ceramic
Cerium-doped glass
Connector
Copper wire
Diala C
Diester oil
Electronic components
Epoxy resin
Ethylene-propylene rubber (EPR) and (EPDM)
Ethylene-tetrafluoroethylene copolymer (ETFE)
Fluorinated oil
Fluorinated polymer
Foam
Glass
Glass fibre
Heating element
HF absorber
Hoses
Hostalen

Hypermalloy
Hytrel
Insulated wire
Insulating oil
Insulating sleeve
Insulating tape
Iron
Joint
Kapton
Kevlar
Kynar
Lighting
Lithium polysilicate
Lubricating oil
Luminous paint
Lupolen
Magnet coil insulation
Magnetic material
Makrolon
Micatherm
Microswitch
Mineral oil
Motor, electric
Mylar
Neoprene
Nitrile-butadiene rubber
Nomex

Noryl
Novolac
Nylon
 Oil
 Optical fibre
 O-ring
 Pain
 Paper
 Particle detector
Pertinax
Plexiglas
 Polyacrylate
 Polyamide
 Polybutylene terephthalate (PBTP)
 Polycarbonate
 Polychloroprene (*Neoprene*)
 Polyester resin
 Polyethylene (PE) and (XLPE)
 Polyethylene terephthalate (PETP)
 Polyhydantoin
 Polyimide
 Polyolefin
 Polyphenylene oxide (PPO)
 Polyphenylene sulfide (PPS)
 Polypropylene (PP)
 Polysiloxane
 Polytetrafluoroethylene (*Teflon* PTFE)
 Polyurethane resin (PUR)
 Polyvinyl chloride (PVC)
 Polyvinyl toluene
 Quartz
 Relay
 Resin
Resistofol
 Rubber
Ryton
 Scintillator
Scotchcal
 Seal (O-ring)
 Silica
 Silicon detector
 Silicone oil
 Silicone rubber
 Sleeve
 Styrene-butadiene rubber (SBR)
 Switch


Tape
Teflon (PTFE)
Tefzel
 Terminal board
 Textile
 Thermoplastic resin
 Thermosetting resin
 Thermoshrinking sheath
 Vacuum chamber tube
 Vacuum gasket
 Vacuum pump accessory
 Vacuum seal
 Vacuum valve
Valvata
 Valve
Vestolene
Viton
 Wire
 Wood

APPENDIX 2

Chemical structures of some commercial products

BF₃MEA Boron trifluoride monoethylamine: BF₃-NH₂-CH₂-CH₃

CT 200 (CIBA-GEIGY), Araldite B, solid, unmodified epoxy resin based on Bisphenol A:

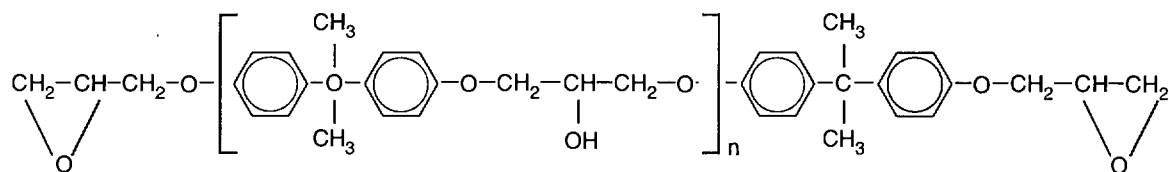

CY 205 (CIBA – GEIGY) Liquid, unmodified epoxy resin based on Bisphenol A


CY 208 (CIBA – GEIGY) Liquid, modified epoxy resin based on Bisphenol A

CY 221 (CIBA – GEIGY) Liquid, modified epoxy resin based on Bisphenol A


CY 222 (CIBA – GEIGY) Liquid, modified epoxy resin based on Bisphenol A

Chemical formula
see CT200 (n ≈ 0.15)

DDM (CIBA-GEIGY) Hardener – 4,4' – Diaminodiphenylmethane (methylenedianiline MDA):




DDS Hardener – Diaminodiphenyl sulphone:

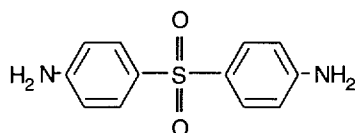


DEN (DOW) Dow Epoxy Novolac


431 } Polyglycidyl ether of phenol formaldehyde novolac
438 }

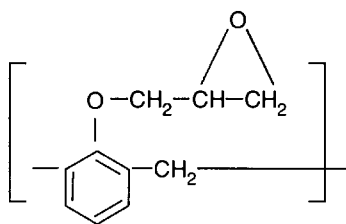

DGEBA Diglycidyl ether of Bisphenol A:

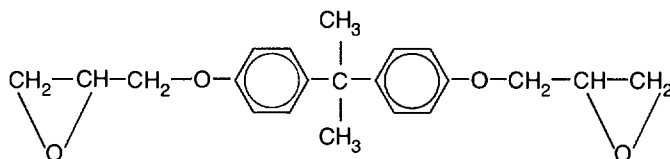

DMP 30 Accelerator – 2, 4, 6–tris[N,N–(dimethylamino)methyl]phenol

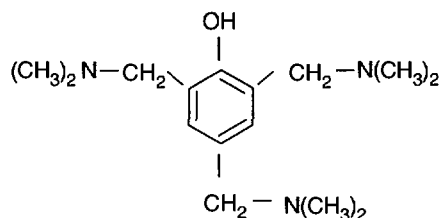


DX 126 (SHELL) }
DX 127 (SHELL) } Curing agent – anhydride

DX 125 (SHELL)

DY 040 (CIBA–GEIGY) flexibilizer – polypropyleneglycol

061 accelerator – aminophenol

062 accelerator – benzyldimethylamine

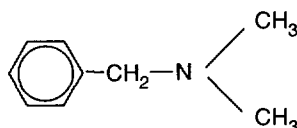

063 accelerator

064 accelerator – aminophenol

065 accelerator unmodified sodium alkoxide

067 accelerator modified " "

EP (SHELL)

EPIKOTE

154 } Polyglycidyl ether of phenol formaldehyde novolac
827 } (Chemical formulae see DEN)

828 Diglycidyl ether of Bisphenol A (see DGEBA)


EPN (CIBA–GEIGY)

Epoxy Phenol Novolac

1138 } Polyglycidyl ether of phenol formaldehyde novolac
1139 } (Chemical formulae see DEN)


HT 903 (CIBA–GEIGY) Acid anhydride hardener, solid, modified

Tetrahydrophthalic anhydride

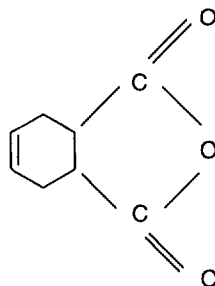

HT 907 (CIBA-GEIGY) Acid anhydride hardener, solid, unmodified

Hexahydrophthalic anhydride

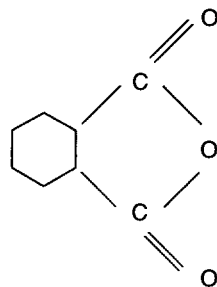


HT 972 (CIBA-GEIGY) Amine hardener, solid, unmodified (see DDM)

HY 905 (CIBA-GEIGY) Acid anhydride hardener, liquid, modified
Hexahydrophthalic anhydride (see HT 907)

HY 906 (CIBA-GEIGY) Acid anhydride hardener, liquid, unmodified


Methyl nadic anhydride (MNA)

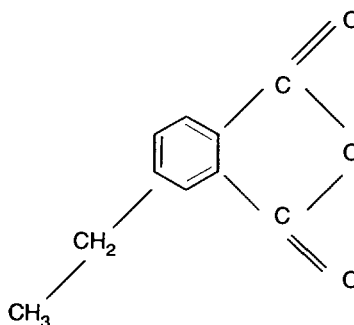

HY 956 (CIBA-GEIGY) Amine hardener, liquid, modified
Triethylenetetramine $\text{H}_2\text{N} [\text{CH}_2 - \text{CH}_2 - \text{NH}] \text{CH}_2 - \text{CH}_2 - \text{NH}_2$


HY 964 (CIBA-GEIGY) Acid anhydride hardener

Dodecenyl succinic anhydride

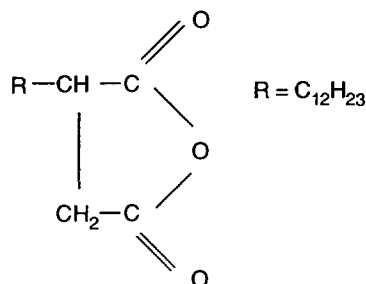


MDA	Hardener Methylenedianiline (see DDM)
MNA	Hardener Methyl nadic anhydride (formula see HY 906)
MY 720 (CIBA-GEIGY)	Liquid, unmodified, epoxy resin Tetrafunctional glycidyl compound of diamines (TGDM)
MY 740 (CIBA-GEIGY)	Liquid, modified epoxy resin based on Bisphenol A (see CY 205)
MY 745 (CIBA-GEIGY)	Liquid, modified epoxy resin based on Bisphenol A (see CY 208, 221 and 222)


PA 4.6

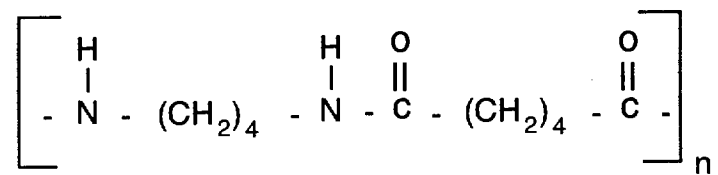


PEEK

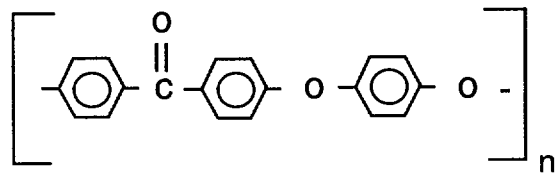


PEI

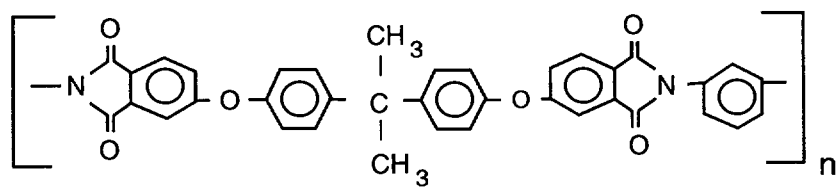


PES

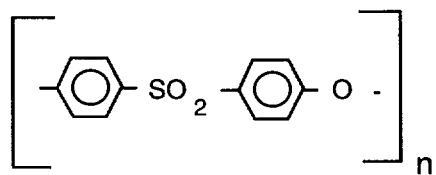


PI

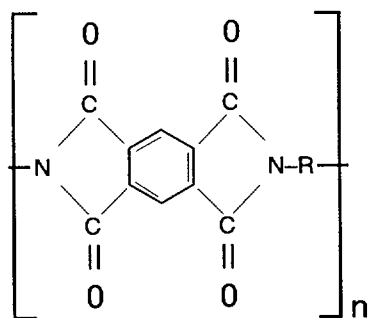

PPS

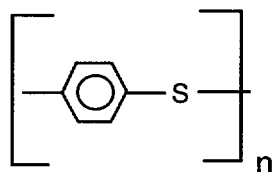


PSU

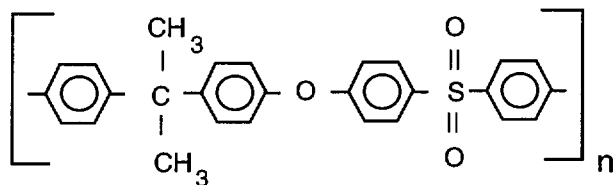

TGDM

N,N'-tetraepoxypropyl-4,4'-methylene-dianiline

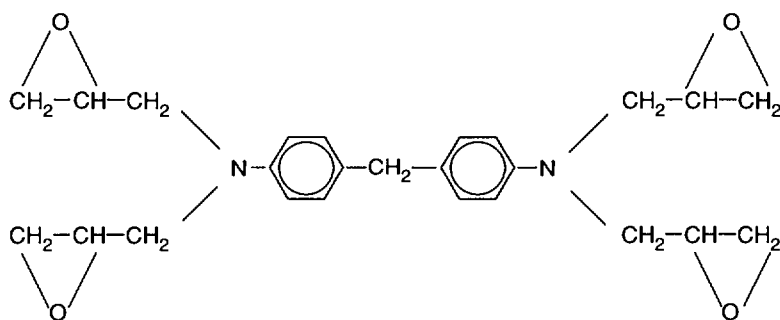

XB 2687 (CIBA-GEIGY) Accelerator, liquid modified, replacement for DY 063
Amine-phenol salt

APPENDIX 3

Alphabetic compilation of data

A

Acetal resin	see polyoximethylene (POM)
Adiprene	trade name for polyurethane, polyester
Araldite	trade name of CIBA-GEIGY for epoxy resins, for behaviour under cryogenic irradiation, see Ref. [35] Araldite B = unmodified epoxy resin based on Bisphenol A; base resin = CT200 Araldite D Araldite F; base resin = CY205 Araldite MY720 = liquid unmodified epoxy resin based on TGDM
Arenka	trade name of ENKA for Epikote reinforced with aramid fibers, see epoxy composite
Arocy	trade name of CIBA-GEIGY for cyanate ester based resins, see cyanate ester

List of materials classified under letter A

TIS number	Material name	Base material	Mechanical properties			
			UTS (MPa)	Deform. (%)	Modulus (MPa)	RI
439	Araldite NU 460	epoxy moulding compound	138	1.04	13.7	< 6.7
441	Araldite NU 461	epoxy moulding compound	117	0.90	18.5	> 8
443	Araldite NU 471	epoxy moulding compound	96.5	0.96	12.8	7.8
447	Araldite NU 481	epoxy moulding compound	87.3	0.98	11.8	7.7
449	Araldite NU 505	epoxy moulding compound	115	0.90	17.6	> 8
453	Araldite NU 511	epoxy moulding compound	158	1.08	17.4	> 8
483	Araldite F	CY 205	89.8	2.61	3.6	7
486	Araldite F	epoxy HY905-DY040-DY061	82.4	2.60	3.30	7.1
492	Araldite NU 514	epoxy moulding compound	115	1.17	12.7	7.9
493	Araldite NU 487	epoxy moulding compound	150	1.19	15.7	7.8
566	Araldite	Av/HV 158GB	60.8	0.53	15.2	6.6

Type **Araldite NU 460**
 Material: **Epoxy moulding compound**

TIS No. **R 439**

Supplier: **Ciba-Geigy**
 Remarks: **standard curing**

UL 94: **n.m.**
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	138 $\pm$ 9	1.04 $\pm$ 0.06	13.7 $\pm$ 6.8
220	5	49 $\pm$ 6	0.67 $\pm$ 0.03	9.9 $\pm$ 1.5
220	10	58 $\pm$ 3	0.73 $\pm$ 0.04	10.6 $\pm$ 0.6
220	50	32 $\pm$ 7	0.61 $\pm$ 0.06	6.3 $\pm$ 1.9

Critical property = flexural strength

Radiation index (RI) = < 6.7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 439

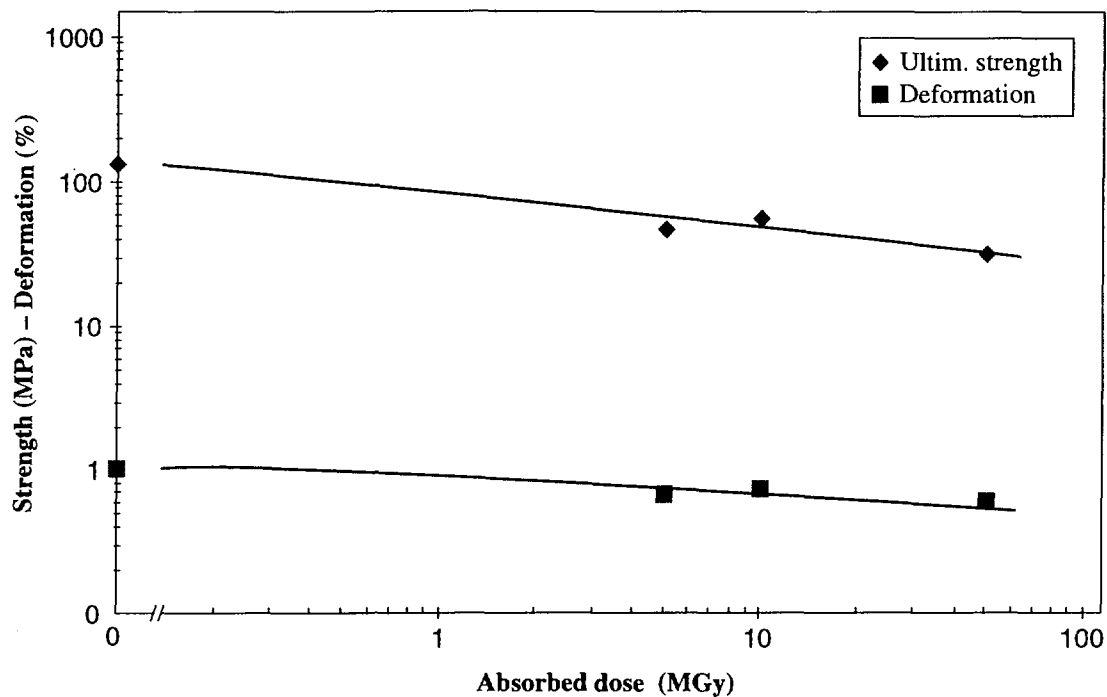

Type: **Araldite NU 461**
 Material: **Epoxy moulding compound**

TIS No. **R 441**

Supplier: **Ciba-Geigy**
 Remarks: **VPI product**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	117 $\pm$ 5	0.90 $\pm$ 0.06	18.5 $\pm$ 0.7
220	5	105 $\pm$ 5	0.76 $\pm$ 0.04	18.3 $\pm$ 0.7
220	10	112 $\pm$ 8	0.77 $\pm$ 0.08	18.4 $\pm$ 0.4
220	50	115 $\pm$ 4	0.64 $\pm$ 0.03	21.4 $\pm$ 0.4
220	100	92 $\pm$ 10	0.50 $\pm$ 0.05	20.1 $\pm$ 1.1

Critical property = deformation

Radiation index (RI) = > 8 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 441

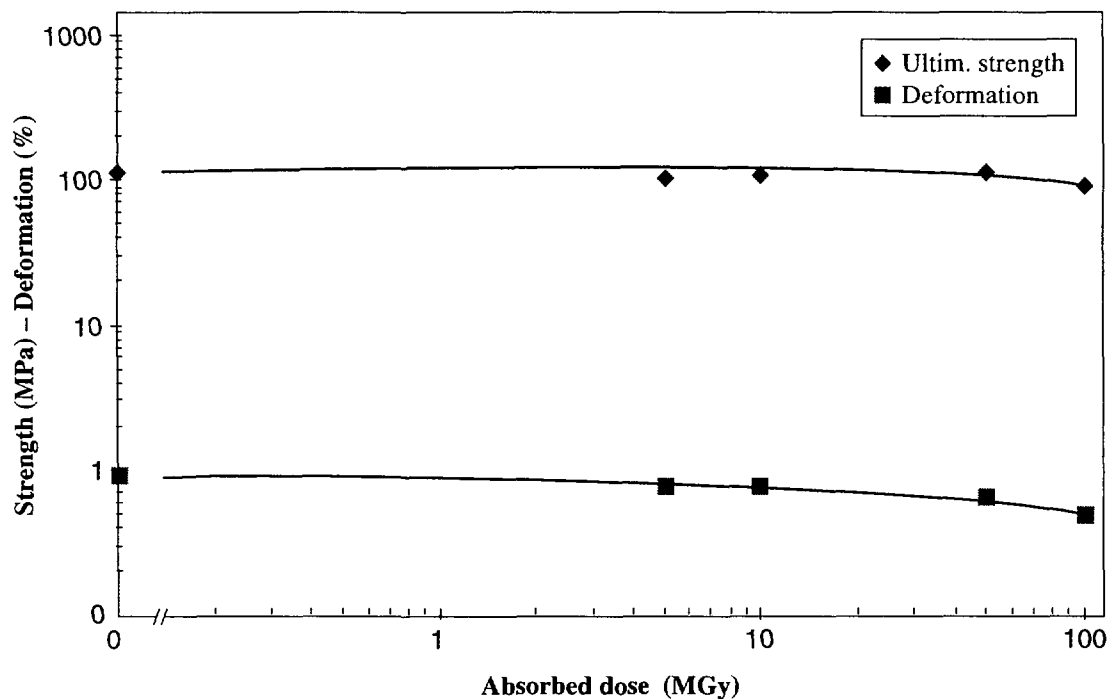

Type **Araldite NU 471**
 Material: **Epoxy moulding compound**

TIS No. **R 443**

Supplier: **Ciba-Geigy**
 Remarks: **VPI product, not cured**

UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	97$\pm$3	0.96$\pm$0.03	12.8$\pm$0.3
0.1	0.5	88$\pm$3	0.80$\pm$0.04	13.7$\pm$0.2
0.1	2.5	78$\pm$1	0.63$\pm$0.01	15.2$\pm$0.7
220	5	74$\pm$2	0.62$\pm$0.02	12.9$\pm$1.3
10	6.4	87$\pm$2	0.72$\pm$0.01	14.4$\pm$0.1
220	10	74$\pm$7	0.57$\pm$0.08	15.1$\pm$0.4
220	50	75$\pm$3	0.51$\pm$0.03	16.6$\pm$0.3
220	100	51$\pm$2	0.36$\pm$0.02	17.8$\pm$1.7

Critical property = deformation

Radiation index (RI) = 7.8 at a mean dose rate of 220 kGy/h

Radiation index (RI) = > 6.8 at a mean dose rate of 10 kGy/h

Radiation index (RI) = > 6.4 at a mean dose rate of 100 Gy/h

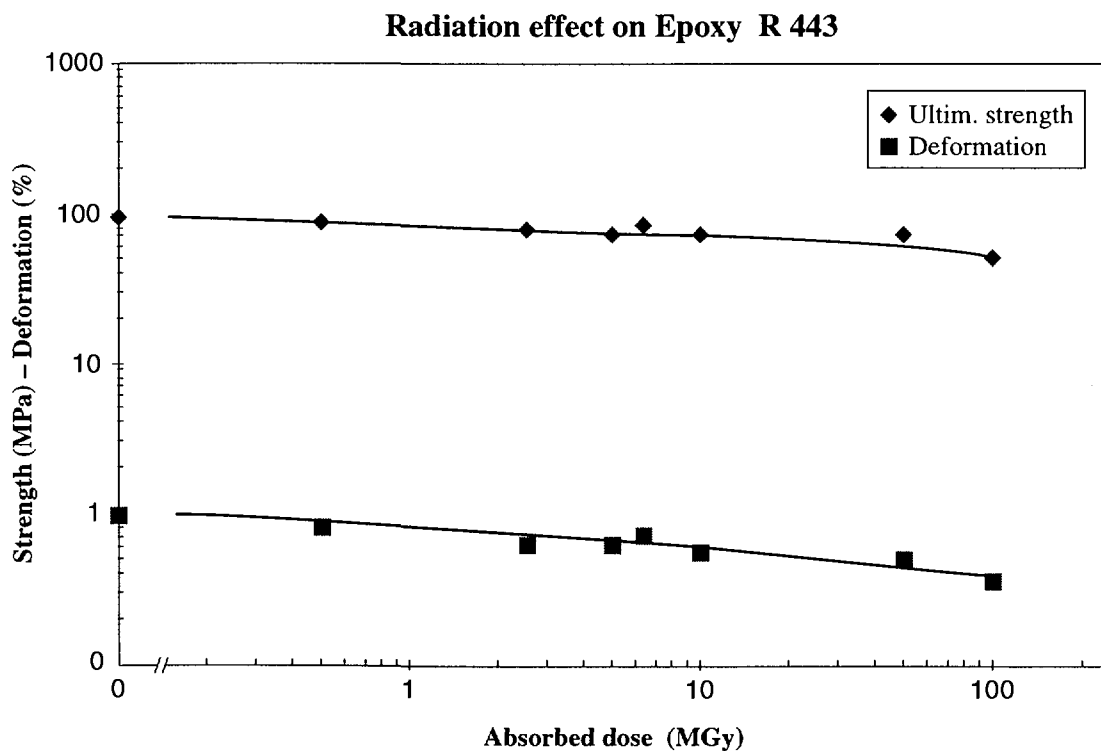

Type **Araldite NU 481**
 Material: **Epoxy moulding compound**

TIS No. **R 447**

Supplier: **Ciba-Geigy**
 Remarks: **VPI product**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	87±2	0.98±0.02	11.8±0.2
220	5	70±1	0.67±0.02	12.7±0.2
220	10	75±2	0.67±0.02	13.5±0.4
220	50	63±3	0.49±0.03	15.6±0.2
220	100	46±1	0.36±0.01	15.4±0.7

Critical property = deformation

Radiation index (RI) = 7.7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 447

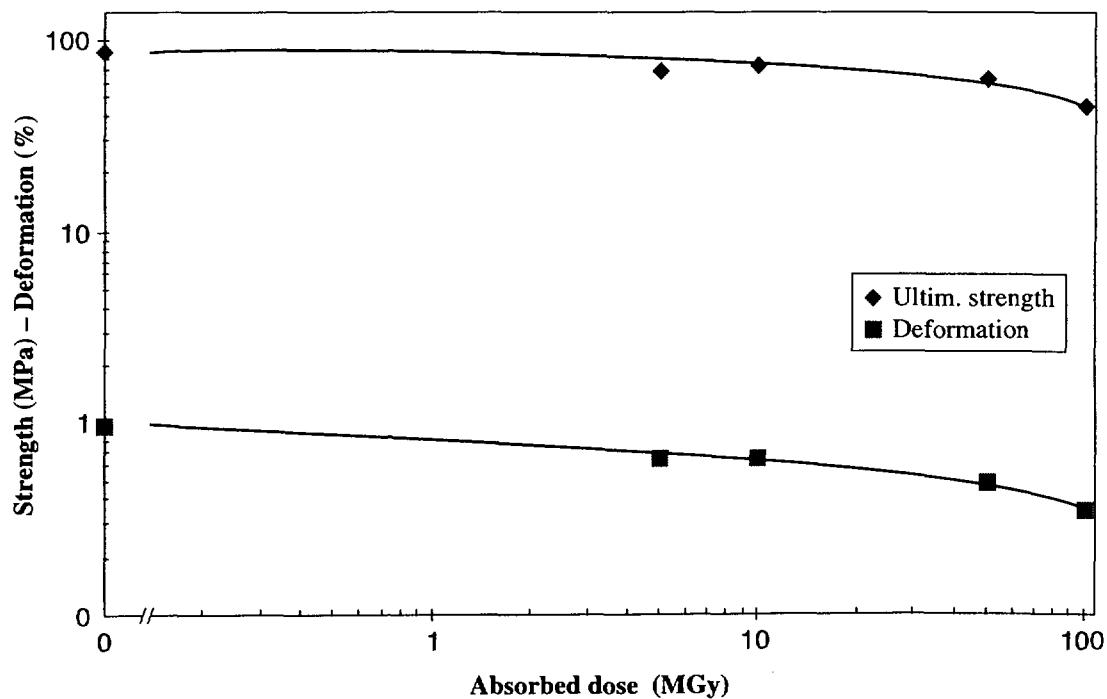

Type **Araldite NU 505**
 Material: **Epoxy moulding compound**

TIS No. **R 449**

Supplier: **Ciba-Geigy**
 Remarks: **VPI product**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	115±12	0.9±0.1	17.6±0.5
220	5	113±4	0.84±0.02	17.7±0.7
220	10	111±7	0.81±0.04	17.3±0.5
220	50	111±3	0.67±0.01	20.0±0.6
220	100	91±4	0.51±0.04	18.7±1.0

Critical property = deformation

Radiation index (RI) = > 8 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 449

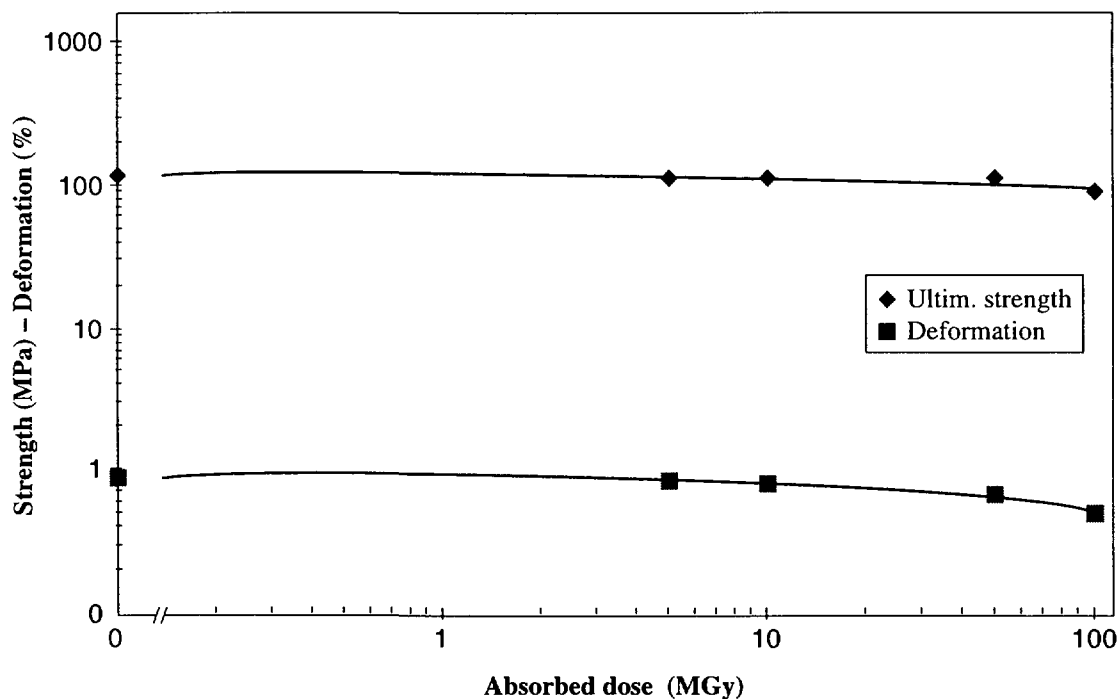

Type **Araldite NU 511**
 Material: **Epoxy moulding compound**

TIS No. **R 453**

Supplier: **Ciba-Geigy**
 Remarks: **VPI product**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	158±20	1.08±0.13	17.4±0.6
220	5	163±8	1.06±0.06	17.7±0.4
220	10	159±12	1.06±0.09	16.8±0.3
220	50	162±6	0.94±0.03	18.6±0.7
220	100	128±5	0.78±0.04	18.1±0.4

Critical property = deformation

Radiation index (RI) = > 8 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 453

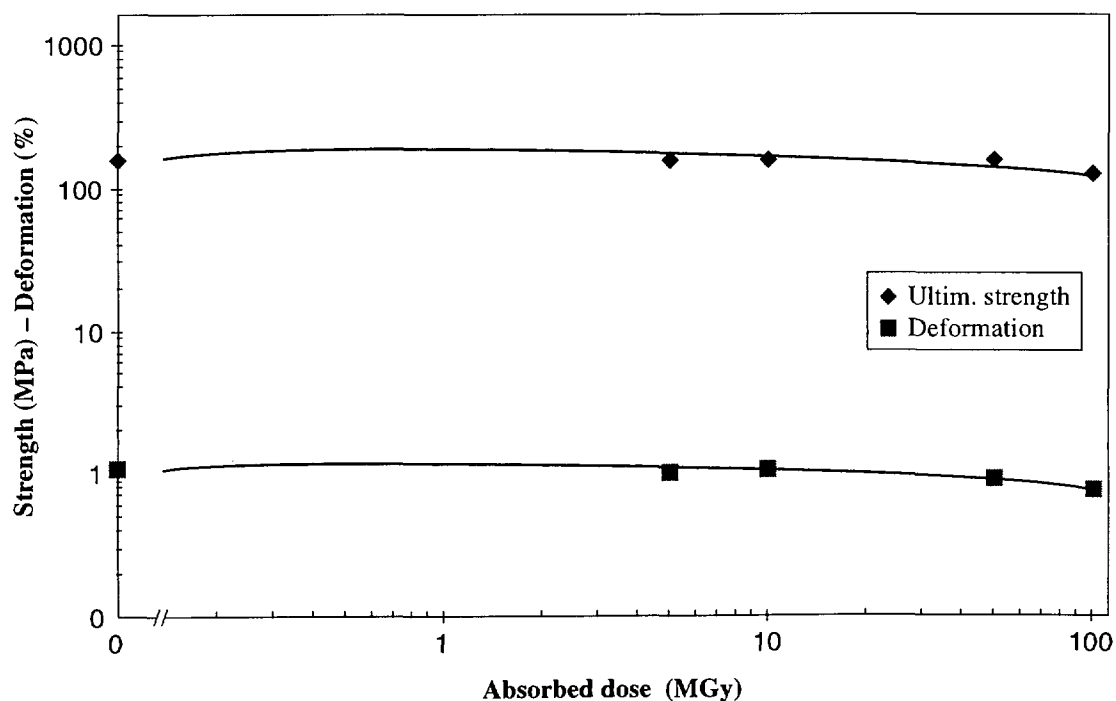

Material: **Araldite F**
Type **CY 205**

TIS No. **R 483**

Supplier: **ABB Augsburg**
Remarks: **Insulation of LEP quadrupole coils**

UL 94: n.m.
LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	90±12	2.61±0.38	3.6±0.05
0.02	0.37	73±15	1.81±0.42	3.8±0.07
0.2	3	48±9	1.35±0.20	3.6±0.29
2	4	59±10	1.86±0.50	3.2±0.20
200	5	76±20	2.24±0.53	3.5±0.14
2	8	28±4	0.91±0.10	3.2±0.80
2	10	30±2	0.96±0.10	3.2±0.10
200	30	33±11	1.03±0.25	3.5±0.44

Critical property = flexural strength

Radiation index (RI) = 7.3 at a mean dose rate of 220 kGy/h

Radiation index (RI) = 6.7 at a mean dose rate of 200 Gy/h

Radiation effect on Araldite F - R 483

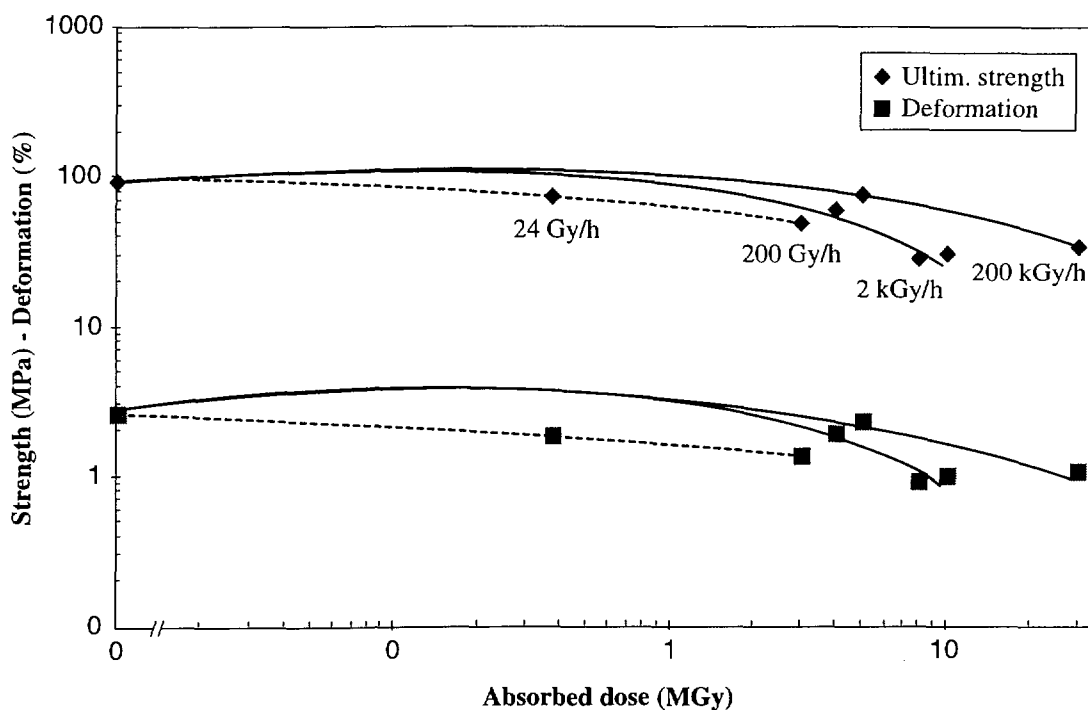

Comment: Low-dose rate irradiations (dotted lines) correspond to life irradiation in LEP.

Material: **Araldite F**
 Type: **HY 905 + DY 040 + DY 061**

TIS No. **R 486**

Supplier: **Ciba-Geigy**
 Remarks: via Ansaldo
 this resin is used for LEP QA magnets

UL 94: n.m.

LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	82±11	2.6±0.38	3.3±0.09
220	5	71±13	2.1±0.4	3.5±0.10
220	10	51±6	1.5±0.18	3.6±0.07
220	50	15±2	0.5±0.04	3.3±0.13

Critical property = flexural strength

Radiation index (RI) = 7.1 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 486

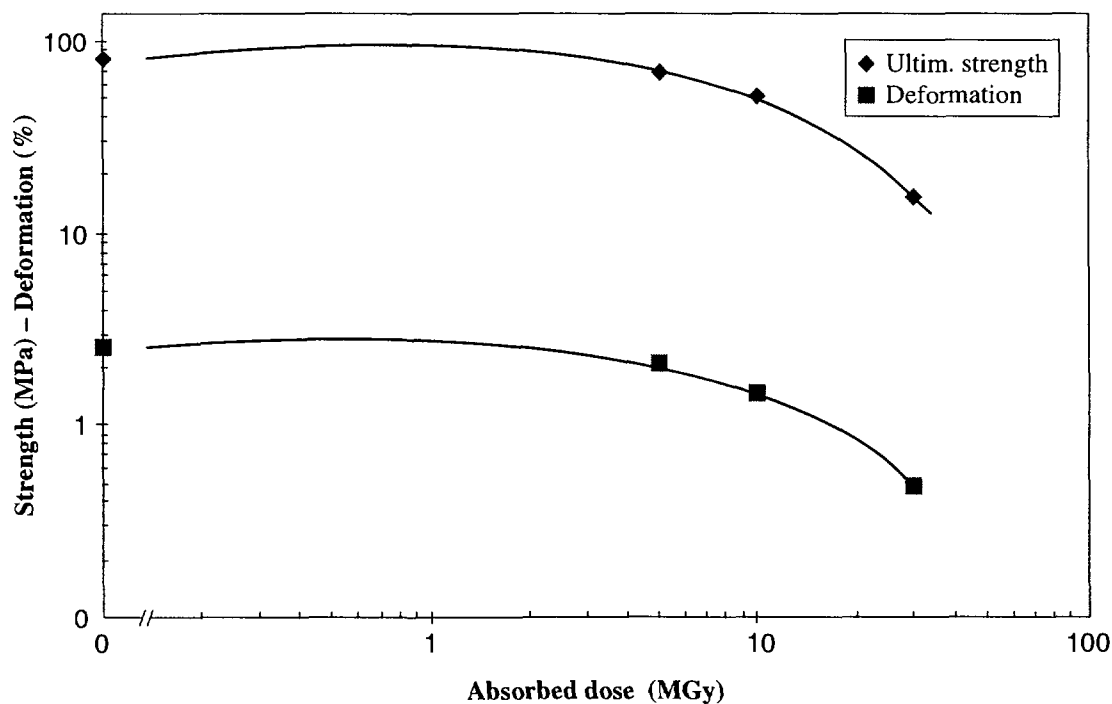

Type **Araldite NU 514**
 Material: **Epoxy moulding compound**

TIS No. **R 492**

Supplier: **Ciba-Geigy**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	115$\pm$9	1.17$\pm$0.10	12.7$\pm$0.2
170	5	110$\pm$10	1.07$\pm$0.13	13.6$\pm$0.3
170	10	103$\pm$3	1.10$\pm$0.04	13.5$\pm$0.2
170	50	98$\pm$2	0.77$\pm$0.02	15.6$\pm$0.2
170	100	63$\pm$12	0.6$\pm$0.1	12.7$\pm$0.7

Critical property = deformation

Radiation index (RI) = 7.9 at a mean dose rate of 170 kGy/h

Radiation effect on insulating resin R 492

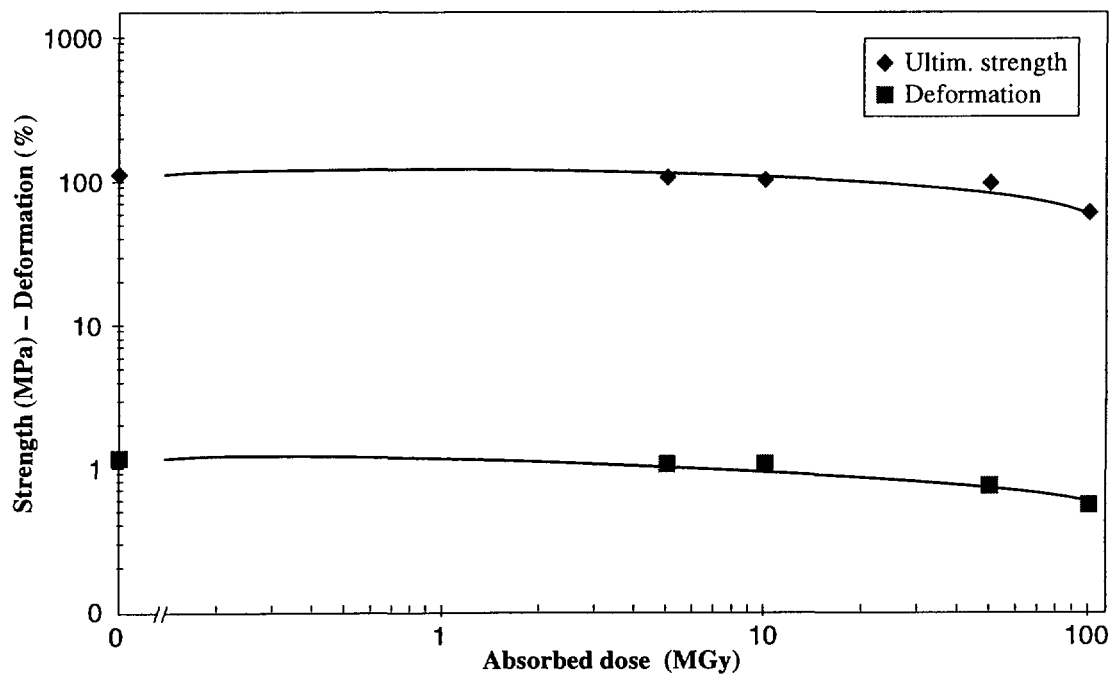

Type **Araldite NU 487**
 Material: **Epoxy moulding compound**

TIS No. **R 493**

Supplier: **Ciba-Geigy**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	150±9	1.19±0.05	15.7±0.5
170	5	127±11	0.89±0.08	16.5±0.4
170	10	108±12	0.74±0.08	17.1±0.5
170	50	96±13	0.59±0.08	18.9±0.5
170	100	47±2	0.36±0.01	15.7±0.5

Critical property = deformation

Radiation index (RI) = 7.8 at a mean dose rate of 170 kGy/h

Radiation effect on insulating resin R 493

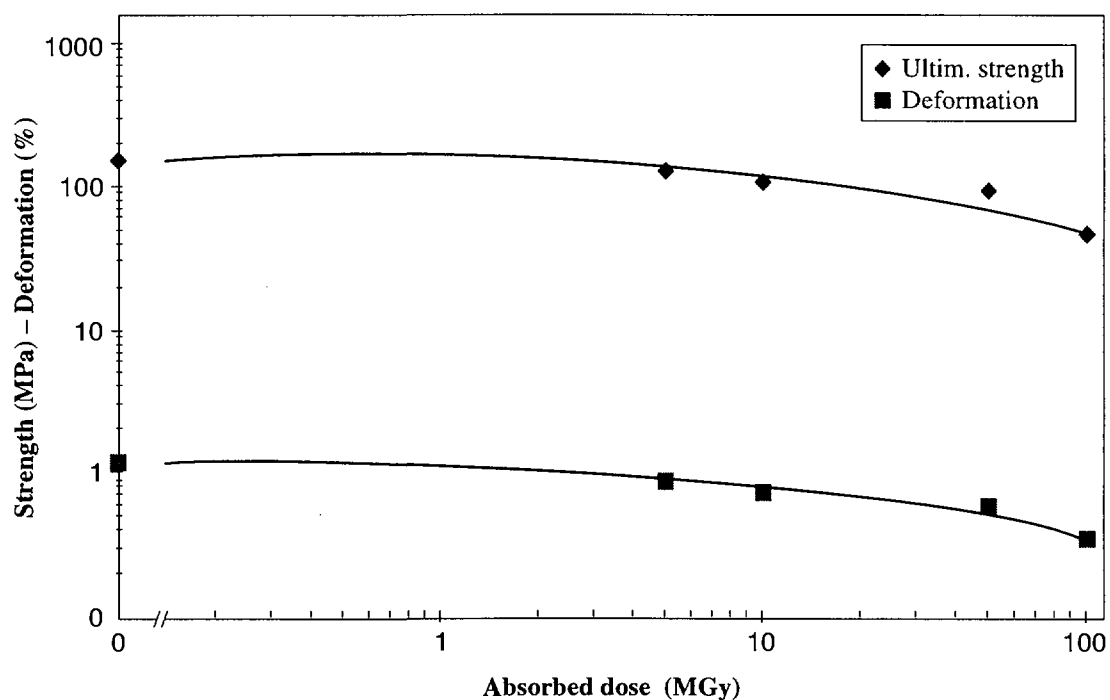

Type **Araldite AV/HV 1580 GB**
 Material: **Epoxy resin putty**

TIS No. **R 566**

Supplier: **Ciba-Geigy**
 Remarks:


UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	61$\pm$2	0.53$\pm$0.04	15.2$\pm$0.3
0.1	1	54$\pm$3	0.50$\pm$0.01	14.5$\pm$0.9
65	5	51$\pm$7	0.45$\pm$0.04	10.6$\pm$2.5
240	10	23$\pm$3	0.31$\pm$0.02	8.5$\pm$0.8
225	30	18$\pm$2	0.25$\pm$0.03	8.6$\pm$1.2

Critical property = flexural strength

Radiation index (RI) = 6.6 at a mean dose rate of 240 kGy/h

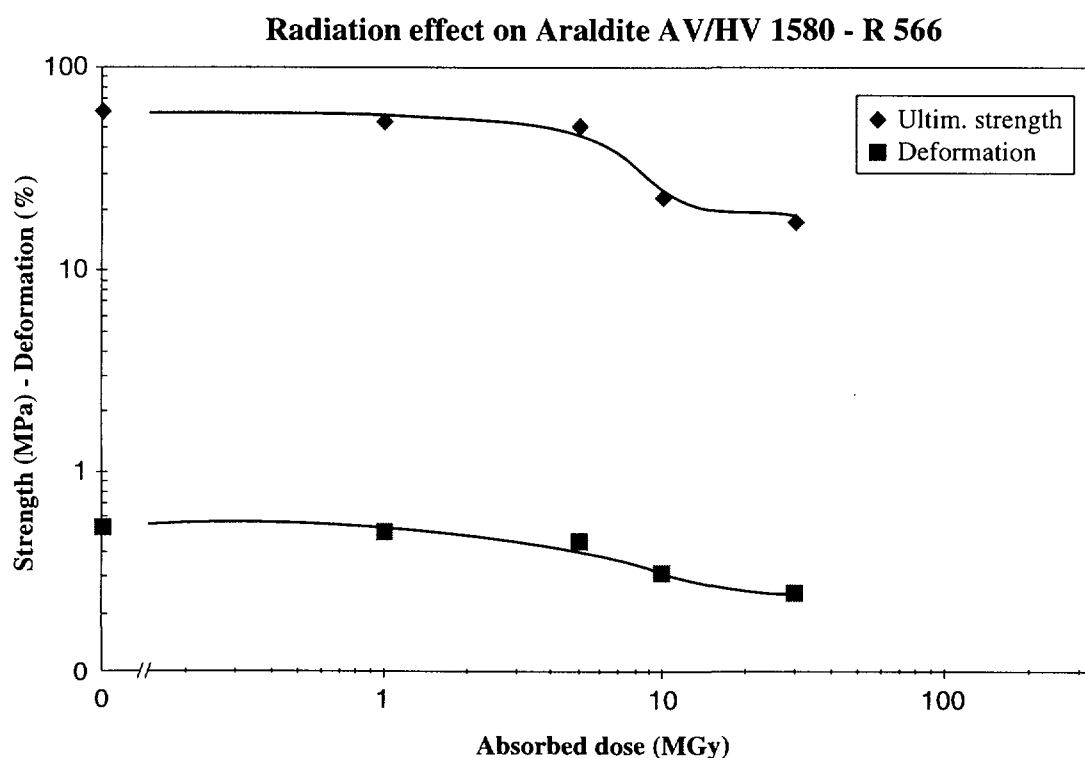

**NEXT PAGE(S)
left BLANK**

Bakelite	trade name for Phenol-Formaldehyde (PF) resins
Birakrit	trade name for glass-fibre epoxy laminate, see Ref. [25], RI = 7.3
Bisphenol A	base product for epoxy resins, see Araldite and epoxy resins
Borolene	trade name by DSM for polyethylene; see PE

**NEXT PAGE(S)
left BLANK**

Cestidur	trade name of DSM EPP for polyethylene, see PE
Cestilene	trade name of DSM EPP for polyethylene, see PE
Cestitech	trade name of DSM EPP for polyethylene, see PE
Cevolit	trade name for glass-fibre reinforced polyester resin, see Ref. [25]; RI = 6.7
CFRP	Carbon-fibre-reinforced plastics (composites) for behaviour under cryogenic irradiation, see Ref. [35]
Copolymer polyimide and silicone	see silicone-polyimide copolymer
Cross-linked styrene copolymer	see styrene
Crystic	trade name for glass-fibre reinforced unsaturated polyester resin, see Ref. [25]; RI = 7.3
Cyanate-ester resins (type of polyurethane resins), see also CFRP	

List of materials classified under letter C

TIS number	Material name	Type	Mechanical properties			
			UTS (MPa)	Deform. (%)	Modulus (MPa)	RI
550	Carbon-fibre-reinforced epoxy	MY720/MT976	1674	1.54	112	> 7.7
552	Carbon-fibre-reinforced epoxy	LY556/HY917/DY070	929	1.17	80.5	8.1
553	Carbon-fibre-reinforced epoxy	LY556/HY2954	884	1.10	81.1	6.6
555	Carbon-fibre-reinforced epoxy	Fibredux	1208	1.80	70.5	> 8.1
556	Carbon-fibre-reinforced epoxy	Vicotex	841	1.93	47.0	7.2
558	Cyanate ester resin	Arocy	125	4.53	3.20	7.5
559	Cyanate ester resin + epoxy		139	5.82	3.30	7.3
561	Cyanate ester resin	RS-3	94.7	3.95	2.80	7.3
562	Cyanate ester resin + carbon fibre	RS-3 + XM50A	304	0.64	66.1	> 7.7

Material: **Carbon-fibre-reinforced epoxy**
 Type **MY720/HT976 + 67.8% fibres**

TIS No. **R 550**

Supplier: **Ciba-Geigy**
 Remarks: **unidirectional fibres orientation**

UL 94: **n.m.**
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	1674$\pm$134	1.54$\pm$0.05	112$\pm$3
10	9	1535$\pm$94	1.50$\pm$0.06	102$\pm$8
200	10	1681$\pm$122	1.65$\pm$0.09	106$\pm$2
200	50	1579$\pm$76	1.56$\pm$0.06	106$\pm$1

Critical property = flexural strength

Radiation index (RI) = > 7 at a mean dose rate of 10 kGy/h

Radiation index (RI) = > 7.7 at a mean dose rate of 220 kGy/h

Radiation effect on carbon-epoxy R 550

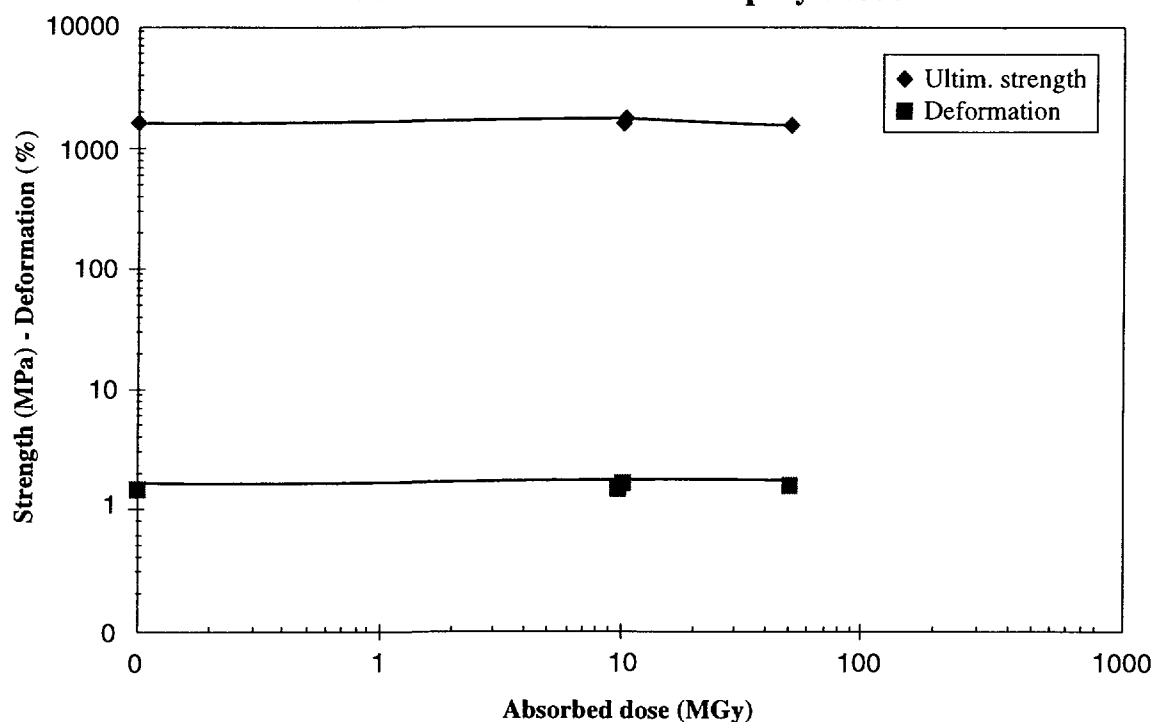

Material: **Carbon-fibre-reinforced epoxy**
 Type **LY 556/HY 917/DY 070**

TIS No. **R 552**

Supplier: **Ciba-Geigy**
 Remarks: **8 layers of fibre mat**


UL 94:
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	929±187	1.17±0.23	80.5±2.6
230	3	816±99	0.97±0.16	81.5±2.1
230	10	857±114	1.06±0.13	82.2±1.4
230	62	837±90	1.02±0.12	83.0±1.2
230	112	487±29	0.64±0.05	81.3±3.9

Critical property = flexural strength

Radiation index (RI) = 8.1 at a mean dose rate of 230 kGy/h

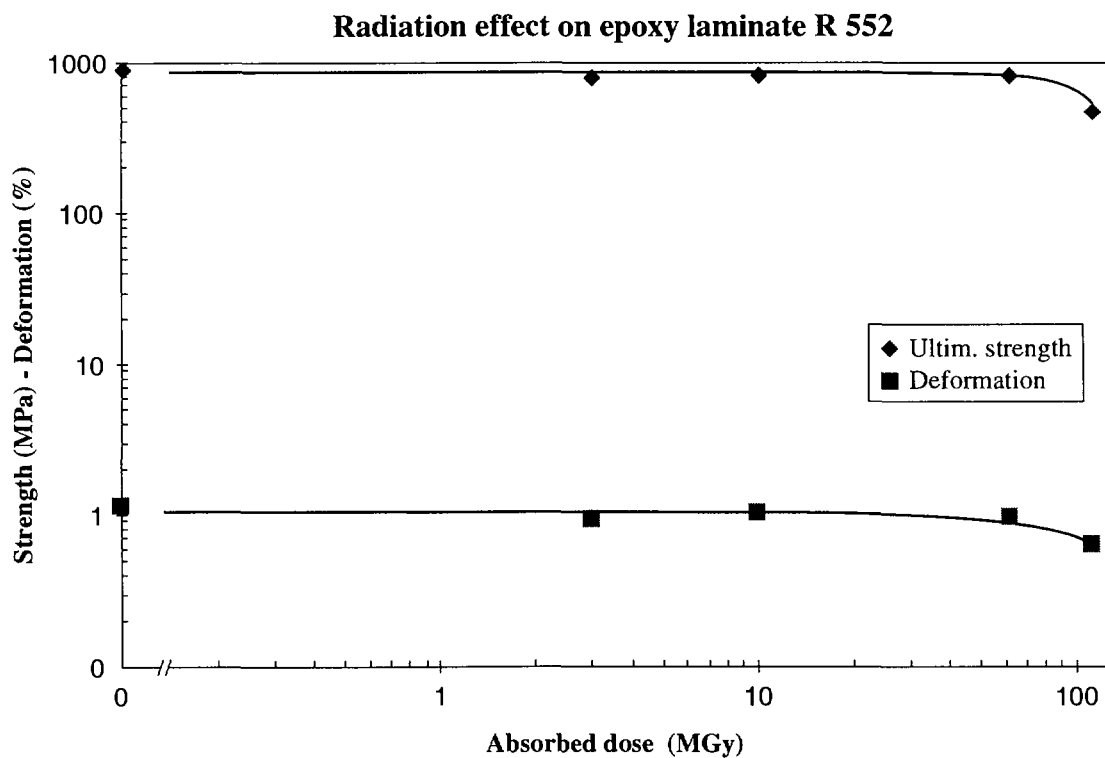

Material: **Carbon-fibre-reinforced epoxy**
 Type **LY 556/HY 2954**

TIS No. **R 553**

Supplier: **Ciba-Geigy**
 Remarks: 8 layers of fibre mat

UL 94:
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	884±98	1.10±0.12	81.1±1.0
230	3	860±99	1.05±0.11	83.3±2.0
0.5	3	774±113	0.39±0.06	192±17
230	10	190±26	0.29±0.03	79.7±3.8
230	62	102±5	0.18±0.01	79.3±1.1
230	112	114±8	0.17±0.02	84.9±2.4

Critical property at a mean dose rate of 230 kGy/h = flexural strength

Radiation index (RI) = 6.6 at a mean dose rate of 230 kGy/h

Critical property at a mean dose rate of 0.5 kGy/h = deformation

Radiation index (RI) = 6.4 at a mean dose rate of 0.5 kGy/h

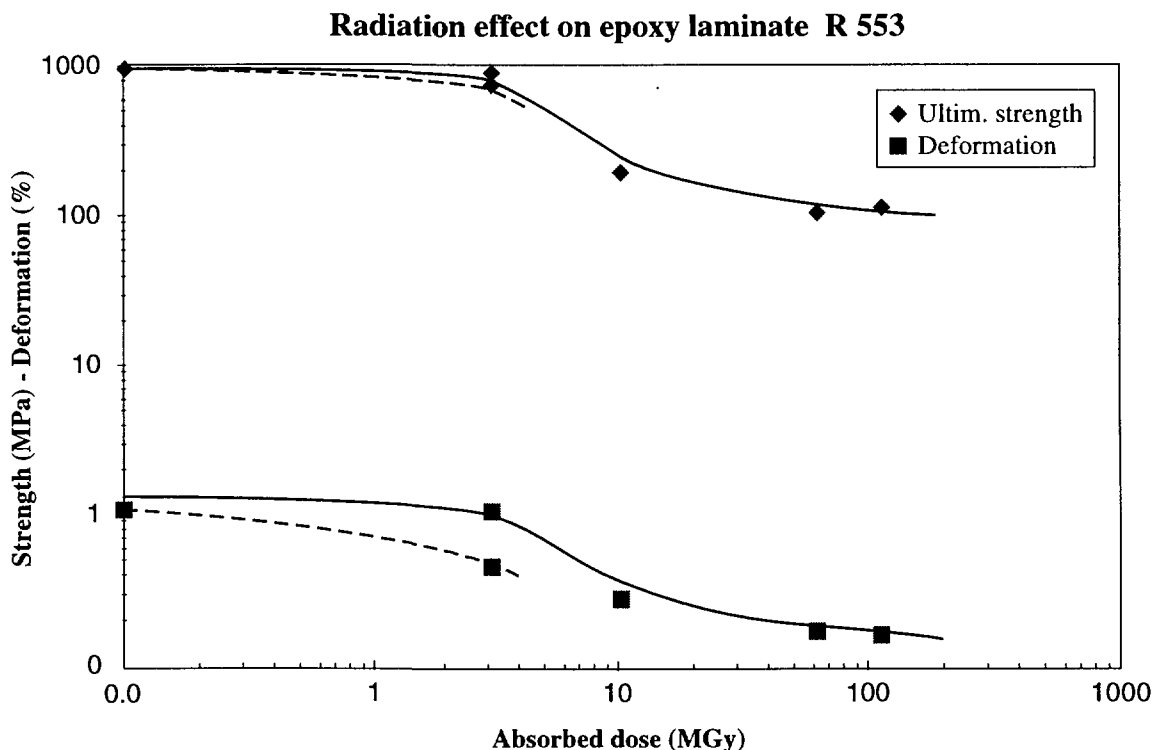

Comment: Dotted lines correspond to low dose rate irradiation.

Material: **Carbon-fibre-reinforced epoxy**
 Type **Fibredux 91 4c-TS(6K)-5-34%**

TIS No. **R 555**

Supplier: **Ciba-Geigy**
 Remarks: **8 layers of prepreg**

UL 94:
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	1208±35	1.80±0.04	70.5±0.2
230	3	1239±42	1.68±0.09	76.1±2.0
230	10	1255±82	1.75±0.12	75.9±2.5
230	62	1077±275	1.47±0.22	75.2±3.2
230	112	1013±192	1.56±0.31	67.6±4.4

Critical property = flexural strength

Radiation index (RI) > 8.1 at a mean dose rate of 230 kGy/h

Radiation effect on epoxy laminate R 555

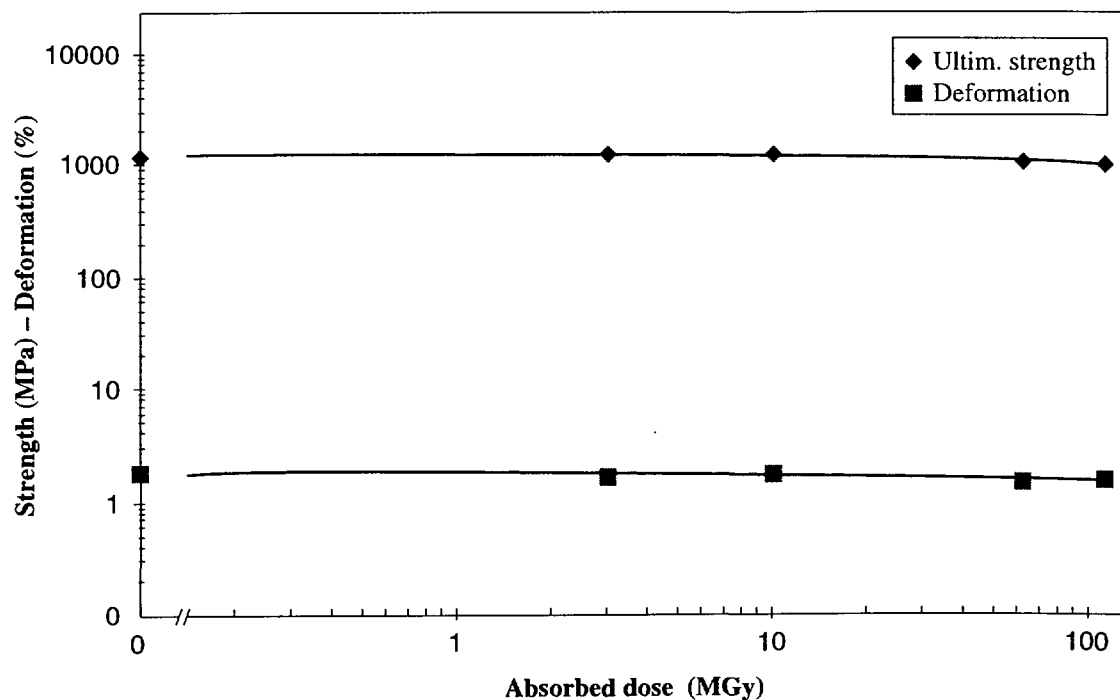

Material: **Carbon-fibre-reinforced epoxy**
 Type **Vicotex M 10 G 1071**

TIS No. **R 556**

Supplier: **Ciba-Geigy**
 Remarks:

UL 94:
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	841±31	1.93±0.06	47.0±1.0
230	3	865±36	1.93±0.05	48.0±1.4
230	10	852±32	1.83±0.06	49.1±1.6
230	62	201±71	0.66±0.26	39.4±12
230	112	42±10	0.33±0.15	19.4±4.8

Critical property = flexural strength

Radiation index (RI) = 7.2 at a mean dose rate of 230 kGy/h

Radiation effect on epoxy laminate R 556

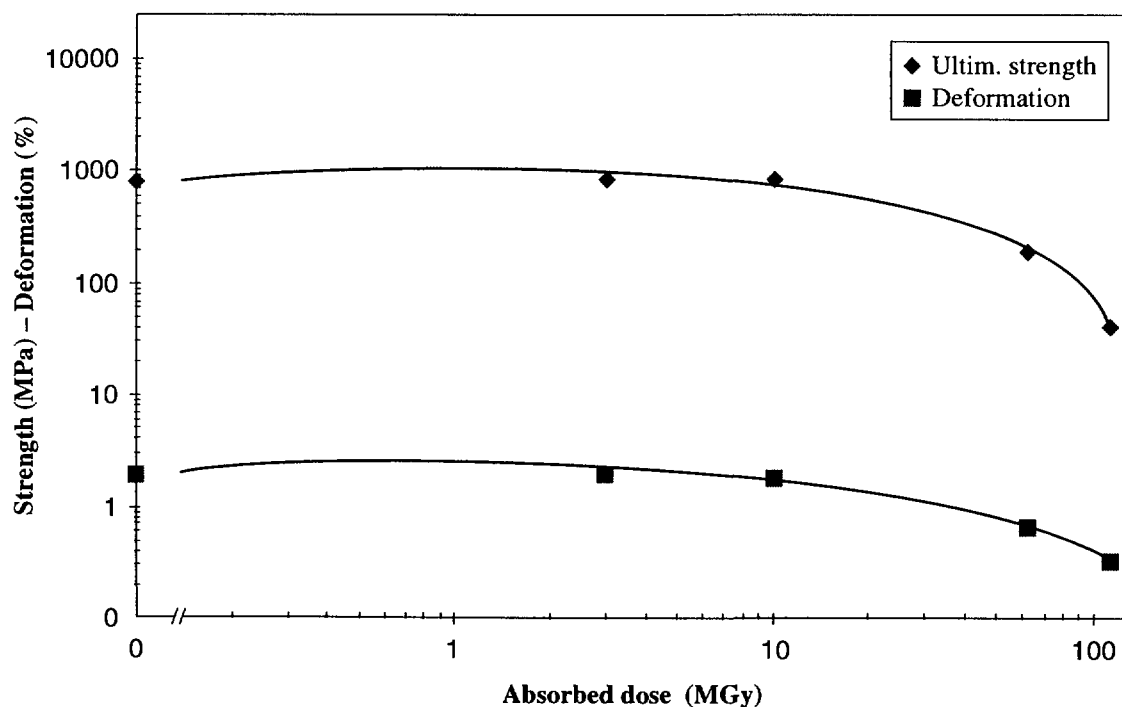

Material: **Cyanate ester resin**
 Type: **Arocy B 10 (M 7.009/9)**

TIS No. **R 558**

Supplier: **Ciba-Geigy**
 Remarks: **Bisphenol-Adicyanate ester**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	125±11	4.53±0.49	3.2±0.02
6	1	189±11	8.25±1.53	4.2±0.04
230	3	161±5	6.62±1.00	3.8±0.05
230	10	160±2	7.62±1.24	3.8±0.07
180	50	69±4	1.76±0.07	4.0±0.06

Critical property = deformation

Radiation index (RI) = 7.5 at a mean dose rate of 180 kGy/h

Radiation effect on cyanate ester R 558

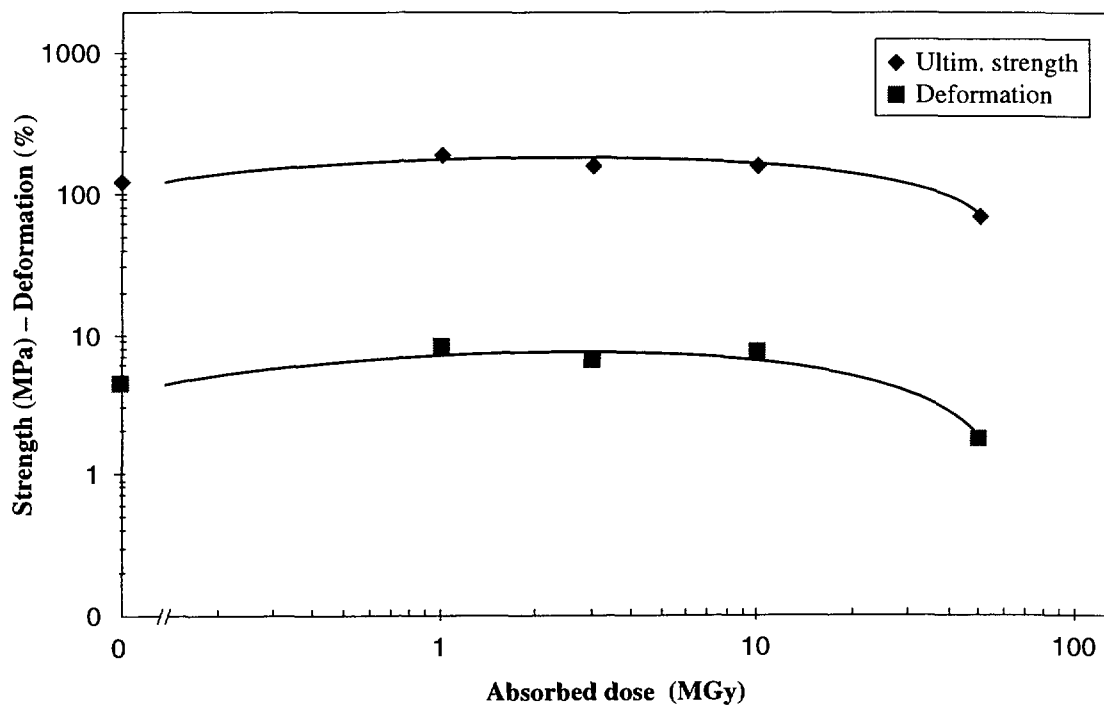

Material: **Cyanate ester + Epoxy**
 Type **Arocy B 10/LY556 / Zn (M 7.10/6)**

TIS No. **R 559**

Supplier: **Ciba-Geigy**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	139±9	5.82±1.00	3.3±0.09
6	1	141±11	6.42±1.93	3.5±0.07
230	3	147±6	6.04±0.83	3.7±0.03
230	10	150±3	5.34±0.34	3.9±0.10
180	50	25±12	0.68±0.28	4.1±0.09

Critical property = deformation

Radiation index (RI) ~ 7.3 at a mean dose rate of 180 kGy/h

Radiation effect on cyanate ester + epoxy R 559

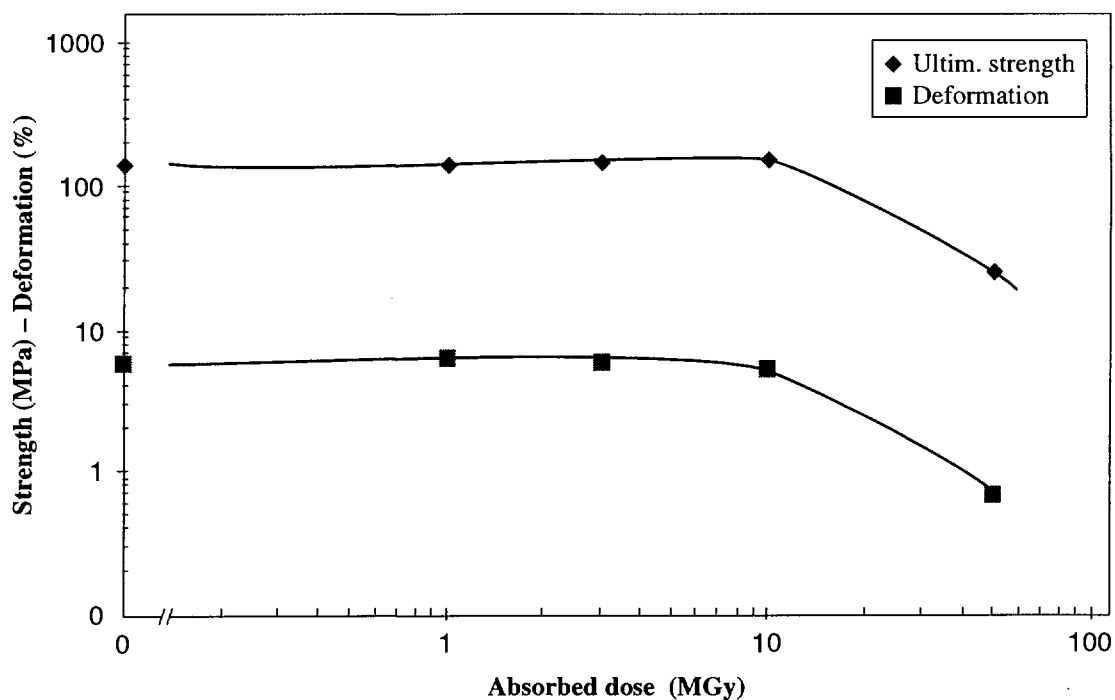

Material: **Cyanate ester resin**
Type **RS-3**

TIS No. **R 561**

Supplier: **YLA**
Remarks:

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	94.7±13.1	3.95±0.80	2.8±0.13
18	3	80.8±7.3	2.55±0.51	3.4±0.37
190	10	78.0±8.8	2.30±0.30	3.4±0.13
230	50	42.9±7.8	1.28±0.21	3.5±0.13

Critical property = deformation

Radiation index (RI) = 7.3 at a mean dose rate of 200 kGy/h

Radiation effect on Cyanate ester resin R 561

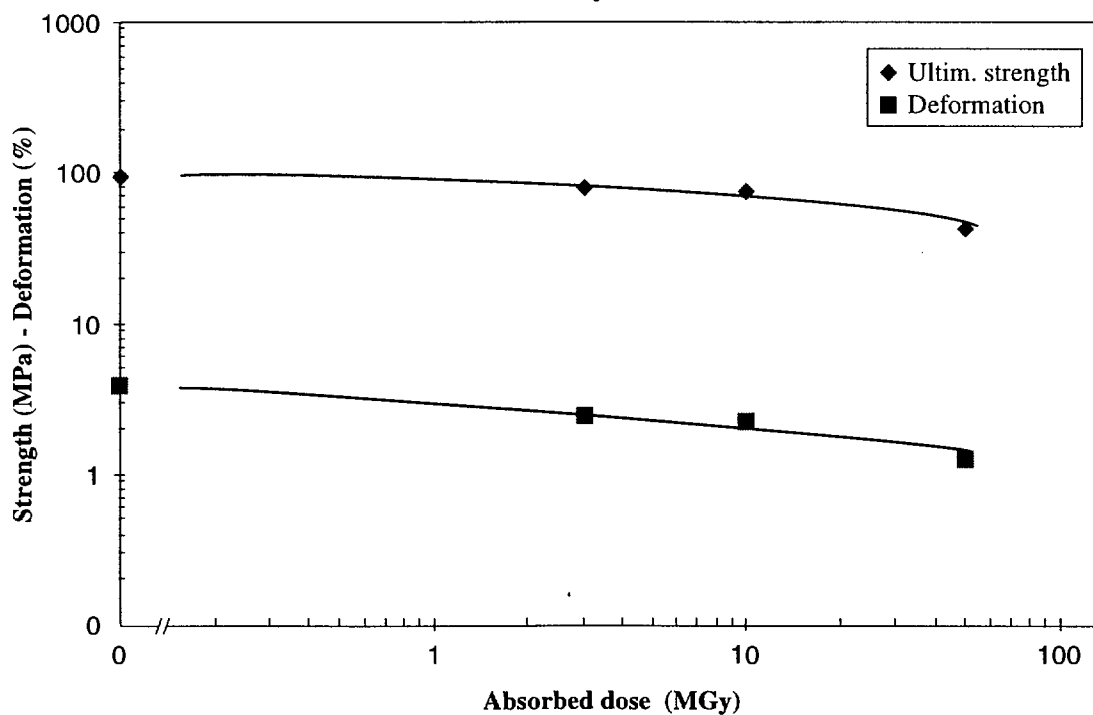

Material: **Cyanate ester + carbon fibres**
 Type: **RS-3 + XN 50A**

TIS No. **R 562**

Supplier: **YLA**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	304±26	0.64±0.11	66.1±11.9
18	3	330±17	0.57±0.05	77.6±1.2
180	10	320±26	0.54±0.05	79.7±5.3
180	50	313±33	0.52±0.06	76.9±3.3

Critical property = deformation

Radiation index (RI) > 7.7 at a mean dose rate of 180 kGy/h

Radiation effect on Cyanate ester laminate R 562

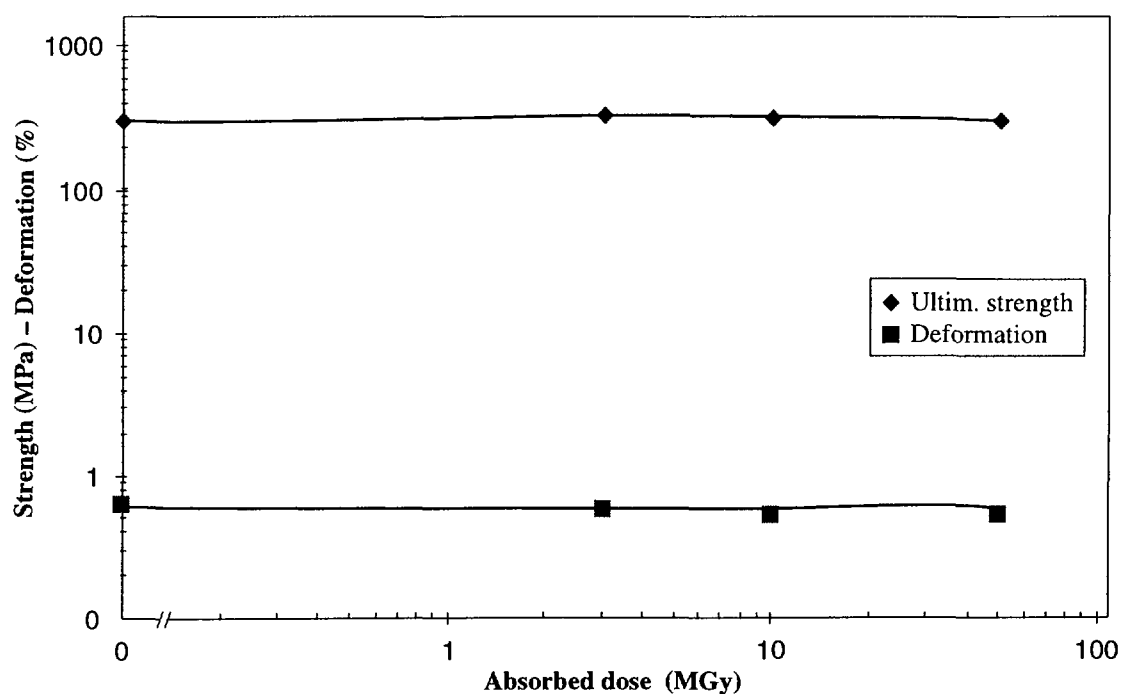

**NEXT PAGE(S)
left BLANK**

D

Dacron	trade name of Dupont for polyester fibres, see Ref. [25]; RI = 5.5
Delrin	trade name of DUPONT de Nemours for polyoxymethylene (POM), see polyoxymethylene (POM)
Dobekan IF	trade name for polyurethane, see Ref. [25]; RI > 7
Dobekot	trade name for epoxy resins, see Ref. [25]; RI < 7
Durotenax	trade name of ISOLA for bisphenol A epoxy, see epoxy resins

**NEXT PAGE(S)
left BLANK**

Envex	trade name for polyimide (PI)
Epikote	trade name of SHELL for epoxy resin
Epoxy resins	for chemical formulas, see Appendix 2 and Ref. [25] Araldite B, D, F trade names of CIBA-GEIGY, see Araldite Bisphenol A epoxy (BPA) Durotenax Epikote Novolac, see Ref. [25] Samicatherm Scotchcast, epoxy base compound Vetresit for behaviour under cryogenic irradiation, see Ref. [35]
Epoxy based laminates,	see also CFRP
Epoxy based prepreg	
Epoxy moulding compound	Araldite NU 460, 461, 471, 481, 487, 505, 511, 514. See Araldite Neonit
Ertalon	trade name of ERTA-EPEC for polyamides, see polyamide
Ertalyte	trade name of ERTA for PETP, see PETP
Ertapeek	trade name of ERTA-EPEC for polyether-ether-ketone, see PEEK
Ertaxel	trade name of ERTA-EPEC for PPS, see PPS
Etronax	trade name of Elektro-Isola for phenolic resins, see phenolic resins

List of materials classified under letter E

TIS number	Material name	Type	Mechanical properties			
			UTS (MPa)	Deform. (%)	Modulus (MPa)	RI
409	Epoxy + glass mat	HGW 2372.4	453.3	2.3	22.08	> 8
414	Epoxy laminate – prepreg	Isopreg 0.28 VP 288	371.1	2.6	16.8	> 7.7
417	Epikote + Aramid fiber	Arenka 900	247.6	3.8	14.4	> 6.7
422	Epoxy resin MY745/EPN1138/CY221/HY905/DY073		153	13.1	3.8	6.6
423	Epoxy resin MY745/HY906/DY073		148.1	8.8	3.8	7.1
424	Epoxy resin (based on Bisphenol A)	Durotenax	61.2	1.05	5.93	6.7
426	Epoxy + glass fibres	Vetresit 1101	1341.5	3.2	42.8	7.9
427	Epoxy (cycloaliphatic) + glass	Vetresit 312	547.4	1.88	31.03	7.7
428	Epoxy (cycloaliphatic) + glass	Vetresit 300	388.4	2.33	18.75	7.9
433	Epoxy resin (based on Bisphenol A)	Durotenax Art. 521-02	141.2	1.58	10.09	7.5
434	Epoxy resin (based on Bisphenol A) + Methyl hexahydrophthal. anhydr.		78.3	2.19	3.6	6.5
437	Epoxy moulding compound	Neonit EG61	92.9	1.03	10.77	~ 7.1
460	Epoxy resin SIB3309 + tape:Samicapor 326.95-47X		116.7	0.54	31.7	7.3
461	Epoxy resin SIB3309 + tape:Samicapor 326.96-86X		162.8	0.52	41.4	> 8
465	Epoxy resin + glass fabric	G-Etronax EP11	387.6	2.28	18.7	> 7.5
466	Epoxy moulding compound	MY790 + HY1102BD	84	2.24	3.91	6.5
467	Epoxy resin + Mica + GF	MY790 + HY1102BD	544.7	2.87	23	7.4
468	Epoxy – prepreg	Isopreg EP spess 0.33	354.8	1.79	22.6	> 8
502	Epoxy moulding compound	R112 + H232	57.6	> 12	1.57	7.1
506	Epoxy laminated + glass	ACO1+GLASS A	408	1.96	22.98	7.3
507	Epoxy laminated + glass	ACO2+GLASS A	431.3	2.47	22.13	7.4
508	Epoxy laminated + glass	ACO1+GLASS B	404.7	2.1	23.1	7.5
509	Epoxy laminated + glass	ACO2+GLASS B	459.1	2.06	24.1	7.5
511	Epoxy	Scotchcast 9	34.3	> 12	1.5	6.8
512	Epoxy	Scotchcast 281	32.9	> 12	2.3	< 6.5
514	Epoxy	Scotchcast 804	90.5	5.44	2.4	< 6.5
515	Epoxy	Scotchcast 824	54.6	1.53	5.6	6.8
525	Epoxy A + glass + Kevlar	Novolac resin	376.5	2.05	33.3	6.9
539	Epoxy resin	Vetronite	362.9	2.1	20.9	> 7.7
540	Epoxy resin + mineral filler + glass mica + Dacron	Samicatherm	143.5	1.14	19.8	7.6
541	Epoxy resin	XNR 4153 / XNH 4153	111.5	1.18	11.34	6.8
554	Epoxy resin	AS/37-3	126	8.4	2.9	6.1
557	Epoxy moulding compound	Matramid 5292A/B	165	6.27	3.9	7.6
564	Epoxy laminate	Isopreg EP 0316	239	1.14	n.m.	7.8
565	Epoxy laminate	Isopreg EP 1037/IDT	552	2.46	30.3	> 8

Material: **Epoxy + glass mat**
 Type **HGW 2372.4**

TIS No. **R 409**

Supplier: **Elin Union**
 Remarks: **LEP-QP insulations based on EPN**
1138 from Ciba-Geigy

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	453±15	2.3±0.1	22.1±0.42
220	10	445±13	2.24±0.06	22.2±0.45
220	30	429±16	2.27±0.07	22.1±0.42
220	50	419±25	2.30±0.11	21.7±0.3
220	100	360±26	2.05±0.21	21.7±0.59

Critical property = flexural strength

Radiation index (RI) = > 8 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 409

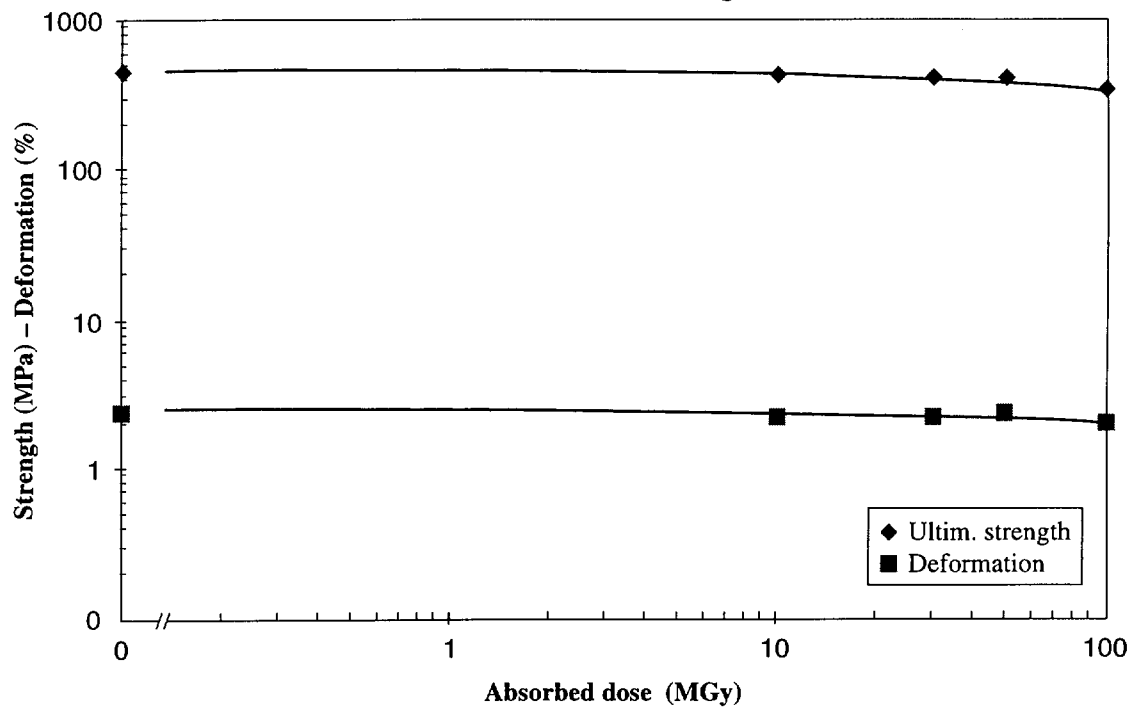

Material: **Epoxy laminate – prepreg**
 Type: **ISOPREG 0.28 VP 288**

TIS No. **R 414**

Supplier: **Isovolta**
 Remarks: **via Ansaldo**

UL 94: **n.m.**
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	371±13	2.6±0.1	16.8±0.7
220	5	350±12	2.6±0.2	19.6±0.8
220	10	362±16	2.7±0.2	17.7±1.0
220	50	272±14	2.2±0.4	16.5±0.4

Critical property = flexural strength

Radiation index (RI) = > 7.7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 414

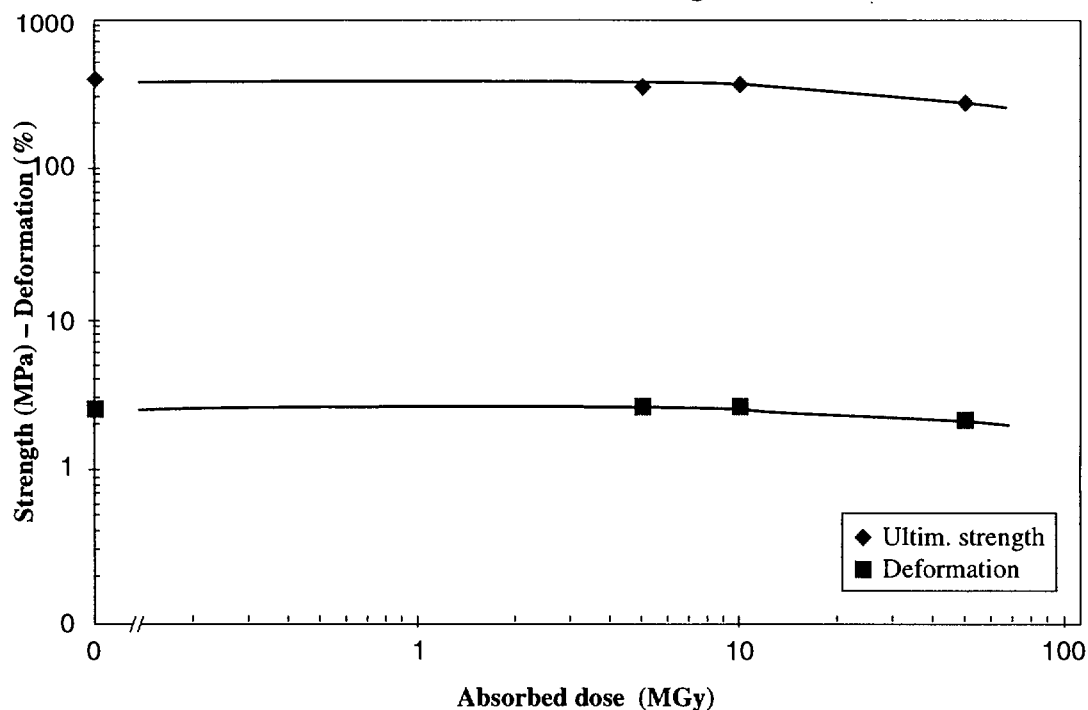

Material: **Epikote + Aramid fibre**
 Type: **Arenka 900**

TIS No. **R 417**

Supplier: **Enka (D)**
 Remarks: **SC coils**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	248±35	3.79±0.8	14.4±3.7
220	0.5	251±84	2.93±0.64	17.0±4.6
220	1	279±33	3.86±0.71	14.4±2.7
220	5	240±34	3.04±0.34	14.9±1.7

Critical property = flexural strength

Radiation index (RI) > 6.7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 417

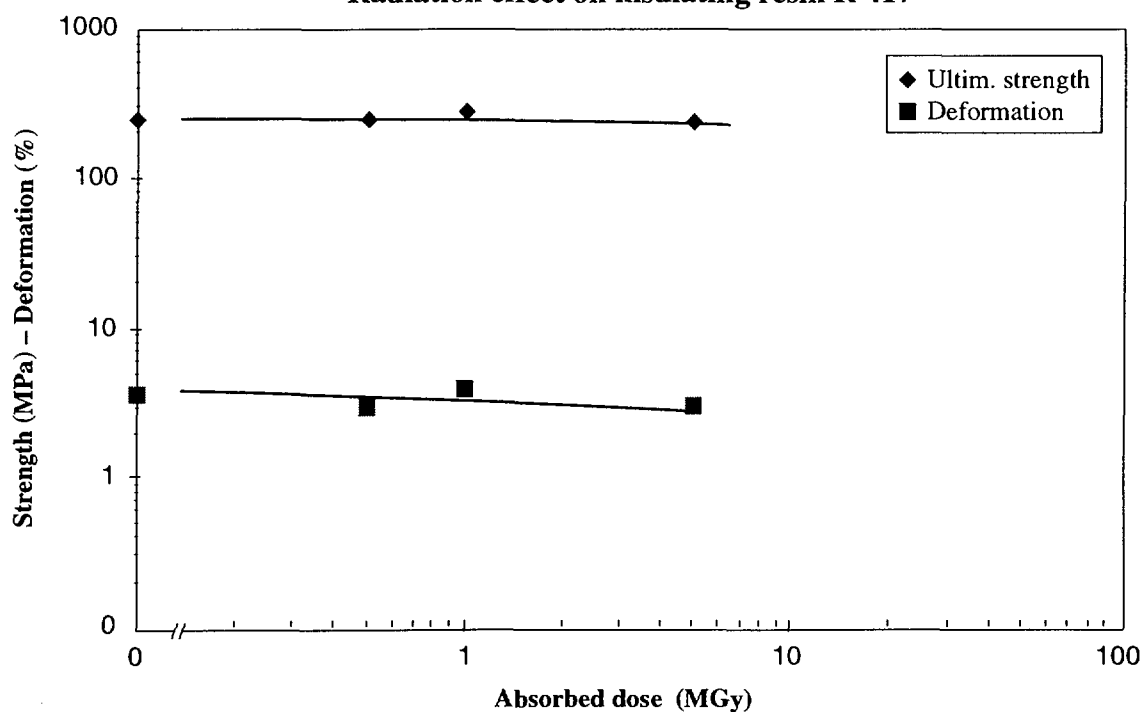

Material: **Epoxy resin**
 Type **MY 745 (50) + EPN 1138 (50) + CY 221 (20) + HY 905 (120) + DY 073 (0.3)**

TIS No. **R 422**

Supplier: **Ciba-Geigy**
 Remarks: **used for the ISR dipoles**


UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	153±3	13.1±1.9	3.80±0.03
0.2	0.5	142±1	12.9±0.3	3.50±0.02
0.2	2.0	140±1	7.9±0.3	3.50±0.02
180	5	93±2	6.1±0.3	4.00±0.03
180	10	73±3	4.2±0.2	4.10±0.04
0.5	12	71±6	2.1±0.2	3.7±0.1
180	20	13±1	1.1±0.1	3.40±0.04

Radiation index (RI) = 6.9 if strength is the critical property

Radiation index (RI) = 6.6 if deformation is the critical property

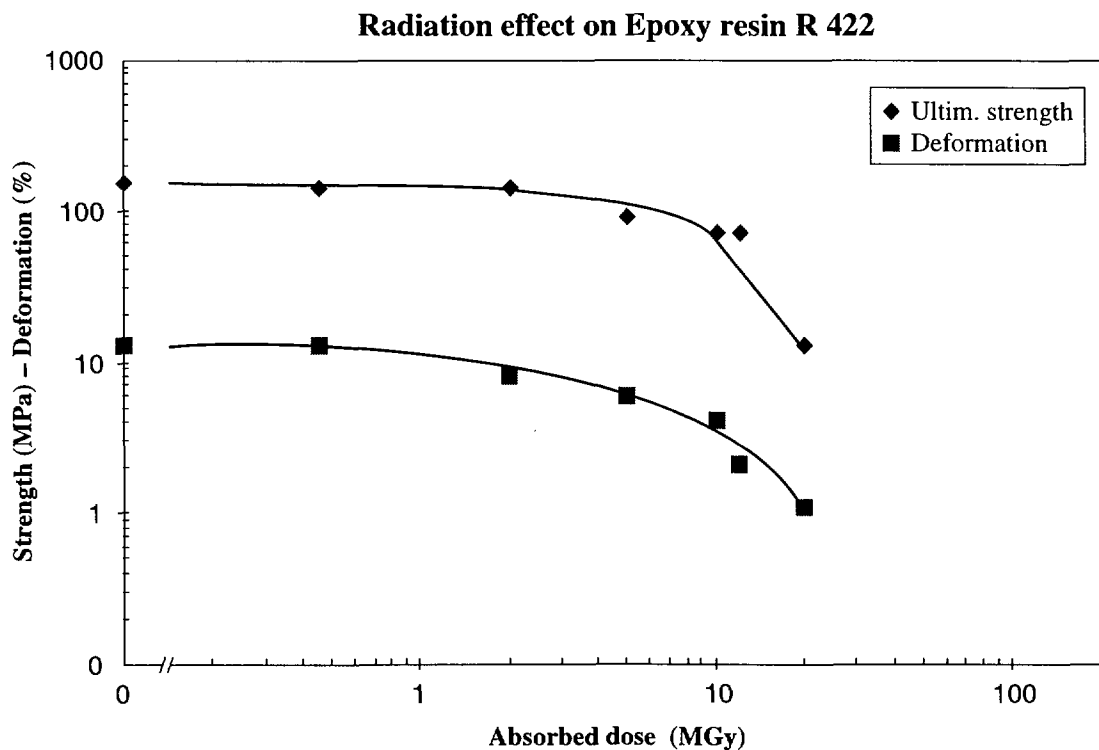

Material: **Epoxy resin**
 Type: **MY 745 (100) + HY 906 (90) + DY 073 (1.5)**

TIS No. **R 423**

Supplier: **Ciba-Geigy**
 Remarks: **used for the SPS dipoles**

UL 94: **n.m.**
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	148±15	8.8±1.3	3.8±0.1
0.2	0.4	149±1	12.9±0.8	3.47±0.01
0.2	2	118±33	7.1±3.7	3.47±0.01
180	5	118±10	10±2	3.7±0.3
180	10	98±5	7.2±1.4	4.1±0.4
0.5	12	45±6	1.3±0.1	3.7±0.3
180	20	43±4	3.2±0.6	4.2±0.4

Radiation index (RI): 6.6 at 500 Gy/h

Radiation index (RI): 7.1 at 180 kGy/h

Radiation effect on Epoxy resin R 423

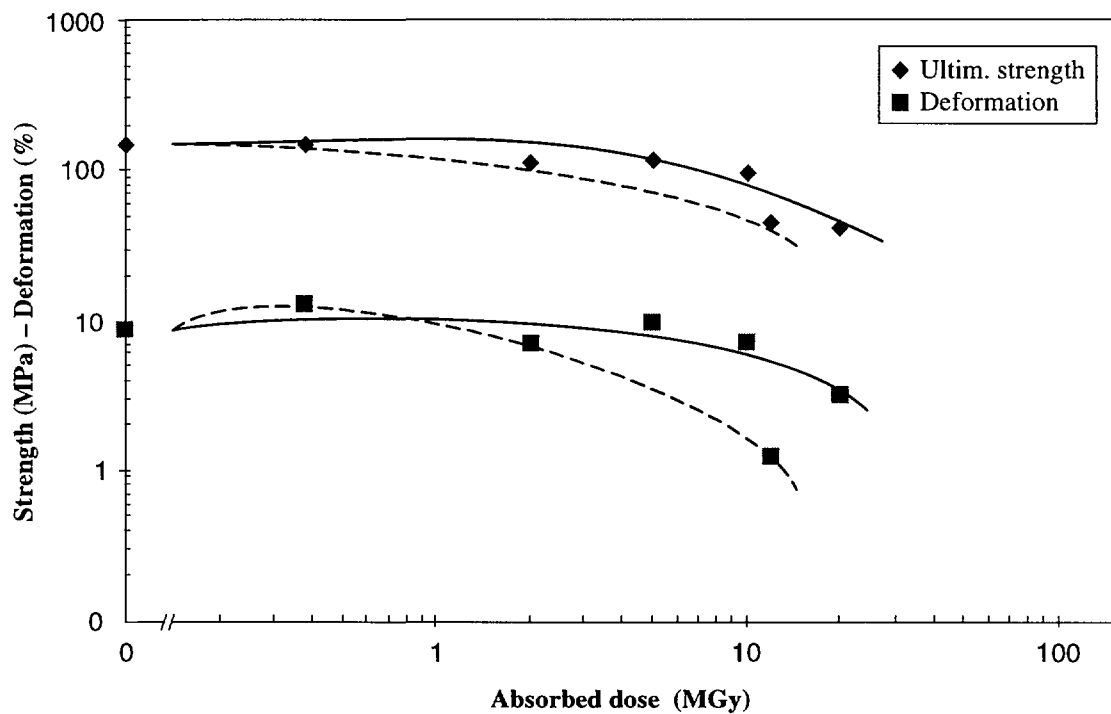

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy resin (based on Bisphenol A)**
 Type: **Durotenax**

TIS No. **R 424**

Supplier: **Isola (CH)**
 Remarks: **protection against X-rays**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	61.2±5.2	1.05±0.09	5.93±0.10
220	1	58.6±7.3	0.88±0.11	6.33±0.17
220	5	26.9±3.2	0.43±0.04	6.30±0.25

Critical property = flexural strength

Radiation index (RI) = 6.6 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 424

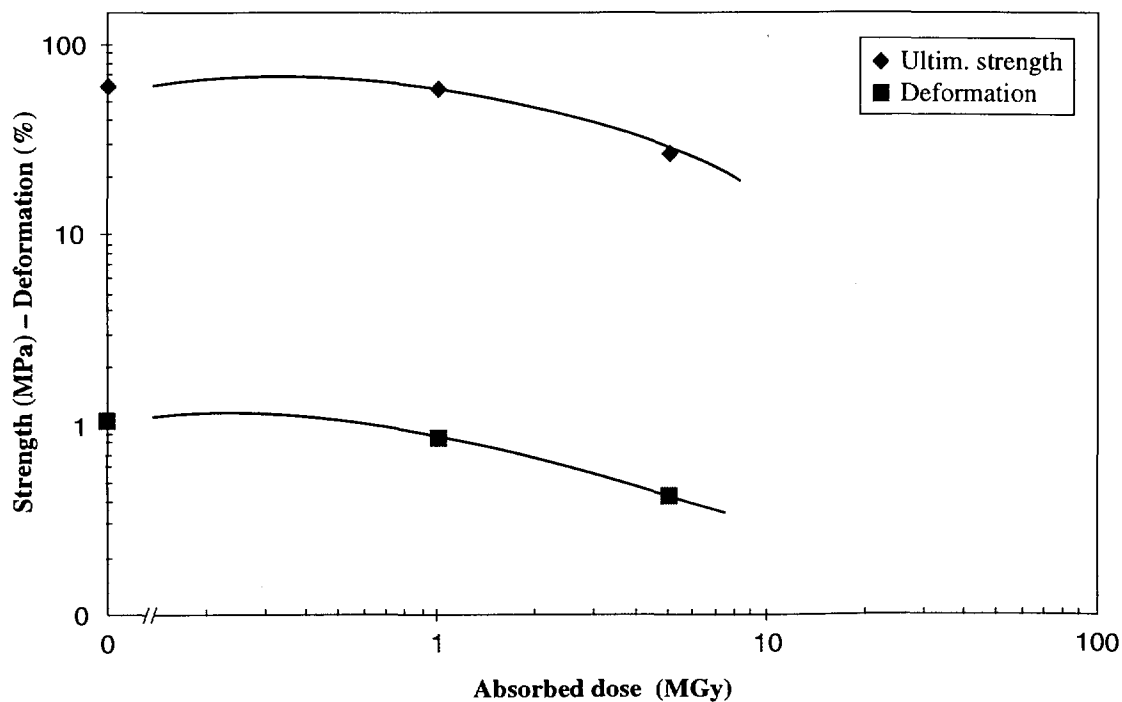

Material: **Epoxy + glass fibres**
 Type: **Vetresit 1101**

TIS No. **R 426**

Supplier: **Micafil**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	1342±61	3.20±0.14	42.8±0.9
170	5	1282±74	3.10±0.18	43.2±1.1
170	10	1351±53	3.17±0.26	43.5±0.9
170	50	1017±65	3.44±0.29	42.7±1.6
170	100	543±132	2.18±0.32	35.8±3.8

Critical property = flexural strength

Radiation index (RI) = 7.9 at a mean dose rate of 170 kGy/h

Radiation effect on insulating resin R 426

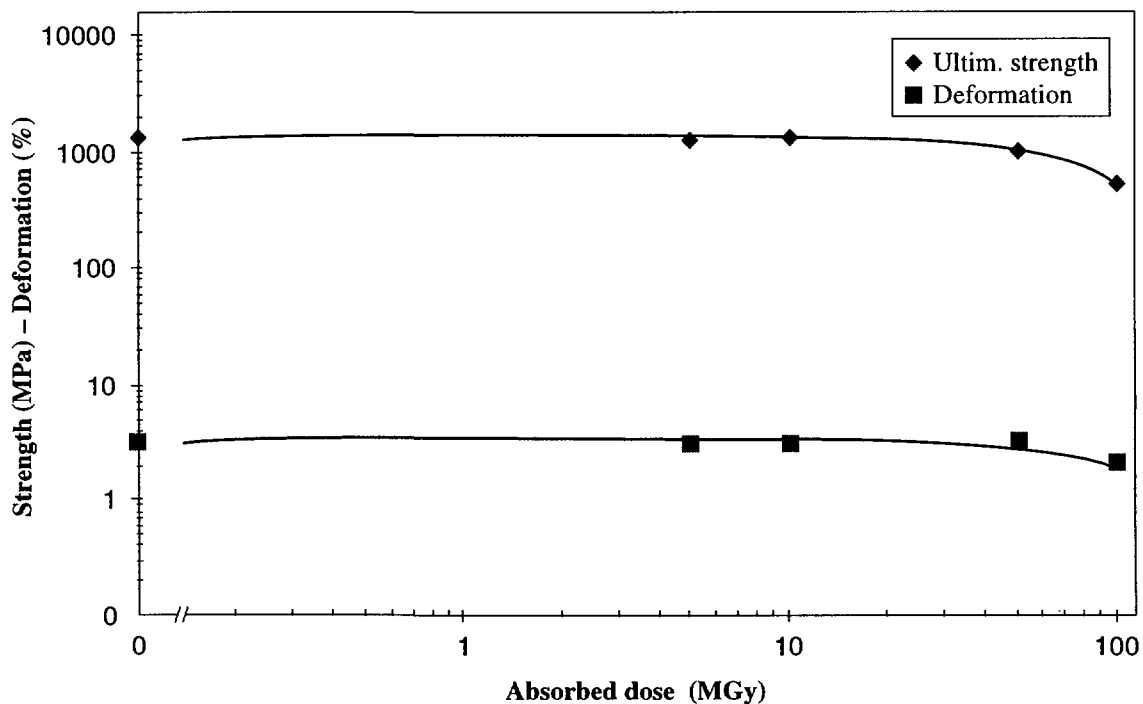

Material: **Epoxy (cycloaliphatic) + glass**
 Type: **Vetresit 312**

TIS No. **R 427**

Supplier: **Micafil**
 Remarks: **+ roving glass**


UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	547±26	1.88±0.13	31.0±1.7
170	5	533±26	1.83±0.16	31.9±1.5
170	10	529±33	1.94±0.17	31.2±0.8
170	50	266±21	1.08±0.08	27±1.5
170	100	43±7	0.56±0.26	17.8±1.8

Critical property = flexural strength

Radiation index (RI) = 7.7 at a mean dose rate of 170 kGy/h

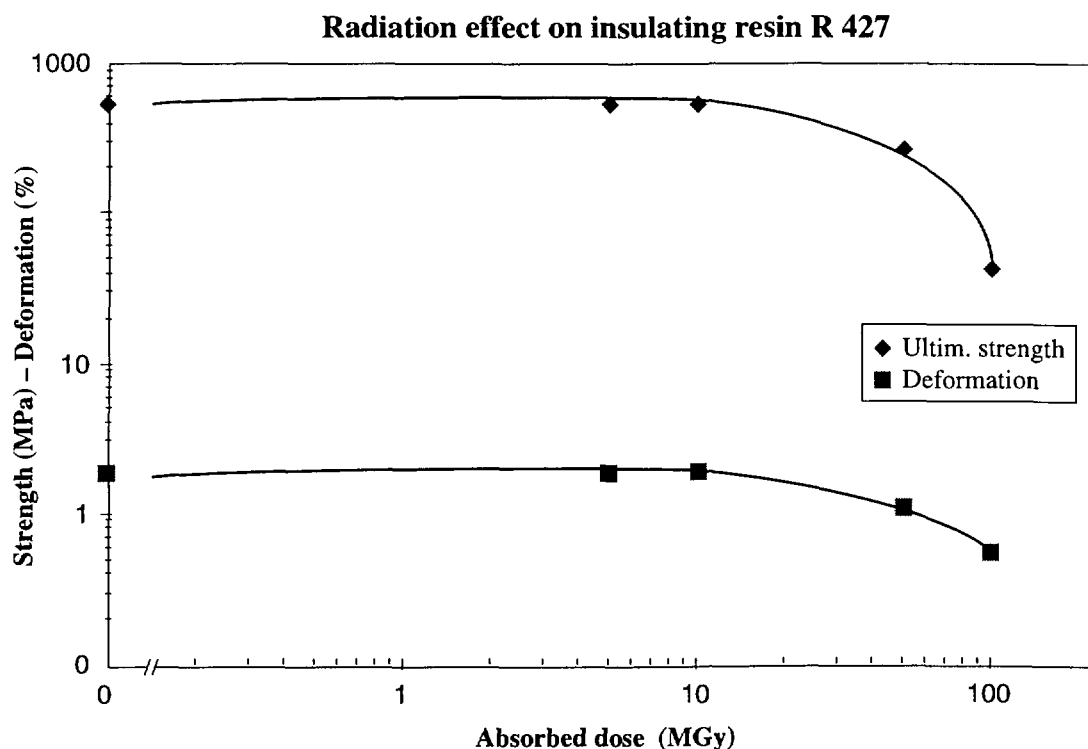

Material: **Epoxy (cycloaliphatic) + glass**
 Type: **Vetresit 300**

TIS No. **R 428**

Supplier: **Micafil**
 Remarks: **+ glass mat**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	388±11	2.33±0.06	18.8±0.4
170	5	359±18	2.29±0.14	18.1±1
170	10	386±21	2.47±0.13	18.1±1
170	50	284±12	2.06±0.05	17.8±0.5
170	100	178±7	1.48±0.25	15.7±1.1

Critical property = flexural strength

Radiation index (RI) = 7.9 at a mean dose rate of 170 kGy/h

Radiation effect on insulating resin R 428

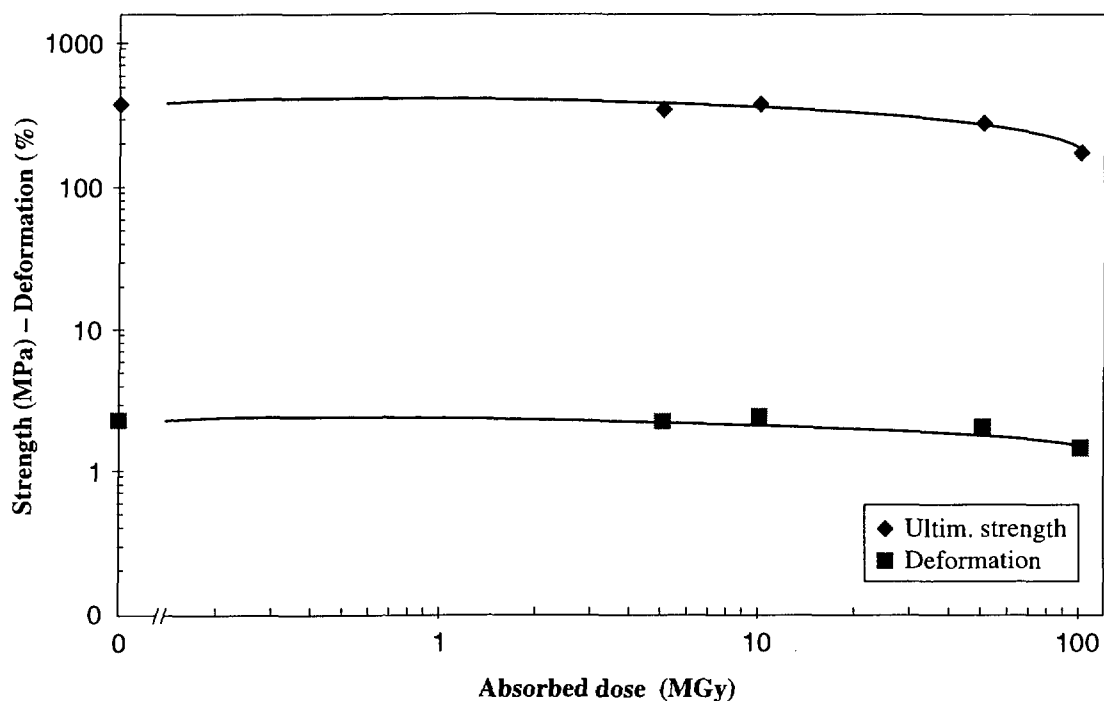

Material: **Epoxy resin (based on Bisphenol A)**
 Type: **Durotenax Art. 521-02**

TIS No. **R 433**

Supplier: **Isola**
 Remarks: **Bisphenol A + quartz-powder**

UL 94: **n.m.**
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	141$\pm$8	1.58$\pm$0.11	10.1$\pm$0.6
220	5.2	119$\pm$4	1.24$\pm$0.05	10.4$\pm$0.6
220	10	114$\pm$3	1.1$\pm$0.1	11.2$\pm$0.5
220	30	78$\pm$2	0.79$\pm$0.02	10.4$\pm$0.4

Critical property = deformation

Radiation index (RI) = 7.5 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 433

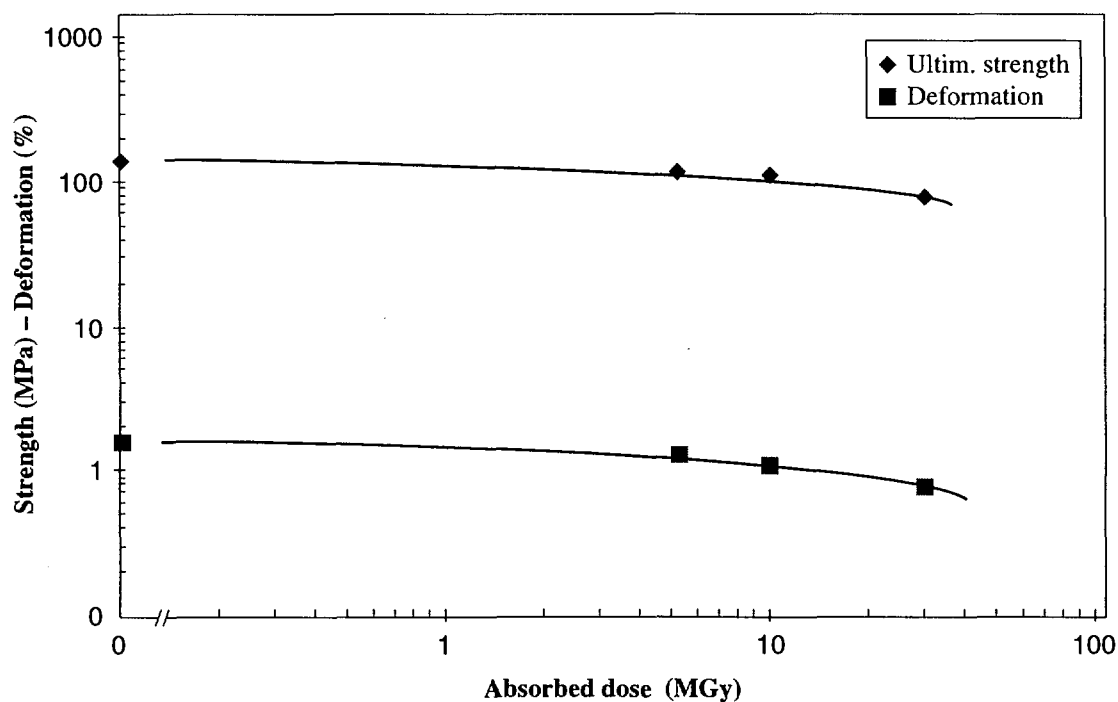

Material: **Epoxy resin (based on Bisphenol A)
Type + Methyl Hexahydrophthal Anhydride**

TIS No. **R 434**

Supplier: **Elin Union**
Remarks: **Dipole for SPS-LEP transfer lines**

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	78$\pm$22	2.2$\pm$0.5	3.6$\pm$0.5
0.1	1	47$\pm$9	1.5$\pm$0.2	3.0$\pm$0.3
170	5.2	76$\pm$15	2.2$\pm$0.4	3.6$\pm$0.2
170	10	57$\pm$4	1.6$\pm$0.1	3.5$\pm$0.1

Critical property = flexural strength

Radiation index (RI) = > 7 at a mean dose rate of 170 kGy/h

Radiation index (RI) = > 6 at a mean dose rate of 100 Gy/h

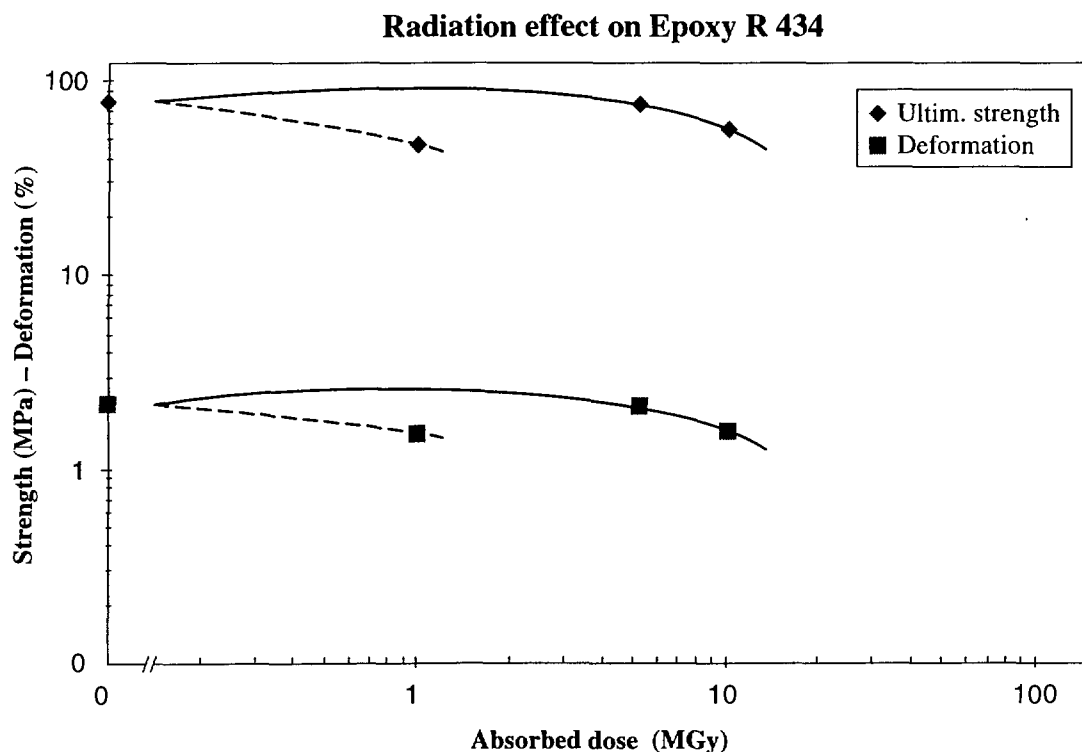

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy moulding compound**
 Type: **Neonit EG 61**

TIS No. **R 437**

Supplier: **Ciba-Geigy**
 Remarks: **not cured**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	92.9±2.7	1.03±0.11	10.8±1
220	5	86.8±14.4	0.88±0.17	11.4±0.4
220	10	89.6±11.4	0.85±0.11	12.2±0.6
220	30	55.8±8.7	0.51±0.08	12.7±0.3
220	100	39.9±6.9	0.39±0.07	11.4±0.2

Critical property = deformation

Radiation index (RI) = 7.5 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 437

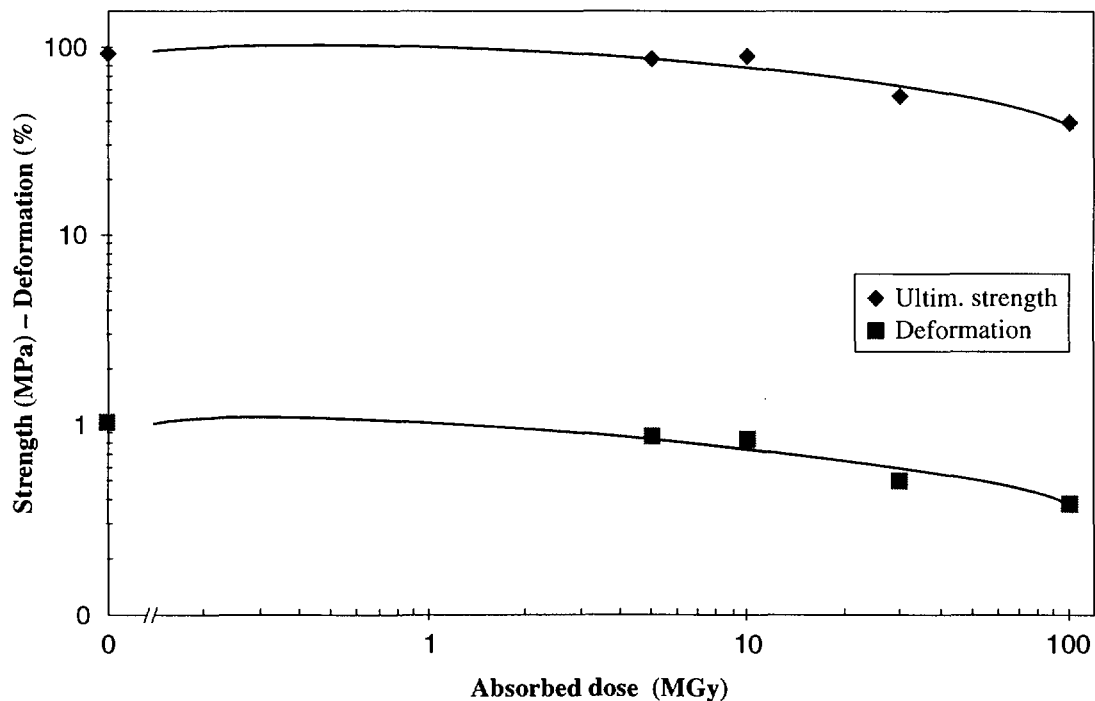

Material: **Epoxy resin SIB 3309 + tape**
 Type: **tape: Samicapor 326.95-47X**

TIS No. **R 460**

Supplier: **Isola**
 Remarks: **LEP-QP insulations based on EPN**
1138 from Ciba-Geigy

UL 94: **n.m.**
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	117$\pm$8	0.54$\pm$0.08	31.7$\pm$1.6
220	3	110$\pm$6	0.49$\pm$0.07	31.9$\pm$2.1
220	10	87$\pm$21	0.42$\pm$0.06	27.4$\pm$6.1
220	30	48$\pm$12	0.5$\pm$0.1	15.0$\pm$2.5
220	100	46$\pm$6	0.57$\pm$0.06	11.2$\pm$1.9

Critical property = flexural strength

Radiation index (RI) = 7.3 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 460

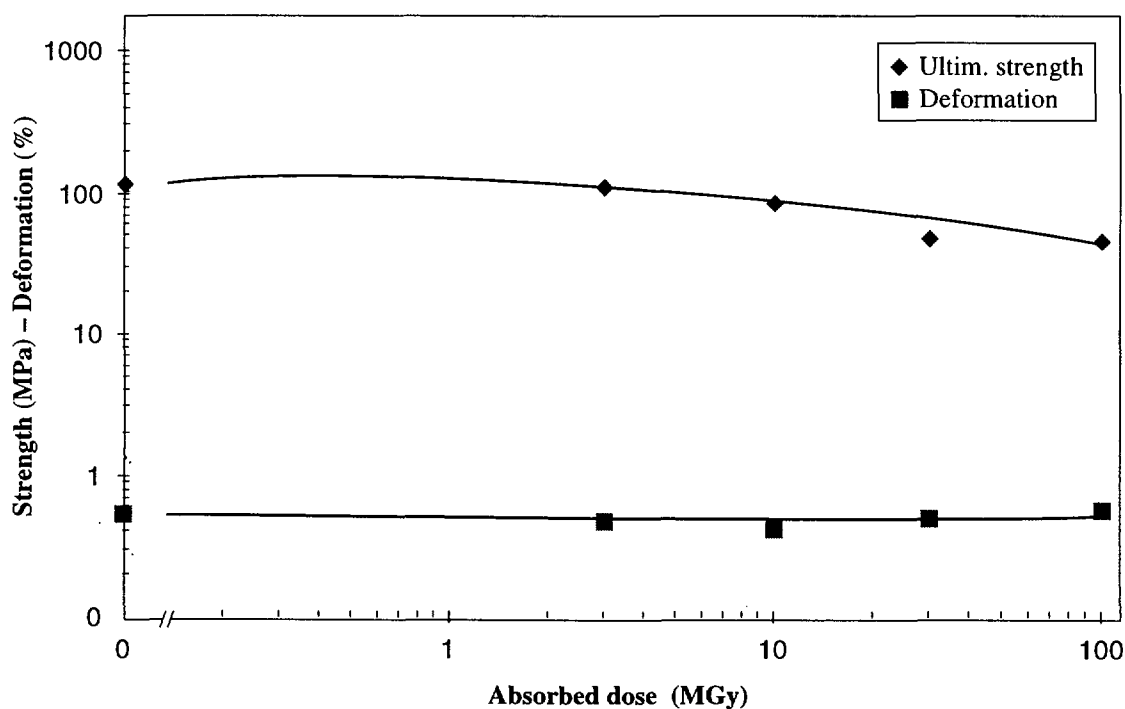

Material: **Epoxy resin SIB 3309 + tape**
 Type **tape: Samicapor 326.96-86X**

TIS No. **R 461**

Supplier: **Isola**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	163±11.2	0.52±0.08	41.4±1.7
220	3	159±13.5	0.51±0.05	40.2±2.2
220	10	135±13.0	0.52±0.07	36.2±1.8
220	30	104±10.0	0.69±0.05	19.4±5.8
220	100	85±3.0	0.58±0.15	16.9±2.5

Critical property = flexural strength

Radiation index (RI) = > 8 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 461

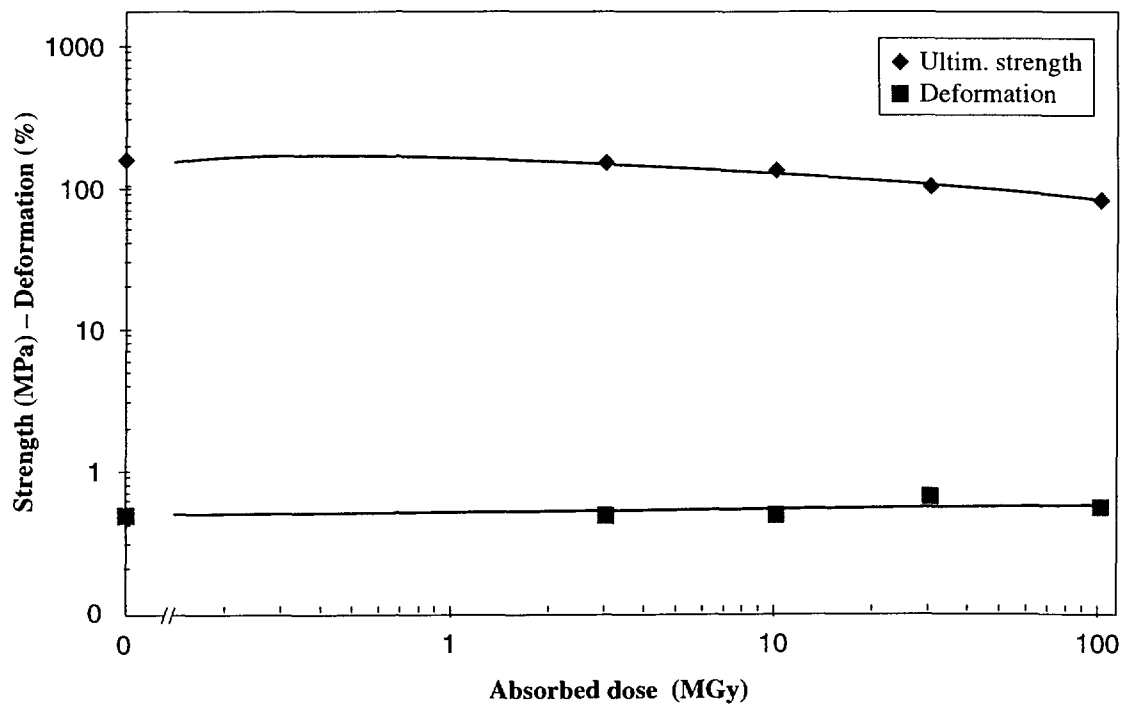

Material: **Epoxy resin + glass fabric**
 Type **G-Etronax EP 11**

TIS No. **R 465**

Supplier: **Elektro-Isola**
 Remarks: **insulations for the dipoles in LEP**

UL 94: **n.m.**
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	388±23	2.28±0.11	18.7±0.5
220	1	413±31	2.34±0.16	20.0±1.0
220	3	418±21	2.35±0.12	20.9±1.8
220	5	418±30	2.34±0.08	20.0±1.0
220	30	383±11	2.2±0.1	21.9±0.9

Critical property = none

Radiation index (RI) = > 7.5 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 465

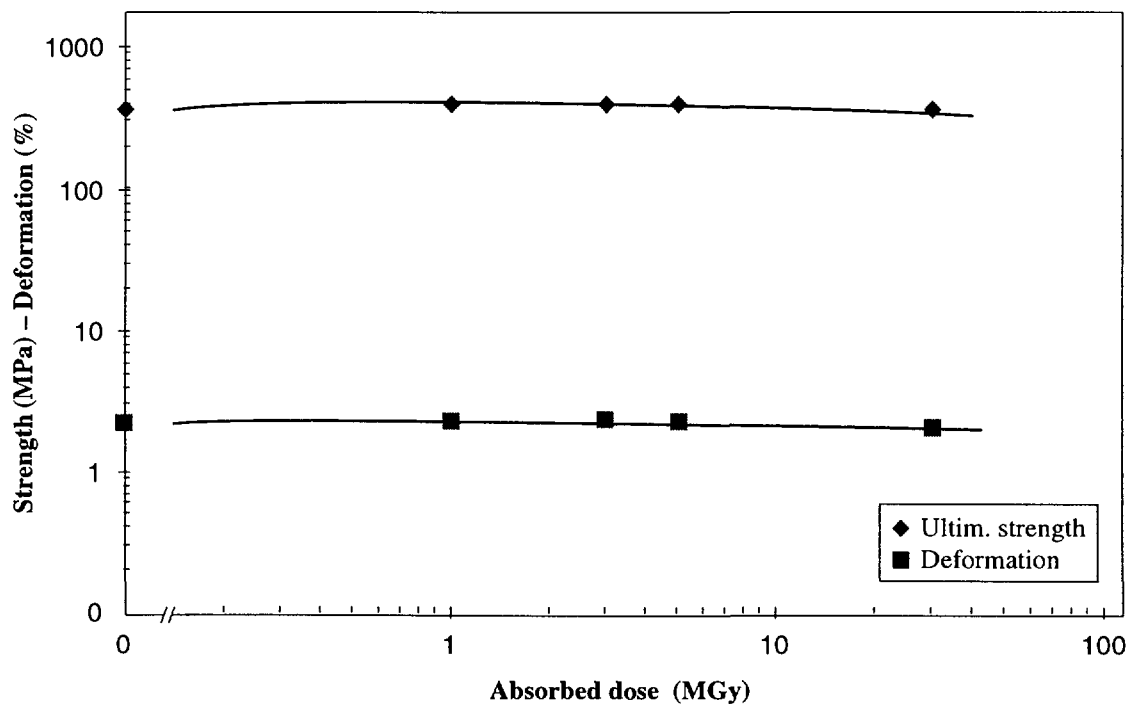

Material: **Epoxy moulding compound**
 Type **MY 790 + HY 1102BD**

TIS No. **R 466**

Supplier: **Ciba-Geigy**
 Remarks: **via Elin Union**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	84±19	2.24±0.56	3.91±0.25
0.1	1	69±15	1.82±0.35	3.87±0.04
1	3	43±8	1.21±0.23	3.74±0.11
220	10	41±9	1.16±0.24	3.64±0.08
220	30	12±2	0.34±0.05	3.78±0.23
220	50	9±3	0.25±0.08	3.6±0.4

Critical property = flexural strength

Radiation index (RI) = 6.9 at a mean dose rate of 220 kGy/h

Radiation index (RI) = 6.5 at a mean dose rate of 1000 Gy/h

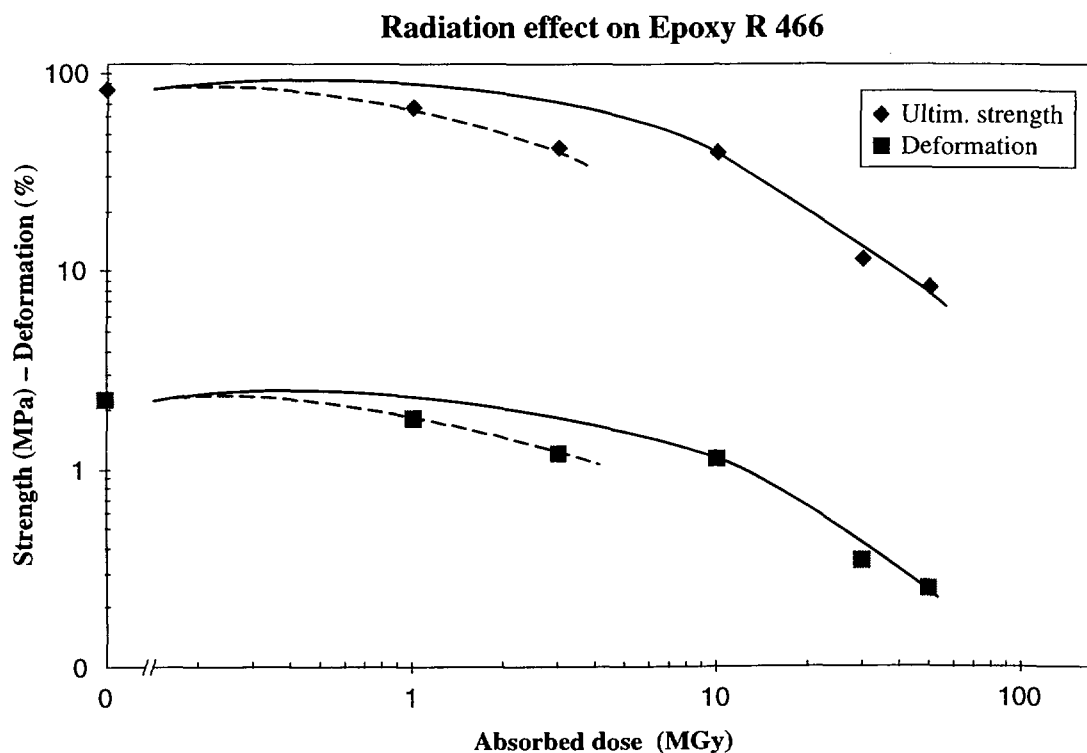

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy MY 790 + HY 1102 BD**
 Type **= R 466 + Mica + glass fibres**

TIS No. **R 467**

Supplier: **Ciba-Geigy**
 Remarks: **via Elin Union**

UL 94: **n.m.**
 LOI:

This resin is used for the AA magnets

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	545±9	2.87±0.08	23.0±0.1
1	3	463±28	2.54±0.08	21.8±1.5
220	10	490±35	2.7±0.1	22.0±1.5
1	12	398±31	2.42±0.04	20.9±1.2
220	30	371±19	2.0±0.1	22.7±1.1
220	50	250±12	1.56±0.35	21.6±1.1

Critical property = flexural strength

Radiation index (RI) = 7.6 at a mean dose rate of 220 kGy/h

Radiation index (RI) = 7.4 at a mean dose rate of 1000 Gy/h

Radiation effect on Epoxy composite R 467

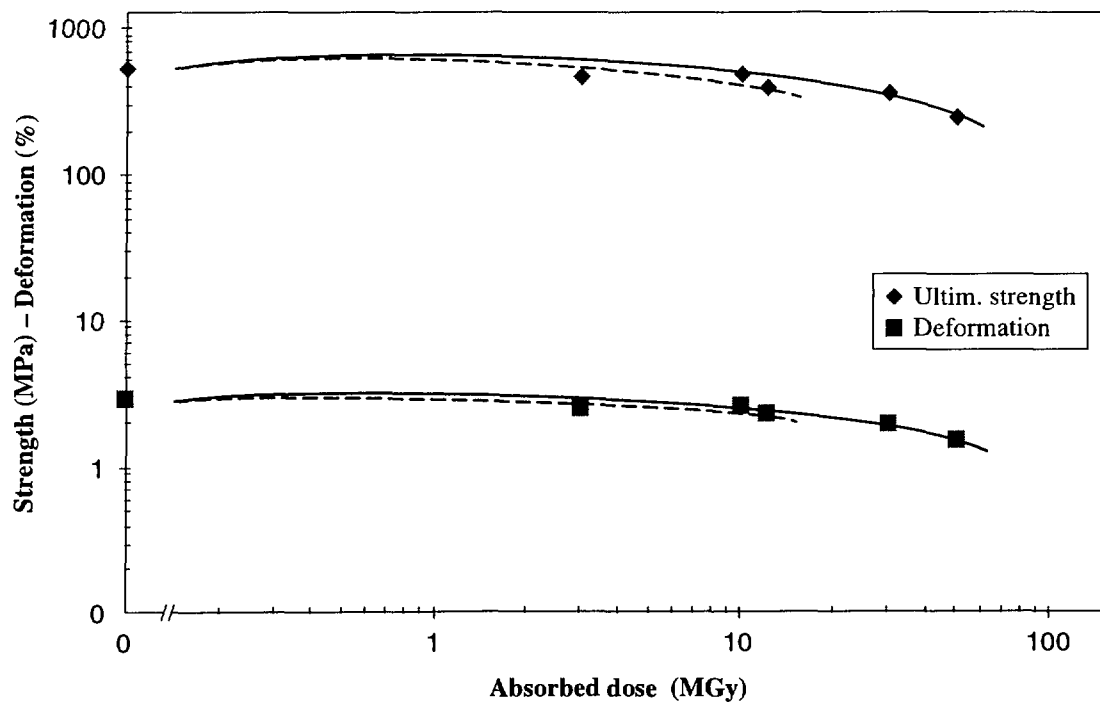

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy laminate – prepreg**
 Type: **Isopreg EP spess 0.33**

TIS No. **R 468**

Supplier: **Isovolta**
 Remarks: **Used by Ansaldo**
for LEP dipoles

UL 94: n.m.

LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Irradiation Conditions	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0		355±28	1.79±0.05	22.6±2.3
0.02	0.25	LEP	331±16	1.99±0.03	22.6±1.1
0.20	3	LEP	115±28	0.54±0.15	18.4±1.0
2	3	Co-60	432±21	2.09±0.05	22.9±0.4
220	8	reactor	446±25	2.11±0.02	23.6±1.4
2	12	Co-60	426±34	2.18±0.05	20.8±2.2
200	30	reactor	420±25	2.03±0.04	23.3±1.6
200	100	reactor	281±9	1.72±0.08	18.4±0.7

Critical property = flexural strength

Radiation index (RI) = > 8 at a mean dose rate of 200 kGy/h

Radiation index (RI) = 6.2 at a mean dose rate of 200 Gy/h

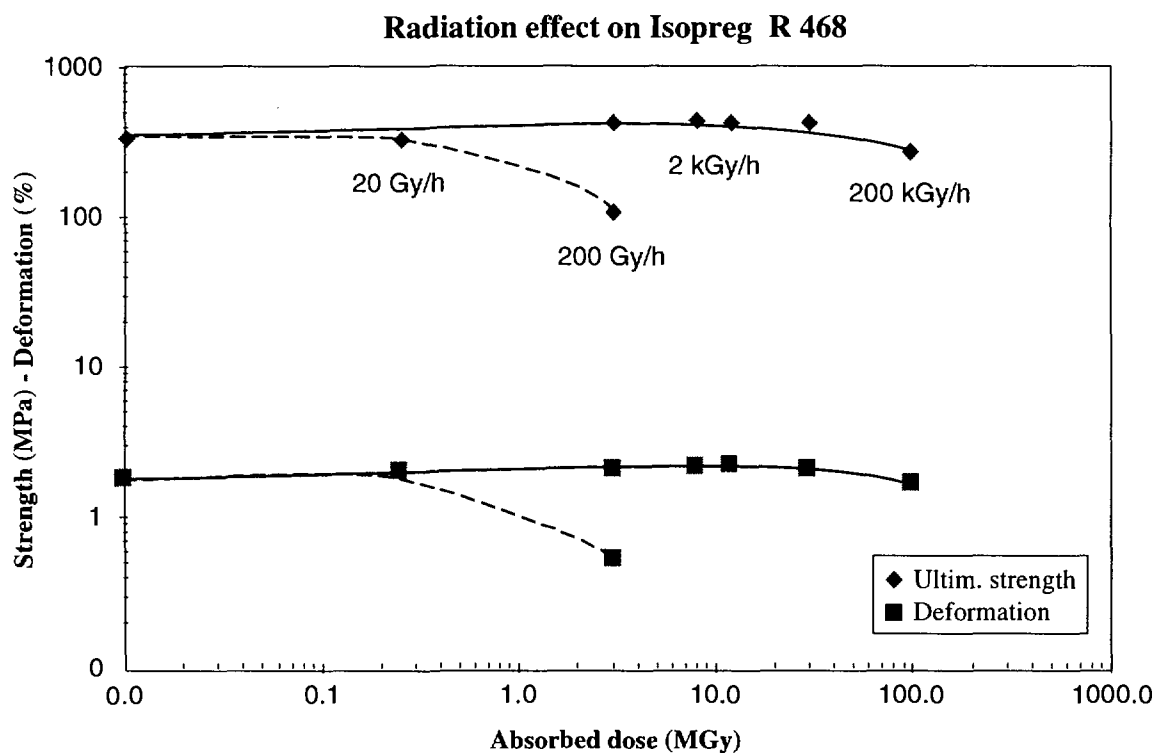

Comment: Low-dose rate irradiations — dotted lines — correspond to life irradiation in LEP.

Material: **Epoxy moulding compound**
 Type: **R112 + H 232**

TIS No. **R 502**

Supplier: **Ciba-Geigy**
 Remarks: **via L.E. Pink**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	57.6±1.8	> 12	1.57±0.05
4	5	64.7±3	> 12	1.8±0.1
220	10	49.4±9.4	9.87±4.36	1.49±0.37
220	30	16.2±4.7	1.07±0.36	1.58±0.15

Critical property = deformation

Radiation index (RI) = ~ 7.1 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 502

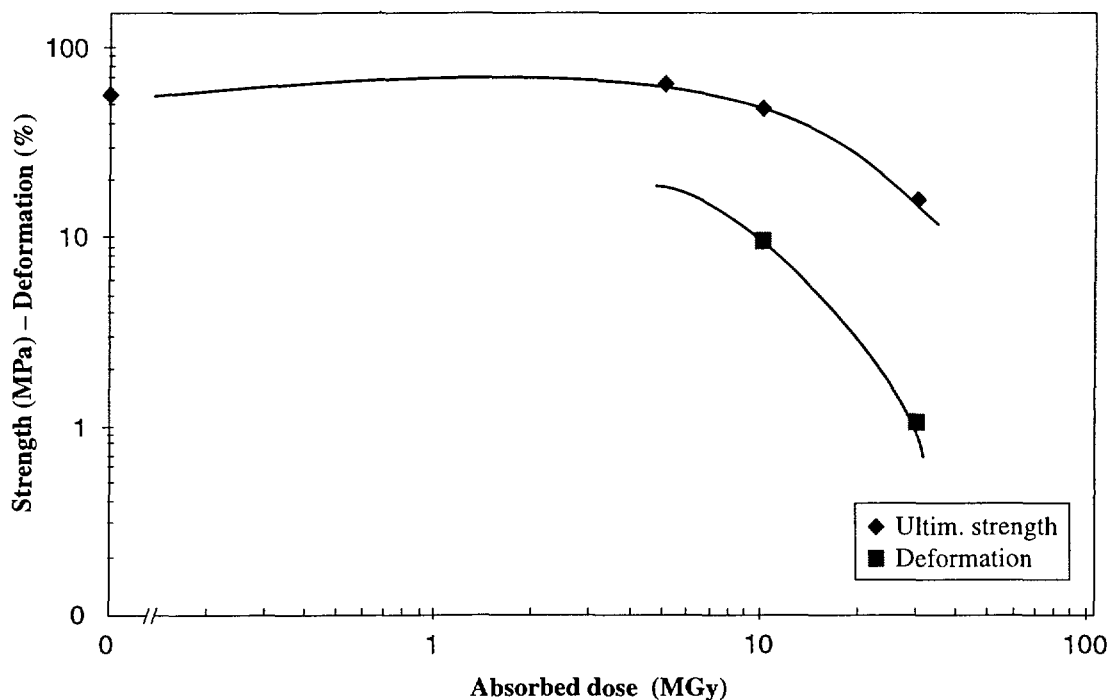

Material: **Epoxy laminate + glass**
 Type **ACO 1 + GLASS A**

TIS No. **R 506**

Supplier: **Ciba-Geigy**
 Remarks: **via Ansaldo**
VPI product


UL 94: **n.m.**
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	408±15	1.96±0.04	23±1.1
220	3	388±11	2.06±0.24	23±0.9
220	10	393±13	2.02±0.07	24±0.9
250	30	154±8	0.92±0.03	21.2±2.1
10	30.4	44±4	0.73±0.04	6.8±0.4
220	100	43±11	0.45±0.07	12.6±3.4

Critical property = flexural strength

Radiation index (RI) = 7.3 at a mean dose rate of 220 kGy/h

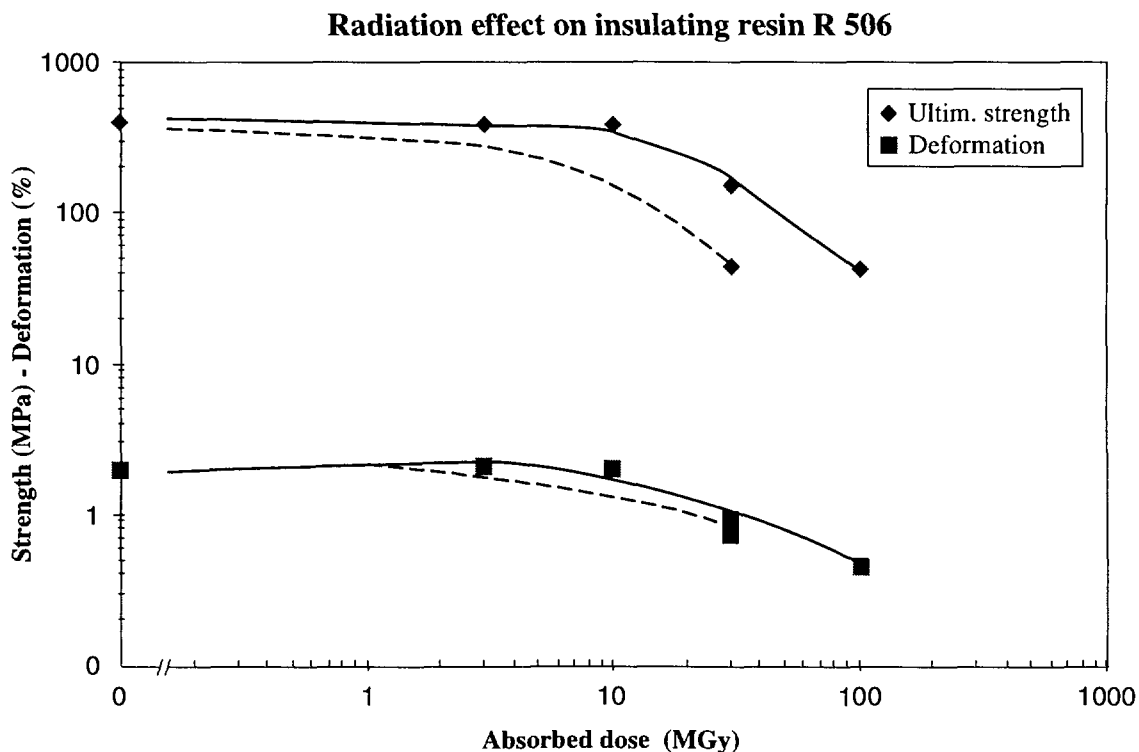

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy laminate + glass**
 Type: **ACO 2 + GLASS A**

TIS No. **R 507**

Supplier: **Ciba-Geigy**
 Remarks: **via Ansaldo**
VPI product

UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	431$\pm$25	2.47$\pm$0.12	22.1$\pm$1.78
220	3	409$\pm$18	2.50$\pm$0.24	21.2$\pm$1.78
220	10	431$\pm$10	2.11$\pm$0.13	23.4$\pm$1.16
220	30	243$\pm$23	1.66$\pm$0.13	19.5$\pm$2.07
10	30.4	150$\pm$14	0.87$\pm$0.17	18.9$\pm$1.92
220	100	80$\pm$16	0.81$\pm$0.10	15$\pm$3.03

Critical property = flexural strength

Radiation index (RI) = 7.4 at a mean dose rate of 220 kGy/h

Radiation index (RI) = 7.0 at a mean dose rate of 10 kGy/h

Radiation effect on insulating resin R 507

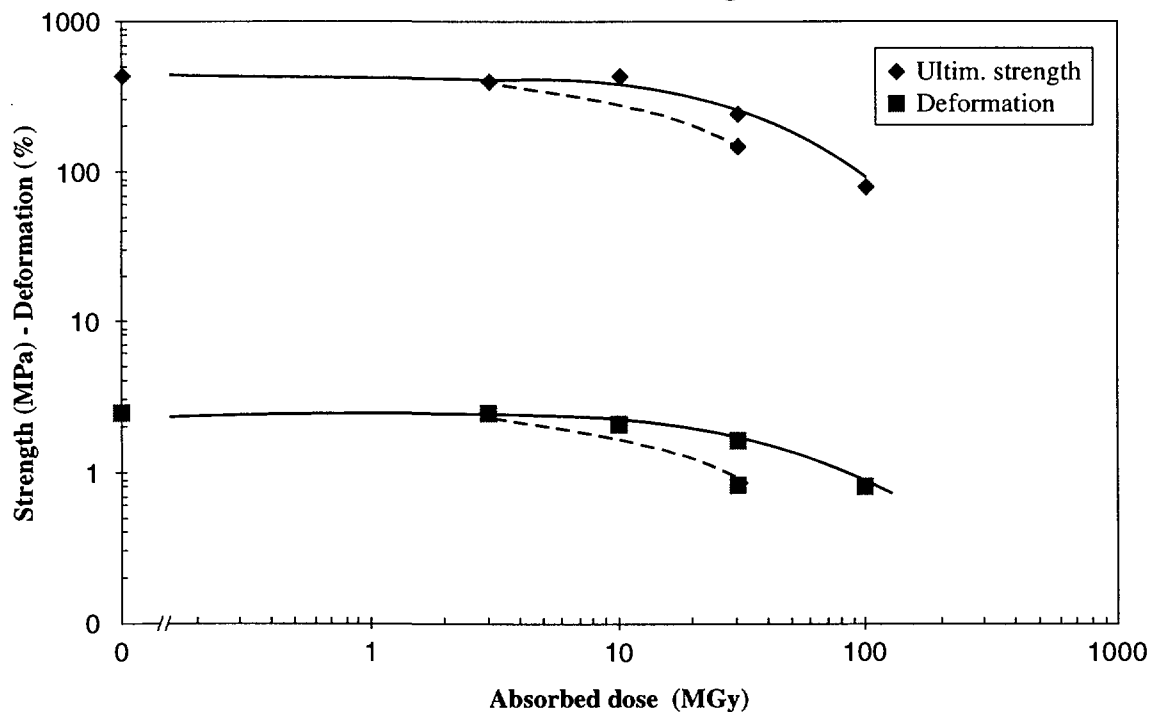

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy laminate + glass**
 Type: **ACO 1+ GLASS B**

TIS No. **R 508**

Supplier: **Ciba-Geigy**
 Remarks: **via Ansaldo**
VPI product

UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	405±13.8	2.05±0.10	23.1±0.7
220	3	406±19.9	2.06±0.22	23.0±0.9
220	10	383±20.2	1.83±0.12	23.3±0.9
220	30	213±11.8	1.52±0.15	19.8±0.7
10	30	87±3.1	0.61±0.08	15.6±0.6
220	100	46±9.0	0.41±0.06	13.6±1.9

Critical property = flexural strength

Radiation index (RI) = 7.5 at a mean dose rate of 220 kGy/h

Radiation index (RI) = 6.2 at a mean dose rate of 10 kGy/h

Radiation effect on insulating resin R 508

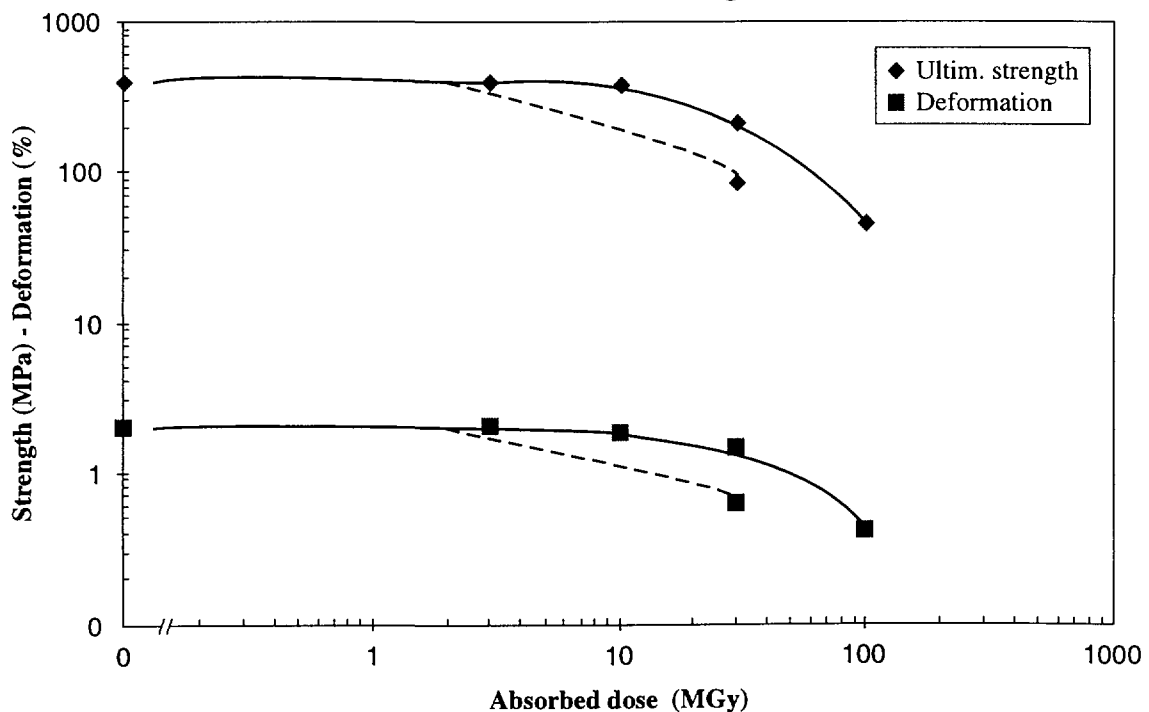

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy laminate + glass**
 Type **ACO 2+ GLASS B**

TIS No. **R 509**

Supplier: **Ciba-Geigy**
 Remarks: **via Ansaldo**
VPI product

UL 94: **n.m.**
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	459±28	2.06±0.13	24.1±1.6
220	3	465±19	2.09±0.15	24.4±0.5
220	10	439±29	2.09±0.06	25.8±0.9
220	30	258±7	1.84±0.06	18.8±0.7
10	30.4	28.2±0.4	0.77±0.08	19.1±0.3
220	100	74.4±5	0.75±0.10	14.3±1.3

Critical property = flexural strength

Radiation index (RI) = 7.6 at a mean dose rate of 220 kGy/h

Radiation index (RI) = 6 at a mean dose rate of 10 kGy/h

Radiation effect on insulating resin R 509

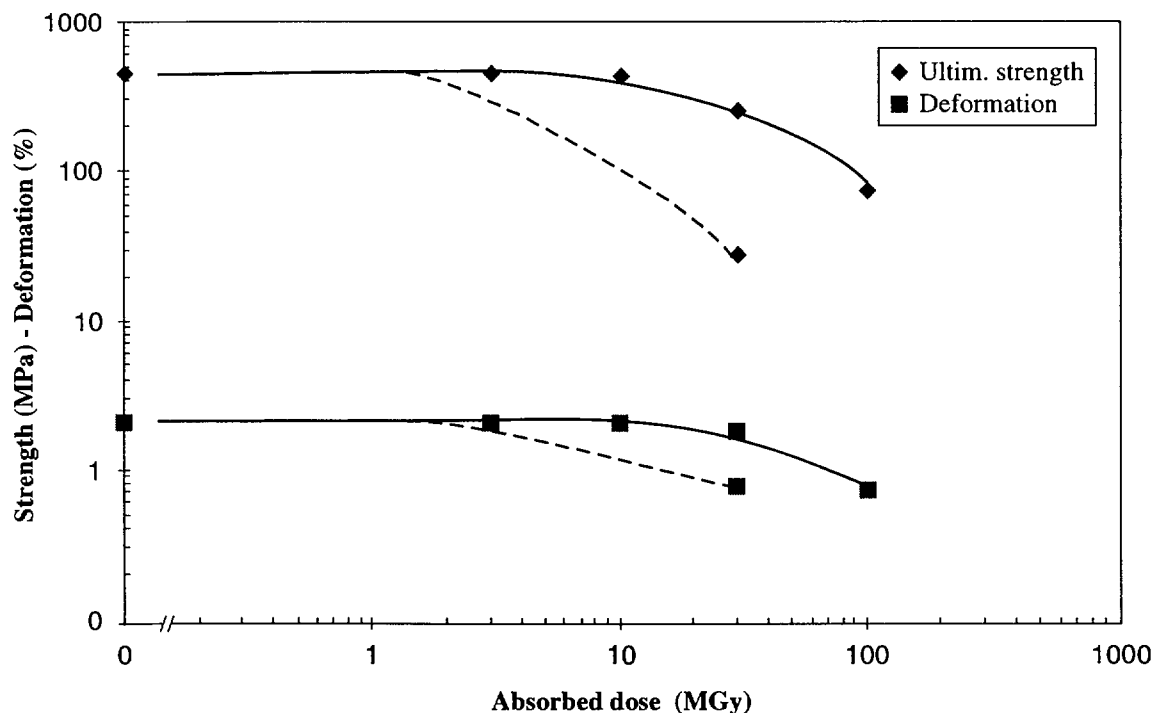

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy**
 Type: **Scotchcast 9**

Supplier: **3M**
 Remarks: **mid-flexibility (cold)**

TIS No. **R 511**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	34.3±3.7	> 12	1.5±0.2
200	3.4	26.4±3.2	> 12	1.5±0.1
3	5	9.5±2.1	> 12	0.7±0.1
3	10	10.4±1.1	> 12	1.0±0.1
200	10	31.1±4.7	> 12	1.9±0.1
200	29	24.6±3.5	2.52±1.84	2.1±0.5

Critical property = deformation for short term and flexural strength for long term

Radiation index (RI) = 7 at a mean dose rate of 200 kGy/h

Radiation index (RI) = 6 at a mean dose rate of 3000 Gy/h

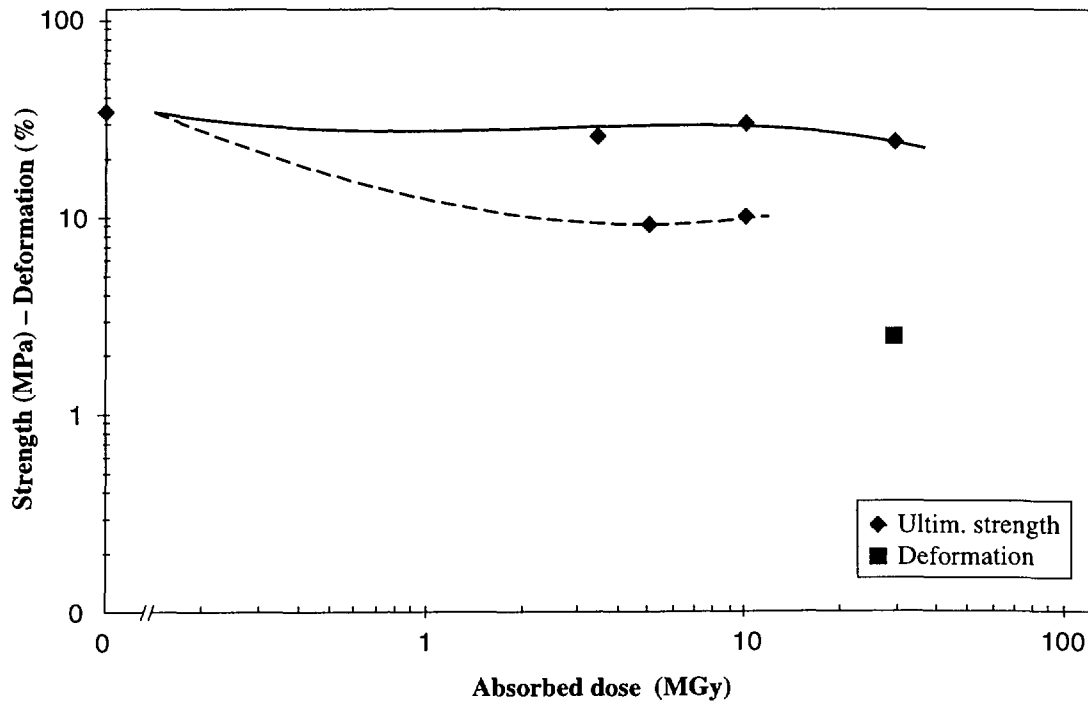Radiation effect on Epoxy R 511


Comment: Dotted line corresponds to long-term irradiation.

Material: **Epoxy**
Type **Scotchcast 281**

TIS No. **R 512**

Supplier: **3M**
Remarks: **mid-flexibility (cold)**

UL 94: **n.m.**
LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	32.9±0.6	>12	2.3±0.1
200	3.4	65.2±3.4	1.5±0.1	5.2±0.2
3	5	58.0±4.4	1.5±0.2	4.7±0.3
3	10	47.4±7.9	1.2±0.3	4.8±0.1
200	10	47.6±2.6	1.0±0.1	5.5±0.1
200	29	25.3±5.8	0.8±0.2	4.0±0.2

Critical property = deformation

Radiation index (RI) = < 6.5 at a mean dose rate of 200 kGy/h

Radiation index (RI) = < 6.5 at a mean dose rate of 3000 Gy/h

Radiation effect on Epoxy R 512

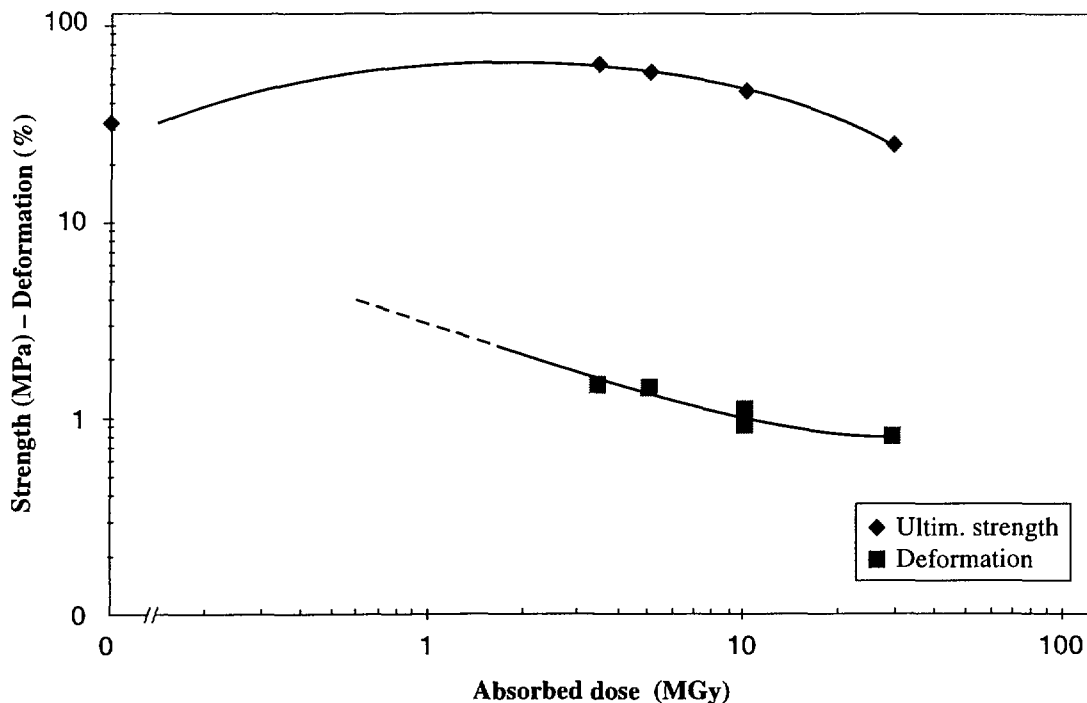

Material: **Epoxy**
Type: **Scotchcast 804**

TIS No. **R 514**

Supplier: **3M**
Remarks: rigid (cold)
contains chlorine

UL 94: n.m.
LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	90.5±9.6	5.4±1.5	2.4±0.1
200	3.4	19.6±0.3	0.9±0.3	2.3±0.8
3	5	8.5±0.1	0.5±0.1	1.9±0.1

Critical property = flexural strength

Radiation index (RI) < 6.5 at a mean dose rate of 200 kGy/h

Radiation index (RI) < 6.7 at a mean dose rate of 3000 Gy/h

Radiation effect on Epoxy R 514

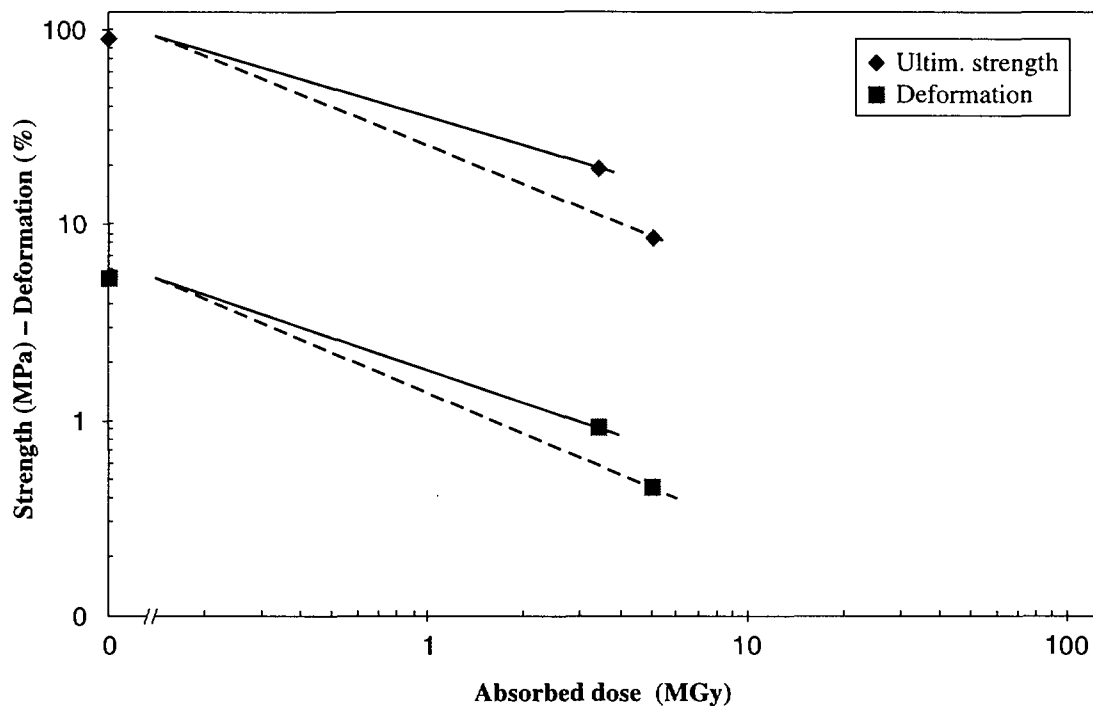

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy**
Type: **Scotchcast 824**

TIS No. **R 515**

Supplier: **3M**
Remarks: **rigid (cold)**

UL 94: n.m.
LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	54.6±3.1	1.53±0.11	5.6±0.6
200	3.4	57.5±2.2	0.94±0.03	7.5±0.4
3	5	41.0±3.4	1.2±0.1	5.0±0.3
3	10	21.5±2.7	0.44±0.03	6.0±0.4
200	10	39.3±10.6	0.6±0.2	8.2±0.6
200	29	16.6±5.2	0.3±0.1	6.7±0.8

Critical property = deformation

Radiation index (RI) = 6.8 at a mean dose rate of 200 kGy/h

Radiation index (RI) = 6.8 at a mean dose rate of 3000 Gy/h

Radiation effect on Epoxy R 515

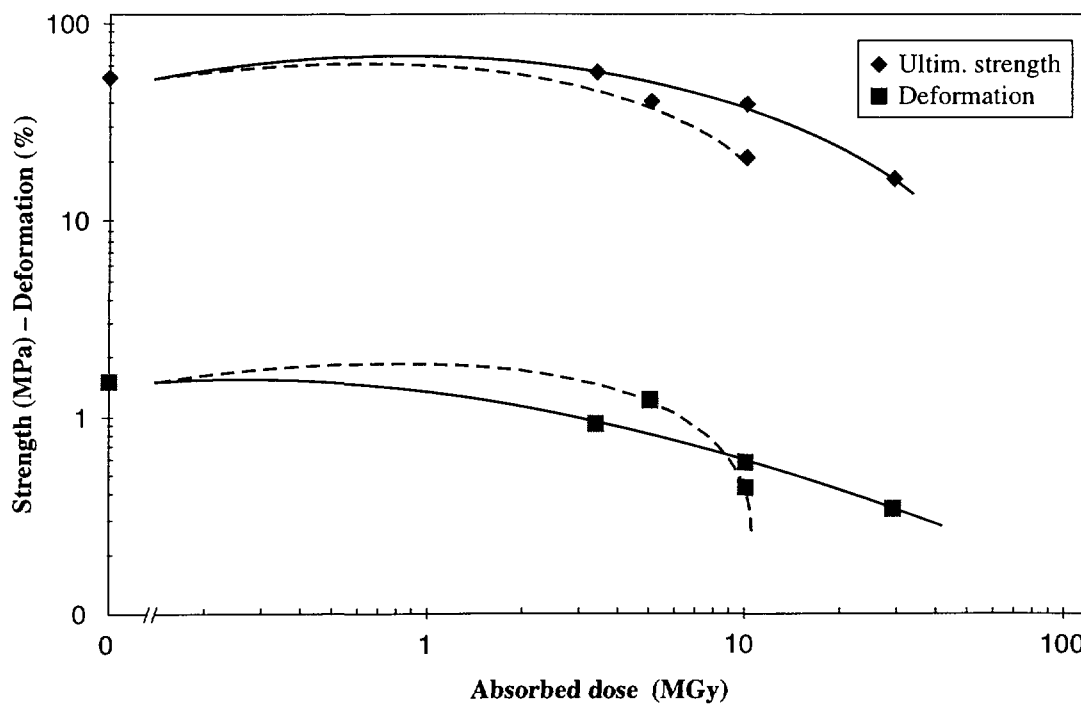

Comment: Dotted lines correspond to long-term irradiation.

Material: **Epoxy A + glass + Kevlar**
 Type **Novolac resin + fibres**

TIS No. **R 525**Supplier: **Isovolta**

UL 94: n.m.

Remarks: **prepreg for LHC magnets for coil insulation**

LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	377$\pm$9	2.05$\pm$0.02	33.3$\pm$1.4
240	3	289$\pm$8	1.62$\pm$0.07	30.3$\pm$0.8
1	8	337$\pm$19	2.05$\pm$0.21	29.4$\pm$0.9
210	10	169$\pm$21	0.95$\pm$0.11	27.1$\pm$2.4
210	50	280$\pm$5	1.58$\pm$0.06	29.0$\pm$1.0
220	100	139$\pm$42	1.68$\pm$1.92	26.3$\pm$3.9

Critical property = flexural strength

Radiation index (RI) = 6.9 at a mean dose rate of 210 kGy/h

Radiation index (RI) > 6.9 at a mean dose rate of 1000 Gy/h

Radiation effect on Epoxy R 525

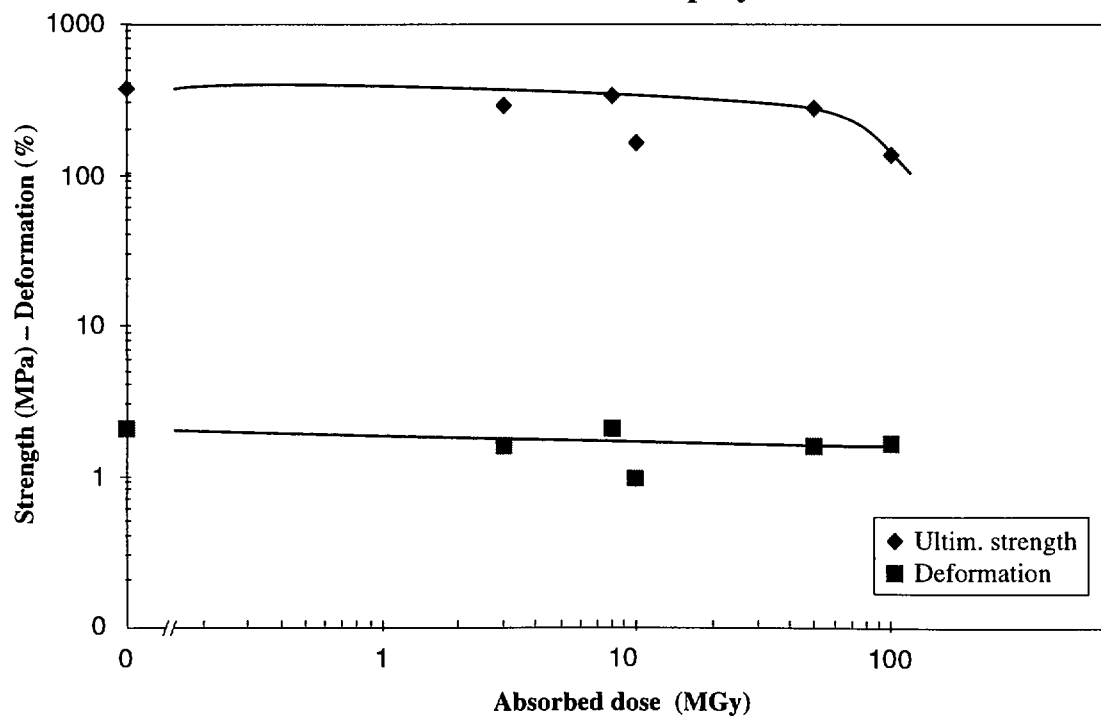

Material: **Epoxy resin**
 Type: **Vetronite**

Supplier: **Von Roll Isola**
 Remarks: **grade tube 64770**

TIS No. **R 539**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	363±33	2.10±0.09	20.9±1.3
220	5	280±8	1.92±0.06	18.7±1.4
220	10	342±20	1.90±0.10	21.9±0.3
230	50	264±8	1.77±0.08	20.1±0.8
230	100	206±20	1.31±0.07	19.9±1.3

Critical property = flexural strength

Radiation index (RI) > 7.7 at a mean dose rate of 220 kGy/h

Radiation effect on Epoxy Vetronite R 539

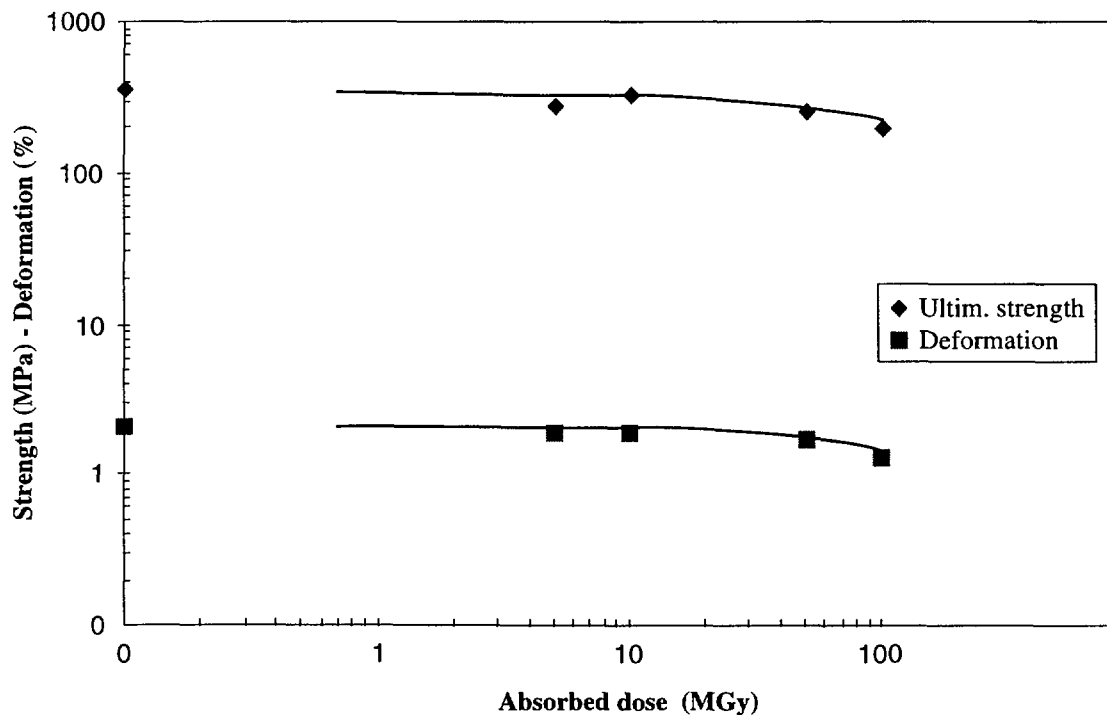

Material: **Epoxy resin + mineral filler
+ glass mica + Dacron**
Type **Samicatherm**

TIS No. **R 540**

Supplier: **Ansaldo**
Remarks: **conductor insulation for the LHC dump**

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	143±14.5	1.14±0.12	19.8±3.1
220	3	141±8.7	1.09±0.09	20.2±1.7
220	10	108±15.9	1.28±0.20	14.5±3.3
220	50	76±18.2	1.26±0.13	8±2
220	100	84±7.5	1.55±0.27	7±2

Critical property = Modulus

Radiation index (RI) = 7.6 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 540

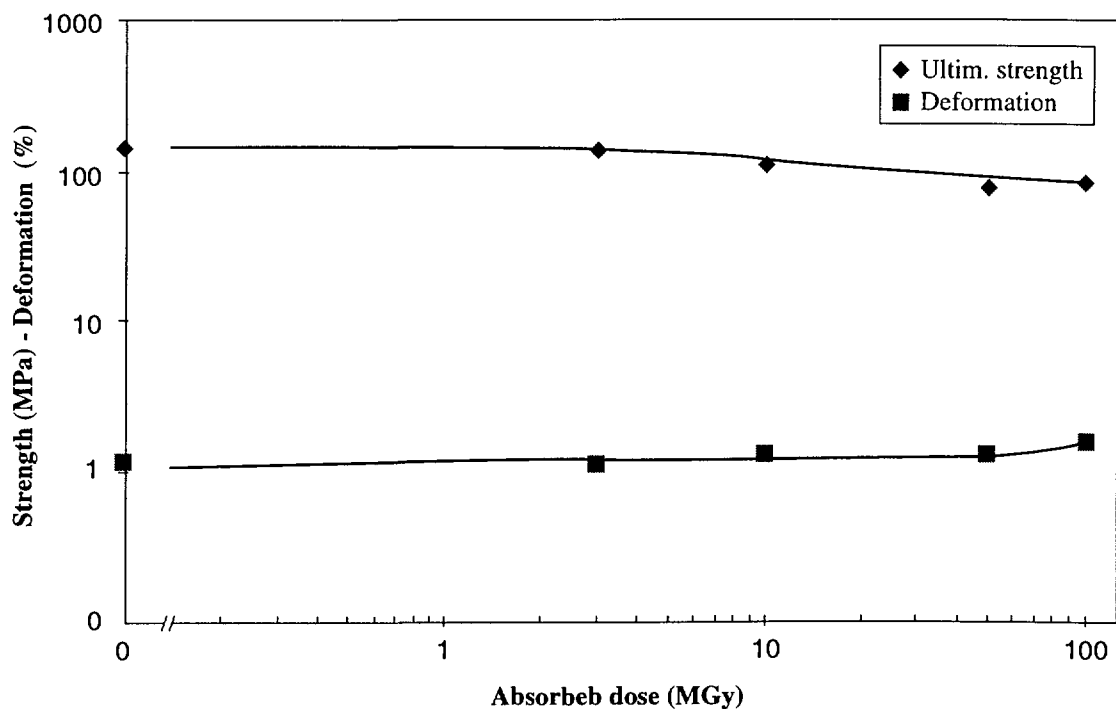

Material: **Epoxy resin**
 Type: **XNR 4153/XNH 4153**

TIS No. **R 541**

Supplier: **Ciba-Geigy (Japan)**
 Remarks: **via Ansaldo**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ε (%)	Modulus (GPa)
0	0	112 $\pm$ 3	1.18 $\pm$ 0.07	11.3 $\pm$ 0.3
220	3	84 $\pm$ 3	0.81 $\pm$ 0.04	11.6 $\pm$ 0.5
220	10	57 $\pm$ 3	0.48 $\pm$ 0.03	13.0 $\pm$ 0.6
230	30	61 $\pm$ 2	0.44 $\pm$ 0.01	15.9 $\pm$ 0.9
220	100	67 $\pm$ 2	0.46 $\pm$ 0.01	15.5 $\pm$ 0.8

Critical property = Deformation at break

Radiation index (RI) = 6.9 at a mean dose rate of 220 kGy/h

Radiation effect on Epoxy 4153 R 541

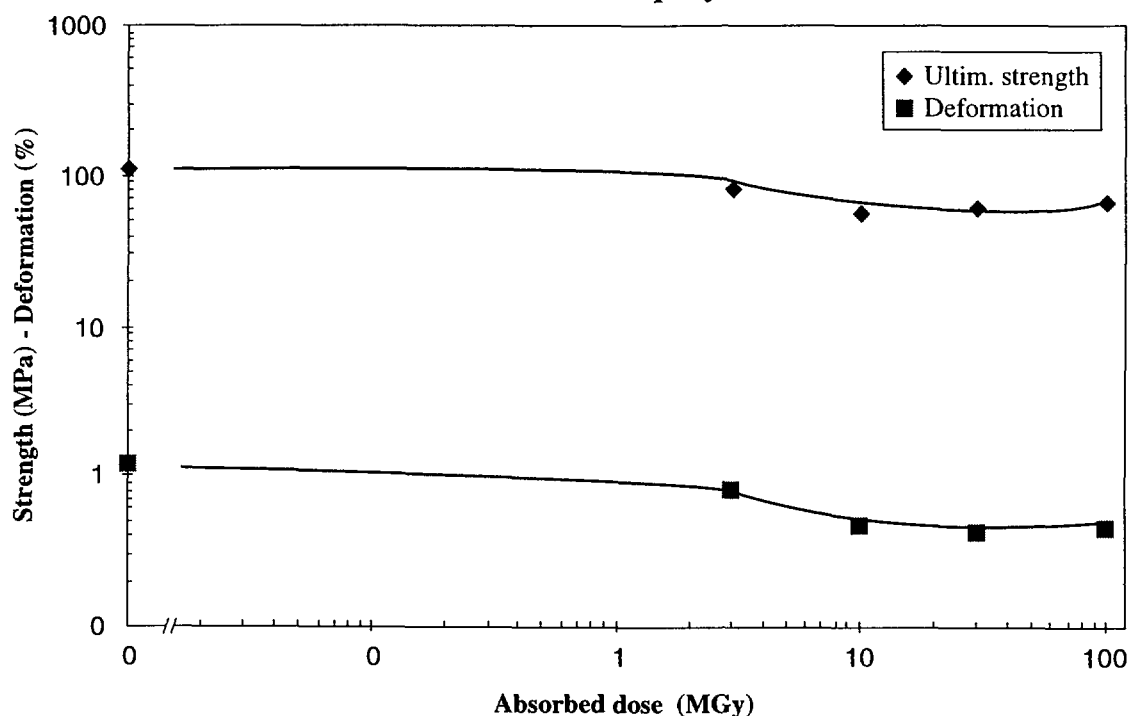

Material: **Epoxy resin**
Type **AS/37-3**

TIS No. **R 554**

Supplier: **Ciba-Geigy**
Remarks:

UL 94: n.m.
DATE: Nov-97

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	126 $\pm$ 2.2	8.35 $\pm$ 0.42	2.88 $\pm$ 0.09
4	0.5	93 $\pm$ 19.4	1.38 $\pm$ 0.44	7.79 $\pm$ 0.17
230	1	126 $\pm$ 4.1	5.82 $\pm$ 0.69	3.29 $\pm$ 0.05
230	3	48 $\pm$ 10.1	1.33 $\pm$ 0.28	3.82 $\pm$ 0.13
0.5	3	22 $\pm$ 6.3	0.26 $\pm$ 0.08	8.92 $\pm$ 0.63
230	10	4 $\pm$	0.26 $\pm$	4.30 $\pm$

Critical property = deformation

Radiation index (RI) ~ 6.1 at a mean dose rate of 230 kGy/h

Radiation index (RI) < 5.7 at a mean dose rate of 4 kGy/h

Radiation effect on Epoxy resin - R554

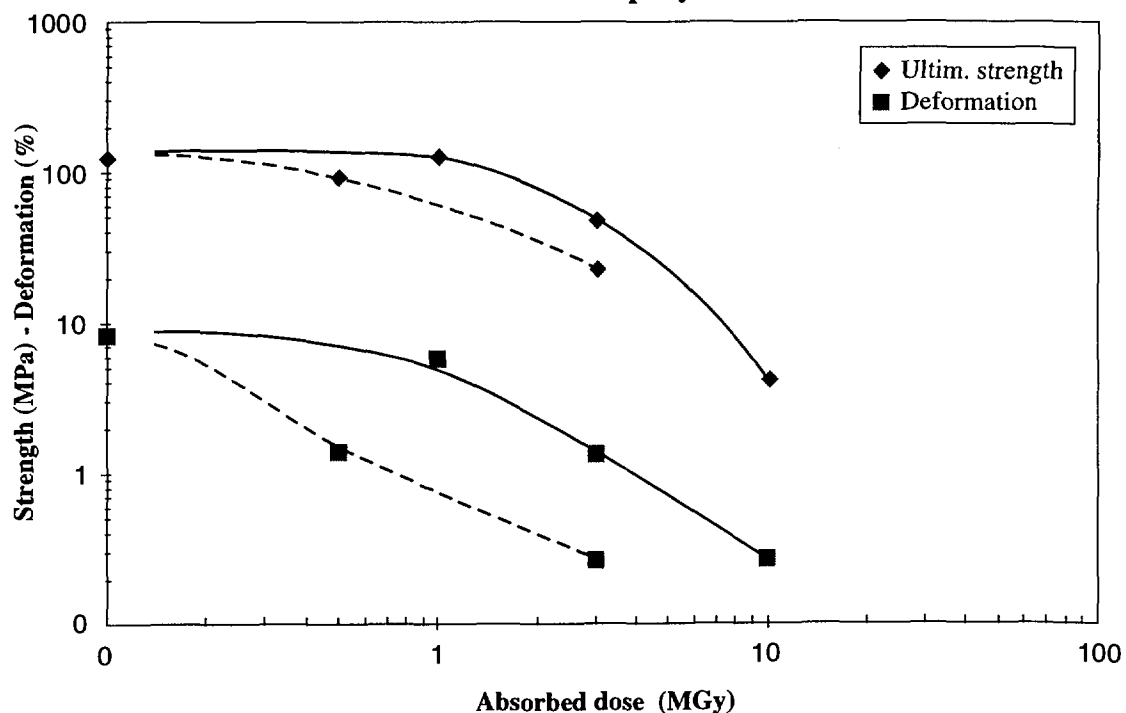

Comments: At 10 MGy, one sample was tested, the four others were broken before test.
Dotted lines correspond to long-term irradiation.

Material: **Epoxy moulding compound**
 Type: **Matramid 5292 A/B (M 5.500/1)**

TIS No. **R 557**

Supplier: **Ciba-Geigy**
 Remarks:


UL 94:
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	165±3	6.27±0.3	3.9±0.06
6	1	152±24	5.32±1.4	3.9±0.03
230	3	159±8	5.83±0.67	4.0±0.04
230	10	152±16	5.61±0.97	4.0±0.17
180	50	109±21	2.80±0.6	4.1±0.19

Critical property = deformation

Radiation index (RI) = 7.6 at a mean dose rate of 180 kGy/h

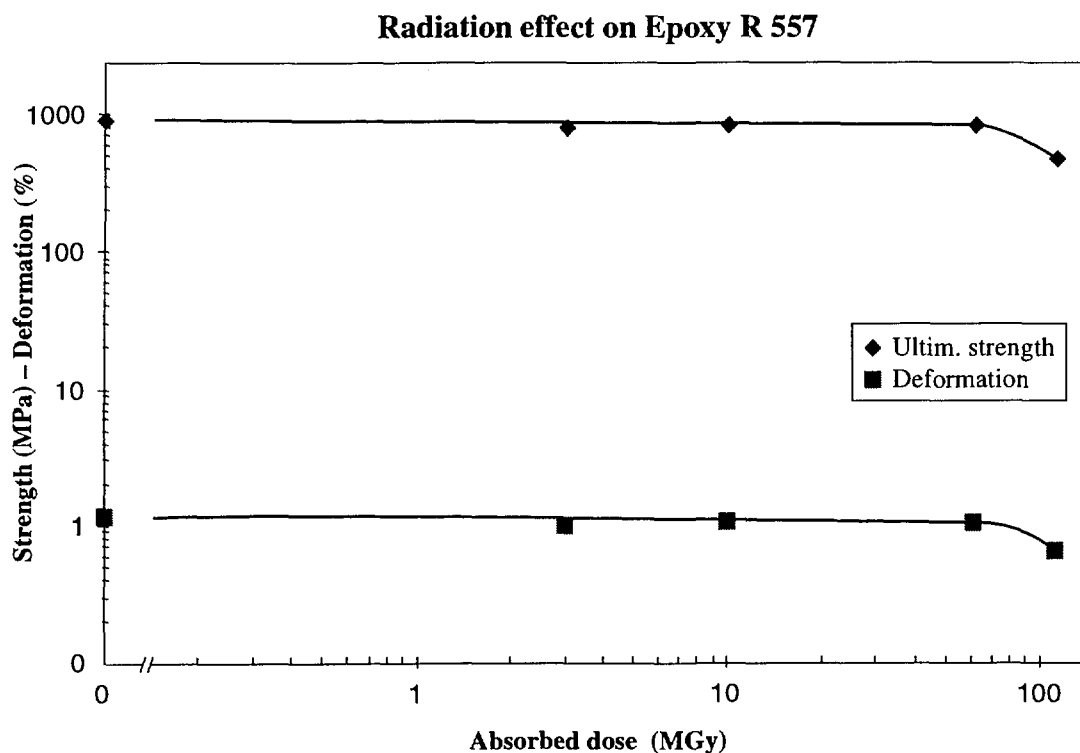

Material: **Epoxy laminate**
Type: **ISOPREG EP 0316**

TIS No. **R 564**

Supplier: **ISOVOLTA AG**
Remarks:

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	239±61	1.14±0.35	±
220	10	243±92	1.84±0.91	±
220	50	234±69	1.39±0.64	±
220	100	40±6	1.60±1.15	±

Critical property = flexural strength

Radiation index (RI) = 7.8 at a mean dose rate of 220 kGy/h

Radiation effect on Isopreg EP 0316 - R 564

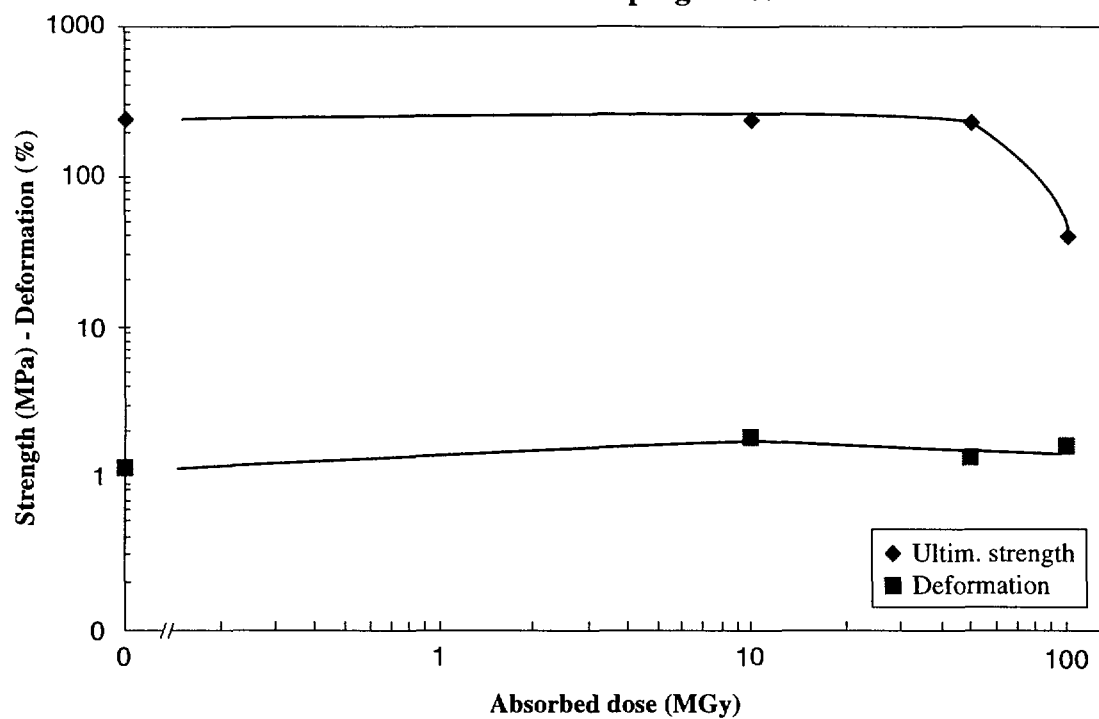

Comment: Tests carried out at the Österreichisches Forschungszentrum Seibersdorf.

Material: **Epoxy laminate**
 Type **ISOPREG EP 1037/IDT**

TIS No. **R 565**

Supplier: **ISOVOLTA AG**
 Remarks:


UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	552±6	2.46±0.04	30.3±0.7
220	10	561±7	2.54±0.11	30.5±0.6
220	50	479±9	2.61±0.05	32.1±0.2
220	100	306±8	4.64±0.39	29.8±1.4

Critical property = flexural strength

Radiation index (RI) > 8 at a mean dose rate of 220 kGy/h

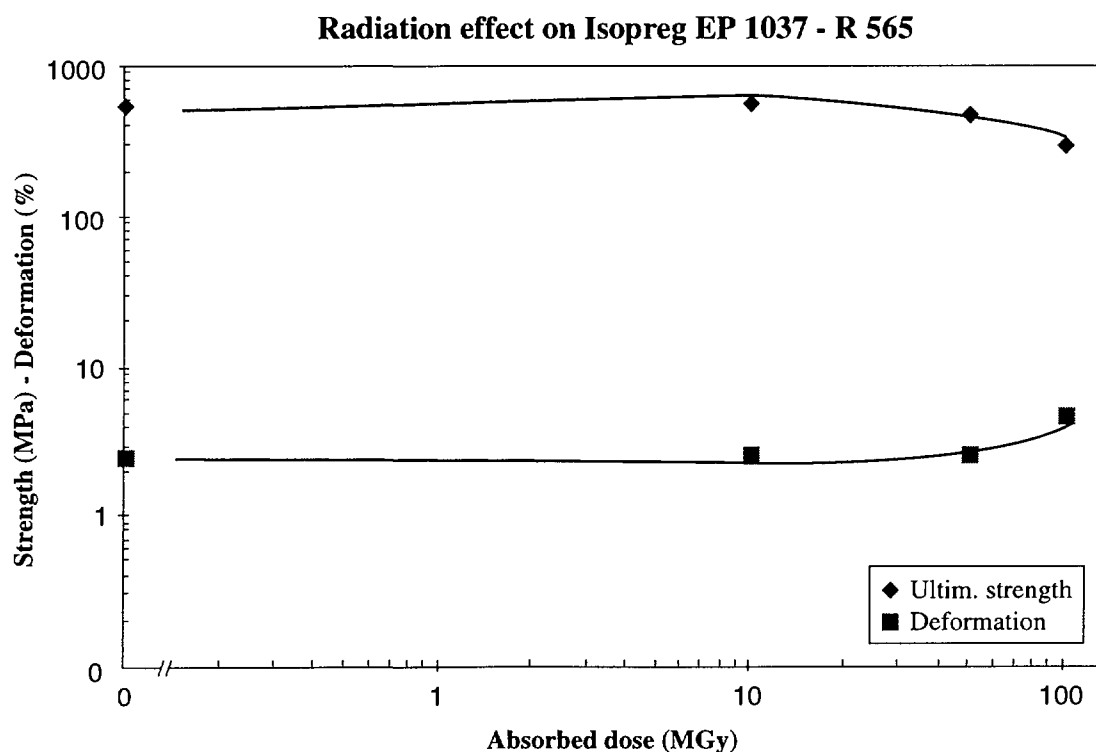

Comment: Tests carried out at the Österreichisches Forschungszentrum Seibersdorf.

NEXT PAGE(S)
lost BLANK

Fibredux trade name of CIBA-GEIGY for carbon fibre reinforced epoxy laminate, see CFRP

**NEXT PAGE(S)
left BLANK**

- G-Etronax trade name of Elektro-Isola for glass-reinforced epoxy resins
- GFRP glass fibre reinforced plastics; for behaviour under cryogenic irradiation, see Ref. [35]
- Araldite + glass fibres, see Araldite
- Epoxy + glass fibres, see Epoxy
- Epoxy laminates, see Epoxy
- Epoxy prepreg, see Epoxy
- Polyamides + glass fibres, see PA
- Polyesters + glass fibres, see Polyester
- Polyetherimide + glass fibres, see PEI
- Polyphenylsulfone + glass fibres, see PPS

NEXT PAGE(S)
left BLANK

Isaryl	trade name of Isonova for polyarylate (PAr), see polyarylate
Isopreg	trade name of Isovolta for epoxy pre-impregnated glass mat, see epoxy resin
Isoval	trade name of Isovolta for glass reinforced epoxy resin, see Ref. [25]; RI $\cong$ 7
Ixef	trade name of Solvay for polyarylamide (PAA), see polyarylamide

NEXT PAGE(S)
left BLANK

K

Kerimid	trade name of Rhône-Poulenc for polyimide (PI), see Ref. [25]; RI = 7.8
Kevlar	trade name of Dupont for para-aramid fibres; RI $\approx$ 7
Kinel	trade name of Rhône-Poulenc for polyimide (PI), see Ref. [25]; RI = 7.9

**NEXT PAGE(S)
left BLANK**

L

Laminates see CFRP, GFRP, epoxy and other corresponding Polymers

Lexan trade name of General Electric Plastics for polycarbonates (PC)

Liquid Crystal Polymer (LCP)

List of materials classified under letter L

TIS number	Material name	Type	Mechanical properties			
			UTS (MPa)	Deform. (%)	Modulus (MPa)	RI
560	Liquid crystal polymer + 30% GF	Vectra C130	131	2	8.8	> 7.7

Material: **Liquid Crystal Polymer + 30% GF**
 Type: **Vectra C130**

TIS No. **R 560**

Supplier: **Celanese (USA) via Hoechst**
 Remarks: **anisotropic material**

UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	131±13	2.0±0.2	8.8±1.8
185	1	118±36	2.9±1.8	7.0±2.0
10	9.4	124±16	2.0±0.2	7.7±0.9
190	10	128±26	2.1±0.1	7.7±1.6
230	50	113±11	1.7±0.1	7.7±0.7

Critical property =

Radiation index (RI) > 7.7 at a mean dose rate of 230 kGy/h

Radiation index (RI) > 7.0 at a mean dose rate of 10 kGy/h

Radiation effect on Liquid Cristal Polymer R 560

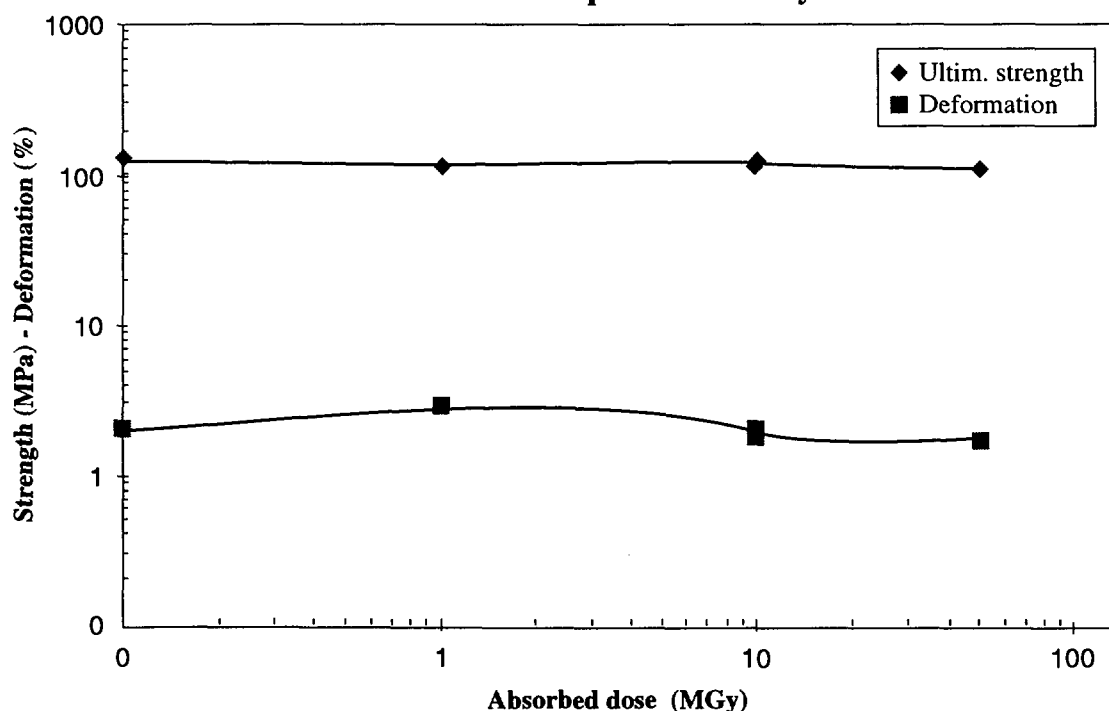

**NEXT PAGE(S)
left BLANK**

M

Makrolon	trade name of BAYER for polycarbonates, see polycarbonate
Matramid	trade name of CIBA-GEIGY for epoxy moulding compound, see epoxy
Micares	trade name of Micafil for polyurethanes, see Ref. [25] and PUR

NEXT PAGE(S)
left BLANK

Neonite	trade name of CIBA-GEIGY epoxy moulding compounds, see epoxy moulding compound
Nogentite	trade name of D.F.C. for polyester, see polyester
Nomex	trade name of Dupont for meta-aramid fibres, see Ref. [26]; RI $\approx$ 6.5
Noryl	trade name of General Electric Plastics for PPO based compound, see PPO based compound
Novolac	trade name of ISOLA for epoxy resins, see Ref. [25]
Nylon	trade name of Dupont for polyamides

NEXT PAGE(S)
left BLANK

Orlitherm trade name of BBC Baden for glass fibre reinforced epoxy resins based on DGEBA with MNA, see Ref. [25]; RI > 7.7

NEXT PAGE(S)
left BLANK

Phenolic resin

Plexiglas trade name of Röhm for polyarylates and PMMA

Polyamide (PA)

Polyamide-imide (PAI)

Polyarylamide base thermoplastic (PAA)

Polyaryl ether ketone (PAEK)

Polyarylate (PAr)

Polycarbonate (PC)

Polyester

Polyether-ether-ketone (PEEK); for behaviour under cryogenic irradiation, see Ref. [35]

Polyetherimide (PEI); for behaviour under cryogenic irradiation, see Ref. [35]

Polyethersulfone (PES); for behaviour under cryogenic irradiation, see Ref. [35]

Polyethylene (PE)

Polyethylene terephthalate PETP (for Mylar film, see Ref. [26])

Polyimide (PI)

Polyimide + silicon copolymer (see silicon)

Polymethyl-metacrylate (PMMA)

Polyoximethylene (POM)

Polypenco trade name of Cellpack for cross-linked styrene copolymer, see styrene

Polyphenyl sulfone

Polysulfone (PSu)

Polyurethane (PUR) see also cyanate-ester

Polyphenyl oxide (PPO) based compound

Prepreg see epoxy

List of materials classified under letter P

TIS number	Material name	Type	Mechanical properties			
			UTS (MPa)	Deform. (%)	Modulus (MPa)	RI
375	Polyphenyl Oxide based plastic	Noryl ENV 125	77.6	> 5	2.3	< 6.5
416	Polyurethane	Micares 700	95.4	3.30	5.09	7.7
419	Polycarbonate	Makrolon 218	86.3	> 10	2.30	5.7
435	Polyester + glass mat	Nogentite NR2-71A	141	2.39	6.8	> 7
459	Polyester + glass fibres	Nogentite NZ-3 71E	96.1	1.25	11.2	> 7.5
464	Polyphenyl Oxide based plastic	Noryl ENV 509	82.8	> 12	2.9	< 5
473	Polyester resin + glass fibres	KK/RI	93.7	2.1	12.3	7.5
474	Polyester resin + glass fibres	KK/530I	106	2.1	11	> 7
491	Polyphenyl Oxide based plastic	Univolt HFT	68.1	> 6	2.59	6.7
499	Polyester resin + glass mat	Polyester 1	215.9	3.6	5.89	> 7
500	Polyester resin + glass mat	Polyester 2	148.1	3.77	5.3	> 7
501	Polyester resin + glass mat	Polyester 3	129.6	3.6	3.5	> 7
503	Polyoximethylene	Delrin	98.6	> 13	3.4	< 5
504	Polyetherimide + glass fibres	Ultem 1000	288	2.83	10.5	> 8
513	Polyurethane, polyalcohol	Scotchcast 800	114.6	6.5	3.0	6.8
516	Polyurethane, polyalcohol	Scotchcast 840	0.9	> 12	0.0	6.5
520	PEEK Natural polyether-ether-ketone		176.9	> 15	4.30	6.8
521	Polyimide	Sintimid	223.2	6.60	3.91	> 6.8
522	Polyetherimide + Siloxane	Siltem STM1500	25.8	> 10	0.71	6.8
523	Polyarylamide base thermoplastic	IXEF1002	274.1	2.71	11.30	7.5
524	Polyarylamide base thermoplastic	IXEF1501	271.1	2.62	11.81	> 7.5
526	Polyamide 4.6	Ertalon	125.3	5.20	5.80	6.5
528	Polyamide 6	Ertalon 6PLA	97.6	> 15	2.50	6
529	Polyamide PA 6	Ertalon LFX	84.4	> 15	2.07	6
530	Polyamide 6	Ertalon 6XAU+	76.1	> 15	1.84	6.5
531	PETP	Ertalyte	134.8	> 15	3.28	5.7
532	PETP	Ertalyte TX	119.9	6.37	3.05	8
533	Polyetherimide	Erta PEI	171.0	> 15	3.15	> 7.7
534	Polyethersulfone	Erta PES	140.7	> 15	2.70	6.3
535	Polysulfone	Erta PSU	120.15	> 15	2.59	6.5
536	Polyamide 6	Ertalon 6 SA	63.4	> 15	1.38	~ 7
537	Polyamide 66	Ertalon 66SA	101.6	> 15	2.4	6.5
542	Polyarylate	Isaryl 15M	110.4	> 12	2.40	6.3
563	Polyaryl ether ketone	Stilan/Ultrapek	153.0	> 6	5.46	> 7.5
568	Polyimide	Vespel SP-1	91.9	4.18	2.52	> 7.5
569	Polyphenyl sulfone + glass fibres	Ertaxel	89.3	3.32	3.29	> 7.5
570	Polyamide + 30% glass fibres	Ertalon 66GF30	197	4.58	5.76	6.7
571	Polyoximethylene	Ertacetal	101.0	> 15	3.09	4
572	Polyethylene	Borolene 4505	23.8	> 15	1.11	~ 5.7
573	Polyethylene	Cestilene HD 1000	23.3	> 15	0.81	~ 6
574	Polyethylene	Cestilene HD 500	37.1	> 15	1.69	~ 6.5
575	Polyethylene	Cestidur	22.7	> 14.5	0.78	> 6.5
576	Polyethylene	Cestitech	23.4	> 14	0.83	6.4
577	Polyamide-imide	Torlon 4203	188.2	14.96	4.06	> 7.5
578	Polyamide-imide	Torlon 4301	182.3	7.88	6.12	> 7.5

Material: **Polyphenyl oxide (PPO) based plastic**
 Type **Noryl ENV 125**

TIS No. **R 375**

Supplier: **Angst & Pfister**
 Remarks: no glass fibre
 bus bar insulation for LEP

UL 94: V-1
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	77.6±8.1	> 5	2.3±0.3
220	3	58.4±6.1	2.1±0.1	5.6±0.6
220	10	38.5±4.7	1.3±0.1	3.1±0.2

Critical property = deformation

Radiation index (RI) = < 6.5 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 375

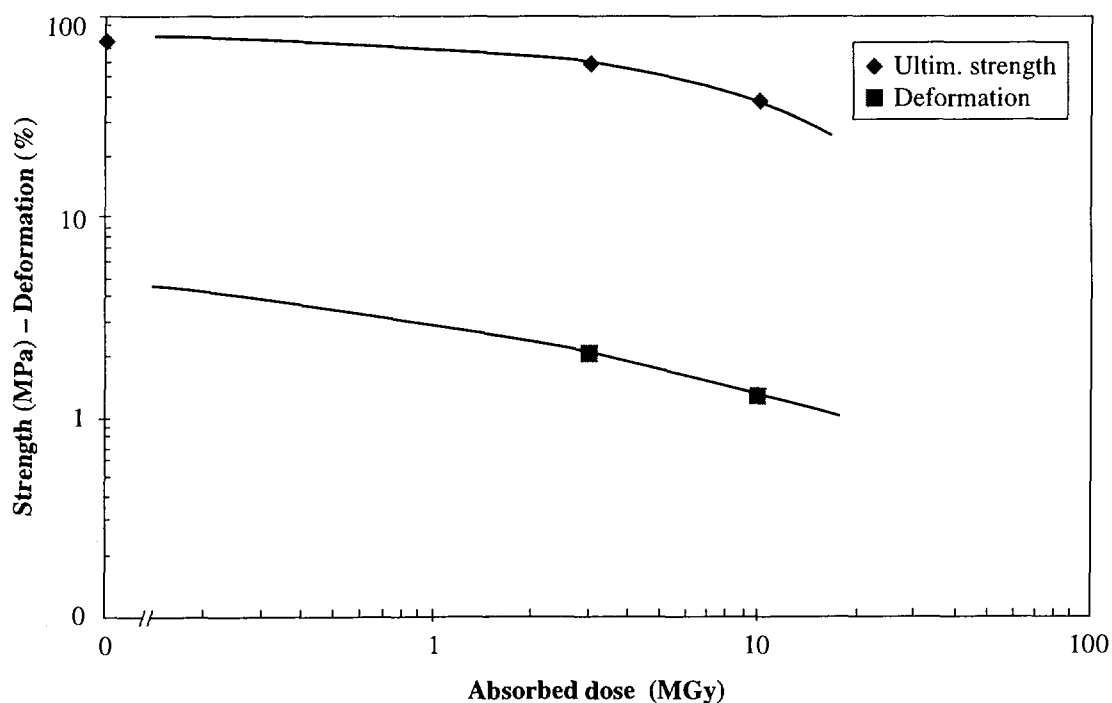

Material: **Polyurethane**
Type **Micares 700**

TIS No. **R 416**

Supplier: **Micafil**
Remarks:

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	95.4±1.7	3.30±0.42	5.09±0.23
170	5	90.6±2.8	2.75±0.14	5.04±0.16
170	10	88.1±2.0	1.83±0.08	5.60±0.20
170	50	86.4±9.7	1.60±0.10	6.00±0.60

Critical property = deformation

Radiation index (RI) = 7.7 at a mean dose rate of 170 kGy/h

Radiation effect on insulating resin R 416

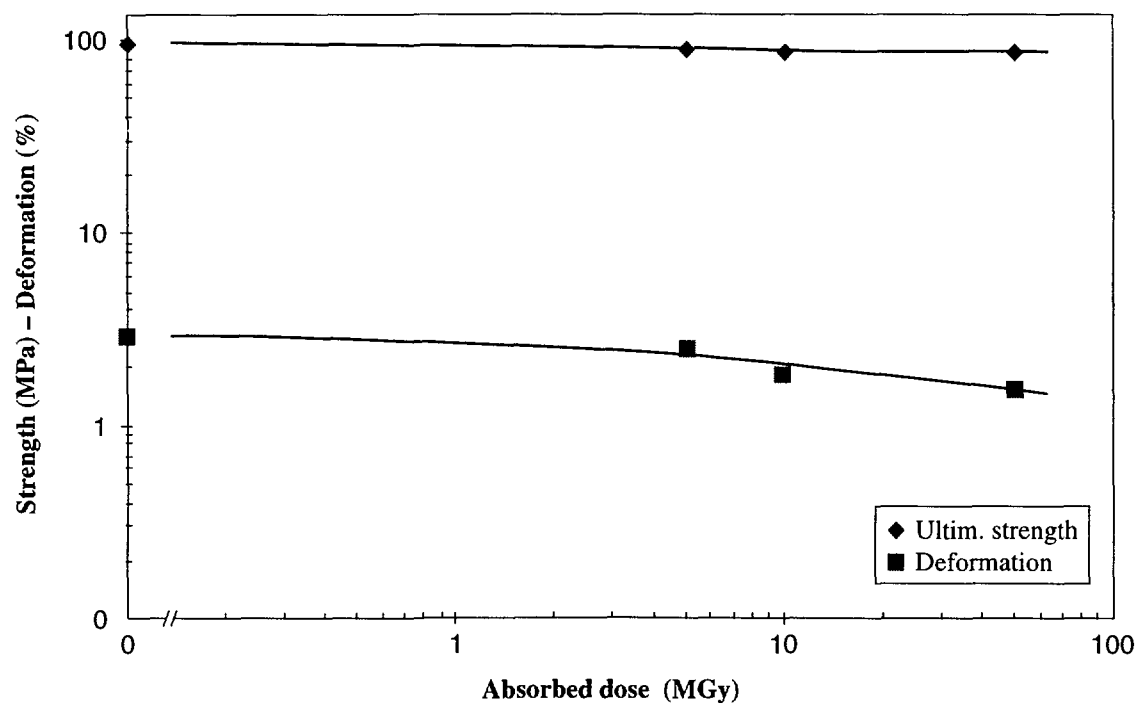

Material: **Polycarbonate**
Type **Makrolon 218**

TIS No. **R 419**

Supplier: **Bayer (CERN stores)**
Remarks: **translucent**

UL 94: V-2
LOI: 26%


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0.0	86.3±2.9	> 10	2.3±0.1
0.1	0.2	86.6±2.5	> 10	2.5±0.1
0.1	0.5	85.0±1.3	> 10	2.6±0.1
4.0	1.0	44.4±13.5	1.71±0.53	2.7±0.1
190	1.0	91.6±2.2	5.49±0.13	2.7±0.1
190	5.0	17.2±2.9	0.62±0.09	2.8±0.1
190	10	11.3±2.0	0.39±0.07	2.9±0.1
190	30	7.8±2.5	0.29±0.08	3.2±0.2

Critical property = deformation

Radiation index (RI) = < 6 at a mean dose rate of 190 kGy/h

Radiation index (RI) = 5.7 at a mean dose rate of 100 Gy/h

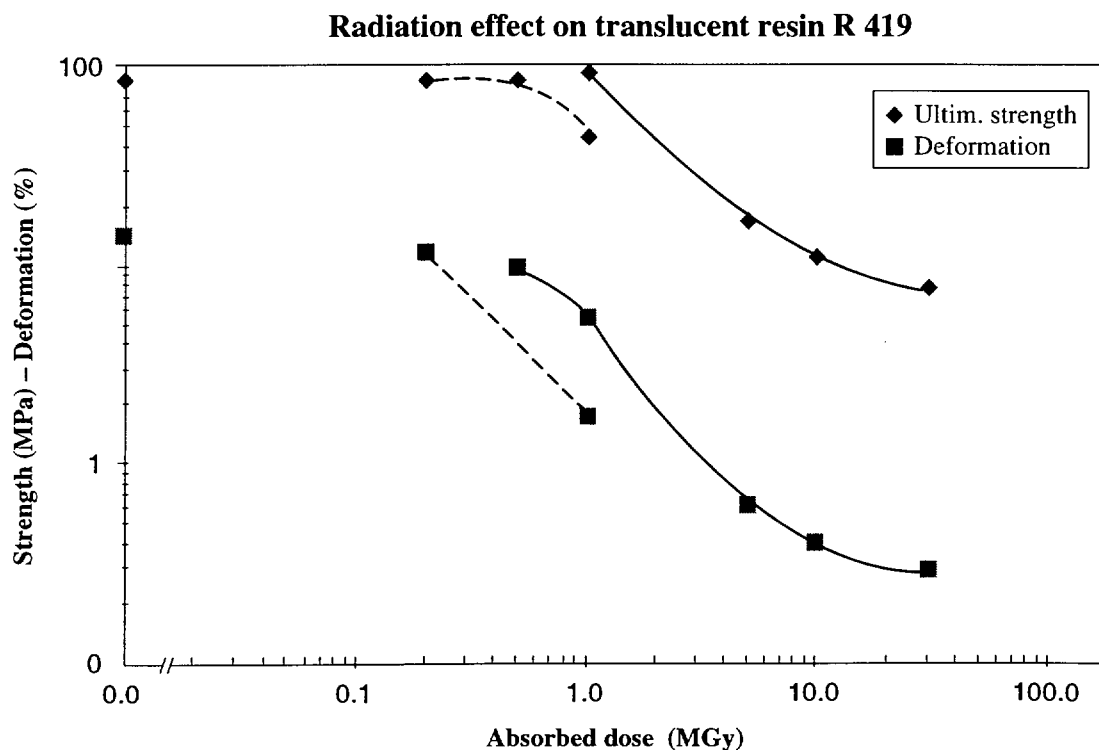

Comment: Dotted lines correspond to long-term irradiation.

Material: **Polyester + glass mat**
 Type: **Nogentite NR2-71A**

TIS No. **R 435**


Supplier: **D.F.C.**
 Remarks: **high temperature applications**

UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	141±20	2.39±0.22	6.8±0.8
0.1	1	114±12	2.21±0.17	7.5±0.1
220	1	138±12	2.05±0.23	7.4±0.0
220	5.2	131±13	2.12±0.23	6.8±0.2
220	10	123±19	2.28±0.16	5.8±0.4

Radiation effect on Nogentite R 435

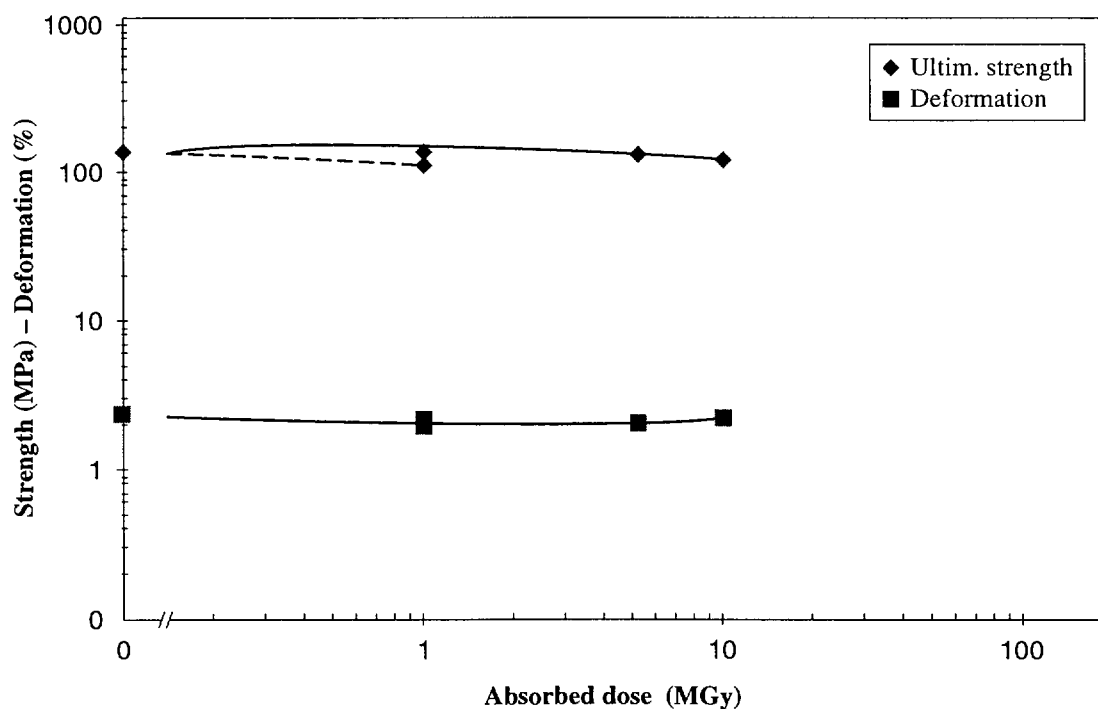

Comment: Dotted line corresponds to low-dose-rate irradiation.

Material: **Polyester + glass fibres**
 Type: **Nogentite NZ-3 71E**

TIS No. **R 459**

Supplier: **D.F.C.**
 Remarks: **high temperature applications**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	96±24	1.25±0.29	11.2±0.8
220	5	111±25	1.24±0.14	12.2±1.0
220	10	103±23	1.06±0.26	12.7±1.5
220	30	93±31	1.11±0.35	11.9±1.5

Critical property = flexural strength

Radiation index (RI) = > 7.5 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 459

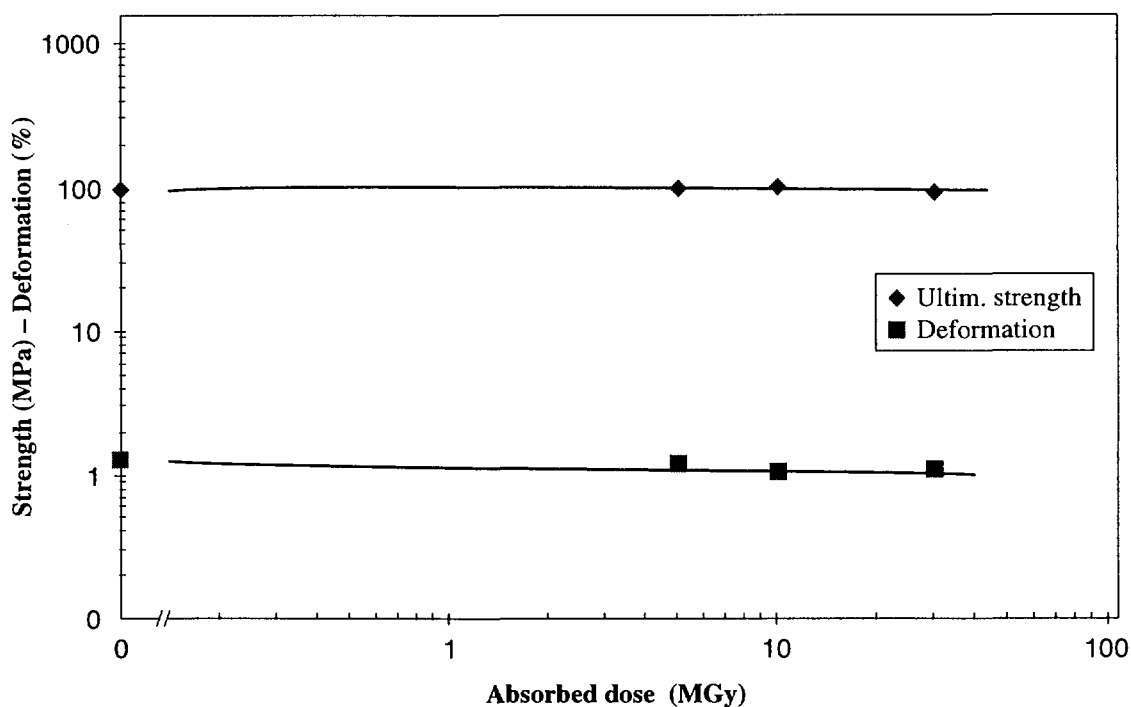

Material: **Polyphenyl oxide (PPO)-based plastic**
 Type: **Noryl ENV 509**

TIS No. **R 464**

Supplier: **General Electric Plastics**
 Remarks: **insulation of LEP monorail**

UL 94: V-1
 LOI: 31%

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	82.8±2.9	> 12*	2.9±0.1
0.1	0.2	84.7±2.5	2.5±0.1	6.7±0.1
0.1	0.5	57.1±1.3	0.9±0.2	6.8±0.1
220	3	104.0±2.2	9.0±1.4	3.0±0.1
220	5	75.4±20.4	2.7±0.7	3.2±0.1
220	10	59.9±0.7	1.9±0.1	3.3±0.1

Critical property = deformation

Radiation index (RI) < 5 at a mean dose rate of 220 kGy/h

Radiation index (RI) ~ 6 at a mean dose rate of 100 Gy/h

Radiation effect on Noryl ENV 509 R 464

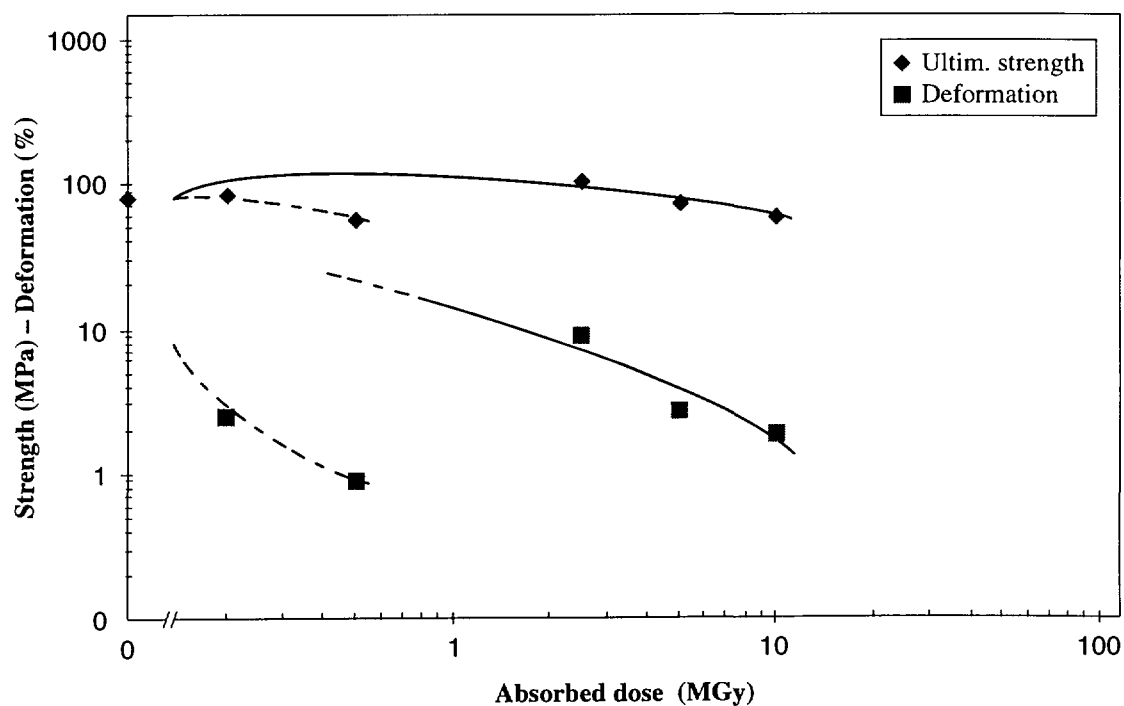

Comment: Dotted lines correspond to long-term irradiation.

Material: **Polyester resin + glass fibres**
 Type: **KK/RI**

TIS No. **R 473**

Supplier: **EBO AG**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	93.7±11.4	2.1±0.2	12.3±0.7
220	5	95.7±11.8	2.3±0.2	7.3±0.9
220	10	83.4±4.8	2.2±0.2	7.1±0.4
220	50	68.4±5.4	2.2±0.1	4.9±0.3

Critical property = Modulus

Radiation index (RI) = 7.5 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 473

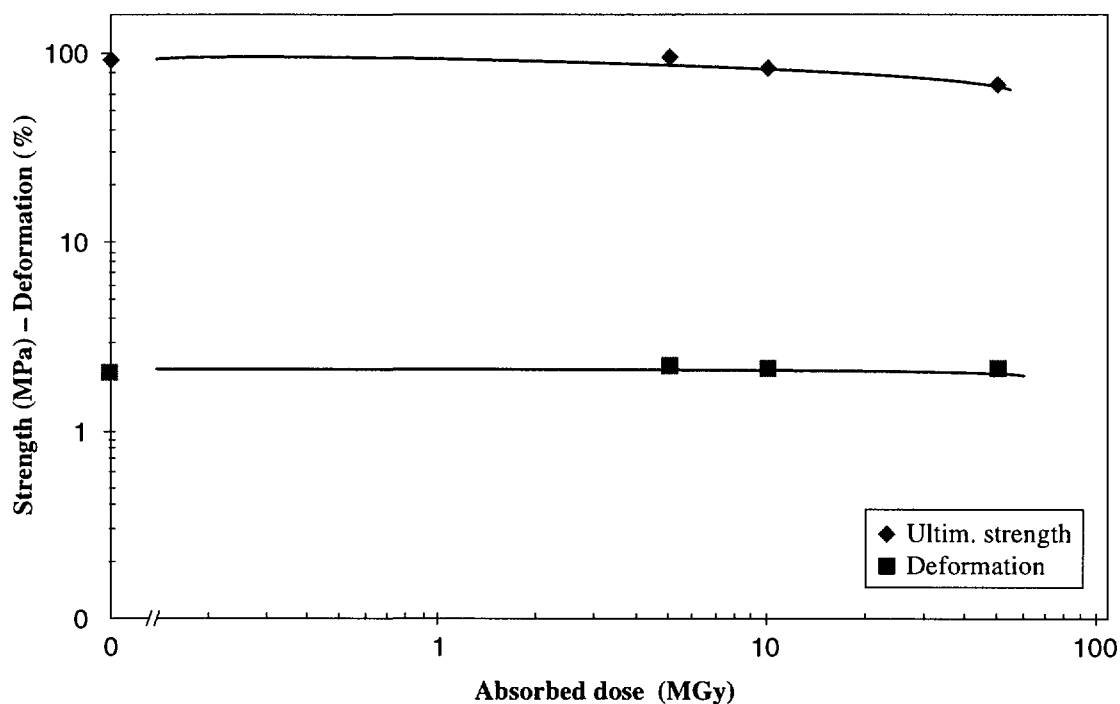

Material: **Polyester resin + glass fibres**
 Type **KK/530I**

TIS No. **R 474**

Supplier: **EBO AG**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	106±12	2.1±0.2	11.0±0.7
220	5	111±11	2.0±0.2	11.4±0.6
220	10	110±10	2.1±0.1	11.3±1.1
220	50	99±17	2.1±0.1	8.1±0.5

Critical property = none

Radiation index (RI) = > 7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 474

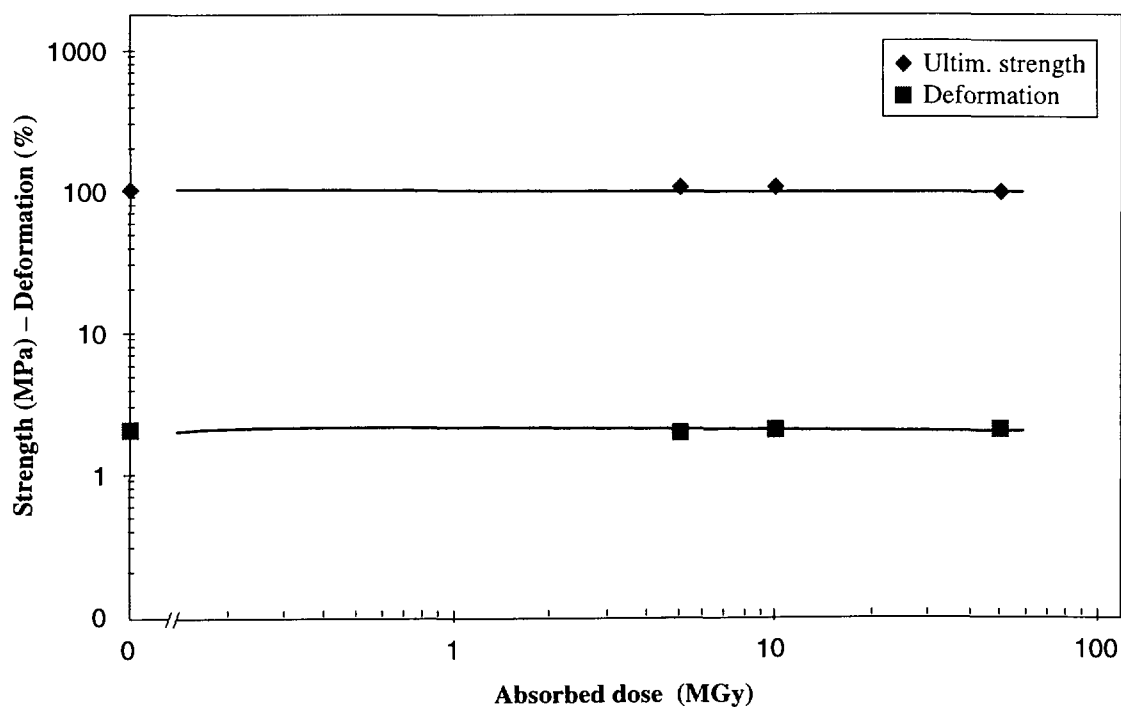

Material: **Polyphenyl oxide (PPO) based plastic**
 Type: **Univolt HFT**

TIS No. **R 491**

Supplier: **AGRO, via Dietzel Electro GMBH**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	68.1±1.5	> 6	2.59±0.06
0.1	0.5	73.7±0.8	> 6	2.53±0.04
0.1	1	74.2±2.2	> 6	2.54±0.05
220	5	75.4±2.2	> 6	2.66±0.02
220	10	51.0±7.9	2.29±0.46	2.66±0.07
220	50	30.5±3.9	1.3±0.2	2.41±0.19

Critical property = deformation

Radiation index (RI) = 6.7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating plastic R 491

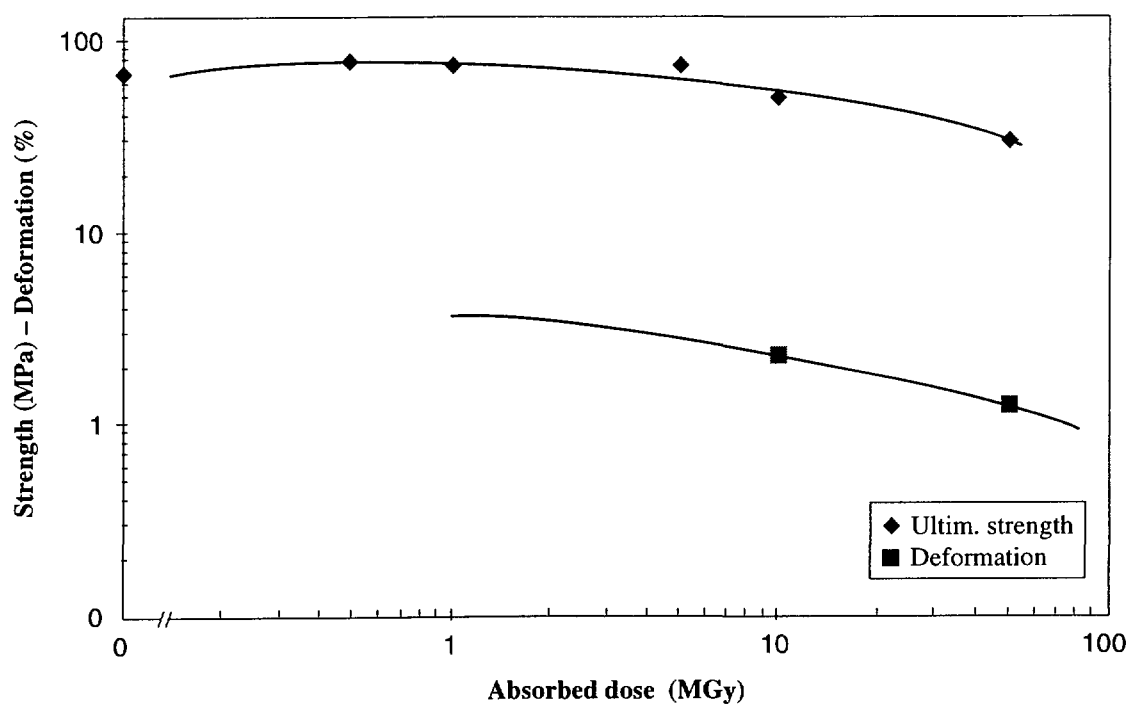

Material: **Polyester resin + glass mat**
 Type: **Polyester 1**

Supplier: **FA-BA**
 Remarks: proposed for LEP magnet covers
 (hand-made)

TIS No. **R 499**

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	216±27	3.60±0.28	5.89±3.04
220	5	214±11	3.51±0.26	7.57±0.71
220	10	180±20	3.29±0.43	6.91±0.57

Critical property = flexural strength

Radiation index (RI) = > 7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 499

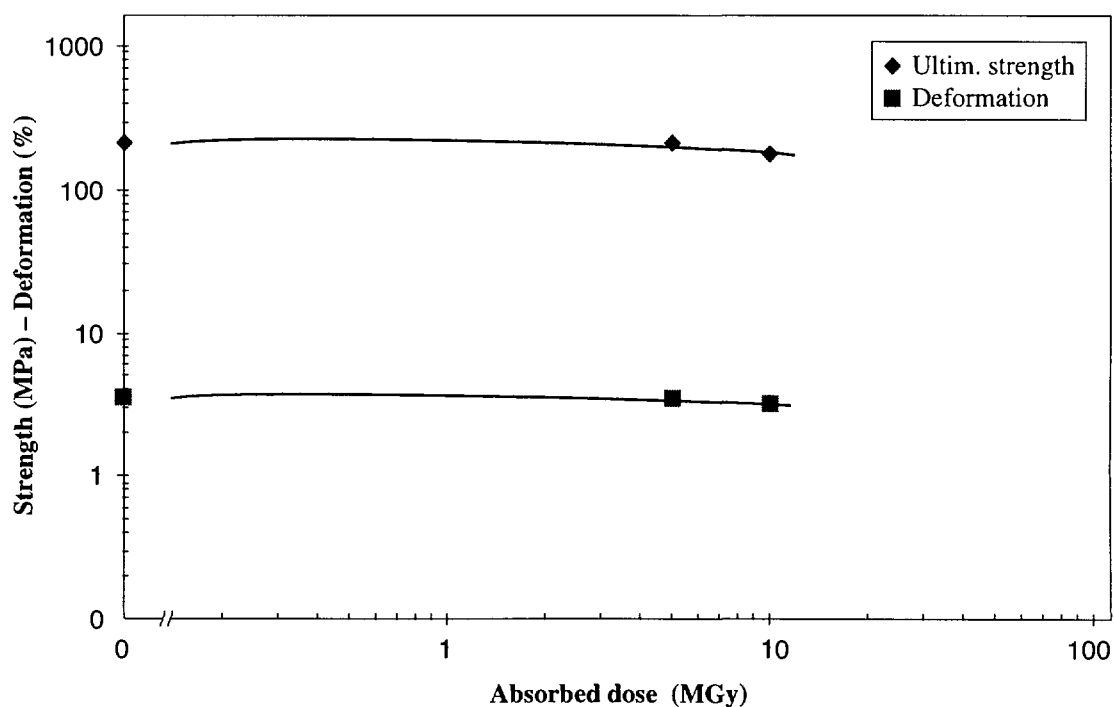

Material: **Polyester resin + glass mat**
 Type: **Polyester 2**

TIS No. **R 500**

Supplier: **FA-BA**
 Remarks: proposed for LEP magnet covers
 (hand-made)

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	148±5	3.77±0.59	5.30±2.53
220	5	143±29	3.73±0.32	7.07±1.23
220	10	132±27	4.27±0.33	5.56±0.75

Critical property = flexural strength

Radiation index (RI) = > 7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 500

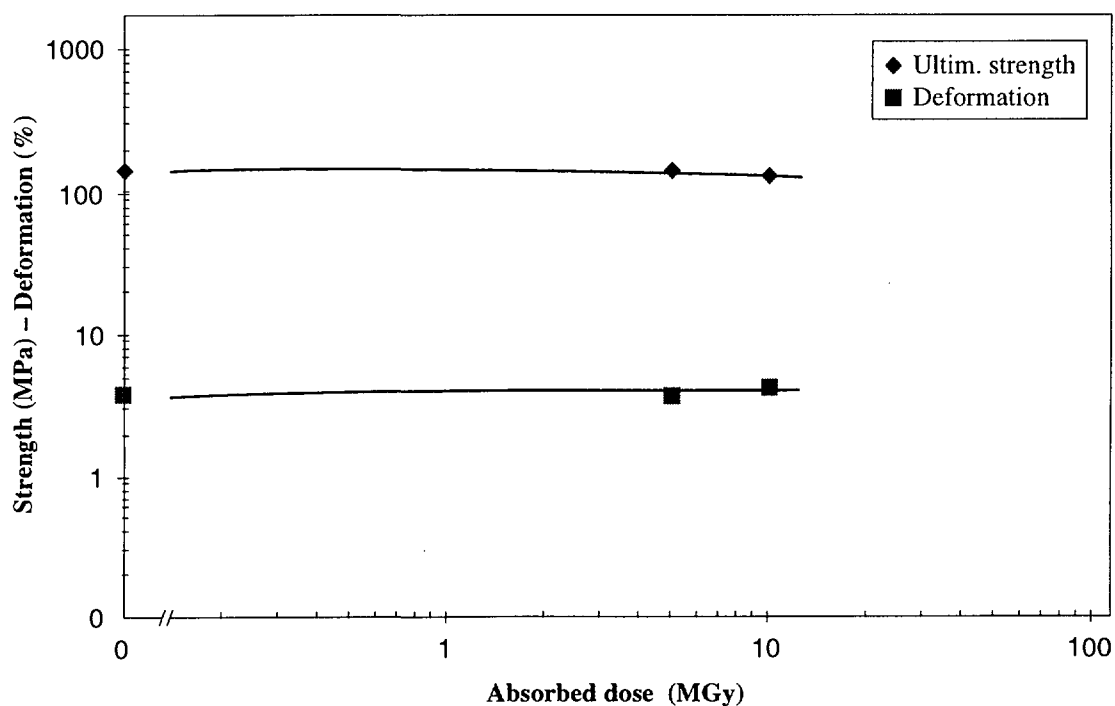

Material: **Polyester resin + glass mat**
 Type: **Polyester 3**

TIS No. **R 501**

Supplier: **FA-BA**
 Remarks: proposed for LEP magnet covers
 (hand-made)

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	130±25	3.6±0.9	3.5±2.8
220	5	160±9	3.4±0.2	8.5±0.6
220	10	123±15	3.5±0.1	5.9±1.4

Critical property = flexural strength

Radiation index (RI) = > 7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 501

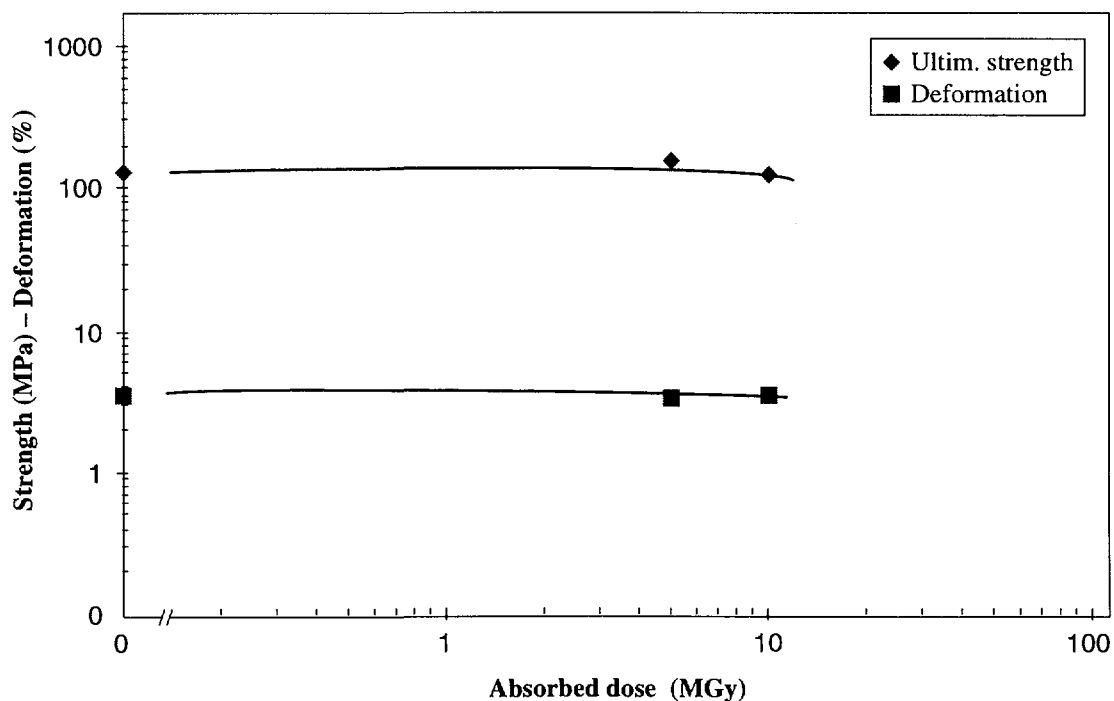

Material: **Polyoximethylene (POM)**
Type: **Delrin**

TIS No. **R 503**

Supplier: **DuPont de Nemours**
Remarks: also called acetal resin
CERN stores Scem 44 88 20 104.1


UL 94: n.m.
LOI: n.m.

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	98.6±9.4	> 13	3.4±0.6
250	0.2	4.9±0.9	0.1±0.3	3.5±0.3

Critical property = flexural strength and deformation

Radiation index (RI) < 5 at a mean dose rate of 250 kGy/h

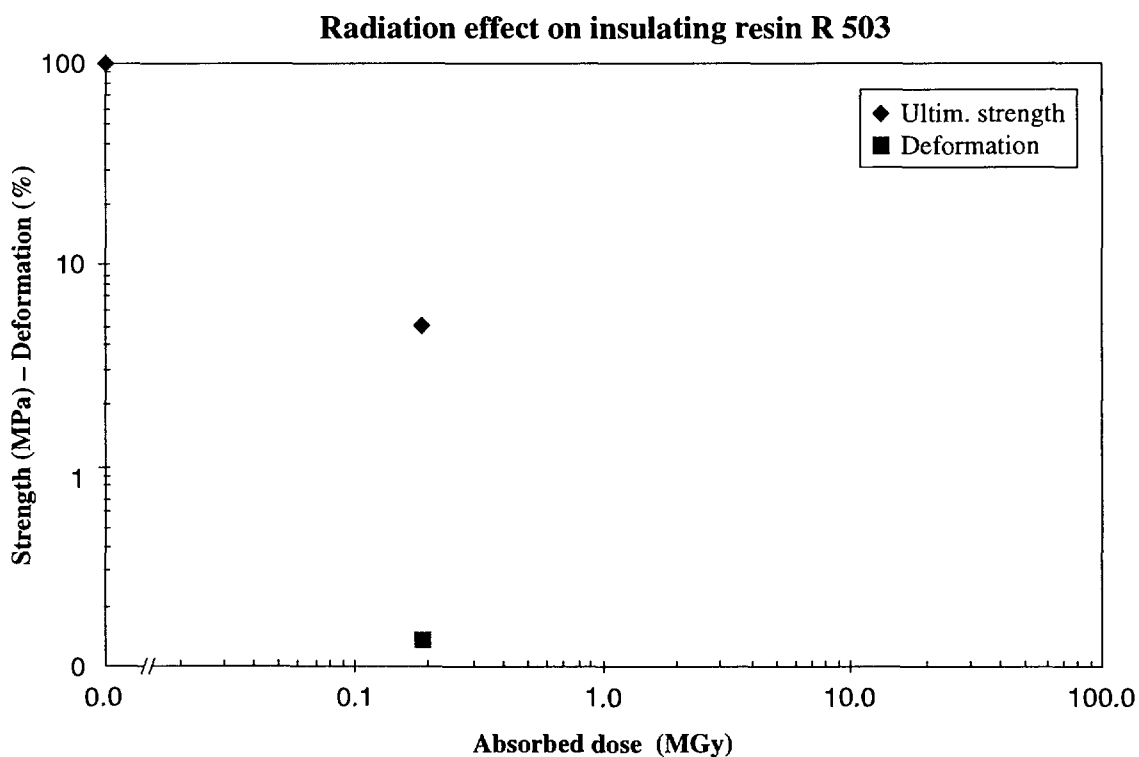

Comment: This material should never be used in a radiation environment.

Material: **Polyetherimide + glass fibres**
 Type: **Ultem 1000**

TIS No. **R 504**

Supplier: **General Electric Plastics**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	288±54	2.83±0.08	10.5±1.3
170	5	234±29	2.86±0.14	9.1±1.4
70	10	235±9	2.65±0.09	9.5±0.4
70	50	214±6	2.39±0.10	10.0±0.5
220	100	216±3	2.15±0.04	10.8±0.1

Critical property = flexural strength

Radiation index (RI) = > 8 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 504

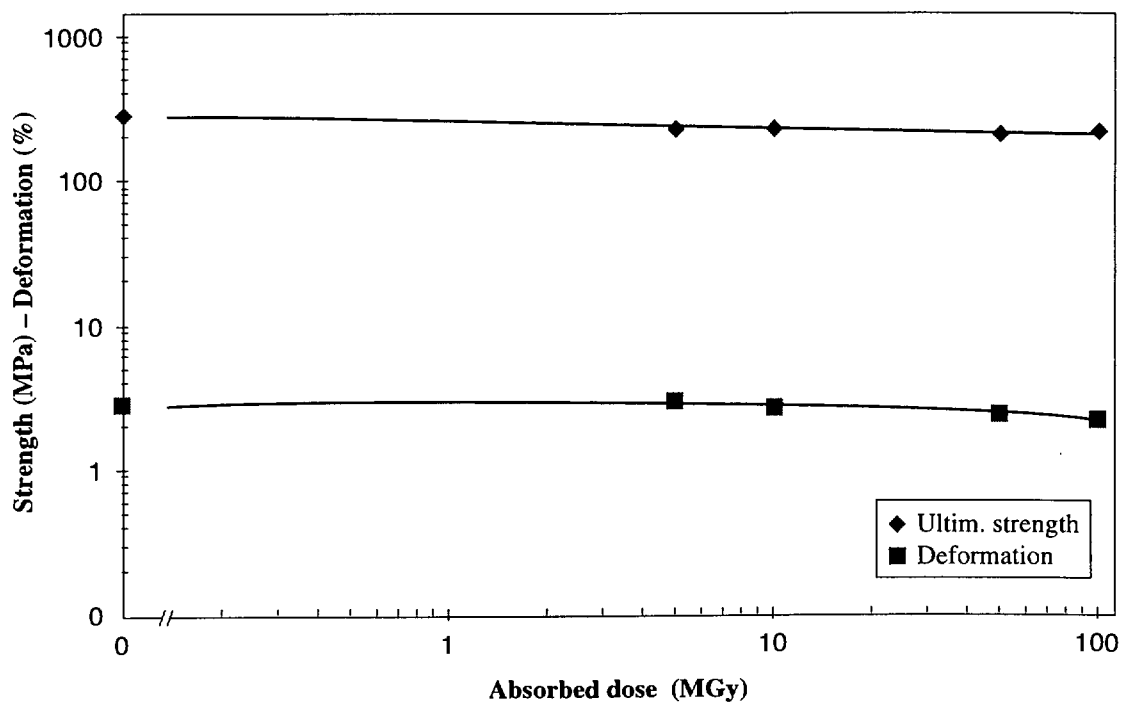

Material: **PUR, Polyalcohol**
Type **Scotchcast 800**

TIS No. **R 513**

Supplier: **3M**
Remarks: rigid (cold)
contains chlorine

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	115±2	6.46±0.69	3.0±0.0
200	3.4	93.1±9.2	3.98±0.6	2.8±0.1
3	5	81.7±9.2	3.9±0.6	2.5±0.1
3	10	58.7±8.3	2.5±0.3	2.5±0.2
200	10	70.4±9.2	2.3±0.4	3.3±0.1
200	29	20.7±2.8	1.1±0.2	2.0±0.1

Critical property = deformation

Radiation index (RI) = 6.8

Radiation effect on Polyalcohol R 513

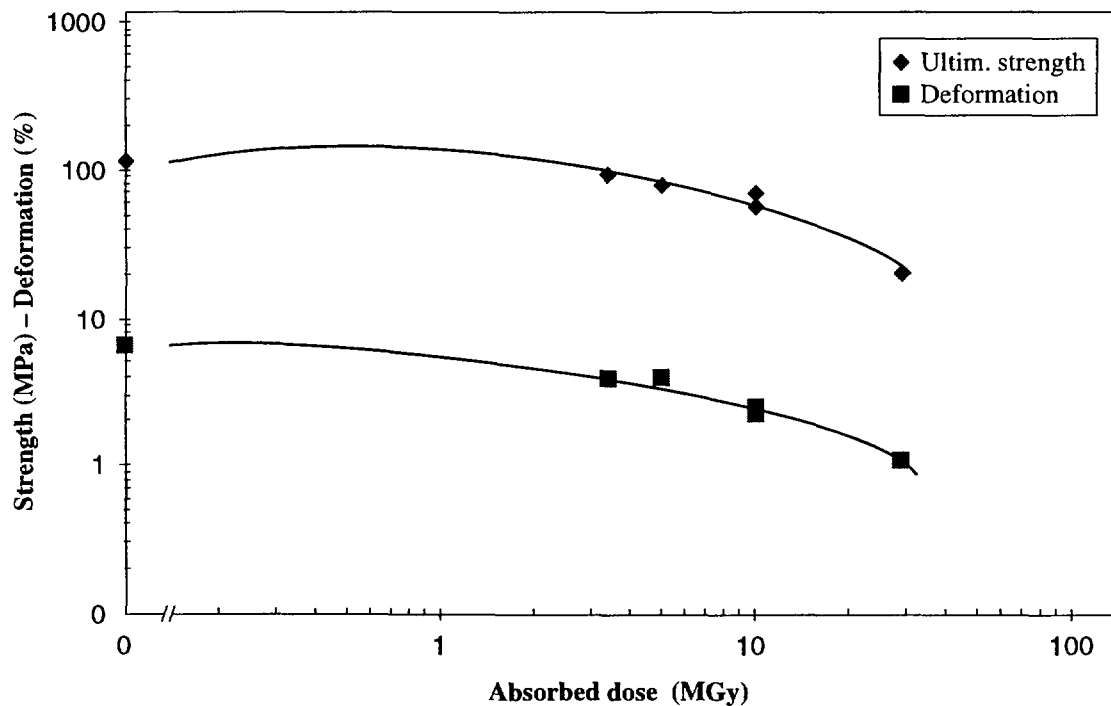

Material: **PUR, Polyalcohol**
Type: **Scotchcast 840**

TIS No. **R 516**

Supplier: **3M**
Remarks: flexible (cold)
contains chlorine

UL 94: n.m.
LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	0.9±0.1	> 12	0.0±0.0
200	3.4	35.5±1.9	7.2±1.6	0.9±0.1
3	5	43.5±2.2	3.6±0.2	1.6±0.1
3	10	48.6±3.3	2.8±0.2	4.1±0.2
200	10	44.2±3.7	2.7±0.2	1.9±0.1
200	29	27.2±3.0	1.6±0.1	1.9±0.2

Critical property = deformation

Radiation index (RI) = 6.5 at a mean dose rate of 200 kGy/h

Radiation index (RI) = < 6.7 at a mean dose rate of 3000 Gy/h

Radiation effect on Polyalcohol R 516

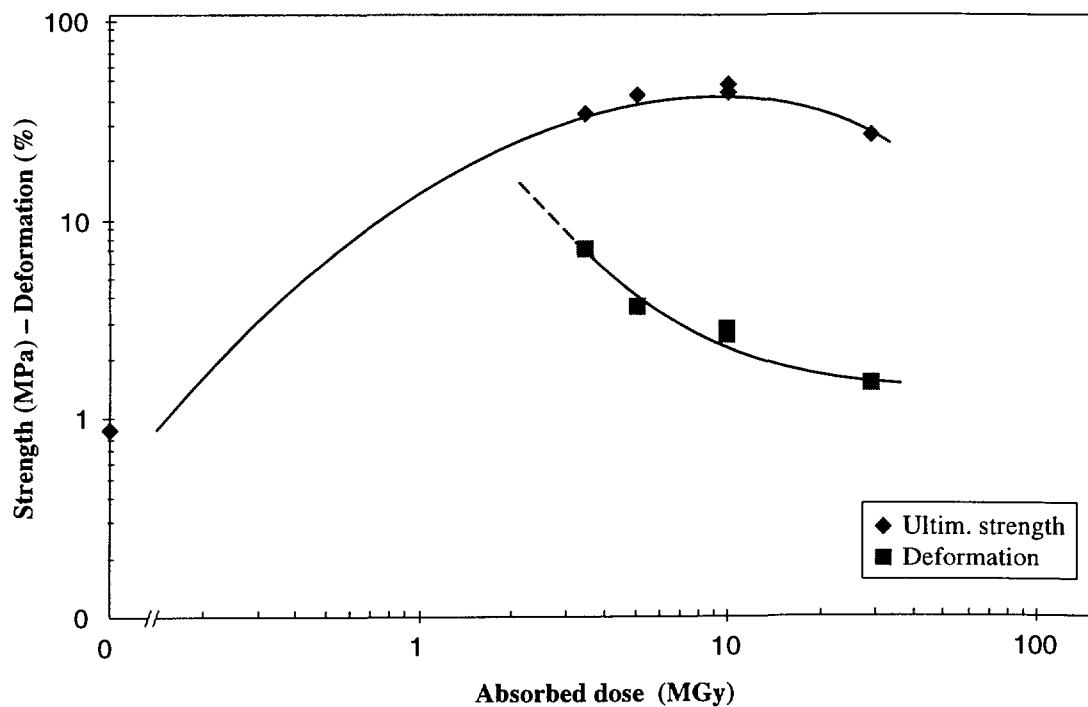

Material: **PEEK**
 Type: **Natural polyether-ether-ketone**

TIS No. **R 520**

Supplier: **Erta-Epec**
 Remarks: **via Angst and Pfister**

UL 94: **V-0**
 LOI: **35%**


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	177 $\pm$ 3	> 15	4.3 $\pm$ 0.1
1	1	177 $\pm$ 5	> 15	4.3 $\pm$ 0.1
180	5	179 $\pm$ 0.3	> 15	4.1 $\pm$ 0.1
180	10	161 $\pm$ 35	9.2 $\pm$ 4.5	4.2 $\pm$ 0.1
1	10	126 $\pm$ 7	3.4 $\pm$ 0.3	4.3 $\pm$ 0.3
210	50	81 $\pm$ 41	3.0 $\pm$ 1.1	4.3 $\pm$ 0.1
220	100	143 $\pm$ 22	4.7 $\pm$ 1.2	4.2 $\pm$ 0.1

Critical property = deformation

Radiation index (RI) = 7.1 at a mean dose rate of 220 kGy/h

Radiation index (RI) = 6.8 at a mean dose rate of 1 kGy/h

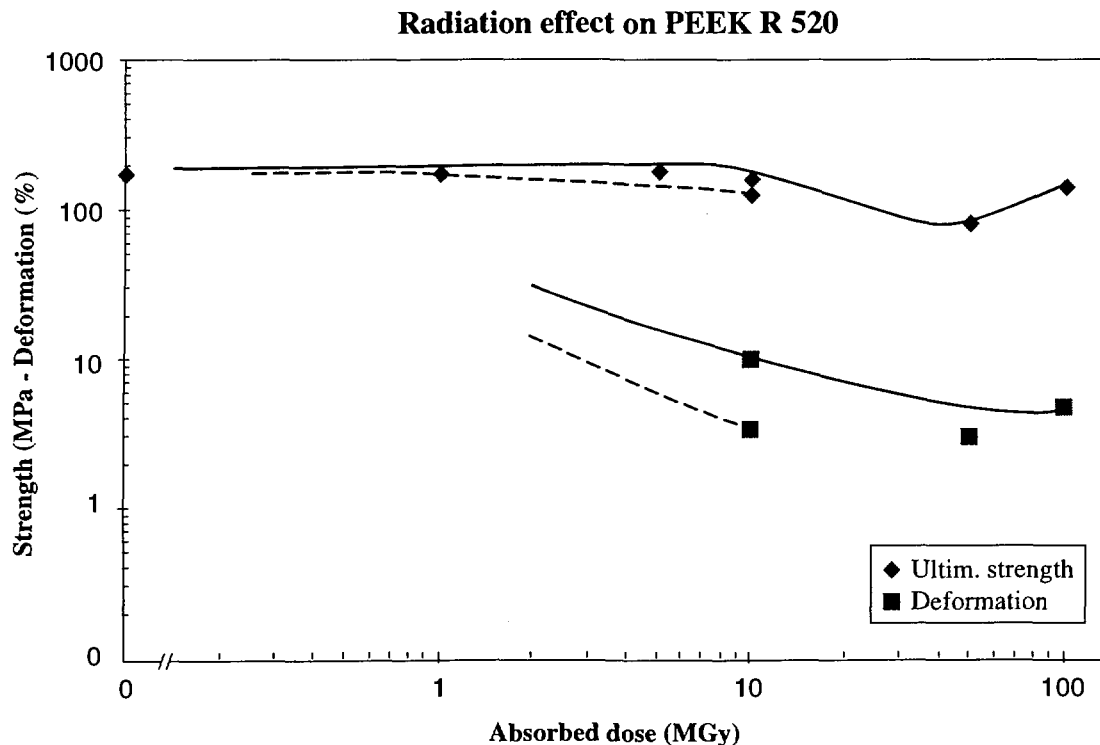

Comment: Dotted lines correspond to long-term irradiation.

Material: **Polyimide**
Type: **Sintimid**

TIS No. **R 521**

Supplier: **Lenzing & Plansee**
Remarks: **free of charge**

UL 94: n.m.
LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	223±16	6.60±0.62	3.91±0.05
1	1	189±32	5.38±0.84	3.91±0.18
185	5	176±20	4.71±0.62	3.94±0.08
1	7	152±16	4.21±0.40	3.85±0.10
185	10	120±5	3.24±0.07	3.72±0.09
210	50	73±10	2.12±0.29	3.52±0.34

Critical property = deformation

Radiation index (RI) = 7 at a mean dose rate of 185 kGy/h

Radiation index (RI) > 6.8 at a mean dose rate of 1000 Gy/h

Radiation effect on Sintimid R 521

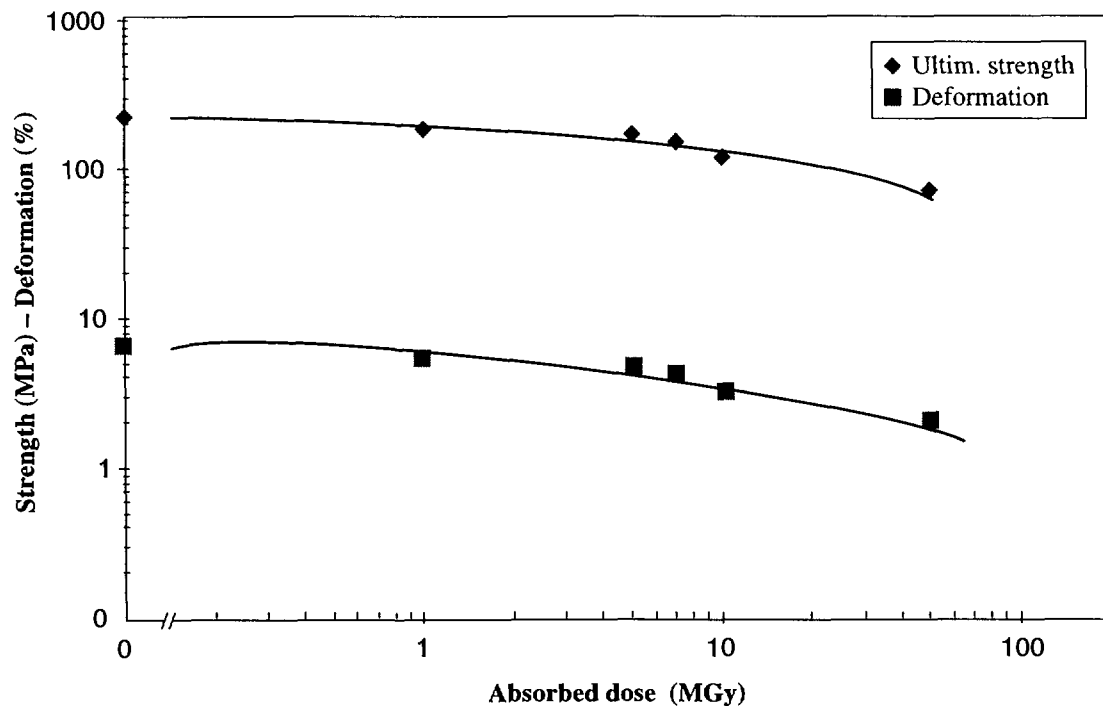

Material: **Polyetherimide + Siloxane**
Type **Siltem STM 1500**

TIS No. **R 522**

Supplier: **General electric Plastics**
Remarks: copolymer, free of charge
for wire insulation

UL 94: V-O
LOI: 46%

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	25.8 $\pm$ 1	> 10	0.71 $\pm$ 0.03
1	1	27.3 $\pm$ 0.7	> 10	0.72 $\pm$ 0.02
185	5	45.0 $\pm$ 0.1	> 10	1.10 $\pm$ 0.03
1	7	53.2 $\pm$ 2.1	5.14 $\pm$ 0.58	1.40 $\pm$ 0.03
185	10	56.5 $\pm$ 3.2	4.8 $\pm$ 0.3	1.55 $\pm$ 0.03
220	50	23.2 $\pm$ 2.4	1.0 $\pm$ 0.1	2.68 $\pm$ 0.06

Critical property = deformation

Radiation index (RI) = 6.8 at a mean dose rate of 185 kGy/h

Radiation index (RI) = 6.8 at a mean dose rate of 1000 Gy/h

Radiation effect on Siltem R 522

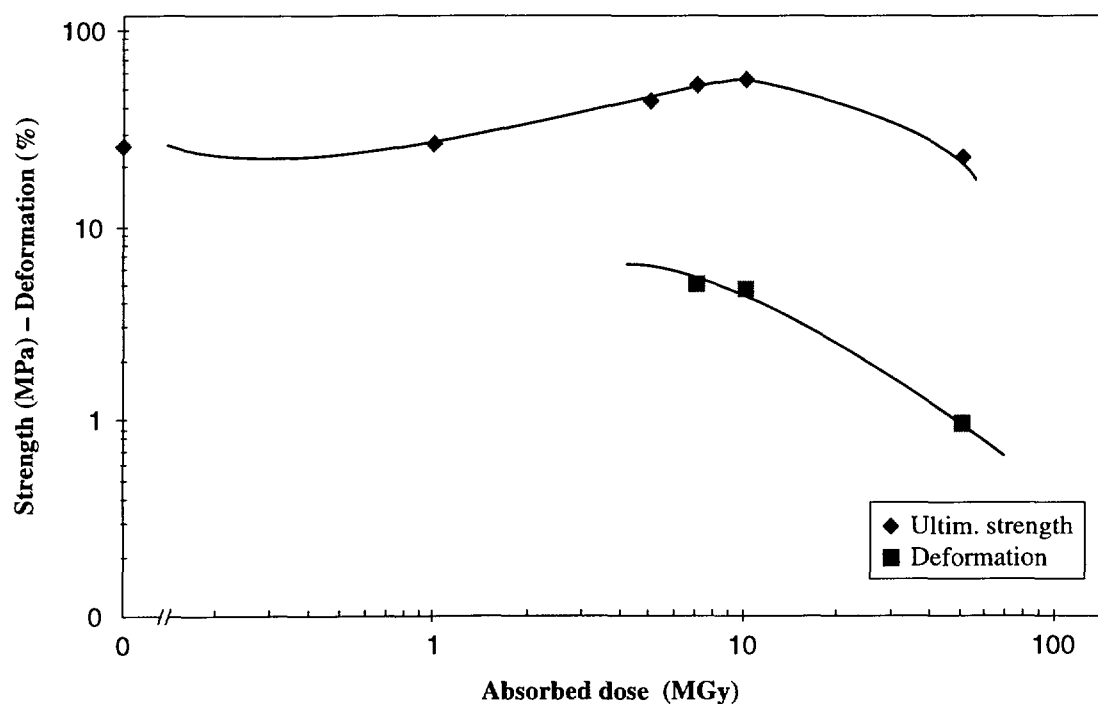

Material: **Polyarylamide base thermoplastic**
Type: **IXEF 1002**

TIS No. **R 523**

Supplier: **Solvay**
Remarks: **compound, + 30% glass fibre**

UL 94: **HB**
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	274±3	2.71±0.03	11.3±0.1
6	1	247±9	2.40±0.10	11.4±0.1
200	3	189±7	1.88±0.07	10.9±0.1
200	10	151±2	1.55±0.02	10.8±0.1
200	30	144±3	1.55±0.02	10.9±0.1
200	100	105±10	1.35±0.07	7.65±1.0

Critical property = flexural strength

Radiation index (RI) = 7.5 at a mean dose rate of 200 kGy/h

Radiation effect on insulating resin R 523

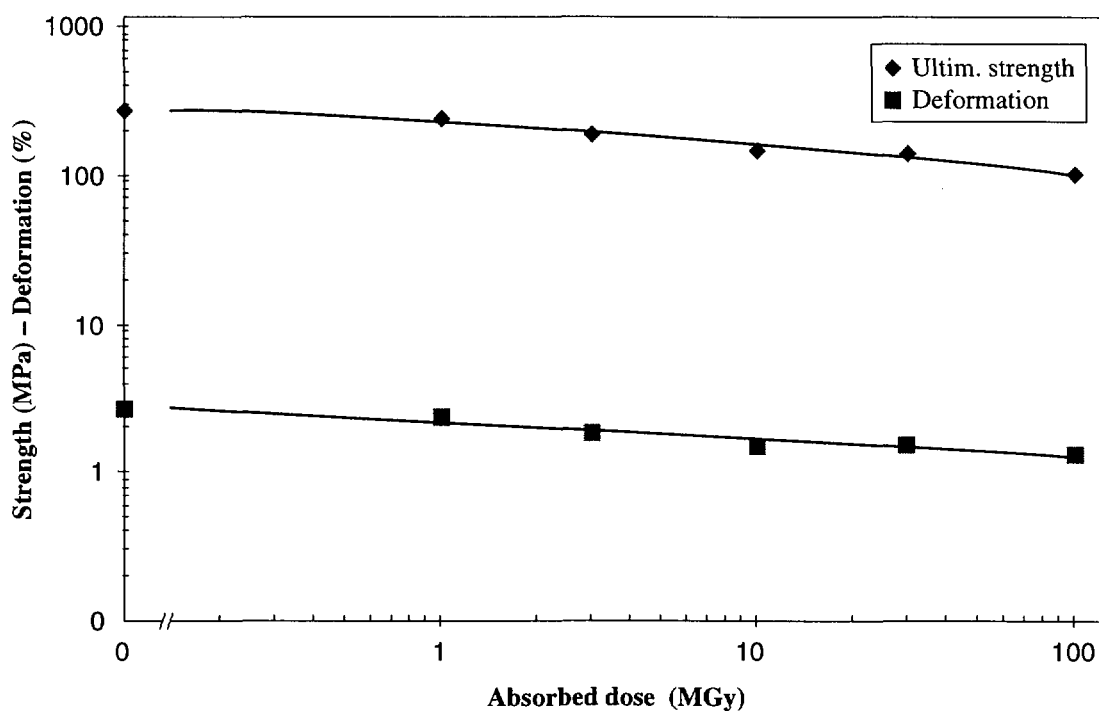

Material: **Polyarylamide base thermoplastic**
 Type: **IXEF 1501**

TIS No. **R 524**

Supplier: **Solvay**
 Remarks: compound, + 30% glass fibre
 contains bromine as flame retardant

UL 94: HB

LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	271 $\pm$ 7	2.62 $\pm$ 0.07	11.8 $\pm$ 0.2
6	1	254 $\pm$ 5	2.37 $\pm$ 0.07	11.8 $\pm$ 0.1
200	3	194 $\pm$ 7	1.84 $\pm$ 0.06	11.4 $\pm$ 0.1
200	10	158 $\pm$ 4	1.69 $\pm$ 0.21	11.4 $\pm$ 0.1
200	30	147 $\pm$ 9	1.50 $\pm$ 0.10	11.3 $\pm$ 0.2

Critical property = flexural strength

Radiation index (RI) = > 7.5 at a mean dose rate of 200 kGy/h

Radiation effect on insulating resin R 524

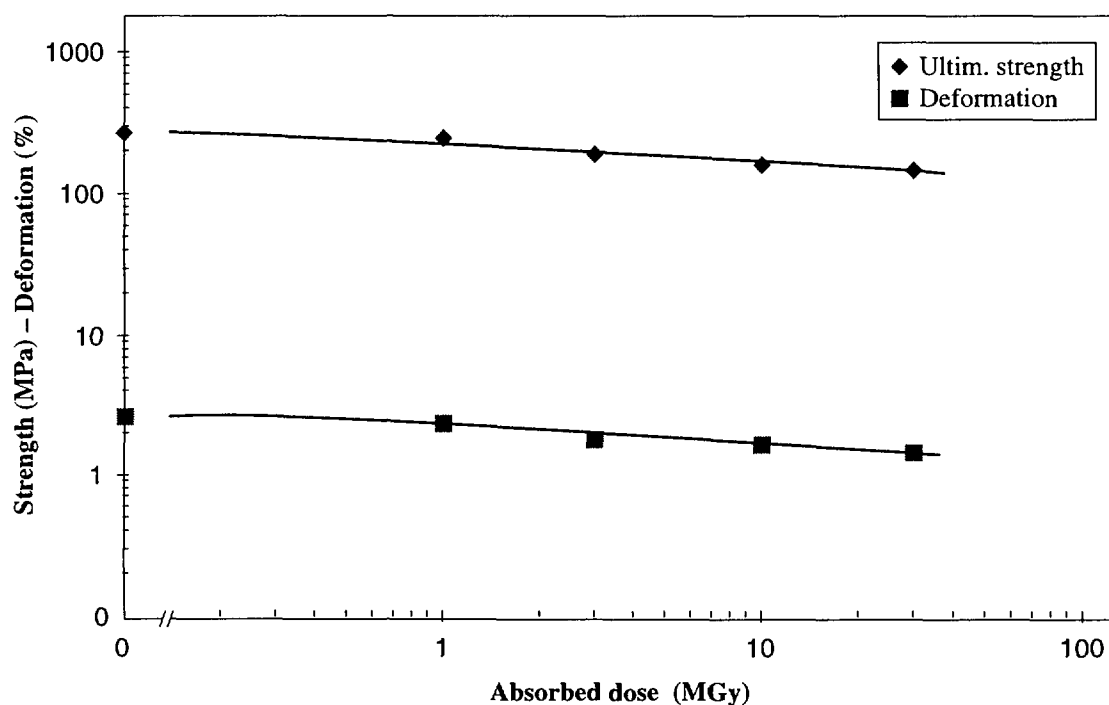

Material: **Polyamide (PA) 4.6**
Type: **Ertalon**

TIS No. **R 526**

Supplier: **Erta-Epec**
Remarks: **via Angst and Pfister**

UL 94: **V-2**
LOI: **24%**

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	125±2	5.2±0.3	5.8±0.3
240	3	128±9	4.5±0.4	5.6±0.6
0.5	3	92±7	7.4±1.3	2.0±0.2
1.0	7	50±6	1.7±0.2	3.0±0.1
210	10	61±7	2.0±0.1	3.6±0.4
220	50	32±9	2.0±0.7	2.0±0.2

Critical property = deformation

Radiation index (RI) = 6.7 at a mean dose rate of 220 kGy/h

Radiation index (RI) = < 6.5 at a mean dose rate of 500 Gy/h

Radiation effect on insulating resin R 526

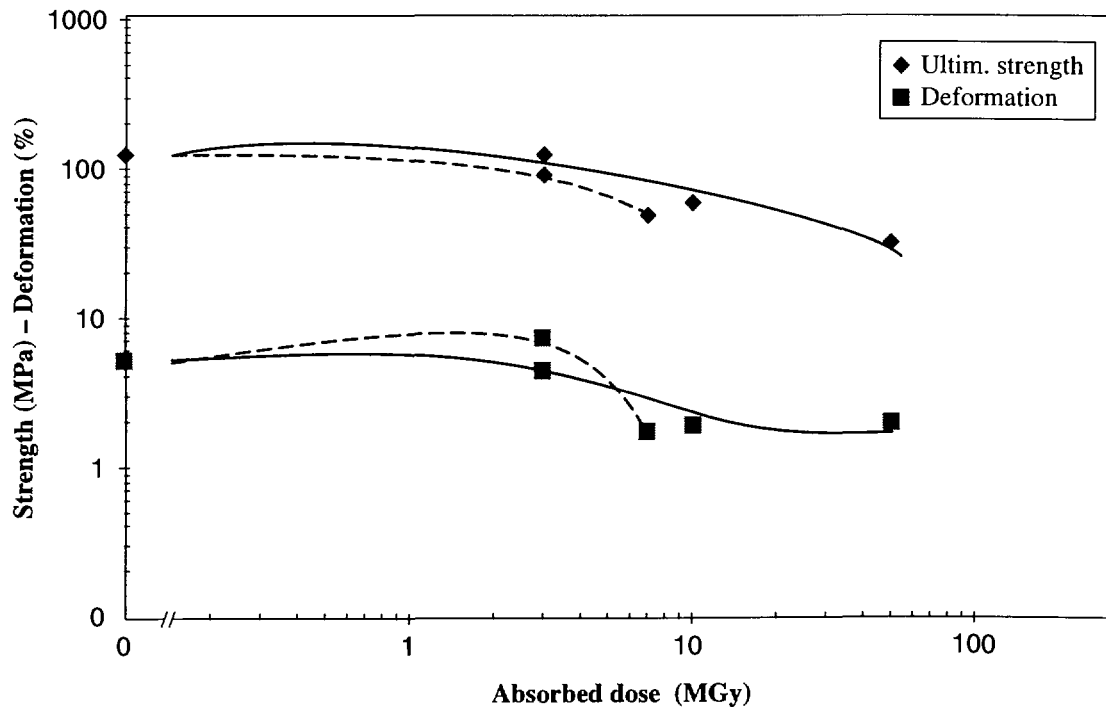

Comment: Dotted lines correspond to long-term irradiation.

Material: **Polyamide (PA) 6**
Type **Ertalon 6 PLA**

TIS No. **R 528**

Supplier: **Erta-Epec**
Remarks: **moulded**

UL 94: **V-2**
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	98±2	> 15	2.5±0.1
4	0.5	101±1	> 15	2.6±0.1
4	1	101±3	> 15	2.6±0.2
220	3.2	91±8	3.48±0.03	3.11±0.03
220	10	53±6	1.76±0.24	3.2±0.1

Critical property = deformation

Radiation index (RI) = 6 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 528

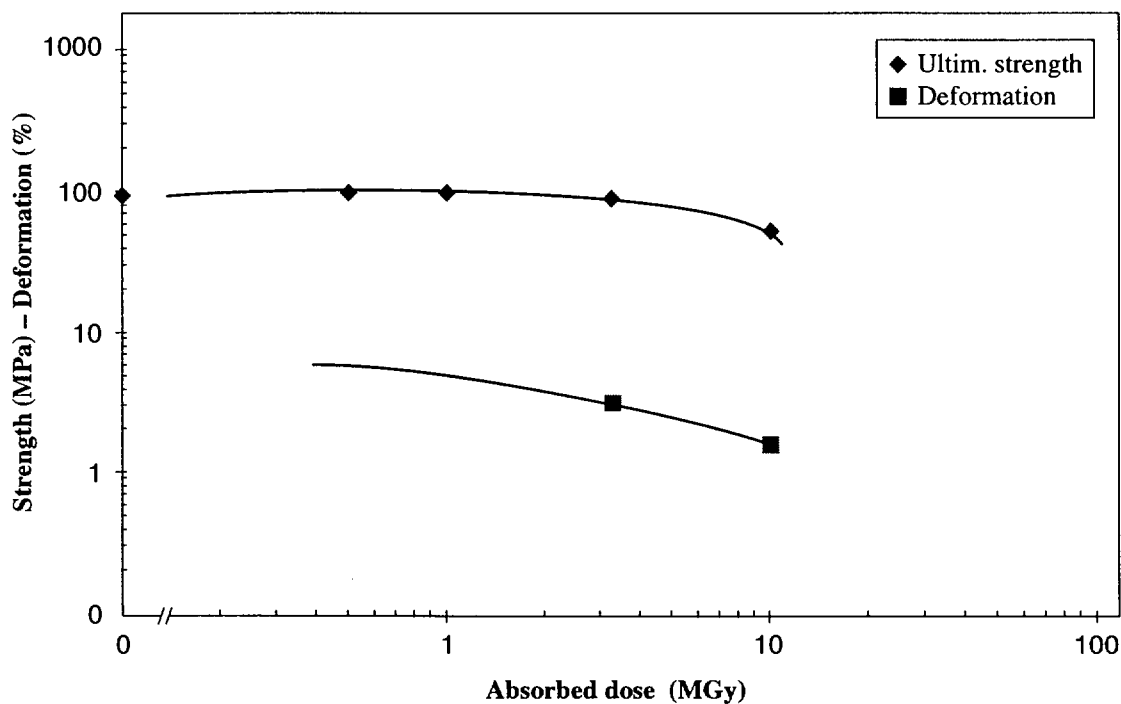

Material: **Polyamide PA 6**
Type: **Ertalon LFX**

TIS No. **R 529**

Supplier: **Erta-Epec**
Remarks: **= 6 PLA + lubricant**

UL 94: V-2
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	84.4±1.3	> 15	2.07±0.05
4.0	1	85.4±3.6	> 15	2.18±0.22
220	3.20	105.3±3.2	6.82±0.64	2.80±0.02
220	10	34.5±4.9	1.32±0.18	2.80±0.09

Critical property = deformation

Radiation index (RI) = 6 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 529

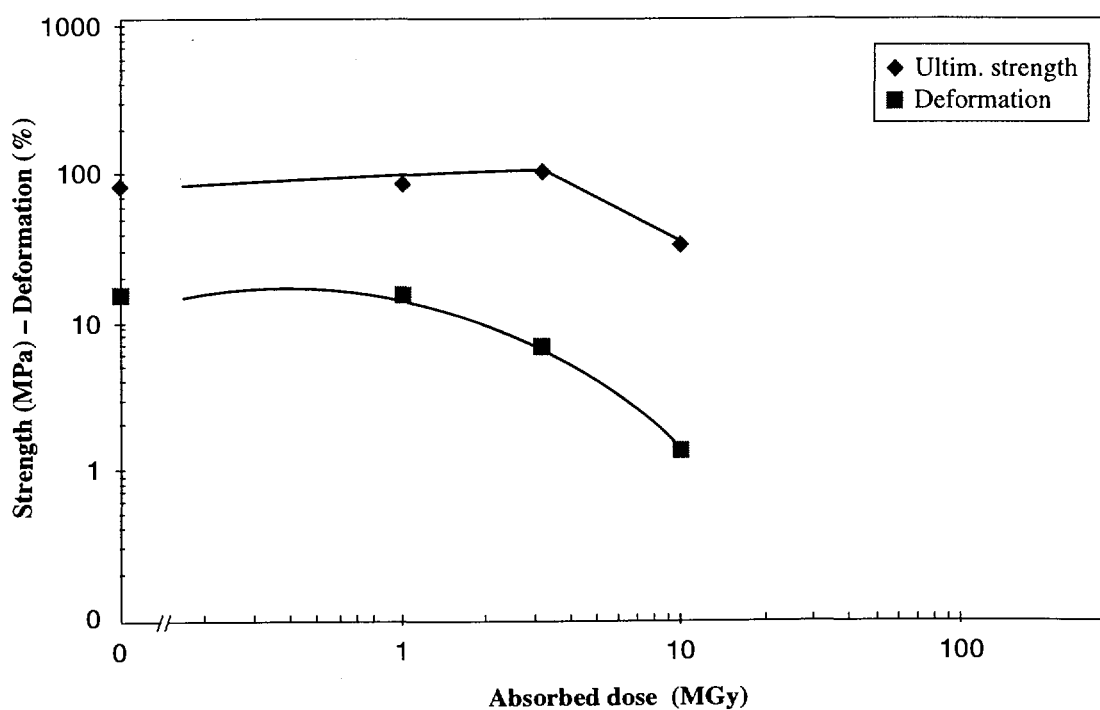

Material: **Polyamide PA 6**
Type **Ertalon 6 XAU+**

TIS No. **R 530**

Supplier: **Erta-Epec**
Remarks: **= 6 PLA + heat stabilizer**

UL 94: **V-2**
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	76.1±2.2	> 15	1.84±0.08
4.0	1	77.1±2.1	> 15	1.84±0.12
220	3.2	107.6±1.3	13.8±2.4	2.42±0.12
220	10	51.9±13.1	1.7±0.4	3.18±0.06

Critical property = deformation

Radiation index (RI) = 6.5 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 530

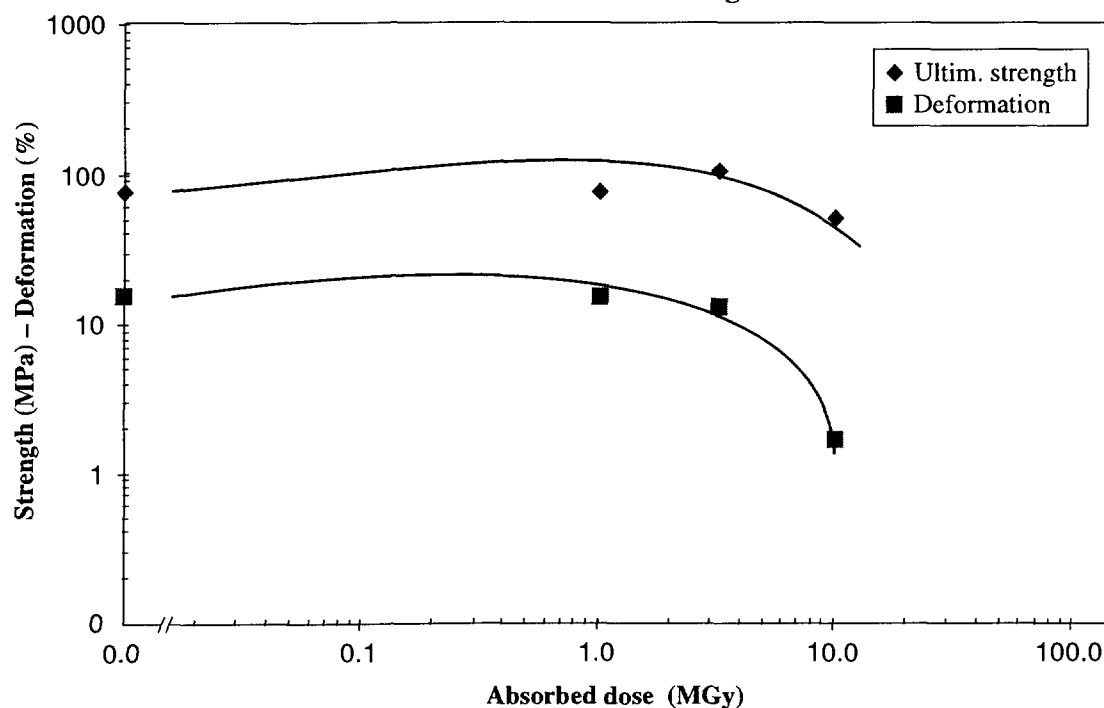

Material: **Polyethylene terephthalate PETP**
 Type **Ertalyte**

TIS No. **R 531**

Supplier: **Erta-Epec**
 Remarks: **no additives**

UL 94: **HB**
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	135±2	> 15	3.28±0.12
4.00	0.50	129±5	8.57±4.71	3.25±0.06
4.00	1	105±9	3.59±0.52	3.20±0.09
220	3	47.4±7	1.44±0.20	3.53±0.04
220	10	13±***	0.31±***	3.66±***

Critical property = deformation

Radiation index (RI) = 5.7 at a mean dose rate of 4 kGy/h

Radiation effect on insulating resin R 531

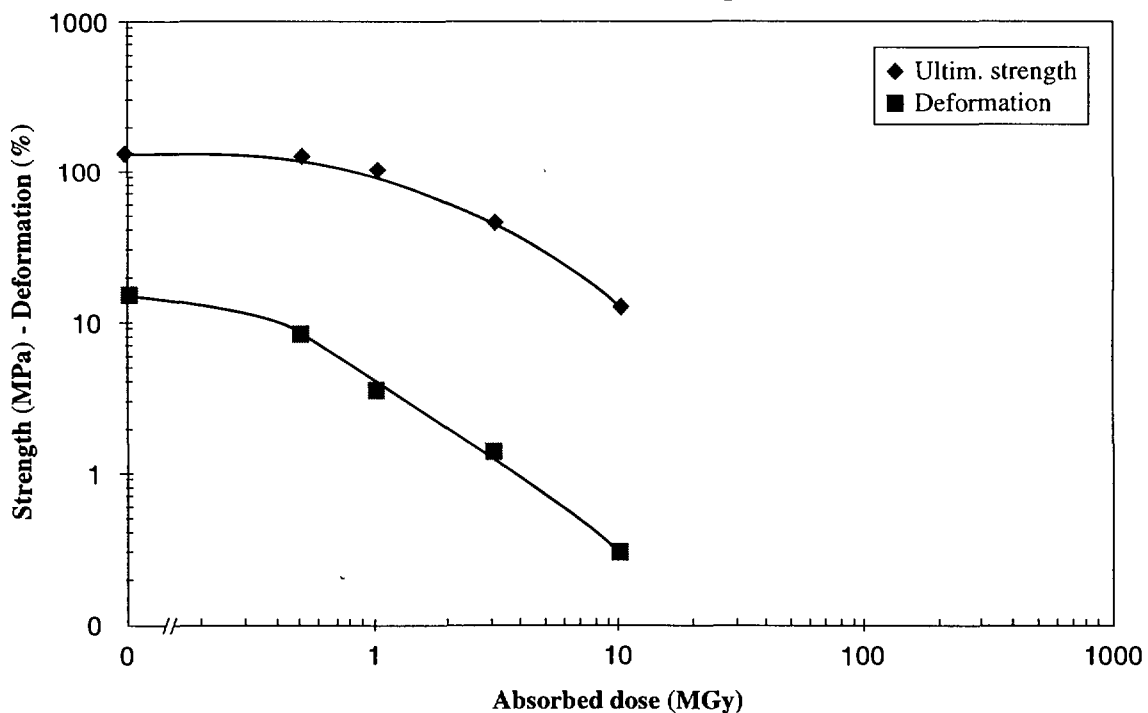

Comment: At 10 MGy, only one sample was tested; the others were already broken.

Material: **Polyethylene terephthalate PETP**
 Type **Ertalyte TX**

TIS No. **R 532**

Supplier: **Erta-Epec**
 Remarks: **= PETP + lubricant**

UL 94: **HB**
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	120±4	6.37±0.27	3.05±0.05
4.0	0.50	107±3	4.16±0.11	3.20±0.08
4.0	1	64±14	1.75±0.15	3.18±0.19
220	3	24±3	0.77±0.08	3.48±0.14
220	10	15±1	0.57±0.04	3.14±0.23

Critical property = deformation

Radiation index (RI) = 8 at a mean dose rate of 4 kGy/h

Radiation effect on insulating resin R 532

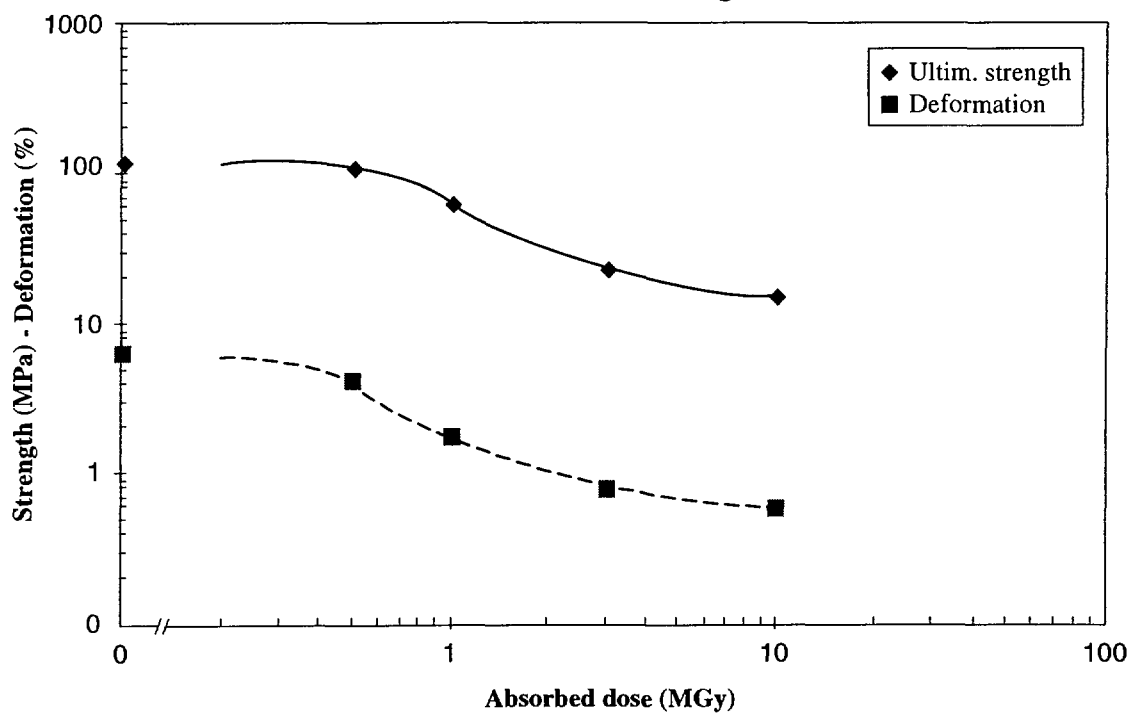

Material: **Polyetherimide**
Type: **Erta PEI**

TIS No. **R 533**

Supplier: **Erta-Epec**
Remarks: based on Ultem 1000


UL 94: V-0
LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	171±1	> 15	3.15±0.05
4.0	1	174±2	> 15	3.23±0.08
220	3	180±1	> 15	3.27±0.07
220	10	158±29	10.9±5.6	3.16±0.02
220	50	102±7	3.3±0.2	3.31±0.04

Critical property = deformation

Radiation index (RI) = > 7.7 at a mean dose rate of 220 kGy/h

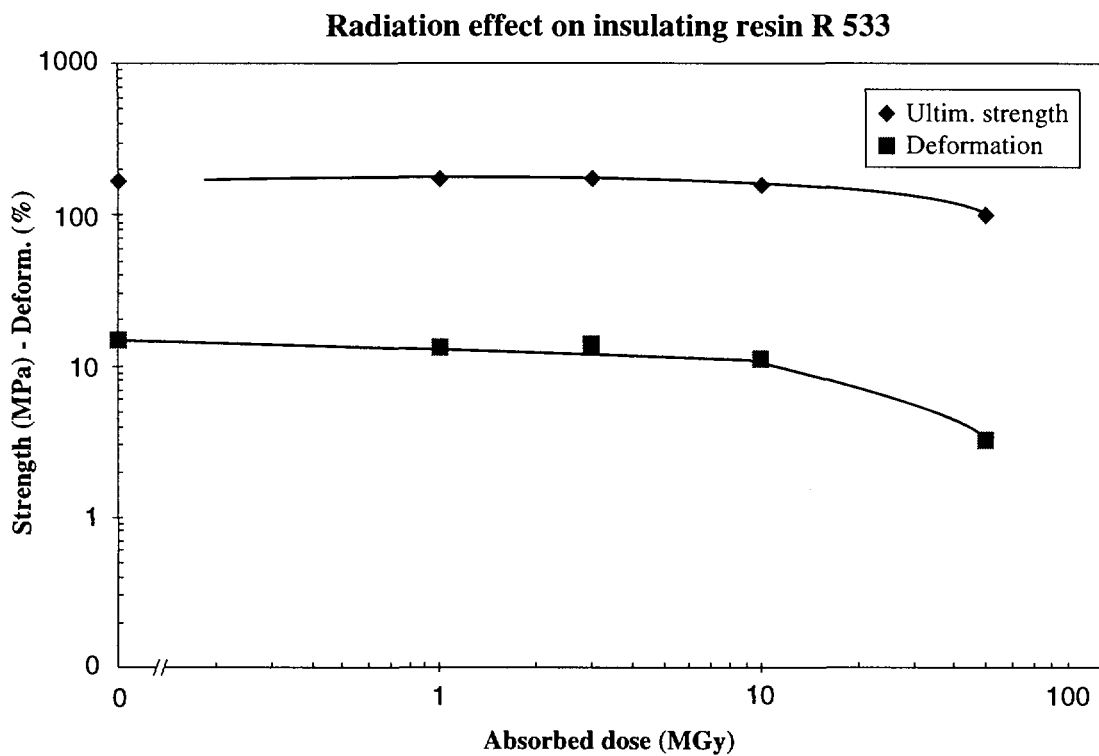

Material: **Polyethersulfone**
Type **Erta PES**

TIS No. **R 534**

Supplier: **Erta-Epec**
Remarks: based on Victrex

UL 94: V-0
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0.00	141 $\pm$ 1	> 15	2.70 $\pm$ 0.05
4.0	0.50	134 $\pm$ 1	> 15	2.79 $\pm$ 0.12
4.0	1	132 $\pm$ 5	11.6 $\pm$ 4.6	2.92 $\pm$ 0.07
220	3	46.9 $\pm$ 3.4	1.7 $\pm$ 0.1	3.07 $\pm$ 0.06
220	10	14.3 $\pm$ 6.3	0.5 $\pm$ 0.2	3.28 $\pm$ 0.27

Critical property = deformation

Radiation index (RI) = 6.3 at a mean dose rate of 220 kGy/h

Radiation effect on Erta-PES R 534

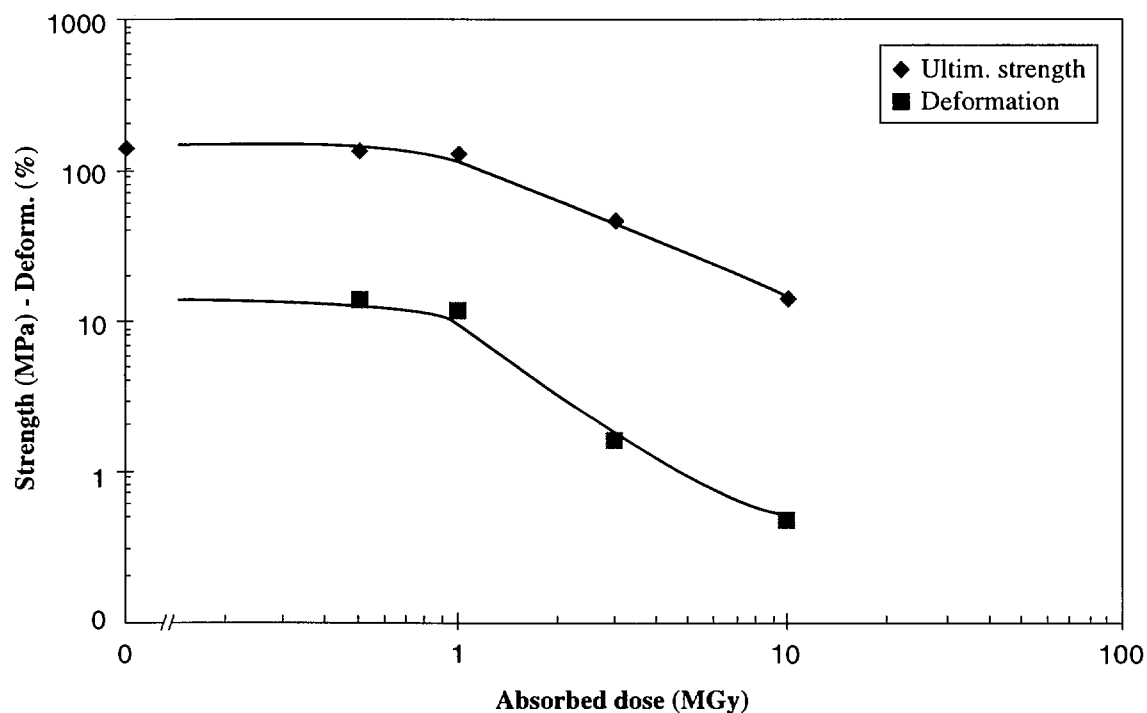

Material: **Polysulfone**
Type **Erta PSU**

TIS No. **R 535**

Supplier: **Erta-Epec**
Remarks: based on Udel P 3500

UL 94: HB
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	120±1	> 15	2.59±0.05
4	0.50	114±0.3	> 15	2.70±0.05
4	1	102±11	9.6±6.7	2.75±0.04
220	3	58±3	2.08±0.11	2.95±0.03
220	10	19±3	0.71±0.09	3.02±0.12

Critical property = flexural strength

Radiation index (RI) = 6.5 at a mean dose rate of 110 kGy/h

Radiation effect on PSU R 535

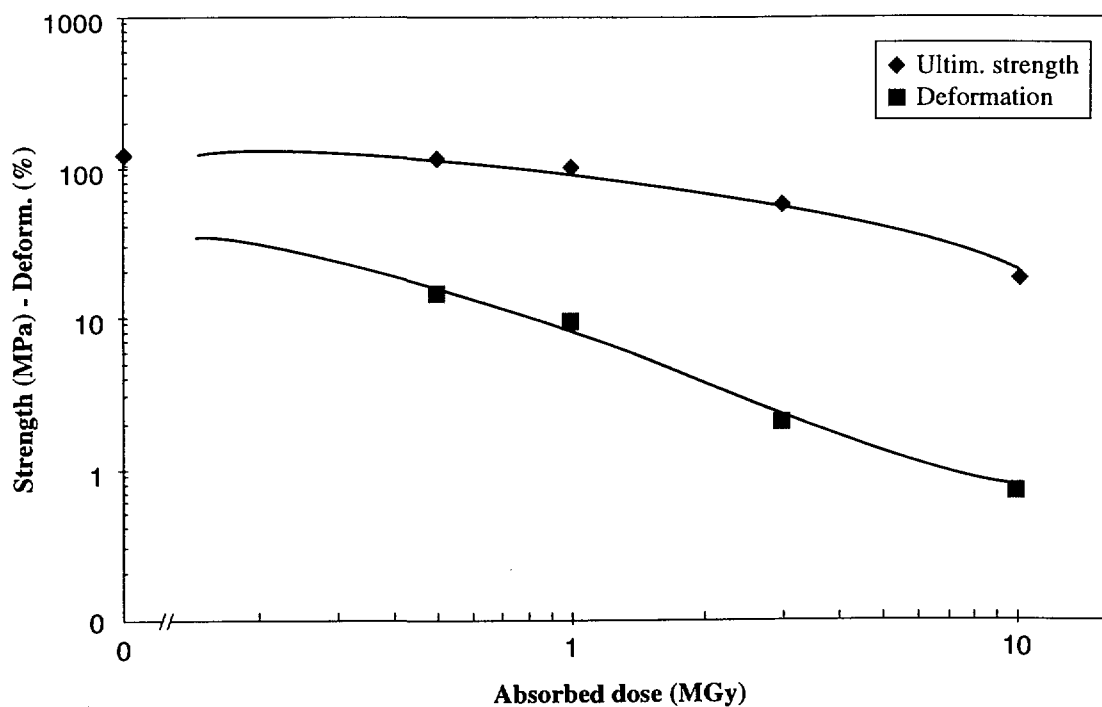

Material: **Polyamide PA 6**
Type: **Ertalon 6 SA**

TIS No. **R 536**

Supplier: **Erta-Epec**
Remarks: **extruded**

UL 94: **V-2**
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0.10	63.4±1.7	> 15	1.38±0.03
4.0	1	72.7±1.0	> 15	1.59±0.05
220	3.30	100.7±0.9	> 15	2.37±0.70
220	10	109.9±36	9.47±6.13	2.88±0.04

Critical property = deformation

Radiation index (RI) ~ 7 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 536

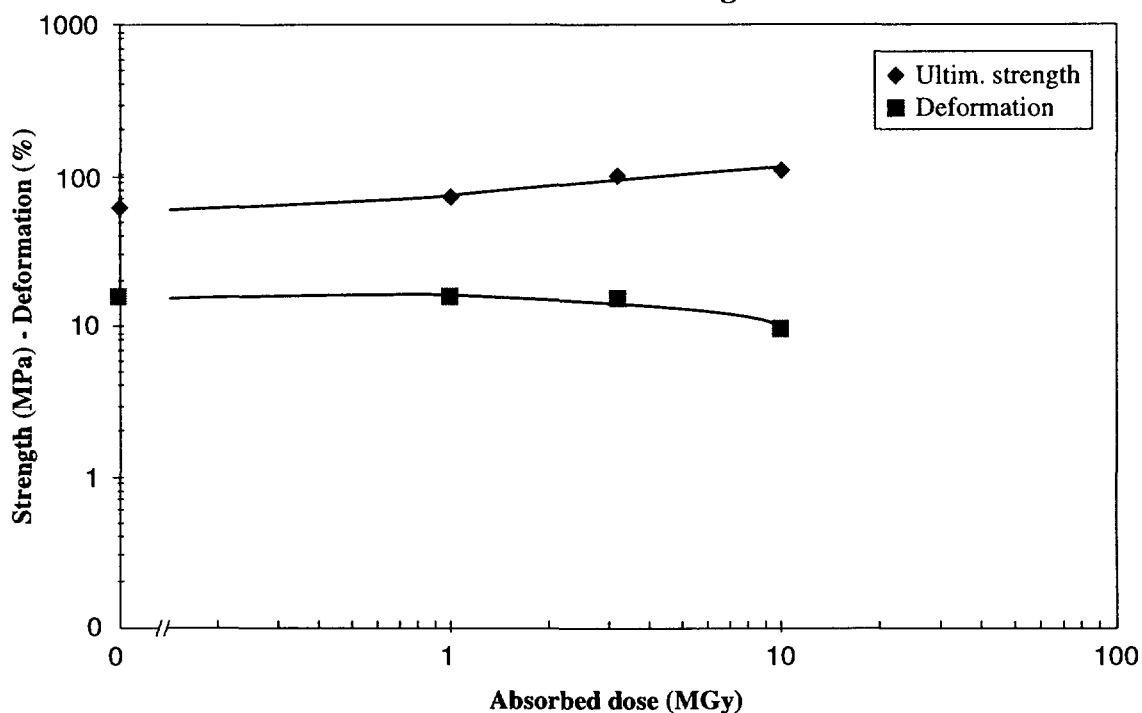

Material: **Polyamide PA 66**
 Type **Ertalon 66 SA**

TIS No. **R 537**

Supplier: **Erta-Epec**
 Remarks: **extruded**

UL 94: **V-2**
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	102±3	> 15	2.4±0.1
4	1	110±1	> 15	2.6±0.1
220	5	125±10	7.7±2.4	3.0±0.1
230	10	67±16	2.1±0.5	3.2±0.1

Critical property = deformation

Radiation index (RI) = 6.5 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 537

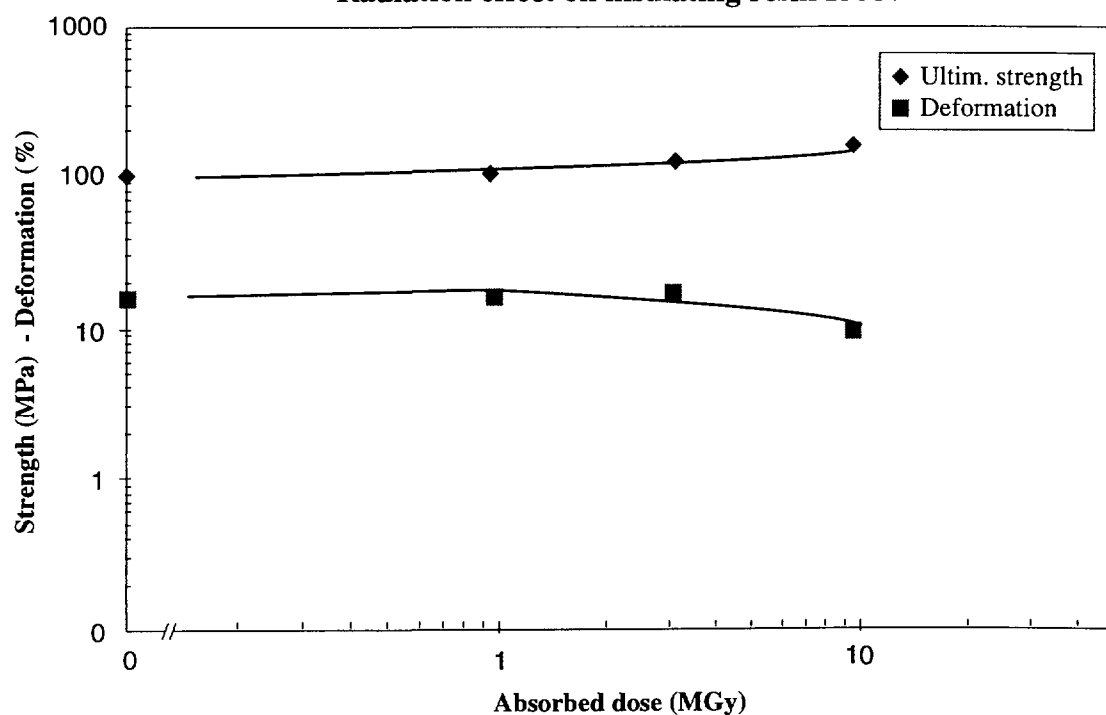

Material: **Polyarylate**
Type **ISARYL 15 M**

TIS No. **R 542**

Supplier: **Isonova**
Remarks: **moulded**


UL 94: **V-0**
LOI: **33%**

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	110±4	> 12	2.4±0.1
3.6	0.1	107±2	> 12	2.4±0.1
220	1	107±3	> 12	2.5±0.1
1.0	2	105±2	> 12	2.7±0.1
220	10	83±11	6.1±5.3	2.9±0.1
230	29	31±13	1.1±0.4	3.1±0.0
180	80	26±5	0.8±0.2	3.4±0.2

Critical property = deformation

Radiation index (RI) = 6.3 at a mean dose rate of 220 kGy/h

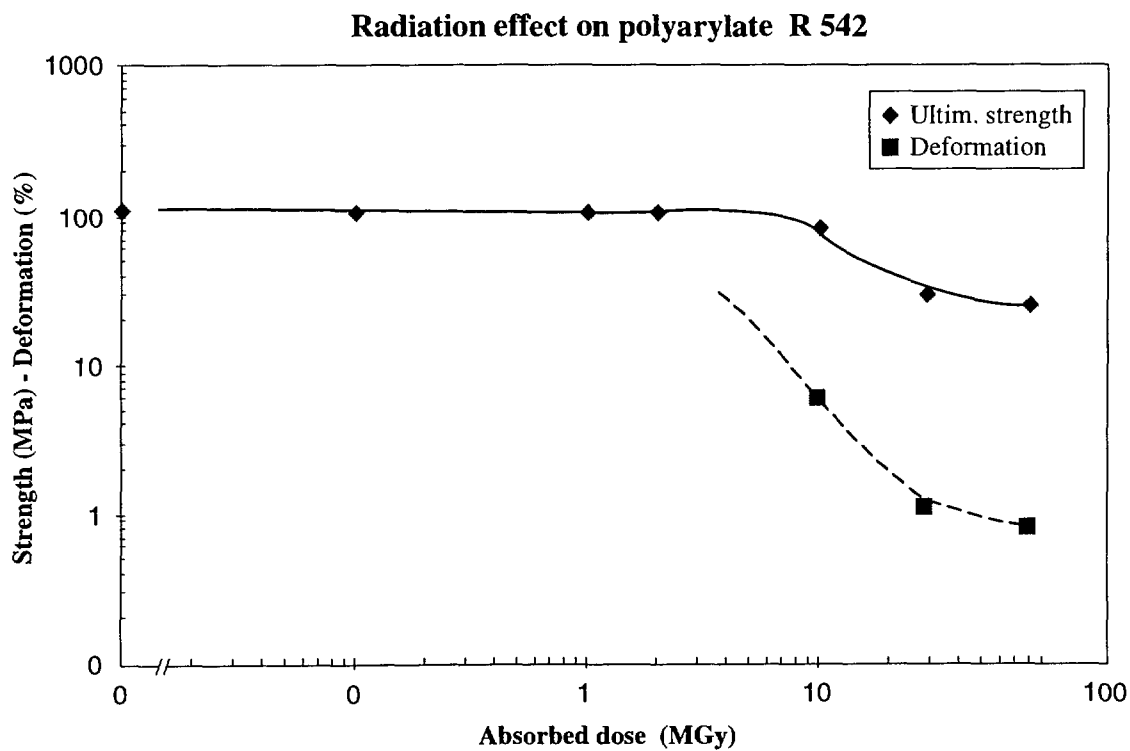

Material: **Polyaryl ether ketone (PAEK)**
 Type **Stilan/Ultrapek**

TIS No. **R 563**

Supplier: **Raychem BASF**
 Remarks:

UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)


Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	153±4	> 6	5.46±0.38
1	3	153±7	> 6	5.46±0.42
1	5	132±2	> 6	4.52±0.22
225	30	117±5	> 6	4.12±0.18

Critical property = flexural strength

Radiation index (RI) = > 7.5 at a mean dose rate of 225 kGy/h

Radiation index (RI) = > 6.7 at a mean dose rate of 1 kGy/h

Radiation effect on PAEK - R 563

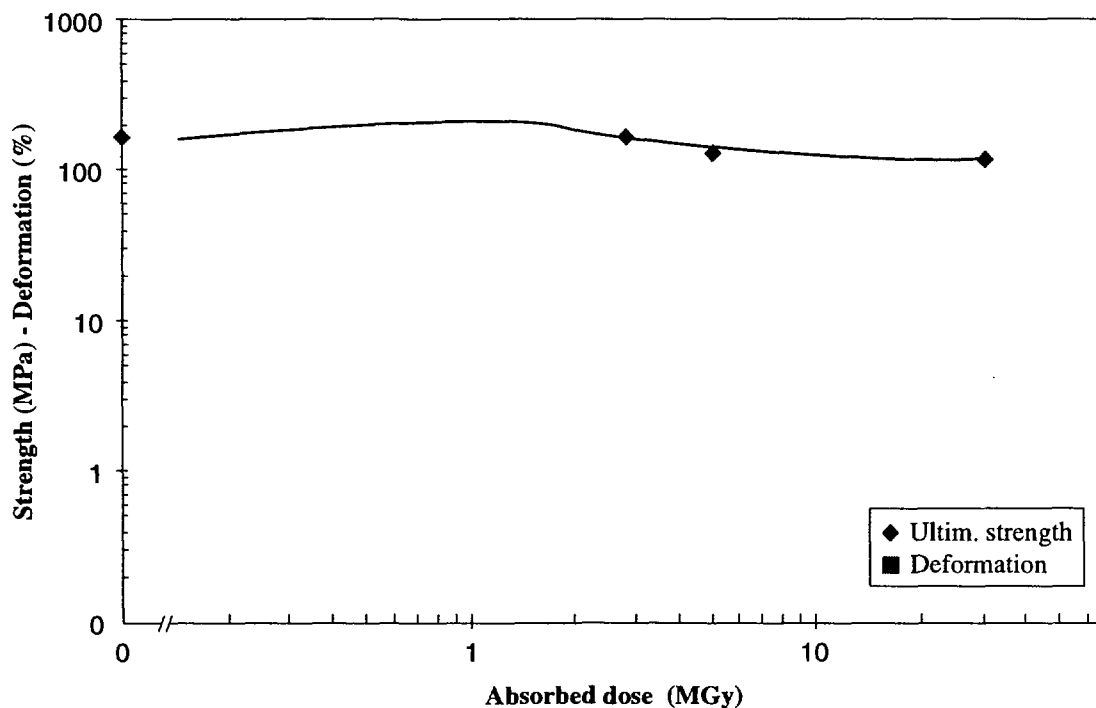

Comment: Samples don't break.

Material: **Polyimide**
Type **Vespel SP-1**

TIS No. **R 568**

Supplier: **DuPont**
Remarks: via Erta-Epec

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	91.9±7.7	4.18±0.64	2.52±1.22
225	30	80.8±15.2	3.09±0.75	3.20±0.07

Critical property = flexural strength

Radiation index (RI) = > 7.5 at a mean dose rate of 225 kGy/h

Radiation effect on Vespel SP-1 - R 568

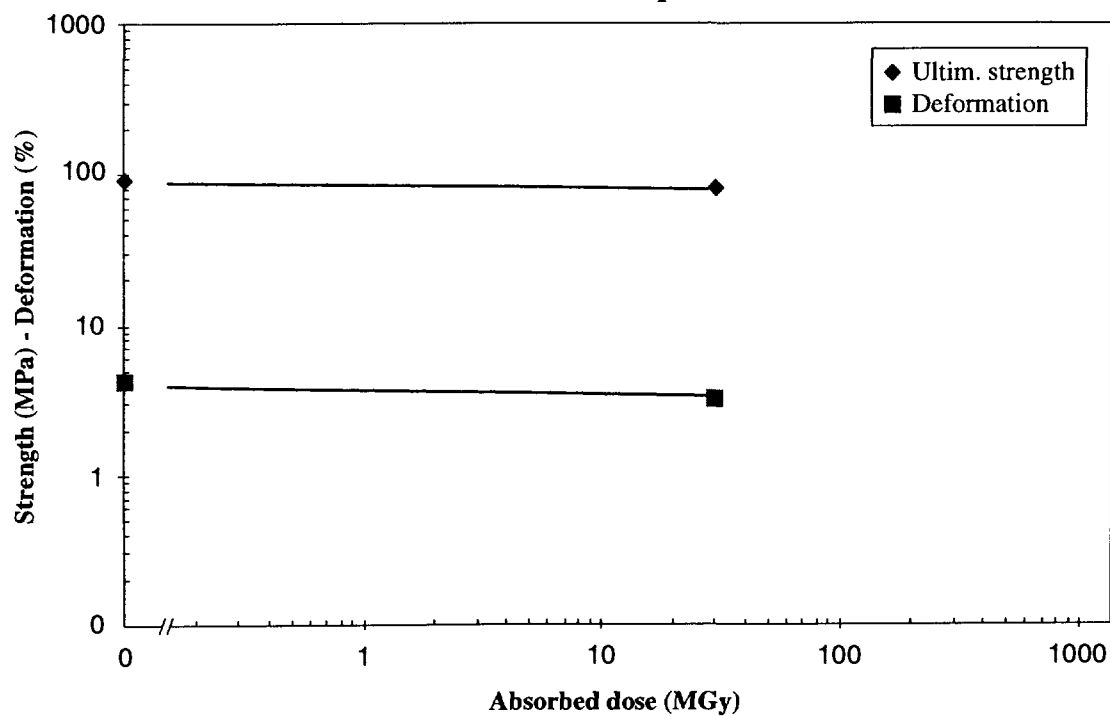

Material: **Polyphenylsulfone (PPS) + glass fibres**
 Type: **Ertaxel**

TIS No. **R 569**

Supplier: **Erta-Epec**
 Remarks: contains PTFE as lubricant

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	89.3±2.3	3.32±0.04	3.29±0.09
225	30	64.5±2.6	1.99±0.09	3.52±0.13

Critical property = flexural strength

Radiation index (RI) > 7.5 at a mean dose rate of 225 kGy/h

Radiation effect on Ertaxek - R 569

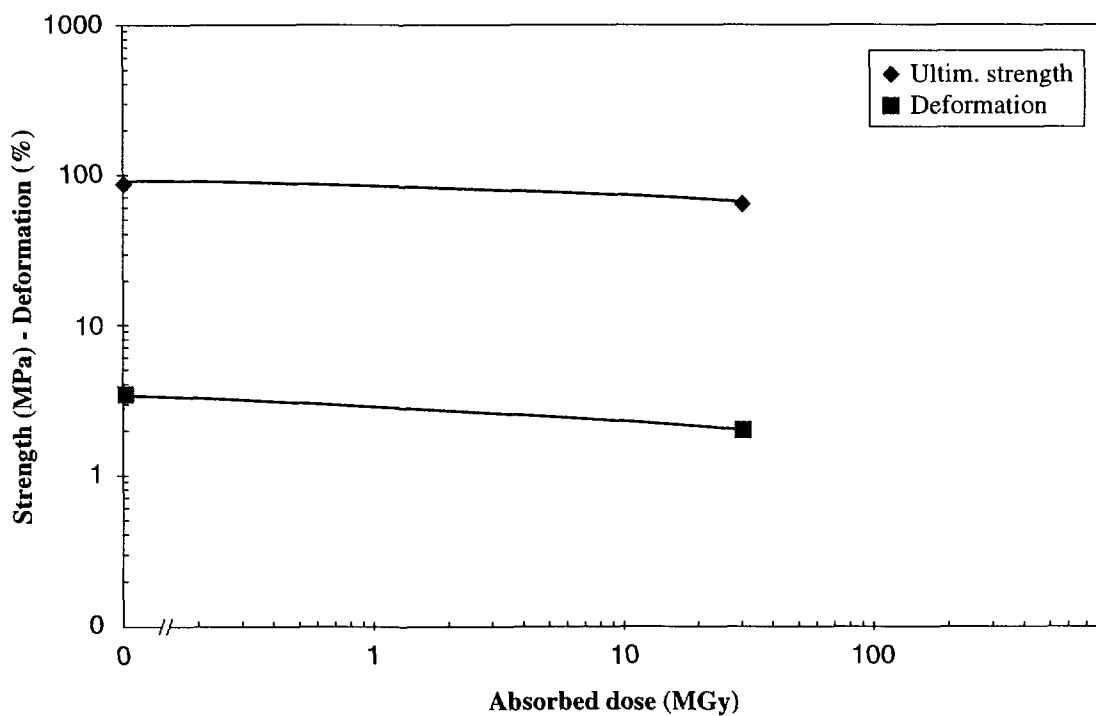

Material: **Polyamide (PA)66 + 30% glass fibres**
 Type: **Ertalon 66 GF 30**

TIS No. **R 570**

Supplier: **ERTA**
 Remarks:


UL 94: n.m.
 LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	197±1	4.58±0.31	5.76±0.27
0.1	0.5	117±8	9.95±1.36	3.18±0.44
1	2	188±2	3.11±0.08	6.19±0.24
220	3.4	110±9	4.14±0.54	3.84±0.30
240	10	71±15	3.91±1.07	2.52±0.18

Critical property = flexural strength

Radiation index (RI) 6.7 at a mean dose rate of 240 kGy/h

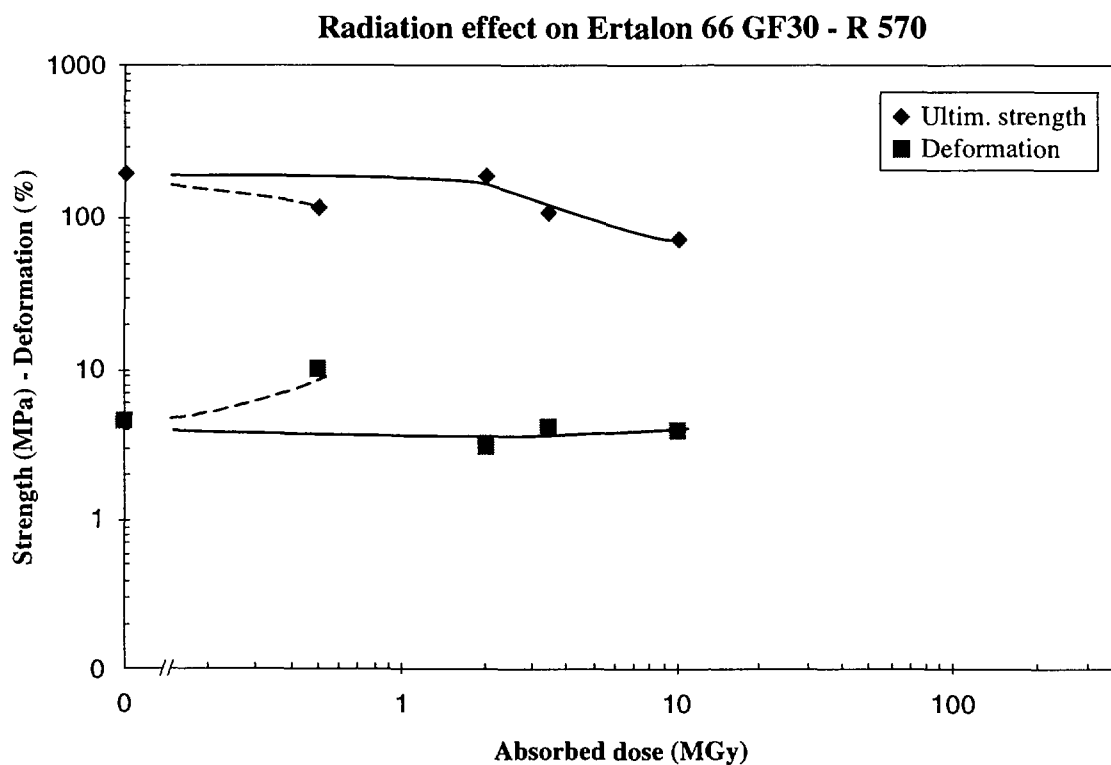

Comments: Dotted lines correspond to long-term irradiation.
 Young's modulus is also affected by radiation.

Material: **Polyoximethylene resin (POM)**
 Type: **Ertacetal C**

TIS No. **R 571**

Supplier: **Erta - Epec**
 Remarks: **also called acetal resin**

UL 94:
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	101±2	> 15	3.09±0.04
0.01	0.005	101±2	> 15	2.95±0.06
0.04	0.024	74±3	3.07±0.21	3.00±0.14
4	0.200	4±0.6	0.15±0.01	2.72±0.30

Critical property = deformation

Radiation index (RI) = ≈ 4 at a mean dose rate of 40 kGy/h

Radiation effect on Acetal resin (POM) - R 571

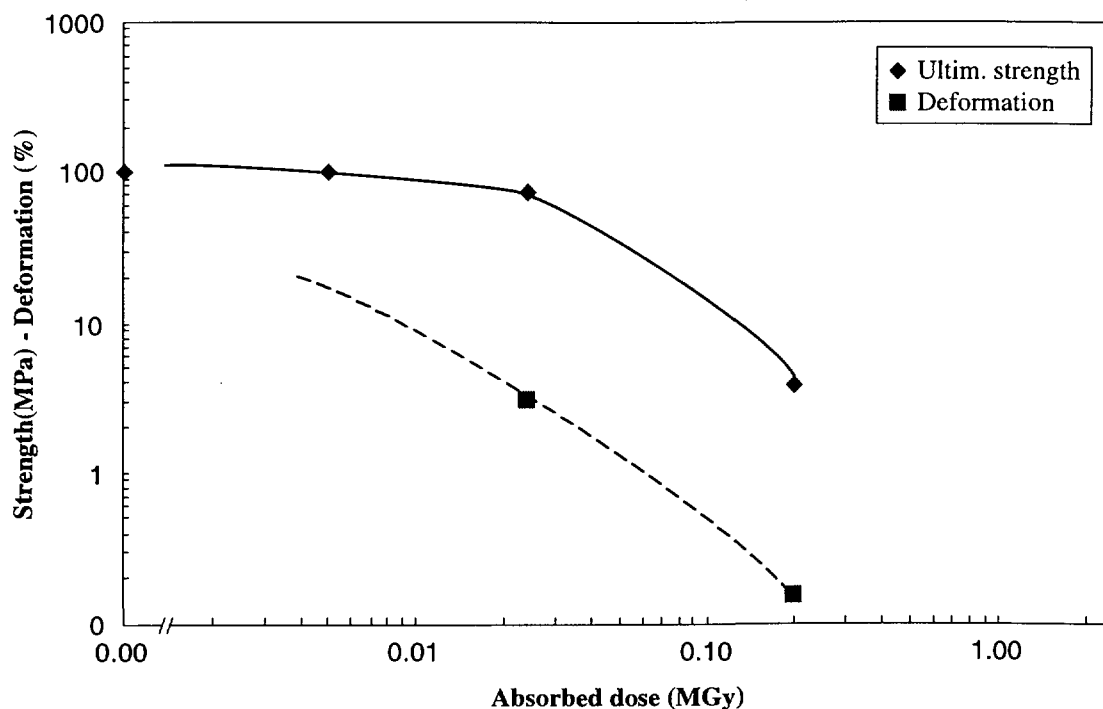

Comment: Should not be used in a radiation environment.

Material: **Polyethylene Cestidur**
Type **Borolene 4505**

TIS No. **R 572**

Supplier: **ERTA**
Remarks:

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	23.8$\pm$0.2	> 15	1.11$\pm$0.06
4	0.2	28.7$\pm$0.9	> 15	1.47$\pm$0.07
4	0.5	32.3$\pm$0.4	7.90$\pm$0.30	1.63$\pm$0.02
1	1	28.9$\pm$0.6	5.24$\pm$0.43	1.62$\pm$0.05
220	3.4	31.4$\pm$0.7	4.01$\pm$0.15	1.49$\pm$0.06

Critical property = deformation

Radiation index (RI) = ~ 5.7 at a mean dose rate of 1 kGy/h

Radiation effect on Cestidur PE - R 572

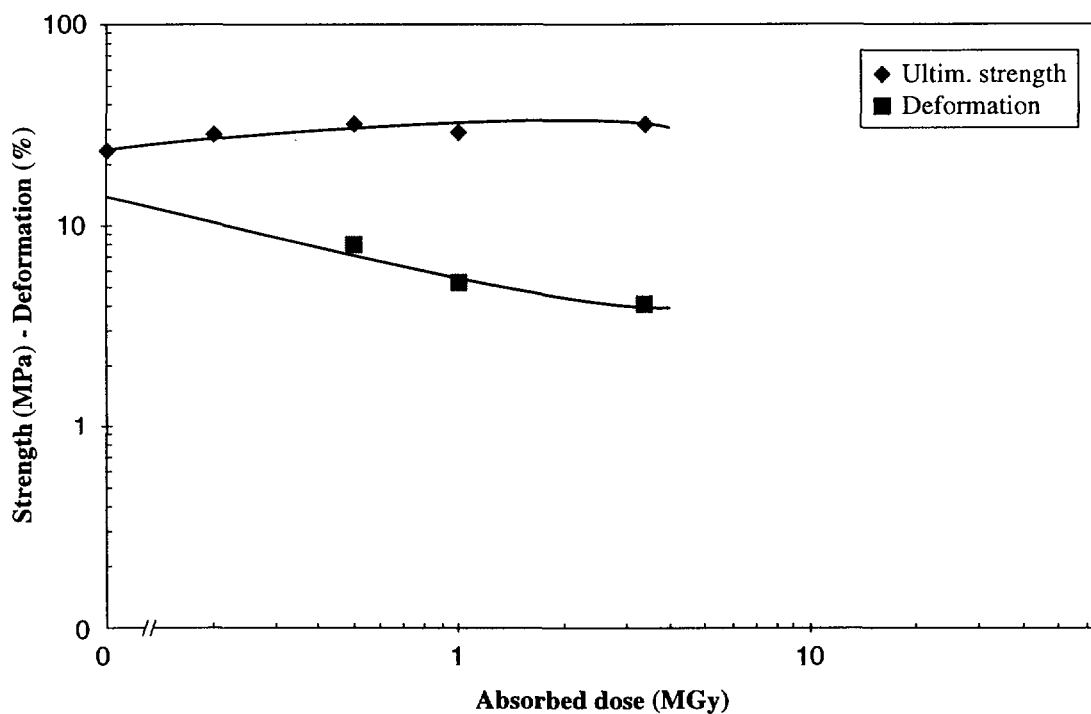

Comment: Samples do not break before 0.5 MGy.

Material: **Polyethylene Cestidur**
Type: **Cestilene HD 1000**

TIS No. **R 573**

Supplier: **ERTA - EPEC**
Remarks:

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	23.3±0.5	> 15	0.81±0.01
4	0.2	31.2±0.8	> 15	1.18±0.04
4	0.5	34.4±1.1	> 15	1.29±0.06
1	1	38.6±0.4	> 15	1.56±0.07
220	3.4	44.7±0.8	8.6±0.9	1.34±0.07

Critical property = deformation

Radiation index (RI) = ~ 6 at a mean dose rate of 220 kGy/h

Radiation effect on Cestidur PE - R 573

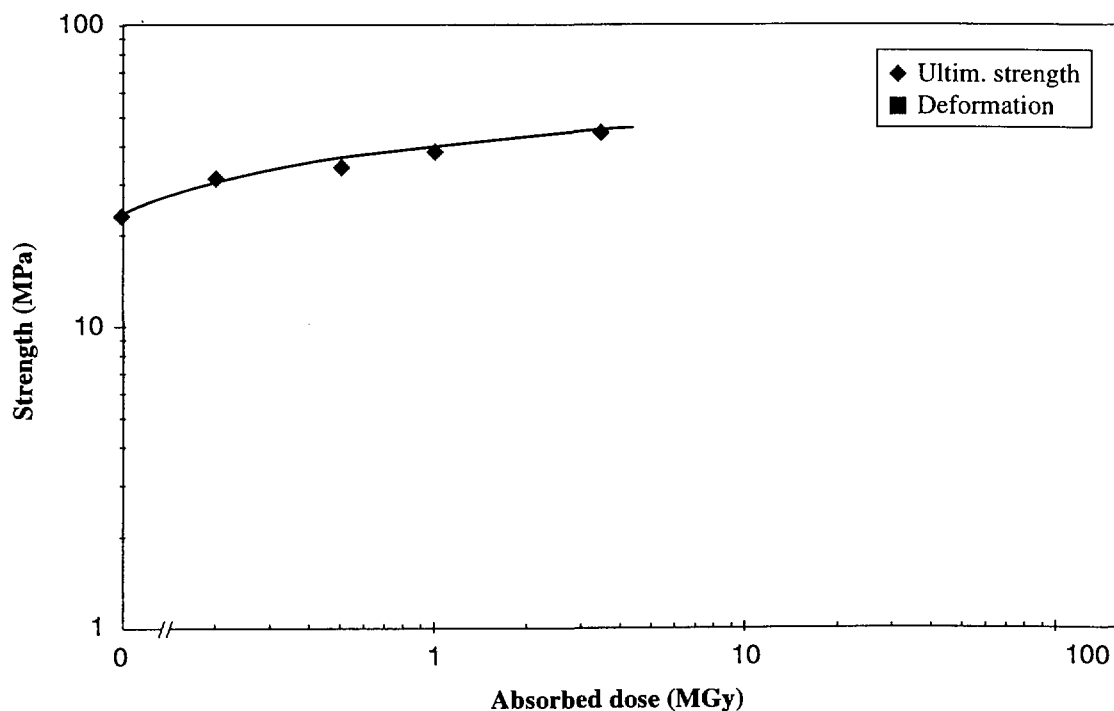

Material: **Polyethylene Cestidur**
Type **Cestilene HD 500**

TIS No. **R 574**

Supplier: **ERTA - EPEC**
Remarks:


UL 94: n.m.
LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	37.1±0.8	> 15	1.69±0.08
4	0.2	46.9±0.4	> 15	2.10±0.04
4	0.5	57.6±0.5	> 15	2.47±0.08
1	1	54.6±1.7	> 15	2.31±0.10
220	3.4	61.7±0.9	9±0.3	2.02±0.03

Critical property = deformation

Radiation index (RI) = ~ 6.5 at a mean dose rate of 220 kGy/h

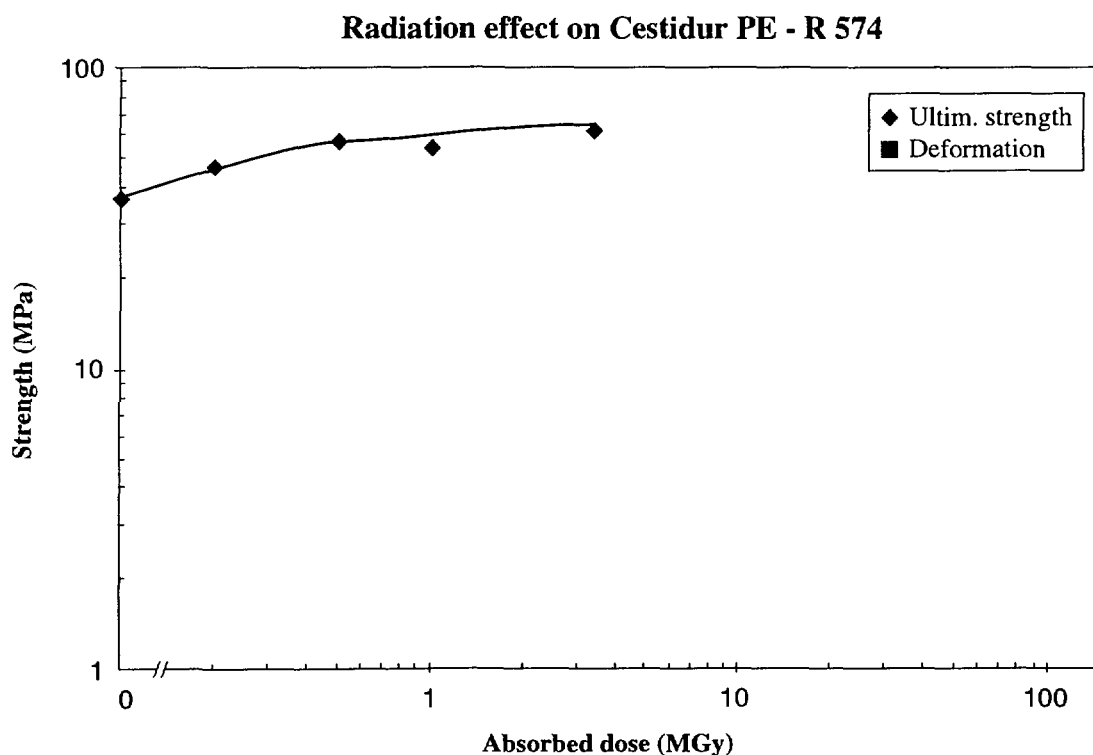

Comment: Samples do not break before 3.4 MGy.

Material: **Polyethylene Cestidur**
Type

TIS No. **R 575**

Supplier: **ERTA - EPEC**
Remarks:


UL 94: n.m.
LOI:

Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	22.7±0.2	> 15	0.78±0.01
4	0.2	30.0±0.3	> 15	1.09±0.04
4	0.5	33.1±0.4	> 15	1.20±0.04
1	1	36.3±0.2	> 15	1.39±0.05
220	3.4	41.7±0.3	9.3±0.1	1.19±0.03

Critical property = deformation

Radiation index (RI) = > 6.5 at a mean dose rate of 220 kGy/h

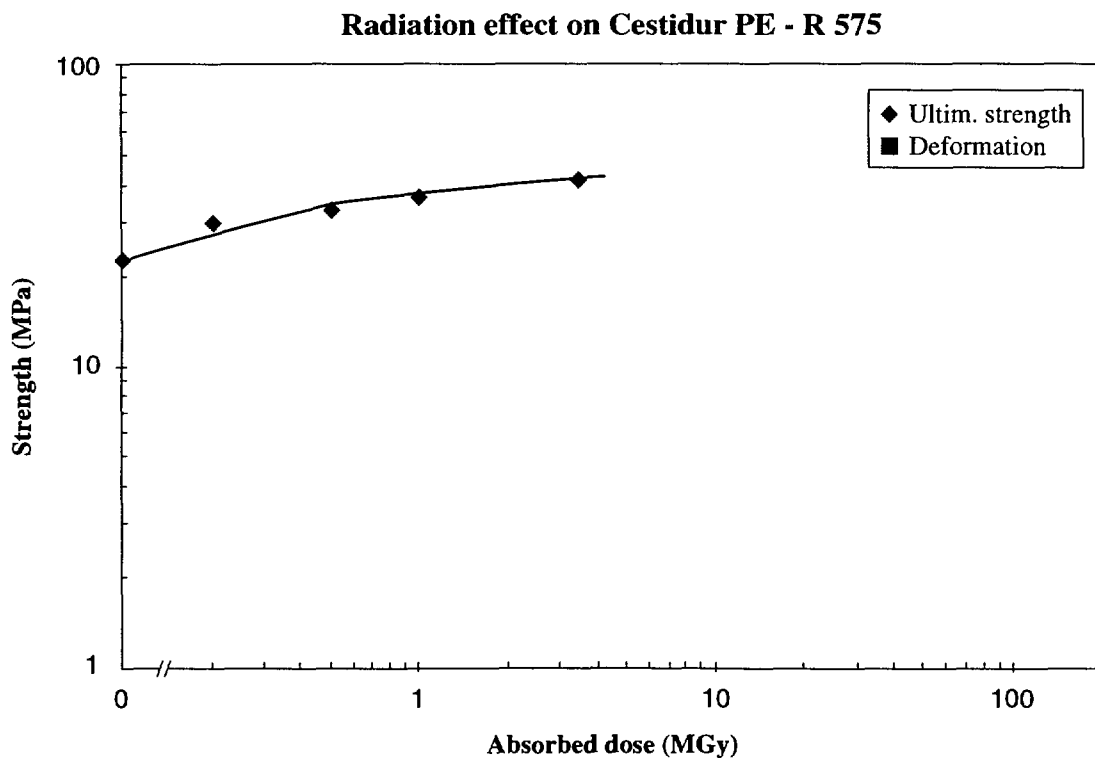

Comment: Samples do not break before 3.4 MGy.

Material: **Polyethylene Cestidur**
Type: **Cestitech**

TIS No. **R 576**

Supplier: **ERTA - EPEC**
Remarks:

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	23.4±0.6	> 14	0.83±0.05
4	0.2	31.1±0.2	> 14	1.15±0.05
4	0.5	33.4±1.2	> 14	1.26±0.11
1	1	34.7±1.2	5.46±0.53	1.56±0.06
220	3.4	38.8±0.6	5.10±0.31	1.43±0.03

Critical property = deformation

Radiation index (RI) = 5.9 at a mean dose rate of 1 kGy/h

Radiation index (RI) = 6.4 at a mean dose rate of 220 kGy/h

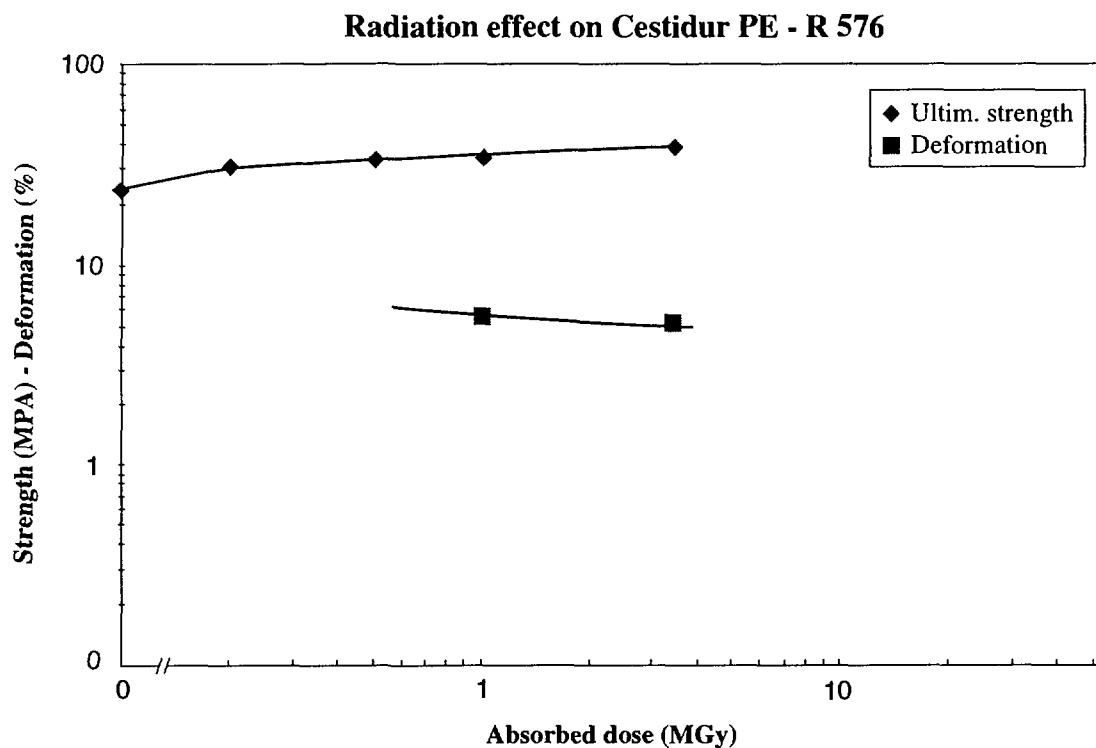

Comment: Samples do not break before 1 MGy.

Material: **Polyamide imide (PAI)**
 Type: **Torlon 4203**

TIS No. **R 577**

Supplier: **DSM EPP**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	188$\pm$3	14.96$\pm$0.09	4.06$\pm$0.03
225	30	191$\pm$2	15.04$\pm$0.05	4.27$\pm$0.06

Critical property = flexural strength

Radiation index (RI) = > 7.5 at a mean dose rate of 225 kGy/h

Radiation effect on Torlon 4203 - R 577

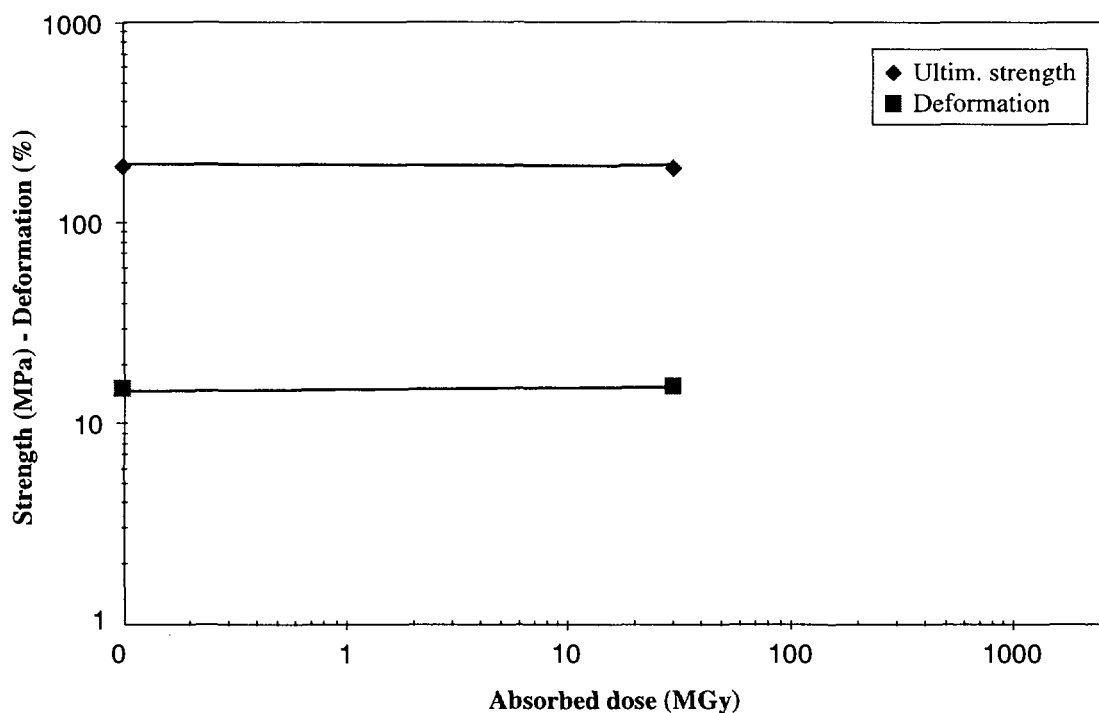

Material: **Polyamide imide (PAI)**
 Type: **Torlon 4301**

TIS No. **R 578**

Supplier: **DSM EPP**
 Remarks:

UL 94: n.m.
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	182±4	7.88±0.59	6.12±0.13
225	30	181±4	6.71±0.50	6.01±0.11

Critical property = flexural strength

Radiation index (RI) = > 7.5 at a mean dose rate of 225 kGy/h

Radiation effect on Torlon 4301 - R 578

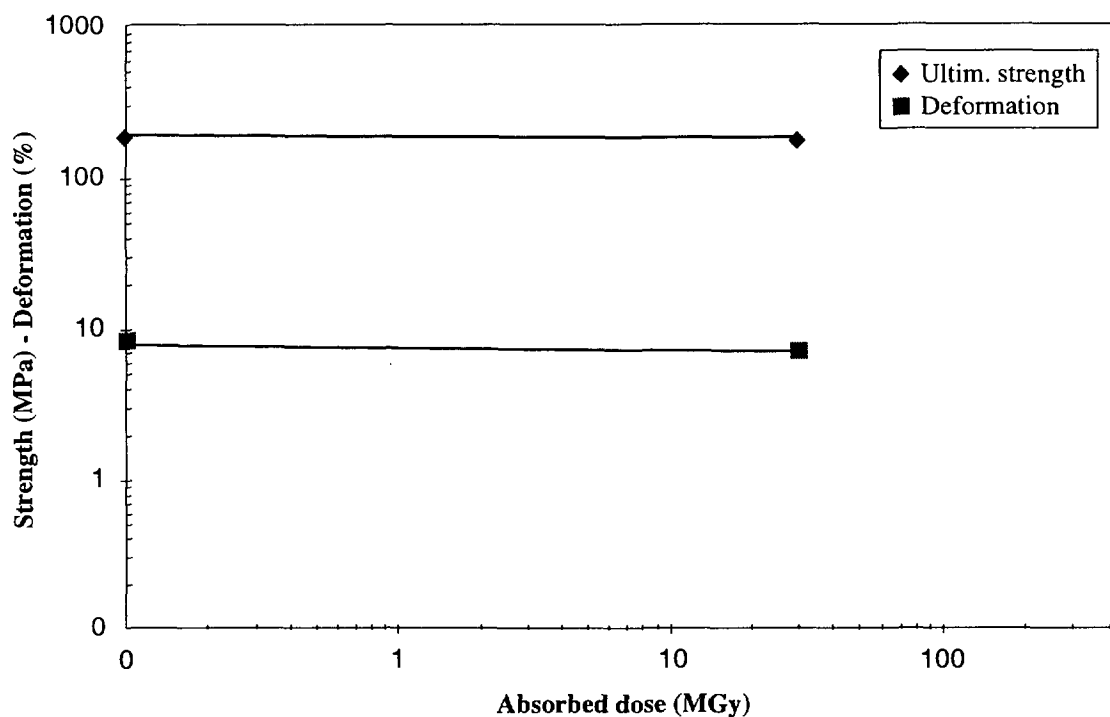

NEXT PAGE(S)
left BLANK

Resofil	trade name of Micafil for phenolic resin, see Ref. [25]; RI < 5.7
Rilsan	trade name of Atochem for polyamide; RI ~ 6
Ryton	trade name of Phillips Petroleum Company for polyphenil sulfide (PPS), see Ref. [25]

**NEXT PAGE(S)
left BLANK**

Samicanit	trade name of Isola for Mica and glass reinforced epoxy resins, see Ref. [25]
Samicapor	trade name of Isola for GFRP, see epoxy resin
Samicatherm	trade name of ANSALDO for Mica and glass reinforced epoxy resins, see Epoxy resin and Ref. [25]
Scotchcast	trade name of 3M for epoxy base compounds, see epoxy
Silicone resins	see Ref. [25]; RI > 7.7
Siltem	trade name of General Electric Plastics for polyimide-silicones copolymer also for polyetherimide-siloxane copolymer, see also polyetherimide
Sintimid	trade name of Lenzing& Planzee for polyimide, see polyimide
Stilan	trade name by Raychem for PAEK
Styrene	
Silicone-polyimide copolymer	

List of materials classified under letter S

TIS number	Material name	Type	Mechanical properties			
			UTS (MPa)	Deform. (%)	Modulus (MPa)	RI
544	Silicones-polyimide copolymer	Siltem 1550	70.52	> 10	1.84	6.5
418	Styrene: cross-linked copolymer	PolypencoQ.200.5	89.7	4.3	3.2	> 5.7

Material: **Silicones-polymide copolymer**
 Type **Siltem 1550**

TIS No. **R 544**

Supplier: **General Electric Plastics**
 Remarks:

UL 94: V-0
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	70.5±0.6	> 10	1.84±0.01
1	2	71.2±1.0	> 10	1.96±0.04
220	5	78.8±3.2	> 10	1.95±0.10
220	10	74.8±3.6	1.41±0.10	5.88±0.33
220	50	42.2±1.3	1.66±0.03	2.72±0.10

Critical property = deformation

Radiation index (RI) = > 7.7 at a mean dose rate of 220 kGy/h

Radiation effect on Siltem - R 544

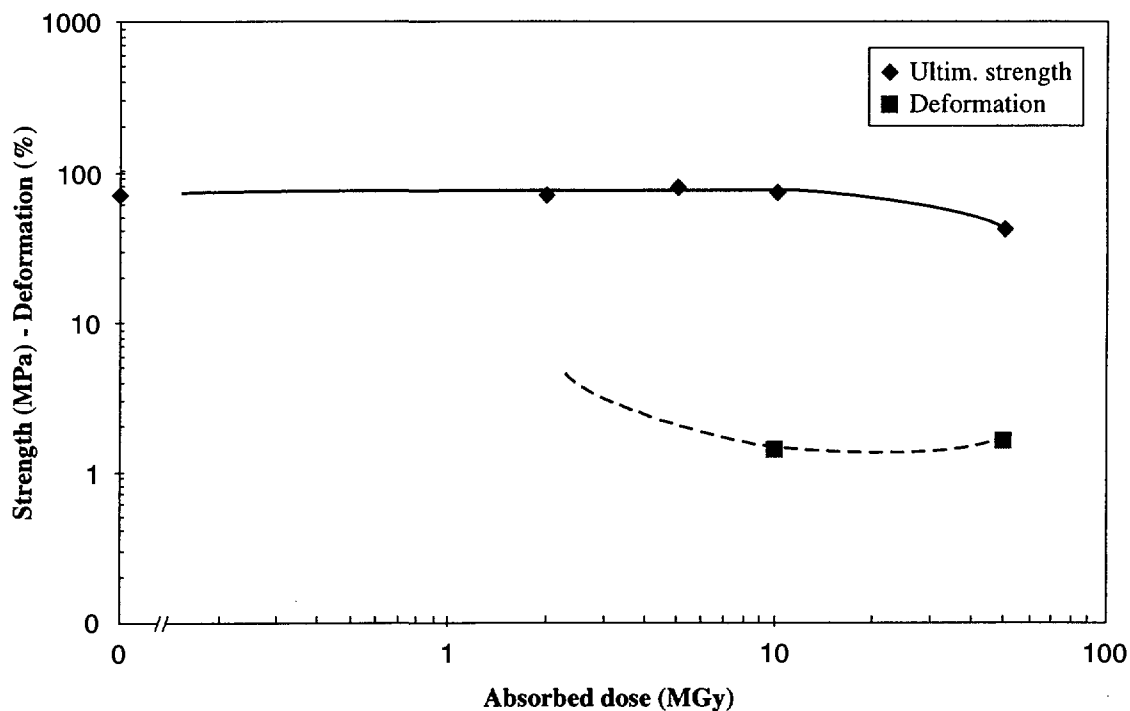

Material: **Styrene: cross-linked copolymer**
 Type **Polypenco Q.200.5**

TIS No. **R 418**

Supplier: **Cellpack**
 Remarks: **translucent**

UL 94:
 LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0.0	89.7±6.4	4.3±0.1	3.2±0.1
0.1	0.2	96.6±2.8	3.3±0.1	3.2±0.1
0.1	0.5	96.6±1.5	3.2±0.0	3.3±0.1
160	5	83.1±8.0	3.3±1.0	3.3±0.1
160	10	73.4±5.5	2.3±0.2	3.3±0.1
160	30	33.1±4.7	1.0±0.1	3.2±0.1

Critical property = deformation

Radiation index (RI) = 7.0 at a mean dose rate of 160 kGy/h

Radiation index (RI) = > 5.7 at a mean dose rate of 100 Gy/h

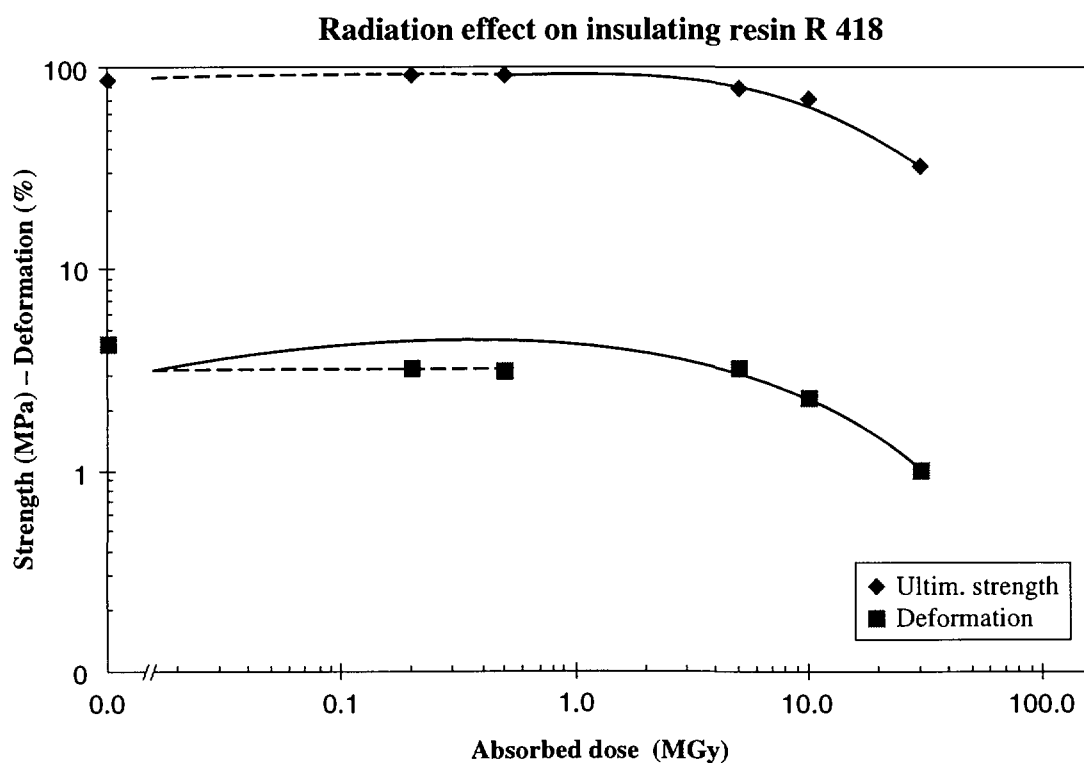

Comment: Dotted lines correspond to long-term irradiation.

T

Tedur	trade name of Bayer for polyphenylene sulfide, see PPS
Teflon	trade name of Dupont for PTFE; very sensitive to radiation; not to be used in radiation environments
Tefzel	trade name of Dupont for ETFE
Torlon	trade name of Polypenco for polyamide-imide, see PAI

**NEXT PAGE(S)
left BLANK**

U

Udel	trade name of General Electric Plastics for polysulfone, see polysulfone
Ultem	trade name of General Electric Plastics for polyetherimide, see polyetherimide
Ultraform	trade name of BASF for acetal resin, see POM
Ultramid	trade name of BASF for polyamides
Ultrapek	trade name of BASF for polyaryl-ether-ketone
Univolt	trade name of Dietzel Electro for PPO based plastics

NEXT PAGE(S)
left BLANK

Varnish

Vectra trade name of Hoechst for liquid crystal polymer, see LCP

Veridur trade name of BBC Baden for Silicone resin, see Ref. [25]

Vespel trade name of Dupont for polyimide, see PI

Vetresit trade name of MICAFIL for cycloaliphatic-epoxy, see epoxy resin

Vetronite trade name of Von Roll Isola for epoxy resins, see epoxy resin

Victrex trade name of ICI for polyether (-ether)-ketone, see PEEK

Vicotex trade name of CIBA-GEIGY for carbon fibre reinforced epoxy laminate,
see CFRP, and Ref. [35] for behaviour at cryogenic temperature

List of materials classified under letter V

TIS number	Material name	Type	Mechanical properties			
			UTS (MPa)	Deform. (%)	Modulus (MPa)	RI
519	Varnish 4.302		100	4.5	3.09	> 7

Material: **Varnish 4.302**
Type

TIS No. **R 519**

Supplier: **Isola**
Remarks: **ex SIB 775**

UL 94: n.m.
LOI:


Radiation test results according to IEC Standard 544 (and ISO 178)

Dose rate (kGy/h)	Dose (MGy)	Ultim. strength (MPa)	Deformation ϵ (%)	Modulus (GPa)
0	0	100 $\pm$ 30	4.5 $\pm$ 1.7	3.09 $\pm$ 0.11
220	5	122 $\pm$ 7	4.54 $\pm$ 0.59	3.4 $\pm$ 0.1
220	10	112 $\pm$ 37	4.22 $\pm$ 1.77	3.56 $\pm$ 0.02
220	50	38.6 $\pm$ 3.6	1.60 $\pm$ 0.97	3.79 $\pm$ 0.09

Critical property = flexural strength

Radiation index (RI) = > 7.1 at a mean dose rate of 220 kGy/h

Radiation effect on insulating resin R 519

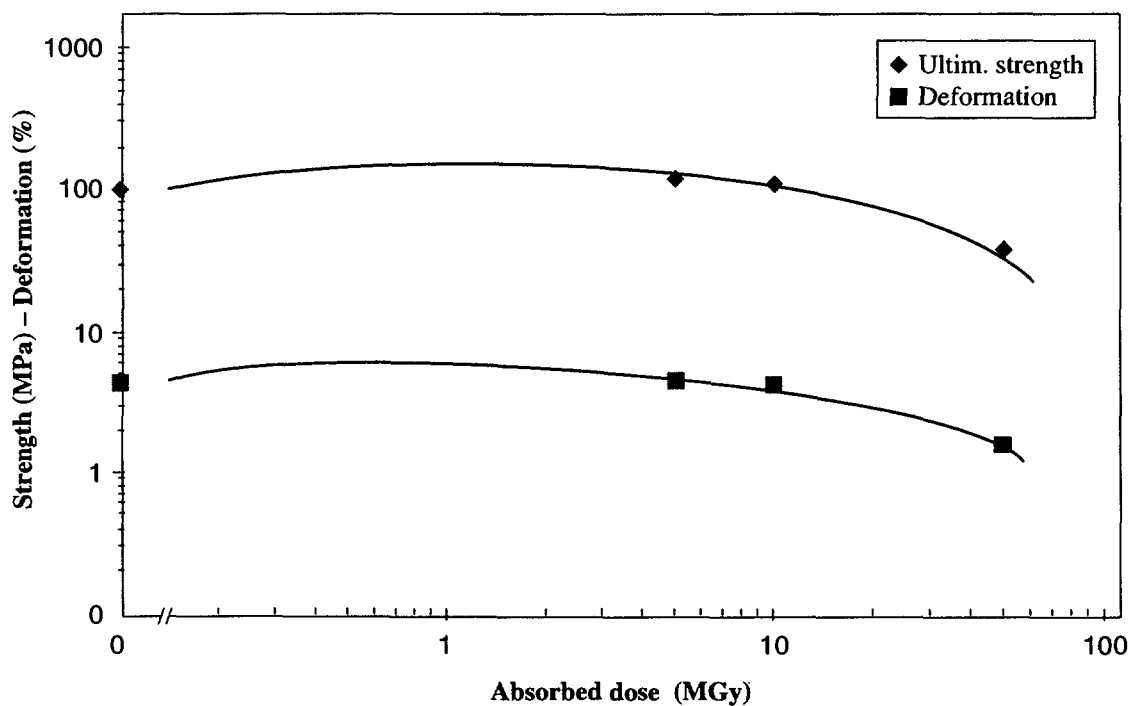

NEXT PAGE(S)
left BLANK

APPENDIX 4

List of abbreviations used in the present volume (for chemical abbreviation of polymers, see Tables 2a and 2b)

ASTM	American Society for Testing and Materials
B	breadth of the samples (mm)
CEI	Commission Electrotechnique Internationale
D	maximum deflexion during the test (mm)
ϵ	deformation = $\epsilon = \frac{6DT}{L^2}$ (%)
F	deflexion interval in linear flexural curve (mm)
IEC	International Electrotechnical Commission
ISO	International Organization for Standardization
L	distance between supports of the flexion test = 67 mm
LOI	Limit of Oxygen Index (%)
M	flexural modulus = M (or E) = $\frac{P \cdot L^3}{4FB \cdot T^3}$ (MPa)
P	strength interval in linear flexural curve (N)
P_x	maximum strength (N)
RI	radiation index (see definition in Section 3 of the text)
S	flexural strength = $S = \frac{3P_x \cdot L}{2B \cdot T^2}$ (MPa)
T	thickness of the samples (mm)
TIS	Technical Inspection and Safety Commission at CERN
UL	Underwriters' Laboratories
VPI	vacuum press impregnated composite

NEXT PAGE(S)
left BLANK

APPENDIX 5

List of suppliers of base materials, of transformers, and of some users who gave samples to CERN

Agro AG	Korbackerweg 2, CH-5502 Hunzenschwil
Angst & Pfister (seller)	52, route du Bois-des-Frères, 1219 Genève-le-Lignon
Ansaldo (magnet maker)	8, via Lorenzi, I-16152 Genova
BASF	D-6700 Ludwigshafen
Bayer AG	D-Dormagen
Cellpack AG	CH-5610 Wölen
Ciba-Geigy AG	CH-4002 Basel
Ciba-Geigy Marienberg	Postfach 1253, D-6140 Bensheim 1
Ciba-Geigy Brochier	ZI Les Chartinières, BP 27, F-01121 Montluel
Ferrettite (DFC)	ZI de Nogent, BP 6, F-60104 Creil
Dornier GmbH	D-88039 Friedrichshafen
DuPont de Nemours	2, ch. du Pavillon, P.O. Box, 1218 Genève
Ebo AG	Zürichstrasse 103, CH-8134 Adiswil
Elektro Isola AS	197 Grønlandsvej, DK-7100 Vejle
Elin (magnet maker)	Penzinger Strasse 76, A-1141 Vienna
Enka AG	Postfach 100149, D-5600 Wuppertal 1
Erta Epec	Industriepark Noord, B-8700 Tielt
FA.BA.	2, via delle Fabbriche, I-16158 GE-Voltri
General Electric Plastics	1 Plasticlaan, P.O. Box 117, NL-4600 Bergen/Zoom
ICI	P.O. Box 6, Welwyn Garden City, Herts. AL7 1HD, UK
Isola Werke	CH-4226 Bretenbach
Isovolta / Isonova	A-2355 Wiener Neudorf
L.E. Pink Eng. Ltd	Rose Kiln Lane, Reading RG2 0HP, UK
Micafil AG	Badenerstrasse 780, CH-8048 Zürich
Permali Composites	8, rue A. Fruchard, F-54320 Maxéville
Shell	Bederstrasse 66, CH-8002 Zürich
Sintimid	Postfach, A-4860 Lenzing
Solvay	Rue de Ransbeek, B-1120 Bruxelles
Stesalit AG	CH-4234 Zullwil
YLA	2970C Bay Vista Court, Benicia, California 94510
3M GmbH	Eggstrasse 93, Postfach, CH-8803 Rüschlikon

List of CERN Reports published in 1998

CERN 98-01

CERN, Geneva

Tavlet, M; Fontaine, A; Schönbacher, H

Compilation of radiation damage test data,

Part II, 2nd edition: Thermoset and

thermoplastic resins, composite materials;

Index des résultats d'essais de radiorésistance,

II^e Partie, 2^e édition: Résines thermodurcies et

thermoplastiques, matériaux composites

CERN, 18 May 1998. – 180 p