

[Prepared for publication as a Review in *Science*]

Manuscript number: aar6611

Title

Beyond fossil-fuel-driven nitrogen transformations

One-Sentence Summary

This review article reports on the current state of the field of nitrogen activation chemistry and discusses future directions.

Authors and Affiliations

Jingguang G. Chen,* Department of Chemical Engineering, Columbia University, New York, NY 10027, USA; Chemistry Department, Brookhaven National Laboratory, Upton, NY 11973, USA

Richard M. Crooks,* Department of Chemistry, The University of Texas at Austin, Austin, TX 78712, USA

Lance C. Seefeldt,* Department of Chemistry and Biochemistry, Utah State University, Logan, UT 84332, USA

Kara L. Bren, Department of Chemistry, University of Rochester, Rochester, NY 14627, USA

R. Morris Bullock, Pacific Northwest National Laboratory, Richland, WA 99352, USA

Marcetta Y. Darensbourg, Department of Chemistry, Texas A&M University, College Station, TX 77843, USA

Patrick L. Holland, Department of Chemistry, Yale University, New Haven, CT 06511, USA

Brian Hoffman, Department of Chemistry, Northwestern University, Evanston, IL 60208, USA

Michael J. Janik, Department of Chemical Engineering, Pennsylvania State University, University Park, PA 16802, USA

Anne K. Jones, School of Molecular Sciences, Arizona State University, Tempe, AZ 85282, USA

Mercouri G. Kanatzidis, Department of Chemistry, Northwestern University, Evanston, IL 60208, USA

Paul King, National Renewable Energy Laboratory, Golden, CO 80401, USA

Kyle M. Lancaster, Department of Chemistry and Chemical Biology, Cornell University, Baker Laboratory, Ithaca, NY 14853, USA

Sergei V. Lymar, Chemistry Department, Brookhaven National Laboratory, Upton, NY 11973, USA

Peter Pfromm, Voiland School of Chemical Engineering and Bioengineering, Washington State University, Pullman, WA 99164-6515, USA

William F. Schneider, Department of Chemical and Biomolecular Engineering, University of Notre Dame, Notre Dame, IN 46556, USA

Richard R. Schrock, Department of Chemistry, MIT, 6-331, Cambridge MA 02139, USA.

*To whom correspondence should be addressed.

Email: jgchen@columbia.edu; crooks@cm.utexas.edu; lance.seefeldt@usu.edu

Submission Date: 4 December, 2017

Revised: 12 April, 2018

Abstract

Nitrogen is fundamental to all of life and to many industrial processes. The interchange of nitrogen oxidation states in industrial production of ammonia, nitric acid, and other commodity chemicals is largely powered by fossil fuel. A key goal of contemporary research in the field of nitrogen chemistry is to minimize the use of fossil fuels by developing more efficient heterogeneous, homogeneous, or photo/electrocatalytic processes, or by looking to adapt the enzymatic processes underlying the natural nitrogen cycle. These approaches, as well as the challenges involved, are discussed in this review.

Main Text

Reduced forms of nitrogen, particularly ammonia (NH_3), are vital to life. Prior to the early 1900's, all reduced N came from biological nitrogen fixation by microbes. This landscape changed in the early 1900's with the invention of an industrial process to reduce N_2 to NH_3 ($\text{N}_2 + 3\text{H}_2 \rightleftharpoons 2\text{NH}_3$) by Haber and Bosch (H-B). The H-B process, in turn, has led to fundamental changes in the way food is produced, and its impact is underscored by the fact that about 50% of the N atoms in humans today originate from the H-B process (1). For these reasons and others, the H-B process has been called the most impactful invention of the 20th century (2). The H-B process is, however, energy intensive, consuming 1-2% of the world's annual energy output (3). The main energy requirements arise from the high reaction temperatures (~ 700 K) and pressures (~ 100 atm), and, most importantly, from the need for large quantities of H_2 . Nevertheless, at scale H-B is surprisingly energy efficient. In addition to the high energy demand, however, there is a second problem with H-B that is potentially more serious. Specifically, the source of H_2 is usually natural gas, (4) and consequently H-B generates about 1.9 metric tons of CO_2 per metric ton of NH_3 produced (3 CO_2 per 8 NH_3) (5).

Nitrogen in its more oxidized forms is also industrially, biologically, and environmentally important. Oxidation of N_2 to nitric oxide (NO) and nitrogen dioxide (NO_2), which are collectively referred to as NO_x (the representation of neutral forms of oxidized nitrogen), occurs naturally in lightning and also during combustion of fuels in air (6). In fact, plasma-driven oxidation of N_2 to NO (the Birkeland-Eyde, or B-E, process) preceded H-B as the first commercial nitrogen fixation process (7). However, B-E is not economically competitive with the H-B process, and as a result the demand for oxidized nitrogen, primarily in the form of nitric acid (HNO_3), is satisfied by catalytic oxidation of H-B-generated NH_3 at elevated temperatures via the Ostwald process (8).

Nitrogen oxides (NO_x , which represents both neutral and anionic forms of oxidized nitrogen) are also produced on a large scale by bacteria. These processes include oxidation of NH_3 to nitrate (NO_3^-) by nitrifying bacteria and reduction of NO_3^- to nitrite (NO_2^-), NO , nitrous oxide (N_2O), and ultimately to N_2 by denitrifying bacteria. The conversion of NH_3 and NO_3^- to N_2 by the action of these bacteria is used in waste-water treatment and is the primary pathway for loss of applied fertilizers in agriculture. Nitrogen oxides are common environmental pollutants, and thus catalysts to reduce these oxides to N_2 are also of considerable practical importance. For example, NO_x generated during combustion is a primary component of photochemical smog (9). The development of active catalysts for reducing NO_x to N_2 (the TWC, or three-way catalytic converter) led to remarkable improvements in air quality in the late 1970's (10), and there are now TWCs operating on hundreds of millions of vehicles worldwide. However, increasingly stringent emissions regulations coupled with the low exhaust temperatures from high efficiency engines present challenges for future combustion emissions control (11). The soluble forms of the nitrogen oxides, primarily NO_2^- and NO_3^- , are similarly hazardous to human health and contribute to the eutrophication of waterways (12). Sustainable approaches for catalytically converting these pollutants to N_2 remain an unmet challenge (13).

In the present article, we report on the results of a U. S. Department of Energy workshop held in October, 2016 that focused on the challenges and opportunities associated with fundamental aspects of nitrogen chemistry. We begin by discussing the thermochemistry of nitrogen transformations, and then focus on the reduced forms of nitrogen, primarily NH_3 , followed by the oxidized forms.

Thermochemistry of nitrogen fixation

The energy expenditures for various reductive and oxidative N_2 fixation pathways are compared in Figure 1 (14-16). Hydrocarbons, including biomass and fossil fuels (particularly methane), and water are the only two sources of hydrogen atoms that can sustain long-term, large-scale NH_3 production. The use of water as the hydrogen source for NH_3 production requires substantially more energy than methane (by 613.4 kJ/mol N_2), but it is also more environmentally benign, does not contribute to the accumulation of greenhouse gases, and does

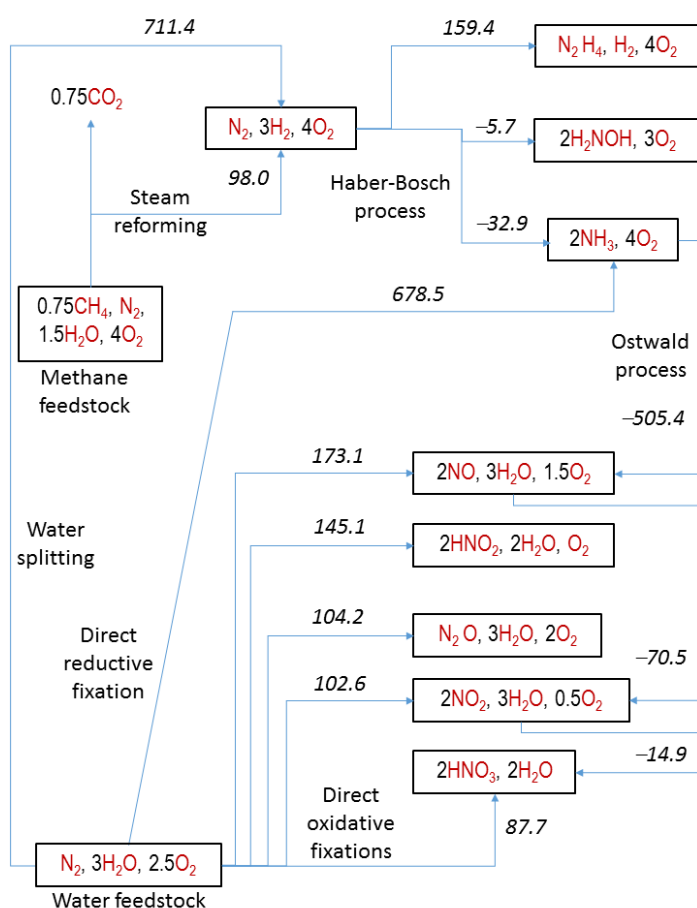


Figure 1. Atom and energy economy of nitrogen fixation. The numerical values represent standard (14) Gibbs free energies in kJ/mol of fixed N_2 in the direction of the arrows. All thermochemical data are from (15), except for H_2NOH (16).

not compete for valuable and limited hydrocarbon resources. However, these advantages can be fully realized only if the energy comes from a clean, renewable source such as the sun or wind.

When water is used as the feedstock, there is only a small (32.9 kJ/mol N_2) thermodynamic advantage for the direct synthesis of NH_3 compared to a two-stage synthesis involving water splitting followed by H-B. The overall energy saving may, however, become more significant if the H-B process is avoided altogether and direct reductive N_2 fixation is conducted under milder conditions.

The two most important N-containing commodity chemicals are NH₃ and HNO₃. In 2017, their worldwide production was estimated to be 150 (17) and 50 (18) million metric tons, respectively. Presently, nearly all HNO₃ is manufactured using a three-stage process: steam reforming of methane, H-B, and then the Ostwald process (Figure 1), but this approach is energetically wasteful compared to direct oxidative N₂ fixation.

An attractive alternative route to HNO₃, which avoids the NH₃ intermediate, is direct N₂ oxidation to aqueous HNO₃ (eq 1).



The equilibrium constant for this reaction is $\sim 2.7 \times 10^{-3} \text{ M}^4/\text{bar}^{3.5}$ ($\Delta G^0 = 14.6 \text{ kJ/mol N}_2$) (14-16, 19), which is large enough to drive spontaneous formation of $\sim 0.1 \text{ M HNO}_3$ in any pool of water on the surface of the earth. Moreover, if equilibrium were to be achieved between the earth's atmosphere and the world's oceans, the oceans would contain $\sim 0.02 \text{ M HNO}_3$ and $\sim 90\%$ of atmospheric O₂ would be consumed. Fortunately for life on Earth, under ordinary conditions and in the absence of a catalyst, eq 1 is immeasurably slow in both directions.

Reduction of N₂ to NH₃

Overview. As discussed in the previous two sections, the most important N₂ reduction reaction is NH₃ synthesis, specifically $\text{N}_2 + 3\text{H}_2 \rightleftharpoons 2\text{NH}_3$. Given that this reaction is slightly thermodynamically favorable under ambient conditions, major effort has been devoted to developing alternative and environmentally friendly processes that would allow NH₃ to be produced at distributed sources under more benign conditions rather than the large-scale centralized H-B process. This goal is particularly important in developing countries where the population, and hence the need for food, is increasing rapidly. In these countries, access to

fertilizer is hampered by poor transportation infrastructure and insufficient capital to build large chemical plants. For example, there are no large-scale NH_3 production facilities in all of East Africa. To address this need, there has been substantial effort expended to understand N_2 reduction using a variety of catalysts, including: heterogeneous, enzymatic, and homogeneous catalysts, and electro- and photocatalysts.

Heterogeneous catalysis. The commercial H-B process is carried out using a heterogeneous catalyst based on iron and promoted with Al_2O_3 and potassium. It is now well accepted that the relative activity of metallic catalysts can be correlated to their binding energies with N-containing species in terms of a volcano-shaped relationship. Metals that bind nitrogen too strongly or too weakly are on either side of the volcano (20). For those having low binding energies, N_2 dissociation is rate-limiting. For those metals exhibiting high binding energies, N_2 dissociation occurs but desorption of the resulting atomic N (and other N-containing intermediates) is slow, limiting the number of available binding sites and thereby slowing the catalytic rate (21).

Recent calculations suggest that the energies of all intermediates and transition states involved in a conventional NH_3 synthesis reaction network scale with the N binding energy. As shown in Figure 2, these correlations limit the rate of NH_3 synthesis on transition metals to much lower values than would be possible on a material with both a low N_2 dissociation barrier and more moderate intermediate binding energies (22). Clearly, an important challenge is to break this type of scaling relationship, which should lead to the development of catalysts yielding reaction rates that are potentially orders of magnitude higher than the current state of the art.

Advances in the synthesis, characterization, and modeling of non-traditional heterogeneous catalysts, such as intermetallics, alloys containing a single heteroelement, and shape-controlled materials, whose discovery might be driven by computational models, offer the promise for more active catalysts. These combined efforts should lead to catalysts that could

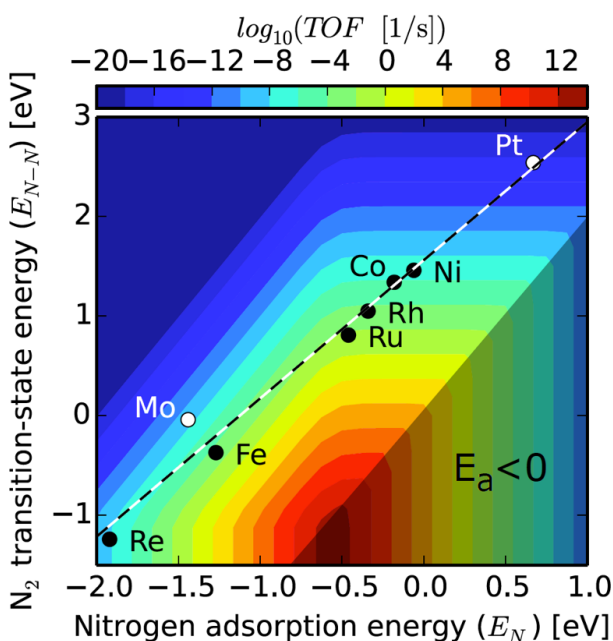



Figure 2. Linear scaling between nitrogen binding energy and activation barrier for N_2 dissociation. TOF = turnover frequency. Reproduced with permission from (22).

potentially operate at lower temperatures and thus reduce the operating pressures of the H-B process. Another opportunity to reduce the CO_2 footprint of the H-B process is to replace the methane reformer with a water-electrolyzer to provide CO_2 -free H_2 , but this would require cost-effective, large-scale electrolyzers.

Enzyme catalysis. A range of

microbes (bacteria and archaea) living in all major ecosystems are able to reduce N_2 to NH_3 using the enzyme nitrogenase. Nitrogen

fixation by these microbes contributes to global supply of NH_3 , but it is insufficient to support modern intensive agriculture food production. Exciting frontier areas for the use of microbial N_2 fixation include engineering the nitrogen fixation genes into eukaryotes (23), such as plants, and using nitrogen-fixing microbes in microbial electrocatalysis cells that permit sustained N_2 reduction to NH_3 (24). Such systems offer the promise of providing localized solutions to N_2 reduction, but are not likely to displace the need for large-scale N_2 reduction in the near term.

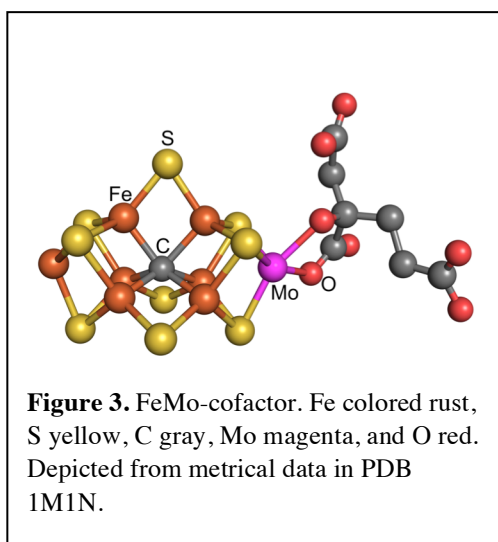

One important lesson to learn from biological nitrogen fixation is a better understanding of how the enzyme nitrogenase accomplishes reduction of N_2 to NH_3 at low temperatures and pressures and without H_2 . The first nitrogenase to be purified (and the most widely distributed) is Mo-dependent and, as shown in Figure 3, has a metal-cluster active site containing Mo, Fe, S, C, and homocitrate (FeMo-cofactor).

An important step toward mechanistic understanding of nitrogenase emerged from trapping an intermediate with four H^+ and four e^- accumulated immediately prior to binding N_2 . Characterization of this intermediate (25) (termed the E_4 state) has revealed the presence of bridging hydrides (Fe-H-Fe). The E_4 state undergoes reductive elimination of the two hydrides with release of H_2 , with concomitant activation of the metal core by two e^- for binding and reduction of N_2 to a metal-bound diazenido species ($HN=N-Fe$). Although these studies have provided insights into the central catalytic step, which is the cleavage of the N_2 triple bond, many challenges remain before the entire mechanism can be elucidated. These include a molecular level understanding of both the early and late stages of the N_2 reduction pathways, an understanding of the roles of ATP hydrolysis in driving electron transfer, and then reconciliation of the resulting empirical mechanism with computational studies.

These foregoing challenges primarily involve substrate moieties bound as catalytic intermediates. In parallel, important questions remain about the FeMo-cofactor active site of Mo-dependent nitrogenase. For example, what changes in redox and spin states of the seven Fe centers and the Mo center accompany the stepwise transformations of substrates? Additionally,

the FeMo-cofactor contains the first example of a carbide (C^{4-}) in biology. The significance and function of this carbide with respect to mechanism are unknown. Understanding the structure of FeMo-cofactor intermediates and synthetic analogues could provide important clues to guide the design of new homogeneous and heterogeneous catalysts for N_2 reduction (26). Biomimetic approaches could take advantage of not only the coordination chemistry in the FeMo-cofactor, but also the cooperative interactions with nearby acidic amino acid residues in the nitrogenase protein.

Electrochemical techniques offer a powerful alternative method of delivering electrons to nitrogenase without a requirement for ATP hydrolysis, and they also offer new avenues for addressing aspects of the nitrogenase mechanism. Electron transfer from an electrode, previously demonstrated for a number of redox enzymes, has been applied to nitrogenase but only via mediators (i.e., no direct electron transfer) (27-29). As illustrated in a recent study, this approach, in combination with computations (30), provides insights into catalytic nitrogen transformations.

A related frontier area is using nanomaterials to deliver electrons to nitrogenase. For example, it has been recently demonstrated that a CdS nanorod-nitrogenase MoFe protein hybrid achieves light-dependent N_2 reduction to NH_3 using a sacrificial electron donor (31). Such systems offer a means to use light as the exclusive energy source to drive N_2 reduction.

Homogeneous catalysis. Synthetic homogeneous catalysts designed for N_2 reduction provide well-defined molecular pre-catalysts and intermediates, which can be thoroughly characterized by diverse spectroscopic techniques and thereby provide excellent opportunities for determining mechanistic information about N_2 reduction to NH_3 . The reactivity of synthetic inorganic complexes provides insights into molecular reactivity and individual bond-making processes that occur in nitrogenases. The discovery of nitrogenase, along with a transition metal

compound that contains N_2 bound to ruthenium (32), initiated a race to prepare NH_3 catalytically under mild conditions via a transition metal complex. Indeed, entire institutes were created in England and Russia in the late 1960s for this purpose. The stoichiometric N_2 -to- NH_3 conversion using H_2SO_4 was demonstrated using low-valent Mo- N_2 and W- N_2 complexes in the 1970s (33); typically the electrons required came from the metal complex. In 1985, the synthesis of NH_3 was accomplished by Pickett and Talarmin using an electrochemical route starting from the tungsten complex $[\text{W}(\text{N}_2)_2(\text{PMe}_2\text{Ph})_4]$, with the electrons supplied by the electrode and protons from an added acid (34). The catalytic reduction of N_2 to NH_3 by H^+/e^- was reported in subsequent studies, using, for example, a well-defined Mo-containing catalyst (35). Up to eight equivalents of NH_3 per Mo were formed, along with H_2 . Both experiments and calculations support a mechanism involving the addition of 6H^+ and 6e^- to the N_2 initially bound to a Mo(III) center. Altogether, eight of these proposed intermediates were prepared and characterized.


Additional Mo pre-catalysts for reduction of N_2 using chemical reductants and an acid, a dimolybdenum–dinitrogen complex (36) and a molybdenum nitride (37), were subsequently reported in 2011 and 2015, respectively. In 2013, Fe complexes were reported that catalyze reduction of N_2 to NH_3 using a strong reducing agent (KC_8) and a strong acid at 200 K (38); improvements to the Fe system recently produced as many as 84 equivalents of NH_3 per Fe (39). These Fe complexes were designed to reflect the trigonal symmetry of the Fe in the catalytic face of the FeMo-cofactor (Figure 3) and to allow variation of an axial ligand, so as to explore tuning of N_2 binding/reduction by the unusual carbide at the center of the FeMo-cofactor.

In all these cases it appears that catalytic N_2 reduction is a 6-electron process, involving many intermediate chemical species $[\text{M}-\text{N}_x\text{H}_y^{n+}]$, but unlike nitrogenase without a mechanistic requirement for production of H_2 . Nonetheless, in all cases N_2 reduction is accompanied by

production of H₂, and at least with the Fe complexes, this has been shown to involve a catalytic process, with H⁺ reduction competing with N₂ reduction.

Much work remains to move this field forward. For example, rational design of potential catalysts will be guided by accurate determination of the bond dissociation free energies (BDFEs) of N-H bonds, including likely intermediates such as M-N=NH, M=N-NH₂, and M=N-NH₃. Initial experimental and theoretical estimates have shown that N-H BDFEs of coordinated NH₃ can vary significantly and demonstrate the importance of metal identity and its oxidation state as well as the possibility of ligand control to tune the stability of potential intermediates. In addition, determination of the energies of these bonds will allow evaluation of energetic requirements of the individual chemical steps that ultimately lead to NH₃. It is also important to identify features that tune the reduction potentials of relevant complexes to ensure that the multiple reductions required for catalysis are energetically feasible. Thus, research should focus on exploring complexes designed to simultaneously promote N₂ binding and multiple reductions at the metal site.

Electrocatalysis and photocatalysis. The potential-pH predominance (Pourbaix) diagram for the N₂-H₂O system shown in Figure 4 reveals that reduction of N₂ to NH₄⁺/NH₃ (eq 2 and the N₂ reduction line in Figure 4) is thermodynamically possible under moderately reducing conditions.



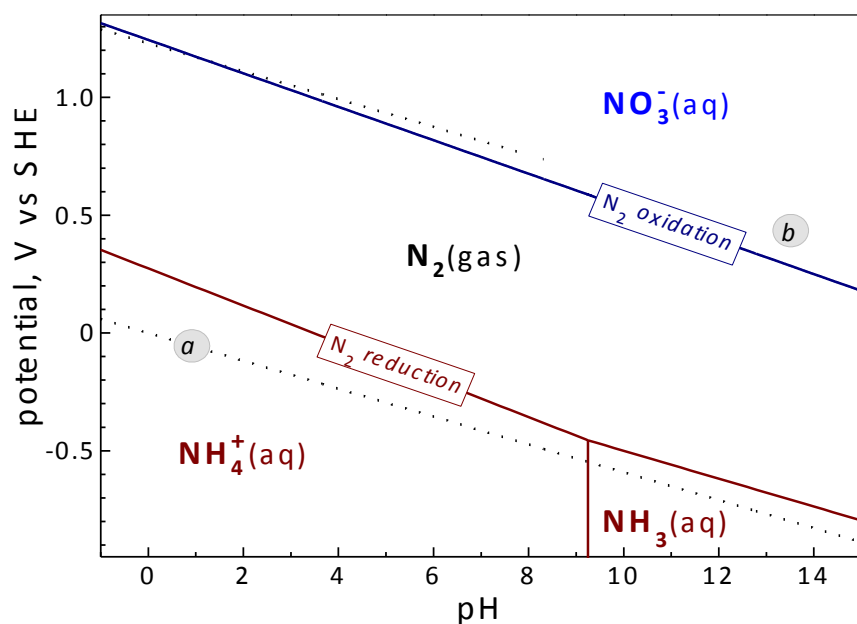


Figure 4. Partial Pourbaix diagram for the $\text{N}_2\text{-H}_2\text{O}$ system showing solid lines corresponding to N_2 reduction to $\text{NH}_4^+/\text{NH}_3$ and N_2 oxidation to NO_3^- . Dotted lines *a* and *b* straddle the region of water stability (reduction to H_2 and oxidation to O_2 , respectively). See (14) for details and (15, 19) for primary data.

Moreover, with a sufficiently active electrocatalyst, the N_2 reduction reaction can, in principle, proceed in a narrow range of negative potentials without interference from water reduction (line *a* in Figure 4) over the entire pH range. However, at potentials below line *a*, an extremely selective electrocatalyst would be required to suppress parasitic water reduction. Note that the nitrogen reduction reaction could be paired with a water oxidation half-reaction to supply the H^+ and e^- required for a complete electrolysis cell. Such a cell would essentially combine water splitting with NH_3 formation as depicted by the direct reductive fixation route in Figure 1. Despite the inviting prospect of a scalable NH_3 electrolysis cell running on renewable electricity at or near room temperature, the difficulty of selectively catalyzing the nitrogen reduction reaction has prevented development of an efficient electrochemical system.

At present, only a few examples of pairing the nitrogen reduction reaction with water oxidation at ambient temperature and pressure have been reported, and in all cases, due to competing H_2 evolution, the faradaic efficiencies for NH_3 are so low that even its reliable detection is challenging (40, 41). For example, an efficiency of 0.83% and a production rate of

$9.4 \times 10^{-10} \text{ mol-NH}_3 \text{ cm}^{-2} \text{ s}^{-1}$ were measured at 353 K at an applied cell voltage of 1.2 V using Pt electrodes and a Nafion electrolyte (42). Another electrochemical approach involved an electrochemical cycling process for producing NH_3 (43). The cycling included separate steps of LiOH electrolysis, Li nitridation, and Li_3N hydrolysis, thereby circumventing the parasitic H_2 evolution reaction and leading to higher faradaic efficiencies for NH_3 .

Proton-conducting ceramic oxides have been explored as electrodes for nitrogen reduction, and when they operate at higher temperatures both the rate and faradaic efficiency increase (44). For example, efficiencies in excess of 50% and rates in the range of 10^{-9} - $10^{-8} \text{ mol-NH}_3 \text{ cm}^{-2} \text{ s}^{-1}$ have been attained above 673 K using oxide or molten chloride electrolytes and a variety of metal or metal oxide cathodes (44, 45). Note, however, that higher temperatures introduce an additional energy burden and hence compromise the advantage of this approach compared to H-B.

Photochemical reduction of N_2 to NH_3 has also been reported, and there may be guidance in these studies relevant to electrochemistry (46, 47). Photocatalytic routes to NH_3 have been summarized recently (48). One of the biggest challenges for photocatalytic NH_3 synthesis is the discovery of active and stable photoelectrode materials responsive to visible light. Synthetic nitrogenase mimics in the form of chalcogels, composed of Mo and Fe-containing biomimetic clusters, can potentially accomplish photocatalytic N_2 fixation and conversion to NH_3 at ambient temperature and pressure. Both Fe-S and Mo-Fe-S chalcogels have displayed promising activity toward N_2 reduction (49).

Plasma-driven transformations. The feasibility of using plasmas consisting of ions, electrons, and excited molecular species to drive chemical reactions that are thermally inaccessible has been known for many years (7). For example, NH_3 was synthesized in

laboratory-scale, non-thermal $\text{N}_2 + \text{H}_2$ plasmas at temperatures and pressures lower than those used in H-B as early as the 1970s, and more recently the synthesis has been demonstrated under much milder conditions (1 atm and 140°C) (50). The plasma synthesis of NH_3 has been carried out both homogeneously and in combination with heterogeneous catalysts (7, 50, 51).

Several mechanisms have been proposed to account for enhancements in catalytic activity in the presence of non-thermal plasmas (52-54). However, the fundamental science and practical engineering of plasma-driven NH_3 syntheses lag behind thermal and electrochemical routes and are therefore ripe for additional research. Further progress in this field will draw on the insights gained from traditional heterogeneous and electrochemical reductions.

Chemical looping. Chemical looping is perhaps most familiar from combustion where two connected fluidized beds are used to cycle solid particles between an oxidized and a reduced state to combust a carbon-containing fuel with oxygen (55). Chemical looping could also be performed with two fixed beds instead of fluidized beds. Nitrogen can be used instead of oxygen for a similar looping approach in NH_3 synthesis (56). First, N_2 is contacted with a suitable solid-state transition metal to yield a nitride (activation). In the second step, NH_3 is harvested by contacting the nitride with steam or H_2 (57). Recently, lithium has been employed as the parent metal for the nitride, but this approach requires liquid-phase electrolysis to recycle lithium and this step is usually not present in chemical looping (43).

Potential advantages of chemical looping include the ability to independently control process conditions for N_2 activation and product harvest. In this sense chemical looping can break the scaling relationship alluded to in Figure 2. Operation at atmospheric pressure is another major advantage of chemical looping for nitrogen activation (58). Based on results from a pilot-scale plant, chemical looping for combustion, including CO_2 capture, has been compared

to conventional combustion and appears to be economically attractive (59). This may be an indication of the possible economic feasibility of chemical looping for nitrogen activation.

Oxidation of N₂

Overview. The dominance of the H-B process in commercial N₂ fixation is arguably a direct consequence of the ready availability of H₂ from fossil hydrocarbons. As shown in Figure 1, oxidative fixation of N₂ can, in principle, be achieved with a lower energy input than reductive fixation if N₂, H₂O, and O₂ are used as reactants. Other nitrogen oxides are accessible at even lower free energies, especially when coupled with water to form the corresponding oxoacids.

Although H-B and natural processes have motivated substantial research into N₂ reductive fixation, direct N₂ oxidation remains largely unexplored despite its great practical value as a replacement for the Ostwald process. The fact that living organisms have not evolved to consume N₂ and O₂ and produce aqueous HNO₃ suggests fundamental chemical challenges that merit investigation. As a result, there is very little literature on the homogeneous oxidative chemistry of N₂.

Direct oxidation of N₂ with O₂. NO_x is unavoidably generated at the high temperatures that prevail during combustion in air. NO is the primary combustion-generated component of NO_x, and its formation can be viewed in the context of its equilibrium with N₂ and O₂ (eq 3).



The standard enthalpy of this reaction is 90.3 kJ/mol NO and the entropy is 12.4 J/(K•mol NO) (14, 15), indicating that equilibrium is unfavorable for NO production under ambient conditions. Due to the positive entropy, however, the equilibrium NO concentration rises rapidly with temperature, reaching 0.8% in air at 2000 K (60).

The direct bimolecular reaction of N₂ and O₂ to produce NO is symmetry-forbidden and has a negligible rate even at combustion temperatures. Rather, NO is produced during combustion via eqs 4 and 5, where O (and similarly OH) radicals attack N₂, as originally proposed by Zeldovich (61).




Analogous reactions are at play in high-temperature thermal plasmas, as in the original B-E arc process. Thermal plasmas are unlikely to be energy-competitive with the H-B process, even if the latter uses a renewable H₂ source (62), because the overall energy efficiencies of N₂ activation are low and rapid thermal quenching is required to suppress NO decomposition back to N₂ and O₂.

The aforementioned fundamental limitations can be mitigated using low-temperature, non-thermal plasmas generated by either a dielectric barrier discharge or microwave absorption at or below atmospheric pressure, potentially coupled with appropriate catalysts (7). According to current estimates, theoretical energy consumption for N₂ fixation via eq 3 in a non-thermal plasma (~400 kJ/mol N₂) is more than 2.5 times lower than that for the H-B process with methane-derived H₂ (62-64), and the energy efficiencies already attained in the laboratory (600-1200 kJ/mol N₂, assuming 100% efficient plasma generation (63, 64)) are better than the H-B process using H₂ from water electrolysis (~3000 kJ/mol N₂ (62)), 40% of which would go to electrolysis (65). Experiments and kinetic models show that the primary effect of the non-thermal plasma is to accelerate Zeldovich-like reactions involving athermal, vibrationally excited N₂. Practical implementation of non-thermal plasmas is hampered by their relatively low power per unit reactant mass and thus low throughput.


A thermal, heterogeneous N₂ oxidation catalyst would have to activate N₂ and O₂ and be stable at the extreme temperatures at which NO production becomes thermodynamically favored. Because of these stringent demands, non-thermal electro-, photo-, or plasma-assisted oxidation routes likely offer the greatest opportunities for progress. The development of catalytic systems that can effectively couple with these external energy sources will be key to practical advances. Preliminary results with non-thermal plasmas, especially coupled to catalysts, are promising. There is a pressing need to uncover the fundamental mechanisms that couple plasma chemistry, surface chemistry, catalysts, and theory to guide optimization of plasma and rational development of appropriate catalytic materials.

Electrochemical oxidation of N₂ to HNO₃. The oxidation line in Figure 4 shows that N₂ is electrochemically unstable toward NO₃⁻ under moderately oxidizing conditions (eq 6).



At pH > 1.3, this ten-electron reaction is more thermodynamically favorable than the parasitic four-electron water oxidation to O₂. Thus, it is possible for NO₃⁻ to be the only product of an anodic process, particularly in neutral and alkaline solutions, if a sufficiently active and selective electrocatalyst for eq 6 can be discovered. The corresponding cell-completing cathodic reaction can be either water reduction to H₂ or O₂ reduction to water. Little apparent progress has yet been made in developing such catalysts, but there is no reason to believe that they cannot eventually be discovered given the necessary resources.

By coupling cathodic N₂ reduction (eq 2) with anodic N₂ oxidation (eq 6), an electrochemical cell consuming only atmospheric N₂ and water as feedstock to yield aqueous NH₄NO₃ (eq 7) can be envisioned.



The additional H_2 production is necessary for matching cathodic and anodic currents and maintaining the electrolyte pH constant. Such a cell would require a minimum of 1.08 V to operate in neutral or alkaline electrolyte, which is slightly lower than the minimum water electrolysis voltage of 1.23 V. Advances relating to electrochemical N_2 oxidation will require development of catalysts that are sufficiently active (capable of good current densities at low overpotentials), selective (with respect to water oxidation), and stable (toward deactivation under harsh redox and pH operating conditions).

NO_y reduction and NH_3 oxidation

Overview. The redox chemistry of forms of nitrogen other than N_2 is immense and rich, and it is extensively incorporated into biological systems. Both NO_y and NH_3 are environmentally hazardous pollutants generated by industrial and transportation activity, and thus extensive research has gone into developing and applying NO_y reduction and NH_3 oxidation catalysts. As is often the case, the understanding of these catalysts lags their applications

Ammonia oxidation and NO_y reduction are critical to environmental protection and are much less well understood or optimized than the synthesis of NH_3 . There are appealing opportunities to apply the experimental and computational tools of modern heterogeneous catalysis to these reactions, both to develop a fundamental understanding of the processes and to identify superior materials and catalytic transformations; for example, catalysts that can selectively reduce NO_y to N_2 using hydrocarbon reductants. Environmental applications generally demand high longevity, durability, and tolerance to poisons. Key gaps in understanding include how activity and selectivity can be achieved in relatively cool gas streams, how catalyst structure evolves over long periods of time, how sulfur and other common poisons interfere with

reactions, and especially how these effects can be mitigated.

NO_y reduction. NO decomposition, the reverse of eq 3, is thermodynamically downhill but difficult to catalyze under the oxygen-rich conditions of interest for environmental protection (66). Nevertheless, NO decomposition has been demonstrated using both homogeneous and heterogeneous catalysts. Decomposition appears to involve a two-electron reduction of two NO molecules to a hyponitrite (eq 8).



Coordination complexes of hyponitrites are not uncommon, and a tri-Cu hyponitrite coordination complex has been isolated as an intermediate in the catalytic decomposition of NO to N₂ (67). A Cu dimer is similarly implicated as the active site in a Cu-exchanged zeolite catalyst for NO decomposition (68).

NO_x can be catalytically reduced to N₂ via several routes. Precious metals are active for NO_x reduction by CO and hydrocarbons, but only under conditions in which O₂ concentrations are low (10). Vanadia/titania and metal-exchanged zeolites catalyze selective reduction of NO_x by NH₃ (69). Nitrosamine appears to be the key N₂-forming intermediate in the catalytic pathway (eq 9).



This N₂-forming reaction is exothermic, implying significant, but perhaps not insurmountable, kinetic challenges to reversing the chemistry.

NO_x can also be catalytically reduced with H_2 over Pd and Pt catalysts (13), and N_2 is typically the desired product (66). By suitable selection of promoters and control of the NO/H_2 ratio, however, NH_3 can be produced over Pt catalysts (70). Likewise, NH_3 competes with N_2 as the product of the catalytic reduction of NO_2^- and NO_3^- by H_2 over Pd catalysts (13).

Bacteria analogously reduce NO_3^- and NO_2^- through a series of gaseous intermediates leading ultimately to N_2 in a process called denitrification (eq 10). In these bacteria, NO_y acts as a terminal electron acceptor in an anaerobic respiration process. Electrons flowing through membrane-bound proteins produce a proton gradient that in turn is used to make ATP. Each step in the denitrification process is catalyzed by well-studied metalloenzymes that use some rather unusual metal clusters to achieve their chemistry (71, 72). From a global nitrogen perspective, denitrification by these bacteria functions to convert fixed forms of N (NO_y) into N_2 . In some cases, this process is beneficial, such as during waste-water treatment to remove nitrates. In other cases, such as in agriculture, denitrification results in loss of N that was applied to crops as fertilizer.



NH₃ oxidation. Heterogeneous NH_3 oxidation with O_2 is at the heart of the Ostwald process and is practiced in a variety of environmental protection applications. Precious metals remain the workhorse catalysts, and therefore opportunities exist to develop lower-cost materials having equivalent or better activity and selectivity. The preferred NH_3 oxidation products shift from N_2 at low temperatures to NO at higher temperatures, with N_2O being a minor but highly undesirable product. At present, a full mechanistic understanding of this process and of the kinetic origins of selectivity is not available.

NH₃ and/or NO₂⁻ are fuel for bacteria and archaea that employ multi-electron oxidative reactions to generate reducing equivalents for cellular respiration and to establish a proton gradient for ATP synthesis (73, 74). Ammonia-oxidizing bacteria (AOB) and archaea (AOA) stoichiometrically convert NH₃ to NO₂⁻. AOA and AOB first carry out the selective conversion of NH₃ to hydroxylamine (NH₂OH) using an integral membrane Cu monooxygenase called ammonia monooxygenase (AMO) (eq 11). Active AMO has never been purified, and thus this challenging transformation awaits mechanistic elucidation.



The NH₂OH generated by AMO is oxidized to provide a net electron flow for cellular respiration. How AOA processes NH₂OH is unknown (75). In AOB, this process is carried out by hydroxylamine oxidoreductase (HAO), which contains a rare, covalently modified *c*-heme, heme P460, to which NH₂OH binds at Fe and undergoes proton-coupled oxidation (73). Recent experiments strongly support NO as the enzymatic product of HAO reactivity, contrary to decades of dogma asserting NO₂⁻ as the enzymatic product (76). Assuming a 2-electron turnover of AMO, the 3-electron oxidation of NH₂OH by HAO furnishes one net electron for cellular respiration. Stoichiometric production of NO₂⁻ from NH₃ by AOB likely involves an additional, but as-yet unidentified, third enzyme in the pathway. Cytotoxicity of both NO and NH₂OH may be managed by cytochrome P460, a monoheme enzyme that selectively produces N₂O from the reaction of NH₂OH with Fe-bound NO (77). NO₂⁻ is itself cellular fuel for nitrite-oxidizing bacteria (NOB) that effect the 2-electron oxidation of NO₂⁻ to NO₃⁻ and for recently discovered "complete ammonia oxidation" (COMAMMOX) bacteria that effect the 8-electron oxidation of

NH_3 to NO_3^- (78).

Opportunity abounds to extract broadly applicable insights through the study of the oxidative enzymes operative in nitrification. Establishing the mechanism of NH_3 oxidation by AMO remains a grand challenge whose difficulty is exacerbated by the integral membrane nature of the enzyme and the sluggish growth of its host organisms. The end goal is tantalizing technology: selective hydroxylation of relatively inert bonds generalizable beyond N-species, especially considering that enzymes related to AMO, such as particulate methane monooxygenase, effect similar transformations of unactivated alkanes (79).

Mechanistic understanding of NH_2OH and NO_2^- oxidation in turn offers insights into proton-coupled, multi-electron transformations that are crucial to redox catalysis. NH_2OH is an energetic, cytotoxic metabolite that AOB and AOA harness as a source of reducing equivalents. The absence of requisite *c*-heme biosynthesis pathways in AOA necessitates substitution of HAO for either a non-heme or Cu-based enzyme for NH_2OH oxidation (80). Thus, opportunities exist to fill a missing link in the biogeochemical nitrogen cycle while expanding understanding of how transition metals can transduce energy from redox-active small molecules.

Concluding outlook

Since the beginning of the 20th century, both the ability to produce and the need to remediate nitrogen-containing compounds have been coupled to fossil fuels. Demands for greater energy efficiency, smaller and more flexible distributed processes, and environmental protection provide growing impetus to expand the scope of practically viable oxidative and reductive transformations of nitrogen that are not driven by fossil fuels. Opportunities exist to achieve radically improved, new, and different pathways, but progress in this regard will require a

molecular-level understanding of nitrogen transformation reactions, as well as the translation of these core insights to the discovery of new catalytic systems and alternative means of delivering the energy needed to drive those reactions. These understandings will emerge through the collective knowledge and insights to be gained from fundamental research that integrates experiments and theory in hetero- and homogeneous catalysis science, in photon- and electron-driven processes, and in biology.

Acknowledgments

Funding: This article evolved from presentations and discussion at the workshop “Frontiers, Opportunities, and Challenges in Biochemical and Chemical N₂ Activation” held in October 2016, in Gaithersburg, Maryland. The workshop was sponsored by the Council on Chemical Sciences, Geosciences and Biosciences of the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences. The authors thank the members of the Council for their encouragement and assistance in developing this workshop. The authors have no competing interests relevant to this publication.

References and Notes

1. J. W. Erisman, M. A. Sutton, J. Galloway, Z. Klimont, W. Winiwarter, How a Century of Ammonia Synthesis Changed the World. *Nat. Geosci.* **1**, 636-639 (2008).
2. V. Smil, Detonator of the population explosion. *Nature* **400**, 415 (1999).
3. "Ammonia Production: Moving Towards Maximum Efficiency and Lower Ghg Emissions. ," In *Fertilizer Facts*, International Fertilizer Industry Association <http://www.fertilizer.org/> (2014).
4. G. Booth, H. Zollinger, K. McLaren, W. Sharples, A. E. Westwall, in *Ullmanns encyclopedia of industrial chemistry*, B. Elvers, S. Hawkins, G. Schulz, Eds. (2002), vol. 17.
5. I. Rafiqul, C. Weber, B. Lehmann, A. Voss, Energy efficiency improvements in ammonia production - Perspectives and uncertainties. *Energy* **30**, 2487-2504 (2005).
6. J. A. Miller, C. T. Bowman, Mechanism and modeling of nitrogen chemistry in combustion. *Prog. Energy Comb. Sci.* **15**, 287-338 (1989).
7. B. S. Patil, Q. Wang, V. Hessel, J. Lang, Plasma N₂-fixation: 1900–2014. *Catal. Today* **256**, 49–66 (2015).
8. C. H. Bartholomew, R. J. Farrauto, *Fundamentals of Industrial Catalytic Processes*. (Wiley, Hoboken, NJ, 2006).
9. P. A. Leighton, *Photochemistry of Air Pollution*. (Academic Press, 1961).
10. M. Shelef, R. W. McCabe, Twenty-five years after introduction of automotive catalysts: what next? *Catalysis Today* **62**, 35-50 (2000).
11. M. Zammit *et al.*, "Future automotive aftertreatment solutions: The 150C challenge workshop report," Tech. Rep., U.S. Drive Report PNNL-22815," (Southfield, Michigan, 2013).
12. *National Research Council Clean Coastal Waters: Understanding and Reducing the Effects of Nutrient Pollution*. (Natl. Acad. Press, Washington DC, 2000).
13. B. P. Chaplin *et al.*, Critical Review of Pd-Based Catalytic Treatment of Priority Contaminants in Water. *Environ. Sci. Technol.* **46**, 3655-3670 (2012).
14. The following standard states at 298 K and 1 bar are adopted throughout this paper: pure liquid for water, 1 mol/L for aqueous solutes, gaseous state for all other compounds; these states are designated by subscripts (liq), (aq), and (g), respectively. Aqueous nitric acid is considered to be fully ionized.
15. D. D. Wagman *et al.*, The NBS tables of chemical thermodynamic properties. *J. Phys. Chem. Ref. Data* **11**, Suppl. No. 2, (1982).
16. L. V. Gurvich, I. V. Veyts, C. B. Alcock, *Thermochemical Properties of Individual Substances*. (Hemisphere Publishing Corp., New York, NY, 1989), vol. 1, part two.
17. *U.S. Geological Survey, Mineral Commodity Summaries*, 117 (2018).
18. The Essential Chemical Industry – Online: <http://essentialchemicalindustry.org/chemicals/nitric-acid.html> (accessed Feb. 22, 2018).
19. D. A. Armstrong *et al.*, Standard electrode potentials involving radicals in aqueous solution: inorganic radicals (IUPAC Technical Report). *Pure Appl. Chem.* **87**, 1139-1150 (2015).
20. A. Logadottir *et al.*, The Brønsted–Evans–Polanyi Relation and the Volcano Plot for Ammonia Synthesis over Transition Metal Catalysts. *J. Catal.* **197**, 229-231 (2001).
21. C. J. H. Jacobsen *et al.*, Catalyst Design by Interpolation in the Periodic Table: Bimetallic Ammonia Synthesis Catalysts. *J. Am. Chem. Soc.* **123**, 8404-8405 (2001).
22. A. J. Medford *et al.*, From the Sabatier Principle to a Predictive Theory of Transition-Metal Heterogeneous Catalysis. *J. Catal.* **328**, 36 (2015).
23. E. J. Vicente, D. R. Dean, Keeping The Nitrogen-Fixation Dream Alive. *Proc. Natl. Acad. Sci. U.S.A.* **114**, 3009 (2017).
24. R. D. Milton *et al.*, The In Vivo Potential-Regulated Protective Protein of Nitrogenase in

- Azotobacter vinelandii Supports Aerobic Bioelectrochemical Dinitrogen Reduction In Vitro. *Journal of the American Chemical Society* **139**, 9044-9052 (2017).
25. B. M. Hoffman, D. Lukoyanov, Z.-Y. Yang, D. R. Dean, L. C. Seefeldt, Mechanism of nitrogen fixation by nitrogenase: the next stage. *Chem. Rev.* **114**, 4041-4062 (2014).
 26. I. Čorić, P. L. Holland, Insight into the Iron–Molybdenum Cofactor of Nitrogenase from Synthetic Iron Complexes with Sulfur, Carbon, and Hydride Ligands. *J. Am. Chem. Soc.* **138**, 7200-7211 (2016).
 27. P. Paengnakorn *et al.*, Infrared spectroscopy of the nitrogenase MoFe protein under electrochemical control: Potential-triggered CO binding. *Chem. Sci.* **8**, 1500-1505 (2017).
 28. R. D. Milton *et al.*, Bioelectrochemical Haber-Bosch Process: An Ammonia-Producing H₂/N₂ Fuel Cell. *Angew. Chem. Int. Ed.* **56**, 2680-2683 (2017).
 29. K. Danyal *et al.*, Uncoupling nitrogenase: Catalytic reduction of hydrazine to ammonia by a MoFe protein in the absence of Fe protein-ATP. *J. Am. Chem. Soc.* **132**, 13197-13199 (2010).
 30. N. Khadka *et al.*, Mechanism of Nitrogenase H₂ Formation by Metal-Hydride Protonation Probed by Mediated Electrocatalysis and H/D Isotope Effects. *J. Am. Chem. Soc.* **139**, 13518-13524 (2017).
 31. K. A. Brown *et al.*, Light-driven dinitrogen reduction catalyzed by a CdS:nitrogenase MoFe protein biohybrid. *Science* **352**, 448-450 (2016).
 32. A. D. Allen, C. V. Senoff, Nitrogenopentammineruthenium(II) complexes. *Chem. Commun.*, 621-622 (1965).
 33. J. Chatt, J. R. Dilworth, R. L. Richards, Recent Advances in the Chemistry of Nitrogen Fixation. *Chem. Rev.* **78**, 589-625 (1978).
 34. C. J. Pickett, J. Talarmin, Electrosynthesis of ammonia. *Nature* **317**, 652-653 (1985).
 35. D. V. Yandulov, R. R. Schrock, Catalytic reduction of dinitrogen to ammonia at a single molybdenum center. *Science* **301**, 76-78 (2003).
 36. K. Arashiba, Y. Miyake, Y. Nishibayashi, A molybdenum complex bearing PNP-type pincer ligands leads to the catalytic reduction of dinitrogen into ammonia. *Nat. Chem.* **3**, 120-125 (2011).
 37. K. Arashiba *et al.*, Catalytic reduction of dinitrogen to ammonia by use of molybdenum–nitride complexes bearing a tridentate triphosphine as catalysts. *J. Am. Chem. Soc.* **137**, 666–5669 (2015).
 38. J. S. Anderson, J. Rittle, J. C. Peters, Catalytic conversion of nitrogen to ammonia by an iron model complex. *Nature* **501**, 84-87 (2013).
 39. M. J. Chalkley, T. J. Del Castillo, B. D. Matson, J. P. Roddy, J. C. Peters, Catalytic N₂-to-NH₃ conversion by Fe at lower driving force: A proposed role for metallocene-mediated PCET. *ACS Cent. Sci.* **3**, 217-223 (2017).
 40. V. Rosca, M. Duca, M. T. de Groot, M. T. M. Koper, Nitrogen Cycle Electrocatalysis. *Chem. Rev.* **109**, 2209-2244 (2009).
 41. F. Zhou *et al.*, Electro-synthesis of ammonia from nitrogen at ambient temperature and pressure in ionic liquids. *Energy Environ. Sci.* **10**, 2516-2520 (2017).
 42. R. Lan, S. Tao., Electrochemical synthesis of ammonia directly from air and water using a Li⁺/H⁺/NH₄⁺ mixed conducting electrolyte. *RSC Adv.*, 18016-18021 (2013).
 43. J. M. McEnaney *et al.*, Ammonia synthesis from N₂ and H₂O using a lithium cycling electrification strategy at atmospheric pressure. *Energy & Environmental Science* **7**, 1621-1630 (2017).
 44. S. Licht *et al.*, Ammonia synthesis by N₂ and steam electrolysis in molten hydroxide suspensions of nanoscale Fe₂O₃. *Science* **345**, 637-640 (2014).
 45. V. Kyriakou, I. Garagounis, E. Vasileiou, A. Vourros, M. Stoukides, Progress in the electrochemical synthesis of ammonia. *Catalysis Today* **286**, 2-13 (2017).

46. R. J. Hamers, J. A. Bandy, D. Zhu, L. Zhang, Photoemission from diamond films and substrates into water: dynamics of solvated electrons and implications for diamond photoelectrochemistry. *Faraday Discuss.* **172**, 397-411 (2014).
47. C. Guo, J. Ran, A. Vasileff, S.-Z. Qiao, Rational design of electrocatalysts and photo(electro)catalysts for nitrogen reduction to ammonia (NH₃) under ambient conditions. *Energy Environ. Sci.* **11**, 45-56 (2018).
48. A. J. Medford, M. C. Hatzell, Photon-Driven Nitrogen Fixation: Current Progress, Thermodynamic Considerations, and Future Outlook. *ACS Catal.* **7**, 2624 (2017).
49. J. Liu *et al.*, Nitrogenase-Mimic Iron-Containing Chalcogels for Photochemical Reduction of Dinitrogen to Ammonia. *Proc. Natl. Acad. Sci. U.S.A.* **113**, 5530-5535 (2016).
50. J. H. van Helden *et al.*, Detailed study of the plasma-activated catalytic generation of ammonia in N₂-H₂ plasmas. *J. Appl. Phys.* **101**, 043305 (2007).
51. J. Hong, S. Prawer, A. B. Murphy, Plasma Catalysis as an Alternative Route for Ammonia Production: Status, Mechanisms, and Prospects for Progress. *ACS Sustainable Chemistry & Engineering* **6**, 15-31 (2018).
52. E. C. Neyts, K. Ostrikov, M. K. Sunkara, A. Bogaerts, Plasma Catalysis: Synergistic Effects at the Nanoscale. *Chem. Rev.* **115**, 13408-13446 (2015).
53. J. C. Whitehead, Plasma-catalysis: the known knowns, the known unknowns and the unknown unknowns. *J. Phys. D: Appl. Phys.* **49**, 243001 (2016).
54. P. Mehta *et al.*, Overcoming Ammonia Synthesis Scaling Relations with Plasma-enabled Catalysis. *Nature Catal.* **In Press**, (2018) doi: 10.1038/s41929-018-0045-1.
55. J. Adanez, A. Abad, F. Garcia-Labiano, P. Gayan, L. F. d. Diego, Progress in Chemical-Looping Combustion and Reforming Technologies. *Prog. Energy Combust. Sci.* **38**, 215-282 (2012).
56. R. Michalsky, A. M. Avram, B. A. Peterson, P. H. Pfromm, A. A. Peterson, Chemical looping of metal nitride catalysts: low-pressure ammonia synthesis for energy storage. *Chem. Sci.* **6**, 3965-3974 (2015).
57. M. E. Gálvez, M. Halmann, A. Steinfeld, Ammonia production via a two-step Al₂O₃/AlN thermochemical cycle. 1. thermodynamic, environmental, and economic analyses. *Ind. & Eng. Chem. Res.* **46**, 2042-2046 (2007).
58. R. Michalsky, P. Pfromm, An Ionicity rationale to design solid phase metal nitride reactants for solar ammonia production. *J. Phys. Chem. C* **116**, 23243-23255 (2012).
59. L. Anders, B. Leckner, A 1000 MWth boiler for chemical-looping combustion of solid fuels - Discussion of design and cost. *Appl. Energy* **157**, 475-487 (2015).
60. W. F. Schneider, in *Environmental Catalysis*, V. H. Grassian, Ed. (Wiley-VCH, 2004), pp. 233-268.
61. A. M. Dean, J. W. Bozzelli, in *Gas-Phase Combustion Chemistry*, W. C. Gardiner, Ed. (Springer New York, New York, NY, 2000), pp. 125-341.
62. N. Cherkasov, A. O. Ibhadon, P. Fitzpatrick, A review of the existing and alternative methods for greener nitrogen fixation. *Chem. Eng. Process. Process Intensif.* **90**, 24-33 (2015).
63. A. Fridman, *Plasma Chemistry*. (Cambridge University Press, Cambridge, 2008).
64. V. D. Rusanov, A. A. Fridman, G. V. Sholin, The physics of a chemically active plasma with nonequilibrium vibrational excitation of molecules. *Soviet Physics Uspekhi* **24**, 447-474 (1981).
65. M. Carmo, D. Fritz, J. Mergel, D. Stolten, *A comprehensive review on PEM electrolysis*. (2013), vol. 38, pp. 4901-4934.
66. V. I. Pârvulescu, P. Grange, B. Delmon, Catalytic removal of NO. *Catal. Today* **46**, 233-316 (1998).
67. D. Lionetti, G. de Ruiter, T. Agapie, A trans-Hyponitrite Intermediate in the Reductive Coupling and Deoxygenation of Nitric Oxide by a Tricopper-Lewis Acid Complex. *J. Am. Chem. Soc.* **138**, 5008-5011 (2016).
68. M. H. Groothaert, J. A. van Bokhoven, A. A. Battiston, B. M. Weckhuysen, R. A. Schoonheydt, Bis

- (μ -oxo)dicopper in Cu-ZSM-5 and Its Role in the Decomposition of NO: A Combined in Situ XAFS, UV-Vis-Near-IR, and Kinetic Study. *J. Am. Chem. Soc.* **125**, 7629-7640 (2003).
69. C. Paolucci *et al.*, Dynamic Multinuclear Sites Formed By Mobilized Copper Ions In Nox Selective Catalytic Reduction. *Science* **357**, 898 (2017).
 70. Y. J. Mergler, B. E. Nieuwenhuys, NO reduction by H₂ over promoted Pt catalysts. *Appl. Catal., B* **12**, 95-110 (1997).
 71. R. M. Martínez-Espinosa, J. A. Cole, D. J. Richardson, N. J. Watmough, Enzymology and ecology of the nitrogen cycle. *Biochem. Soc. Trans.* **39**, 175-178 (2011).
 72. P. Tavares, A. S. Pereira, J. J. G. Moura, I. Moura, Metalloenzymes of the denitrification pathway. *J. Inorg. Biochem.* **100**, 2087-2100 (2006).
 73. A. B. Hooper, D. Arciero, D. Bergmann, M. P. Hendrich, in *Respiration in Archaea and Bacteria: Diversity of Prokaryotic Respiratory Systems. Advances in Photosynthesis and Respiration*, D. Zannoni, Ed. (Springer, Dordrecht, 2004), vol. 16, pp. 121-147.
 74. M. Konneke *et al.*, Isolation of an autotrophic ammonia-oxidizing marine archaeon. *Nature* **437**, 543-546 (2005).
 75. N. Vajrala *et al.*, Hydroxylamine as an intermediate in ammonia oxidation by globally abundant marine archaea. *Proc. Natl. Acad. Sci. U.S.A.* **110**, 1006-1011 (2013).
 76. J. D. Caranto, K. M. Lancaster, Nitric oxide is an obligate bacterial nitrification intermediate produced by hydroxylamine oxidoreductase. *Proc. Natl. Acad. Sci. U.S.A.* **114**, 8217 (2017).
 77. J. D. Caranto, A. C. Vilbert, K. M. Lancaster, Nitrosomonas europaea cytochrome P460 is a direct link between nitrification and nitrous oxide emission. *Proc. Natl. Acad. Sci. U.S.A.* **113**, 14704-14709 (2016).
 78. H. Daims *et al.*, Complete nitrification by Nitrospira bacteria. *Nature* **528**, 504-509 (2015).
 79. T. J. Lawton, J. Ham, T. Sun, A. C. Rosenzweig, Structural conservation of the B subunit in the ammonia monooxygenase/particulate methane monooxygenase superfamily. *Proteins Struct. Funct. Bioinf.* **82**, 2263-2267 (2014).
 80. C. B. Walker *et al.*, Nitrosopumilus maritimus genome reveals unique mechanisms for nitrification and autotrophy in globally distributed marine crenarchaea. *Proc. Natl. Acad. Sci. U.S.A.* **107**, 8818-8823 (2010).