

Microporous polymeric composite membranes with advanced film properties: Pore intercalation yields excellent CO₂ separation performance

Ali K. Sekizkardes,^{a,b} Victor A. Kusuma,^{a,b} Joshua S. McNally,^c David W. Gidley,^d Kevin Resnik^{a,b}, Surendar R. Venna,^{a,b*} and David Hopkinson^a*

US. Email; ali.sekizkardes@netl.doe.gov; Surendar.Venna@netl.doe.gov

^{a.} U.S. Department of Energy National Energy Technology Laboratory, Pittsburgh, PA 15236

^{b.} AECOM, Pittsburgh, PA 15236, United States

^{c.} Idaho National Laboratory, Idaho Falls, ID 83415, United States

^{d.} Department of Physics, University of Michigan, Ann Arbor MI 48109, United States

Keywords: PIM-1, polyphosphazene, polymer blend, gas separation, CO₂

Abstract

Polymers of intrinsic microporosity (PIMs) are revolutionary gas separation materials because of their ultra-high permeability, but suffer from low gas pair selectivity (for example CO₂/N₂) and poor durability due to brittleness. Here we present a simple solution to these problems by blending PIM-1 with compatible polymer blend composed of PIM-1 and an ether side chain polyphosphazene (MEEP80), which possess better mechanical flexibility and higher CO₂/N₂ selectivity than the native PIM-1 while maintaining high CO₂ permeability. Under mixed gas test conditions, a blend of 25 wt% MEEP80 in PIM-1 has a CO₂ permeability of 2440 barrer and a CO₂/N₂ selectivity of 39 under mixed gas testing conditions, putting it among the best known polymers for CO₂/N₂ separation.

Introduction

Polymeric gas separation membranes have been studied extensively for gas separations but require further performance improvements for emerging industrial applications such as CO₂/N₂ separation for carbon capture from fossil fuel power generation.¹ An analysis by Merkel and co-authors suggests that a polymer membrane should have a CO₂/N₂ selectivity of at least 30 and a CO₂ permeance exceeding 2000 GPU in order to be considered economically viable in a two stage membrane process with an air sweep.² Achieving higher values of CO₂ permeance is desirable in order to process the enormous volume of flue gas that is emitted from fossil fuel power plants while minimizing the required membrane area.

In 2004, Budd et al. reported a new class of polymeric membranes known as polymers of intrinsic microporosity (PIMs) which have gained considerable attention for their ultra-high gas permeability.³ The most extensively studied PIM, named PIM-1, was constructed from monomers which polymerized into a contorted backbone structure, leading to inefficient polymer chain packing and an intrinsic microporosity with unusually high free volume for a polymeric membrane.⁴ With a CO₂ permeability of over 5800 barrer and a CO₂/N₂ selectivity of 16, PIM-1 sits just below the 2008 Robeson upper bound, which identifies the gas separation performance limit for pure polymeric materials.⁵ This unprecedented permeability would make it a strong candidate for CO₂ capture, if not for several major drawbacks that are a result of its unique polymer structure. First, the average pore size of PIM-1 (~1 nm) leads to poor size discrimination between all gases compared to conventional glassy polymeric membranes such as Matrimid or polysulfone.⁶ Second, a lack of hydrogen bonding between polymer chains results in a brittle film that is prone to cracking.

In recent years, many studies have been conducted with the goal of improving the gas selectivity of PIM-1.⁷ Many of these studies involve post-functionalization to convert the nitrile groups of PIM-1 into functional groups such as carboxylic acids, amines, tetrazoles and amidoximes

which can interact with CO₂.^{8,9} Alternatively, PIM-1 has been blended with various polymers such as Matrimid, Torlon, polysulfone and polyionic liquids to improve the mechanical properties and/or gas selectivity.^{10,11} Both functionalization and blending of PIM-1 have been shown to improve CO₂/N₂ selectivity, but it invariably comes at the expense of decreased free volume and CO₂ permeability. In addition, modified PIM-1 membranes were often still brittle and in most cases phase separation was reported due to poor blend compatibility.^{10,12-14}

We report herein that an ether-functionalized polyphosphazene, PN[2-(2-methoxyethoxy)ethoxy](p-methoxyphenoxy o-allylphenoxy)_n (MEEP80), exhibited better phase compatibility across a larger composition range with PIM-1 compared to other polymers that have been blended with PIM-1. MEEP80 is an amorphous and rubbery polymer composed of a phosphazene backbone with a high concentration of ether side chains.^{15,16} The phosphazene backbone provides high polymer chain flexibility and a low glass transition temperature, which are correlated with the enhancement of CO₂ permeability.¹⁷ The polar interaction ability of the ether side chains of MEEP80 further contribute to high CO₂ permeability. Here, we chose MEEP80 for blending it with PIM-1 to enhance chain flexibility of the final composite membrane and for high selectivity of CO₂ over other other light gases. MEEP80 is a high-performance polymer material that also lies close to the Robeson upper bound for CO₂/N₂, but presents an opposite set of challenges compared to PIM-1. This material has a CO₂ permeability range of 400-500 barrer and a CO₂/N₂ selectivity over 30 at testing temperature of 30°C, but has a tacky, gel-like consistency. Blending the materials creates an ideal balance of the two, yielding a new Robeson upper bound polymer with improved selectivity for CO₂ compared to neat PIM-1, and with the distinct advantage of having excellent mechanical stability and durability.

Results and Discussion

PIM-1 was synthesized based on the low-temperature polycondensation reaction reported by Budd et al.³ (NMR spectrum in Figure S1 and N₂ adsorption isotherm in Figure S2). MEEP80

was synthesized using the post-polymerization substitution of the chloro side groups of poly(dichlorophosphazene) (NPCl_2) with nucleophiles such as 2-(2-methoxyethoxy)ethanol (MEE), *o*-allylphenol and *p*-methoxyphenol (NMR shown in Figure S3).^{18,19}

The 80 designation in MEEP80 refers to the 80 mol% substitution with the MEE group, with the phenolic groups making up the balance (Figure 1A). These phenolic groups improved the MEEP80 mechanical properties over 100% MEE-substituted polyphosphazene and increased its glass transition temperature (T_g).²⁰ While pure PIM-1 film coupons were brittle, MEEP80 is a semi-solid gel with more viscous than elastic characteristics (Figure 1B).²¹ To form the blend polymer, both PIM-1 and MEEP80 were dissolved in chloroform at the desired composition, forming uniform and miscible solutions. Tetrahydrofuran was also found to be a suitable co-solvent. Solutions were poured into poly(tetrafluoroethylene) (PTFE) dishes and the solvent was allowed to evaporate at ambient conditions overnight. Cast films were removed from the PTFE dishes without any solvent treatment. Two different blend membranes were fabricated with 25 wt% and 50 wt% of MEEP80 in PIM-1 and are denoted as PIM-1/25 wt% MEEP80 and PIM-1/50 wt% MEEP80 respectively. All membranes were thermally treated at 70°C for 24 hours. Thermogravimetric analysis (TGA) of membranes resulted in two apparent decomposition temperatures corresponding to PIM-1 and MEEP80 (Figure S4). The onset of the higher decomposition temperature of PIM-1 decreased as the MEEP80 content increased. Blend membranes showed high thermal stability over 290°C, which is higher than most polymeric membranes.

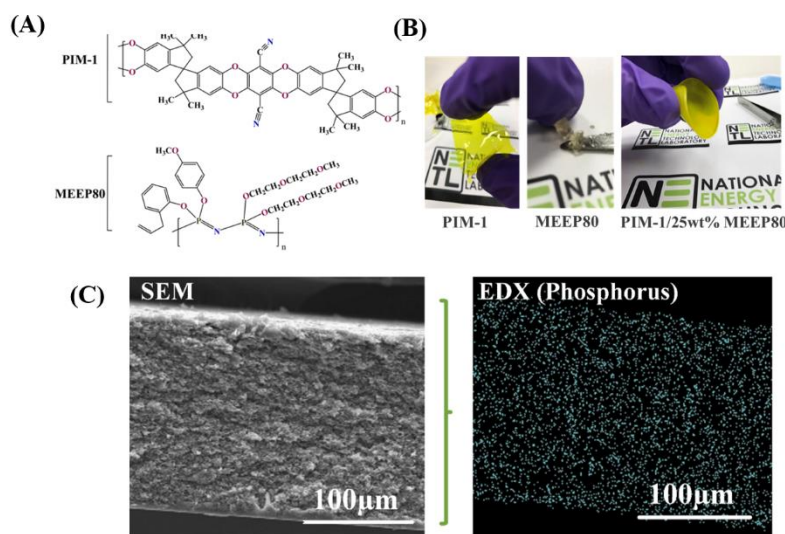


Figure 1. (A) Structures of PIM-1 and MEEP80, (B) photographs (left to right) of a brittle PIM-1 film, gel-like MEEP80 and a flexible PIM-1/25wt % MEEP80 films. (C) SEM image and EDX mapping of phosphorous in PIM-1/25 wt% MEEP80 showing the relatively uniform distribution of MEEP80.

Scanning electron microscopy (SEM) analysis and energy dispersive X-ray (EDX) mapping for phosphorous (present only in MEEP80) revealed that MEEP80 was distributed uniformly throughout the film cross-section with no visible defects or large-scale phase separation (Figure 1C and Figure S5 and S6). This was true for both 25 and 50 wt% MEEP80 blends (Figure 1C, Figure S7 and S8).

Blend polymers, in general, can display morphological defects such as multiple phase transitions, polymer aggregation, and void formation due to phase incompatibility.²² Differential scanning calorimetry (DSC) can be performed to evaluate polymer miscibility by comparing the glass transition temperatures (T_g) of the blend with those of the pure polymers. However, the T_g of PIM-1 is above its decomposition temperature (Figure 2A) and thus cannot be measured. The T_g analysis therefore depends entirely on comparison with pure MEEP80, which has a distinct T_g of -69.5°C . Blending PIM-1 into MEEP80 increased the T_g slightly to -66.3°C at 50 wt% MEEP80. The result suggests at least partial miscibility of MEEP80 with PIM-1 as chain interactions and entanglement decrease the MEEP80 chain mobility. Also secondary interactions such as Van der Waal's forces may contribute to the T_g shift. We propose that the flexible MEEP80 chains can be intercalated within the relatively rigid and unconventionally large pores of the PIM-1 network, held together primarily by chain entanglement.^{23,24}

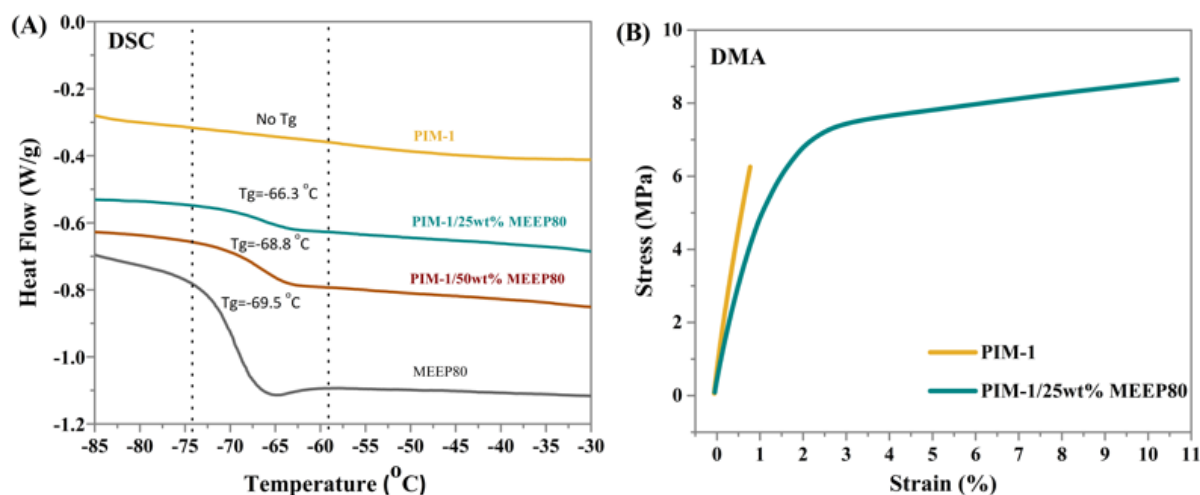


Figure 2. (A) DSC analysis of PIM-1, MEEP80 and blends of PIM-1/25 wt% MEEP80 and PIM-1/50 wt% MEEP80. (B) Tension tests for PIM-1 and 25 wt% PIM-1/MEEP80.

Further evidence of intermolecular interactions between PIM-1 and MEEP80 can be found in the FT-IR spectra. Incorporation of MEEP80 into PIM-1 resulted in increasing intensity of the P=N stretch at 1200 cm^{-1} on the MEEP80 backbone (Figure S9 and 10). Stretching of the dibenzodioxane C-O-C linkages in PIM-1 caused subtle shifts to higher frequency in a peak from 1008 to 1011 cm^{-1} and from 1261 to 1265 cm^{-1} with a higher MEEP80 concentration. This trend can be attributed to a molecular-level interaction between PIM-1 and MEEP80.²⁵

A tensile test was performed using a dynamic mechanical analyzer (DMA) to quantitatively demonstrate the improvement in mechanical properties. While the Young's modulus of PIM-1 (830 MPa) is higher than PIM-1/25 wt% MEEP80 (550 MPa), PIM-1 also has a very low strain to failure (< 1%) (Figure 2B) and it is a challenge to complete a measurement on the delicate thin film due to its brittleness. In contrast, the PIM-1/25 wt% MEEP80 membrane has a strain to failure of about 10.5%, giving it enough flexibility and durability to be handled and tested easily (Figure 1B).

Positron annihilation lifetime spectroscopy (PALS) was used to quantify the average inter-chain pore diameter and free volume of membranes by positronium (Ps) lifetime in the reported polymer dense films (see the SI for detailed procedure).²⁶ PALS measurements showed a clear trend in the pore size distribution of the polymers (Figure 3). The pore size distribution for PIM-1 is dominated by a peak with average pore diameter around 1 nm, while the pore distribution for MEEP80 is unimodal and centered around 0.7 nm. Incorporating MEEP80 into PIM-1 gradually decreased the intensity of the 1 nm pores with a modal shift towards the smaller pore size (Figure 3). At the same time, the 0.2 nm pores were eliminated. The results suggest that the flexible polyphosphazene can intercalate with the PIM-1, to some extent filling in the smaller void spaces. The prevalence of the 0.7 nm pores associated with MEEP80 was much more prominent for the 50 wt% blend compared to the 25 wt% blend, suggesting that for the 50 wt% composition a MEEP80-rich phase could be forming within the polymer once most of the smaller PIM-1 pores were filled. Since the blends do not present unimodal pore size distributions with proportionately changing average pore diameter it is difficult to assert that the PIM-1 and MEEP80 molecules have fully intertwined to form hybrid or blended voids.


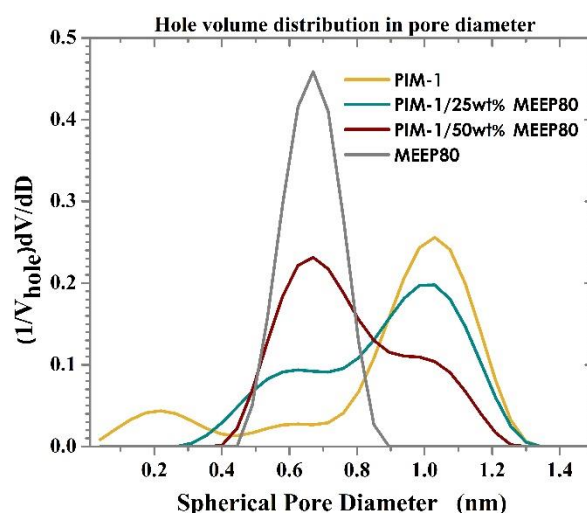


Figure 3. Pore diameter distribution measured by PALS for PIM-1, MEEP80, PIM-1/25 wt% MEEP80 and PIM-1/50 wt% MEEP80.

Pure gas permeability of the membranes was measured using an isochoric (constant volume) gas permeance test apparatus (described in the SI) at 40°C. Neat PIM-1 films have a pure gas CO₂ permeability of 5800 barrer with a CO₂/N₂ selectivity of 16, which is consistent with previous studies. PIM-1 blends with 25 wt% and 50 wt% MEEP80 showed significant improvement in the CO₂/N₂ selectivity (21 and 29, respectively) while the CO₂ permeability was decreased to 2450 and 2000 barrer, respectively (Figure 4A). In addition to CO₂ and N₂, permeability of CH₄, H₂, and O₂ was tested for neat PIM-1 and PIM-1/25 wt% MEEP80 membranes (Table S1). In the blended membranes, a larger loss in permeability for H₂ and O₂ compared to CO₂ and CH₄ is due to lower solubility (polarizability) of the former gases in the more rubbery MEEP80 component. The gas permeability decrease of the blend membranes was inevitable given the total free volume reduction but the CO₂ permeability remains significantly

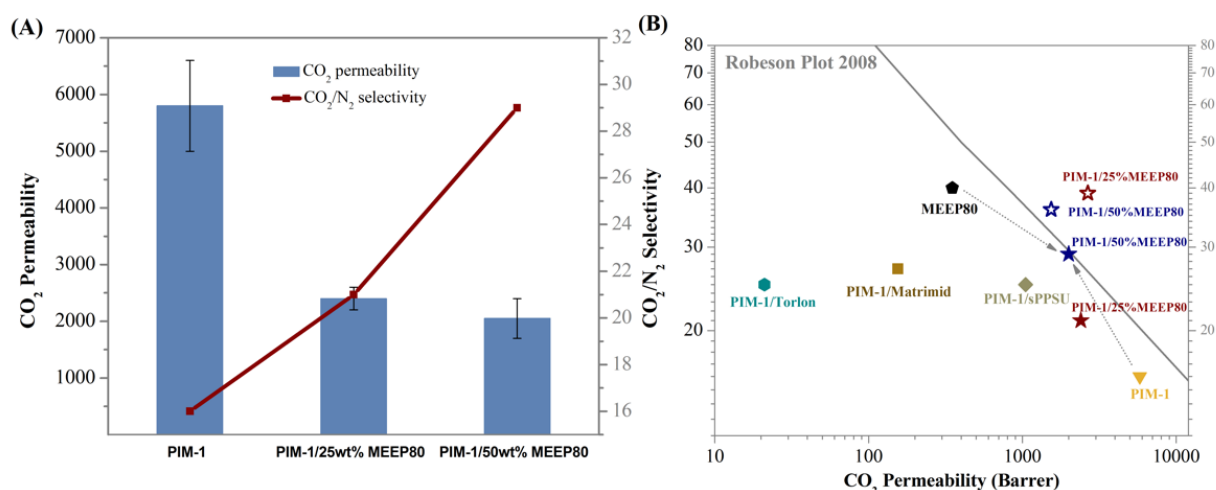

higher than most conventional polymer materials considered for carbon capture.^{27,28}

Figure 4. (A) Pure gas CO₂ permeability and CO₂/N₂ selectivity for neat PIM-1, and blends of 25 and 50 wt% MEEP80 in PIM-1. (B) CO₂ permeability and CO₂/N₂ selectivity of neat PIM-1 (yellow triangle, pure gas), neat MEEP80 (black pentagon, pure gas), and PIM-1/25 wt% MEEP80 (filled red star, pure gas; open red star, mixed gas) and PIM-1/50 wt% MEEP80 (filled blue star, pure gas; open blue star, mixed gas).^{10,12,22,29}

The higher selectivity achieved by the blend membranes compared with neat PIM-1 was possible due to the incorporation of MEEP80, which possesses oligo(ethylene oxide) side groups that are known to interact well with CO₂.³⁰ Despite the weak size sieving ability of PIM-1, the improved selectivity was possible due to an increase in CO₂ solubility selectivity compared to the other non-polar gases evaluated here. The blends reported here exhibited a more significant improvement in CO₂/N₂ selectivity compared to other recent reports of PIM-1 based polymer blends.²⁷ In particular, PIM-1/50 wt% MEEP80 is the first blend polymer to fall on the Robeson upper bound for CO₂/N₂ separation.²⁷ Blends of PIM-1 with 50 wt% Torlon,²⁹ 50 wt% Matrimid,¹² 20 wt% sPPSU,¹⁰ and 70 wt% Ultem³¹ all resulted in a lower CO₂ permeability and CO₂/N₂ selectivity compared with PIM-1/MEEP80 blend membranes (Figure 4B).

The effects of aging on PIM-1/50 wt% MEEP80 was characterized by gas permeation testing up to 120 days from casting of the film (Figure S11). The CO₂ permeability of the blend polymer decreased by about 35% after 60 days, with only a slight reduction in CO₂/N₂ selectivity. The CO₂ permeability was unchanged after an additional 60 days, while the CO₂/N₂ selectivity again decreased slightly.

We also evaluated gas permeation properties of PIM-1/25 wt% MEEP80 and PIM-1/50 wt% MEEP80 blend membranes in mixed gas conditions (CO₂/N₂/Ar 20:20:60) at 40 °C, 103 kPa. CO₂ permeability of blend membranes increased to 2660 and 1540 with CO₂/N₂ selectivity of 39 and 36, respectively for PIM-1/25 wt% MEEP80 and PIM-1/50 wt% MEEP80 (Figure 4B).

In conventional glassy polymers, the mixed gas selectivity is lower than the pure gas selectivity due to the plasticization effect of CO₂.³² But, in the case of high free volume glassy polymers like PIM, poly[1-(trimethylsilyl)-1-propyne] (PTMSP) and thermally rearranged (TR) polymers, the mixed gas selectivity can be higher than the pure gas selectivity due to the preferential adsorption of the more condensable gas (in this case CO₂) in the free volume of the polymer.^{13,33} Further evidence for this effect is shown in the CO₂ and N₂ isotherms (Figures S12 and S13). Henry's law slope calculations of CO₂ and N₂ isotherms at 298K showed that neat PIM-1 possesses CO₂/N₂ solubility selectivity of 24 whereas the blend membrane PIM-1/25 wt% MEEP80 shows a higher CO₂/N₂ solubility selectivity of 42.

The adsorption of condensable gas also blocks the transport of the less condensable gas, similar to that of microporous materials, resulting in further improvement in selectivity. The fact that the mixed gas selectivity is enhanced even more for PIM-1/25 wt% MEEP80 than PIM-1/50 wt% MEEP80 is further evidence that this phenomenon is caused by the high free volume glassy (PIM-1) component of the blend.

Conclusions

This work presents a polymeric blend composed of PIM-1 and MEEP80 polyphosphazene which exhibits sufficient miscibility to make cohesive, mechanically robust membranes. The blend overcomes severe drawbacks that exist with both of the pure polymers, i.e. the brittleness of PIM-1 and the gel-like nature of MEEP80, yielding a composite which has excellent flexibility and toughness. These blends are soluble in common solvents, and hence are suitable for solution processing to form films and coatings for use in practical membrane applications. Most importantly, the high CO₂ permeability and CO₂/N₂ selectivity observed for PIM-1/25 wt% MEEP80 and PIM-1/50 wt% MEEP80 membranes make them the best PIM-1 blends reported to date for this gas separation, with performance on the Robeson upper bound for PIM-1/50 wt% MEEP 80 when tested in pure gas and above the Robeson upper bound for both blend

compositions when tested in mixed gas. The materials are especially attractive for the application of post-combustion carbon capture where very high CO₂ permeability coupled with moderate CO₂/N₂ selectivity is desired in order to minimize the cost of an integrated carbon capture system.

Acknowledgments

This technical report was performed in support of the National Energy Technology Laboratory's ongoing research in CO₂ capture under the Carbon Capture field work proposal.

Disclaimer

This project was funded by the Department of Energy, National Energy Technology Laboratory, an agency of the United States Government, under the Carbon Capture Field Work Proposal and in part through a support contract with AECOM (DE-FE0004000). Neither the United States Government nor any agency thereof, nor any of their employees, nor AECOM, nor any of their employees, makes any warranty, expressed or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

References

- (1) Koros, W. J.; Fleming, G. K. Membrane-based gas separation. *Journal of Membrane Science* **1993**, *83*, 1-80.
- (2) Merkel, T. C.; Lin, H.; Wei, X.; Baker, R. Power plant post-combustion carbon dioxide capture: An opportunity for membranes. *Journal of Membrane Science* **2010**, *359*, 126-139.
- (3) Budd, P. M.; Elabas, E. S.; Ghanem, B. S.; Makhseed, S.; McKeown, N. B.; Msayib, K. J.; Tattershall, C. E.; Wang, D. Solution-Processed, Organophilic Membrane Derived from a Polymer of Intrinsic Microporosity. *Advanced Materials* **2004**, *16*, 456-459.
- (4) Low, Z.-X.; Budd, P. M.; McKeown, N. B.; Patterson, D. A. Gas Permeation Properties, Physical Aging, and Its Mitigation in High Free Volume Glassy Polymers. *Chemical Reviews* **2018**.
- (5) Robeson, L. M. The upper bound revisited. *Journal of Membrane Science* **2008**, *320*, 390-400.
- (6) McKeown, N. B.; Budd, P. M. Polymers of intrinsic microporosity (PIMs): organic materials for membrane separations, heterogeneous catalysis and hydrogen storage. *Chemical Society Reviews* **2006**, *35*, 675-683.
- (7) Mason, C. R.; Maynard-Atem, L.; Heard, K. W. J.; Satilmis, B.; Budd, P. M.; Friess, K.; Lanč, M.; Bernardo, P.; Clarizia, G.; Jansen, J. C. Enhancement of CO₂ Affinity in a Polymer of Intrinsic Microporosity by Amine Modification. *Macromolecules* **2014**, *47*, 1021-1029.
- (8) Yanaranop, P.; Santoso, B.; Etzion, R.; Jin, J. Facile conversion of nitrile to amide on polymers of intrinsic microporosity (PIM-1). *Polymer* **2016**, *98*, 244-251.
- (9) Zhang, J.; Schott, J. A.; Mahurin, S. M.; Dai, S. Porous Structure Design of Polymeric Membranes for Gas Separation. *Small Methods* **2017**, *1*, 1600051-n/a.
- (10) Yong, W. F.; Lee, Z. K.; Chung, T.-S.; Weber, M.; Staudt, C.; Maletzko, C. Blends of a Polymer of Intrinsic Microporosity and Partially Sulfonated Polyphenylenesulfone for Gas Separation. *ChemSusChem* **2016**, *9*, 1953-1962.
- (11) Halder, K.; Khan, M. M.; Grünauer, J.; Shishatskiy, S.; Abetz, C.; Filiz, V.; Abetz, V. Blend membranes of ionic liquid and polymers of intrinsic microporosity with improved gas separation characteristics. *Journal of Membrane Science* **2017**, *539*, 368-382.
- (12) Yong, W. F.; Li, F. Y.; Xiao, Y. C.; Li, P.; Pramoda, K. P.; Tong, Y. W.; Chung, T. S. Molecular engineering of PIM-1/Matrimid blend membranes for gas separation. *Journal of Membrane Science* **2012**, *407*, 47-57.
- (13) Du, N.; Park, H. B.; Robertson, G. P.; Dal-Cin, M. M.; Visser, T.; Scoles, L.; Guiver, M. D. Polymer nanosieve membranes for CO₂-capture applications. *Nat Mater* **2011**, *10*, 372-375.
- (14) Tien-Binh, N.; Vinh-Thang, H.; Chen, X. Y.; Rodrigue, D.; Kaliaguine, S. Crosslinked MOF-polymer to enhance gas separation of mixed matrix membranes. *Journal of Membrane Science* **2016**, *520*, 941-950.
- (15) Orme, C. J.; Stewart, F. F. Mixed gas hydrogen sulfide permeability and separation using supported polyphosphazene membranes. *Journal of Membrane Science* **2005**, *253*, 243-249.
- (16) Jankowsky, S.; Hiller, M. M.; Wiemhöfer, H. D. Preparation and electrochemical performance of polyphosphazene based salt-in-polymer electrolyte membranes for lithium ion batteries. *Journal of Power Sources* **2014**, *253*, 256-262.
- (17) Orme, C. J.; Klaehn, J. R.; Harrup, M. K.; Luther, T. A.; Peterson, E. S.; Stewart, F. F. Gas permeability in rubbery polyphosphazene membranes. *Journal of Membrane Science* **2006**, *280*, 175-184.

- (18) Stewart, F. F.; Harrup, M. K.; Luther, T. A.; Orme, C. J.; Lash, R. P. Formation of pervaporation membranes from polyphosphazenes having hydrophilic and hydrophobic pendant groups: Synthesis and characterization. *Journal of Applied Polymer Science* **2001**, *80*, 422-431.
- (19) Orme, C. J.; Harrup, M. K.; Luther, T. A.; Lash, R. P.; Houston, K. S.; Weinkauff, D. H.; Stewart, F. F. Characterization of gas transport in selected rubbery amorphous polyphosphazene membranes. *Journal of Membrane Science* **2001**, *186*, 249-256.
- (20) Rothmund, S.; Teasdale, I. Preparation of polyphosphazenes: a tutorial review. *Chemical Society Reviews* **2016**, *45*, 5200-5215.
- (21) Blonsky, P. M.; Shriver, D. F.; Austin, P.; Allcock, H. R. Polyphosphazene solid electrolytes. *Journal of the American Chemical Society* **1984**, *106*, 6854-6855.
- (22) Mei Wu, X.; Gen Zhang, Q.; Ju Lin, P.; Qu, Y.; Mei Zhu, A.; Lin Liu, Q. Towards enhanced CO₂ selectivity of the PIM-1 membrane by blending with polyethylene glycol. *Journal of Membrane Science* **2015**, *493*, 147-155.
- (23) Venna, S. R.; Spore, A.; Tian, Z.; Marti, A. M.; Albenze, E. J.; Nulwala, H. B.; Rosi, N. L.; Luebke, D. R.; Hopkinson, D. P.; Allcock, H. R. Polyphosphazene polymer development for mixed matrix membranes using SIFSIX-Cu-2i as performance enhancement filler particles. *Journal of Membrane Science* **2017**, *535*, 103-112.
- (24) Ghanem, B. S.; McKeown, N. B.; Budd, P. M.; Selbie, J. D.; Fritsch, D. High-Performance Membranes from Polyimides with Intrinsic Microporosity. *Advanced Materials* **2008**, *20*, 2766-2771.
- (25) Wu, X.; Tian, Z.; Wang, S.; Peng, D.; Yang, L.; Wu, Y.; Xin, Q.; Wu, H.; Jiang, Z. Mixed matrix membranes comprising polymers of intrinsic microporosity and covalent organic framework for gas separation. *Journal of Membrane Science* **2017**, *528*, 273-283.
- (26) Gidley, D. W.; Frieze, W. E.; Dull, T. L.; Sun, J.; Yee, A. F.; Nguyen, C. V.; Yoon, D. Y. Determination of pore-size distribution in low-dielectric thin films. *Applied Physics Letters* **2000**, *76*, 1282-1284.
- (27) Ma, C.; Urban, J. J. Polymers of Intrinsic Microporosity (PIMs) Gas Separation Membranes: A mini Review. *Proceedings of the Nature Research Society* **2018**, *2*, 02002.
- (28) Wang, S.; Li, X.; Wu, H.; Tian, Z.; Xin, Q.; He, G.; Peng, D.; Chen, S.; Yin, Y.; Jiang, Z.; Guiver, M. D. Advances in high permeability polymer-based membrane materials for CO₂ separations. *Energy & Environmental Science* **2016**, *9*, 1863-1890.
- (29) Yong, W. F.; Li, F. Y.; Chung, T. S.; Tong, Y. W. Molecular interaction, gas transport properties and plasticization behavior of cPIM-1/Torlon blend membranes. *Journal of Membrane Science* **2014**, *462*, 119-130.
- (30) Lin, H.; Van Wagner, E.; Freeman, B. D.; Toy, L. G.; Gupta, R. P. Plasticization-Enhanced Hydrogen Purification Using Polymeric Membranes. *Science* **2006**, *311*, 639-642.
- (31) Hao, L.; Li, P.; Chung, T.-S. PIM-1 as an organic filler to enhance the gas separation performance of Ultem polyetherimide. *Journal of Membrane Science* **2014**, *453*, 614-623.
- (32) Park, H. B.; Jung, C. H.; Lee, Y. M.; Hill, A. J.; Pas, S. J.; Mudie, S. T.; Van Wagner, E.; Freeman, B. D.; Cookson, D. J. Polymers with Cavities Tuned for Fast Selective Transport of Small Molecules and Ions. *Science* **2007**, *318*, 254-258.
- (33) I., P.; G., C. C.; A., M.; D., F. B. Hydrocarbon/hydrogen mixed gas permeation in poly(1 - trimethylsilyl - 1 - propyne) (PTMSP), poly(1 - phenyl - 1 - propyne) (PPP), and PTMSP/PPP blends. *Journal of Polymer Science Part B: Polymer Physics* **1996**, *34*, 2613-2621.