










RESEARCH ARTICLE | FEBRUARY 08 2022

# Excess noise in high-current diamond diodes SCI F FREE

Special Collection: [Wide- and Ultrawide-Bandgap Electronic Semiconductor Devices](#)

Subhajit Ghosh ; Harshad Surdi ; Fariborz Kargar ; Franz A. Koeck ; Sergey Rumyantsev ; Stephen Goodnick ; Robert J. Nemanich ; Alexander A. Balandin  

 Check for updates

*Appl. Phys. Lett.* 120, 062103 (2022)

<https://doi.org/10.1063/5.0083383>



View Online



Export Citation

CrossMark

## Articles You May Be Interested In

Perspective: Excess-entropy scaling

*J. Chem. Phys.* (December 2018)

Excess attenuation of an acoustic beam by turbulence


*J Acoust Soc Am* (December 2003)

Excess Noise in Cavity Magnetrons

*Journal of Applied Physics* (April 2004)

Webinar

### Boost Your Signal-to-Noise Ratio with Lock-in Detection



Sep. 7th – Register now



Zurich Instruments

# Excess noise in high-current diamond diodes

Cite as: Appl. Phys. Lett. **120**, 062103 (2022); doi: [10.1063/5.0083383](https://doi.org/10.1063/5.0083383)

Submitted: 24 December 2021 · Accepted: 21 January 2022 ·

Published Online: 8 February 2022



View Online



Export Citation



CrossMark

Subhajit Ghosh,<sup>1</sup>  Harshad Surdi,<sup>2</sup>  Fariborz Kargar,<sup>1</sup>  Franz A. Koeck,<sup>3</sup>  Sergey Rumyantsev,<sup>4</sup>   
Stephen Goodnick,<sup>2,4</sup>  Robert J. Nemanich,<sup>3</sup>  and Alexander A. Balandin<sup>1,a)</sup> 

## AFFILIATIONS

<sup>1</sup>Department of Electrical and Computer Engineering, Bourns College of Engineering, University of California, Riverside, California 92521, USA

<sup>2</sup>School of Electrical, Computer and Energy Engineering, Arizona State University, Tempe, Arizona 85281, USA

<sup>3</sup>Department of Physics, Arizona State University, Tempe, Arizona 85287, USA

<sup>4</sup>CENTERA Laboratories, Institute of High-Pressure Physics, Polish Academy of Sciences, Warsaw 01-142, Poland

Note: This paper is part of the APL Special Collection on Wide- and Ultrawide-Bandgap Electronic Semiconductor Devices.

<sup>a)</sup> Author to whom correspondence should be addressed: [balandin@ece.ucr.edu](mailto:balandin@ece.ucr.edu). URL: <https://balandingroup.ucr.edu/>

## ABSTRACT

We report the results of an investigation of low-frequency excess noise in high-current diamond diodes. It was found that the electronic excess noise of the diamond diodes is dominated by the  $1/f$  and generation-recombination noise, which reveals itself as Lorentzian spectral features ( $f$  is the frequency). The generation-recombination bulges are characteristic of diamond diodes with lower turn-on voltages. The noise spectral density dependence on forward current,  $I$ , reveals three distinctive regions in all examined devices—it scales as  $I^2$  at the low ( $I < 10 \mu\text{A}$ ) and high ( $I > 10 \text{mA}$ ) currents and, rather unusually, remains nearly constant at the intermediate current range. The characteristic trap time constants, extracted from the noise data, show a uniquely strong dependence on current. Interestingly, the performance of the diamond diodes improves with the increasing temperature. The obtained results are important for the development of noise spectroscopy-based approaches for device reliability assessment for high-power diamond electronics.

Published under an exclusive license by AIP Publishing. <https://doi.org/10.1063/5.0083383>

Ultra-wide bandgap (UWBG) semiconductors have emerged as important materials for power converters to meet increasing efficiency needs.<sup>1–6</sup> Diamond is a promising UWBG material in terms of its critical electric field, drift velocity, carrier mobility, and thermal conductivity.<sup>7–13</sup> However, diamond chemical vapor deposition growth, processing, and doping are still in the early stages of development. Diamond technology is not as mature as that of GaN or SiC. Rather large concentrations of defects, including trap levels within the bandgap, can detrimentally affect diamond diode operation, e.g., by an increase in the diode turn-on voltage.<sup>8,14–18</sup> Typical traps in diamonds have energy levels ranging from 0.2 to 1.7 eV. In the  $n$ -layer of the diode, the phosphorus dopant activation energy level is 0.43 to 0.63 eV (Refs. 19 and 20) while in the  $p$ -layer the boron dopant activation energy level is  $\sim 0.3$  eV.<sup>19</sup> Due to the high activation energies, only a small fraction of the dopant atoms is ionized. The defects and impurities, acting as charge carrier traps, negatively affect the reliability of the diodes, which is one of the most important metrics for applications in power converters for electricity grids. These considerations explain the need for developing innovative techniques for assessing the material quality and reliability of diamond diodes.

Low-frequency electronic noise, also referred to as excess noise, has been used in characterizing reliability-limiting defects and impurities in electronic materials and devices.<sup>21–25</sup> The excess noise includes the  $1/f$  and generation-recombination (G-R) noise with a Lorentzian type spectrum, which adds to the thermal and shot noise background ( $f$  is the frequency). It is known that  $1/f$  noise can be an early indicator of electromigration damage and provide insight into the nature and energy distributions of reliability-limiting defects in the as-processed and aged materials and devices.<sup>21,26–29</sup> The excess noise often originates in the non-ideal components or the non-ideal currents of a device. These include leakage current, defects in the material, or parasitic resistances. The noise level increases at a much faster rate than the DC parameters as a device degrades under stress or as a result of its aging.<sup>30</sup> For this reason, noise can be used as a sensitive predictor of a lifetime. The rate of increase in the noise level can be related to the device mean-time-to-failure (MTTF). Since only short-time noise measurements are needed, the procedure for determining MTTF is nondestructive. To develop noise-based reliability assessment techniques for diamond diodes, one needs to conduct thorough studies of excess noise for this specific device type. The currently available data

on noise in diamond devices are limited, with only a few published reports.<sup>31,32</sup>

In this Letter, we report the results of the investigation of excess noise in diamond diodes designed specifically for applications as high-current switches. The main objective of the study is to provide the noise-level baseline required for the development of reliability assessment. The diamond diodes were grown on a  $\langle 111 \rangle$  highly boron-doped ( $\sim 2 \times 10^{20} \text{ cm}^{-3}$ ) single crystal diamond plate ( $3 \times 3 \times 0.3 \text{ mm}^3$ ; TISNCM).<sup>33</sup> A  $\sim 0.2 \mu\text{m}$  i-layer was grown on top of the B doped  $p^{++}$  substrate using a plasma-enhanced chemical vapor deposition (PECVD) with a mixture of  $\text{H}_2:\text{CH}_4:\text{O}_2$  under a chamber pressure of 63 Torr and at 1000 W of microwave power. A  $\sim 0.15 \mu\text{m}$  moderately phosphorus-doped ( $\sim 10^{18} \text{ cm}^{-3}$ ) n-layer was grown on top of the i-layer using an  $\text{H}_2:\text{CH}_4:\text{TMP}$  mixture under 60 Torr pressure and 2000 W microwave power in the PECVD chamber. A  $\sim 0.1 \mu\text{m}$  near-metallic highly conductive nitrogen-doped nano-carbon (nanoC) layer was grown on top of the n-layer to lower the contact resistance of the cathode contact. Additional growth details can be found in Ref. 34. The active area of the diodes was defined by partial mesa etching the diamond into the i-layer using a  $\text{SiO}_2$  hard mask and  $\text{O}_2/\text{SF}_6$  chemistry in a reactive ion etcher. The top cathode and bottom anode contacts were defined by UV photolithography and e-beam deposition of a Ti-Ni-Au metal stack with 50 nm–50 nm–300 nm thicknesses. The layered structure of the devices and band diagram are shown in Figs. 1(a) and 1(b).

Although the nanoC layer provides a reduced contact resistance at the circular cathode contact, a Schottky barrier to electrons exists due to the Fermi-level pinning at the nanoC-n-layer interface. The Schottky barrier at the cathode contact can be seen from the band diagram generated from Silvaco ATLAS simulations using the diode structure [see Figs. 1(a) and 1(b)]. The diode current is, therefore, largely dominated by the holes injected over the  $p^{++}$ -i-n junction barrier. The hole injection initially follows thermionic emission (TE) regime where the current is exponentially dependent on the small forward bias voltage and, then, transitions into a space charge limited conduction (SCLC) where the current is proportional to  $V^m$ , where  $m$  is  $\geq 2$  depending on the trap energy levels and trap density in the diode.<sup>8,35</sup>

The current–voltage ( $I$ - $V$ ) and low-frequency noise characteristics for all diodes were measured in a vacuum (Agilent; Lake Shore). The noise spectra were acquired with a dynamic signal analyzer (Stanford Research). Detail of our noise measurements procedures, in

the context of other material systems, has been reported by some of us elsewhere.<sup>36–38</sup> Figures 2(a) and 2(b) show the  $I$ - $V$  characteristics in linear and logarithmic scales, respectively. From the  $I$ - $V$  characteristics, the tested diodes can be separated into two groups based on the respective turn-on voltage,  $V_T$ , of each diode. Devices 1–3 have lower turn-on voltages, close to 5 V as compared to devices 4–6 that have turn-on voltages of  $\sim 10$  V or higher. The deviations from the ideal characteristics of these diodes and current jumps indicate the material imperfections owing to the infancy of the diamond diode growth and processing technology.

The noise measurements were conducted for all devices to examine variations in the noise characteristics for diodes with different turn-on voltages. In Fig. 2(c), we present the noise current spectral density,  $S_I$ , as a function of frequency for device 2 ( $V_T \sim 5$  V) for different currents through the diode. The noise spectra at all currents are the superposition of the  $1/f$  and G-R noise with the pronounced Lorentzian spectral features. Similar noise spectra were measured for devices 1 and 3 with the low turn-on voltage. The noise spectral density,  $S_I$ , as a function of frequency for device 6 with the highest turn-on voltage is presented in Fig. 2(d). Interestingly, in this and other high turn-on voltage diodes, the noise is predominantly of the  $1/f$ -type. Some signatures of the deviation from  $1/f$  spectrum and contribution of the G-R noise appear only at higher frequency ( $f \sim 10$  kHz). These noise characteristics were similar for all diodes with high turn-on voltages. The diamond diodes with the larger turn-on voltages are typically those that have a higher concentration of defects.<sup>8</sup> One may consider it unusual that the devices with more defects have  $1/f$  spectrum while those with fewer defects show G-R spectral features. Below we explain it by the specifics of the noise mechanisms in diodes as compared to linear resistors or field-effect transistors (FETs).

Figure 3(a) shows the noise current spectral density,  $S_I$ , as a function of the current density,  $J$ , at a fixed frequency  $f = 10$  Hz for all six tested devices. The  $S_I$  vs  $J$  ( $S_I$  vs  $I$ ) relation for the measured diamond diodes follows the  $S_I \sim J^2$  ( $S_I \sim I^2$ ) trend at low currents. Although the dependence  $S_I \sim I$  can be considered as a typical one for forward-biased diodes,  $S_I \sim I^2$  dependences were also reported in  $p$ - $n$  junction and Schottky diodes, including those based on wide bandgap semiconductors.<sup>39</sup> The  $S_I(J)$  dependence becomes almost flat in the intermediate current density range, i.e., from about  $J \sim 0.1$  to  $100 \text{ A/cm}^2$ . The  $S_I \sim J^2$  noise behavior is restored at higher currents. It is interesting to note that the transition to the flat  $S_I(J)$  dependence at the intermediate


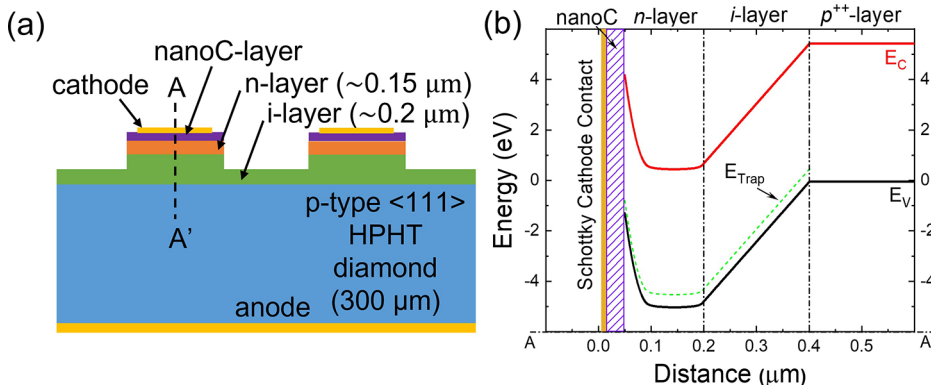


FIG. 1. (a) Schematic of the layered structure of diamond diodes. (b) The band diagram at zero bias of a diamond diode including the trap levels as simulated by Silvaco ATLAS.

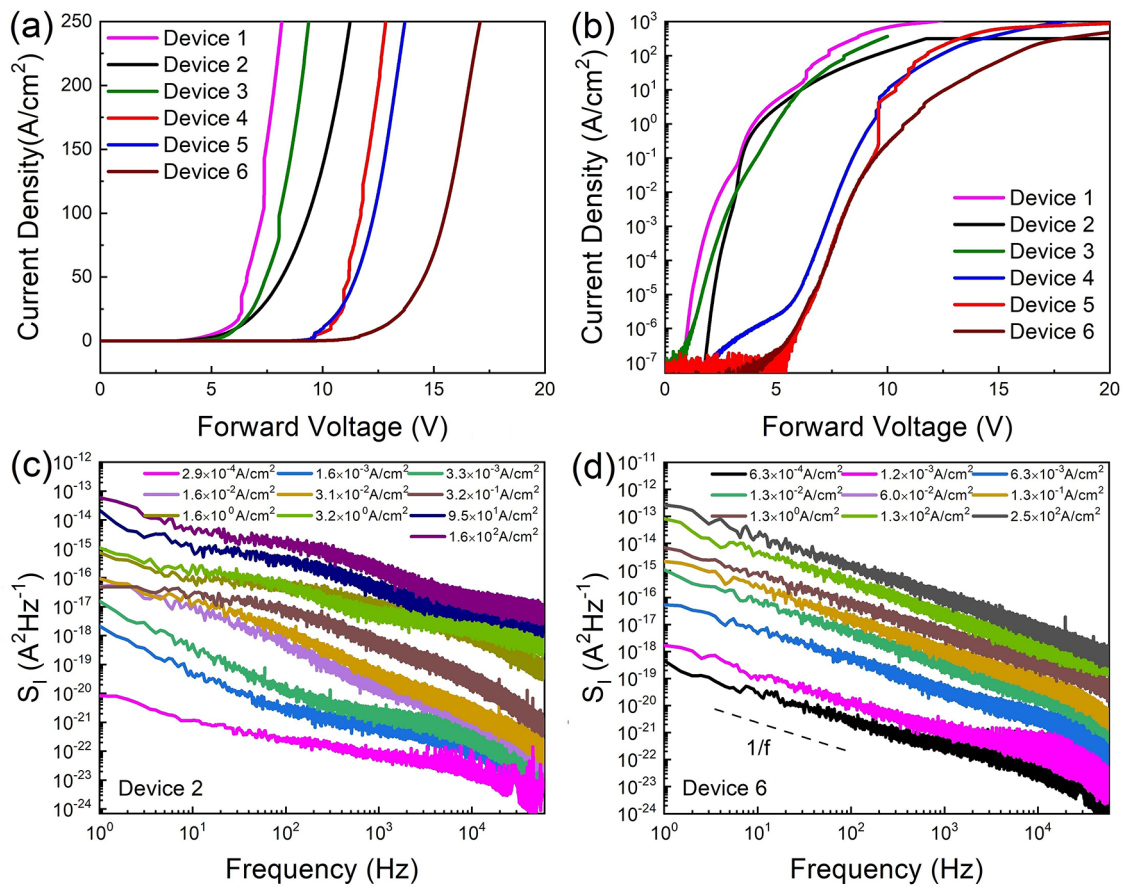


**FIG. 2.** Current–voltage characteristics of six different diamond diodes plotted in linear (a) and logarithmic (b) scales. The diodes can be grouped as those with lower ( $V_T \sim 5$  V) and higher ( $V_T \sim 10$  V) turn-on voltages. (c) Noise current spectral density,  $S_I$ , as a function of frequency for different current densities,  $J$ , for device 2, with the low turn-on voltage. (d) Noise current spectral density,  $S_I$ , as a function of frequency for different current densities,  $J$ , for a device 6, with the high turn-on voltage.

current levels roughly corresponds to the transition from the TE to SCLC hole transport regimes. In previous studies, the non-monotonic trends in the noise spectral density of GaN diodes were interpreted as the interplay of contributions to noise from the diode base,  $p$ - $n$  junction region, and the series resistances associated with the contacts.<sup>40</sup> A quantitative description for a non-monotonic trend was developed for SiC diodes.<sup>41</sup>

To compare the noise characteristics of diamond diodes with those made of other material systems, we present the noise spectral density normalized by the current and device area in Fig. 3(b). For all measured diamond diodes, the normalized noise spectral density,  $S_I/I^2 \times \Omega$ , measured at fixed  $f = 10$  Hz, decreases with the increasing current density,  $J$  ( $\Omega$  is the area of the top cathode contact). The decrease becomes slow or saturates completely at high current densities when the contributions from series resistances start to dominate the noise response. A comparison of the noise spectral density normalized to the area indicates a substantially higher noise level in diamond than that in GaN diodes.<sup>25</sup> Additional comparison of the noise characteristics in different device technologies is provided in the [supplementary material](#). The  $I$ - $V$  and noise characteristics of the diamond diodes

at elevated temperatures are shown in Figs. 3(c) and 3(d). One can see that both current and noise are weak functions of temperature, which are beneficial for high-power switching applications. Despite the high thermal conductivity of diamond, the high-current diodes can still experience substantial Joule heating at the considered power levels.<sup>8,42,43</sup> The thermal interface resistances between the layers increase the overall thermal resistance of the device structure.<sup>44</sup> The dashed lines in Fig. 3(c) show the slope of the exponential part of  $I$ - $V$  characteristics, e.g.,  $I \sim \exp(V/\eta KT)$ , at low currents. The ideality factor,  $\eta$ , decreases with the temperature increase. The decrease in the ideality factor together with almost constant noise level with temperature indicates that the performance of the diamond diodes can be improved with the increasing temperature. The latter is an extra benefit for applications of diamond diodes as high-power switches.

We now turn to a more detailed analysis of the G-R bulges observed in the spectra of the low turn-on voltage devices. Figures 4(a) and 4(b) show the noise spectra of device 1 for  $J = 1.3$  A/cm<sup>2</sup> and  $J = 1.3 \times 10^{-3}$  A/cm<sup>2</sup>, respectively. One can see an overlap of two Lorentzians at the intermediate current levels [panel (a)], and just one pronounced Lorentzian superimposed over  $1/f$  shape at the small

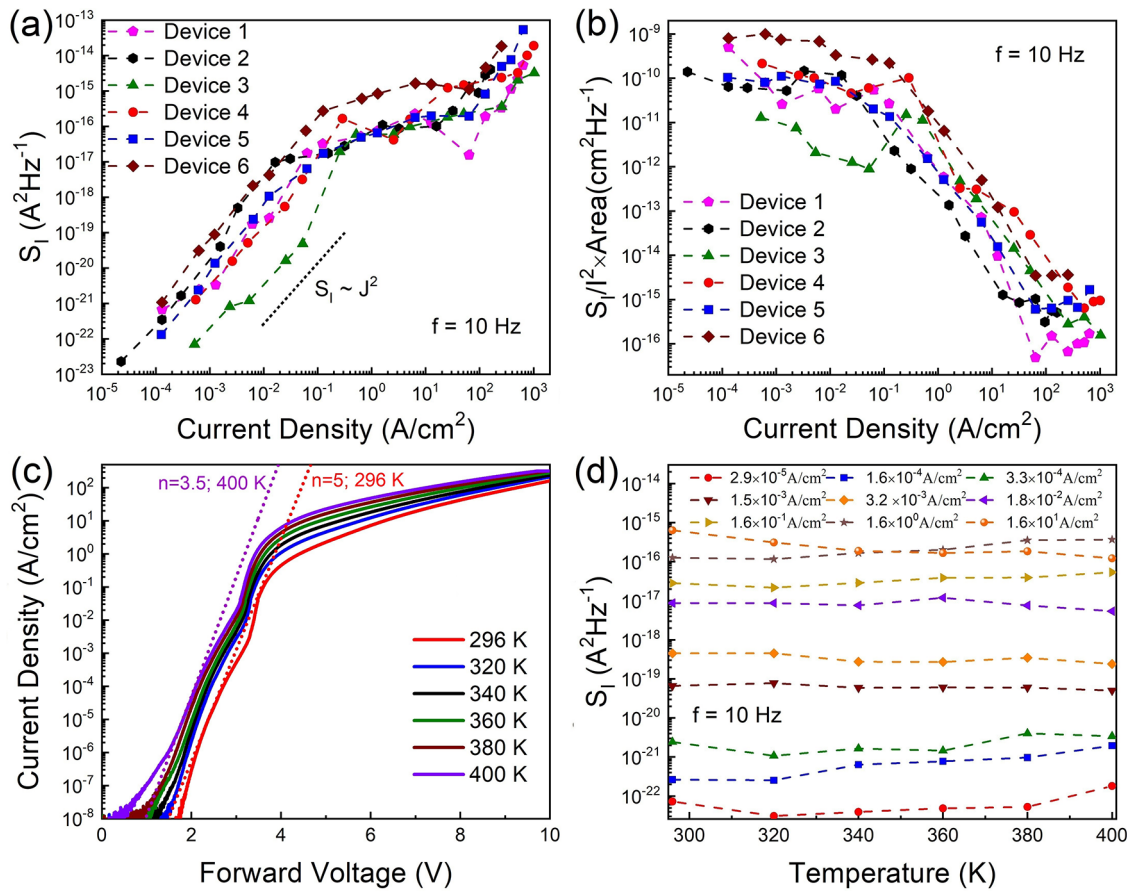


**FIG. 3.** (a) Noise current spectral density,  $S_I$ , as a function of the current density,  $J$ , at  $f = 10$  Hz for all devices, measured at room temperature. (b) The normalized noise current spectral density,  $S_I/f^2 \times \Omega$ , as a function of  $J$  at  $f = 10$  Hz. (c) Current–voltage characteristics of a diamond diode (device 2) at elevated temperatures. (d) The noise spectral density,  $S_I$ , at  $f = 10$  Hz, as a function of temperature, measured for different current densities.

current level [panel (b)]. The Lorentzians are shifting with the changing current level and can go beyond the measurable range. We used fitting with Lorentzians to determine the corner frequency of the G-R noise. The G-R noise spectral density is described by the Lorentzians using an expression  $S_I(f) = S_0/[1 + (2\pi f\tau)^2]$ , where  $S_0$  is the frequency-independent portion of  $S_I(f)$  observed at  $f \ll (2\pi\tau)^{-1}$  and  $\tau$  is the time constant associated with a particular fluctuation process. Figures 4(c) and 4(d) show the characteristic frequency  $f_c = (1/2\pi\tau)$  as a function of  $J$  for diamond diodes 1 and 2, respectively. The general trend for  $f_c$  is to increase with  $J$ . The functional dependence can be approximated as  $f_c \sim J^\beta$ , where  $\beta$  takes the values 0.31 and 1.15 for device 1, 1.39 for device 2, and 1.35 for device 3 (see the supplementary material). The dependence of  $f_c$  on current in the diodes can be explained by the dependence of the trap capture time  $\tau_{\text{cap}} = (n\nu\sigma)^{-1}$  on the carriers concentration,  $n$  (where  $\nu$  is the charge carrier thermal velocity and  $\sigma$  is the capture cross section).<sup>45</sup> The current increase leads to the increase in the concentration,  $n$ , and corresponding increase in the corner frequency,  $f_c = (1/2\pi\tau)$ . This is true if the time constant  $\tau$  is dominated by capture rather than emission time. Since our diamond diodes are characterized by the deeper, not fully ionized donor and

acceptor states, high trap concentration, and the hole-dominated charge transport, the obtained  $f_c(J)$  relations for the diamond diodes are substantially different from those reported for GaN diodes.<sup>45</sup> It is interesting to note that characteristic frequencies for some Lorentzian, e.g., red line in Fig. 4(c), coincide with the current jumps in  $I$ - $V$  characteristics—see the current jump at 3.3 V in Fig. 2(a). This adds support to the model, which correlates current jumps in the  $I$ - $V$ s with the traps in the energy bandgap.<sup>8</sup>

The G-R noise mechanisms in diodes are different from the G-R and  $1/f$  noise mechanisms in bulk semiconductors and FETs.<sup>26,46</sup> In the McWhorter model for FETs, the  $1/f$  noise emerges as an overlap of Lorentzian bulges due to traps with different time constants. The time constant,  $\tau$ , of the trap is determined by its distance from the conduction channel, e.g.,  $\tau = \tau_0 \exp(\lambda z)$ , where  $z$  is the distance of the trap from the channel,  $\tau_0 \sim 10^{-10}$  s and  $\lambda$  is the tunneling parameter. In bulk semiconductors, one needs several levels or a continuous band of trap levels with different capture cross sections, like the density of state tails near conduction and valence band edges, to construct the  $1/f$  noise spectrum.<sup>47</sup> The situation in diodes is different. One of the conventional models for the low-frequency noise in a diode assumes that

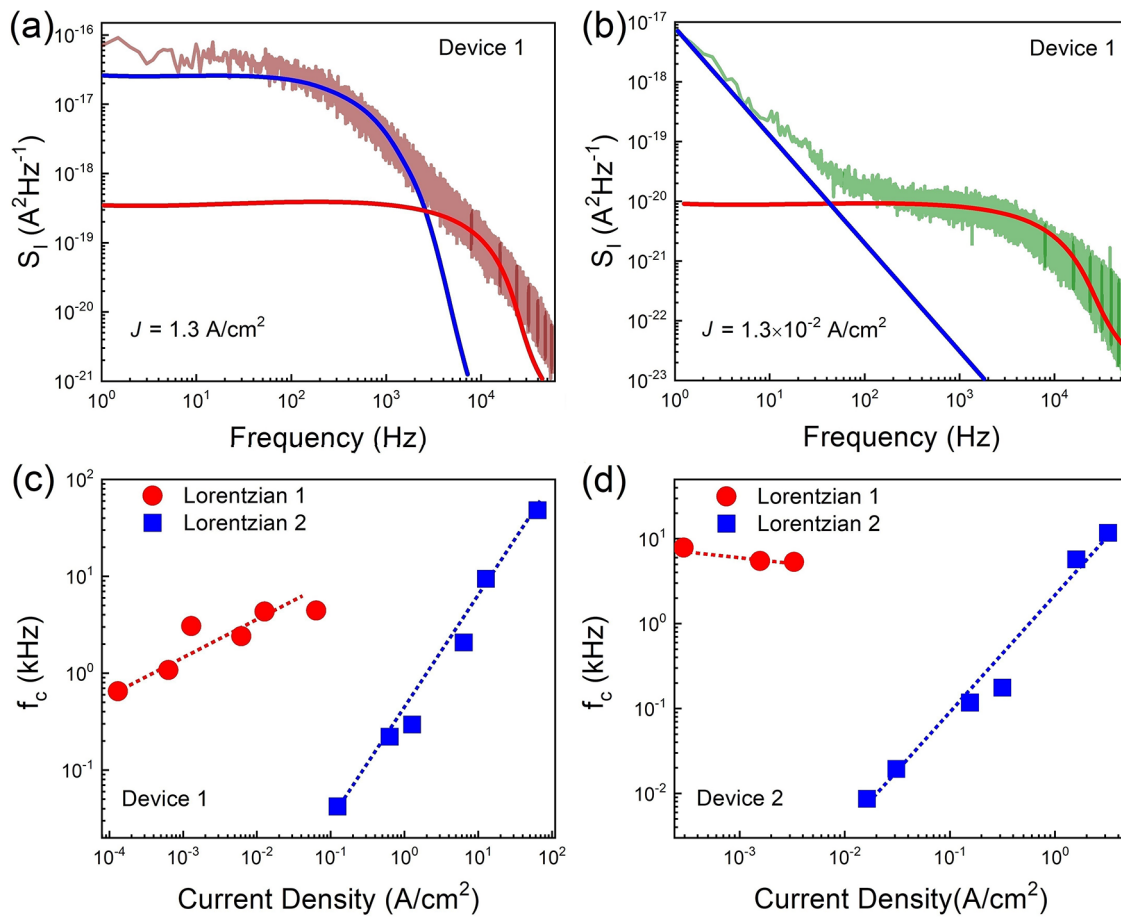

**FIG. 4.** (a) Current noise spectral density,  $S_i$ , as a function of frequency at an intermediate current density,  $J = 1.3 A/cm^2$ , for a device 1 with the low turn-on voltage. (b) The current noise spectral density,  $S_i$ , as a function of frequency at a low current density,  $J = 1.3 \times 10^{-2} A/cm^2$ , for the same device. Dependence of the corner frequency of the G-R bulges on the current density shown for (c) device 1 and (d) device 2.

the emission and capture of carriers by the recombination level lead to the fluctuations of the charge state of this trap, and, as a result, to the fluctuations of the electric field distribution in the space charge region with the corresponding current fluctuations.<sup>48</sup> This model has been refined to correlate the current fluctuations with the fluctuations of the electric field not in the entire space-charge region but rather in a small vicinity of a trap in a specific location in the p-n junction region.<sup>41</sup> The local fluctuations of the electric field are caused by the fluctuations of the charge state of the trap due to the exchange of electrons between this trap and the conduction band. Within this model, the same type of trap can give different time constants depending on its position in the diode structure since its energy level with respect to the Fermi energy is a strong function of the coordinate along the diode structure [see Fig. 1(b)]. This can explain the evolution of G-R noise spectra to  $1/f$  noise, and observed differences in the noise for the same type of devices that have low and high turn-on voltages [see Figs. 2(c) and 2(d)]. The diodes with the high turn-on voltage, which typically have more traps, have sufficient variation in the time constant, integrated over the junction length, to smooth out the G-R bulges to the  $1/f$  envelope.

The noise in diamond diodes shows variations not only for the devices with different turn-on voltage but also for low-current, intermediate-current, and high-current regimes [e.g., see Figs. 2(c) and 2(d)]. In our case, the current regimes roughly correspond to TE, SCLC, and series resistance limited currents. In conventional diodes, the TE and SCLC regimes can be replaced with recombination and diffusive transport, respectively. The noise data for each regime have important implications for device reliability assessment.<sup>49</sup> The low-frequency noise measured at low bias is sensitive to the degradation of the active region.<sup>23,50</sup> At high bias, the measured noise reflects the degradation of the metal contacts and semiconductor layers contributing to the series resistance. Our data demonstrate that the difference in the noise level for different diodes is large at all currents [see Fig. 3(b)]. The variations in the noise level are at their maximum, and span about three orders of magnitude, at the low currents. Interestingly, the smallest noise level was observed for the devices with the low turn-on voltage and the highest noise was recorded for the devices with the high turn-on voltage. These observations attest to the potential of the noise spectroscopy for diamond diode reliability assessment.

In conclusion, we reported the results of the investigation of excess noise in high-current diamond diodes. In high turn-on voltage diodes, the  $1/f$  noise dominated, which can be attributed to the higher concentration of traps responsible for noise in these diodes. The G-R noise was found to be characteristic of diamond diodes with lower turn-on voltages. The dependences of noise spectral density,  $S_B$ , on forward current show different slopes, which can be correlated with different transport regimes in the diodes. The characteristic time constants, extracted from the G-R noise data, reveal uniquely strong dependence on current, attributed to the specifics of the charge transport and recombination processes in our diamond diodes. The obtained results are important for developing the noise spectroscopy-based approaches for the device reliability assessment for high-power diamond electronics.

See the [supplementary material](#) for additional excess noise data and analysis.

The work at UCR and ASU was supported by ULTRA, an Energy Frontier Research Center (EFRC) funded by the U.S. Department of Energy, Office of Science, Basic Energy Sciences under Award No. DE-SC0021230. S.R. who contributed to noise data analysis acknowledges the support by CENTERA Laboratories in a frame of the International Research Agendas program for the Foundation for Polish Sciences co-financed by the European Union under the European Regional Development Fund (No. MAB/2018/9).

## AUTHOR DECLARATIONS

### Conflict of Interest

The authors declare no conflict of interest.

### Author Contributions

A.A.B. coordinated the project, lead data analysis, and manuscript preparation. S.G. measured current-voltage and low-frequency noise characteristics. H.S. fabricated diamond diodes. F.A.K. contributed to device fabrication. R.N. supervised device fabrication. S.R., F.K., S.G., and R.N. contributed to the current-voltage and electronic noise data analysis. All authors contributed to manuscript preparation.

### DATA AVAILABILITY

The data that support the findings of this study are available from the corresponding author upon reasonable request.

## REFERENCES

- S. Choi, S. Graham, S. Chowdhury, E. R. Heller, M. J. Tadjer, G. Moreno, and S. Narumanchi, *Appl. Phys. Lett.* **119**, 170501 (2021).
- Z. Liang, H. Du, Y. Yuan, Q. Wang, J. Kang, H. Zhou, J. Zhang, Y. Hao, X. Wang, and G. Zhang, *Appl. Phys. Lett.* **119**, 252101 (2021).
- M. Higashiwaki, R. Kaplar, J. Pernot, and H. Zhao, *Appl. Phys. Lett.* **118**, 200401 (2021).
- T. Matsumoto, T. Yamakawa, H. Kato, T. Makino, M. Ogura, X. Zhang, T. Inokuma, S. Yamasaki, and N. Tokuda, *Appl. Phys. Lett.* **119**, 242105 (2021).
- M. Wohlfahrt, M. J. Uren, Y. Yin, K. B. Lee, and M. Kuball, *Appl. Phys. Lett.* **119**, 243502 (2021).
- S. Lu, M. Deki, J. Wang, K. Ohnishi, Y. Ando, T. Kumabe, H. Watanabe, S. Nitta, Y. Honda, and H. Amano, *Appl. Phys. Lett.* **119**, 242104 (2021).
- N. Donato, N. Rouger, J. Pernot, G. Longobardi, and F. Udrea, *J. Phys. D: Appl. Phys.* **53**, 093001 (2020).
- H. Surdi, F. A. M. Koeck, M. F. Ahmad, T. J. Thornton, R. J. Nemanich, and S. M. Goodnick, *IEEE Trans. Electron Devices* **69**, 254 (2022).
- V. Jha, H. Surdi, M. Faizan Ahmad, F. Koeck, R. J. Nemanich, S. Goodnick, and T. J. Thornton, *Solid-State Electron.* **186**, 108154 (2021).
- Y. Sasama, T. Kageura, K. Komatsu, S. Moriyama, J. I. Inoue, M. Imura, K. Watanabe, T. Taniguchi, T. Uchihashi, and Y. Takahide, *J. Appl. Phys.* **127**, 185707 (2020).
- D. Das, A. Kandasami, and M. S. Ramachandra Rao, *Appl. Phys. Lett.* **118**, 102102 (2021).
- Y. Sasama, K. Komatsu, S. Moriyama, M. Imura, T. Teraji, K. Watanabe, T. Taniguchi, T. Uchihashi, and Y. Takahide, *APL Mater.* **6**, 111105 (2018).
- R. Nelz, J. Görlitz, D. Herrmann, A. Slablab, M. Challier, M. Radtke, M. Fischer, S. Gsell, M. Schreck, C. Becher, and E. Neu, *APL Mater.* **7**, 011108 (2019).
- D. Araujo, F. Lloret, G. Alba, M. P. Alegre, and M. P. Villar, *Appl. Phys. Lett.* **118**, 052108 (2021).
- T. Murooka, M. Shiigai, Y. Hironaka, T. Tsuji, B. Yang, T. M. Hoang, K. Suda, K. Mizuno, H. Kato, T. Makino, M. Ogura, S. Yamasaki, M. Hatano, and T. Iwasaki, *Appl. Phys. Lett.* **118**, 253502 (2021).
- T. Hanada, S. Ohmagari, J. H. Kaneko, and H. Umezawa, *Appl. Phys. Lett.* **117**, 262107 (2020).
- R. E. Lake, A. Persaud, C. Christian, E. S. Barnard, E. M. Chan, A. A. Bettiol, M. Tomut, C. Trautmann, and T. Schenkel, *Appl. Phys. Lett.* **118**, 084002 (2021).
- P. Muret, J. Pernot, A. Kumar, L. Magaud, C. Mer-Calfati, and P. Bergonzo, *Phys. Rev. B* **81**, 235205 (2010).
- I. Stenger, M. A. Pinault-Thaury, T. Kociniwski, A. Lusson, E. Chikoidze, F. Jomard, Y. Dumont, J. Chevallier, and J. Barjon, *J. Appl. Phys.* **114**, 073711 (2013).
- J. Y. Tsao, S. Chowdhury, M. A. Hollis, D. Jena, N. M. Johnson, K. A. Jones, R. J. Kaplar, S. Rajan, C. G. van de Walle, E. Bellotti, C. L. Chua, R. Collazo, M. E. Coltrin, J. A. Cooper, K. R. Evans, S. Graham, T. A. Grotjohn, E. R. Heller, M. Higashiwaki, M. S. Islam, P. W. Juodawlkis, M. A. Khan, A. D. Koehler, J. H. Leach, U. K. Mishra, R. J. Nemanich, R. C. N. Pilawa-Podgurski, J. B. Shealy, Z. Sitar, M. J. Tadjer, A. F. Witulski, M. Wraback, and J. A. Simmons, *Adv. Electron. Mater.* **4**, 1600501 (2018).
- L. K. J. Vandamme, *IEEE Trans. Electron Devices* **41**, 2176 (1994).
- Y. Dai, *Microelectron. Reliab.* **31**, 75 (1991).
- X. Y. Chen, A. Pedersen, and A. D. van Rheenen, *Microelectron. Reliab.* **41**, 105 (2001).
- D. M. Fleetwood, S. Beyne, R. Jiang, S. E. Zhao, P. Wang, S. Bonaldo, M. W. McCurdy, Z. Tokei, I. Dewolf, K. Croes, E. X. Zhang, M. L. Alles, R. D. Schrimpf, R. A. Reed, and D. Linten, *Appl. Phys. Lett.* **114**, 203501 (2019).
- S. Ghosh, K. Fu, F. Kargar, S. Rumyantsev, Y. Zhao, and A. A. Balandin, *Appl. Phys. Lett.* **119**, 243505 (2021).
- A. A. Balandin, *Noise and Fluctuations Control* (American Scientific Publishers, 2002), Vol. 258.
- A. Szewczyk, Ł. Gawel, K. Darowicki, and J. Smulko, *Energies* **14**, 8340 (2021).
- Z. Gingl, C. Pennetta, L. B. Kiss, and L. Reggiani, *Semicond. Sci. Technol.* **11**, 1770 (1996).
- J. Xu, D. Abbott, and Y. Dai, *Microelectron. Reliab.* **40**, 171 (2000).
- B. K. Jones, *IEE Proc.* **149**, 13 (2002).
- M. V. Hauf, L. H. Hess, J. Howgate, M. Dankerl, M. Stutzmann, and J. A. Garrido, *Appl. Phys. Lett.* **97**, 093504 (2010).
- J. Wu, T. Tshepe, J. E. Butler, and M. J. R. Hoch, *Phys. Rev. B* **71**, 113108 (2005).
- V. S. Bormashov, S. A. Tarelkin, S. G. Buga, M. S. Kuznetsov, S. A. Terentiev, A. N. Semenov, and V. D. Blank, *Diamond Related Mater.* **35**, 19 (2013).
- F. A. Koeck, M. Benipal, and R. J. Nemanich, *Diamond Related Mater.* **101**, 107607 (2020).
- P. Mark and W. Helfrich, *J. Appl. Phys.* **33**, 205 (1962).
- S. Ghosh, F. Kargar, A. Mohammadzadeh, S. Rumyantsev, and A. A. Balandin, *Adv. Electron. Mater.* **7**, 2100408 (2021).
- A. Mohammadzadeh, A. Rehman, F. Kargar, S. Rumyantsev, J. M. Smulko, W. Knap, R. K. Lake, and A. A. Balandin, *Appl. Phys. Lett.* **118**, 223101 (2021).
- A. Geremew, C. Qian, A. Abelson, S. Rumyantsev, F. Kargar, M. Law, and A. A. Balandin, *Nanoscale* **11**, 20171 (2019).
- L. Dobrzanski and W. Strupinski, *IEEE J. Quantum Electron.* **43**, 188 (2007).

- <sup>40</sup>G. Cywiński, K. Szkudlarek, P. Kruszewski, I. Yahniuk, S. Yatsunenko, G. Muzioł, C. Skierbiszewski, W. Knap, and S. L. Rumyantsev, *Appl. Phys. Lett.* **109**, 033502 (2016).
- <sup>41</sup>S. L. Rumyantsev, A. P. Dmitriev, M. E. Levinshtein, D. Veksler, M. S. Shur, J. W. Palmour, M. K. Das, and B. A. Hull, *J. Appl. Phys.* **100**, 064505 (2006).
- <sup>42</sup>J. S. Lundh, D. Shoemaker, A. G. Birdwell, J. D. Weil, L. M. de La Cruz, P. B. Shah, K. G. Crawford, T. G. Ivanov, H. Y. Wong, and S. Choi, *Appl. Phys. Lett.* **119**, 143502 (2021).
- <sup>43</sup>V. D. Blank, V. S. Bormashov, S. A. Tarelkin, S. G. Buga, M. S. Kuznetsov, D. V. Teteruk, N. V. Kornilov, S. A. Terentiev, and A. P. Volkov, *Diamond Related Mater.* **57**, 32 (2015).
- <sup>44</sup>V. Turin and A. A. Balandin, *Electron. Lett.* **40**, 81 (2004).
- <sup>45</sup>S. Sawyer, S. L. Rumyantsev, M. S. Shur, N. Pala, Y. Bilenko, J. P. Zhang, X. Hu, A. Lunev, J. Deng, and R. Gaska, *J. Appl. Phys.* **100**, 034504 (2006).
- <sup>46</sup>A. L. McWhorter and R. H. Kingston, *Semiconductor Surface Physics* (University of Pennsylvania Press, 1957).
- <sup>47</sup>N. V. D'yakonova, M. E. Levinshtein, and S. L. Rumyantsev, *Sov. Phys. Semicond.* **25**, 1241 (1991).
- <sup>48</sup>J. A. Jiménez Tejada, A. Godoy, A. Palma, and P. Cartujo, *J. Appl. Phys.* **90**, 3998 (2001).
- <sup>49</sup>S. Sawyer, S. L. Rumyantsev, and M. S. Shur, *Solid-State Electron.* **52**, 968 (2008).
- <sup>50</sup>S. Bychikhin, D. Pogany, L. K. J. Vandamme, G. Meneghesso, and E. Zanoni, *J. Appl. Phys.* **97**, 123714 (2005).