

Conf. 930676 -- 59

UCRL-JC-113299
PREPRINT

High Pressure Hugoniot of Sapphire


David Erskine

RECEIVED
OCT 14 1993
OSTI

This paper was prepared for submittal to the
Proceedings of the Joint AIRAPT/APS Conference
Colorado Springs, CO
June 28-July 2, 1993

July 1993

This is a preprint of a paper intended for publication in a journal or proceedings. Since changes may be made before publication, this preprint is made available with the understanding that it will not be cited or reproduced without the permission of the author.

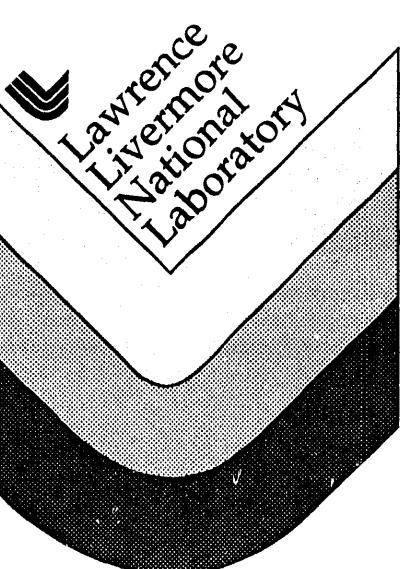

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

DISCLAIMER

This document was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor the University of California nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial products, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or the University of California, and shall not be used for advertising or product endorsement purposes.

HIGH PRESSURE HUGONIOT OF SAPPHIRE

Dave Erskine

Lawrence Livermore National Laboratory, PO Box 808 L-299, Livermore, CA 94550

The Hugoniot of sapphire was measured for the first time above 145 GPa, from 80 GPa to 340 GPa in shock-wave experiments using projectiles accelerated by a two stage gas gun. The transit times of the shock waves were measured either optically with a streak camera or through electrical pin contacts. The Hugoniot in this pressure range fits $U_s = 8.74 + 0.96 U_p$ in km/s.

INTRODUCTION

Sapphire is a technologically important material frequently used in high pressure physics. In the form of ruby (Cr-doped sapphire) it indicates pressure in a diamond anvil cell through the pressure shift of its fluorescence. However, at megabar pressures the fluorescent lineshape changes, making its interpretation increasingly difficult¹. A first-principles calculation of the optical properties of ruby requires its high pressure equation of state (EOS).

In shock-wave physics, sapphire is an important window material because it has a high density (4.0 g/cm³) relative to other window materials such as LiF (2.64 g/cm³). This produces higher shock pressures upon impact. Also, its density can be a better impedance match to some samples, minimizing undesired reflected waves. Often in these applications an EOS accurate at multi-megabar pressures is needed. Previously the Hugoniot (shock EOS) of sapphire had not been measured² beyond 145 GPa. We have measured the Hugoniot from 80 to 340 GPa in two stage gas gun experiments using optical and electrical pin contact methods.

METHOD

The Hugoniot was determined by measuring the speed of a shock through sapphire created by impact of a disk projectile. The projectile density, Hugoniot and velocity combined with the sapphire shock speed (U_s) using elementary shock relations^{3,4} yields the sapphire mass velocity (U_p). The locus of U_s - U_p data constitutes the Hugoniot.

The sample was high quality sapphire of [0001] orientation obtained from either Union Carbide Co. or Crystal Systems Co.⁵ Its density averaged $\rho = 3.989$ g/cm³. Except for a shot using Pt, the projectile was a Ta disk, 1 - 2 mm thick and 24 mm diameter. The projectile was accelerated by a two

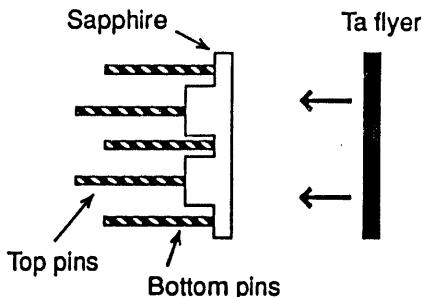


Figure 1. Target design using the electrical pin technique to measure shock speed in a sapphire "tophat". The electrical pins short when they encounter the shock-wave. Six "top" pins and six "bottom" pins encircle a center pin.

Shorting Pin Technique

Figure 1 shows the target design employing electrical shorting pins to record the shock transit time across a "top-hat" sample. The technique is described in more detail in ref. 4. The bottom and top pin circle diameters were 19.3 and 9.6 mm respectively and the step height was 1.3 mm. The tilt and bowing of the flyer at impact were determined from the distribution of pin arrival times and used in calculating the transit time of the center of the shock surface. If the center pin failed the amount of bowing could not be determined, and this amount could be significant (20 ns out of a transit time of 100 ns for high velocity shots). This critical reliance on a single pin is a disadvantage which motivated us to employ the optical technique described below.

Optical Technique

Figure 2 illustrates the target design used with an optical technique similar to that described in ref. 6, but using an indicator fluid. A sapphire (Sp) cylinder 5 mm thick and 18 mm diameter is mounted against a copper baseplate and surrounded by an indicating fluid such as bromoform or benzene. The fluid emits light when shocked. An opaque gold film covering

MASTER

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

JP

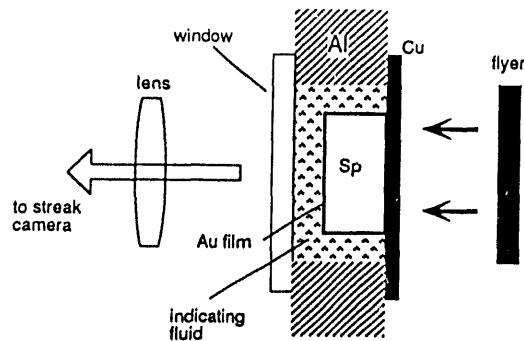


Figure 2. Target design for the streak-camera technique. The indicating fluid emits light when shocked. The lens images the sapphire (Sp) face and the Cu baseplate to the streak camera slit.

the sapphire blocks light internal to the sapphire. The Sp/Au/fluid and baseplate/fluid surfaces are imaged to the entrance slit of a streak camera. The shock emerging from the baseplate first creates light at the baseplate/fluid interface, then later at the rear of the sample.

Figure 3 shows a digitization of a streak camera record plotting first appearance of light along a line bisecting the target. Light first appears on either side of the sapphire as it breaks out of the baseplate. It appears at the rear face of the sapphire later. The tilted and bowed nature of the shock front due to the projectile distortion is clearly seen, especially in the expanded view Fig. 3b. The release wave propagating inside and from the sapphire sides slows the periphery of the shock front, forming the "bat-ears" shape.

The transit time is found by translating the shoulder points upward until they fit the same parabolic curve defined by the top points inside the bat-ears. The turn-on time of the flash was assumed to be identical for the Cu/fluid and Sp/Au/fluid interfaces. This is reasonable since the calculated pressures developed at the two surfaces are similar.

An advantage of this technique over the electrical pin method is that amount of bowing can be determined with confidence. Secondly, the sample can be approximately twice as thick while still avoiding side release waves, since there is no central hole for the center pin as in the tophat shape. The disadvantage of the technique is that amount of light produced in the flash and the proper exposure to use for the camera for a given impact velocity is not easily calculated and must be discovered empirically.

RESULTS AND DISCUSSION

The U_s - U_p data are plotted in Fig. 4 along with data of ref. 2. A linear best fit through all the data yields the relation $U_s = 8.74 + 0.957U_p$ for $80 < P < 340$ GPa. The error bars for most of our data are smaller than the datum symbols. We have not determined the source of the statistical fluctuations in the data. Since the fluctuations are much greater than our estimated measurement error it is due to either sample-to-sample variations in material properties, or an unknown source of uncertainty in our experiment.

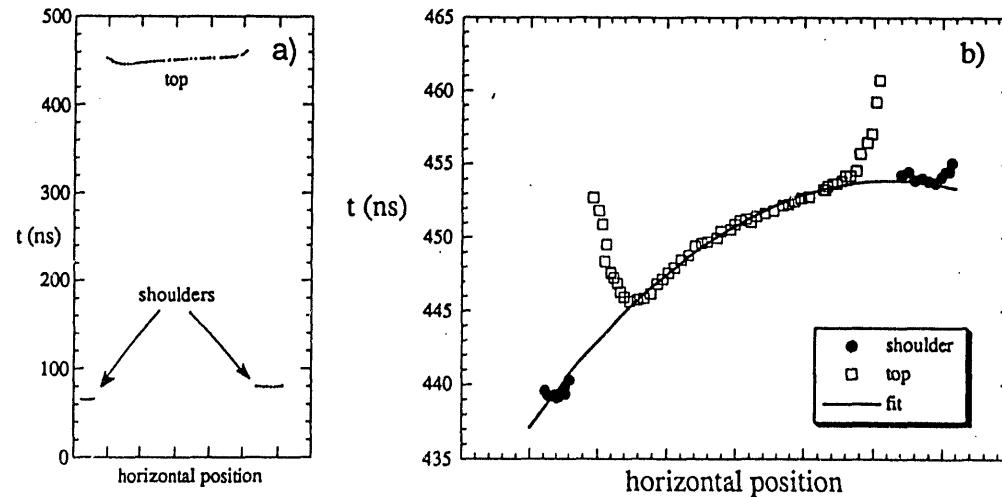


Figure 3. a) Streak camera record plotting time of breakout of shock versus horizontal position across a line bisecting the target. Breakout first occurs from baseplate (shoulders), then from the rear face of the sapphire cylinder. b) Close up of same record, with the shoulder points translated 374 ns upward. The "bat-ears" are due to the side release waves. A parabola is fitted through the top points inside the bat-ears. The bowing and tilt of the shock wave front due to the projectile distortion is clearly seen.

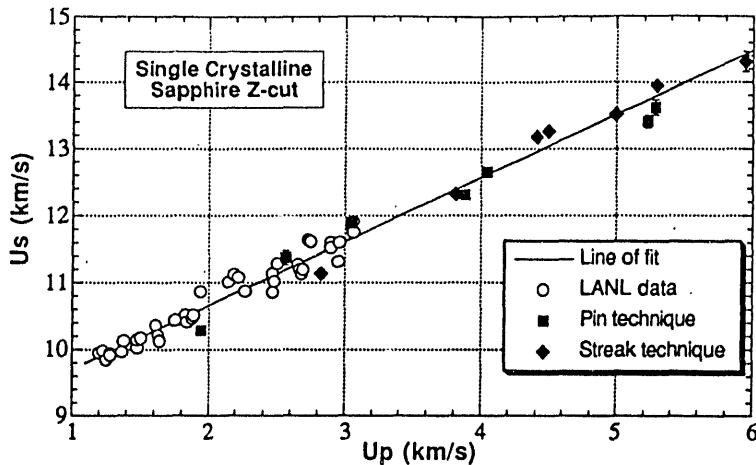


Figure 4. Experimental Hugoniot data (shock speed vs. mass velocity) from this work and ref. 2 (circles, Los Alamos Nat. Lab.). Symbols distinguish the two techniques used, diamonds: electrical pin contacts, squares: streak camera. The line of best fit through all the data is $U_s = 8.74 + 0.957 U_p$. For our data only, most error bars are smaller than the symbols.

The slope (S) of the U_s - U_p relation is less than unity. This is atypical of most materials, which have slopes² 1.2 - 1.7. We don't believe sapphire's low S value is due to its hardness, since although some hard materials⁷ have low S (diamond: 1.0, B_4C : 0.67), others don't (TaC: 1.27, WC: 1.17). In a counter-example, two soft materials having low S values are calcium ($S=0.95$) and cesium ($S=1.04$).

Materials undergoing polymorphic phase transitions under shock can have a depressed U_s which could manifest a low S for a limited range of pressures. If the transformation is rapid a two-wave profile⁸ results with the faster wavefront maintaining a constant U_s for a range of pressures. In this case the transformation nature is easy to notice. If the transformation is sluggish (producing a mixed-phase final state over a broad pressure range), a single wavefront can be produced which has a depressed U_s . This could produce a low S . For sufficiently high pressures when the shocked state is entirely of the final phase, the U_s - U_p behavior should possess a higher and more typical S value.

We are aware of no direct evidence that sapphire is undergoing a phase transition, and we have no higher pressure Hugoniot data to check whether its S value eventually increases, which would support this notion. Since there are no projectile materials significantly denser than Pt, our 340 GPa datum is the highest we can attain in a direct shock with our gas gun.

ACKNOWLEDGEMENTS

Work performed under the auspices of the U.S. Department of Energy by the Lawrence Livermore National Laboratory under contract number W-7405-ENG-48.

REFERENCES

- [1] H.K. Mao, P.M. Bell, J.W. Shaner and D.J. Steinberg, *J. Appl. Phys.* **49** 3276 (1978);
J.H. Eggert, K.A. Goettel, and I.F. Silvera, *Phys. Rev. B* **40** 5724 (1989).
- [2] S. Marsh ed. *LASL Shock Hugoniot Data*, Berkeley: Univ. of Cal. Press 1980.
- [3] Ya.B. Zel'dovich and Yu.P. Raizer, *Physics of Shock Waves and High-Temperature Hydrodynamic Phenomena* (Academic, NY 1967), Vol. II, p726;
- [4] A.C. Mitchell and W.J. Nellis, *J. Appl. Phys.* **52**, 3363 (1981).
- [5] Crystal Systems, 27 Congress Str., Salem, MA 01970. 508-745-0088.
- [6] N.Holmes, *Rev. Sci. Instr.* **62**, 1990 (1991).
- [7] M.N. Pavlovskii, *Sov. Phys. Solid State* **13**, 741 (1971);
M.N. Pavlovskii, *Sov. Phys. Solid State* **12**, 1736 (1971).
- [8] D.J. Erskine and W.J. Nellis, *J. Appl. Phys.* **71**, 4882 (1992).

END

DATE
FILMED

12 / 11 / 93

