

LA-UR-

*Approved for public release;  
distribution is unlimited.*

*Title:* In-situ Investigation of Water Distribution in Polymer Electrolyte Fuel Cell Using Neutron Radiography

*Author(s):* Jeffrey Mishler

*Intended for:* 218th ECS Meeting  
October 10-15, 2010  
Las Vegas, NV, USA



Los Alamos National Laboratory, an affirmative action/equal opportunity employer, is operated by the Los Alamos National Security, LLC for the National Nuclear Security Administration of the U.S. Department of Energy under contract DE-AC52-06NA25396. By acceptance of this article, the publisher recognizes that the U.S. Government retains a nonexclusive, royalty-free license to publish or reproduce the published form of this contribution, or to allow others to do so, for U.S. Government purposes. Los Alamos National Laboratory requests that the publisher identify this article as work performed under the auspices of the U.S. Department of Energy. Los Alamos National Laboratory strongly supports academic freedom and a researcher's right to publish; as an institution, however, the Laboratory does not endorse the viewpoint of a publication or guarantee its technical correctness.

# In-situ Investigation of Water Distribution in Polymer Electrolyte Fuel Cell Using Neutron Radiography

Jeffrey Mishler<sup>a</sup>, Yun Wang<sup>a\*</sup>, Rangachary Mukundan<sup>b</sup>, Rodney Borup<sup>b</sup>, Daniel S. Hussey<sup>c</sup>, David L. Jacobson<sup>c</sup>

<sup>a</sup> Renewable Energy Resources Lab, Department of Mechanical and Aerospace Engineering,

The University of California, Irvine, 92697-3975, USA

<sup>b</sup> Los Alamos National Laboratory (LANL), MS D429, MPA-11, Los Alamos, NM 87545, USA

<sup>c</sup> National Institute of Standards and Technology (NIST), Center for Neutron Research, 100 Bureau Drive, MS 8461, Gaithersburg, MD 20899, USA

This paper investigates the water content within operating polymer electrolyte membrane (PEM) fuel cells using neutron radiography. We consider fuel cells with various PTFE loadings in their gas diffusion layers (GDL) and microporous layers (MPL), and examine the impacts of MPL/GDL properties on the liquid water behavior and fuel cell performance. Fuel cells are tested at both dry and fully hydrated conditions with different serpentine flow fields. Water contents in the projected areas of channel and land regions are probed. We find that the fuel cell may be subject to more flooding at low current-density operation. In addition, both MPL and GDL wetting properties have substantial impacts on the water content in fuel cell. The cell performance also varies on different scenarios of the MPL/GDL wetting properties. The quad-channel flow field exhibits higher water content without remarkable change in performance at low current densities. Liquid water profile along the channel is presented and liquid water on-set clearly indicated.

## Introduction

PEM fuel cells for automotive applications will likely operate with inlet gas streams at less than saturated conditions. With dry gas flows it is important to fully understand the water management within the fuel cell in order to ensure membrane hydration to reduce the ohmic polarization.

Liquid water may emerge in PEM fuel cell (1) even at low humidity operation (2). Different GDLs show various liquid distributions (3). The addition of a microporous layer (MPL) to the gas diffusion layer (GDL) has been shown to increases the catalyst utilization and improve fuel cell water management (4). Weber et al. (5) developed a developed an analytical model to examine the effect of wettability of the diffusion media on water management, and demonstrated that owing to its higher hydrophobicity and lower porosity the MPL is less susceptible to water flooding than the carbon substrate, and also proposed that the MPL acts as a valve that pushes water away from the GDL to the flow field to minimize water flooding (6). The PTFE serves as a binder to maintain

the integrity of carbon particles in the MPL, and provides high hydrophobicity to avoid water flooding. However, the optimized value of PTFE has been shown in the literature to vary by condition from 15% (7), 10% (8), 20% (9), and 30% on substrate and 15% on the MPL (10). Park (11) used water permeation experiments to indicate that PTFE increases the resistance of the water flow through the GDL due to a decrease of the MPL porosity and an increase of the volume fraction of hydrophobic pores, and performance showed that the optimized PTFE loading of 23% had effective water management. Wood (12) tested the effect of PTFE loadings in the GDL by use of a segmented cell to show in-plane performance differences.

By utilizing neutron imaging we are able to quantify the water content and distribution in a running fuel cell. Analysis of the response to current step-up and step-down for different PTFE loadings in the GDL was presented by Davey and Mukundan (13). This study presents experimental results and analysis of the effect of different PTFE weight loadings on the water content inside a fuel cell and fuel cell performance. We consider both dry and fully hydrated conditions and a wide range of operating current densities.

## Experimental

### Fuel Cell Steady-State Testing

The fuel cell hardware was designed specifically for neutron imaging, designed at LANL and built by Fuel Cell Technologies employing gold-plated aluminum. Two different flow field designed were tested, either single serpentine or quad-serpentine. The MEA used was a Gore™ Primea® MEA Series 57 with 18  $\mu\text{m}$  thick GORE-SELECT® membrane with carbon supported 0.2 mg Pt  $\text{cm}^{-2}$  on the cathode and 0.1 mg Pt  $\text{cm}^{-2}$  on the anode (GORE-SELECT, PRIMEA and GORE are trademarks of W. L. Gore & Associates, Inc). The GDLs used were SGL Carbon's carbon paper 24-Series with a 200  $\mu\text{m}$  thick substrate and a 50  $\mu\text{m}$  thick MPL. The cells differed in the channel flow field patterns and in the PTFE weightings, as described in Table I.

**Table I.** Properties of tested fuel cells.

Cell Number	Flow Field Type	Anode Substrate	PTFE Loading (weight %)		
			Anode MPL	Cathode Substrate	Cathode MPL
1	Single Serpentine	5%	23%	20%	10%
2	Single Serpentine	5%	23%	5%	23%
4	Single Serpentine	5%	5%	20%	10%
5	Quad Serpentine	5%	23%	20%	10%

The fuel cells were operated at 80°C. Anode hydrogen and cathode air stoichiometries of 1.2 and 2.0 respectively, and with minimum anode and cathode flows of 50 and 75 standard  $\text{cm}^3 \text{ min}^{-1}$ . The relative humidity of the anode and gas flow streams was set at either 0%, 50%, and 100% for the anode and cathode sides. Most measurements were taken with the flows in co-flow operation, with some additional measurements made in counter-flow operation. The outlet gas backpressure was 172 kPa absolute.

Steady state operation tests were carried out at constant current, with the current density varied from 0 to 1.6 A/cm<sup>2</sup> in intervals of 0.4A/cm<sup>2</sup> (0, 0.4, 0.8, 1.2, 1.6 A/cm<sup>2</sup>). This was achieved by setting the fuel cell to a certain current density, and then waiting for at least 15 minutes for a steady state to be reached.

The effects of the humidity of the inlet gases, hydrogen on the anode side and air on the cathode side, onto the water density within the operating fuel cell. For the steady state tests, relative humidity for the steady state conditions was either 50% anode/50% cathode or 100% anode/100% cathode. For the transient cases at 80 degrees C, the humidity was set to 100% anode/100% cathode, 100% anode/50% cathode, and 50% anode/50% cathode. For the transient cases at 40 degrees C, the humidity was set to 0% anode/0% cathode and 0% anode, 50% cathode.

### Neutron Imaging

Neutron imaging was performed at the NIST Center for Neutron Research (NCNR) on thermal beam tube 2. The sensor used for imaging had a per-pixel resolution of 127 $\mu$ m  $\times$  127 $\mu$ m.

Neutron image analysis was performed using the IDL programming language, a dry reference image, and an additional reference image to correlate water thickness to imaging response, as described by Hickner et al. (14).

Masks were made to represent the lands, channels and active area of the cells. For the pixels at the boundaries between the channel and land areas it cannot be said what percent of the detected water is from the channel and what percent is in the land. We have chosen to not include these pixels as either land or channel. This means that the channel and land masks cover the middle (~80%) of the channel and land area, respectively. The active area mask includes the area under the channel, lands, and the above-mentioned area between the channel and land.

The masks were further broken down into segments to determine the along-channel distribution of water in the fuel cells. The single-serpentine flow field was segmented into 7 parts.

Each fuel cell was imaged for one-second, and the 60 exposures for each minute then averaged into a single image. For each operating condition at least 30 1-minute intervals were imaged, and then averaged to get the average steady state water content of the cell.

## **Results and Discussion**

### PTFE loading in the anode and cathode GDL

The water content of the land and channel area in each of the three single-serpentine cells is shown in Figure 1 below.

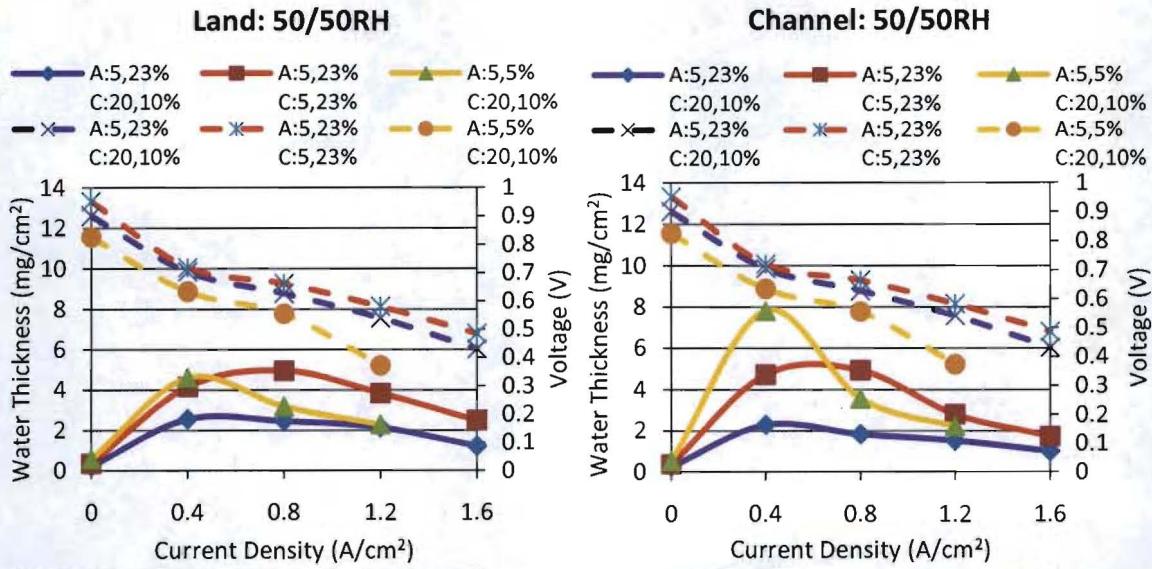


Figure 1: Comparison of water in the land area (left) and channel area (right) among single-serpentine channel fuel cells operating at 50%/50% RH.

It can be seen in all cells that there is little water at low current densities, and that the maximum water content is at medium current densities, between 0.4 and 0.8 A/cm<sup>2</sup>. At higher current densities there are higher volume flow rates, which is more effective at removing liquid water from the channels. This agrees with prior neutron imaging studies (15).

In comparison to cell 1, cell 4 has a change in PTFE loading in the anode-side GDL and MPL, and cell 2 has a change in the PTFE loading on the cathode-side GDL and MPL. It can be seen that a large impact is made on both performance and water content is made by increasing the PTFE loading in the MPL on the anode side from 5% (orange) to 23% (blue). The performance increased at all current densities, and there is less water in both the channel and land. When the MPL is not very hydrophobic, water is driven to the anode side and accumulates more. The decrease in the water under the lands is not as significant.

The second comparison, between cells 1 and 2, is a change in PTFE loading on the cathode side from 5% substrate and 23% MPL (red) to 20% substrate and 10% MPL (blue). The 20%/10% GDL/MPL had higher performance and also had higher water content.

Similar comparisons were made for the three single-serpentine cells operating at 100%/100% RH, as shown in Figure 2 below. Not all operating conditions were tested. There is an increase in water content at the higher RH. At 0 A/cm<sup>2</sup> there is still water, indicating that the saturated flows are unable to remove water and residual water exists.

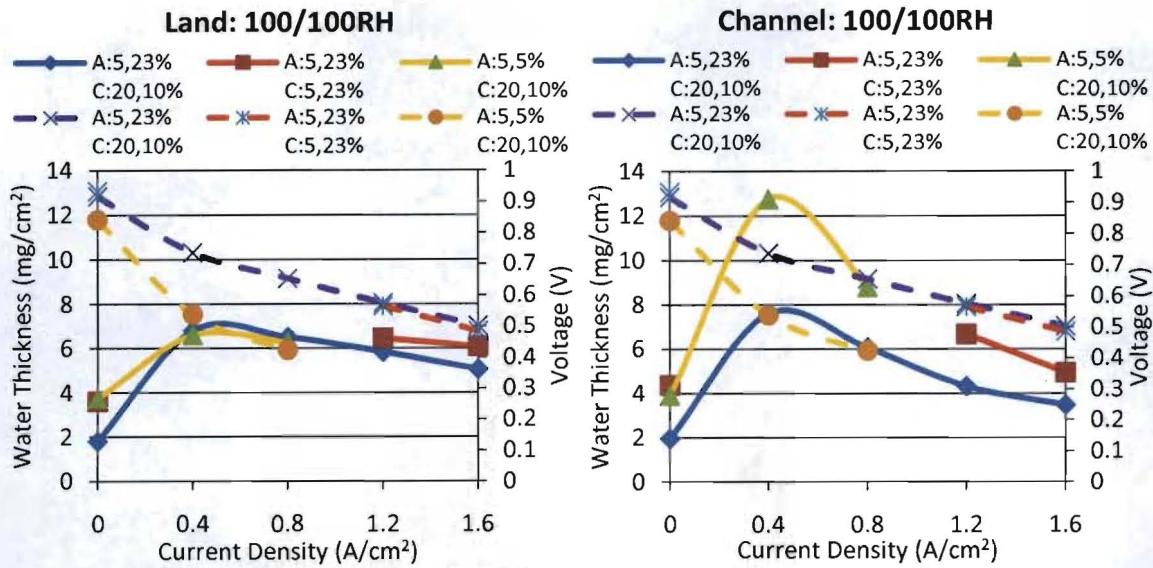


Figure 2: Comparison of water in the land area (left) and channel area (right) among single-serpentine channel fuel cells operating at 100%/100% RH.

#### Single vs Quad Serpentine Flow Fields

Comparisons of cells 1 and 5, which have the same PTFE loading for different flow-field arrangements, are shown below in Figure 3.

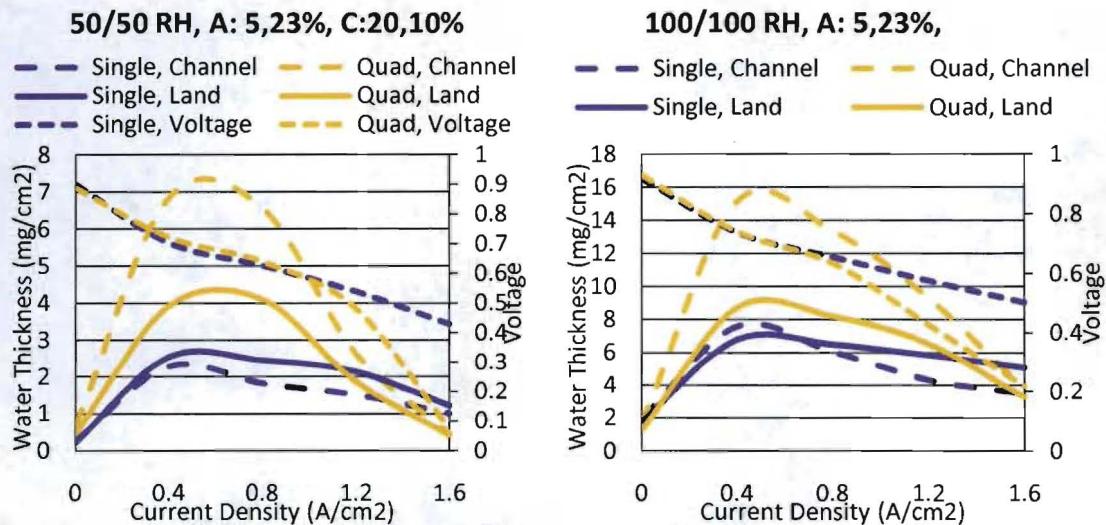


Figure 3: Comparison of water content between single and quad serpentine cells

The quad serpentine cell exhibits higher water content than the single serpentine cell except at the highest current density. There was also a reversal of the channel/land trend from the single-serpentine case, in that the quad-serpentine case had more water under the channels than under the lands. Along each path from inlet to outlet there are fewer 180° turns for a quad-serpentine flow field than for the single-serpentine flow field, which results in a lower pressure drop, and lower flow velocities within each channel. This decreases the water removal abilities of the fuel cell, leaving much higher channel water content.

### Along-channel water distribution

Wood used segmented cells to show the performance (12) along the channel for different GDLs. This can be compared to the water content found in this study.

The colorized neutron images of the water content for cells 1 and 2 are shown in the left and center part of Figure 4, and they were segmented according to the diagram shown on the right part of as shown below on the left part of Figure 4, and additionally broken into channel and lands. The water evolution along the channel is shown in Figure 5.

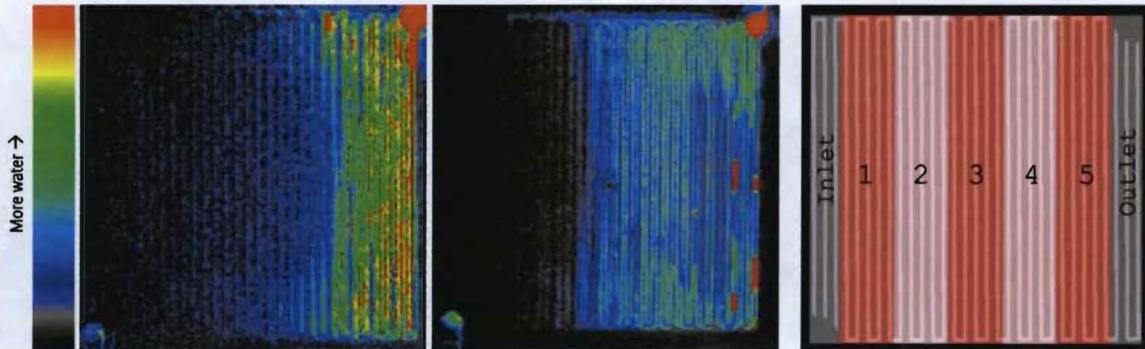


Figure 4: Segments for single-serpentine channel (left), water density images at 50%/50% RH and 0.8 A/cm<sup>2</sup> for cell 1 (center) and cell 4 (right).

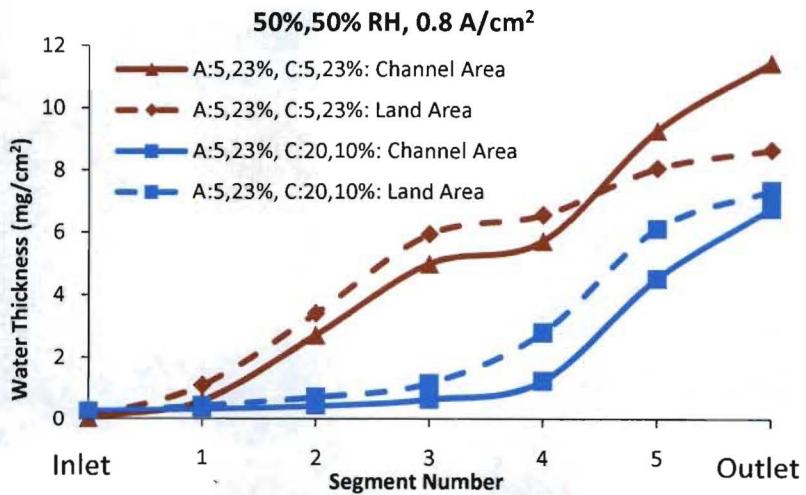


Figure 5: Water evolution along the channel for cells 1 and 2.

The previous section showed that there is higher water content overall for cell 2 (red). When looking at the segments, it can be seen that the water begins to accumulate much earlier than in cell 1. The performance data in Ref. (12) showed higher performance for the last segment of the fuel cell, and also showed that the BC 5,23% PTFE GDL outperformed the DI 20,10% PTFE. Figure 5 shows that the water evolves earlier and the cell has more water content through the cell. At dry gas flows, the higher PTFE content of the MPL helps to keep the membrane hydrated.

### Conclusions

This study examines the water content in four PEM fuel cells using various combinations of SGL Carbon GDLs with different PTFE loadings for steady state operation at different relative humidities and various current densities. In-situ neutron imaging was used to determine the liquid water content inside fuel cell. The effect of these GDLs on the water content and fuel cell performance was presented and discussed. Higher PTFE loading in the MPL of the anode-side GDL was shown to decrease the water content under both the channel and lands, while also increased the fuel cell performance. A more hydrophobic MPL can prevent water from accumulating in the anode side. The second comparison decreases the PTFE on the cathode GDL substrate and increases it on the cathode MPL. This higher PTFE on the cathode impedes water loss from the PEM at low humidity, which helps to increase performance.

### Acknowledgments

This work was supported by the U.S. Department of Energy (DOE) Office of Hydrogen, Fuel Cells, and Infrastructure Technology (Program Manager: Nancy Garland). This work was also supported by the U.S. Department of Commerce, the NIST Ionizing Radiation Division, the Director's Office of NIST, the NIST Center for Neutron Research, and the Department of Energy through interagency agreement no. DE-AI01-01EE50660. We also thank Peter Wilde of SGL Group for providing the GDL materials.

### References

1. C.-Y. Wang, *Chemical Reviews*, **104**, 4727 (2004).
2. Y. Wang, *Journal of Power Sources*, **185**, 261 (2008).
3. Y. Wang, C. Y. Wang and K. S. Chen, *Electrochimica Acta*, **52**, 3965 (2007).
4. U. Pasaogullari, C.-Y. Wang and K. S. Chen, *Journal of The Electrochemical Society*, **152**, A1574 (2005).
5. A. Z. Weber, R. M. Darling and J. Newman, *Journal of The Electrochemical Society*, **151**, A1715 (2004).
6. A. Z. Weber and J. Newman, *Journal of The Electrochemical Society*, **152**, A677 (2005).
7. V. A. Paganin, E. A. Ticianelli and E. R. Gonzalez, *Journal of Applied Electrochemistry*, **26**, 297 (1996).
8. L. Giorgi, E. Antolini, A. Pozio and E. Passalacqua, *Electrochimica Acta*, **43**, 3675 (1998).
9. F. Lufrano, E. Passalacqua, G. Squadrito, A. Patti and L. Giorgi, *Journal of Applied Electrochemistry*, **29**, 445 (1999).
10. E. Antolini, R. R. Passos and E. A. Ticianelli, *Journal of Applied Electrochemistry*, **32**, 383 (2002).
11. S. Park, J.-W. Lee and B. N. Popov, *Journal of Power Sources*, **177**, 457 (2008).
12. D. L. Wood, R. Mukundan and R. Borup, *ECS Transactions*, **25**, 1495 (2009).
13. J. R. Davey, R. Mukundan, J. S. Spendelow, P. P. Mukherjee, D. S. Hussey, D. L. Jacobson, M. Arif and R. Borup, *ECS Transactions*, **25**, 971 (2009).
14. M. A. Hickner, N. P. Siegel, K. S. Chen, D. N. McBrayer, D. S. Hussey, D. L. Jacobson and M. Arif, *Journal of The Electrochemical Society*, **153**, A902 (2006).
15. T. A. Trabold, J. P. Owejan, D. L. Jacobson, M. Arif and P. R. Huffman, *International Journal of Heat and Mass Transfer*, **49**, 4712 (2006).