

Charles Pye is studying Surface Nanostructure Analysis in the SULI Program at the Ames Laboratory, where he investigated "Novel Coarsening of Pb Nanostructures on Si(111) 7 X 7." As an undergraduate, he studied physics at the University of Kansas in Lawrence, Kansas, his hometown. Mr. Pye is a member of the American Physical Society, and he enjoys music and drawing.

Michael Yakes received his Ph.D. from Iowa State University in 2006. His thesis research was focused on the study of Pb nanostructures on Si substrates using high resolution electron diffraction. He is currently studying III/V semiconductor devices using cross-sectional scanning tunneling microscopy as a National Research Council postdoc at the Naval Research Laboratory in Washington, D.C.

Myron Hupalo received a Ph.D. in physics from Lviv State University in Ukraine, in 1982. He is currently Associate Scientist at Ames Laboratory

USA-DOE. His expertise is in surface physics, especially the construction and use of Scanning Tunneling Microscope. He is author or coauthor of more than 45 publications in the study of epitaxial growth in the 2-d physics of surface overlayers and self organization on surfaces. Currently he is interested in the study of Quantum Size Effects in metal nanostructures.

Michael C. Tringides is a Professor of Physics at Iowa State University, and Senior Scientist at Ames Laboratory USA-DOE. He received his PhD from University of Chicago in 1984 on surface physics. He is the organizer of two major conferences in surface diffusion, and coeditor of the proceedings books. He is author or coauthor of 120 publications and has given more than 125 invited talks at international conferences and institutions. His current interests involve the study of surface physics, epitaxial growth and nanostructure formation with the use of High Resolution Electron Diffraction and Scanning Tunneling Microscopy.

NOVEL COARSENING OF Pb NANOSTRUCTURES ON Si(111) 7 X 7

CHARLES J. PYE, MICHAEL YAKES, MYRON HUPALO, AND MICHAEL TRINGIDES

ABSTRACT

In order to study a possible means of controlling the growth of an epitaxially grown, self-assembled nanostructure, Pb/Si(111) was analyzed. An atomically clean Si(111) 7 X 7 crystal was prepared under Ultra High Vacuum (UHV) conditions followed by Pb deposition. The islands were monitored over time with a Scanning Tunneling Microscope (STM) to see how they coarsen (the process of smaller islands disappearing and larger islands growing even larger) and determine the applicability of the classical theory of Ostwald ripening. STM Images of the resulting Pb islands were taken as they evolved in time. Height measurements indicated that initially, the majority of islands (25 out of 33) were 4 or 5 layer islands, but by the end of the experiment 68 minutes later, the majority (18 out of 24 islands) were 7 or 9 layer islands. Additional measurements of the area indicate that the total area of all the islands was reduced by 10%, but the total coverage increased by ~40%, presumably coming from the wetting layer. Measurements of island area and height over time indicated that an increase in height was accompanied by a sudden (within 2-3 minutes) increase in volume and decrease in area. Interestingly, some islands grew by adding a ring of higher height around the edge before filling in the center. These rings, on average, would fill in less than 5 minutes. Generally, the islands started with a random shape, and gradually became more like a regular hexagon over time. These observations are very unusual because they do not fit the classical expectations based on Ostwald ripening and they show the role of Quantum Size Effects upon the coarsening process.

INTRODUCTION

One of the major goals of surface science has been the creation of self-assembled nanostructures of a controlled height, size, and shape. Many patterns have already been discovered in the formation of these nanostructures. The ability to control these nanostructures would be of great importance, both in practical applications such as computer miniaturization, and in basic understanding of how nature functions at the scale of 10^{-9} meters.

The particular goal of this experiment was to determine whether Pb on Si(111) 7 X 7 followed classical Ostwald Ripening. In Ostwald Ripening, atoms transfer from islands smaller than a certain radius to those larger than that radius so as to minimize the Gibbs free

energy of formation [1]. This causes a coarsening process which results in fewer islands of a larger size, which continuously change volume while the total volume of all the islands remains constant [2]. Pb on Si(111) 7 X 7 has shown several unusual behaviors in the past which are not explained by Ostwald Ripening, particularly its Quantum Size Effects (QSE) [3,4,5].

Some of the specific questions investigated during this experiment were: how did the height of the islands change over time? How did their size, volume and shape change over time? How did these change when the islands changed height? What were the sizes and durations of the rings that often accompanied a change in height? What was the growth mechanism of the islands?

MATERIALS AND METHODS

An atomically clean Si(111) 7 X 7 crystal was prepared at a pressure of 2×10^{-11} torr followed by Pb deposition at a flux of 0.05 monolayers (ML)/minute and a temperature of 242K. Images of the resulting lead islands were taken with a Scanning Tunneling Microscope (STM) using a constant voltage of 1.5V and a current of 1nA over an area of 500 x 500nm as they evolved in time. Commercial imaging software (Scala 4.2 and Scion Image 4.03) was used to take measurements of the islands on the resulting images.

RESULTS AND DISCUSSION

Figure 1(a) shows the average volume for an individual island in each image. The large increase shows that some sort of coarsening process is going on. Figure 1(b) shows that the number of islands is decreasing, from 33 islands at time 0 to only 24 after 68 minutes, which is further indication of a coarsening process. This decrease in the number of islands can be seen in the difference between figures 1(c) and 1(d). Both images show an area measuring 500 x 500nm, at a temperature of 242K and a voltage of 1.5V. Figure 1(c) was taken just after Pb deposition, but 1(d) was the last image taken, 68 minutes after the acquisition of 1(c). It is apparent in these images that the number of islands had decreased, and detailed measurements showed that their height had also grown. The islands with the smallest volumes had decayed completely. This is consistent with the coarsening process that occurs during Ostwald Ripening.


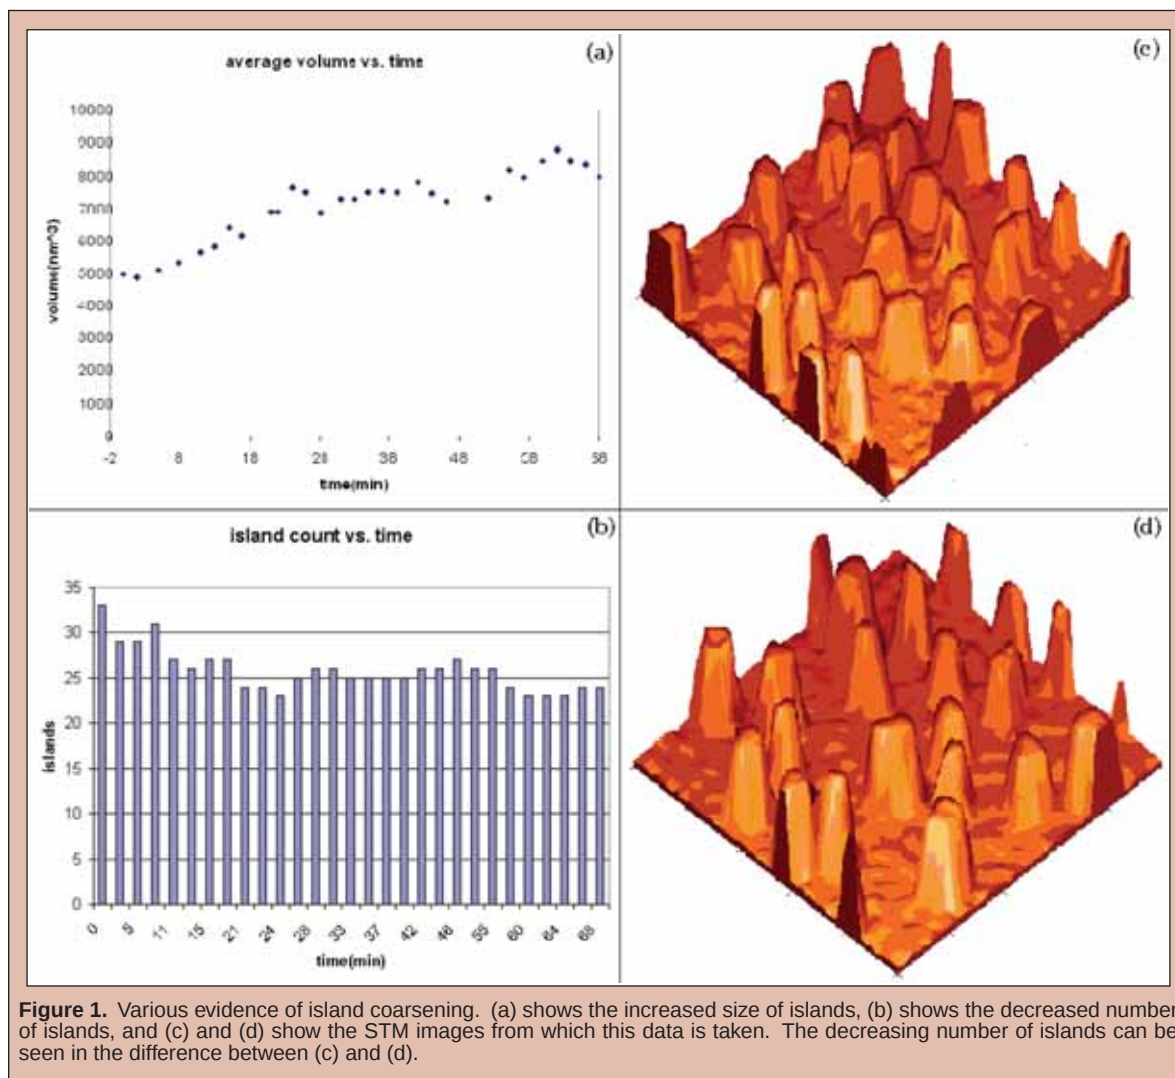


Figure 2 shows the total island volume increasing over time. In Ostwald Ripening, however, overall volume is conserved. The increase in total volume indicates that there is a transfer of atoms from the wetting layer to the islands throughout the experiment. Another important difference is that, in Ostwald Ripening, islands continuously change in volume depending on their size and the size

of their neighboring islands [3]. However, these observations show that islands grow suddenly in volume when they grow in height, but before or after the sudden increase their volume changes very little. The reason for this growth pattern is not yet understood. This increase in volume is also typically accompanied by a decrease in area.

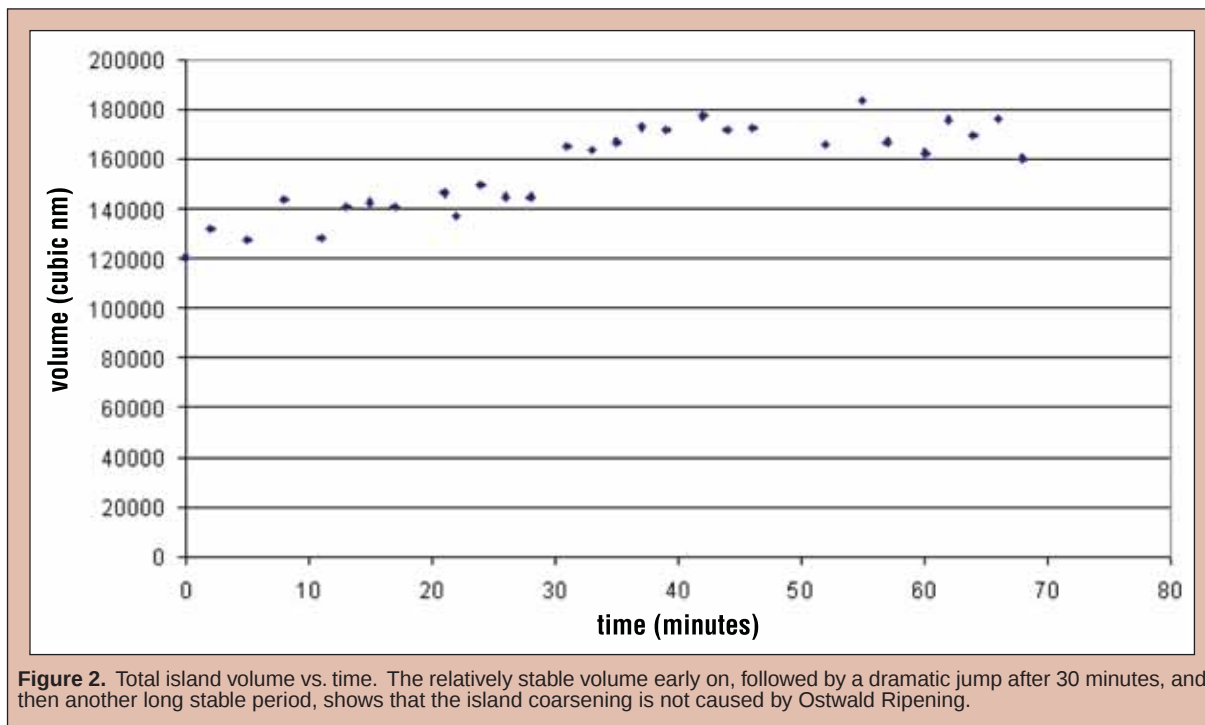

Figures 3(a) and 3(b) show this behavior. 3(a) shows the volume of one typical island over time: the blue represents the volume of the island when it is 5 layers tall, and the yellow represents the volume of the island when it is 7 layers tall. At 23 minutes it grew a ring, so some of it was 5 layers tall and some of it was 7 layers tall. There is a ~20% increase in volume from time 21 to 24, but

before and after the increase the volume remained constant. Figure 3(b) relates the percentage change in volume to the change in area for all islands that increased in height. All increases in height led to an increase in volume and 14 of the 17 changes in height were accompanied by a decrease in area.

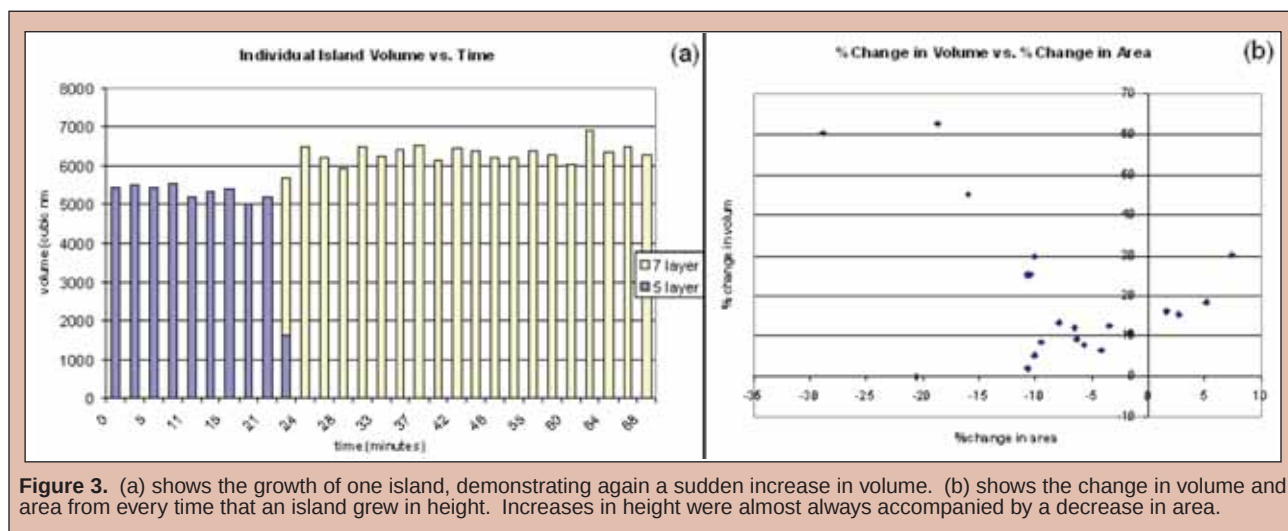


Figure 4(a) shows the height of islands as they evolved over time. Initially, 24 of the 33 islands were either 4 or 5 layers tall. After 68 minutes, 18 of the 24 visible islands were 7 or 9 layers tall, and none of the islands were 4 or 5 layers tall. Figures 4(b) and 4(c) show this difference in the distribution of island heights between the first and last images taken. This is clear evidence of QSE,

because it shows that 7- and 9-layer heights are the most stable[3]. It should be noted that some of the small spikes in figure 4(a) are the result of islands which moved on or off the imaged area due to instrument drift (an unavoidable problem with the STM especially for experiments that take long times).

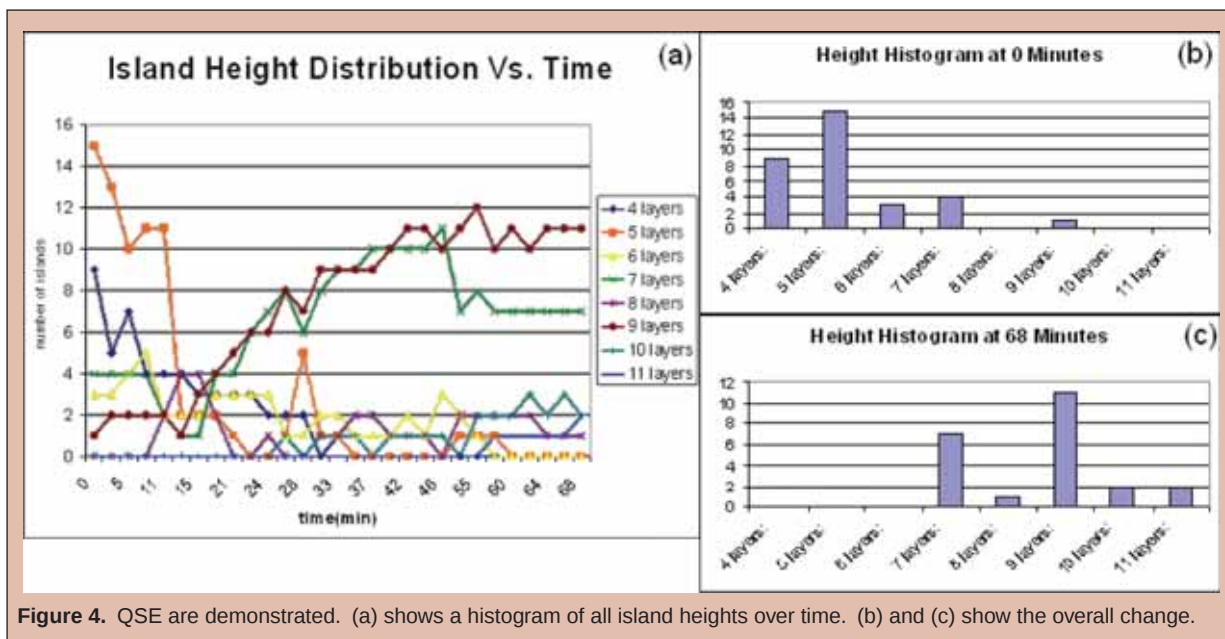


Figure 4. QSE are demonstrated. (a) shows a histogram of all island heights over time. (b) and (c) show the overall change.

Figure 5(a) is a 500nm x 500nm STM image showing numerous rings. These islands, instead of being atomically flat on top, have a section at least one level higher than the rest of the island. One of the rings in this image is still incomplete, and divides the island in half instead of stretching around the edge as complete rings do. Figure 5(b) shows a histogram of how long an island maintained a ring before becoming flat again. These rings appear to be unstable, and fill in to produce the next stable layer. 13 of the 23 rings lasted

less than five minutes, and it is possible that many more lasted less than two minutes, but were not detected due to the two minute gap between images. The temperature of 242K is high for this sort of experiment, and lowering this temperature would lead to longer lasting rings.

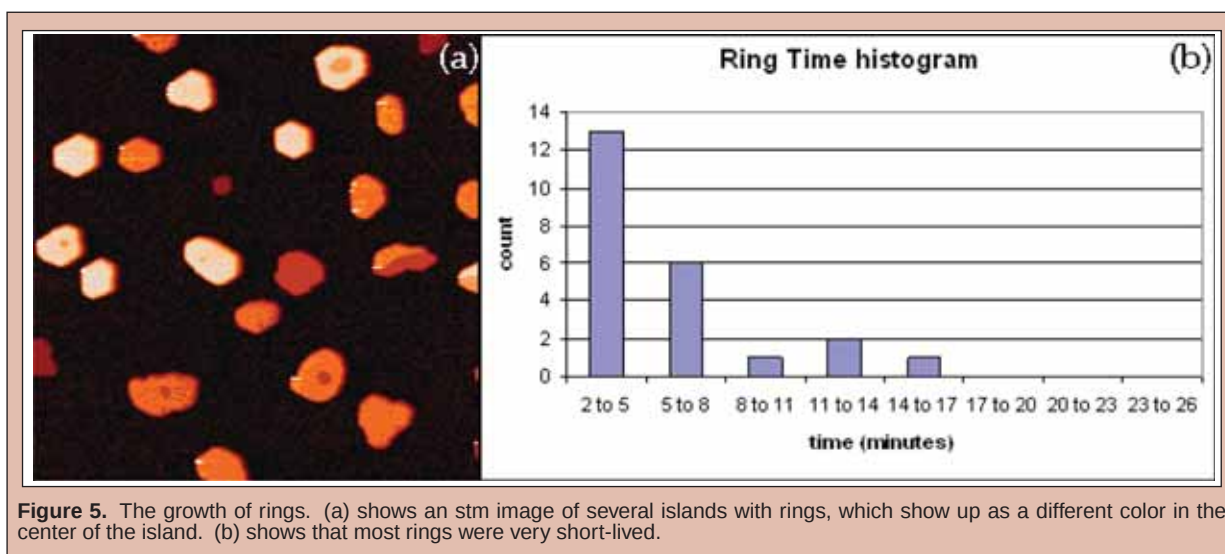


Figure 5. The growth of rings. (a) shows an stm image of several islands with rings, which show up as a different color in the center of the island. (b) shows that most rings were very short-lived.

DISCUSSION AND CONCLUSIONS

These results provide some insight into the behavior of Pb on a Si(111) 7 X 7 crystal, but much is still unknown about its behavior. It is clear that QSE play a strong role in its coarsening process, due to the very strong preference for heights of 7- and 9- layers. It also seems clear that the coarsening process is not classical Ostwald Ripening. Although the growth in average island volume and the decay of the islands with the smallest volume shows that a similar coarsening process is going on, the increase in total volume and the stepwise growth in island volume clearly differ from classical Ostwald Ripening. The question of what causes these differences remains: it could be the result of QSE, or it could be a different process entirely.

One of the most unusual characteristics of Pb/Si(111) is its ring growth. The rings in this experiment were frequently associated with an increase in height, suggesting that whatever process is causing the coarsening of these islands is also causing their ring growth. The instability of these rings implies that they might be even more frequent than what was observed here. Any ring which lasted less than 2 minutes might not have been observed (due to the gap between images) — it is possible that all increases in height began with a ring.

A key investigation which remains is to determine how the islands grow in height. The results of this experiment seem to indicate that there is a transfer of atoms from the wetting layer to the islands. This could be accomplished either by adding atoms from the wetting layer which push the atoms in the island higher, or by adding atoms from the wetting layer directly to the top of the island after diffusing on the facet planes. These two processes would be indistinguishable in this experiment, so further work must be done to establish the process by which the islands are growing in height. Understanding this process is crucial to understanding the overall coarsening process.

ACKNOWLEDGMENTS

I would like to thank the Department of Energy and the Office of Science, for funding my research. I would also like to thank Ames Laboratory and Iowa State University for hosting me. Finally, I would like to thank Jizhou Chen and Steven Binz for all of their help with this project.

REFERENCES

- [1] M. Zinke-Allmang, L.C. Feldman, and M.H. Grabow, "Clustering on Surfaces," Surface Science Reports, vol.16, issue 8, pp. 377-463, Dec. 1992.
- [2] L. Ratke and P.W. Voorhees, Growth and Coarsening. Berlin: Springer, 2002.
- [3] C.A. Jeffrey, E.H. Conrad, R. Feng, M. Hupalo, C. Kim, P.J. Ryan, P.F. Miceli, and M.C. Tringides, "Influence of Quantum Size Effects on Island Coarsening," Physical Review Letters, vol. 96, no. 106105, March 17 2006.
- [4] K. Budde, E. Abram, V. Yeh, M. C. Tringides, "Uniform, self-organized, seven-step height Pb/Si(111)-(7×7) islands at low temperatures," Physical Review B, vol. 61, R10602, April 15 2000.
- [5] Hiroshi Okamoto, Dongmin Chen, and Toshishige Yamada, "Competing Classical and Quantum Effects in Shape Relaxation of a Metallic Island," Physical Review Letters, vol 89, no. 25, Dec. 16 2002.