



# Carbon Dioxide Separation Technology: R & D Needs for the Chemical and Petrochemical Industries

A Chemical Industry Vision 2020 Initiative to Identify Future R & D Needs



**Approved and Issued by the  
Chemical Industry Vision2020 Technology Partnership**

**An electronic copy of this plan can be found at:  
[www.chemicalvision2020.org](http://www.chemicalvision2020.org)**

**Copyright Information**

The information in this document is meant to be distributed widely throughout the chemical industry and the broader research community. The authors encourage reproduction and dissemination of portions of or the entire document with attribution and without changes.

**Acknowledgements**

This study was carried out by James A. Ritter and Armin D. Ebner under a subcontract with Oak Ridge National Laboratory (Managed by UT-Battelle, LLC for the Department of Energy under contract DE-AC05-00OR22725) and sponsored by the U.S. Department of Energy's Office of Energy Efficiency and Renewable Energy, Industrial Technologies Program. The programmatic support of Dickson Ozokwelu, the Chemicals Industry of the Future team lead who funded this effort, is greatly appreciated.

We would also like to thank members of the Chemical Industry Vision2020 Technology Partnership committee who contributed to this study: Francis Via of Fairfield Resources (Chair); Sharon Robinson of Oak Ridge National Laboratory (Vice Chair); Linda Curan of BP; Timothy Frank, Parick H. Au-Yeung, and John G. Pendergast, Jr. of Dow; Scott Barnicki of Eastman Chemical; Hans Wijmans of Membranes Research & Technology, Inc.; Krish R. Krishnamurthy and Stevan Jovanic of BOC; Dante Bonaquist and Neil Stephenson of Praxair, Inc.; Santi Kulprathipanja of UOP; Dilip Kathold of Air Products and Chemicals, Inc.; Charles G. Scouten of The Fushfeld Group; Brendan Murray of Shell; and Greg Chambers of GE. H. Lee Schultz and Borys Marriza of BCS, Incorporated participated in final preparation of this document.

**Disclaimer**

This report was prepared as an account of work sponsored in part by agencies of the United States Government. Neither the United States Government, nor any agency thereof, nor any of their employees make any warranty, expressed or implied, or assume any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represent that its use would not infringe privately owned rights.

Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. *This report represents the views and opinions of the chemical industry and not those of the United States Government or any agency thereof.*

***Carbon Dioxide Separation Technology:  
R&D Needs For the Chemical and Petrochemical Industries***

*November 2007*

# Carbon Dioxide Separation Technology:

## R&D Needs For the Chemical and Petrochemical Industries

### Table of Contents

|                                                                                                  |      |
|--------------------------------------------------------------------------------------------------|------|
| <b><u>FOREWORD</u></b> .....                                                                     | x    |
| <b><u>EXECUTIVE SUMMARY</u></b> .....                                                            | ES-1 |
| <b><u>INTRODUCTION</u></b> .....                                                                 | 1    |
| <b><u>CURRENT COMMERCIAL PRACTICES</u></b> .....                                                 | 2    |
| Overview of CO <sub>2</sub> Emissions and Production Processes .....                             | 2    |
| CO <sub>2</sub> Removal Processes .....                                                          | 4    |
| <i>Absorption Processes</i> .....                                                                | 5    |
| <i>Adsorption Processes</i> .....                                                                | 7    |
| <i>Membrane Processes</i> .....                                                                  | 9    |
| <i>Cryogenic Liquefaction Processes</i> .....                                                    | 10   |
| Summary of Current Commercial Practices.....                                                     | 11   |
| <b><u>EMERGING LITERATURE CONCEPTS</u></b> .....                                                 | 12   |
| Adsorption .....                                                                                 | 12   |
| <i>Adsorption Process Refinements</i> .....                                                      | 12   |
| <i>Sorption Enhanced Reaction (Periodic Adsorptive Separating Reactors)</i> .....                | 17   |
| <i>Selective Adsorbents</i> .....                                                                | 18   |
| Membranes .....                                                                                  | 20   |
| <i>Polymeric Membranes</i> .....                                                                 | 20   |
| <i>Facilitated Transport Membranes</i> .....                                                     | 23   |
| <i>Inorganic Membranes</i> .....                                                                 | 25   |
| <i>Hybrid Membranes</i> .....                                                                    | 26   |
| <i>Hollow Fiber Gas-Liquid Contactors</i> .....                                                  | 27   |
| Conclusions from Background Survey .....                                                         | 29   |
| <b><u>RECOMMENDATIONS FOR FUTURE R&amp;D</u></b> .....                                           | 31   |
| Near-Term Adsorbent Development.....                                                             | 31   |
| Near-Term Membrane Development.....                                                              | 32   |
| Near-Term Adsorption Process Development.....                                                    | 33   |
| Near-Term Absorbent and Absorption Process Development .....                                     | 35   |
| Long-Term Flow Sheet Augmentation with Adsorption and Membrane Processes .....                   | 36   |
| Long-Term Advanced Adsorbent Materials and Process Development for CO <sub>2</sub> Removal ..... | 36   |
| Long-Term Advanced Membrane Materials for CO <sub>2</sub> Removal.....                           | 37   |
| <b><u>SUPPORTIVE INFORMATION ON ENVIRONMENTAL CO<sub>2</sub> EMISSIONS</u></b> .....             | 38   |
| Main Sources of Industrial CO <sub>2</sub> Emissions .....                                       | 38   |

|                                                                                                 |     |
|-------------------------------------------------------------------------------------------------|-----|
| <i>Combustion Processes</i> .....                                                               | 39  |
| <i>Coal Gasification</i> .....                                                                  | 41  |
| <i>Iron and Steel Manufacture</i> .....                                                         | 45  |
| <i>Lime and Cement Production</i> .....                                                         | 46  |
| <i>Hydrogen, Syngas, and NH<sub>3</sub> Production</i> .....                                    | 48  |
| <i>Natural Gas Production</i> .....                                                             | 50  |
| <i>Aluminum Manufacture</i> .....                                                               | 51  |
| <i>Sulfur Recovery Processes</i> .....                                                          | 53  |
| <i>Landfill and Coal Bed Methane Gases</i> .....                                                | 54  |
| <i>Fermentation to Produce Ethanol</i> .....                                                    | 56  |
| <b>Mitigation Approaches to Combat CO<sub>2</sub> Emissions</b> .....                           | 56  |
| <b>Expanding the Definition of CO<sub>2</sub> Capture Approaches used in Power Plants</b> ..... | 59  |
| <b>Conceptual Flow Sheets for Additional Guidance</b> .....                                     | 61  |
| <b><u>References</u></b> .....                                                                  | 71  |
| <b><u>Vision 2020 for the Chemical Industry Separations Committee Members</u></b> .....         | 132 |
| <b><u>Glossary</u></b> .....                                                                    | 133 |

## **List of Tables**

|           |                                                                                                                                                             |     |
|-----------|-------------------------------------------------------------------------------------------------------------------------------------------------------------|-----|
| Table 1.  | 1990 and 2004 Worldwide and U.S. CO <sub>2</sub> emissions. ....                                                                                            | 97  |
| Table 2.  | Summary of 2002 U.S. CO <sub>2</sub> emissions. ....                                                                                                        | 98  |
| Table 3.  | Average U.S. CO <sub>2</sub> emissions per plant within several industries. ....                                                                            | 99  |
| Table 4.  | Number of patents and peer review manuscripts per researcher or research group<br>on CO <sub>2</sub> related separation processes since 1995 and 2002. .... | 100 |
| Table 5.  | Number of patents per company on CO <sub>2</sub> related separation processes since 1995<br>and 2002. ....                                                  | 104 |
| Table 6.  | Licensors of CO <sub>2</sub> separation processes, type of process, production rate, and<br>number of plants worldwide. ....                                | 105 |
| Table 7.  | Characteristics of key alkanolamines used in gas treating. ....                                                                                             | 106 |
| Table 8.  | Major types of acid gas absorbent processes. ....                                                                                                           | 107 |
| Table 9.  | Number of papers since 2000 containing in the title the indicated alkanolamine<br>and other absorbents for CO <sub>2</sub> removal. ....                    | 108 |
| Table 10. | Typical capacities of commercial and developmental CO <sub>2</sub> and CO selective<br>adsorbents. ....                                                     | 109 |
| Table 11. | Performances of various PSA cycle configurations investigated for CO <sub>2</sub><br>concentration from flue gas. ....                                      | 110 |
| Table 12. | Permeabilities and permeances of membrane materials used for CO <sub>2</sub> separations. ....                                                              | 111 |
| Table 13. | Trans-membrane flux for different capillary hollow fiber membrane contactors<br>reported in the literature. ....                                            | 127 |
| Table 14. | Typical molar fraction concentrations in each of the streams listed in Figures 4<br>to 14. ....                                                             | 129 |
| Table 15. | Typical capacities and gas flows for processes in Figures 4 to 14. ....                                                                                     | 130 |
| Table 16. | Largest IGCC and NGCC plants in the world as of January 2000. ....                                                                                          | 131 |

## List of Figures

|            |                                                                                                                                                                                                                             |    |
|------------|-----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|----|
| Figure 1.  | U.S. 2002 CO <sub>2</sub> emissions in MMt: Total, Electric Power, Transportation, Industrial, Residential and Commercial.....                                                                                              | 2  |
| Figure 2.  | U.S. Industry 2002 CO <sub>2</sub> Emissions in MMt .....                                                                                                                                                                   | 3  |
| Figure 3.  | U.S. Industry 2002 CO <sub>2</sub> emissions in MMt: non-energy related processes.....                                                                                                                                      | 38 |
| Figure 4.  | Flow sheet of a typical, state-of-the-art, combustion process that includes burners, incinerators, flaring, utility boilers, etc.....                                                                                       | 40 |
| Figure 5.  | Flow sheet of typical, state-of-the-art coal gasification (also referred to as integrated gasification combined cycle, IGCC) plants for power generation/syngas production. ....                                            | 42 |
| Figure 6.  | Flow sheet of typical, state-of-the-art coal gasification (also referred to as integrated gasification combined cycle, IGCC) plants for power generation/H <sub>2</sub> production. ....                                    | 43 |
| Figure 7.  | Flow sheet of a typical, state-of-the-art stainless steel production plant consisting of a coke oven, sinter plant, blast furnace, basic oxygen furnace (BOF), and electric arc furnace (EAF).....                          | 45 |
| Figure 8.  | Flow sheet of a typical, state-of-the-art process for the manufacture of lime and cement.....                                                                                                                               | 47 |
| Figure 9.  | Flow sheet of a typical, state-of-the-art H <sub>2</sub> or NH <sub>3</sub> production plant. ....                                                                                                                          | 49 |
| Figure 10. | Flow sheet of a typical, state-of-the-art process for the production of natural gas. ....                                                                                                                                   | 50 |
| Figure 11. | Flow sheet of typical, state-of-the-art processes for the manufacture of aluminum. ....                                                                                                                                     | 51 |
| Figure 12. | Flow sheet of a typical, state-of-the-art Claus-SCOT process for the production of sulfur from a stream rich in sulfur-bearing compounds.....                                                                               | 53 |
| Figure 13. | Flow sheet of a typical, state-of-the-art a) solid waste landfill gas recovery process and b) coal bed methane gas recovery process. ....                                                                                   | 55 |
| Figure 14. | Flow sheet of a typical, state-of-the-art fermentation process for the production of ethanol typically out of corn-starch.....                                                                                              | 56 |
| Figure 15. | The three conventional approaches for CO <sub>2</sub> capture in the fossil fuel power plant industry are defined here in broader terms for use in any CO <sub>2</sub> producing industrial process (Figures 16 to 23)..... | 60 |
| Figure 16. | Post-combustion and oxyfuel-combustion approaches for the capture and concentration of CO <sub>2</sub> in combustion processes for stream 1 in Figure 4.....                                                                | 61 |
| Figure 17. | Pre-combustion approaches for the capture and concentration of CO <sub>2</sub> in the coal gasification industry for stream 1 in Figures 5 and 6.....                                                                       | 62 |
| Figure 18. | Post-combustion, pre-combustion, and oxyfuel combustion approaches for capture and concentration of CO <sub>2</sub> in the stainless steel industry for the streams 1 through 4 defined in Figure 7.....                    | 63 |
| Figure 19. | Post-combustion and oxyfuel-combustion approaches for capture and concentration of CO <sub>2</sub> in the cement and lime industry for stream 1 defined in Figure 8.....                                                    | 64 |
| Figure 20. | Pre-combustion and post-combustion approaches for capture and concentration of CO <sub>2</sub> in the ammonia manufacture industry for streams 1 through 4 in Figure 9.....                                                 | 65 |



|                                                                                                                                                                                                                                                                                                                              |    |
|------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|----|
| Figure 21. Pre-combustion approach for capture and concentration of CO <sub>2</sub> in the natural, coal, and landfill gas industries for stream 1 defined in Figures 10 and 13.....                                                                                                                                         | 66 |
| Figure 22. Post-combustion and pre-combustion approaches for capture and concentration of CO <sub>2</sub> in the aluminum industry for the streams 1 and 2 defined in Figure 12.....                                                                                                                                         | 67 |
| Figure 23. Post-combustion approach for capture and concentration of CO <sub>2</sub> in the ethanol production industry for stream 1 defined in Figure 14. ....                                                                                                                                                              | 68 |
| Figure 24. Flow diagram representing a CO <sub>2</sub> separation and concentration step for streams in Figures 16, 18, 19 and 22 that contain N <sub>2</sub> , O <sub>2</sub> , CO or CH <sub>4</sub> as permanent gases (PG) in addition to CO <sub>2</sub> . ....                                                         | 68 |
| Figure 25. Flow diagram representing a CO <sub>2</sub> separation and concentration step for streams in Figures 17, 18, 20 and 22 that contain N <sub>2</sub> , O <sub>2</sub> , CO or CH <sub>4</sub> as permanent gases (PG) as well as significant concentrations of H <sub>2</sub> in addition to CO <sub>2</sub> . .... | 69 |
| Figure 26. Flow diagram representing a CO <sub>2</sub> separation and concentration step for streams in Figure 21 that contain N <sub>2</sub> , O <sub>2</sub> , CO or CH <sub>4</sub> as permanent gases (PG) as well as sulfur bearing compounds (e.g, H <sub>2</sub> S, COS, etc.) in addition to CO <sub>2</sub> .....   | 70 |

## **FOREWORD**

The Vision2020 Technology Partnership, an industry-led organization for accelerated innovation and technology development, formed a committee to identify research and development needs for separation technology to drive equilibrium processes for the Chemical and Petrochemical Industry. This committee was established in June 2004 and chartered with the responsibility to define the drivers and R&D requirements of the chemical and petrochemical industries for equilibrium separations. Several chemical production processes were selected for review and two topics, hydrogen and carbon dioxide separations, were developed into full studies. This report, the second of two, is directed to commercial, industrial CO<sub>2</sub> production.

## **EXECUTIVE SUMMARY**

A Chemical Industry Vision 2020 sub-committee was established in June 2004 and chartered with the responsibility of identifying research and development needs for separation technology to drive equilibrium processes for the Chemical and Petrochemical Industry. This report, the second in a series, is designed to summarize and present recommendations for improved CO<sub>2</sub> separation technology for industrial processes. The first report on hydrogen manufacture and separation has been published as a review article and as a DOE report [1].

This report provides an overview of 1) the principal CO<sub>2</sub> producing processes, 2) the current commercial separation technologies and 3) emerging adsorption and membrane technologies for CO<sub>2</sub> separation, and makes recommendations for future research. Current industrial practices are summarized with the use of flow sheets. The overall goal of this review is to foster the development of new adsorption, absorption, and membrane technologies to improve manufacturing efficiency and reduce CO<sub>2</sub> emissions. This study focuses on the chemical and petrochemical industries.

The need for improving the energy intensive separation processes involving CO<sub>2</sub> are well recognized. The U.S. Department of Energy has shown that the separation of CO<sub>2</sub> represents 75% of the overall cost associated with its separation, storage, transport, and sequestration. The growing concern about global warming is placing greater demand on improving energy efficiency and reducing CO<sub>2</sub> emissions.

Energy efficient CO<sub>2</sub> separation technologies with improved economics are needed for industrial processing and for future options to capture and concentrate CO<sub>2</sub> for reuse or for sequestration. A very small portion (0.2%) of U.S. CO<sub>2</sub> emissions is separated for industrial or commercial use. Hence, other means besides CO<sub>2</sub> consumption must be considered to mitigate the CO<sub>2</sub> emissions. There are many programs outside the scope of this report addressing these issues (e.g. new power plant design, Kyoto protocol, carbon tax structure, sequestration).

Recommendations are set-forth for future R&D in CO<sub>2</sub> separation and recovery for both near-term (i.e., 0 – 5 years) and longer-range (i.e., 7 – 15 years) research. Flow sheets of existing CO<sub>2</sub> producing processes are provided for guidance and new conceptual flow sheets have also been designed.

The recommendations of this Vision 2020 Chemical Industry team are summarized below. In reviewing this section, please be patient as a summary of recommendations can, at times, appear rather apparent. Full details including scope of scientific space to be explored and justifications are provided in the report starting on page 31.

For near-term adsorbent development:

- 1) Develop high-capacity, 3-4 mol/kg, CO<sub>2</sub>-selective adsorbents to operate at elevated temperatures and pressures in the presence of sulfur and steam.

For near-term membrane development:

- 1) Develop CO<sub>2</sub> permselective polymeric glassy or rubbery membranes with CO<sub>2</sub>/H<sub>2</sub> selectivity of >15-20, with high flux and high temperature stability.
- 2) Specific Goal: Develop polymeric glassy or rubbery membranes for CO<sub>2</sub>/CH<sub>4</sub> that have selectivity > 50, double the current commercial membrane CO<sub>2</sub> flux, resists plasticizing and is stable to heavy oil.
- 3) Develop CO<sub>2</sub> permselective facilitated transport membranes that can operate in the absence of water for long periods of time.
- 4) Develop CO<sub>2</sub> permselective inorganic membranes with selectivity of > 15-20.
- 5) Develop CO<sub>2</sub> permselective selective surface flow membranes with higher CO<sub>2</sub> selectivity with H<sub>2</sub>, N<sub>2</sub>, and CH<sub>4</sub>.
- 6) Develop CO<sub>2</sub> permselective hybrid mixed-matrix membranes with improved selectivity, permeance, and stability.
- 7) Develop CO<sub>2</sub> permselective hollow fiber membrane contactors with improved permeance and stability.

For near-term adsorption process development:

- 1) Develop new pressure swing adsorption (PSA) cycle designs that take advantage of new or existing CO<sub>2</sub> selective adsorbents; possibly temperature swing adsorption (TSA) or PSA/TSA hybrid cycles. For example, develop new PSA cycles that take advantage of the heavy reflux concept, where a pure heavy product like CO<sub>2</sub> is more desirable than pure light product such as H<sub>2</sub>.
- 2) Improve efficiency for thermal management in the design of TSA and PSA/TSA hybrid cycles. Rethink bed designs for rapid heating and cooling.

For near-term absorbent and absorption process development

- 1) Develop absorbents with improved capacity and greatly improved heat of absorption.
- 2) Develop new regeneration techniques, as opposed to thermal or vacuum regeneration, to be conducted at high pressure.
- 3) Develop absorbents that work on high temperature gases.
- 4) Develop absorbents that are stable to trace contaminants (e.g., amines).
- 5) Develop more selective absorbents, CO<sub>2</sub> over sulfur species, for processes with H<sub>2</sub>S and COS species present (e.g., natural gas and coal bed methane).

For long-term flow sheet augmentation with adsorption and membrane processes:

- 1) Develop hybrid technology for H<sub>2</sub> production (e.g., for steam methane reforming by combining the reactor with a CO<sub>2</sub> selective adsorbent and an H<sub>2</sub> permeable membrane).
- 2) Develop new CO<sub>2</sub> adsorbent and membrane technologies that are amenable to integrated gasification combined cycle (IGCC) and related power and chemical production technologies with CO<sub>2</sub> sequestration as a potential long term objective.

- 3) Specific Goal: Develop hybrid technology, possibly coupled with adsorption or membranes processes, that removes CO<sub>2</sub> by chemical reaction in the chemical process.

For long-term advanced adsorbent materials and process development for CO<sub>2</sub> removal:

- 1) Develop advanced structured adsorbent materials for use in rapid-cycle PSA.
- 2) Develop improved designs for rapid-cycle PSA for CO<sub>2</sub> capture and concentration with both heavy and dual reflux cycles steps.
- 3) Reduce cycle time in rapid PSA to improve throughput - investigate the relationship between adsorbent particle size, surface properties, and accelerated cycle times (i.e., mass transfer limitations).
- 4) Develop TSA and or PSA/TSA hybrid cycles with improved materials - quantify the effect on cycle time and bed sizes for a forced temperature swing/PSA cycle.
- 5) Develop improved CO<sub>2</sub> separations with sorption enhanced reaction processes using PSA, TSA, and hybrid cycles.

For long-term advanced membrane materials for CO<sub>2</sub> removal:

- 1) Develop next generation membrane materials with high selectivity for CO<sub>2</sub> (> 100), operating at high temperatures and pressures and with resistance to fouling and cracking or embrittlement.



## **INTRODUCTION**

The overall goal of this review is to foster the development of new adsorption, absorption, and membrane technologies for CO<sub>2</sub> separation. The underlying economic and environmental drivers are encouraging the development of more energy-efficient CO<sub>2</sub> separation technologies. This report provides an overview of 1) the principal CO<sub>2</sub> producing processes, 2) the current commercial separation technologies, and 3) the emerging adsorption, absorption, and membrane technologies for CO<sub>2</sub> separation, and makes recommendations for future separations research and development.

Carbon dioxide production is ubiquitous in combustion, energy generation and manufacturing processes. Some CO<sub>2</sub> is produced as a by product of chemical manufacturing, while most is produced in the generation of power through the combustion of fossil fuels. The growing concern about global warming is placing greater demands on improving the energy efficiency of processes and on reducing CO<sub>2</sub> emissions. The U.S. Department of Energy has shown that the separation of CO<sub>2</sub> represents 75% of the overall cost associated with its separation, storage, transport, and sequestration. Hence, more energy-efficient CO<sub>2</sub> separation processes are needed.


While reading this report, it is recommended that the following questions be kept in mind:

- What are the generic technologies with the most promise?
- What are the high-level technical issues to be overcome in commercializing a new CO<sub>2</sub> separation technology (e.g., costs, sulfur tolerance)?
- What is the estimated time of development for a new commercial application without additional action?
- What will it take to deliver a new commercial application in 3-5 years?
- What will it take to accelerate these developments?
- What breakthroughs, if any, are needed to accelerate these developments?

These questions constitute the overall focus and direction of this study. Direct answers are dependent on specific applications. This report provides specific recommendations for improving only adsorption, absorption, and membrane technologies for CO<sub>2</sub> separation. Furthermore, recommendations have been developed for certain technologies that might meet the CO<sub>2</sub> separation challenge.

## **CURRENT COMMERCIAL PRACTICES**

This section provides an overview of the sources of CO<sub>2</sub> emissions and CO<sub>2</sub> production processes. Most of the CO<sub>2</sub> emissions originate from the generation of electricity, as shown in Figure 1.

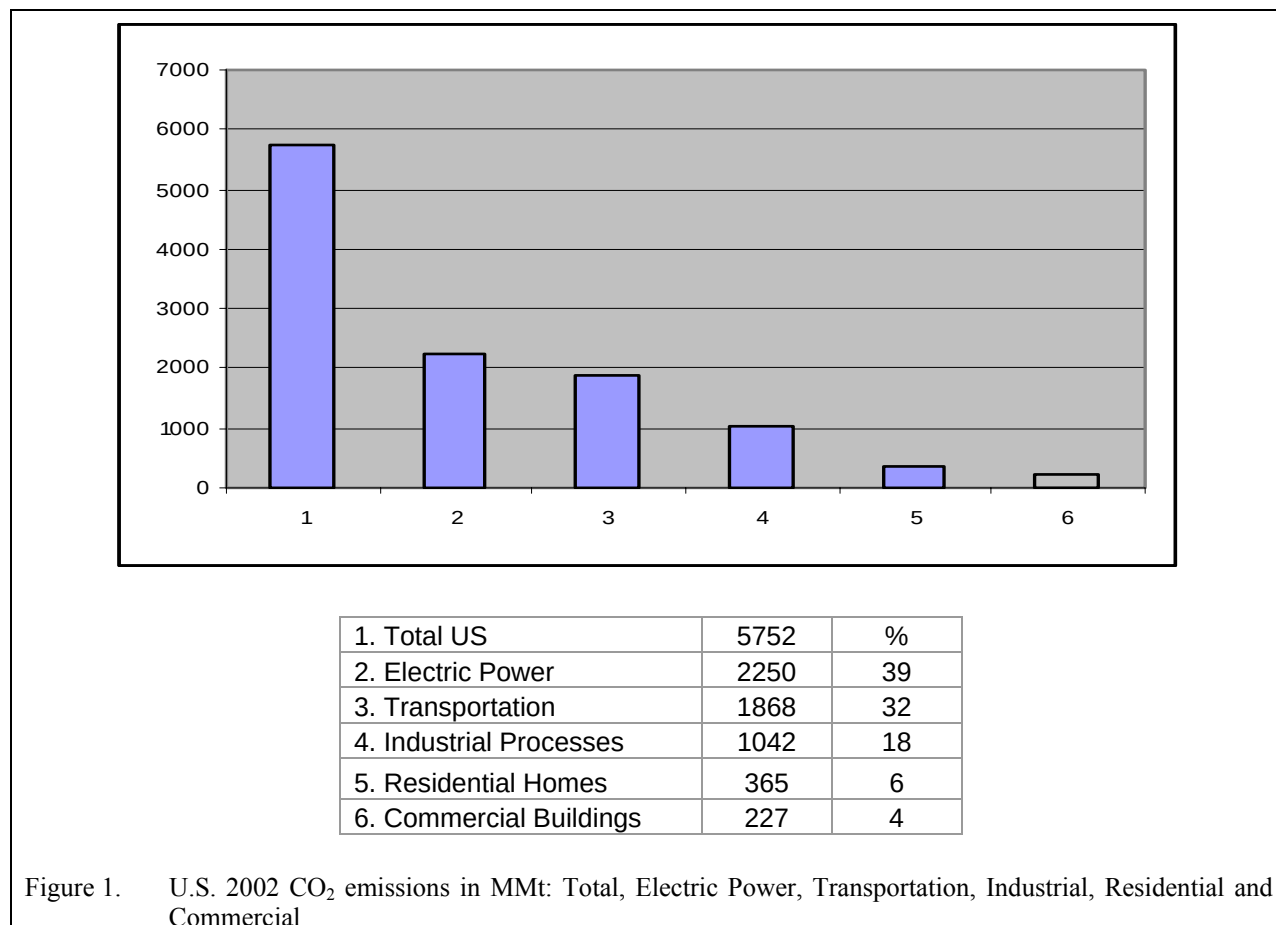

While the focus of this report is on industrial separation technology associated with the purification of gas streams containing CO<sub>2</sub> or the production of CO<sub>2</sub>, an overview of sources CO<sub>2</sub> and environmental emissions is provided in the supportive information section starting on page 38.

The four most widely used, commercial CO<sub>2</sub> removal processes are reviewed. These are absorption, adsorption, membrane, and cryogenic processing. All four processes are commercially important. Absorption is the most prevalent of CO<sub>2</sub> removal methods.

### **Overview of CO<sub>2</sub> Emissions and Production Processes**

The literature on the production and emissions of CO<sub>2</sub> from the chemical and petrochemical industries is rapidly expanding, demonstrating that CO<sub>2</sub> separation and capture technologies are of growing importance. The general concern is that the continued production of CO<sub>2</sub> will




adversely impact global warming [2]. Hence, development efforts are underway to improve the efficiency of production and separation processes and to mitigate CO<sub>2</sub> emissions.

Table 1 (tables begin on page 97) provides a summary of worldwide CO<sub>2</sub> emissions, which in 2004 were estimated at 27,043 million metric tons (MMt), a 26% increase over the 1990 emissions. By 2015 this number is expected to increase by 23% to 33,284 MMt, and by 2025 it is expected to increase by 43% to 38,790 MMt [3]. It is no surprise that CO<sub>2</sub> emissions track very well with population growth, and with the rise of developing countries.

Table 2 summarizes the CO<sub>2</sub> emissions from various U.S. sources in 2002 with a further breakdown for fuel type. In 2002 the U.S. was responsible for 5,752 MMt of CO<sub>2</sub> emissions or about 22% of the world's total. U.S. industrial activities accounted for 1,042 MMt of CO<sub>2</sub> emissions or about 18% of the total. When adding the CO<sub>2</sub> equivalence for the electricity consumed by industry, then industry was responsible for 1,685 MMt of CO<sub>2</sub> or about 29% of the U.S. total. Overall, electric power generation was responsible for 2,250 MMt, or 39% of the total. It is noteworthy that about 98% of the CO<sub>2</sub> emissions were from burning fossil fuels to produce energy. These numbers are shown in Figure 1.

As shown in Table 2 industrial production accounts for 29% of CO<sub>2</sub> emissions. Figure 2, however, reveals that 88% of these emissions are associated with energy generation, steam, etc. Only 11% of industrial emissions are associated with chemical or petrochemical processing.

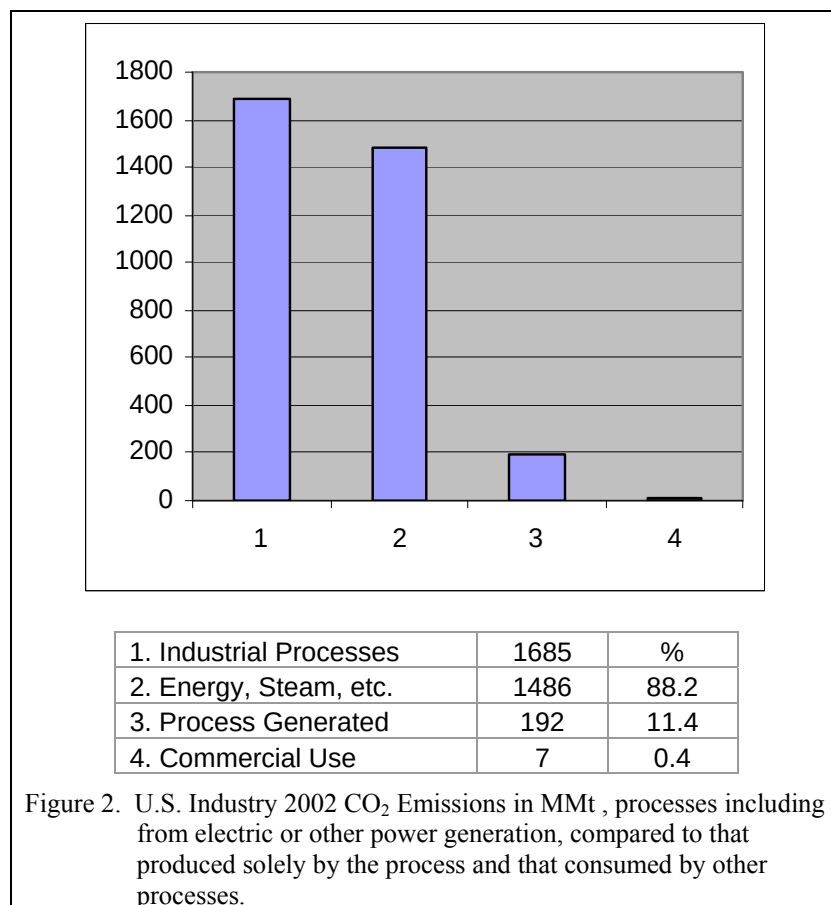

The main sources of commercial CO<sub>2</sub> include synthetic ammonia and hydrogen plants, flue gas from fossil fuel combustion processes, fermentation, lime-kiln operations, sodium phosphate manufacture, and natural gas wells [4]. Table 2 provides a breakdown of the leading industries that produce the most (non-energy related) CO<sub>2</sub> emissions. These industries include iron and steel, cement, ammonia, natural gas, lime and aluminum production. The energy related CO<sub>2</sub> emissions are also given for comparison.

It appears that the CO<sub>2</sub> emissions from the energy generated to support the chemical and petrochemical

industries overwhelms the CO<sub>2</sub> emissions from the actual chemicals or petrochemical processes, 88% vs. 11% (see Figure 2). Table 3 illustrates average point-source (plant) CO<sub>2</sub> emissions for a number of industrial sectors.

A very small portion of the produced CO<sub>2</sub> is recovered for industrial or commercial use. Nevertheless, CO<sub>2</sub> production was nineteenth on the list of the top 50 highest volume chemicals produced in the U.S. in 2004 [5]. The main uses of CO<sub>2</sub> include 1) beverage carbonization, 2) chemical manufacture, 3) firefighting, 4) food freezing and processing, 5) foundry-mold preparation, 6) greenhouses, 7) mining operations, 8) oil well secondary recovery, 9) rubber tumbling, 10) therapeutical work, 11) welding, and 12) extraction processes [4]. Depending on the application, purification of this CO<sub>2</sub> may be required.

Most significantly, of the twelve uses listed above, only in the manufacture of chemicals (#2) is CO<sub>2</sub> consumed (i.e., reacted to form a different carbon-containing chemical). None of the other commercial uses of CO<sub>2</sub> actually consume CO<sub>2</sub>. In fact, it is clear from the CO<sub>2</sub> production and emission numbers (Figure 2) that the industrial consumption of CO<sub>2</sub> constitutes only a negligible fraction of all the CO<sub>2</sub> produced by human activities and it is doubtful that this fact will change in the foreseeable future [6,7]. Hence, other means besides CO<sub>2</sub> consumption must be considered to mitigate the CO<sub>2</sub> emissions from industrial and energy-related sources. There are many programs outside the scope of this report addressing these issues (e.g., new power plant design, Kyoto protocol, carbon tax structure, sequestration).

## **CO<sub>2</sub> Removal Processes**

There are three incentives to remove CO<sub>2</sub> from a process stream. First, and in most cases, CO<sub>2</sub> is being removed from a valuable product gas, such as H<sub>2</sub>, where it is eventually emitted to the atmosphere as a waste by-product. Second, CO<sub>2</sub> is recovered from a process gas, such as in ethanol production, as a saleable product. However, as mentioned above, only a modest fraction of the CO<sub>2</sub> produced is marketed as a saleable product, and much of this CO<sub>2</sub> finds its way to the atmosphere because the end use does not consume the CO<sub>2</sub>. Third, CO<sub>2</sub> is recovered simply to prevent it from being released into the atmosphere, but, this necessarily requires sequestration of the recovered CO<sub>2</sub>. In spite of the Kyoto Protocol and potential penalties and taxes associated with CO<sub>2</sub> emissions, there is little if any use of commercially available CO<sub>2</sub> capture processes for this purpose. At the moment these processes are simply too expensive to use, and in most cases there is no place to put the CO<sub>2</sub> once it is captured.

Processes to remove CO<sub>2</sub> from gas streams vary from a simple once-through wash or treatment operations to complex multistep recycle systems. Most of these processes were developed for natural gas sweetening or H<sub>2</sub> recovery from syngas. Recently, interest has built on the capture of CO<sub>2</sub> from flue gas, and even landfill gas and coal bed methane gas. Natural gas, flue gas, landfill gas, and coal bed methane gas systems are more complex than the typical H<sub>2</sub> system. Along with CO<sub>2</sub>, other contaminants generally must be removed or handled. Among these are particulates, H<sub>2</sub>O, N<sub>2</sub>, H<sub>2</sub>S, and C<sub>2</sub>+ hydrocarbons and trace elements in various oxidation states. In addition, flue gas, coal bed methane and some landfill gases contain O<sub>2</sub> that can interfere with certain CO<sub>2</sub> separation systems. This complication is generally not present in natural gas, most landfill gas, or H<sub>2</sub> systems. For these reasons, commercial CO<sub>2</sub> gas treatment plants are usually

integrated gas processing systems; few are designed simply for CO<sub>2</sub> removal.

Four different CO<sub>2</sub> removal technologies are widely practiced in industry. These are 1) absorption, both chemical and physical, 2) adsorption, 3) membranes, and 4) cryogenic processes [8]. Tables 4 and 5 provide information on CO<sub>2</sub> removal technologies in terms of the number of patents and or peer-reviewed articles published by a company or research team since 1995 and since 2005. Table 6 lists the licensors of CO<sub>2</sub> separation processes as of 2004 [9].

### ***Absorption Processes***

The overwhelming majority of CO<sub>2</sub> removal processes in the chemical and petrochemical industries take place by absorption (see Table 6). The chemical process industries (CPI) removes CO<sub>2</sub> to meet process or product requirements (e.g., the production of natural gas requires the removal of CO<sub>2</sub> in order to be effectively utilized). Other examples include the removal of CO<sub>2</sub> from the circulating gas stream in ammonia manufacture or ethylene oxide manufacture.

A variety of liquid absorbents are being used to remove CO<sub>2</sub> from gas streams. Absorption processes generally can be divided into two categories. Processes where the solvent chemically reacts with the dissolved gas are referred to as chemical absorption processes. For these applications alkanolamines are commonly used as reactive absorbents.

Physical absorption processes are those where the solvent only interacts physically with the dissolved gas. Here a solvent is used as an absorbent with thermodynamic properties such that the relative absorption of CO<sub>2</sub> is favored over the other components of the gas mixture. Some commonly used physical solvents are methanol (Rectisol Process) and glycol ethers (Selexol Process).

In many industrial applications, combinations of physical solvents and reactive absorbents may be used in tandem. Table 7 lists the most widely used absorbents. These include monoethanolamine (MEA), diethanolamine (DEA), diisopropanolamine (DIPA), methyldiethanolamine (MDEA), and diglycolamine (DGA). Ammonia and alkaline salt solutions are also used as absorbents for CO<sub>2</sub>. Water is used as a CO<sub>2</sub> absorbent, but only at high pressures where solubility becomes appreciable. However, in all cases solvent recycling is energy and capital intensive.

Tables 7 and 8 compare key properties of some of the important alkanolamines used in acid gas treating. Ethanolamine has the highest capacity and the lowest molecular weight. It offers the highest removal capacity on either a unit weight or a unit volume basis.

Table 8 also lists the major types of CO<sub>2</sub> and acid gas absorption processes that are commonly used in gas treating. Of the CO<sub>2</sub> producing processes listed above, natural gas, H<sub>2</sub>, syngas, and NH<sub>3</sub> production, as well as coal gasification, utilize absorption processes for removing CO<sub>2</sub> and or acid gases. As far as the authors are aware, the use of CO<sub>2</sub> scrubbers for the production of CO<sub>2</sub> from the iron and steel, cement, lime, and aluminum industries and from combustion is virtually non-existent.

Natural gas is treated to remove the acid gas constituents ( $\text{H}_2\text{S}$  and  $\text{CO}_2$ ) by contacting the natural gas with an alkaline liquid. The most commonly used treating solutions are aqueous solutions of the ethanolamines or alkali carbonates, although a considerable number of other treating agents have been developed in recent years, as illustrated in Tables 6 to 8. Most of the newer treating agents rely on a combination of physical absorption and chemical reaction. When only  $\text{CO}_2$  is to be removed in large quantities, or when only partial removal is necessary, a hot carbonate solution or one of the physical solvents is economical preferred.

MEA has good thermal stability, but reacts irreversibly with COS and  $\text{CS}_2$ . In addition to the main desired, readily-reversible product, ammonium bicarbonate, MEA also reacts with  $\text{CO}_2$  to give a series of products that lead to slow losses of this alkanolamine. More serious is the MEA loss by evaporation. Its vapor pressure is much higher than those of the other compounds in Table 7. Thus, using MEA to meet pipeline specifications for  $\text{H}_2\text{S}$  may be difficult.

DEA has a lower capacity than MEA and it reacts more slowly. Although its reactions with COS and  $\text{CS}_2$  are slower, they lead to different products that cause fewer filtration and plugging problems. Triethanolamine has been almost completely replaced in sour gas treating because of its low reactivity toward  $\text{H}_2\text{S}$ . Diglycolamine has the same reactivity and capacity as DEA, with a lower vapor pressure and lower evaporation losses.

DIPA is used in the Sulfinol and Shell Adip processes to treat gas to pipeline specifications. DIPA can remove COS and is selective for  $\text{H}_2\text{S}$  removal over  $\text{CO}_2$  removal. MDEA selectively removes  $\text{H}_2\text{S}$  in the presence of  $\text{CO}_2$ , has good capacity, good reactivity, and very low vapor pressure. As a result, MDEA is a preferred solvent for gas treating.

By-product  $\text{CO}_2$  from  $\text{H}_2$ , syngas and  $\text{NH}_3$  production via methane stream reforming is recovered using hot carbonate absorption or MEA absorption. The hot carbonate systems used in many ammonia plants typically afford 95-97 vol%  $\text{CO}_2$  byproduct. MEA systems generally are capable of recovering a  $\text{CO}_2$  stream that is 99.5+ vol% pure. Indeed, saleable  $\text{CO}_2$  is being recovered from  $\text{H}_2$ , syngas and  $\text{NH}_3$  production plants, where absorption processes are being used. Here the scrubber delivers a high-purity  $\text{CO}_2$  product which requires little, if any, further purification.

Coal gasification to produce syngas (mostly  $\text{CO} + \text{H}_2$ ) also yields some  $\text{CO}_2$  that generally must be removed before using the syngas (e.g., for making methanol or acetic acid). If water gas shift is used to make more  $\text{H}_2$ , the by-product is additional  $\text{CO}_2$ . Also, for synthetic natural gas (SNG) production via coal gasification followed by methanation, some  $\text{CO}_2$  is recovered. Recovery of the  $\text{CO}_2$  requires treating a gas stream rich in  $\text{CH}_4$  and  $\text{H}_2\text{O}$ . Absorption processes similar to those used in  $\text{H}_2$ , syngas and  $\text{NH}_3$  production also are used in coal gasification.

Flue gas from combustion processes associated with burners, flaring, incineration, utility boilers, etc. contain significant amounts of  $\text{CO}_2$ . However, as discussed above, this  $\text{CO}_2$  is generally of low quality because its concentration tends to be low, the flue gas is very hot, and it contains a variety of other gaseous species and particulates that make  $\text{CO}_2$  recovery difficult and expensive. Nevertheless,  $\text{CO}_2$  is being recovered from flue gas for commercial use [9]. A train of separation and purification equipment is being used, with the  $\text{CO}_2$  being removed via MEA absorption

technology, which was developed in the 1970s and 1980s for enhanced oil recovery [8].

Fluor Enterprises Inc. has 24 Econamine FG plants operating worldwide and producing a saleable CO<sub>2</sub> product for both the chemical and food industries. Randall Gas Technologies, ABB Lummus Global Inc. has four installations of similar technology operating on coal fired boilers. Two of these plants produce chemical grade CO<sub>2</sub> and the other two plants produce food grade CO<sub>2</sub>. Mitsubishi Heavy Industries Ltd. also has commercialized a flue gas CO<sub>2</sub> recovery process, based on their newly developed and proprietary hindered amine solvents (KS-1, KS-2 and KS-3). As of April 2005, they have agreed to license two KD CDR Process<sup>1</sup> plants to a fertilizer company in India. Each plant can capture 450 metric tons per day of CO<sub>2</sub>, making them the world's largest CO<sub>2</sub> recovery plants. It appears that these are the only examples of marketing flue gas CO<sub>2</sub> recovery technology.

With CO<sub>2</sub> emissions becoming more of a concern worldwide, and with absorption processes dominating CO<sub>2</sub> removal from industrial streams, the literature on the subject of CO<sub>2</sub> removal has grown substantially in the last few years. A review of the recent literature identified about 230 articles since 2000. Table 9 lists the number of papers and the corresponding absorbent that was studied. Although other reactive absorbents are represented, the family of amines is clearly dominant. It is noteworthy that a recent review article on this subject was not found during this search. Clearly, a review of the recent literature on absorption processes for the removal of CO<sub>2</sub> and other acid gases from process streams would be quite valuable.

### ***Adsorption Processes***

Only a few classes of adsorbents and adsorption processes are being used to remove CO<sub>2</sub> from gas streams. These adsorbents include aluminosilicate zeolite molecular sieves, titanosilicate molecular sieves, and activated carbons. CO<sub>2</sub> adsorption capacities of typical commercial adsorbents are given in Table 10. Other classic adsorbents are being used to remove contaminants from CO<sub>2</sub> streams destined for commercial use. In this case, the adsorbents include activated carbons for sulfur compounds and trace contaminant removal, silica gels for light hydrocarbon removal, and activated aluminas, bauxite, and silica gels for moisture removal. The adsorption processes include pressure swing adsorption (PSA), temperature swing adsorption (TSA), and hybrid PSA/TSA. Of the CO<sub>2</sub> producing processes listed above, only H<sub>2</sub>, syngas, NH<sub>3</sub>, fermentation ethanol, natural gas, and combustion are beginning to use adsorption processes for removing or purifying CO<sub>2</sub>.

By-product CO<sub>2</sub> from H<sub>2</sub> production via methane stream reforming is recovered using PSA in lieu of absorption. In the early 1980s, new H<sub>2</sub> plants were being built with PSA units as the main H<sub>2</sub> purification process. This eliminated the CO<sub>2</sub> scrubber, the low temperature CO shift reactor and the methanation reactor. The PSA unit offers advantages of improved H<sub>2</sub> product purity (99-99.99 vol% H<sub>2</sub>, 100 ppmv CH<sub>4</sub>, 10-50 ppmv carbon oxides, and 0.1-1.0 vol% N<sub>2</sub>) with capital and operating costs comparable to those of wet scrubbing.

Modern PSA plants for H<sub>2</sub> purification generally utilize layered beds containing 3 to 4 adsorbents (e.g., silica gel or alumina for water, activated carbon for CO<sub>2</sub>, and 5A zeolite for

---

<sup>1</sup> Kansai-Mitsubishi proprietary Carbon Dioxide Recovery Process

CH<sub>4</sub>, CO, and N<sub>2</sub> removal). Depending on the production volume requirements, from four to sixteen columns are used in tandem. The PSA unit is operated at ambient temperature with a feed pressure ranging between 20 and 60 atm. Hydrogen recovery depends on the desired purity, but ranges between 60 and 90%, with the tail gas (i.e., the desorbed gas containing H<sub>2</sub>O, N<sub>2</sub>, CO<sub>2</sub>, CH<sub>4</sub>, CO, and H<sub>2</sub>) generally being used as fuel for the reformer.

Although PSA systems are increasingly used for H<sub>2</sub> recovery, they yield a by-product CO<sub>2</sub> stream that is only about 50 vol% pure. Low purity makes this tail gas stream less attractive as a commercial CO<sub>2</sub> source. PSA systems are under development to process this tail gas into H<sub>2</sub> and CO<sub>2</sub> rich streams, as discussed later in the *Emerging Literature Concepts* section (see page 12).

Fermentation to produce ethanol has recently emerged as a major source of CO<sub>2</sub> by-product for industrial use. The crude by-product is typically 99.8% pure CO<sub>2</sub> on a dry basis. But the product is wet (saturated with water at ambient temperature) and not odor-free. After recovery, the CO<sub>2</sub> is usually washed with a simple water scrubber to remove water soluble compounds. It is then treated with activated carbon to remove traces of H<sub>2</sub>S, SO<sub>2</sub>, and organics. The gas is finally dried with activated alumina, bauxite, or silica gel before compression and cooling to the liquid or solid form. When destined for large-scale industrial use (urea, enhanced oil recovery, industrial inerting, etc.), the purification is not as exacting as it is for food grade CO<sub>2</sub>.

The composition of natural gas varies widely depending on the location of the well. Since landfill gas and coal bed methane gas are somewhat similar in composition to natural gas, they are included here for convenience. The CO<sub>2</sub> concentration in natural gas varies between 3 and 40 vol%; but it could be as high as 80 vol%. Because of the complexity and variability of the composition of natural gas, a train of separation processes, including adsorption, absorption, and cryogenic and membrane separation, may be used to process it into pipeline quality methane. CO<sub>2</sub> traditionally has been removed using an amine-based scrubbing process, as described in detail above. However, PSA technology is beginning to supplant some of the absorption technology in natural gas treatment, especially in the so called shut-in natural gas wells that previously contained too much N<sub>2</sub> to justify processing. The molecular gate adsorption technology commercialized by Engelhard Corporation uses a titanasilicate adsorbent combined with a PSA process in a vacuum swing adsorption mode to remove N<sub>2</sub> and/or CO<sub>2</sub> from natural gas streams. Two of these units were in operation as of 2004 [9].

To remove CO<sub>2</sub> from coal bed methane, Engelhard Corporation uses molecular gate adsorption technology with a more traditional PSA mode with compressed feeds ranging in pressure from 80 to 800 pounds per square inch gauge (psig) [10]. Ten of these units are being built and three are in operation for upgrading methane from abandoned coal mines [10]. Similarly, Axens has commercialized natural gas purification technology, based on alumina and zeolite molecular sieve adsorbents and a TSA regeneration mode. The alumina removes trace and bulk contaminants in the natural gas other than CO<sub>2</sub> through both chemisorption and physisorption mechanisms. The zeolite molecular sieve serves to remove CO<sub>2</sub> and other contaminants via physisorption. Axens has over 60 installations operating worldwide that treat a variety of natural gas and industrial process streams [9].

The recovery of CO<sub>2</sub> from flue gas by adsorption technology is not commonly practiced by

industry. The only example was obtained from a recent report in the literature that indicated CO<sub>2</sub> is being recovered from flue gas commercially using a layered PSA bed containing X and A type zeolites and activated carbon in Japan [11]. Neither the flow sheet nor the purity of the recovered CO<sub>2</sub> is known; but, the CO<sub>2</sub> appears not to be used for commercial applications.

### ***Membrane Processes***

In general, membrane technology for separating gas streams is attractive for many reasons [12-19]. First, it neither requires a separating agent nor involves phase changes. As a consequence, the elevated processing costs associated with regeneration and phase change are eliminated. In addition, membrane systems involve small footprints compared to other processes and require low maintenance. They are also compact and lightweight and can be positioned either horizontally or vertically, which is especially suitable for retrofitting applications. Finally, the modular aspect of membrane units allow for multi-stage operation and linear scale up costs.

Membranes are an appealing option for CO<sub>2</sub> separation, mainly because of the inherent permeating properties of this species. CO<sub>2</sub> is a very small gas molecule, with a smaller kinetic radius (i.e., 3.3 Angstrom units (Å)) than lighter gases, such as O<sub>2</sub> (3.46 Å), N<sub>2</sub> (3.64 Å) and CH<sub>4</sub> (3.8 Å). In fact, among permanent gases, only He (2.59 Å) and H<sub>2</sub> (2.89 Å) are smaller than CO<sub>2</sub>. Hence, CO<sub>2</sub> is a fast diffusing gas in many membrane materials, such as glassy and rubbery polymers, molecular sieves, and several other inorganic materials. On the other hand, CO<sub>2</sub> also has a relatively high molecular weight and a large quadrupole moment, enabling it naturally to adsorb more strongly to or dissolve at much higher concentrations in these membrane materials compared to many other gas species. These properties give rise to very high CO<sub>2</sub> permeation rates and selectivities over many other gas species, sometimes even higher than H<sub>2</sub> and He.

Membrane systems potentially or actually commercialized for gas separations are listed in Tables 4 and 5, with the number commercialized given in Table 6. Of the CO<sub>2</sub> producing processes listed above, only natural gas production, to a lesser extent landfill gas production, and H<sub>2</sub>, syngas, and NH<sub>3</sub> production are beginning to use membrane processes for removing or purifying CO<sub>2</sub>.

The first commercial cellulose acetate membrane units for CO<sub>2</sub> removal from natural gas were implemented only few years after the introduction in 1980 of the first commercial PRISM membrane air separation system developed by Monsanto [14,15]. By the end of the 1980s companies such as Natco (Cynara), UOP (Separex) and Kvaerner (Grace Membrane Systems) were producing membrane plants for this purpose. A few years later, more selective polyimides and only recently polyaramides were slowly introduced to displace the old cellulose acetate systems. Today, commercial membrane technology for CO<sub>2</sub> separation is largely based on glassy polymeric materials (cellulose acetate, polyimides, and polyaramides).

Currently, the membrane market devoted to CO<sub>2</sub> separation from natural gas is about 20%, which is only 2% of the total separations market for natural gas. Amine-based absorption processes dominate this market, as shown in Table 6. Membranes are used in situations where the produced gas contains high levels of CO<sub>2</sub>. However, a key sensitivity with these current membranes is that they must be protected from the heavier C<sub>5+</sub> hydrocarbons present in wet

natural gas streams. Exposure to these compounds immediately degrades performance and can cause irreversible damage to the membranes.

Membranes for large-scale recovery of CO<sub>2</sub> from, for example, natural gas for use as a salable product are a relatively recent development. As gleaned from above, current membranes have been designed generally to remove unwanted CO<sub>2</sub> from a desired product, rather than to recover CO<sub>2</sub> for its own value. The advent of enhanced oil recovery (EOR) projects using CO<sub>2</sub> has changed this situation. Natural gas fields in West Texas now recover CO<sub>2</sub> that is pipelined to areas where it is needed for EOR. A variety of membranes, including ones with separating layers made of cellulose acetate, polysulfone, and polyimide, are used for this purpose. Air Products and Chemicals and Ube are marketing membrane systems for EOR and landfill gas upgrading, respectively.

Membrane units have also been commercialized for H<sub>2</sub> purification in reforming processes (UOP, Air Products and Chemicals). For example, membrane processes, such as the Polysep membrane systems developed by UOP and the PRISM membrane systems developed by Monsanto and now sold by Air Products and Chemicals [9] recover H<sub>2</sub> from various refinery, petrochemical, and chemical process streams. Both are based on polymeric asymmetric membrane materials composed of a single polymer or layers of at least two different polymers, with the active polymer layer being a polyimide. The PRISM system is based on a hollow fiber design and Polysep is a spiral-wound, sheet-type contactor. Both are used to recover H<sub>2</sub> from refinery streams at purities ranging from 70 to 99 vol% and with recoveries ranging from 70 to 95%. Relatively pure H<sub>2</sub> containing a very low concentration of CO<sub>2</sub> leaves these units in the low pressure permeate stream. This stream can be sent to a methanator for CO<sub>2</sub> removal and further purification. The high-pressure retentate stream, consisting of H<sub>2</sub> and CO<sub>2</sub> with low concentrations of CO and CH<sub>4</sub>, can be used as fuel.

### ***Cryogenic Liquefaction Processes***

Recovery of CO<sub>2</sub> by cold liquefaction has the advantage of enabling the direct production of very pure liquid CO<sub>2</sub>, which can be readily transported. Liquefaction is achieved by the dual action of external refrigeration and the Joule-Thompson effect that results from the compression and adiabatic expansion of the stream. The disadvantages associated with the cryogenic separation of CO<sub>2</sub> are the amount of energy required in refrigeration, particularly in dilute gas streams, and the requirement to remove gases, such as water and heavy hydrocarbons, that tend to freeze and block the heat exchangers.

Liquefaction technology for CO<sub>2</sub> recovery is still incipient. Cryogenic CO<sub>2</sub> recovery is typically limited to streams that contain high concentrations of CO<sub>2</sub>, with a lower limit of about 50 vol%, but with a preferred concentration of > 90 vol%. It is not considered to be a viable CO<sub>2</sub> capture technology for streams that contain low concentrations of CO<sub>2</sub>, which includes most of the industrial sources of CO<sub>2</sub> emissions. Cryogenic separation of CO<sub>2</sub> is most applicable to high-pressure gas streams, like those available in precombustion and oxyfuel combustion processes [2]. One exception is for the production of ethanol through fermentation. In fact, liquefaction is generally practiced in this case to produce a highly pure liquid CO<sub>2</sub> product. Details about this cryogenic CO<sub>2</sub> process are not readily available, however.



Nevertheless, cryogenic CO<sub>2</sub> recovery is increasingly being used commercially for purification of CO<sub>2</sub> from streams that already have high CO<sub>2</sub> concentrations (typically > 90%). Of the CO<sub>2</sub> producing processes listed above, only ethanol production and H<sub>2</sub>, syngas, and NH<sub>3</sub> production utilize (or are beginning to utilize) cryogenic processes for removing or purifying CO<sub>2</sub>. Tables 4 and 6 provide some information on the cryogenic systems that are described in the literature.

Currently, Costain Oil, Gas & Process Ltd. has commercialized a CO<sub>2</sub> liquefaction process with around seven units installed worldwide. The process is assisted by membrane technology to treat streams with CO<sub>2</sub> fractions greater than 90 vol%. Recently, Fluor Enterprises Inc. also developed a CO<sub>2</sub> liquefaction process called CO<sub>2</sub>LDSEP. This technology exploits liquefaction to separate CO<sub>2</sub> from H<sub>2</sub> and other gases in the tail gas of a H<sub>2</sub> purification PSA unit. However, no commercial operational units of this technology have been reported.

### **Summary of Current Commercial Practices**

The four most widely used commercial CO<sub>2</sub> removal processes are: absorption, adsorption, membranes, and cryogenic processing. Absorption is by far the most prevalent CO<sub>2</sub> removal process. An overview of the sources of CO<sub>2</sub> emissions and CO<sub>2</sub> production processes is provided to exemplify that although most of the CO<sub>2</sub> emissions are from the generation of electricity, industrial point sources can be significant. For a more detailed review of CO<sub>2</sub> emissions and sources, see *Supportive Information on Environmental CO<sub>2</sub> Emissions* section on page 38.

This report is designed to promote the development of new adsorption, absorption, and membrane technologies for CO<sub>2</sub> recovery and capture from commercial processes. Special emphasis has been placed on fostering the development of separation technologies that are economically sound and effective under the operating conditions of CO<sub>2</sub>-producing processes. The uses of adsorption, absorption, and membrane processes in CO<sub>2</sub> removal from industrial process streams are reviewed. Emerging concepts for new approaches in separation are highlighted in the next section of this report; some of the information dates back a few decades. That section is followed by recommendations for future R&D.

## **EMERGING LITERATURE CONCEPTS**

The goal of this report is to achieve energy savings and to improve CO<sub>2</sub> separation process performance and economics. To set forth recommendations for future R&D on CO<sub>2</sub> removal processes, key factors must be considered: 1) the large scale and conditions of industrial production, 2) materials requirements, 3) economic goals and drivers, and 4) purity demands of gases involved. To this end, emerging literature concepts in adsorption and membrane technology for CO<sub>2</sub> removal are reviewed and recommendations are set forth for future R&D. Valuable guidance for this report has been provided by the Vision 2020 committee of industrial scientists active in the field and leading academic scientists referenced at the beginning and end of this report.

For this review, a focus has been placed on emerging concepts in the separation sciences to overcome the limitations of current CO<sub>2</sub> removal processes. The potential for novel adsorbents and membranes and associated processes are outlined. Many opportunities are identified, including hybrid systems that have the potential for significant improvement in separation technology.

### **Adsorption**

The emerging literature concepts on the use of adsorbents and adsorption processes in the chemical and petrochemical industries that produce CO<sub>2</sub> have focused on a few processes. These include the H<sub>2</sub>, syngas, and NH<sub>3</sub> production processes, and the natural gas production processes, which include landfill gas and coal bed methane gas. Emerging literature concepts on the use of adsorbents and adsorption processes to remove CO<sub>2</sub> from flue gas generated from fossil fuel combustion also have been identified. A survey of the recent literature in these areas is given below. The latest developments in PSA and TSA process refinements, sorption enhanced reaction processes (SERP) or periodic adsorptive separating reactors, and selective adsorbents for CO<sub>2</sub> are discussed. The concepts presented in these studies have the potential for both near-term and longer-term impact on adsorption technology for the removal of CO<sub>2</sub> from industrial process streams. Tables 10 and 11 respectively provide a list of adsorbents and PSA cycle configurations currently being investigated for CO<sub>2</sub> removal.

### ***Adsorption Process Refinements***

Adsorption-based CO<sub>2</sub> separation and capture technologies are based primarily on thermal and pressure swing regeneration processes (i.e., TSA and PSA technologies). These are well known cyclic adsorption processes with many commercialized gas separation and purification applications. The performance, cost, and reliability of the adsorbent used are key to its successful commercial acceptance. Another key to success in both PSA and TSA processes is matching the adsorbent with the cycle configuration.

Major breakthroughs in PSA technology for large-scale H<sub>2</sub> purification and associated CO<sub>2</sub> removal were realized in the early 1970's with the development of a 4-bed, multi-layer PSA process. Modifications to improve separation efficiency have included additional beds, typically 7 to 10 beds [20] as many as 16 beds [21], and tanks for storing intermediate process streams

between cycle stages. Along with these additional beds and tanks came more complex cycle sequencing to achieve higher throughputs with the same or even less volume of adsorbent distributed in the additional beds.

Each bed in a PSA plant undergoes adsorption and regeneration cycle steps. These steps include 1) pressurization, 2) high pressure feed, 3) co-current depressurization, 4) counter-current depressurization, 5) counter-current purge (light reflux), and 6) several equalization (pressurization/depressurization) steps between two beds. Improvements, not only in H<sub>2</sub> purification PSA plants but also in CO<sub>2</sub> concentration and recovery PSA plants, can be realized by 1) further refinement of these cycle steps, 2) addition of new cycle steps, and 3) novel refinement of the cycle sequencing to create a more effective separation processes.

The evolution of H<sub>2</sub> PSA technology is a good example of how simple cycle modifications can have a significant impact on the process performance, and shows that intuition may not always be correct. Whysall and Wagemans of UOP [21] recently demonstrated that the duration of the purge step does not have to be equal to or less than the duration of the adsorption step and, by extending the purge step, the production capacity of a PSA H<sub>2</sub> plant for the first time could exceed 110 Nm<sup>3</sup>/hr using 16 beds. Baksh et al. of Praxair Technology, Inc. [22,23] decreased the number of PSA beds with the judicious use of storage tanks to collect and reuse gas during cycle steps so as to increase H<sub>2</sub> production per unit adsorbent. [23] also shows that the PSA process performance can be improved significantly by first removing N<sub>2</sub> from the feed stream using modified (via cation exchange) X-type zeolite adsorbent, which also advantageously remove CO<sub>2</sub>. Xu and Weist of Air Products and Chemicals [24] modified the pressure equalization steps by using four steps with just six beds, and decreasing the cycle time for pressure equalization between beds [25]. Most of these changes are not obvious but have provided a path way for improved separations.

Sircar and Golden [26] describe several other novel approaches to PSA cycle sequencing for both H<sub>2</sub> purification and simultaneous H<sub>2</sub> and CO<sub>2</sub> purification. The latter PSA cycle involves two interconnected cascades of PSA beds each operating with their own unique cycle sequence and number of beds. The complexity between the different cycle steps in a H<sub>2</sub> purification PSA unit has recently been reported by Waldron and Sircar [27]. Many improved and novel PSA cycle sequences are anticipated for use in CO<sub>2</sub> recovery plants, based on continued industrial and academic research.

Another way to improve the performance of a PSA process is to decrease the cycle time, which allows more gas to be processed using less adsorbent. This is referred to as rapid-cycle PSA. For example, QuestAir recently announced an improved H<sub>2</sub> purification technology employing a rapid-cycle PSA unit with a rotary valve. This technology is planned for installation in the largest liquid H<sub>2</sub> plant in Asia, which will be fabricated in Japan.

Rapid-cycle PSA is not a new concept; however, it required major innovations in process design for handling the gas streams before commercialization became feasible. This innovation has been reported in a series of patents by Keefer and Doman of QuestAir Technologies [28-30] which describe the rotary valve and multi-bed cycle sequencing approaches. The same rapid-cycle PSA concepts based on a rotary valve are now being applied by QuestAir to remove CO<sub>2</sub> from natural gas and landfill gas.

Adsorbent attrition and intraparticle mass transfer effects still limit how rapidly the cycle sequencing can be carried out. This problem partly has been alleviated with the recent development of novel structured adsorbents, incorporating very small commercially available adsorbent particles or crystals, like activated carbons and zeolites, in a support material like a sheet of paper. In this way, the effects of mass transfer and adsorbent attrition are minimized. Structured adsorbent materials are described in the recent patents by Golden et al. of Air Products and Chemicals [31-33], and by Keefer et al. [34].

With the development of a very thin, paper like, structured adsorbent material by QuestAir came the development of a second generation, ultra rapid-cycle PSA H<sub>2</sub> purification system. In this system, a rotary adsorbent bed concept has supplanted the rotary valve concept, with the rotary adsorbent bed being comprised of multiple beds within one cylindrical adsorber unit [35]. This unique configuration has resulted in a very compact PSA unit that can be operated at very short cycle times and thus very high H<sub>2</sub> production rates. ExxonMobil recently partnered with QuestAir Technologies to design and build a rotary bed PSA plant for the recovery of H<sub>2</sub> from the tail gas of a conventional H<sub>2</sub> PSA plant [36]. This rotary adsorbent bed concept is certainly applicable to CO<sub>2</sub> capture and concentration from a variety of process streams. However, further improvements in this technology are required for this application, including the continued development of new structured, multilayered adsorbents, with each layer containing an adsorbent that is selective to one or more of the gases to be separated.

A comprehensive review of relevant studies that deal with removing and concentrating CO<sub>2</sub> from simulated flue and stack gases by various PSA cycles has been given recently by Reynolds and co-workers [37]. Table 11 provides a summary of the performances of these various PSA cycles. All utilize a light, heavy, dual, or even a no reflux PSA cycle configuration, intermixed with various cocurrent and or countercurrent depressurization steps, feed, light product, and heavy product pressurization steps, and null (delay) and pressure equalization steps. Note the heavy and dual (light and heavy) reflux cycle steps have been included to concentrate the heavy component (e.g., CO<sub>2</sub>). H<sub>2</sub> PSA plants, which have been designed specifically for producing a very pure light component (e.g., H<sub>2</sub>), only include a light reflux step. The heavy reflux step, or so called high pressure rinse step, has been introduced in several PSA patents with only limited commercialization. Not surprisingly, the fairly complicated two-cascade PSA system developed by Sircar and Golden [26] utilizes a heavy reflux step in the cascade that produces the concentrated CO<sub>2</sub>; the other cascade uses only the light reflux purge step to produce the high purity H<sub>2</sub>.

In addition, these PSA cycles being studied for removing and concentrating CO<sub>2</sub> from simulated flue and stack gases also utilize 1) a vacuum swing cycle with the high pressure set just above atmospheric pressure and the low pressure set at some vacuum level, or 2) a more conventional pressure swing cycle with the purge or low pressure set at or near atmospheric pressure and the feed set at a higher pressure. To concentrate and recover CO<sub>2</sub> from flue or stack gas, most PSA cycles utilize one or more commercially available adsorbents that exhibit a high capacity for CO<sub>2</sub> at ambient temperature and pressure (e.g., activated carbon, carbon molecular sieve, and X and Y type aluminosilicate zeolites). Some of these cycles also utilize a developmental adsorbent (i.e., a K-promoted hydrotalcite-like (HTlc) adsorbent that exhibits a high capacity for CO<sub>2</sub> at elevated

temperatures (e.g., 300 to 500°C) and ambient pressure).

It is clear from the summary in Table 11 that there are numerous designs for operating PSA processes. This also illuminates the challenge associated with choosing one PSA cycle over another one for a given application. After carefully examining the results summarized in Table 11, in most cases it is still not clear which PSA cycle would be more advantageous. For example, it could easily be reasoned by the expert that it would be inappropriate to use a no reflux cycle or just a light reflux cycle in an attempt to concentrate a heavy component by PSA. But even in this light reflux only case, a particular PSA cycle outperformed a PSA cycle with heavy reflux, depending on many factors like the process conditions, cycle times, bed sizes, adsorbent CO<sub>2</sub> capacity, or even the addition of a light end equalization step [38], all of which are interrelated. So, it appears that a PSA cycle with light reflux for concentrating a heavy component can be considered for separating CO<sub>2</sub>, especially since a light reflux-only PSA cycle reduces the capital and operating costs by avoiding the use of an additional compressor for implementing a heavy reflux step.

Hence, PSA cycle configurations are difficult to predict, understand, and interpret, even for an expert. A better understanding of these heavy and dual reflux cycles through R&D clearly is warranted so that more efficient PSA processes can be developed for current commercial separations and for concentrating CO<sub>2</sub> from stack and flue gases. This is true in regard to both the more conventional multi-bed PSA process and to the new rotary bed process described above.

TSA is also being explored for CO<sub>2</sub> capture and concentration from stack and flue gases. For example, Ding and Alpay [39] used K-promoted HTlc as the adsorbent in a TSA process for CO<sub>2</sub> removal from high temperature streams. In a TSA mode, the adsorbent bed is usually regenerated by using a hot purge gas to effect desorption of CO<sub>2</sub>. This purge gas (e.g., steam) can be any gas that does not adsorb appreciably on the adsorbent at the desorption temperature.

PSA processes are also being developed for CO<sub>2</sub> removal from natural gas [40-42], and even landfill gas [43,44] and coal bed methane [10, 45-48]. For example, Engelhard Corporation developed a PSA process to remove H<sub>2</sub>O, CO<sub>2</sub>, and heavier hydrocarbons from methane using their Molecular Gate adsorbent technology. These adsorbents are comprised of titanium silicate molecular sieves that were originally developed to remove only N<sub>2</sub> from natural gas by kinetic separation. This class of materials was subsequently found to provide uniquely higher kinetic and adsorption selectivities for CO<sub>2</sub> and H<sub>2</sub>O, exceeding those of more traditional aluminosilicate molecular sieves. A typical PSA system using the Molecular Gate adsorbent to separate CO<sub>2</sub> from CH<sub>4</sub> rich gas streams at feed pressures between 100 and 800 psia produces a product stream containing CH<sub>4</sub> at concentrations of > 90 vol%. This commercial technology is able to process gas streams containing up to 30 vol% CO<sub>2</sub> with favorable economics [40,42].

Over the past decade, academic researchers also have focused on the development, understanding, and optimization of new PSA cycle configurations for gas separation and purification. For example, Jiang and co-workers [49] are developing important optimization tools for multi-bed PSA processes, especially for H<sub>2</sub> purification and CO<sub>2</sub> recovery. Process design and fine tuning offers opportunities for significant improvements in the PSA process

performance. However, this work needs to be extended to include the number of beds and all possible cycle steps for robust optimization.

Warmuzinski and Tanczyk [50,51], Lee and coworkers [52-54], Reynolds and co-workers [55], and others are studying the design of multi-layered adsorbent beds through mathematical simulation and bench scale experimentation. Multi-layered beds are the industrial standard; however, very little information has been published on the design and optimization of layered bed PSA processes. Most published work involving the purification of  $H_2$  simply reports the performance of a given layered bed; they do not address optimizing the number of layers, types of adsorbents, or depth of each layer. More PSA R&D is needed in the area of recovering the heavy component, like  $CO_2$ , from a gas streams.

Some very novel PSA cycles were introduced to the literature by Diagne and co-workers in Japan [56-59] followed by the work of McIntyre et al. and Reynolds et al. [60,61]. Both groups are studying PSA cycles to concentrate the heavy component in gas streams. The feed step is maintained at low pressure and the adsorbent bed enriches the gas phase with the heavy component due to desorption [61]. This kind of PSA cycle was first described by Wilson [62] and has recently appeared in two patents [63,64].

These uncommon enriching PSA cycles operate in stark contrast to common stripping PSA cycle configurations. The word “stripping” is used to denote that the feed step is carried out at the high pressure and that the adsorbent strips the heavy component from the gas phase due to selective adsorption, whereas the word “enriching” is used to denote that the feed step is carried out at the low pressure and that the adsorbent bed enriches the gas phase with the heavy component due to desorption [61]. Hence, an enriching PSA cycle functions in a reversed or inverted mode compared to a stripping PSA cycle. It appears that the vast majority (> 99%) of the PSA literature involves only the stripping PSA cycle concept. Hence, very little is known about the operation and performance of an enriching PSA cycle [56-59].

Another novel feature includes feeding a PSA column at intermediate position between the ends of the column. In this mode, the feed can be introduced at high (stripping) or low (enriching) pressure, and light and heavy reflux operations can be carried out simultaneously at the respective ends of the column. This type of PSA process mimics the behavior of a distillation column. Dong et al. [65] borrowed ideas from distillation and applied them to PSA by interconnecting two or more sets of twin columns through side, top, and or bottom ports for feeding, recycling, and or collecting gases. This concept was demonstrated by separating a ternary gas mixture (i.e.,  $CO_2$ - $CH_4$ - $N_2$ ) into three enriched products. In one case activated carbon was used in both sets of columns; in two other cases they used activated carbon in one set of columns and layered 13X zeolite and carbon molecular sieve in the other set of columns. The possibility of treating complex gas streams containing multiple components, such as natural gas, landfill gas, and coal bed methane gas streams, with multiple adsorbents appears feasible with these PSA cycles. Clearly, more research needs to be done with these PSA cycles that mimic multi-component distillation operations.

### ***Sorption Enhanced Reaction (Periodic Adsorptive Separating Reactors)***

Conducting reaction and adsorptive separation in a single fixed bed reactor configuration dates back to 1987, beginning with the work of Vaporciyan and coworkers [66-68]. The general idea is to use the adsorbent to selectively remove one or more of the products formed from an equilibrium limited reaction to shift the equilibrium in favor of increased conversion. The adsorbent is then regenerated with a pressure or temperature swing. Improved adsorbents with greater selectivity, larger working capacity, more rapid adsorption and desorption kinetics, and reduced sensitivity to moisture and other poisons are required for this approach to become of commercial interest. These separation characteristics are required at elevated process temperatures. Because performance of most commercial adsorbents like zeolites, activated carbons, activated aluminas or silica gels is lacking at the higher operating temperatures which is typical of the regeneration conditions, the development of new adsorbents is needed specifically for these high temperature applications.

A team at Air Products and Chemicals has developed adsorptive separating reactors using the SERP process. SERP is a fixed bed process with the reactor containing a mixture of a conventional catalyst and a selective, high-temperature adsorbent. For an equilibrium limited reaction, the adsorbent shifts the equilibrium in favor of higher conversion through Le Chatlier's principal. When the adsorbent becomes saturated with the product, a simple pressure swing in the bed can be used for regeneration.

In a series of patents [69-73] and three publications [74-76], this group discusses a redesign of the methane reforming operation. For this approach a high temperature CO<sub>2</sub> selective adsorbent is mixed with a typical reforming catalyst to conduct the steam methane reforming and water gas shift reactions in one unit and at lower temperatures. Reforming can be practiced at these lower temperatures because of the *in situ* removal of CO<sub>2</sub> [71,73]. Medium purity H<sub>2</sub> production (~95%) was achieved by conducting this SERP process in a water gas shift reactor containing the catalyst and a CO<sub>2</sub> selective adsorbent. The feed for this unit was obtained from a conventional steam methane reformer [77].

In a more general patent, three uses of the SERP concept are discussed [78]. In the first case steam methane reforming is driven using CO<sub>2</sub> and or CO selective adsorbents. In the second case, methane reforming with CO<sub>2</sub> can be revamped by using CO or H<sub>2</sub> selective adsorbents. In the third case, H<sub>2</sub>O selective adsorbents are used in the production of CO using a reverse water gas shift reactor. An emphasis is placed on the judicious use of these different adsorptive reactors to optimize the production of H<sub>2</sub>, CO, or syngas from the reforming of methane. There appears to be significant potential for the development of additional applications of and new adsorbents for the SERP concept, especially for CO<sub>2</sub> removal and concentration.

Some very recent work on the SERP concept by Hufton et al. [79] involves the development of precombustion decarbonization technology for CO<sub>2</sub> capture from to integrated gasification combined cycle (IGCC), natural gas combined cycle (NGCC), or related combined cycle processes. This process is referred to as sorption enhanced water gas shift. It involves a multi-bed PSA process operating at high temperature with the columns again packed with catalyst and K-promoted HTlc. CO is converted to CO<sub>2</sub> which is quickly removed by the CO<sub>2</sub> selective

adsorbent. This *in situ* removal of CO<sub>2</sub> facilitates more conversion of the CO to CO<sub>2</sub> through Le Chatlier's principal, as discussed above. A H<sub>2</sub> product free of CO<sub>2</sub> is produced at high pressure and temperature. This gas is burned in a high efficiency gas turbine. After a series of PSA cycle steps, including a heavy reflux step, a concentrated CO<sub>2</sub> product is produced at low pressure. This CO<sub>2</sub> product could be recovered, and either sold for industrial or commercial use or further processed for sequestration.

The success of the SERP relies on CO<sub>2</sub>, H<sub>2</sub>O and even H<sub>2</sub> selective adsorbents. The preferred CO<sub>2</sub> adsorbents include: K-promoted HTlc, modified double layer hydroxides, spinels, and modified spinels, with metal oxides and mixed metal oxides of Mg, Mn, La and Ca, and clay minerals such as sepiolite and dolomite [71-73,76,77]. The preferred H<sub>2</sub>O adsorbents include commercially available A, X and Y zeolites, mordenites, aluminas, and silica gel [69,70,78]. The preferred H<sub>2</sub> adsorbents include metal hydrides such as Pd, PdAg, MgNi, FeTi, and LaNi [78]. The preferred CO adsorbents include Cu(I) or Ag(I) on silica-alumina [78]. Clearly, a wide range of commercially available and developmental adsorbent materials can be used in the SERP concept.

Han and Harrison [80], Harrison and Peng [81], and Ortiz and Harrison [82] have been researching SERP for the steam reforming of methane in a single unit using a TSA cycle to remove CO<sub>2</sub> reversibly from the reaction product gas with CaO. Zou and Rodrigues[83], Xiu et al. [84], Xiu and Rodrigues [85-88], and Ding and Alpay [89,90] have been studying the performance of the SERP for the steam reforming of methane in a single unit using a PSA cycle to remove CO<sub>2</sub> reversibly from the reaction product gas using a K-promoted HTlc. The continued experimental validation of modeling analyses, coupled with the study of various PSA cycle sequences, should contribute to the understanding of this type of adsorptive reactor system, and to optimizing its performance.

It is clear that these SERPs allow steam methane reforming, water gas shift, and/or reverse water gas shift reactors to operate at reduced temperatures or pressures. They can reduce or eliminate downstream separation and purification units currently associated with the production of high purity H<sub>2</sub>, CO, or syngas when removing CO<sub>2</sub> for recovery or sequestration. Although the SERP concept seems to work well, industrial acceptance of this technology has been limited. Again, further implementation of SERP would be fostered with the development of improved adsorbents, especially high temperature adsorbents.

### ***Selective Adsorbents***

New selective adsorbents can play a key role in both H<sub>2</sub> and CO<sub>2</sub> production. A recent review of CO<sub>2</sub> adsorbents by Yong et al. [91] covered activated carbons, aluminosilicate zeolites, metal oxides and HTlcs for reversible adsorption. The overall conclusion is that activated carbons and zeolites are superior to metal oxides and HTlcs for ambient temperature applications, but for high-temperature applications metal oxides and HTlcs are preferred. As shown in Table 10, typical activated carbons exhibit 1.5 to 2.0 mol/kg CO<sub>2</sub> adsorption at 25 °C and 500 torr, which decreases to 0.1 to 0.2 mol/kg at 250 to 300 °C and 500 torr. Similarly, 5A zeolite exhibits ~ 3.0 mol/kg at 25 °C and 500 torr, and 0.2 mol/kg at 250 °C and 500 torr. The capacities of these materials would be less than 0.1 mol/kg at the temperatures associated with the steam methane



reforming, water gas shift, and reverse water gas shift reactive adsorbers.

The recent work by Engelhard Corporation involves the development of novel adsorbent materials for CO<sub>2</sub> separation from natural gas streams. The Molecular Gate technology, which was originally targeted for kinetic separation of N<sub>2</sub> from natural gas, was also found to be uniquely attractive for CO<sub>2</sub> and H<sub>2</sub>O separation from natural gas. Based on titanium silicate molecular sieves, the Molecular Gate process takes advantage of the unique ability to adjust pore size opening of the material within an accuracy of 0.1 angstrom. Despite the small differences of kinetic radius between nitrogen and methane, the material pore size of 3.7 angstroms is effective at excluding methane from its pores while accepting nitrogen and other smaller and far more adsorbing molecules such as CO<sub>2</sub> and H<sub>2</sub>O into its pores [10]. The CO<sub>2</sub>, N<sub>2</sub>, CH<sub>4</sub> and H<sub>2</sub>O capacities of these various Molecular Gate adsorbents are proprietary.

For selective adsorbents, the K-promoted HTlc materials exhibit a high and pressure-reversible CO<sub>2</sub> capacity at temperatures compatible with steam methane reforming, and water gas shift and reverse water gas shift applications [92,93]. Mayorga et al. [93] at Air Products and Chemicals report synthesis procedures and operational capacities for both HTlcs and double layer hydroxides. Yong et al. [94] and Yong and Rodrigues [95] have characterized HTlcs for CO<sub>2</sub> adsorption at ambient and elevated temperatures, as have Ding and Alpay [89,90]. Overall, the reversible CO<sub>2</sub> capacities typically range between 0.4 and 0.7 mol/kg at 300 and 400 °C and 200 and 700 torr, even in the presence of steam. This performance is highly dependent on the synthesis and pretreatment conditions [96]. Double layer hydroxides exhibit even higher reversible capacities in the presence of steam, typically of around 1.5 mol/kg at 375 °C and 230 torr [93]. These adsorbents are attractive not only for SERPs, but also for high temperature PSA processes, as shown recently by Reynolds et al. [61,97]. Table 10 compares the capacities of these developmental CO<sub>2</sub> selective adsorbents to established commercial materials.

Several teams are also exploring alumina as a high temperature and pressure-reversible CO<sub>2</sub> adsorbent for use in a PSA cycle [91,98]. The CO<sub>2</sub> capacity of aluminas undoped and doped with metal oxides and carbonates ranges from 0.06 (undoped) to 0.52 (doped with 9 wt% Li<sub>2</sub>O) mol/kg at 400 °C and 500 Torr [98], which is similar to that reported by Yong et al [91] for commercially available basic aluminas, ~ 0.3 mol/kg at 300 °C and 500 torr (see Table 10).

Lithium zirconate and CaO can function as high-temperature, selective CO<sub>2</sub> adsorbents with temperature-reversibility. Xiong et al. [99], Ida and Lin [100], and Ida et al. [101] are exploring the zirconates, as are Nair et al. [102] in Japan. Typical CO<sub>2</sub> adsorption capacities are high at 3.4 to 4.5 mol/kg at 500 °C and 760 torr, with reasonable regeneration rates exhibited at 780 °C that improve with CO<sub>2</sub> free purge gas [100] (see Table 10). The sensitivity of these materials to H<sub>2</sub>O vapor has not been reported.

CaO adsorbents are being investigated by Iyer et al. [103], Gupta and Fan [104], Gupta et al. [105], Han and Harrison [80], Harrison and Peng [81], Ortiz and Harrison [82], Kuramoto et al. [106] in Japan, and Abanades [107] in Spain. These materials are also showing high CO<sub>2</sub> capacities at high temperatures with reasonable regeneration rates. For example, typical reversible CO<sub>2</sub> capacities range between 4 and 8 mol/kg at 500 °C and 150 torr, with regeneration carried out at 900 °C in N<sub>2</sub> [106]. A similarly high CO<sub>2</sub> capacity of 7 mol/kg

resulted for a CaO exposed to 76 torr of CO<sub>2</sub> and cycled over 50 times at 700 °C using N<sub>2</sub> for purge. This is a large reversible CO<sub>2</sub> capacity (see Table 10). These CaO adsorbents are very sensitive to sulfur but the sensitivity to H<sub>2</sub>O vapor has not been reported [103]. The operating temperature range of this material may be too high for most steam methane reforming (SMR), the water gas shift (WGS) and reverse water gas shift reactors, however.

United Technologies working with NASA in the mid to late 1990s developed novel low temperature solid amine-based CO<sub>2</sub> adsorbents that are pressure and or temperature regenerable [108,109]. One variant of this novel material consists of a liquid amine, such as polyethyleneimine (PEI) chemically bonded to polymethyl methacrylate with poly(ethylene glycol), a second liquid phase, used to enhance mass transfer [110]. This solid amine adsorbent has a reversible CO<sub>2</sub> capacity of around 0.9 mol/kg at 25 °C and 15.2 torr of CO<sub>2</sub>, it can be regenerated using PSA at a moderate vacuum of 1 torr, and its capacity markedly improves in the presence of water vapor [110].

More recently, Xu et al. at Pennsylvania State University, in a series of works [111-113], have been developing a similar reversible solid amine-based adsorbent for CO<sub>2</sub> using MCM-41 as the support and PEI as the CO<sub>2</sub> active amine. Depending on the Si/Al ratio of the MCM-41 and the loading of PEI ranging from 30 to 75 wt%, typical CO<sub>2</sub> adsorption capacities range from 1.5 to 3.0 mol/kg at 75 °C and 1 atm of CO<sub>2</sub>, with complete reversibility achieved simply by purging with pure N<sub>2</sub> at 75 °C [112]. However, the adsorption and desorption kinetics are generally quite slow with 150 minutes required in each case. Most recently they investigated its effectiveness for treating simulated flue gas comprised of 14.9, 4.25 and 80.85 vol% CO<sub>2</sub>, O<sub>2</sub> and N<sub>2</sub>, respectively [113]. The results at 75 °C were encouraging with CO<sub>2</sub>/N<sub>2</sub> selectivities of over 1000 and CO<sub>2</sub>/O<sub>2</sub> selectivities of over 180. This supported solid amine-based adsorbent has limited applications as it is unstable at 100 °C.

## **Membranes**

A wide variety of membrane materials and membrane gas contactors are being developed for gas separation and purification applications involving CO<sub>2</sub>. A survey of the recent literature is given below. The latest developments in polymeric, facilitated transport, inorganic, and hybrid organic/inorganic membranes are reviewed. This is followed by a brief assessment of hollow fiber gas-liquid contactors. Ideas presented in these studies have the potential for both near-term and longer-term impact of membrane applications on the removal of CO<sub>2</sub> from process streams, including flue gas or combustion gas streams. Tables 12 and 13, respectively, provide the permeability and permeance of membrane materials used for CO<sub>2</sub> separation, and the trans-membrane flux data for different capillary hollow-fiber membrane contactors reported in the literature.

### ***Polymeric Membranes***

Polymeric membranes are attractive because they can be manufactured into units with very high surface areas, either in the form of hollow fibers arranged in the tube-and-shell configuration (85% of the market) or in the form of flat sheets packaged as spiral-wound modules with less area but more resilience against adverse conditions [14,15,19]. There are two types of polymeric

membranes. Those that are referred to as glassy polymeric membranes have a glass transition temperature that is higher than room temperature. In contrast, those that have a glass transition temperature that is well below room temperature are referred to as rubbery polymeric membranes. Table 12 summarizes the permeability and permeance obtained with these kinds of membrane materials when used for CO<sub>2</sub> separation.

Most commercial membrane systems in gas separations are based on glassy polymeric materials as opposed to their rubbery counterparts because of their superior mechanical properties and overall permeability-selectivity tradeoffs [114-116]. Common glassy polymeric materials include polysulfones [117-127], polyimides [116,128-150], polyaramides and polycarbonates [151-154], polyphenylene oxides [155-163] and cellulose derivatives [164-168]. Although there are less than 10 commercial membrane processes available today [14,15], these glassy polymeric membranes are still receiving significant attention in the literature [169-176].

As indicated earlier, the selectivity of a large fraction of glassy polymeric membranes depends largely on their ability to discriminate gas species by size and diffusivities through the membrane structure. Such ability is for a large group of glassy polymeric membranes consistent with the solution-diffusion model [14-19,177-180]. In the solution-diffusion model, the transport of molecules is regulated mainly by thermal oscillations of the semi-rigid polymer structure that allows diffusion selectivities based upon subtle changes in size. However, there is a small fraction of stiff glassy polymeric materials (described below) where the diffusion selectivity is governed by a size selection mechanism similar to that found in inorganic molecular sieves [178-187].

Because the performance of most glassy polymers is structure dependent, physical or chemical attacks upon it can lead to a significant deterioration of performance. Glassy membranes that become overexposed for extended periods of time to large concentrations of CO<sub>2</sub> or even traces of vapors from organic solvents may lead to undesirable compaction, swelling, and plasticization that irreversibly change the morphology, and hence may lead to reduced membrane performance [13-19,128-130,135,142,144,145,188-204]. Plasma and thermal treatment (i.e., annealing) [135,188,190,200,202,204] and chemical cross-linking methods [128-130,142,144,145,193-199,201,203], which improve the membrane resistance by increasing the polymer rigidity, are the most frequently used strategies to improve durability.

Thermal treatments of polymeric material for membranes with cross linking agents improve resistance to plasticization and other attacks. Thermally induced densified structures are being investigated with charge transfer complexes [194-198,202], diols [128-130,193-198] and diamines [129,142,144,145,193,203]. The improved resistance against structural modification is realized via covalent bonding of neighboring polymeric strands. These approaches lead to reductions in permeability, sometimes with improvements in selectivity. Others have observed further success by attempting a mixed approach of both techniques [194-198]. Thermal annealing, for example, can further drive cross-linking reactions to stabilize the polymer properties.

The addition of inorganic materials can also lead to further stabilization of the membrane. In this regard, polymers crosslinked with inorganic monomers [205-209], typically alkoxy-silanes,

improve stability and also improve performance. These materials belong to a different class of materials normally regarded as organic-inorganic hybrid materials and are discussed later.

Glassy polymers, characterized by a very rigid ultramicroporous structure, possess pores sufficiently small for gas separation [178,179]. Molecule diffusion in these polymer molecular sieves is similar to that in inorganic molecular sieves. Examples of these materials are polypyrrolone copolymers [178-180,184-187] and the recently developed intrinsic microporous polymers [181-183,210]. In general, these polymeric membranes are very attractive because they display performances normally above the upper bound for conventional polymeric materials and enhanced stability [178,179].

Another type of glassy polymer is di-substituted acetylene-based polymers [116,211-231]. Disubstituted polyacetylenes are known for their unique gas transport properties, characterized mainly by enormous gas permeability, high fractional free volumes (typically > 20%), and unusually high vapor/gas selectivities [116,217,220,221,230,231]. Within polyacetylenes, poly(1-trimethylsilyl-1-propyne) (PTMSP) displays the largest gas permeability of all known polymers [116]. It is believed that the large permeability associated with these polymers is due mainly to a concerted action of the rigid double bonds of the polymeric backbone and the bulky side groups, hindering chain segmental motion and restraining polymer chains from packing efficiently [215]. The resulting effect is a polymeric matrix with large, possibly interconnected, free volume that provides a very efficient permeation pathway for transporting molecules.

Also, unlike the rest of the glassy polymers, polyacetylenes do not discriminate permeates based on diffusivity but rather on solubility, which provides them with the ability to permeate heavier and more soluble organic molecules and CO<sub>2</sub> over smaller gases. Due to this reason, polyacetylenes such as PTMSP [216,217,220-222,224,225,229,230] and Poly(1-methyl-1-pentyne) [217-219,230,231] have been investigated as potential materials for the separation of light hydrocarbon gases and vapors (C<sub>3+</sub>) from natural gas and off-gas H<sub>2</sub>-containing streams (e.g., from fluidized catalytic crackers) in refineries.

As result of their selectivity towards CO<sub>2</sub> over H<sub>2</sub>, polyacetylenes also have found potential use in hydrogen/syngas production processes (e.g., reforming). However, the CO<sub>2</sub>/H<sub>2</sub> selectivities so far displayed by these polymers (i.e., < 6) are still only moderate. This limitation, due mainly to the prohibitive losses of high-pressure H<sub>2</sub> in the low-pressure permeate, reduces the commercial potential for these polymer membranes.

Another major concern behind polyacetylenes is their lack of chemical resistance and performance loss over time [215,224,225]. Polyacetylenes tend to incur irreversible structural changes and degraded performance with long exposures to feed gases. Several approaches have been attempted to overcome these problems with some success and sometimes with loss of performance. These approaches include the addition of silica fillers [223,232-234] to manipulate the molecular polymer chain packing. They also include the addition, preparation, or use of other polyacetylenes more resistant to aggressive feeds, such as poly(4-methyl-2-pentyne) [230], poly(1-phenyl-1-propyne) [231], and diphenylacetylene [215]. Chemical treatments such as fluorination and desilylation [211-215] also have been explored.

The increasing demands for purer and cheaper  $H_2$  has fostered the development of technologies that selectively remove  $CO_2$  from  $H_2$ /syngas under high pressure from reforming, coal and waste gasification and partial oxidation, and other similar processes. In this regard, rubbery polymeric materials allow membrane technology to be a viable option for this industrial application. In general, rubbery polymers tend to display lower performance than their glassy counterparts, but they possess the unique ability to be selective towards  $CO_2$  over  $H_2$ .

The transport of molecules in rubbery polymers also can be explained by the solution-diffusion model. However, in this case the selectivity of rubbery polymers relies upon the physical interactions (i.e., solubility) between gas penetrants and the polymeric phase. Thus, given relatively low temperatures, it is possible for rubbery polymeric materials to be more selective towards heavier gases such as  $CO_2$  or  $H_2S$  over smaller molecules such as  $H_2$  or He [13,175,235-255].

The fact that rubbery polymers do not rely on diffusion selectivity makes their performance much less likely to be affected by swelling, plasticization and other adverse attacks than their glassy counterparts [13,235-239]. In the past, semi-organic rubbery polymers such as silicone membranes (in particular poly(dimethylsiloxane) (PDMS)), have received considerable attention for their high intrinsic permeabilities [116,256-263]. However, because these materials have suffered from reduced selectivities, particularly for the  $CO_2/H_2$  system, their further study as possible membrane materials is somewhat discouraged.

Today, polyphosphazenes [240,241,264,265] and polyethers [175,235-239,242-254] are the rubbery polymers receiving the greatest attention. These materials display the largest  $CO_2/H_2$  selectivities (i.e., 6-10) and show significantly higher  $CO_2/N_2$  or  $CO_2/CH_4$  selectivities (40-60) than commercially available glassy membranes. It is believed that polar groups in the polymer backbone, particularly ether oxygen atoms, are largely responsible for the enhanced selectivity for  $CO_2$ .

Despite the large selectivities, rubbery polymers suffer from modest permeabilities, principally as a consequence of the large degree of crystallinity associated with them [235-238,240,241,264,265]. However, several approaches have been implemented to minimize the existence of crystalline phases within these polymers, including the addition of hydrophobic pendant groups [240,241,264,265], the preparation of block copolymers containing low molecular weight rubbery polymer segments and glassy polymers such as nylons [175,247,252,266,267,], polyimides [267-269] and others [158,159,245-247]. The utilization of cross linking agents that keep rubbery polymer segments small has also been investigated [242-243,235-238,253]. This cross linking improves the mechanical consistency that is normally lacking in rubbery polymers. Despite all these challenges, rubbery polymers seem to offer significant space for improvement with a great potential for future commercial use.

### ***Facilitated Transport Membranes***

Facilitated transport membranes (FTMs) have received considerable attention because of their extremely elevated selectivities and relatively high fluxes [17]. Table 12 summarizes the permeabilities and permeances obtained with these kinds of membrane materials when used for

CO<sub>2</sub> separation. The high selectivity in FTMs is achieved through the existence of carriers within the membrane that selectively interact with given molecules and facilitate their transport through the membranes. FTMs that are selective towards CO<sub>2</sub> can have a great impact on reducing processing costs or improving equilibrium driven processes such as natural gas sweetening, reforming and coal gasification, and flue gas treatment, where CO<sub>2</sub> is to be removed, even if present in low concentrations.

FTMs, however, are widely known for their stability problems, mainly as a result of the evaporation of the carrier medium – a problem that is particularly acute in immobilized liquid membranes (ILMs) [270]. Several approaches have been attempted with moderate success to control evaporation. In some FTMs, evaporation losses have been reduced by alternatively using non-volatile solvents such as carbonate-glycerol [271], glycine-Na-glycerol [272,273], dendrimers [274,275], and, more successfully, glycerol carbonate [270,274]. Similarly, in polyelectrolyte membranes (PEM) [276-281], which are also ILMs, the evaporation is reduced by using non-volatile polyelectrolytes as molten salts or salt hydrates as solvents.

Membranes where the carriers are tightly bound to the polymer also have been developed to counteract degradation. In ionic exchange membranes (IEMs) [282-287], the carrier is ionic and physically binds to the ion exchange membrane via attractive electrostatic forces. In water-swollen membranes [288-290], which are a particular type of IEM, where water serves as the carrier, the membrane physically interacts and retains water, causing swelling which improves the transport of the solute.

The most successful facilitated transport membranes are the so called fixed carrier membranes (FCMs) [291-293]. In FCMs the carrier consists of secondary amines or carbonates that are chemically bonded to the backbone of the membrane. Clearly, the chemically bound carrier alleviates the evaporation and migration problems associated with the free liquid FTMs.

Despite all this work on FTMs, and with the exception of some ILMs and FCMs, most FTMs still require feed preconditioning, particularly with water, to sustain their uniquely high selectivity. Otherwise, their selectivity severely deteriorates. However, FTMs may overcome these problems in applications where humidification preconditioning is not a requirement, such as in reforming, where H<sub>2</sub>O actively participates.

Another problem, perhaps a minor one, of most FTMs is their characteristically strong decay of permeability as the partial pressure of the favored molecule increases [274-277,280-282,288,292,293]. This behavior limits their use to feeds with low partial pressures of this species. At partial pressures over 0.5 atm most carriers rapidly approach saturation and the permeation rates become severely limited.

A particularly novel approach to FTM technology is that associated with the “bulk flow liquid membrane” (BFLM) concept, which was introduced by the group of Teramoto [294-296]. In BLFMs, stability problems due to evaporation of the carrier solution, observed with traditional FTMs, are avoided. The carrier solution is forced to permeate through the membrane and then is continuously recycled to the feed side.

Briefly, with BFLMs the carrier solution is continuously mixed with the feed gas and the carrier selectively reacts with the solute. Once inside the membrane unit the carrier permeates the membrane with the dissolved solute from the feed side (high-pressure side) to the receiving side (low-pressure side). Upon leaving the unit the absorbed CO<sub>2</sub> is released and the regenerated carrier is recycled back to the feed for reuse. Any small amount of carrier solution that does not permeate the membrane is later separated from the treated gas and returned through the receiving side of the membrane to join the carrier that is permeating through the membrane.

Because the membrane is always wetted with carrier solution, the membrane remains highly selective while devoid of any open pores (i.e., pores unfilled with liquid through which the gas may flow unselectively). Also, BFLM units do not require the use of special membranes. The flexibility of this process is such that both microporous and capillary membranes can be successfully used. In addition, thick and porous membranes with sufficient mechanical strength and durability can be used as long as they do not severely restrict the transport of the carrier. Teramoto et al. [294,295] showed CO<sub>2</sub>/N<sub>2</sub> selectivities over 500 and permeances and greater than 300 GPU<sup>2</sup> for a wide variety of BFLMs containing capillary polyethersulfone membranes 250 microns thick.

### ***Inorganic Membranes***

Inorganic membranes are very attractive not only because they have significantly better performance in terms of permeability and selectivity over organic membranes, but also because they are more resistant to high temperatures and pressures, fouling, aggressive feeds, and regeneration treatments. Table 12 summarizes the permeabilities and permeances obtained with these kinds of membrane materials when used for CO<sub>2</sub> separation. Materials typically used as membrane materials include carbon molecular sieves from a wide variety of organic polymeric precursors [134,135,138,148,306-313,250,297-305,], zeolites [314-336], and silicas [337-341]. To improve their productivity, these membranes must be deposited as thin layers upon the surface of other, non-selective inorganic materials, such as aluminas, zirconias, or porous stainless steel that also provide structural consistency.

Most inorganic membranes exploit diffusion selectivity as the main factor for gas separation. An extreme case of diffusion-selective membranes is that of molecular sieves, where the molecular spacing within the pores of the membrane is so restricted that the transport of some larger molecules becomes severely impeded. Most of the literature regarding inorganic membranes that rely on diffusion selectivity for CO<sub>2</sub> separation has been focused on the CO<sub>2</sub>/N<sub>2</sub> or CO<sub>2</sub>/CH<sub>4</sub> systems.

In other materials adsorption and condensation play an additional role. For example, in so called selective surface flow (SSF) membranes, condensation is so important that even the smaller and faster diffusing species become the less permeable ones, sometimes to the point of becoming totally excluded. The first SSF membranes were developed by Air Products and Chemicals and have been extensively studied [71,342-350]. However, the CO<sub>2</sub>/H<sub>2</sub> selectivities of these membranes (< 5 for most species - see Table 12) so far are too low to be of any economic value. Recently others [262,325,351-359] have reported new types of membranes with SSF

---

<sup>2</sup> GPU = 1 x 10<sup>-6</sup> cm<sup>3</sup> (STP)/(cm<sup>2</sup>-s-cm Hg)

characteristics.

Despite all their appealing properties, inorganic membranes are not commercially used for CO<sub>2</sub> separation. It is doubtful that this will change in the near future. Their inherent brittleness and the elevated manufacturing costs associated with making modules that are crack free and have large surface areas are still serious issues that limit their utility.

### ***Hybrid Membranes***

In the past two decades there has been much interest in the development of hybrid membranes consisting of mixtures of organic and inorganic phases. Table 12 summarizes the permeabilities and permeances obtained with these kinds of membrane materials when used for CO<sub>2</sub> separation. Polymeric membranes have shown little progress since Robeson set the permeability-selectivity trade-off upper limit in 1991 [360]. So-called hybrid organic–inorganic membranes seem to offer potential to overcome this limitation. In these membranes, the inorganic phase, which is normally in dispersed form, consists of diverse types of silicas [137,173,205-209,361-387], titanias [125,388], carbon materials [178,179,389-395], and zeolites [396-409]. The organic or polymeric phase serves as the host [390-392]. These membranes are attractive because they synergistically exploit the desired properties of both phases, improving the mechanical (e.g., by increasing bursting pressures) and thermal properties of the inorganic phase and providing the manufacturing flexibility and ductility associated with the organic phase [207,361-364,390-392].

In addition, there has been an abundance of literature reporting that organic-inorganic hybrid membranes can improve the performance of the organic phase, potentially addressing many of the current needs of the membrane industry [178,179,205-208,361-365,375,376,389,390-398,401,402]. Hybrid membranes have been shown to significantly increase the selectivity of the polymer while keeping, and sometimes also increasing, its permeability [178,179,389,390-395]. Further, it also has been reported that hybrid membranes exhibit higher stability against aggressive environments [390].

Organic-inorganic hybrid membranes generally can be classified into two types. In the first type the inorganic phase consists of either preformed submicron particles (fillers) [125,178,179,385-388,389,390-395,397-409,] or in the form sol-gel precursors that are subsequently incorporated into the organic phase [137,365,377-383,389]. In the second type both organic and inorganic phases become intermingled at the molecular level via chemical reactions between monomers of both phases [173,205-208,209,361-364,366,371,375,376]. In the first type the mixing is realized in a slurry that contains both phases dispersed in a solvent that is later removed. In the second type the membrane typically is formed via a sol-gel process whereby hydroxyls of the inorganic monomers (e.g., alkoxy silanes) become covalently bonded to the backbone of the organic monomer via organic functional groups.

There are two main reasons for the enhanced performance observed in hybrid membranes [207]. The first one is due to the particular interactions that the inorganic phase establishes with the favored gas species. In this case, the inorganic phase may act as a molecular sieve, delaying the transport of the less selective species, or as a SSF material which, due to an improved condensation selectivity in favor of the heavier species, retards the flow of the smaller, more



diffusing species. The second reason for the improved performance is a consequence of morphological changes that take place in the polymer structure as a result of the strong interactions now existing between the two phases. A strongly interacting inorganic phase can inhibit chain or backbone mobility (i.e., increase stiffness) and open inter-chain packing (i.e., backbone inter-distance), simultaneously improving both the selectivity and permeability of the organic phase.

Perhaps, the most critical decision in making a hybrid membrane with improved performance lies in the correct selection of the membrane materials [207,391,392]. Both selected phases should facilitate the transport of the more selective gas species, while the transport of the less selective species is delayed. In this regard, matching the permeabilities of the favored gas species in both phases is an important consideration. A polymeric phase that is otherwise too permeable or too impermeable may lead to undesirable gas bypassing (i.e., low selectivity) or poor membrane productivity (i.e., low permeability), respectively.

It is also imperative that the phases display good adhesion at the interface. Defects at the interface and phase separation lead to gas bypassing, which reduces selectivity. The simplest approach to insure interfacial adhesion is to select phases that are physically and chemically compatible with each other and to assure that interfacial surface tension is minimized. For example, interacting mixtures containing zeolites and rubbery polymers [401-402], or carbon based materials with glassy polymers [178,179,389-395] have led to better performing membranes, in some cases significantly better. Limited or no success has been achieved where phase separation occurs (e.g., with mixtures of silicas or zeolites and glassy polymers) [390-392].

Alternative approaches have been attempted to improve adhesion of poorly interacting phases. The use of polymeric compatibilizers [173,209,379,410] to reduce surface tension has been demonstrated. Some success has been achieved by using coupling agents and sol-gel techniques with organic polymers functionalized with, for example, trialkoxysilane groups or alkoxysilane monomers containing functional groups [137,367,380,382,399-402,411]. The same bonding concept has been successfully exploited with *in situ* prepared hybrid membranes where bonding reactions result in the formation of nano-microcomposites [173,205-209,361-364,366,371,375,376].

At present, hybrid membranes are used only to improve the mechanical strength of membranes for liquid separations, such as those used in ultrafiltration, reverse osmosis, ion exchange, etc. [412,413]. In the gas separation industry, hybrid membranes currently are not being used.

### ***Hollow Fiber Gas-Liquid Contactors***

The concept of using a hollow fiber membrane unit to serve as a gas-liquid contactor for absorption was first introduced by Zhang and Cussler [414,415]. Currently, a handful of companies including Kvaerner Oil & Gas, W.L. Gore and Associates GmbH, and TNO Environment Energy and Process Innovation have successfully developed larger-scale units [416-418]. However, commercialization is looming. Nevertheless, because of the inherent high selectivity and relatively large flows, hollow fiber contactors may be very attractive for CO<sub>2</sub>

separations in processes such as reforming and gas sweetening. Table 13 provides a summary of the trans-membrane flux being achieved for different capillary hollow fiber membrane contactors reported in the literature.

The process basically uses a non-selective membrane that serves only as a physical barrier between the gas and the liquid phase. The non-wetted pores in the membrane are such that the membrane does not offer any selectivity over the gas species; the liquid absorbent assumes this role [416-425]. Thus, the membrane must only allow the solute to diffuse through with little resistance before reaching the absorbent. The pores of the membrane must be kept completely gas filled. The presence of stagnant liquid within the pores (i.e., wetting) increases the overall mass transfer coefficient of the process.

Because of its advantages over conventional absorption towers, a great deal of research has been conducted on gas-liquid contactors in acid gas sweetening of natural gas and flue gas streams [416-418,421-424,426-445,]. Hollow fiber gas-liquid contactors are flexible and can be operated over a wider range of conditions, as they are not subject to the common limitations observed in packed beds such as flooding, foaming, channeling, and liquid entrainment [418]. Superficial velocities in these membrane processes easily can exceed 2 cm/s, which is a limit in their packed bed counterparts.

The larger surface area in these contactors is perhaps the most attractive advantage. Depending on the diameter and thickness of the hollow fibers, membrane contactors may display trans-membrane surface areas between 500-3000 m<sup>2</sup>/m<sup>3</sup>, which is significantly higher than the typical 100-500 m<sup>2</sup>/m<sup>3</sup> observed in packed bed systems. The result of having a large surface area is that despite the typically lower mass transfer coefficients associated with the laminar regime of the liquid phase in these membrane contactors, the volumetric mass transfer coefficient (i.e.,  $k_L a$ ) can still be larger than that attained in a packed bed [441-443]. Furthermore, unlike packed bed systems, the contacting area is fixed and does not vary with process conditions, and the particular modularity of the membrane contactors allows their design to be simple and scaled linearly. All these facts could lead to significant operational and capital cost savings.

These membrane contactors also offer advantages over selective membranes. The performance of hollow fiber membrane contactors depends almost exclusively on the liquid absorbent, and unlike dense or selective membranes it is not significantly affected by plasticization and other structural attacks. Also, the extremely high selectivity towards CO<sub>2</sub> that can be achieved with these membrane contactors limits their loss of primary gases such hydrogen, methane, or other hydrocarbons through the permeate, particularly in feeds with low CO<sub>2</sub> concentrations.

In spite of their positive attributes, hollow fiber gas-liquid contactors are unable to sustain processing conditions for prolonged periods of time. This problem has significantly limited commercial interest. The initial high resistance against liquid penetration into the membrane pores tends to break down with time as a result of combined mechanisms that include surface wetting, surface modification and reaction, clogging, and swelling of the polymer [316,418]. Membrane wetting largely depends on an adequate selection of membrane and liquid absorbent. The ability to stop a liquid from wetting or penetrating into the pores of the membrane depends directly on the surface tension of the liquid and inversely on the size of the membrane pores.

With higher surface tension and smaller pores it is less likely that the membrane can be wetted. In general, the use of hydrophobic membranes, such as inexpensive polyolefin membranes, in combination with aqueous based absorbents, such as suspensions of alkanolamines or carbonates, ensures large surface tensions. However, surface tension may also vary with the absorbent concentration and CO<sub>2</sub> loading. In alkanolamines, for example, the interfacial surface tension tends to decrease considerably with increasing alkanolamine concentration, but then recovers as the CO<sub>2</sub> loading increases [418].

In addition, the selected solvent must be compatible with long-term stability of the membrane. For example, alkanolamines tend physically to interact and breakdown the hydrophobicity of polyolefin membranes. More hydrophobic membranes, such as polytetrafluoroethylene (PTFE), have been developed to resolve this problem. However, PTFE is expensive and the PTFE membrane contactors exhibit only limited contacting areas. Amino acid salts made from glycine, alanine, diethyl or di-methyl glycine, which offer similar absorption characteristics to aqueous alkanolamines and do not degrade polyolefin membranes, can be used but are more expensive.

Recently, Yeon et al. [441,442] have shown that adding significant concentrations of triethanolamine (TEA) into the absorbent also can improve membrane stability against wetting. Membranes containing this alkanolamine displayed stable performances for over 3000 hours. TEA offers a lower absorption rate than the alkanolamines; but, it requires less energy consumption and does not react with CO<sub>2</sub>. Korikov and Sirkar [433] showed that aqueous solutions containing polyamidoamine dendrimers as absorbents also may improve membrane stability.

Another way to restrict membrane wetting is by reducing the pore size. Pores, however, cannot be so small that they restrict the flow of solute across the membrane. Below the lowest limit, which corresponds to the mean free path and is equivalent to 70 nm for CO<sub>2</sub>, the membrane becomes selective.

Another significant problem associated with these gas-liquid contactors is pore blocking, which is related to solvent stability. For example, alkanolamines, in particular monoethanolamine (MEA), and some amino acid salts tend to react with the CO<sub>2</sub> and form precipitates that eventually cause pore clogging and fouling.

Most recent efforts are directed towards developing cross-flow membrane contactors, which improve the lower mass transfer coefficients of the traditional contactors [416,417]. A summary of membrane contactors can be found in the reviews of Li and Chen [445], Drioli et al. [425], and Klaassen et al. [419,420].

## **Conclusions from Background Survey**

This survey identified several areas where major improvements or breakthroughs may be achieved in CO<sub>2</sub> removal with the judicious use of adsorption and membrane processes. In several other areas the path forward is potentially blocked by fundamental material limitations. In the next section, recommendations are presented for future work on promising adsorption and membrane technologies. It is anticipated that breakthroughs in adsorption and membrane

technologies will lead to significant reductions in energy consumption, environmental impacts and feedstock requirements, and thereby provide considerable improvements in process economics.

## **RECOMMENDATIONS FOR FUTURE R&D**

Recommendations are set-forth for future CO<sub>2</sub> separations R&D needs based on this technology and industrial assessment. These recommendations are set-forth for both the near-term time frame (i.e., 1 – 5 years) and longer- range research (i.e., 7 – 15 years).

The near-term developments in CO<sub>2</sub> separations technology are divided into four categories:

- Near-Term Adsorbent Development
- Near-Term Membrane Development
- Near-Term Adsorption Process Development
- Near-Term Absorbent and Absorption Process Development

The long-range developments in CO<sub>2</sub> separations technology are divided into three categories:

- Long-Term Flow Sheet Augmentation with Adsorption and Membrane Processes
- Long-Term Advanced Adsorbent Materials and Process Development for CO<sub>2</sub> Removal
- Long-Term Advanced Membrane Materials for CO<sub>2</sub> Removal

It must be emphasized that streams containing CO<sub>2</sub> tend to be dirty and contain many different contaminants, as mentioned throughout this report. This fact is very important and provides the basis for a crosscutting recommendation for adsorption and membrane materials and process development.

***Crosscutting Recommendation: the development of pre-cleaning technologies to remove a wide variety of contaminants from CO<sub>2</sub> streams may be critical to the successful development and implementation of any or most membrane and some adsorption processes.***

### **Near-Term Adsorbent Development**

***Overarching Goal: Develop high-capacity CO<sub>2</sub>-selective adsorbents with rapid adsorption-desorption kinetics, improved selectivity, and operational stability.***

As a guide, the classes of adsorbent materials being studied today include:

- Low-temperature activated carbons, carbon molecular sieves, and zeolites for CO<sub>2</sub>
- High-temperature hydrotalcites, CaOs, and zirconates for CO<sub>2</sub>
- structured adsorbents for rapid PSA, or PSA/TSA processes (e.g., carbon fiber molecular sieves)

In general, these materials have potential for commercial use in CO<sub>2</sub> capture. However, they all suffer from one or more of the following deficiencies:

- too expensive
- insufficient working capacity

- insufficient selectivity
- slow adsorption or desorption or mass transfer kinetics
- moisture sensitivity
- vulnerability to poisons like CO or S
- too rectangular of an adsorption isotherm shape making regeneration difficult with pressure
- too strong of a physiochemical interaction requiring regeneration with relatively high temperature instead of pressure
- limited rapid cycling capability because commercial pellet materials tend to crumble if the cycling is too fast

Table 10 provides some insight into the CO<sub>2</sub> capacities now being achieved. Any improvement in these capacities will be highly desirable.

### ***Recommendations:***

- 1) **Specific Goal: Develop high-capacity CO<sub>2</sub>-selective adsorbents that can operate at elevated temperatures in the presence of sulfur-bearing compounds and possibly steam. Working capacities at elevated temperatures in the range of 3-4 mol/kg are desirable, which is similar to commercial low temperature adsorbents like 5A zeolite for CO<sub>2</sub>. The operating pressures should be in the range that corresponds to this working capacity range (e.g., 1 to 40 atm).**

### **Near-Term Membrane Development**

***Overarching Goal: Develop low- and high-temperature membranes that are selective only to CO<sub>2</sub>, that exhibit high permeability, are robust and resistant to fouling and degradation, and exhibit good mechanical stability under high differential pressures.***

As a guide, the general classes of membrane materials being studied today include:

- polymeric membranes including glassy and rubbery membrane materials
- facilitated transport membranes including immobilized liquid membranes, ionic exchange membranes, fixed carrier membranes, water swollen membranes, and polyelectrolyte membranes
- inorganic membranes including molecular sieves and selective surface flow membranes
- hybrid mixed matrix membranes including inorganic-organic hybrid materials
- hollow fiber membrane contactors that operate with absorbents

In general, these types of membranes or membrane contactors show commercial potential with energy saving impact in CO<sub>2</sub> capture. However, they all suffer from one or more of the following deficiencies:

- polymeric glassy membranes generally suffer from chemical attack by CO<sub>2</sub>, sulfur bearing compounds, and organic solvents
- polymeric rubbery membranes generally suffer from low permeabilities and low

selectivities towards CO<sub>2</sub> over H<sub>2</sub>

- facilitated transport membranes suffer from being too dependent on the presence of moisture to maintain selectivity
- inorganic membranes tend to be brittle and have low surface areas
- selective surface flow membranes tend to have low selectivities
- hybrid mixed-matrix membranes suffer from phase separation
- hollow fiber membrane contactors suffer from plasticization and tend to lose their resistance to wettability with time

Table 12 and 13 provide some insight into the properties of these various membranes towards selective CO<sub>2</sub> separations. Any improvement in these properties will be highly desirable.

### ***Recommendations:***

- 1) Specific Goal: Develop CO<sub>2</sub> permselective polymeric glassy or rubbery membranes with CO<sub>2</sub>/H<sub>2</sub> selectivity of > 15-20, with at least 2 times higher CO<sub>2</sub> flux than current commercial membranes, and with higher stability to syngas production conditions of 200°C or higher.**
- 2) Specific Goal: Develop polymeric glassy or rubbery membranes for CO<sub>2</sub>/CH<sub>4</sub> that have selectivity > 50, double the current commercial membrane CO<sub>2</sub> flux, resists plasticizing and is stable to heavy oil.**
- 3) Specific Goal: Develop CO<sub>2</sub> permselective facilitated transport membranes that can operate in the absence of water for long periods of time, avoid vapor conditioning, control or eliminate carrier evaporation, and minimize the strong dependence between CO<sub>2</sub> permeance and partial pressure as often observed in these materials.**
- 4) Specific Goal: Develop CO<sub>2</sub> permselective inorganic membranes with selectivity of > 15-20 or higher as these systems provide the desirable temperature stability.**
- 5) Specific Goal: Develop CO<sub>2</sub> permselective selective surface flow membranes with a much higher CO<sub>2</sub> selectivity toward gases such as H<sub>2</sub>, N<sub>2</sub>, CH<sub>4</sub>, etc.**
- 6) Specific Goal: Develop CO<sub>2</sub> permselective hybrid mixed matrix membranes with improved selectivity and permeance, and stability against phase separation, bypassing, and plasticization for the case with matrices made of glassy polymer, etc.**
- 7) Specific Goal: Develop CO<sub>2</sub> permselective hollow fiber membrane contactors with improved permeance and prolonged stability against solvent dissolution, wetting, and pore blocking.**

### **Near-Term Adsorption Process Development**

***Overarching Goal: Develop new or modify existing adsorption process technology that offers increased energy savings at lower capital and operating costs, affords higher reliability, and***

***reduces footprint and environmental impact.***

As a guide, adsorption process technology being studied today includes:

- various pressure swing adsorption cycles at ambient and elevated temperatures
- temperature swing adsorption for some CO<sub>2</sub> separations
- sorption-enhanced reaction processes, mainly for H<sub>2</sub> production

In general, state-of-the-art cyclic adsorption processes suffer from the following:

- CO<sub>2</sub> is typically the heavy component discarded in the tail gas of a PSA unit
- poor enrichment of CO<sub>2</sub> in typical PSA units
- TSA is limited to long cycle times and hence low feed throughputs
- PSA generally is limited to ambient or near ambient temperature operation
- PSA feed pressures tend to be very high
- PSA and TSA beds tend to be very large

Table 11 provides some insight into the performances of PSA processes for the recovery of CO<sub>2</sub> from stack and flue gas. Any improvement in these performances will be highly desirable. No attempt has been made to recover CO<sub>2</sub> from the tail gas of H<sub>2</sub> PSA plants.

#### ***Recommendations:***

- 1) Specific Goal: Develop new PSA cycle designs that take advantage of new or even existing CO<sub>2</sub> selective adsorbents; possibly TSA or PSA/TSA hybrid cycle designs could be envisioned.**

Some ideas for improvement include:

- rethink the use of the tail gas or heavy product from PSA processes
- revamp existing PSA plants through cycle modification
- use lower or even higher purge gas pressure
- replace one or more of the adsorbents with more efficient ones
- decrease the number of adsorbent vessels
- add storage tanks to replace some of the adsorbent beds
- develop new PSA cycles that take advantage of the heavy reflux concept, where a pure heavy product like (CO<sub>2</sub>) is more desirable than pure light product (like H<sub>2</sub>)
- foster a clear understanding of the design of such a PSA cycle, which appears to be lacking compared to the commercial light reflux PSA processes; hence, the application of the heavy reflux PSA concept for H<sub>2</sub> production is a desirable near term target

Some existing adsorbents with potential include:

- molecular sieve zeolites
- molecular gate silicotitanates



- activated carbons

Some new adsorbents with potential include:

- hydrotalcites
- CaO
- zirconates

**2) Specific Goal: Need improved efficiency for thermal management in the design of TSA and PSA/TSA hybrid cycles. Some ideas include:**

- rethink bed designs for rapid heating and cooling because the long times required to heat conventional beds for regeneration and then cool them to the feed temperature give rise to long cycle times and thus exceedingly large columns
- take advantage of the many heat sources that are available throughout some of the CO<sub>2</sub> producing plants that may lend themselves to a TSA or a PSA/TSA hybrid cycle configuration for selective CO<sub>2</sub> removal from a process stream

**Near-Term Absorbent and Absorption Process Development**

***Overarching Goal: Develop new or modify existing absorption process technology that offers increased energy savings with lower capital and operating costs, and affords higher reliability and reduces footprint and environmental impact.***

***Recommendations:***

- 1) Specific Goal: Develop absorbents with improved capacity and greatly improved heat of absorption.**
- 2) Specific Goal: Develop new regeneration techniques, as opposed to thermal or vacuum regeneration; in particular develop regeneration techniques that can be done at high pressure to cut down on compression costs for sequestration or enhanced oil recovery uses.**
- 3) Specific Goal: Develop absorbents that work on high temperature gases.**
- 4) Specific Goal: Develop absorbents that are stable to trace contaminants (e.g., amines are more likely to develop problems than most physical solvents).**
- 5) Specific Goal: Develop more selective absorbents (CO<sub>2</sub> over sulfur species) for processes with H<sub>2</sub>S and COS species present (e.g., natural gas and coal bed methane); one approach might be to develop reactive solvents that can convert sulfur species directly to elemental sulfur, while simultaneously or later absorbing CO<sub>2</sub>.**

## **Long-Term Flow Sheet Augmentation with Adsorption and Membrane Processes**

***Overarching Goal: Develop new adsorption and membrane process technology that offers lower capital and operating costs and affords higher reliability on stream with improved energy savings.***

### ***Recommendations:***

- 1) Specific Goal: Develop hybrid technology for H<sub>2</sub> production (e.g., develop a multi-functional hybrid reactor for steam methane reforming by combining the reactor with a CO<sub>2</sub> selective adsorbent and an H<sub>2</sub> permeable membrane).**

Driving equilibrium processes in this way can greatly improve manufacturing process efficiencies. This design would not only shift the equilibrium of the reforming reaction favorably, but it also would facilitate the WGS reaction. The recommended approach involves the development of new adsorbent and membrane separation materials.

It appears that highly selective and highly permeable membranes will always be very difficult to fabricate. However, with hybrid multi-reactive, multi-separation designs, the criteria for selectivity or permeability may be relaxed, so a less selective membrane with a high flux may suffice.

- 2) Specific Goal: Develop new CO<sub>2</sub> adsorbent and membrane technologies that are amenable to IGCC and related power and chemical production technologies with CO<sub>2</sub> sequestration as a potential long term objective.**
- 3) Specific Goal: Develop hybrid technology, possibly coupled with adsorption or membranes processes, that removes CO<sub>2</sub> by chemical reaction in the chemical process.**

## **Long-Term Advanced Adsorbent Materials and Process Development for CO<sub>2</sub> Removal**

***Overarching Goal: Develop new adsorbent materials and CO<sub>2</sub> process technology that offers increased energy savings with lower capital and operating costs, and affords higher reliability and reduces footprint and environmental impact.***

### ***Recommendations:***

- 1) Specific Goal: Develop advanced structured adsorbent materials for use in rapid-cycle PSA. These adsorbents should have comparable working capacity under operational conditions for the current and new non-structured adsorbents mentioned above.**
- 2) Specific Goal: Further develop the design of rapid-cycle PSA for CO<sub>2</sub> capture and concentration. In particular, this includes exploring rapid-cycle PSA with the incorporation of both heavy and dual reflux cycles steps.**
- 3) Specific Goal: Minimize the cycle time in rapid PSA to improve its throughput and**

hence efficiency by investigating the limiting relationship between adsorbent particle size, surface properties, and accelerated cycle times. In particular, the mass transfer limitations associated with ultra fast cycling need to be quantified.

- 4) **Specific Goal:** Develop TSA and or PSA/TSA hybrid cycles with improved materials for use in CO<sub>2</sub> separation technologies. In particular, a deeper understanding of the PSA/TSA hybrid cycle is needed to quantify the effect on the cycle time and bed sizes when adding a forced temperature swing/PSA cycle.
- 5) **Specific Goal:** Develop improved CO<sub>2</sub> separations with sorption enhanced reaction processes using pressure swing, thermal swing, or even hybrid pressure and thermal swing regeneration methods.

#### **Long-Term Advanced Membrane Materials for CO<sub>2</sub> Removal**

*Overarching Goal: Develop new membrane materials that offer increased energy savings with lower capital and operating costs, and affords higher reliability and reduces footprint and environmental impact.*

##### *Recommendations:*

- 1) **Specific Goal:** Next generation membrane materials are needed that offer very high selectivity for CO<sub>2</sub> (> 100), while resisting fouling and cracking or embrittlement, and while withstanding high temperatures and pressures that could save substantial energy associated with operation by replacing existing CO<sub>2</sub> and acid gas removal equipment.

## **SUPPORTIVE INFORMATION ON ENVIRONMENTAL CO<sub>2</sub> EMISSIONS**


In this supportive section, the main sources of industrial CO<sub>2</sub> emissions are reviewed. Ten sources (see Figure 3) are reviewed in order of decreasing impact on CO<sub>2</sub> emissions. Process flowsheets are provided that illustrates where the CO<sub>2</sub> is produced, the process capacity, and the condition and composition of the various process streams addressed. These flow sheets, and corresponding stream compositions and conditions, should be helpful in defining performance and operating condition requirements for the near- and far-term development of new adsorption and membrane processes for CO<sub>2</sub> capture from industrial sources.

Also, in this supportive section, some of the approaches that have been proposed to combat these CO<sub>2</sub> emissions are summarized. These approaches include the worldwide Kyoto Protocol that is designed to cut CO<sub>2</sub> emissions to below 1990 levels, taxation in some parts of Europe on the release of CO<sub>2</sub> into the atmosphere, integrated gasification combined cycle power plants that are more efficient, and the use of CO<sub>2</sub>-consuming algae that can be used to make biodiesel fuel.

### **Main Sources of Industrial CO<sub>2</sub> Emissions**

Brief descriptions of the processes most responsible for producing industrial CO<sub>2</sub> emissions are discussed

below. Listed in order of decreasing CO<sub>2</sub> generation, these industrial processes include 1) combustion - including burners, flaring, incineration, and utility boilers; 2) coal gasification; 3) steel manufacture; 4) lime and cement production; 5) H<sub>2</sub>, syngas, and NH<sub>3</sub> production; 6) natural gas production; 7) aluminum manufacture; 8) Claus/SCOT processes; 9) municipal solid waste landfills; and 10) fermentation to produce ethanol. The flowsheets associated with each of these industrial CO<sub>2</sub> producers is provided in Figures 4 through 14. The corresponding stream compositions and conditions for each of these flow sheets are given in Table 14. Typical process capacities and gas flow rates for these CO<sub>2</sub> producing industries are given in Table 15. Note that with the exception of some of the combustion and gasification processes, these flowsheets are

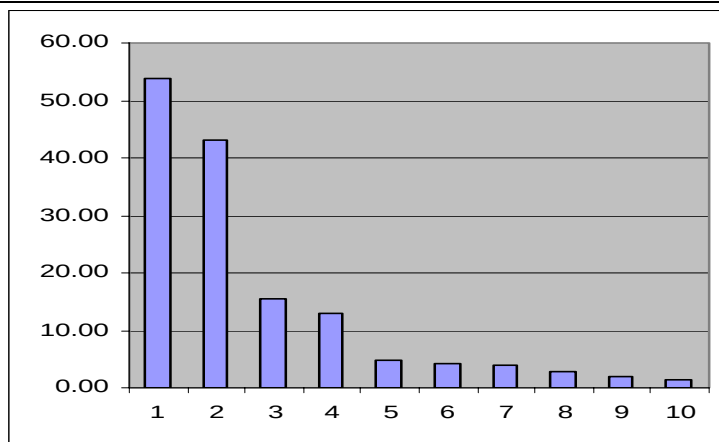


|                                           |       |
|-------------------------------------------|-------|
| 1. Iron and Steel Production              | 53.76 |
| 2. Cement Manufacture                     | 43.03 |
| 3. Ammonia Manufacture & Urea Application | 15.56 |
| 4. Lime Manufacture                       | 12.98 |
| 5. Limestone and Dolomite Use             | 4.72  |
| 6. Aluminum Production                    | 4.22  |
| 7. Soda Ash Manufacture & Use             | 4.08  |
| 8. Petrochemical Production               | 2.78  |
| 9. Titanium Dioxide Production            | 2.01  |
| 10. Phosphoric Acid Production            | 1.38  |

Figure 3. U.S. Industry 2002 CO<sub>2</sub> emissions in MMt: non-energy related processes.

concerned only with CO<sub>2</sub> emissions resulting from chemical and petrochemical processes. Tables 2 and 3 and also Figure 3 present slightly different perspectives on non-energy related CO<sub>2</sub> production from various processes, six of which were mentioned above and are reviewed below.

***Combustion Processes [446-449]***

This section considers the carbon dioxide generated from all types of industrial combustion processes, including those that generate power from burning fossil fuels to simple burners, flares, incinerators, and boilers. Fossil fuel power plants, as well as many chemical and petrochemical plants, utilize burners, utility boilers, incinerators, and or flares to generate heat, energy, or steam or to get rid of a waste product. All of these processes produce CO<sub>2</sub> as a by-product of burning or combusting various fuel sources, such as coal, solid waste, natural gas, or some other type of fossil fuel. A typical flow sheet for a carbon-based combustion process that could be associated with a burner, flare, incinerator, or utility boiler is given in Figure 4.

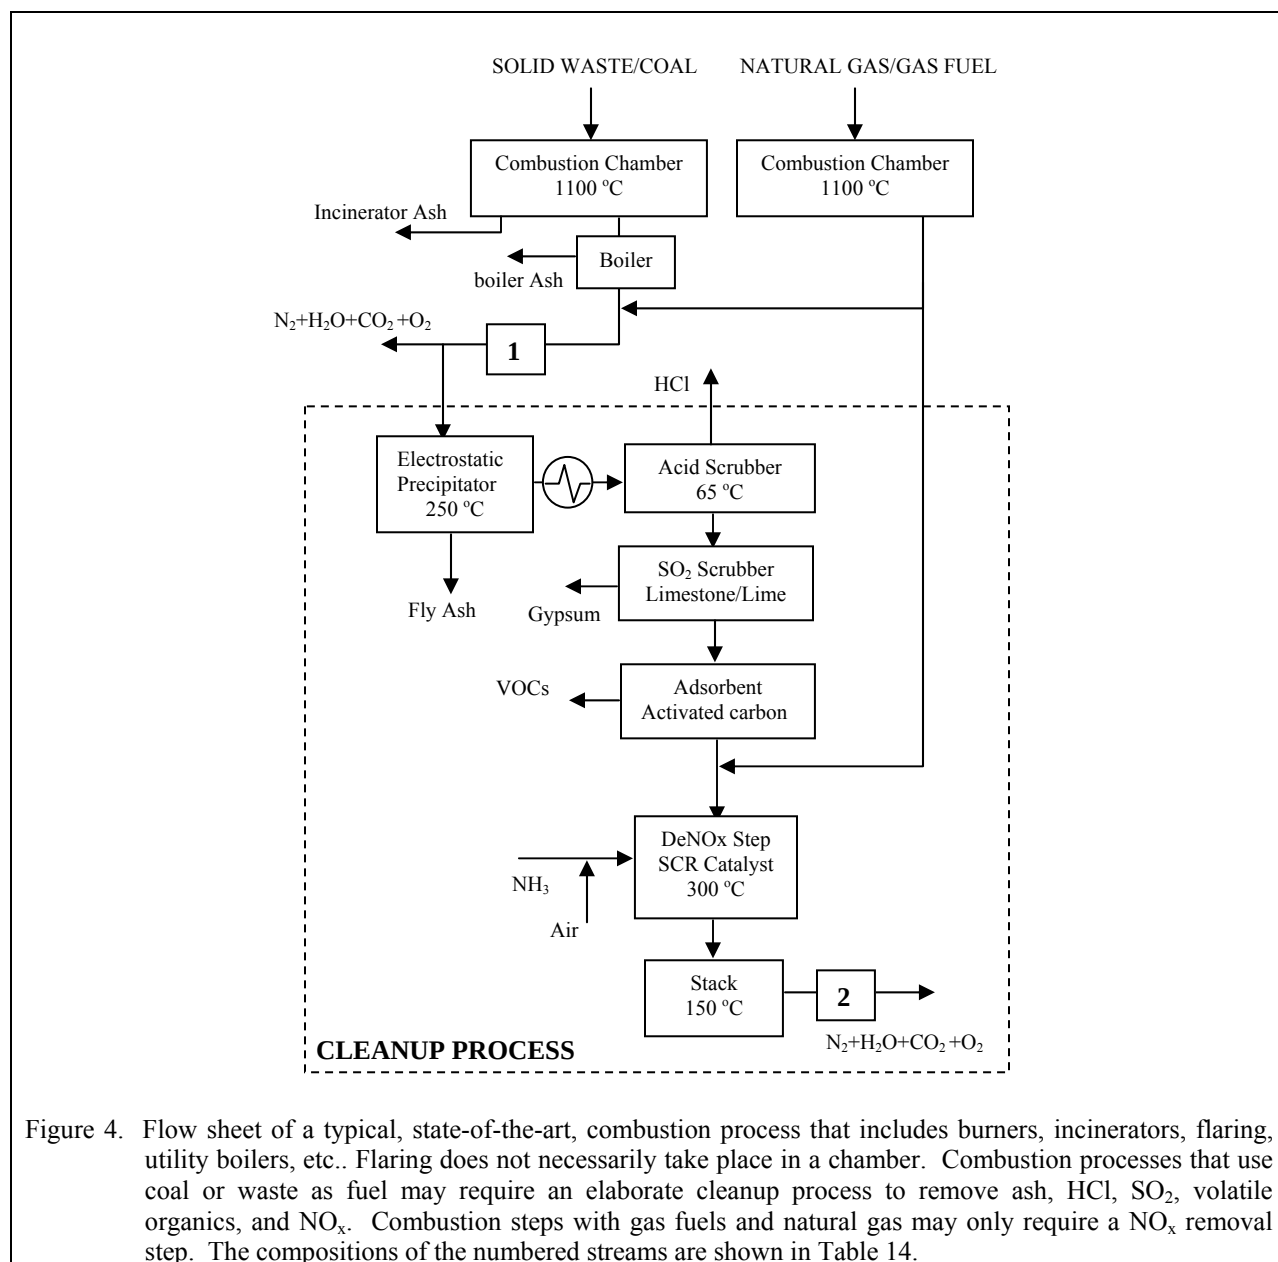

The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15.

Tables 1 and 2, and Figures 1 and 2 provide a breakdown of the energy and non-energy related CO<sub>2</sub> emissions from combustion processes. About 89% of the CO<sub>2</sub> emissions in the manufacturing industry are energy-related emissions. Almost all fossil fuel power plants for the generation of electricity fall into this group, including pulverized coal (PC) and IGCC or NGCC power plants.

The carbon-based fuel enters a chamber where it is combusted in the presence of air at a temperature of up to 1100°C. In power plants and utility boilers, the generated heat is used to generate electricity from steam turbines. In some plants, such as IGCC or NGCC power plants,

gas turbines are also used in addition to steam turbines. In the case of solid fuels, the chamber is designed to cope with the removal of ash from the bottom, and at the flue gas exit cyclones or other devices are used for gas phase particulate removal. Also, because of the ever increasing concerns over reducing the emissions of SO<sub>2</sub>, volatile organic compounds (VOCs), NO<sub>x</sub> and other contaminants from the flue gas, more recent designs include a train of gas phase cleanup processes.


In general, the cleanup of the exiting flue gas starts with the electrostatic precipitation of particles (fly ash) that could not be removed by the particle separators. This process is carried out continuously at 250°C and removes nearly 100% of the fly ash. The gas is then fed into an absorption process for the subsequent removal of HCl and SO<sub>2</sub>. In the latter case, the gas is passed through an aqueous suspension of lime that leads to the formation of CaSO<sub>4</sub> (gypsum). Next, the gas is sent to an adsorption process where activated carbon removes the VOCs. The cleanup of the flue gas is finished after a deNO<sub>x</sub> step. In this step, the NO<sub>x</sub> is catalytically converted into N<sub>2</sub> and H<sub>2</sub>O using a mixture of air and ammonia at a temperature of about 300°C. Currently, CO<sub>2</sub> generally is not recovered from flue gas; hence, it is released into the atmosphere in copious amounts that represent nearly 90% of all CO<sub>2</sub> emissions from industrial processing (Tables 1 and 2, and Figures 1 and 2).

### ***Coal Gasification [446,450-452]***


The increasing need to more efficiently and more cleanly utilize the energy contained within coal motivated the development of coal gasification processes to replace old coal-fired power plants. Typical flow sheets of coal gasification plants are given in Figures 5 and 6.

The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15. Coal gasification not only can be used for power generation, but also it can be used for H<sub>2</sub>, syngas, NH<sub>3</sub>, and even other chemical production. When it is used to generate only power, it falls under the category of combustion (Tables 1 and 2, and Figures 1 and 2). When it is designed to do produce both chemicals and power, it is referred to as an IGCC plant. In this dual mode, clearly it produces both energy and non-energy related CO<sub>2</sub> emissions (Tables 1 to 3 and Figure 3). In the act of producing power or chemicals, coal gasification processes unavoidably produce large amounts of CO<sub>2</sub> that, for the most part, are emitted to the atmosphere.

The coal or fuel in the gasification unit is exposed to a controlled atmosphere (> 20 atm and 1300°C) of both steam and oxygen to produce syngas (i.e., CO + H<sub>2</sub>), while minimizing the fraction of fully combusted carbon. The existence of these combustion and shift reactions leads to the formation of copious amounts of CO<sub>2</sub> that eventually make their way into the atmosphere. The fuel is normally a solid, such as coal, petroleum coke, biomass, or even organic solid waste. It can be fed to the gasifier dry or it can be injected in the form of a wet slurry. Heavy liquid oils can also be used in this process.

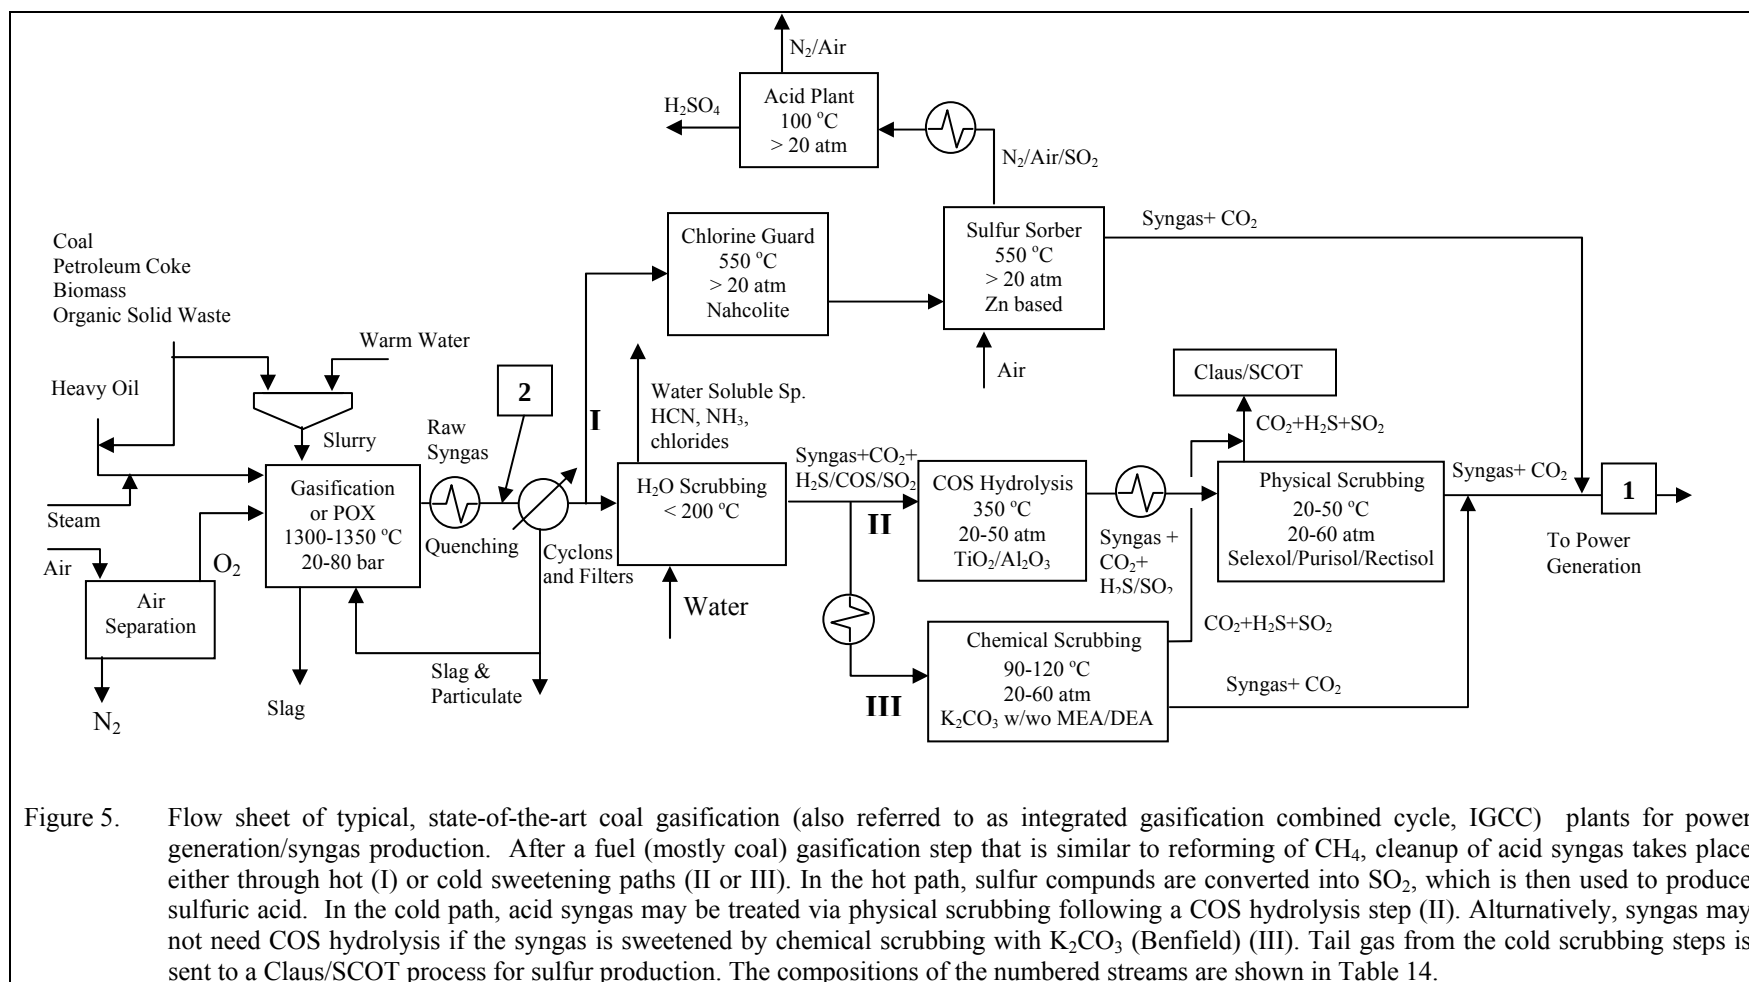



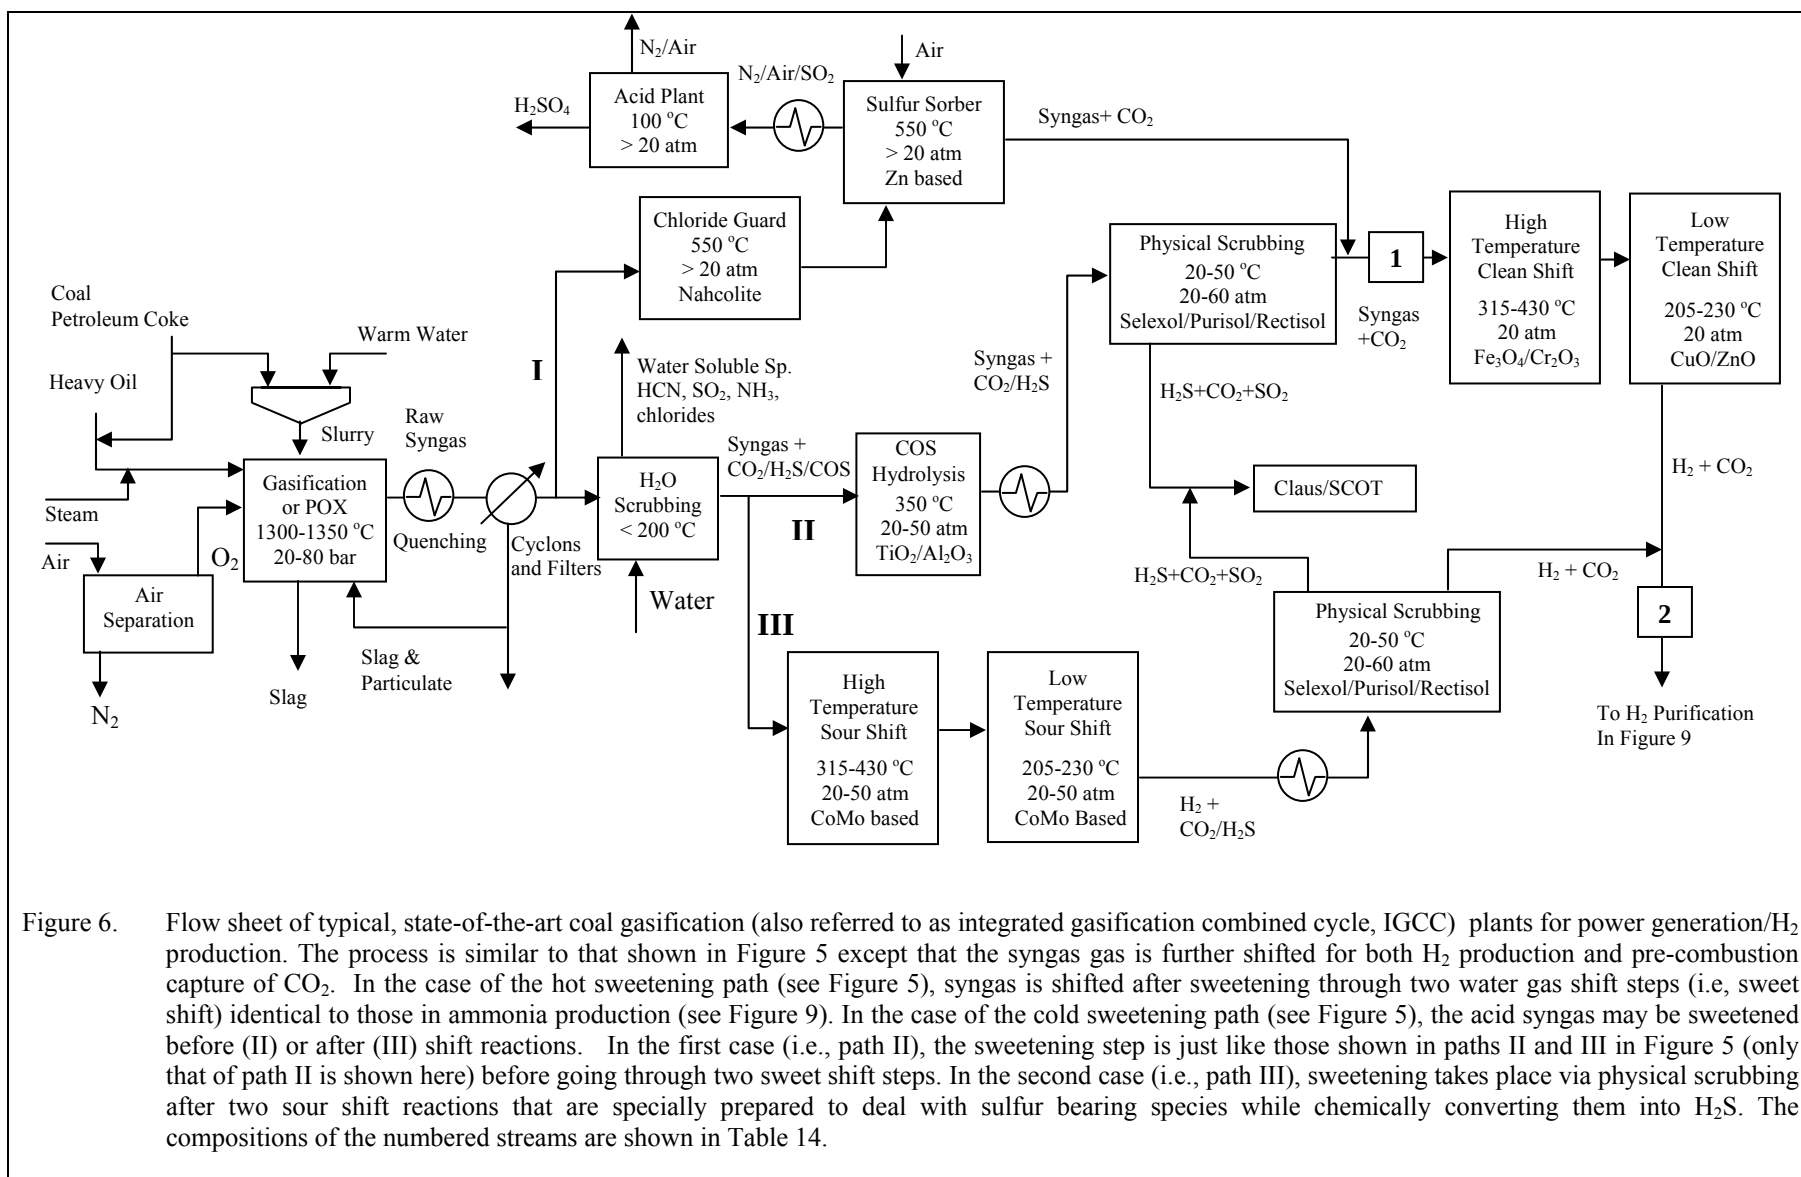

Most gasifiers are provided with purified oxygen (> 95 vol%) to significantly reduce the size of the unit and its operational costs (e.g., heat exchanging). This also is done to minimize the generation of NO<sub>x</sub>. However, due to the additional costs associated with the air separation unit, a considerable number of gasifiers operate with air.

Gasifiers produce both solids and gases as products. The solid slag is easily removed from the bottom of the gasifier. The resulting gas is very hot and contains particulate matter. It is cooled by quenching and heat exchanging. The particulates are removed using cyclones and filters. The cooled and particulate-free sour syngas is then sent through either a hot or cold sweetening process to be used either for power generation or H<sub>2</sub> (chemical) production.

In hot sweetening, the gas leaves the filters at about 550°C and more than 20 atm and enters a chloride guard reactor, followed by a hot gas cleanup unit (HGCU). In the chloride guard reactor, traces of HCl are removed from the gas by reacting with sodium bicarbonate (nahcolite) in the form of pellets. The following reaction takes place:



In the HGCU unit, the gas first goes through a column filled with a solid absorbent that contains ZnO. By simple chemical exchange, the ZnO reacts at about 550°C with all the sulfur containing compounds in the gas and converts them into ZnS. A fraction of the sweet gas produced in this step is recycled and mixed with hot air to regenerate the HGCU unit (or one that operates in parallel) once the ZnO is spent or saturated. This regeneration reaction takes place at a temperature above 750°C and the SO<sub>2</sub>-rich gas leaving the unit is sent to an acid plant to produce sulfuric acid. The resulting syngas is sent to a series of shift reactors and purification units that are based on the same processes used in steam reforming, as described below in the *Hydrogen, Syngas, and NH<sub>3</sub> Production* section.


In cold sweetening, the gas leaves the filters at a much lower temperature (350°C) and enters an acid scrubber where water is used to remove most, if not all, of the HCl, HCN, and NH<sub>3</sub> present in the gas stream. At this point, two different processes have evolved for producing power or H<sub>2</sub> (chemicals) from cold-sweetened sour syngas. In the first process, the gas is first sent to a COS hydrolysis unit (350°C), whereby a TiO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> catalyst converts most of the COS and even CS<sub>2</sub> into H<sub>2</sub>S. Then it is sent to a cold gas cleanup unit (CGCU), such as a Selexol unit or some similar process, where H<sub>2</sub>S, SO<sub>2</sub>, and other traces of sulfur-containing gases are removed. Note that a COS-CS<sub>2</sub> hydrolysis unit is not always required; a chemical scrubbing unit operating as a CGCU at 90-120°C that contains K<sub>2</sub>CO<sub>3</sub> has proven to be successful in hydrolyzing COS and CS<sub>2</sub>, while simultaneously removing sulfur-containing species all in one step. The CGCU tail gas, which contains all the sulfur compounds and a large fraction of CO<sub>2</sub>, is sent to a sulfur recovery process, such as the Claus/SCOT process, where elemental sulfur is produced. Finally, the resulting syngas is sent to a series of shift reactors and purification units that are based on the same processes used in steam reforming, as described below in the *H<sub>2</sub>, Syngas, and NH<sub>3</sub> Production* section.

In the second process, the sour syngas is sent to so a called sour shift reactor located upstream of the CGCU. This unique shift reactor contains a sulfur resistant catalyst made of Co and Mo to

treat the sour syngas. It operates at high pressure ( $> 20$  atm) and in two steps: one at an intermediate temperature ( $315\text{--}430^\circ\text{C}$ ) and the other one at a lower temperature ( $205\text{--}230^\circ\text{C}$ ). Because COS and CS<sub>2</sub> hydrolysis takes place inside this reactor, a separate hydrolysis unit is not needed in this case.

### ***Iron and Steel Manufacture [446,453-456]***

The manufacture of steel constitutes the largest industrial producer of non-energy related CO<sub>2</sub>, being responsible for about 29% of those CO<sub>2</sub> emissions (Tables 2 and 3, and Figure 3). A typical flow sheet for the manufacture of steel is given in Figure 7.

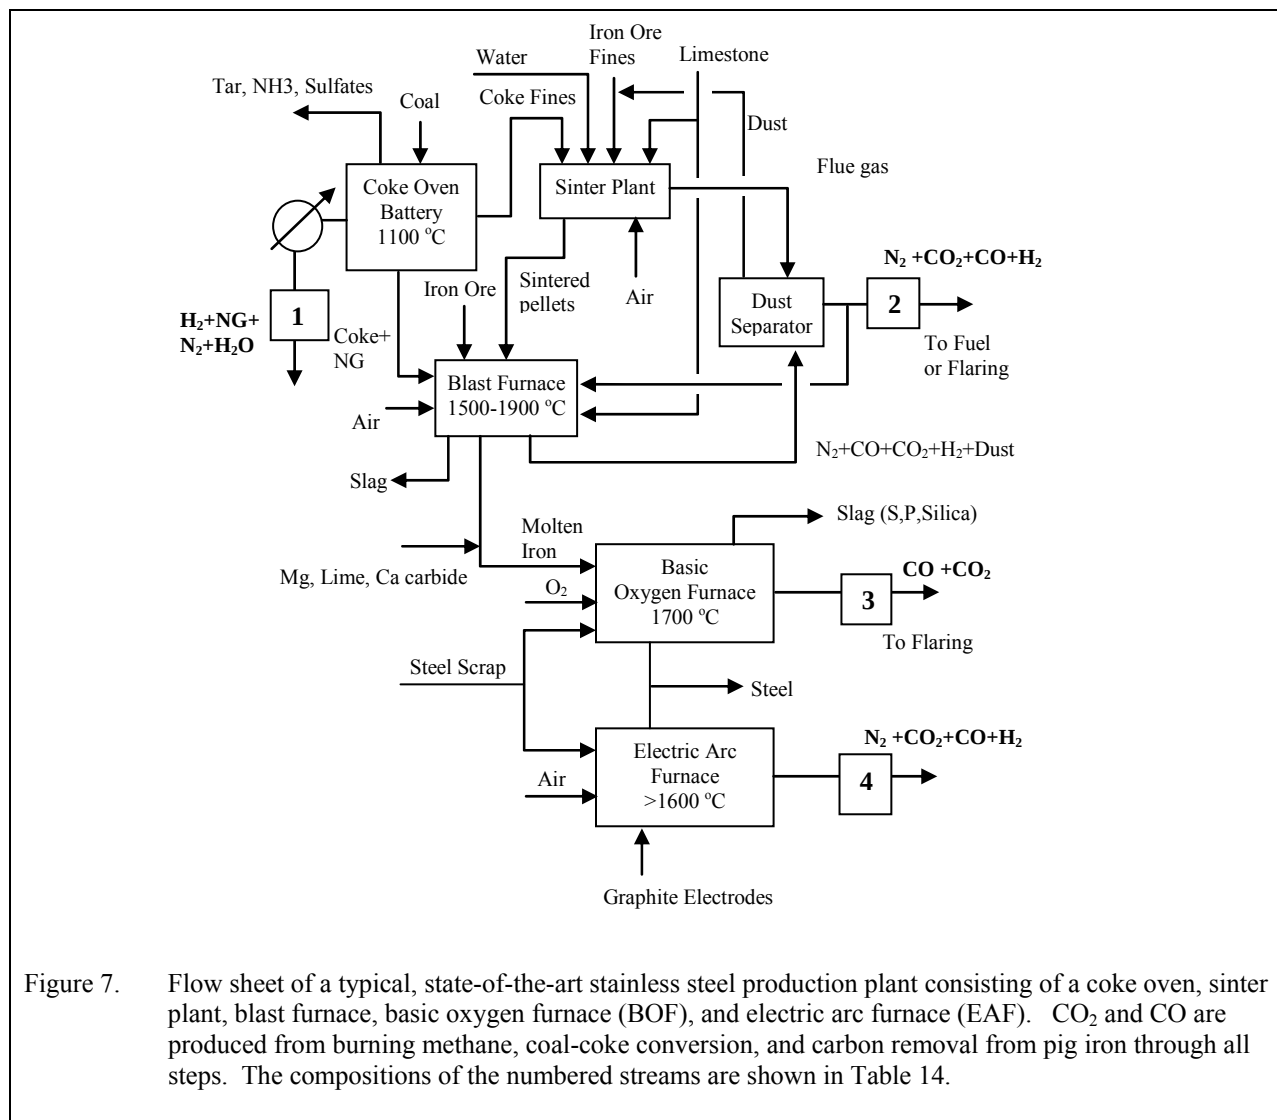

The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15. Steel manufacture starts with the coke making process, which involves the carbonization of coal at high temperature ( $1100^\circ\text{C}$ ) in an oxygen deficient atmosphere to produce coke, which is enriched in carbon relative to the raw coal. The gas leaving the coke oven is composed mainly of CH<sub>4</sub> and H<sub>2</sub> plus CO<sub>2</sub>, CO, and heavier

hydrocarbons. This flue gas is used either as fuel or it is flared.

The next step, which is carried out in a sinter plant, is a pre-treatment step in the production of iron. Fine particles of iron ore, limestone, coke, and collected dust are agglomerated by combustion with air (1200°C). These small agglomerates allow the passage of hot gases during the subsequent blast furnace operation. The result is a semi-molten mass called sinter that solidifies into porous pieces of appropriate size and strength for feeding into the blast furnace. Large quantities of CO<sub>2</sub>, CO, VOCs, and NO<sub>x</sub> emissions are produced during this step.

In the blast furnace, certain proportions of coke, iron ore, sinter, and limestone are mixed together and heated to temperatures of around 1500 to 1700°C with a controlled supply of air to produce the so called pig iron. This step is where most of the CO<sub>2</sub> is generated that does not come from the burning of fuels. The coke as a reactant is essentially burned as a fuel to heat the furnace, and as it burns, it gives off CO, which ultimately reduces the iron oxide in both the iron ore and the sinter into metallic iron according to the following reaction:



The limestone is used to remove the silica present in the ore in the form of fusible calcium silicate, which floats to the top of the molten metal; as such, it is easy to separate. Without limestone, iron silicate is formed, resulting in a loss of metallic iron. The pig iron produced in this step contains about 92% iron, about 4% carbon, and a balance of silicon, manganese, phosphorus, and traces of sulfur.


This step is followed by a step that utilizes a basic oxygen furnace (BOF). About 75% of the hot metal from the blast furnace is poured into a pear-shaped basic oxygen furnace (BOF) that tilts sideways for charging and pouring. This hot metal is then mixed with 25% purchased scrap metal, along with desulfuring agents such as lime, calcium carbide, and magnesium. With a moving lance, pure oxygen is injected into the mix at various places in the BOF to combine with carbon and other unwanted elements such as silicon and phosphorus that are present in the pig iron. The heat released due to these reactions raises the furnace temperature (> 1600°C) and facilitates melting of the mixture. CO is produced and leaves the reactor, while silica, calcium, and magnesium phosphates and sulfides become part of the slag that is separated from the molten steel.

Instead of a BOF, an electric arc furnace (EAF) is also used. In this furnace, energy is supplied electrically via graphite electrodes or chemically via mixing natural gas and oxygen through lances to melt the mixture. Whether the BOF or EAF are used, the steel forms in the same way, while producing CO and slag. Although it can process pig iron in the feed, the EAF process has been designed more specifically for the recuperation of steel from scrap. All CO produced in this and other steps in the steel industry is utilized as a reducing agent and in the generation of heat.

### ***Lime and Cement Production [446,457]***

The manufacture of cement and lime from limestone and dolomite constitute the second and fifth largest sources of CO<sub>2</sub> produced in non-energy related industrial processes (Tables 2 and 3, and

Figure 3), constituting together about 32 % of this total. A typical flow sheet for the manufacture of cement and lime is given in Figure 8. The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15. A review of the global cement industry and its associated CO<sub>2</sub> emissions has been given by Worrell et al. [458].

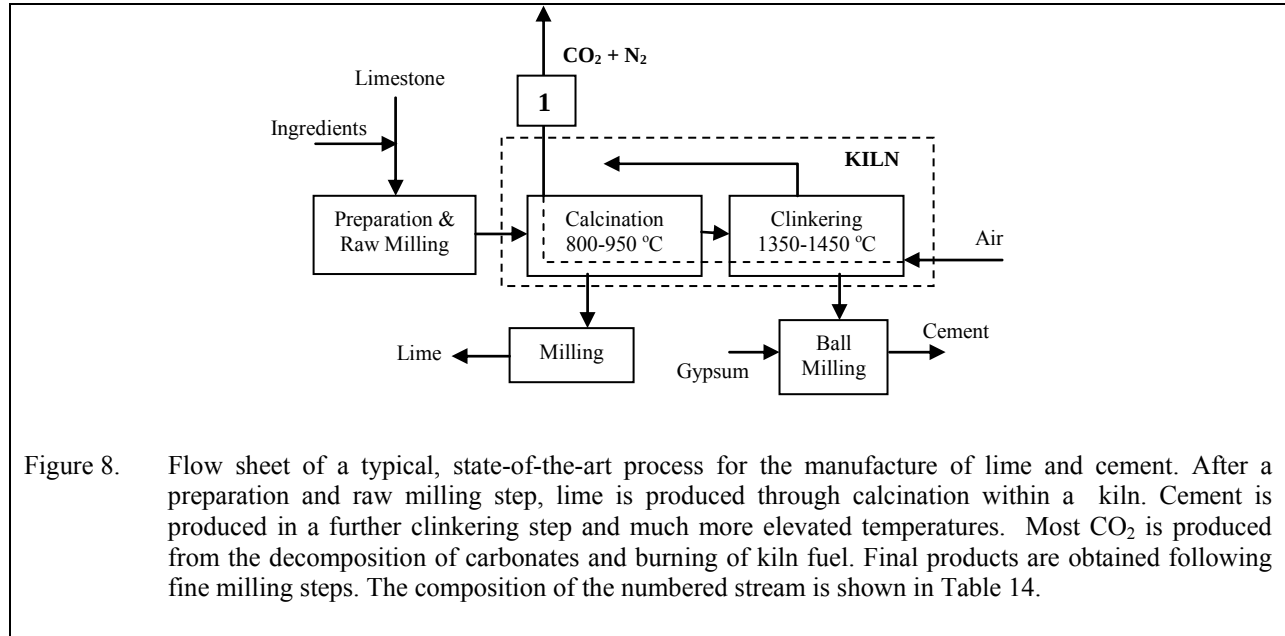

Cement normally is produced in three steps. After an extraction and coarse milling process, the raw limestone is mixed with mineral additives and water in proportions that lead to the formation of pellets (i.e., clinker) of uniform quality. After a preheating step, the pellets are inserted into a rotary kiln where they undergo two steps. The first step consists of a calcination step at 800-900°C where the calcium carbonate (i.e., limestone) in the pellets undergoes decomposition with the release of CO<sub>2</sub> according to:



The CO<sub>2</sub> is produced at around 22 vol%, with it ranging from 14% to 33 vol%. This relatively high concentration of CO<sub>2</sub> makes it ideal for recovery as a saleable product.

Farther down in the kiln, at temperatures between 1350 and 1450°C, additional clinkering completes the calcination stage and fuses the calcined raw mix into hard nodules (again referred to as clinker) that resemble small gray pebbles. The manufacture of cement is finished with a milling of the clinker to produce a fine grey powder. Gypsum (CaSO<sub>4</sub>), which controls the rate of hydration of the cement in the cement-setting process, is blended with the ground clinker, along with other materials, to produce finished cement.

Lime is produced from limestone and dolomite in a very similar process. The major difference between them is that the rotary kiln is operated in one step to form the pellets during calcination at 800-900°C. This calcination step again produces CO<sub>2</sub> according to the reaction depicted in Equation 3. The final product is then milled to produce a fine powder. This lime powder may be

sold as is or it may be mixed with water to produce a milky suspension and sold as lime slurry.

### ***Hydrogen, Syngas, and NH<sub>3</sub> Production [446]***

The manufacture of H<sub>2</sub>, syngas, and NH<sub>3</sub> constitutes the third largest industrial producer of non-energy related CO<sub>2</sub>, being responsible for about 10.4% of those CO<sub>2</sub> emissions (Tables 2 and 3 and Figure 3). A typical flow sheet for the manufacture of H<sub>2</sub>, syngas (H<sub>2</sub> + CO), and NH<sub>3</sub> is given in Figure 9. The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15. A detailed report on hydrogen, syngas, and NH<sub>3</sub> production technologies by reforming, autothermal reforming, and partial oxidation processes has been published recently by the authors [1]. A brief overview is provided below, based on a typical reforming process.

CO<sub>2</sub> is produced as a by-product in the production of H<sub>2</sub>, syngas, and NH<sub>3</sub>. These important gases are all produced in a similar fashion through a chain of reforming and shift reactions. The source of the hydrogen and carbon in these gases, and hence the CO<sub>2</sub> that is formed, stems from the reforming of natural gas and other hydrocarbon feedstocks.

After leaving the reformer reactor at temperatures of over 1000°C and pressures of up to 20 atm, the resulting syngas, which is relatively rich in CO<sub>2</sub>, is cooled down and sent to either one or two water gas shift reactors. In these reactors, H<sub>2</sub>O is utilized to convert most of the remaining CO into CO<sub>2</sub> while more H<sub>2</sub> is generated.

Before the advent of pressure swing adsorption (PSA) for H<sub>2</sub> purification in the early 1980s, older H<sub>2</sub> production plants (still in existence) required two steps for the water gas shift reaction to achieve maximum CO conversion into H<sub>2</sub> using H<sub>2</sub>O and producing more CO<sub>2</sub> as the by-product. The first water gas shift reactor was a high-temperature shift reaction that converted most of the remaining CO into H<sub>2</sub> and CO<sub>2</sub> using a Fe-Cr catalyst at 315-430°C. This step was then followed by the second water gas shift reactor, which was operated at a lower temperature of 203-230°C. This reactor utilized a Cu-Zn catalyst to convert any remaining CO into H<sub>2</sub> and CO<sub>2</sub>. The gas leaving this reactor, which contained less than 0.5 vol% CO, was sent to a high-pressure scrubbing process that removed nearly 100% of the CO<sub>2</sub> in the stream, typically at very high purity (> 98 vol%). It was then sent to a methanator, which reduced CO by converting it back to CH<sub>4</sub>.

With the introduction of new NH<sub>3</sub> plants, with PSA units replacing the CO<sub>2</sub> scrubbing step for the purification of H<sub>2</sub>, new avenues for CO<sub>2</sub> removal came into practice. Hydrogen purification with the PSA option became less expensive because it eliminated the need for the low temperature shift reactor and a methanation step to fully eliminate CO from the hydrogen stream. But the CO<sub>2</sub> was not enriched as much as it was before. The PSA tail gas does not contain more than 40 vol% CO<sub>2</sub> and is balanced with significantly high concentrations of H<sub>2</sub>, CH<sub>4</sub>, and even CO. At the present time the PSA tail gas is used as fuel, with the resulting CO<sub>2</sub> typically being released to the atmosphere.

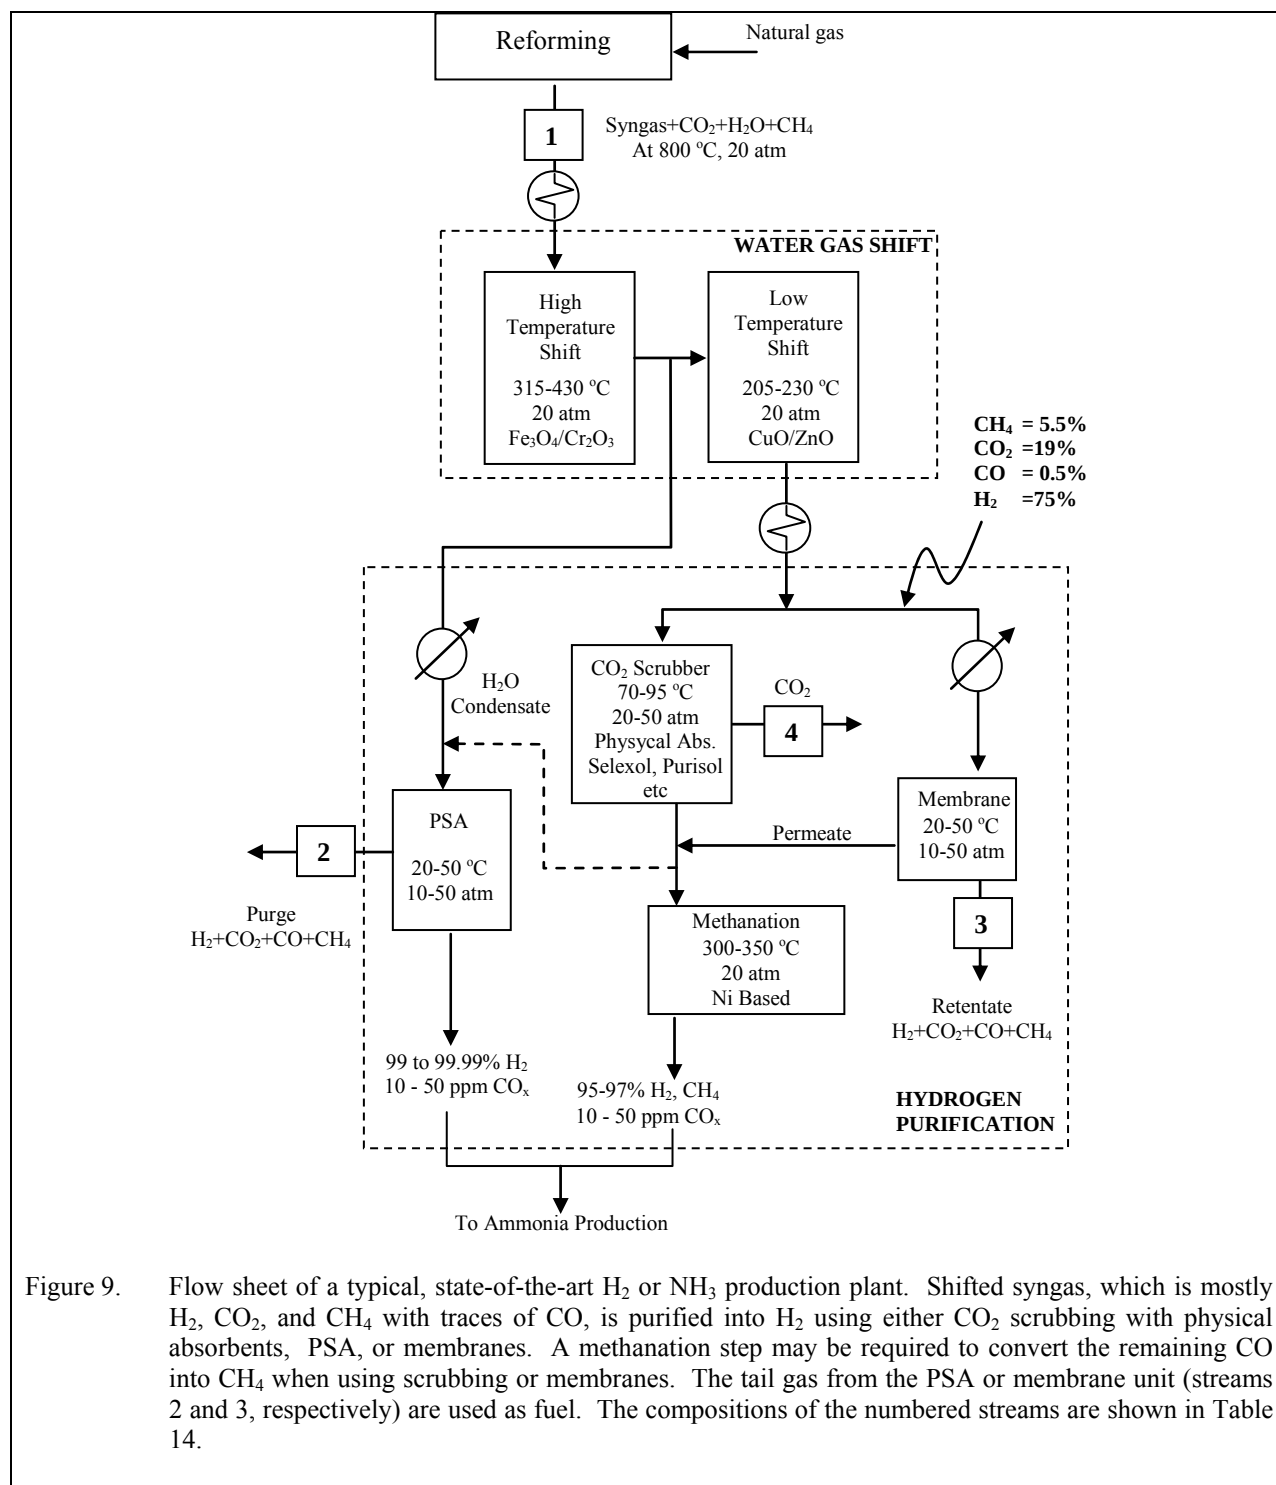



Figure 9. Flow sheet of a typical, state-of-the-art H<sub>2</sub> or NH<sub>3</sub> production plant. Shifted syngas, which is mostly H<sub>2</sub>, CO<sub>2</sub>, and CH<sub>4</sub> with traces of CO, is purified into H<sub>2</sub> using either CO<sub>2</sub> scrubbing with physical absorbents, PSA, or membranes. A methanation step may be required to convert the remaining CO into CH<sub>4</sub> when using scrubbing or membranes. The tail gas from the PSA or membrane unit (streams 2 and 3, respectively) are used as fuel. The compositions of the numbered streams are shown in Table 14.

H<sub>2</sub> selective membrane technology also is available commercially and is being used for H<sub>2</sub> production. This technology takes advantage of the relatively high H<sub>2</sub> concentration (> 75 vol%) produced from the low temperature shift reactor. However, the permeate, which is rich in H<sub>2</sub>, requires recompression and may contain significant amounts of CO<sub>2</sub> that forces further H<sub>2</sub> purification. The high pressure-reject gas, which contains H<sub>2</sub>, CO<sub>2</sub>, CO, and CH<sub>4</sub> currently is

used for fuel, with the CO<sub>2</sub> again being released to the atmosphere.

### **Natural Gas Production [446,459]**

A typical flow sheet for natural gas production is given in Figure 10. The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15. Natural gas production constitutes the fourth largest producer of CO<sub>2</sub> as a result of natural purification. This category accounts for around 10.1% of the non-energy related CO<sub>2</sub> emissions (Tables 2 and 3, and Figure 3).

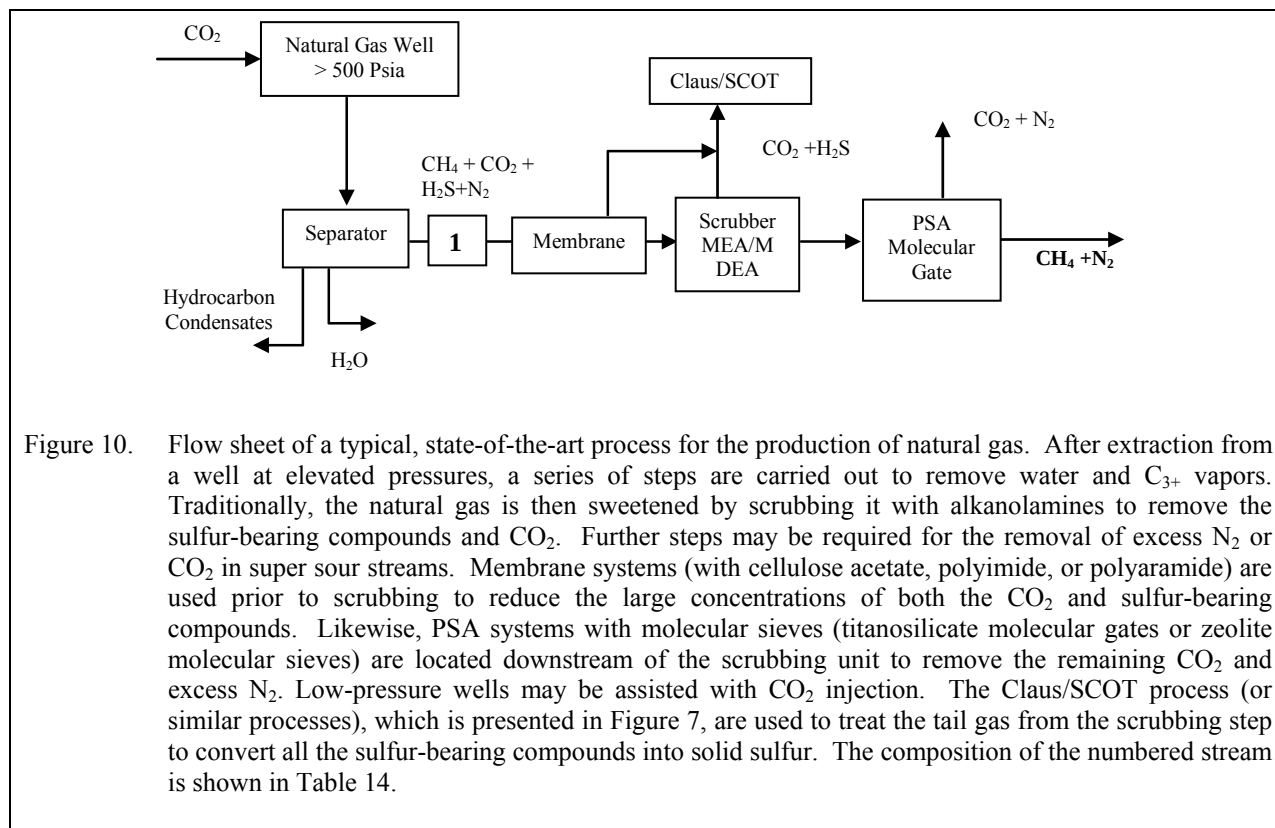

Processed natural gas consists principally of methane, with a much smaller fraction (< 5 vol%) of ethane and propane. In a raw state, it is normally extracted as an associated gas, either free or dissolved, when extracted from oil wells, or as a non-associated gas when extracted from gas and condensate wells where there is little or no crude oil. Once separated from crude oil (if present), in addition to ethane and propane, natural gas in the raw state also contains some butanes and pentanes, and it may contain considerable amounts of water vapor, H<sub>2</sub>S, CO<sub>2</sub>, He, N<sub>2</sub>, and other compounds such as Hg. The CO<sub>2</sub> emissions result from the so called natural gas sweetening steps that are associated with natural gas processing.

When natural gas contains H<sub>2</sub>S, other sulfur bearing compounds, and CO<sub>2</sub>, it normally is referred to as sour gas. After a series of dehydration steps, either with glycol absorption or adsorption with silica gel or activated alumina, and after removal of the C<sub>2</sub>-C<sub>5</sub> fraction via absorption, the sour gas is sweetened through an absorption scrubbing process (typically, an ethanol-amine based process) that is followed by a desulfurization step (Claus/SCOT process), where all sulfur




compounds and CO<sub>2</sub> are removed. Natural gas sweetening is responsible for more than 15% of the total sulfur production in the US.

In the case of natural gas streams that are rich in N<sub>2</sub>, only those streams containing more than 10 vol% N<sub>2</sub> can be economically blended with more dilute streams after the sweetening step. However, the concentration of CO<sub>2</sub>, sulfur, and N<sub>2</sub> in some natural gas wells can be so high that traditional steps for gas sweetening may be insufficient. It is known, for example, that in 1 of every 10 wells the content of CO<sub>2</sub> is larger than 2 vol% and that in 1 of every 100 wells the CO<sub>2</sub> content is larger than 20 vol%. In the latter case, the CO<sub>2</sub> concentration can even exceed 50 vol%. The same is true with H<sub>2</sub>S and N<sub>2</sub>, where concentrations may vary between 2 and 98 vol% for the former and up to 20 vol% for the latter.

### ***Aluminum Manufacture [446,454-456,459,460]***

The manufacture of aluminum constitutes the sixth largest single source of non-energy related CO<sub>2</sub> emissions (Tables 2 and 3, and Figure 3) or about 2.6% of the total. A typical flow sheet for the manufacture of aluminum is given in Figure 11. The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15.

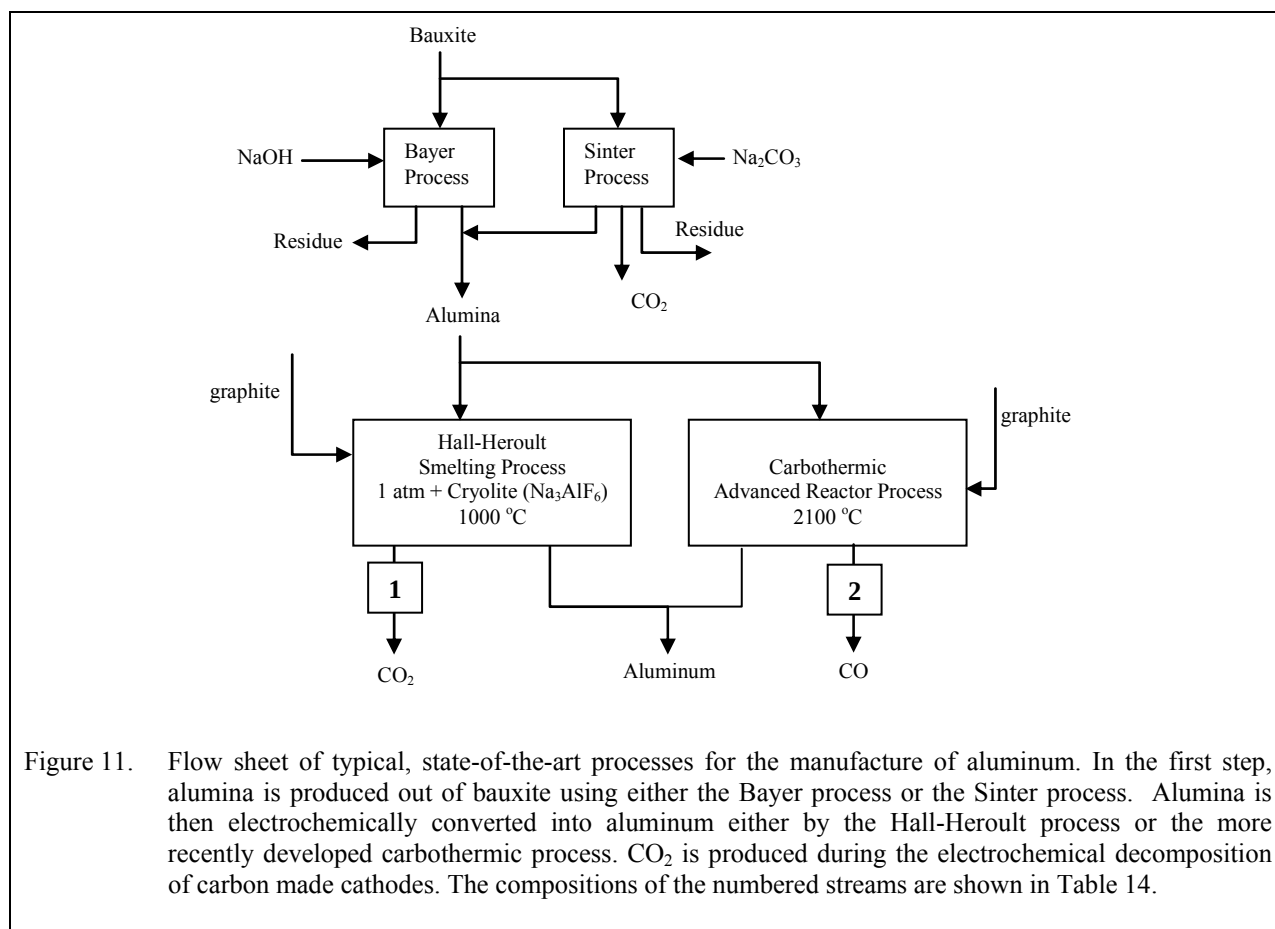


The manufacture of aluminum starts with the production of alumina from bauxite. Bauxite is a mineral rich in gibbsite ( $\text{Al}_2\text{O}_3 \cdot 3\text{H}_2\text{O}$ ) and boehmite ( $\text{Al}_2\text{O}_3 \cdot 3\text{H}_2\text{O}$ ). It also contains significant concentrations of oxides and hydroxides of Fe, Ti, and Si. Alumina is manufactured via the Bayer process, the Sinter process, or a combination of the two processes.

In the Bayer process, which is considered economically suitable for bauxites containing 30-60%  $\text{Al}_2\text{O}_3$  as aluminum hydroxides and less than 7%  $\text{SiO}_2$  as clay (kaolin) minerals, the bauxite is reacted with a hot aqueous solution of NaOH ( $\sim 200 \text{ g/L}$ ) to extract the aluminum in the form of an oxide (such as  $\text{Na}_2\text{O} \cdot \text{Al}_2\text{O}_3$ ). The temperature of the digestion process varies between 150 and 250°C depending on whether the bauxite is richer in gibbsite or boehmite. Boehmite cannot be economically extracted below about 200°C. This digestion process is followed by a sedimentation and filtration step, where oxides of Fe, Ti, and Si are removed. The caustic aluminate liquor is then sent to a crystallizer (60-70°C) that forms precipitates of gibbsite. The precipitate is dried and filtered and finally undergoes a dry calcination step at 900-1100°C that leads to the formation of 99.5% pure alumina.

The Sinter process starts with a rotary kiln, wherein pellets of the bauxite and minerals of sodium carbonate and sodium hydroxide are converted into  $\text{NaAlO}_2$  at a relatively high temperature of 900-1100°C. The sintered material is then converted into a very fine white alumina powder after realizing a series of steps that include water extraction, precipitation, and desilication. However, because of its complexity and high energy consumption, the Sinter process is of minor commercial significance compared to the Bayer process.

The purified alumina is then fed into a Hall-Heroult smelting process, consisting of one or more (typically three) potlines of several ovens, where aluminum is produced electrochemically at about 1000°C. The process is based on the use of cryolite ( $\text{Na}_3\text{AlF}_6$ ), which melts at temperatures a little under 1000°C. It is able to dissolve alumina to the extent of 15 wt% at 1030°C. Without cryolite, the temperature of the reactor would need to be over 2000°C, which is when alumina starts to melt. The electrochemical energy is provided in the form of graphite anodes and carbon cathodes placed in the upper and lower parts of the reactor, respectively.  $\text{CO}_2$  is evolved from the surface of the anodes and becomes the largest fraction of the off gas, while alumina reduces into aluminum when in contact with the cathode surface. The overall reaction is given by:




Besides  $\text{CO}_2$ , the major emissions are perfluorocarbons that result from the decomposition of cryolite and  $\text{SO}_2$  that derives from sulfur impurities in the graphite.

An alternative electrochemical process to the Hall-Heroult process, recently developed for the production of aluminum out of alumina, is the carbothermic advanced reactor process (CARP). CARP also uses graphite as the anode, but it eliminates the use of cryolite so that the reactor temperature must reach 2000°C. This process has been shown to be more economically viable, and it eliminates all perfluorocarbon and carbon anode baking furnace emissions. The major component of the off gas is CO instead of  $\text{CO}_2$ , which can be flared to produce  $\text{CO}_2$  anyway.

## Sulfur Recovery Processes [446,461,462]

Sulfur recovery in the petroleum refineries, coke production and natural gas sweetening is another important source of CO<sub>2</sub> emissions. Sulfur recovery constitutes around 25% of the CO<sub>2</sub> emissions produced in the natural gas industry, while at the same time it constitutes less than 2% of the total non-energy related CO<sub>2</sub> emissions. Hence, the CO<sub>2</sub> emissions due to sulfur recovery processes are not included here in tables or figures.

Today, the sulfur recovery industry produces about 9 millions tons of pure sulfur per year, 10% of which is in the form of sulfuric acid. Around 17 % of the total sulfur produced in the U.S. comes from natural gas sweetening, while the rest comes from oil refineries and a very minor fraction from coke manufacturing. Currently, the principal process that is used for sulfur recovery is based on the Claus and Shell-Claus offgas treating (SCOT) technologies, which constitute more than 80% of the total sulfur recovery plants in service in the U.S. A typical flow sheet for these technologies is given in Figure 12. The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15.

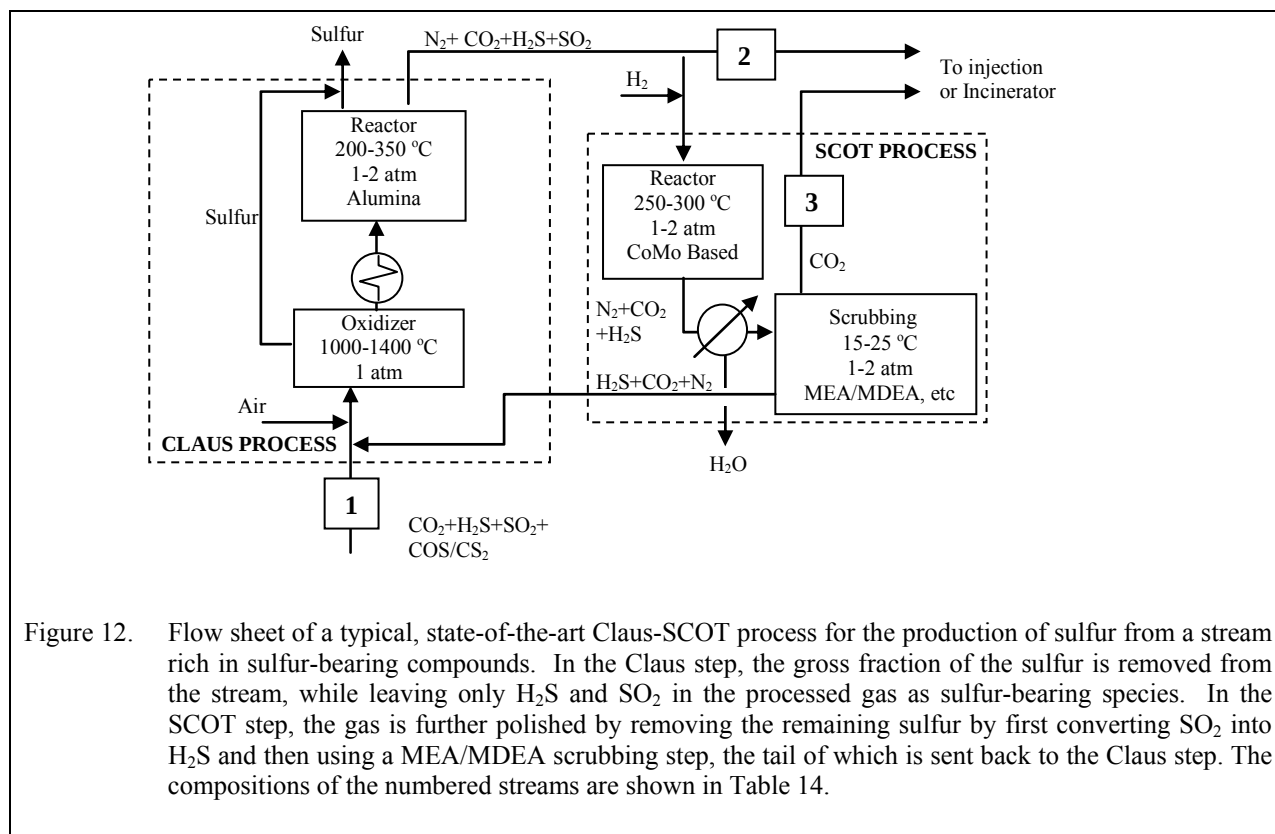

The Claus/SCOT process removes species from sour streams that contain sulfur and converts them into elemental sulfur. The process is designed to treat gas streams containing more than 50 vol% H<sub>2</sub>S, with CO<sub>2</sub> being the second largest species. The process starts with the Claus step, which produces elemental sulfur. This process is followed by the SCOT process, which converts all sulfur compounds in the gas leaving the Claus unit (e.g., SO<sub>2</sub>, COS, CS<sub>2</sub> and elemental sulfur), into H<sub>2</sub>S, which is then recycled back to the Claus step for further processing. The

remaining gas is sent to an incinerator prior to exhausting to the atmosphere.

The Claus process consists of two steps. The first step, which is referred to as the thermal step, is basically an incineration step. It is where the sour gas becomes combined with air at high temperatures (1000-1400°C) to oxidize at least one third of the H<sub>2</sub>S into SO<sub>2</sub> according to:



This reacted gas then goes to the second step that consists of a series of reactors and condensers, where H<sub>2</sub>S and SO<sub>2</sub> react (200-350°C) to produce elemental sulfur according to:



The elemental sulfur is removed in the liquid state through the condensers.

The reactors consist of packed beds containing alumina as the principal catalyst, but they may use as an option Co-Mo as the catalyst. At this step, all traces of NH<sub>3</sub> also react to form H<sub>2</sub> and N<sub>2</sub>, and all traces of organic compounds combust into H<sub>2</sub>O and CO<sub>2</sub>. More than 95% of the sulfur compounds are removed in this step. Several improvements have been done to improve this process. For example, the superclaus process converts H<sub>2</sub>S directly into elemental sulfur in one step. The gases produced during this step are mainly N<sub>2</sub>, CO<sub>2</sub>, and H<sub>2</sub>O.


The SCOT process also consists of two steps. The first step consists of a reactor containing Co-Mo catalyst, where all the sulfur compounds react at about 250-300°C with H<sub>2</sub> to form H<sub>2</sub>S. Hydrogen may already be present in the Claus tail gas. Otherwise, it is added upstream. This reactor is then followed by an absorption process that removes more than 99% of the H<sub>2</sub>S from the processed gas, where the H<sub>2</sub>S-rich gas is sent back to the Claus step. Similar to the Claus process, the gases produced during the SCOT process are mainly N<sub>2</sub>, CO<sub>2</sub>, and H<sub>2</sub>O.

### ***Landfill and Coal Bed Methane Gases [463,464]***

Typical flow sheets for landfill and coal bed methane gas production are given in Figures 13a and 13b. The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15. These two gas streams are not included in any category in Table 2. Nevertheless, they are both sources of CO<sub>2</sub> emissions, albeit, relatively new sources.

Landfills are scattered all over the U.S. and the world. Each one covers anywhere from 10 to 1500 acres of land. They consist of layers 50 to 100 ft thick of solid human-generated wastes that are entombed beneath 5 ft of inert material that plays the role of reducing both gas permeation and rainfall water infiltration.

Landfill gas (LFG) is produced naturally from the anaerobic decomposition of the waste material. As a result, it contains relatively high concentrations of CH<sub>4</sub>. This gas either slowly permeates the landfill cap into the environment, or it builds up pressure within the landfill

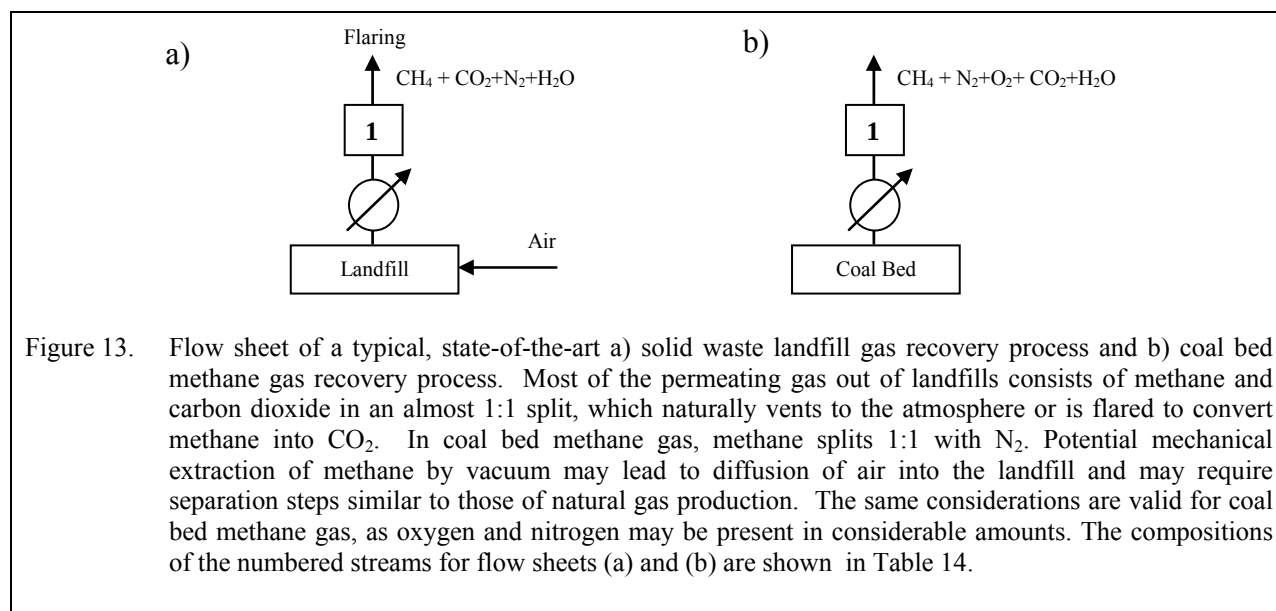

creating the potential for an explosion. Over the past few decades, pipes have been installed in most capped landfills to facilitate bringing the LFG to the surface for flaring or recovery as an energy source. For a typical LFG site, the flow rate is 2.5 million standard cubic feet of gas per day.


About 45 vol% of typical LFG is composed of CH<sub>4</sub>. Another 45 vol% is composed of CO<sub>2</sub>. The remaining 10 vol% is composed of a small amount of water vapor (saturated). N<sub>2</sub> and some toxic non-methane organic compounds, such as VOCs, and sulfur- and chlorine-bearing compounds are also present in typical LFG.

In the forced extraction of LFG for energy recovery, the extraction lines are subjected to vacuum. This causes the infiltration of significant amounts of air into the landfill. As a result, significant amounts of N<sub>2</sub> become incorporated into the extracted gas mixture, which dilutes both the CH<sub>4</sub> and CO<sub>2</sub> constituents. Some, but not necessarily all, of the oxygen is bioprocessed near the surface before reaching the suction lines.

Coal bed methane gas represents not only a virtually untapped source of energy, but also another source of CO<sub>2</sub> emissions if tapped for this energy. However, the coal mine itself is being considered as a viable place to sequester CO<sub>2</sub>. In such a situation, the CO<sub>2</sub> emissions are offset by the CO<sub>2</sub> storage, and the storage of CO<sub>2</sub> comes with energy benefits because the mine produces coal bed methane gas that can be recovered during the storage process. Coal bed methane gas, much like landfill gas, contains N<sub>2</sub>, O<sub>2</sub>, CH<sub>4</sub>, CO<sub>2</sub> and H<sub>2</sub>O, but the amounts of these gases in each case are quite different. Coal bed methane contains about the same amount of CH<sub>4</sub>, but much more N<sub>2</sub> and O<sub>2</sub> and much less CO<sub>2</sub> than landfill gas (Table 14). The composition of coal bed methane gas can vary considerably, however, from coal mine to coal mine.

### ***Fermentation to Produce Ethanol [465]***

A typical flow sheet for the manufacture of ethanol through fermentation is given in Figure 14.

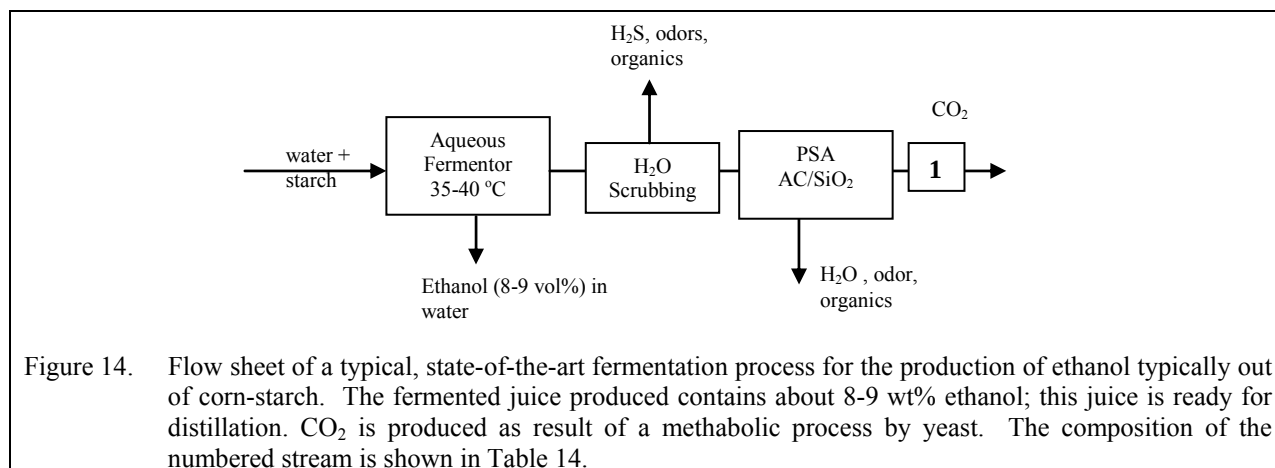

The corresponding stream compositions are given in Table 14, and capacity and flow rate information is given in Table 15. Ethanol manufacture is not included in any table or figure because it constitutes less than 2% of the non-energy related CO<sub>2</sub> emissions. Nevertheless, ethanol manufacture from the fermentation of either cornstarch or ground whole corn is increasingly becoming a significant source of CO<sub>2</sub> emissions. During 2004, 3.4 billion gallons of ethanol were produced in the US, a nearly 21% increase from the 2.81 billion gallons produced the previous year. It is highly likely that the non-fuel related CO<sub>2</sub> emissions in this area have already overcome those of the aluminum industry.

Nearly 4000 tons of CO<sub>2</sub> are produced along with each million gallons of ethanol. In countries that promote the use of ethanol as a motor fuel, a growth trend is apparent and likely to continue. The ethanol produced worldwide by fermentation constitutes more than 90% of the manufactured ethanol destined for use as a motor fuel. In recent years it has accounted for around 1% of the U.S. gasoline supply, which corresponds to the U.S. using nearly 2 billion gallons of fuel ethanol annually. This is changing rapidly in the US, with its use on the rise.

The ethanol fermentation process is carried out in a batch mode at a temperature of around 35°C. Water is mixed with baking yeast and milled corn that contains between 150 and 250 g/L of starch. The reactants are converted into a juice that contains between 7 and 9 vol% percent ethanol. The offgas is mostly CO<sub>2</sub>, with H<sub>2</sub>O and ethanol being very minor components. After a series of purification steps, including odor removal and drying, much (but not all) of the CO<sub>2</sub> produced during ethanol manufacture is being sold for commercial use. Adsorption processes for trace contaminant and moisture removal, followed by condensation and liquefaction are the principal methods for the purification of the CO<sub>2</sub> generated from ethanol production.

### **Mitigation Approaches to Combat CO<sub>2</sub> Emissions**

One approach to address CO<sub>2</sub> emissions worldwide is known as the Kyoto Protocol, which was introduced in December 1997. So far 120 countries, responsible for 44% of the world's

greenhouse gas emissions have ratified this agreement; the U.S. has not signed on. In general, these countries have agreed to reduce their anthropogenic CO<sub>2</sub> equivalent emissions of greenhouse gases to levels that are at least 5% below their 1990 levels for the period of 2008 to 2012. As of early 2006, a number of countries had begun curbing emissions, including Germany, which has cut emissions to four-fifths of their 1990 levels. However, global CO<sub>2</sub> emissions are still rising. Emissions from Canada and Japan, two countries that ratified the Kyoto Protocol, are increasing [466], and Canada has admitted that the required Kyoto protocol emissions levels are unachievable [467]. It appears that the Kyoto Protocol will be challenged to meet its goals.

Another approach that has been quite effective outside the U.S. has been the institution of a tax associated with the release of CO<sub>2</sub> into the atmosphere. As an example, a 1996 Norwegian carbon tax of \$50 U.S. per ton of CO<sub>2</sub> produced forced a natural gas producer to store CO<sub>2</sub> in an undersea aquifer rather than release it into the air [468]. A penalty or tax on CO<sub>2</sub> emissions in the U.S. will likely need to be considered, especially on fossil fuel power plant operations.

There has also been a drive to develop energy efficient and cost effective technologies to integrate the production of energy with the production of chemicals. The IGCC power plants that arose in the mid 1980s are designed to produce H<sub>2</sub>, synthesis gas, Fisher-Tropsch liquids, ammonia, methanol, fuel and town gases, mid distillates, steam, and or electricity from various fossil fuel feedstocks. A summary of the 29 largest commercial IGCC or related processes (e.g., NGCC power plants) that are operating or under development as of January 2000 is provided in Table 16. Also, numerous demonstration projects are under way worldwide and in the US.

There are a number of reported benefits of IGCC technologies compared to traditional PC-fired power plants [469]. An IGCC is currently the most efficient means to convert coal into electricity, requiring around 10 to 35% less fuel compared to traditional coal fired power plants. They also require about 30% less water than their coal fired counterparts because the turbines do not require cooling. Their footprint is also considerably smaller, and an IGCC plant does not contribute nearly as much waste to landfills because many of the wastes are saleable items. Finally, an IGCC plant is more amenable to CO<sub>2</sub> capture and sequestration as the CO<sub>2</sub> can be removed before entering the turbine, whereas in traditional coal fired power plants it can only be removed after combustion. However, the capital and operating costs of an IGCC plant are not as favorable as initially anticipated [470], and operational problems have plagued some units [471].

A recent MIT report [470] presented a study on the impact of a CO<sub>2</sub> emission tax on the cost of retrofitting existing PC or building new (e.g., IGCC) fossil fuel power plants based on old and new technologies with the tax ranging from \$1 to \$35/t CO<sub>2</sub>. When a CO<sub>2</sub> tax was not considered, the PC type power plant was found to be more economical than the IGCC type power plant, but only by a small margin [470]. However, when a tax of \$10 to \$30/t CO<sub>2</sub> was factored into the analysis, the IGCC type plant became marginally more economical than a PC type power plant. Since it is anticipated that CO<sub>2</sub> capture and storage technology may be considered as an essential part of any future power plant, IGCC technology should become the standard for the industry. Because IGCC technology is more amenable to CO<sub>2</sub> capture, it should also foster the continued development of CO<sub>2</sub> recovery, capture, storage, and sequestration technologies.

The U.S. DOE has also shown that the separation of CO<sub>2</sub> represents 75% of the overall cost associated with its separation, storage, transport, and sequestration operations. This would have a significant impact on the cost of electricity. For example, a typical 500 MW PC fired power plant produces 11,000 t CO<sub>2</sub>/day [2]. The U.S. DOE has estimated the cost of capturing CO<sub>2</sub> from power plants and the impact on the cost of electricity [3]. The cost to recovery CO<sub>2</sub> from fossil fuel power plant combustion processes is estimated to be \$40/t of CO<sub>2</sub> produced using currently available technology (e.g., amine scrubbers and cryogenic coolers). This cost could raise the price of electricity by \$0.025 to \$0.04/kWh. With electricity costs varying from around \$0.08 to \$0.11/kWh, this would represent up to a 50% increase in the cost of electricity – thus, the need for improved technology, like IGCC and other technologies, is clear.

It is worth putting the above numbers on the CO<sub>2</sub> emissions from a typical 500 MW coal fired power plant into perspective. There are around five hundred 500 MW coal fired power plants in the U.S. today that produce 11,000 t CO<sub>2</sub>/day. With the density of cryogenic or compressed liquid CO<sub>2</sub> (1.03 g/cm<sup>3</sup>) being essentially that of water (1.00 g/cm<sup>3</sup>), the volume of liquid CO<sub>2</sub> that must be processed per year from each one of these power plants fills two 100 story buildings the size of the twin towers. This is a daunting volume of gas or liquid CO<sub>2</sub> that must be stored underground at each power plant (improbable) or transported via a gas or liquid pipeline to a yet to be determined centralized CO<sub>2</sub> sequestration site (probable, but costly as noted above).

To address the complex issues of CO<sub>2</sub> emissions, a “CO<sub>2</sub> Capture Project” was initiated in 2000 by eight of the world's leading energy companies, including BP, ChevronTexaco, Eni, Norsk Hydro, Suncor, Shell, EnCana, and Statoil. This substantial, international effort addresses the issues to achieve an environmentally acceptable reduction of CO<sub>2</sub> emissions with competitive pricing that is compatible with our global energy supply. Under the leadership of Linda Curran of BP, this team aims to develop new, breakthrough technologies to reduce the cost of CO<sub>2</sub> separation, capture, and geologic storage from combustion sources. This R&D is being conducted together with governments and other stakeholders to deliver technology that is cost-effective and meets the needs of society. Hopefully these technologies will be widely used by many different industries. More information can be found at <http://www.co2captureproject.org>.

In recent years, a group of scientists from Harvard, Columbia, and MIT, led by Isaac Berzin through GreenFuel Technologies Corp., have been developing a technology that uses algae to reduce CO<sub>2</sub> emissions from power plants. The approach is quite attractive as algae not only have the ability and capacity to effectively separate CO<sub>2</sub> from gas streams, but its biomass can also be used for biodiesel production. In fact, algae growth can be so prolific that biodiesel generated from algae can yield about 15,000 gallons of biodiesel per acre per year compared to only 60 gallons of biodiesel per acre per year from soybean. Putting this into perspective, a 1,000 MW power plant using the GreenFuel system could produce 40 million gallons of biodiesel and 50 million gallons of ethanol per year on a 2,000 acre farm near the power plant. The fuel produced from this one farm in a year corresponds with about 20% of the amount consumed daily in the U.S. by transportation. Moreover, with a 3 MW cogeneration demonstration plant at MIT having 50 to 80% of its CO<sub>2</sub> emissions removed by the algae-based system, the potential to remove 100% of the CO<sub>2</sub> emissions from power plants certainly exists. GreenFuel has launched small projects in Arizona, Massachusetts, and New York. A large U.S. utility company and a major U.S. power generator are also poised to begin partnerships with them to build full-scale power



plants. More information can be found in two patent applications by Berzin [472,473] and at the GreenFuel website: <http://www.greenfuelonline.com>.

### **Expanding the Definition of CO<sub>2</sub> Capture Approaches used in Power Plants**

In this section, post-combustion, pre-combustion, and oxyfuel combustion approaches that traditionally have been considered for the capture of CO<sub>2</sub> from fossil fuel power plants are described in such a way as to make them general approaches that can be adopted for use with any CO<sub>2</sub> producing process. The post-combustion approach consists of the removal of CO<sub>2</sub> from flue gas. Flue gas typically is low in both pressure and CO<sub>2</sub> concentration (1 atm, and 3 to 20 vol%, respectively). The post-combustion approach is the only economical approach to existing air-fueled power plants based on pulverized carbon or natural gas fuel sources.

In the pre-combustion approach, CO<sub>2</sub> is separated from the gas stream prior to its conversion into flue gas. This approach is applied to produce gases other than CO<sub>2</sub>, such as CO and H<sub>2</sub>, from a potentially CO<sub>2</sub>-producing source. The pre-combustion approach is unique to the IGCC and NGCC power plant technologies. Nevertheless, the gas to be treated consists typically of synthesis or shifted gas at relatively high partial pressures of CO<sub>2</sub> (15 and 40 vol% at total pressures of over 20 atm).


In the oxyfuel combustion approach, N<sub>2</sub> is excluded from the combustion process to produce flue gas with elevated CO<sub>2</sub> concentrations. This methodology also eliminates the need for post combustion NO<sub>x</sub> removal. Also, in IGCC and NGCC power plant technologies controlled amounts of pure oxygen are added to achieve partial oxidation of the fuel during the initial gasification step. The oxyfuel combustion approach also could be applied to existing fossil fuel power plants, but the design and materials of construction may not be compatible with the use of higher concentrations of oxygen.

More broadly defined post-combustion, pre-combustion, and oxyfuel combustion concepts that can be applied to CO<sub>2</sub> separations in non-energy related processes are presented conceptually in Figure 15. The post combustion approach involves the use of any CO<sub>2</sub> capture step where the gas stream has no energetic value. A typical gas may consist primarily of flue gas produced during a combustion or flaring step. Examples of these kinds of gas streams include those resulting from metabolic combustion (i.e., fermentation) or reactions facilitated by the direct contact of a combustion step, such as autothermal reforming, or those in cement kilns and lime production.

The pre-combustion approach consists of the use of any CO<sub>2</sub> capture step in a process where the gas stream has some value, energetic or otherwise. Examples of these kinds of gas streams are found during steel industry blast furnace operations that typically are rich in CO, the tail gas from a pressure swing adsorption unit of an ammonia production plant that are typically rich in H<sub>2</sub>, or even natural gas before sweetening.


The oxyfuel combustion approach consists of using pure O<sub>2</sub> or O<sub>2</sub> enriched air as oxidants in reaction processes that produce CO<sub>2</sub> as a by-product. This approach offers the possibility for improving the economics of CO<sub>2</sub> production. Examples of where this approach can be used

include in combustion processes and in the production of iron and steel, lime and cement, and  $\text{NH}_3$ .

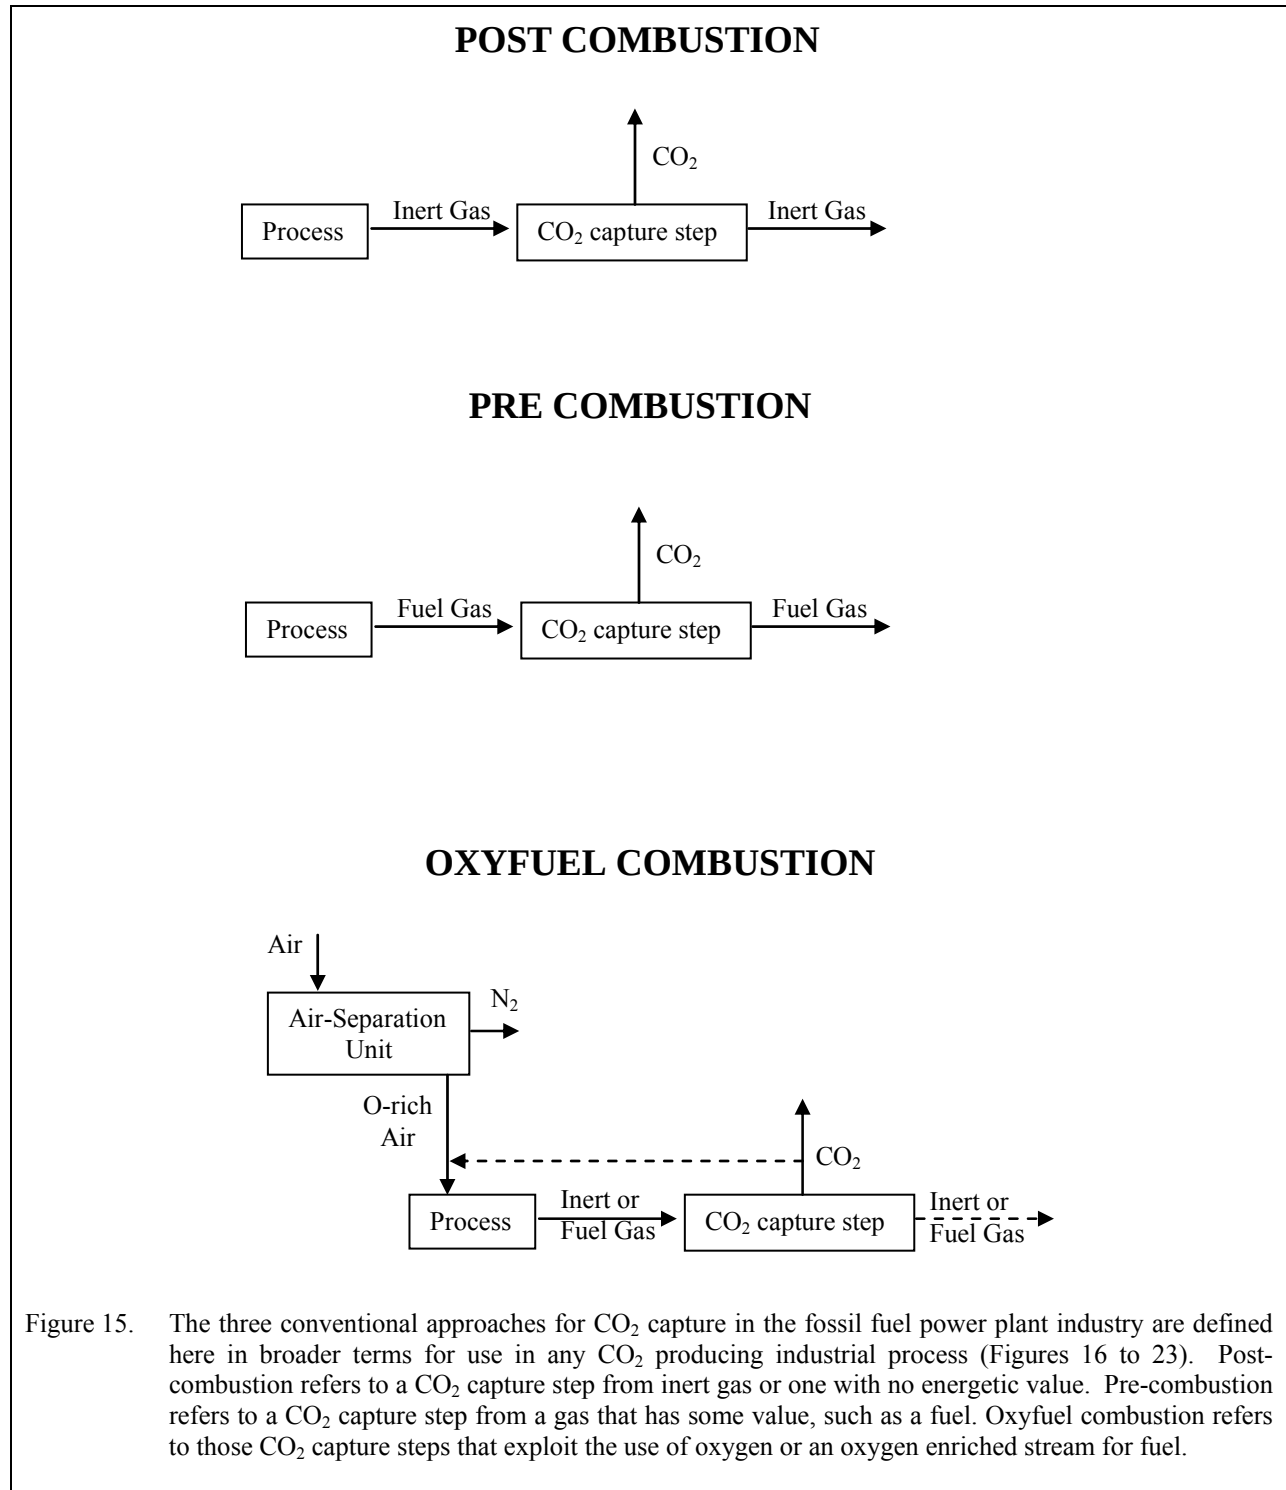

## Conceptual Flow Sheets for Additional Guidance

The flow sheets given in Figures 4 to 14 for the most intense CO<sub>2</sub>- producing processes were discussed at length in a preceeding section. They should be used for guidance to foster ideas for near- and long-term CO<sub>2</sub> production plant modifications with adsorption and membrane technologies. To further assist in this goal, new conceptual flow sheets have also been devised that are based on the post-combustion, pre-combustion and oxyfuel combustion approaches that have evolved over the years for the capture of CO<sub>2</sub> from fossil fuel power plants [468], and that were just introduced in the last section. They are given in Figures 16 to 23. For each of the CO<sub>2</sub> producing processes discussed in this report, a new flow sheet has been drawn that includes the incorporation of post-combustion, pre-combustion and/or oxyfuel combustion approaches.

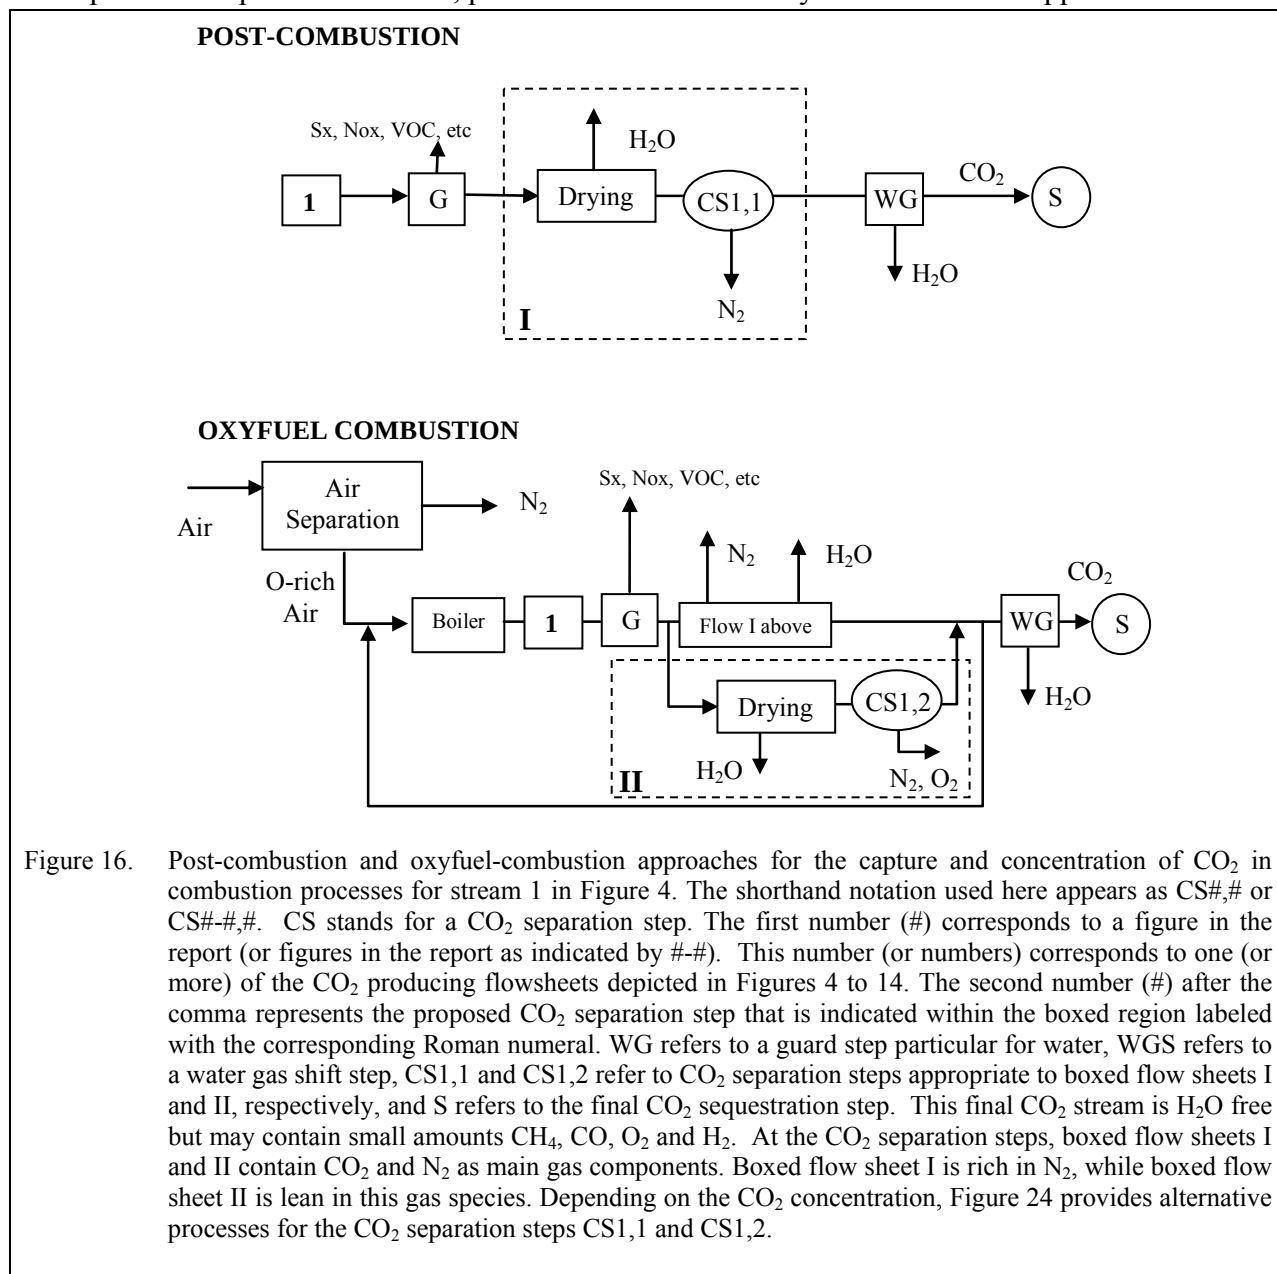


Within each of these new flow sheets, potential locations have been proposed where a CO<sub>2</sub> separations unit may be able to augment the performance of the current CO<sub>2</sub> producing plant.

At this point, the differentiation between these locations is not based on the type of separation process that may be applicable (e.g., adsorption, membrane); rather, it is based on the quality of the stream (i.e., the composition and CO<sub>2</sub> concentration in the stream). Hence, the proposed CO<sub>2</sub> separation processes for each of the indicated locations shown in Figures 16 to 23 are identified in Figures 24 to 26, where streams have been classified according to three main categories: 1) streams free of H<sub>2</sub> and sulfur bearing compounds, 2) streams containing significant H<sub>2</sub> and no sulfur bearing compounds, and 3) streams containing significant concentrations of sulfur bearing compounds. Within each classification and according to the quality of the stream, one or more separation units (e.g., liquefaction, absorption, adsorption, or membrane) is suggested where they may be most advantageous.

Also, stream compositions and conditions differ widely, depending on the process. For example, the removal of CO<sub>2</sub> from coal-fired power plants is very different from natural gas sweetening. In the former, the CO<sub>2</sub> is dilute, at low pressure, and dirty. In the latter, the CO<sub>2</sub> can be concentrated, at high pressure, and potentially may have a high sulfur content. The conditions of all the process streams are given in this report to ensure that these important design and development criteria are not overlooked.

These conceptual flowsheets, and corresponding stream differentiations, should be especially helpful to guide the near- and far-term developments of new adsorption and membrane processes for CO<sub>2</sub> separation or capture from industrial sources.

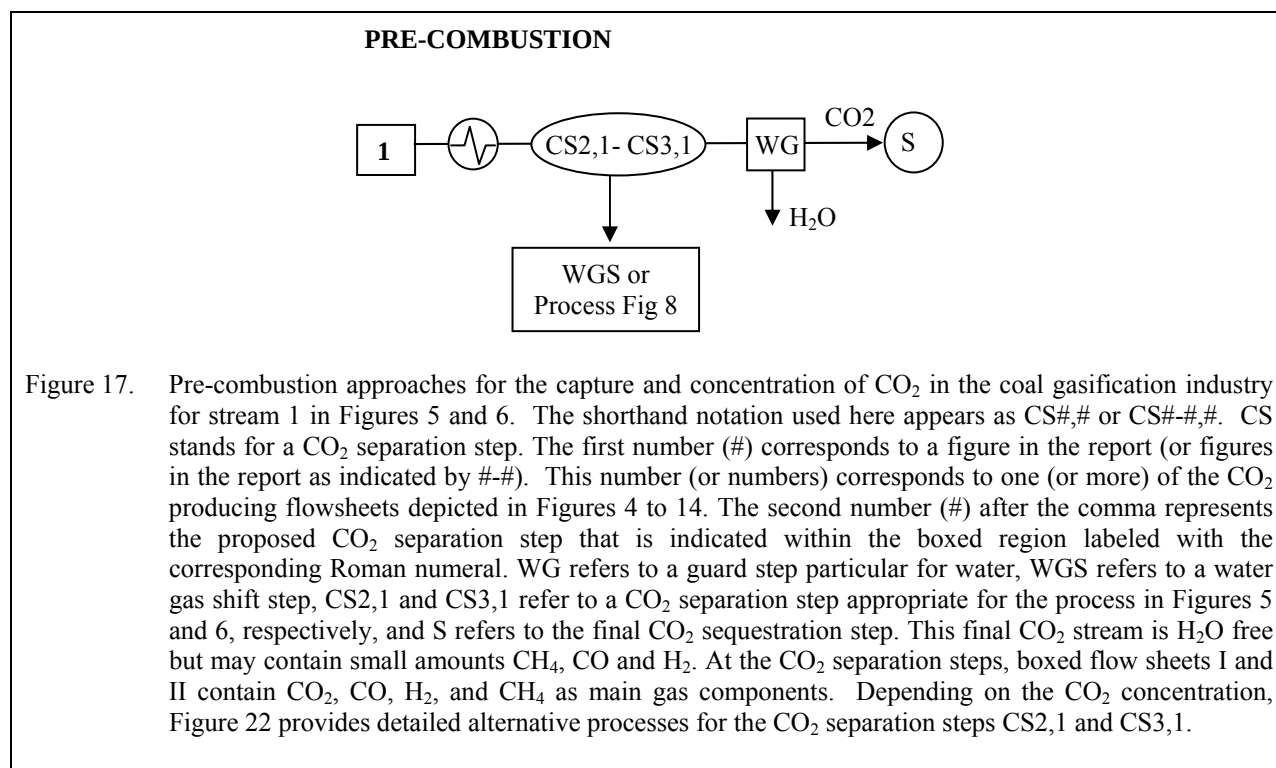



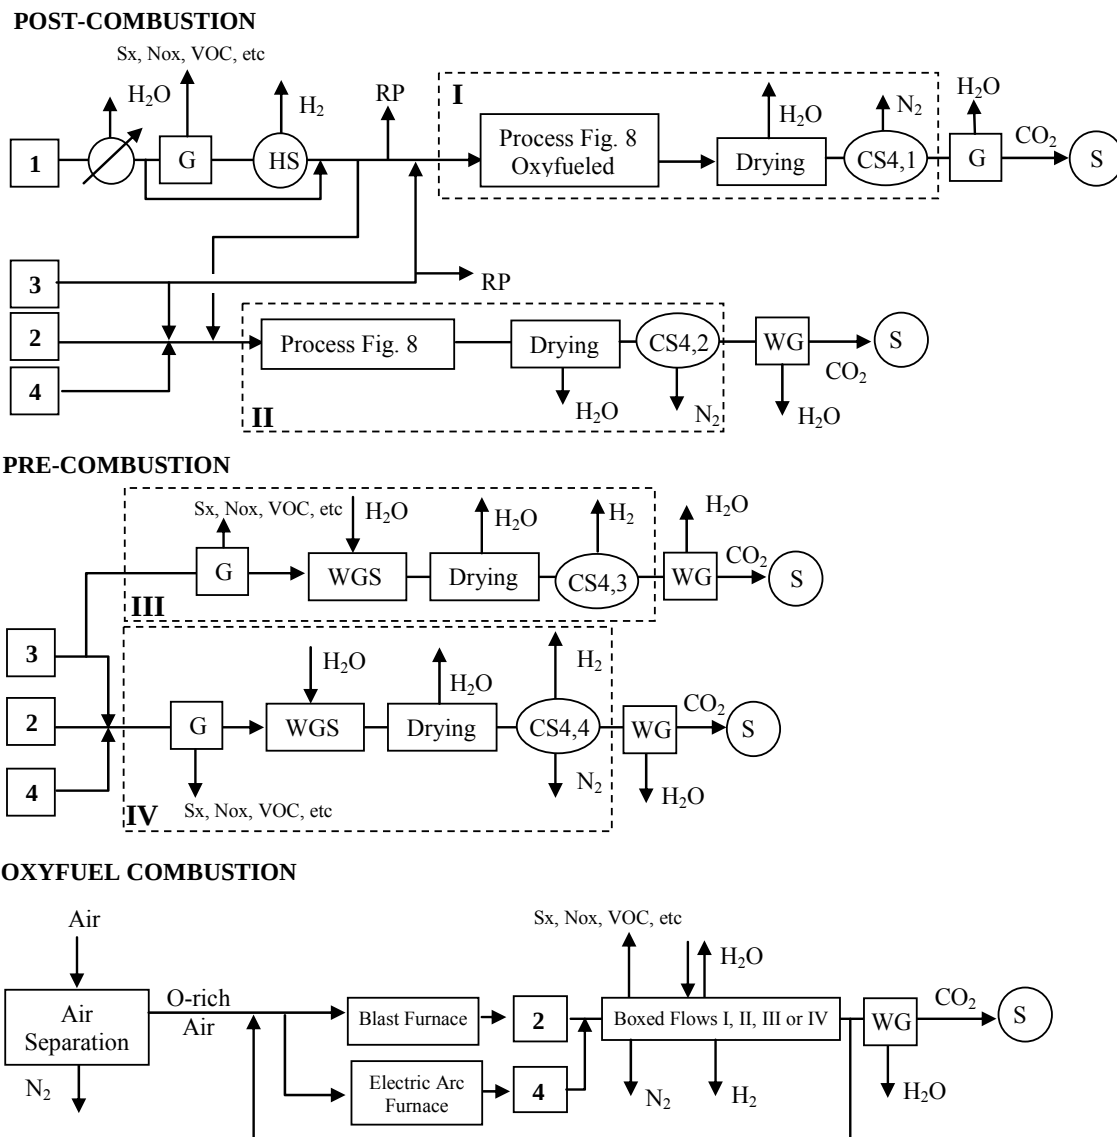


Figure 18. Post-combustion, pre-combustion, and oxyfuel combustion approaches for capture and concentration of CO<sub>2</sub> in the stainless steel industry for the streams 1 through 4 defined in Figure 7. The shorthand notation used here appears as CS#, # or CS#-#/#. CS stands for a CO<sub>2</sub> separation step. The first number (#) corresponds to a figure in the report (or figures in the report as indicated by #-#). This number (or numbers) corresponds to one (or more) of the CO<sub>2</sub> producing flowsheets depicted in Figures 4 to 14. The second number (#) after the comma represents the proposed CO<sub>2</sub> separation step that is indicated within the boxed region labeled with the corresponding Roman numeral. G refers to a guard step, WG refers to a guard step particular for water, HS refers to a hydrogen separation step, WGS refers to a water gas shift step, CS4,1 through CS4,4 refer to CO<sub>2</sub> separation steps appropriate to boxed flow sheets I through IV, respectively, and S refers to the final CO<sub>2</sub> sequestration step. A stream labelled with CO<sub>2</sub> indicates that stream is ready for injection (i.e., sequestration). This stream is H<sub>2</sub>O free but may contain small amounts of N<sub>2</sub>, CH<sub>4</sub>, O<sub>2</sub> and H<sub>2</sub>. At the CO<sub>2</sub> separation steps, boxed flows I and II contain CO<sub>2</sub> and N<sub>2</sub> as main gas components, while boxed flows III and IV contain CO<sub>2</sub>, N<sub>2</sub> and H<sub>2</sub> as the main gas components. Boxed flow sheets I and III are lean in N<sub>2</sub>, while boxed flow sheets II and IV are rich in this gas species. Depending on the CO<sub>2</sub> concentration, Figures 21 and 22 provide alternative processes for the CO<sub>2</sub> separation steps CS4,1 through CS4,4.

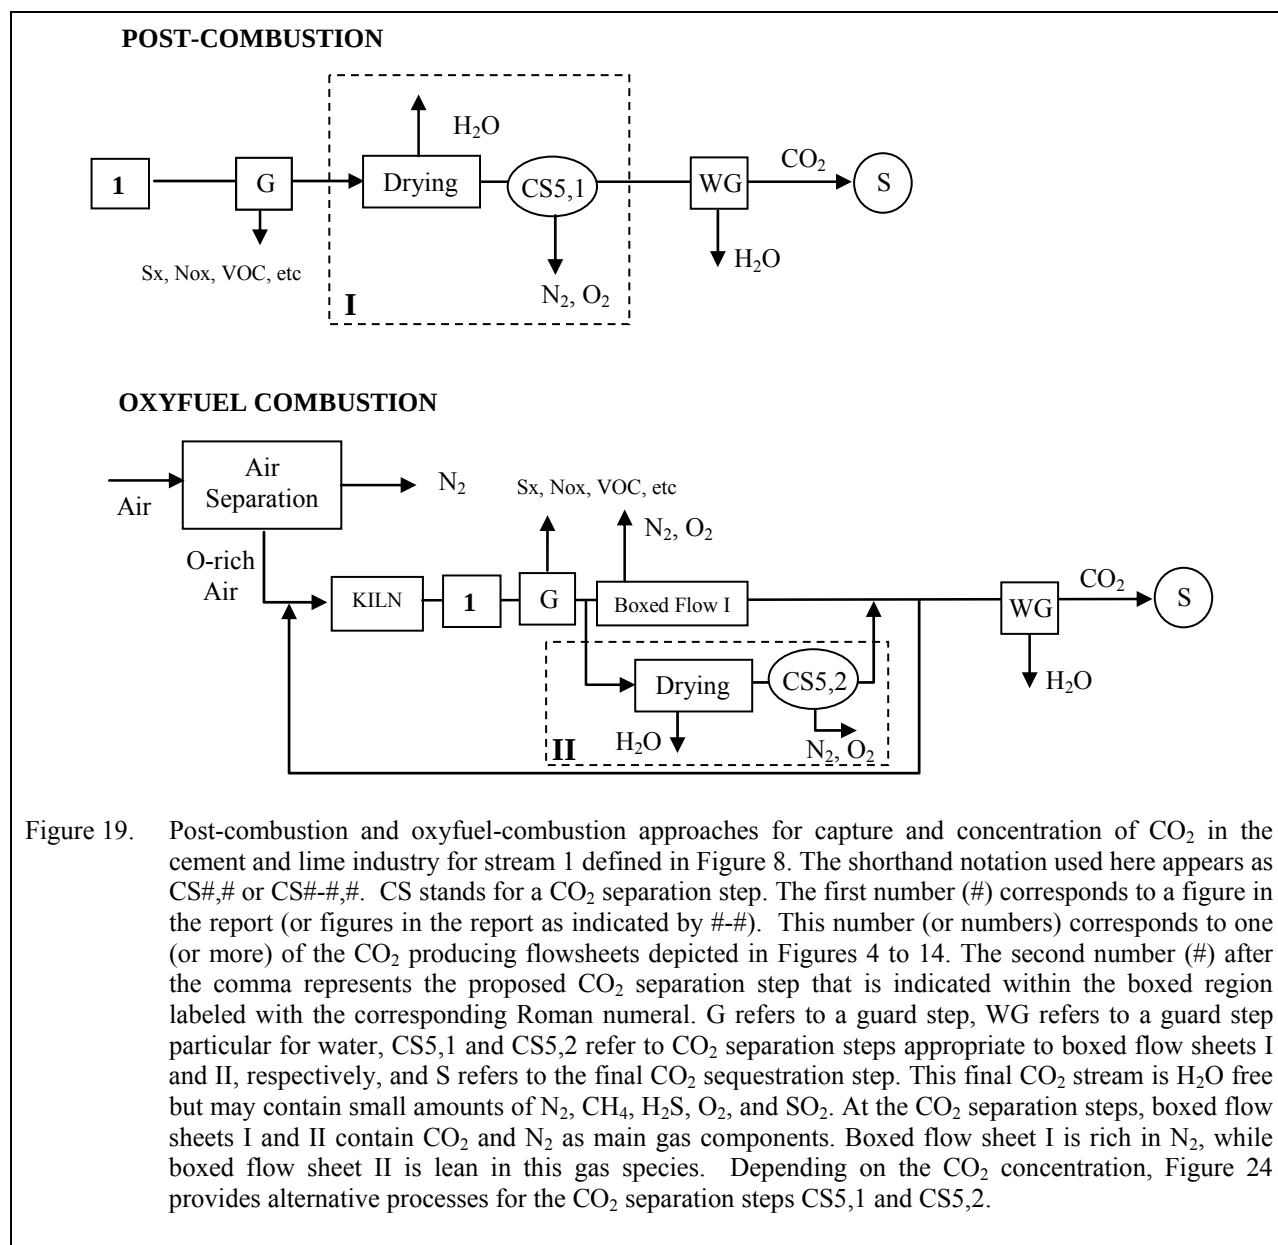

# **PRE-COMBUSTION**

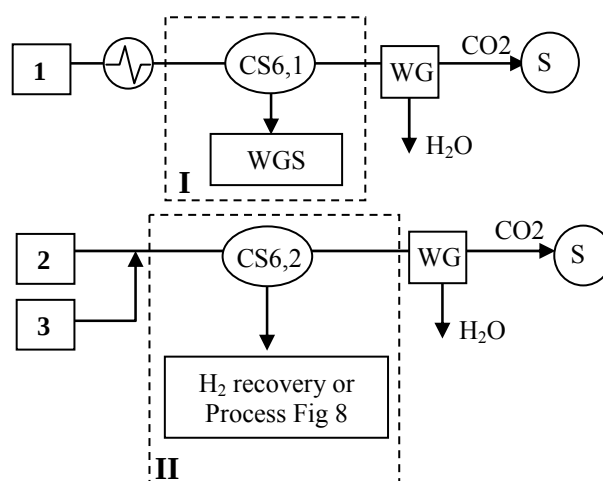

# **POST COMBUSTION**

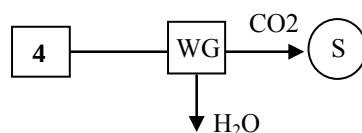


Figure 20. Pre-combustion and post-combustion approaches for capture and concentration of CO<sub>2</sub> in the ammonia manufacture industry for streams 1 through 4 in Figure 9. The shorthand notation used here appears as CS#, # or CS#-#,#. CS stands for a CO<sub>2</sub> separation step. The first number (#) corresponds to a figure in the report (or figures in the report as indicated by #-#). This number (or numbers) corresponds to one (or more) of the CO<sub>2</sub> producing flowsheets depicted in Figures 4 to 14. The second number (#) after the comma represents the proposed CO<sub>2</sub> separation step that is indicated within the boxed region labeled with the corresponding Roman numeral. WG refers to a guard step particular for water, WGS refers to a water gas shift step, CS6,1 and CS6,2 refer to CO<sub>2</sub> separation steps appropriate to boxed flow sheets I and II, respectively, and S refers to the final CO<sub>2</sub> sequestration step. This final CO<sub>2</sub> stream is H<sub>2</sub>O free but may contain small amounts CH<sub>4</sub>, CO and H<sub>2</sub>. At the CO<sub>2</sub> separation steps, boxed flow sheets I and II contain CO<sub>2</sub>, CO, H<sub>2</sub>, and CH<sub>4</sub> as main gas components. Boxed flow sheet I is rich in CO and CH<sub>4</sub>, while boxed flow sheet II is very lean in these gas species. Depending on the CO<sub>2</sub> concentration, Figure 22 provides detailed alternative processes for the CO<sub>2</sub> separation steps CS6,1 and CS6,2. No particular action is taken over stream 4 other than a drying step.

# PRE-COMBUSTION


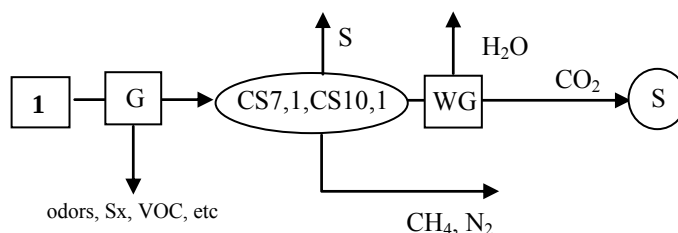


Figure 21. Pre-combustion approach for capture and concentration of CO<sub>2</sub> in the natural, coal, and landfill gas industries for stream 1 defined in Figures 10 and 13. The shorthand notation used here appears as CS#,# or CS#-#,#. CS stands for a CO<sub>2</sub> separation step. The first number (#) corresponds to a figure in the report (or figures in the report as indicated by #-#). This number (or numbers) corresponds to one (or more) of the CO<sub>2</sub> producing flowsheets depicted in Figures 4 to 14. The second number (#) after the comma represents the proposed CO<sub>2</sub> separation step that is indicated within the boxed region labeled with the corresponding Roman numeral. G refers to a guard step, WG refers to a guard step particular for water, CS7,1 and CS10,1 refer to a CO<sub>2</sub> separation step appropriate for the processes in Figures 10 and 13, respectively, and S refers to the final CO<sub>2</sub> sequestration step. This final CO<sub>2</sub> stream is H<sub>2</sub>O free but may contain small amounts of N<sub>2</sub>, CH<sub>4</sub>, and H<sub>2</sub>S. At the CO<sub>2</sub> separation step, the stream contains CO<sub>2</sub>, N<sub>2</sub> and H<sub>2</sub>S as main gas components. Depending on the CO<sub>2</sub> and H<sub>2</sub>S concentrations, Figure 26 provides alternative processes for the CO<sub>2</sub> separation step CS7,1 and CS10,1.



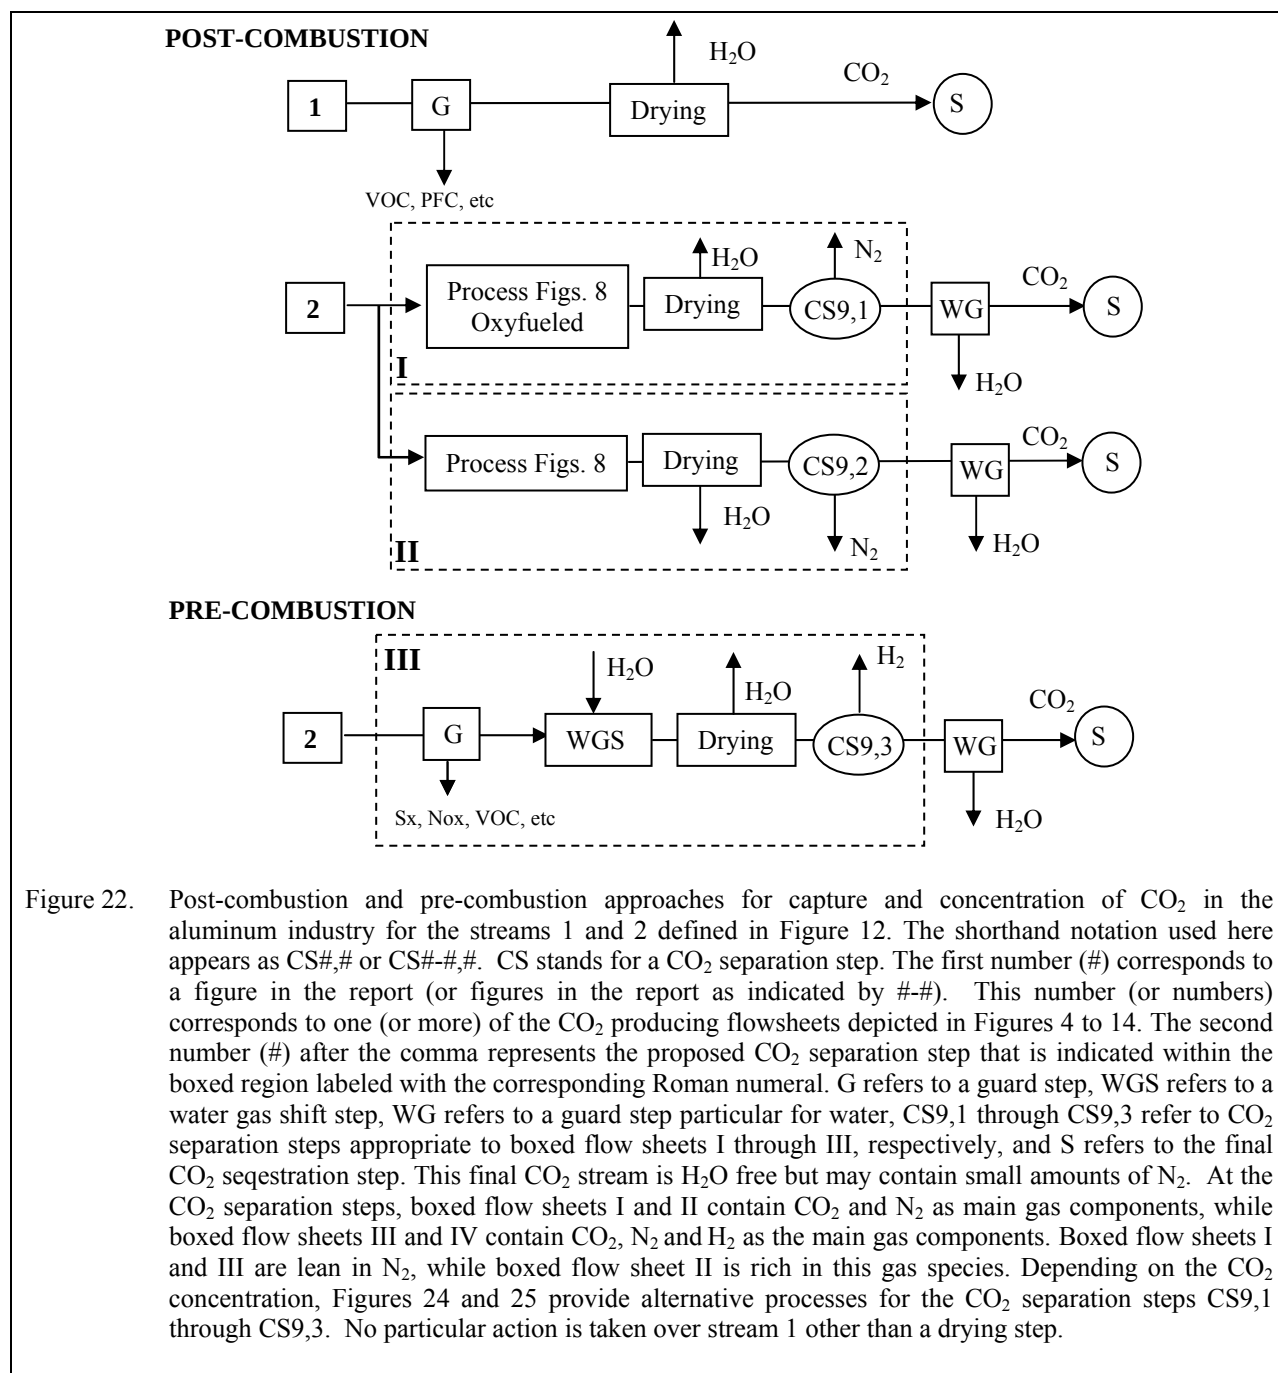

### POST-COMBUSTION


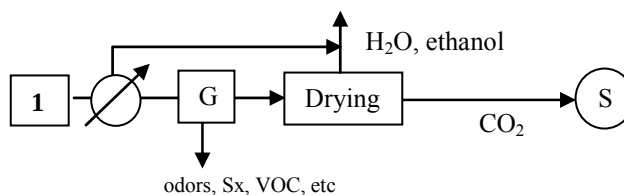


Figure 23. Post-combustion approach for capture and concentration of CO<sub>2</sub> in the ethanol production industry for stream 1 defined in Figure 14. G refers to a guard step and S refers to the final CO<sub>2</sub> sequestration step. This final CO<sub>2</sub> stream is H<sub>2</sub>O free but may contain small amounts of N<sub>2</sub>. No particular action is taken over stream 1 other than a drying step.

### Process I: CO<sub>2</sub> and gases such as N<sub>2</sub>, O<sub>2</sub>, CO and CH<sub>4</sub>

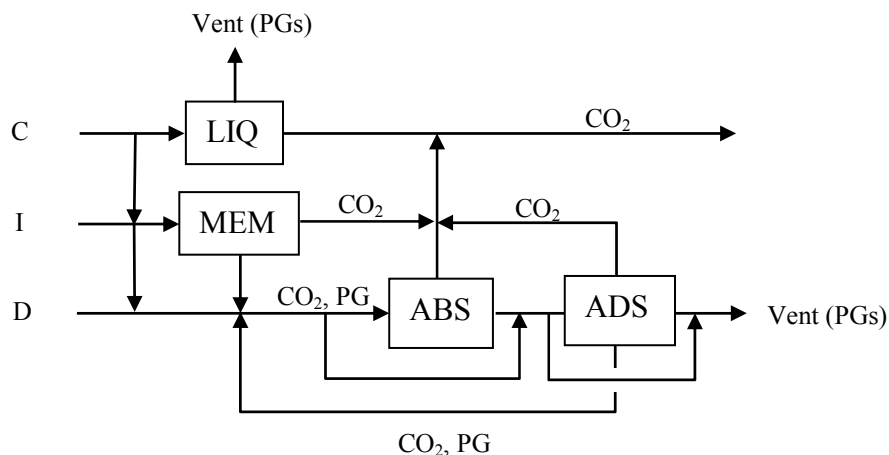


**C:** (>90% CO<sub>2</sub>) CS1,2; CS4,1; CS5,2; CS9,1

**I:** (20-90% CO<sub>2</sub>) CS1,1; CS4,1; CS4,2; CS5,1; CS9,1; CS9,2

**D:** (5-20% CO<sub>2</sub>) CS4,2; CS9,2

Figure 24. Flow diagram representing a CO<sub>2</sub> separation and concentration step for streams in Figures 16, 18, 19 and 22 that contain N<sub>2</sub>, O<sub>2</sub>, CO or CH<sub>4</sub> as permanent gases (PG) in addition to CO<sub>2</sub>. The separation step may consist of one or more separation processes that include liquefaction (LIQ), membrane (MEM), absorption (ABS), and adsorption (ADS). The step flow diagram allows different accesses depending on whether the CO<sub>2</sub> content in the stream is concentrated (C), intermediate (I), or dilute (D).

**Process II: CO<sub>2</sub>, gases such as N<sub>2</sub>, O<sub>2</sub>, CH<sub>4</sub> and significant H<sub>2</sub>**

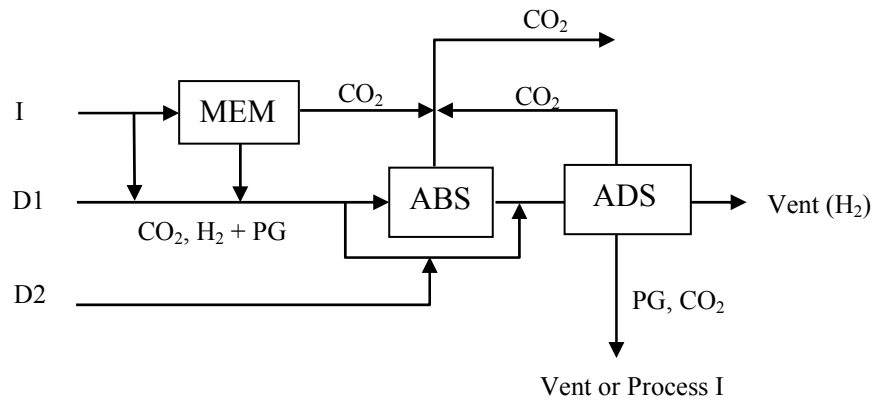


**I:** (20-90% CO<sub>2</sub>) CS4,3; CS4,4; CS6,2; CS9,3

**D1:** (5-20% CO<sub>2</sub>) CS4,4; CS6,2; CS9,2

**D2:** (5-20% CO<sub>2</sub>, HOT) CS2,1; CS3,1; CS6,1

Figure 25. Flow diagram representing a CO<sub>2</sub> separation and concentration step for streams in Figures 17, 18, 20 and 22 that contain N<sub>2</sub>, O<sub>2</sub>, CO or CH<sub>4</sub> as permanent gases (PG) as well as significant concentrations of H<sub>2</sub> in addition to CO<sub>2</sub>. The separation step may consist of one or more separation processes that include membranes (MEM), absorption (ABS), and adsorption (ADS). The step flow diagram allows different accesses for the stream depending on whether its CO<sub>2</sub> content is intermediate (I), or dilute at room temperature (D1) or dilute at high temperature (D2).

### Process III: CO<sub>2</sub>, gases such as N<sub>2</sub>, CH<sub>4</sub> and H<sub>2</sub>S

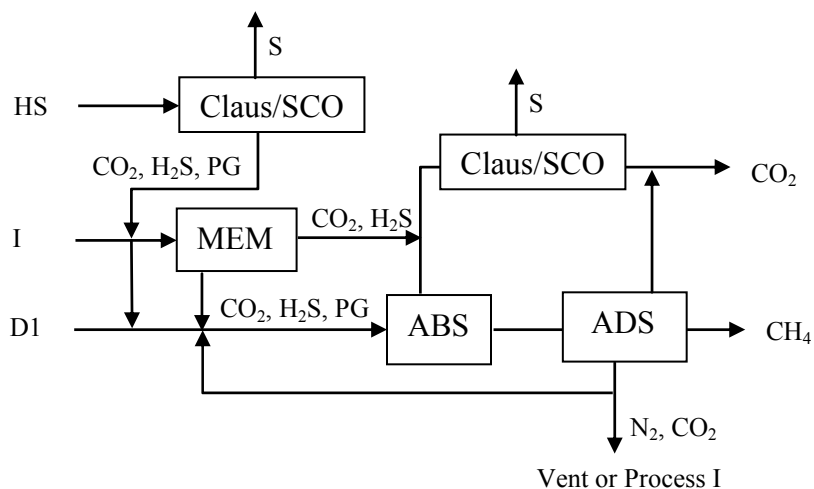

**HS:** (> 20% H<sub>2</sub>S) CS7,1; CS10,1

**I:** (20-90% CO<sub>2</sub>) CS7,1; CS10,1

**D:** (5-20% CO<sub>2</sub>) CS7,1; CS10,1

Figure 26. Flow diagram representing a CO<sub>2</sub> separation and concentration step for streams in Figure 21 that contain N<sub>2</sub>, O<sub>2</sub>, CO or CH<sub>4</sub> as permanent gases (PG) as well as sulfur bearing compounds (e.g., H<sub>2</sub>S, COS, etc.) in addition to CO<sub>2</sub>. The separation step may consist of one or more separation processes that include a Claus/SCOT step for sulfur removal, membranes (MEM), absorption (ABS), and adsorption (ADS). The step flow diagram allows different accesses for the stream depending on whether its CO<sub>2</sub> content is intermediate (I) or dilute (D), or on whether its content of sulfur bearing compounds is elevated (HS).

## **References**

1. Ritter JA, Ebner AD, "State-of-the-Art Adsorption and Membrane Separation Processes for Hydrogen Production in the Chemical and Petrochemical Industries," Sep. Sci. Tech. 42 (2007) 1123-1193; and DOE report: [http://www.chemicalvision2020.org/pdfs/h2\\_report.pdf](http://www.chemicalvision2020.org/pdfs/h2_report.pdf).
2. White CM, Strazisar BR, Granite EJ, Hoffman JS, Pennline HW, "Separation and capture of CO<sub>2</sub> from large stationary sources and sequestration in geological formations - Coalbeds and deep saline," J. Air & Waste Management Association, 53 (2003) 645-715.
3. US DOE Report: DOE/EIA-0484(2005); U.S. DOE <http://www.fe.doe.gov/programs/sequestration/capture/index.html>.
4. Kirk-Othmer, "Concise encyclopedia of chemical technology," Vol. I, 4<sup>th</sup> Ed. John Wiley and Sons, Hoboken, New Jersey (1999).
5. Wittcoff HA, Reuben BG, Plotkin JS, "Industrial organic chemicals," 2<sup>nd</sup> Ed., John Wiley and Sons, Hoboken, New Jersey (2004).
6. Xiaoding X, Moulijn JA, "Mitigation of CO<sub>2</sub> by chemical conversion: Plausible chemical reactions and promising products," Energy and Fuels 10 (1996) 305-325.
7. Aresta M, Dibenedetto A, "The contribution of the utilization option to reducing the CO<sub>2</sub> atmospheric loading: Research needed to overcome existing barriers for a full exploitation of the potential of the CO<sub>2</sub> use," Catalysis Today 98 (2004) 455-462.
8. Kohl AL and Nielsen RB, "Gas Purification," 4<sup>th</sup> ed., Gulf Publishing Company, Houston, Texas (1997).
9. Hydrocarbon Processing, "Gas Processes Handbook 2004," Gulf Publishing Co. (2004).
10. Wills J, Shemaria M, Mitariten MJ, "Production of pipeline quality natural gas with molecular gate CO<sub>2</sub> removal process," SPE Production and Facilities, February (2004).
11. Izumi J, "Adsorption technology applications to the industries in Japan," Abstract and presentation at the 8<sup>th</sup> International Conference on Fundamentals of Adsorption, Sedona, AR, May (2004).
12. Wong S, Bioletti R, "Carbon dioxide separation technologies," Alberta Research Council (2002).
13. Freemantle M, "Membranes for gas separation," Chem. Eng. News 83 (2005) 49.
14. Baker RW, "Gas Separation" in "Membrane technology and applications," 2<sup>nd</sup> Edition, Baker RW editor, John Wiley & Sons, 2004.
15. Baker RW, "Future directions of membrane gas separation technology," Ind. Eng. Chem. Res. 41 (2002) 1393-1411.
16. Basu A, Akhtar J, Rahman MH, Islam MR, "A review of separation of gases using membrane systems," Petrol. Sci. Technol. 22 (2004) 1343-1368.
17. Shekhawat D, Luebke DR, Pennline HW, "A review of carbon dioxide selective membranes - a topical report," DEO/NETL Report, 2003/1200 (2003).
18. Stookey, DJ, "Gas separation membrane applications" in "Membrane technology in the chemical industry," Nunes SP, Peinemann KV editors, Wiley-VCH Verlag GmbH, 2001.
19. Nunes SP, Peinemann KV, "Gas separation with membranes" in "Membrane technology in the chemical industry," Nunes SP, Peinemann KV editors, Wiley-VCH Verlag GmbH, 2001.
20. Fuderer, A, Rudelstorfer, E, "Selective adsorption process," USP 3,986,849 (1976).
21. Whysall M, Wagemans LJM, "Very large-scale pressure swing adsorption processes,"

- USP 6,210,466 B1 (2001).
22. Baksh MSA, Terbot CE, "Pressure-swing adsorption process for the production of hydrogen," U.S. 6,503,299 B2 (2003).
23. Baksh MSA, Ackley MW, Notaro F, "Process and apparatus for hydrogen purification," WO 2004/058630 A2 (2004).
24. Xu J, Weist EL Jr., "Six bed pressure swing adsorption process with four steps of pressure equalization," USP 6,454,838 B1 (2002).
25. Xu J, Rarig DL, Cook TA, Hsu K-K, Schoonover M, Agrawal R, "Pressure swing adsorption process with reduced pressure equalization time," USP 2003/0015091 A1 (2003).
26. Sircar S, Golden TC, "Purification of hydrogen by pressure swing adsorption," Sep. Sci. Tech. 35 (2000) 667-687.
27. Waldron WE, Sircar S, "Parametric study of a pressure swing adsorption process," Adsorption, 6 (2000) 179-188.
28. Keefer BG, "High-frequency rotary pressure swing adsorption," USP 6,176,897 B1 (2001).
29. Keefer BG, Doman DG, "Flow regulated pressure swing adsorption system," USP 6,063,191 (2000).
30. Keefer BG, Doman DG, "Flow regulated pressure swing adsorption system," USP RE38,493 (2004).
31. Golden CMA, Golden TC, Battavio OJ, "Multilayered adsorbent system for gas separations by pressure swing adsorption," USP 2003/0205131 A1 (2003a).
32. Golden TC, Golden CMA, Zwilling DP, "Self-supported structured adsorbent for gas separation," USP 6,656,627 B1 (2003b).
33. Golden TC, Weist EL, "Activated carbon as sole adsorbent in rapid cycle hydrogen PSA," USP 6,660,064 (2003).
34. Keefer BG, Carel A, Sellars B, Shaw I, Larisch B, "Adsorbent laminate structures," USP 6,692,626 B2 (2004).
35. Connor DJ, Doman DG, Jeziorowski L, Keefer BG, Larisch B, Mclean CR, Shaw I, "Rotary pressure swing adsorption apparatus," USP 6,406,523 B1 (2002).
36. "A fast PSA technology to be trialed at petroleum refinery," Chemical and Engineering News, pg. 14, September (2006).
37. Reynolds SP, Ebner AD, Ritter JA, "Stripping PSA cycles for CO<sub>2</sub> recovery from flue gas at high temperature using a hydrotalcite-like adsorbent," Ind. Eng. Chem. Res. 45 (2006a) 4278-4294.
38. Park J-H, Beum H-T, Kin J-N, Cho S-H, "Numerical analysis on the power consumption of the PSA process for recovering CO<sub>2</sub> from flue gas," Ind. Eng. Chem. Res. 41 (2002c) 4122-4131.
39. Ding Y, Alpay E, "High temperature recovery of CO<sub>2</sub> from flue gas using hydrotalcite adsorbent," Proc. Safety Environ. Protection 79 (2001) 45-52.
40. Will J, Shemaria M, "Production of pipeline quality natural gas with molecular gate CO<sub>2</sub> removal process," Production and Facilities, 19 (2004) 4-8.
41. Reinhold HE, D'Amico JS, Knaebel KS, "Natural gas enrichment process," USP 5,536,300 (1996).
42. Dolan WB, Mitariten MJ, "Heavy hydrocarbon recovery from pressure swing adsorption unit tail gas," USP 6,610,124 B1 (2003).

43. Knaebel KS, Reinhold HE, "Landfill gas: from rubbish to resource," *Adsorption* 9 (2003) 87-94.
44. Sircar S, Kumar R., Koch WR, Van Sloun J, "Recovery of methane from land fill gas," USP 4770676 (1988).
45. Cavenati S, Grande CA, Rodrigues AE, "Upgrade of methane from landfill gas by pressure swing adsorption," *Energy & Fuels* 19 (2005) 2545-2555.
46. Mitariten, M, "Adsorption advances," *World Coal*, September (2002).
47. Mitariten, M, "Economic N<sub>2</sub> removal," *Hydrocarbon Engineering*, July (2004).
48. Olajossy A, Gawdzik A, Budner Z, Dula J, "Methane separation from coal methane gas by vacuum pressure swing adsorption," *Trans. IChemE*, 81 (2003) 474-482.
49. Jiang, L, Fox, V G, Biegler, L T, "Simulation and optimal design of multiple-bed pressure swing adsorption systems," *AIChE Journal*, 50 (2004) 2904-2917.
50. Warmuzinski, K, Tanczyk, M, "Multicomponent pressure swing adsorption. Part I. Modeling of large-scale PSA installations," *Chemical Engineering and Processing*, 36 (1997) 89-99.
51. Tanczyk, M, Warmuzinski, K, "Multicomponent pressure swing adsorption. Part II. Experimental verification of the model," *Chemical Engineering and Processing*, 37 (1998) 301-315.
52. Yang J, Ahn H, Lee H, Lee C-H. "Hydrogen recovery from coke oven gas using a layered-column PSA process," in *Fundamentals of Adsorption*, Francis Meunier Ed. Elsevier, Paris, France (1998).
53. Ahn, H, Yang, J, Lee, C-H, "Effects of feed composition of coke oven gas on a layered bed H<sub>2</sub> PSA process," *Adsorption*, 7 (2001) 339-356.
54. Lee, C-H, Yang, J, Ahn, H, "Effects of carbon-to-zeolite ratio on layered bed H<sub>2</sub> PSA for coke oven gas," *AIChE Journal*, 45 (1999) 535-545.
55. Reynolds SP, Ebner AD, Ritter JA, Knox JC and LeVan MD, "Mathematical Simulation of the sorbent-based atmosphere revitalization system for the crew exploration vehicle," in *Proceedings of the 36th International Conference on Environmental Systems*, SAE Aerospace (2006c).
56. Diagne D, Goto M, Hirose T, "Experimental-study of simultaneous removal and concentration of CO<sub>2</sub> by an improved pressure swing adsorption process," *Energy Conversion and Management*, 36 (1995) 431-434.
57. Diagne D, Goto M, Hirose T, "New PSA process with intermediate feed inlet position and operated with dual refluxes: Application to carbon dioxide removal and enrichment," *J. Chem. Eng. Japan*. 27 (1994) 85-89.
58. Diagne D, Goto M, Hirose T, "Parametric studies on CO<sub>2</sub> separation and recovery by dual reflux PSA process consisting of both rectifying and stripping sections," *Ind. Eng. Chem. Res.* 34 (1995) 3083-3089.
59. Diagne D, Goto M, Hirose T, "Numerical analysis of a dual refluxed PSA process during simultaneous removal and concentration of carbon dioxide dilute gas from air," *J. Chem. Tech. Biotechnol.* 65(1996) 29-38.
60. McIntyre JA, Holland CE, Ritter JA, "High enrichment and recovery of dilute hydrocarbons by dual reflux pressure swing adsorption," *Ind. Eng. Chem. Res.* 41 (2002) 3499-3504.
61. Reynolds SP, Ebner AD, Ritter JA, "Enriching PSA cycle for the production of nitrogen from air," *Ind. Eng. Chem. Res.* 45 (2006b) 3256-3264.

62. Wilson, PH, "Inverted Pressure Swing Adsorption Process," USP 4,359,328 (1982).
63. Leavitt FW, "Duplex adsorption process," USP 5,085,674 (1992).
64. Zhong G; Baksh MSA; Notaro F; Leavitt FW, "Pressure swing adsorption process for high recovery of high purity gas," USP 6,500,235, (2002).
65. Dong F, Kodama A, Goto M, Hirose T, "A new concept in the design of PSA processes for the multicomponent gas mixtures," *Ind. Eng. Chem. Res.* 38 (1999) 233-239.
66. Vaporciyan, GG, Kadlec, HR "Equilibrium-limited periodic separating reactors," *AIChE Journal*, 33 (1987) 1334-1343.
67. Vaporciyan, GG, Kadlec, HR, "Periodic separating reactors: experiments and theory," *AIChE Journal*, 35 (1989) 831-844.
68. Kadlec, HR, Vaporciyan, GG, "Periodic chemical processing system," USP 5,254,368 (1993).
69. Hufton, JR, Sircar, S, Baade, WF, Abrardo, JM, Anand, M, "Integrated steam methane reforming process for producing carbon monoxide and hydrogen," USP 6,312,658 B1 (2001b).
70. Hufton, JR, Sircar, S, Baade, WF, Abrardo, JM, Anand, M, "Integrated steam methane reforming process for producing carbon monoxide," USP 6,328,945 B1 (2001a).
71. Sircar S, Hufton JR, Nataraj S, "Process and apparatus for the production of hydrogen by steam reforming of hydrocarbon," USP 6,103,143 (2000).
72. Hufton JR, Nataraj S, "Production of carbon monoxide," USP 6,592,836 B2 (2003).
73. Anand M, Sircar S, Carvill BT, "Process for operating equilibrium controlled reactions," USP 6,303,092 B1 (2001).
74. Nataraj S, Carvill BT, Hufton JR, Mayorga SG, Gaffney TR, Brzozowski JR, "Process for operating equilibrium controlled reactions," USP 6,315,973 B1 (2001).
75. Carvill BT, Hufton JR, Anand M, Sircar S, "Sorption-enhanced reaction process," *AIChE J.* 42 (1996) 2765-2772.
76. Hufton JR, Mayorga S, Sircar S, "Sorption-enhanced reaction process for hydrogen production," *AIChE J.* 45 (1999) 248-256.
77. Waldron WE, Hufton JR, Sircar S, "Production of hydrogen by cyclic sorption enhanced reaction process," *AIChE J.* 47 (2001) 1477-1479.
78. Ying DHS, Nataraj S, Hufton JR, Xu J, Allam RJ, Dullej SJ, "Simultaneous shift-reactive and adsorptive process at moderate temperature to produce pure hydrogen," USP Appl. 20040081614 A1 (2004).
79. Hufton JR, Allam RJ, Chiang R, et al., "Development of a process for CO<sub>2</sub> capture from gas turbines using a sorption enhanced water gas shift reactor system," *Proceedings of the 7<sup>th</sup> International Conference of Green House Gas Technology* (2005).
80. Han C, Harrison DP, "Simultaneous shift reaction and carbon dioxide separation for the direct production of hydrogen," *Chemical Engineering Science* 49 (1994) 5875-5883.
81. Harrison DP, Peng Z, "Low carbon monoxide hydrogen by sorption-enhanced reaction," *International Journal of Chemical Reactor Engineering* 1 (2003) A37.
82. Ortiz AL, Harrison DP, "Hydrogen production using sorption-enhanced reaction," *Ind. Eng. Chem. Res.* 40 (2001) 5102-5109.
83. Zou Y, Rodrigues AE, "The separation enhanced reaction process (SERP) in the production of hydrogen from methane steam reforming," *Adsorption Science and Technology*, 19 (2001) 655-671.
84. Xiu GH, Li P, Rodrigues AE, "Sorption-enhanced reaction process with reactive



- regeneration,” *Chemical Engineering Science* 57 (2002a) 3893-3908.
85. Xiu, G-H, Soares JL, Li P, Rodrigues AE, “Simulation of five-step one-bed sorption-enhanced reaction process,” *AIChE J.* 48 (2002b) 2817-2832.
  86. Xiu GH, Li P, Rodrigues AE, “Adsorption-enhanced steam-methane reforming with intraparticle-diffusion limitations,” *Chemical Engineering Journal* 95 (2003a) 83-93.
  87. Xiu GH, Li P, Rodrigues AE, “New generalized strategy for improving sorption-enhanced reaction process,” *Chemical Engineering Science* 58 (2003b) 3425-3437.
  88. Xiu GH, Li P, Rodrigues, AE, “Subsection-controlling strategy for improving sorption-enhanced reaction process,” *Chemical Engineering Research and Design*, 82 (2004) 192-202.
  89. Ding Y, Alpay E, “Adsorption-enhanced steam-methane reforming,” *Chemical Engineering Science* 55 (2000) 3929-3940.
  90. Ding, Y, Alpay, E, “Equilibria and kinetics of CO<sub>2</sub> adsorption on hydrotalcite adsorbent,” *Chemical Engineering Science* 55 (2000) 3461-3474.
  91. Yong Z, Mata V, Rodrigues AE, “Adsorption of carbon dioxide on basic alumina at high temperatures,” *Journal of Chemical and Engineering Data* 45 (2000) 1093-1095.
  92. Easley MA, Horn WE, “Carbon dioxide adsorption of synthetic meixnerite,” *USP* 5,882,622 (1999).
  93. Mayorga SG, Gaffney TR, Brzozowski JR, Weigel SJ, “Carbon dioxide adsorbents containing magnesium oxide suitable for use at high temperatures,” *USP* 6,280,503 B1 (2001).
  94. Yong Z, Mata V, Rodriguez AE, “Adsorption of carbon dioxide onto hydrotalcite-like compounds (HTLcs) at high temperatures,” *Ind. Eng. Chem. Res.* 40 (2001) 204-209.
  95. Yong Z, Rodrigues AE, “Hydrotalcite-like compounds as adsorbents for carbon dioxide,” *Energy Conversion and Management*, 43 (2002) 1865-1876.
  96. Ebner, AD, Reynolds, SP, Ritter JA, “Understanding the adsorption and desorption behavior of CO<sub>2</sub> on a K-promoted HTlc through non-equilibrium dynamic isotherms,” *Ind. Eng. Chem. Res.*, 45 (2006) 6387-6392.
  97. Reynolds SP, Ebner AD, Ritter JA, “New pressure swing adsorption cycles for carbon dioxide sequestration,” *Adsorption* 11 (2005) 531-536.
  98. Gaffney TR, Golden TC, Mayorga SG, Brzozowski JR, Taylor FW, “Carbon dioxide pressure swing adsorption process using modified alumina adsorbents,” *USP* 5,917,136 (1999).
  99. Xiong R, Ida J, Lin YS, “Kinetics of carbon dioxide sorption on potassium-doped lithium zirconate,” *Chem. Eng. Sci.*, 58 (2003) 4377-4385.
  100. Ida J-I, Lin YS, “Mechanism of high-temperature CO<sub>2</sub> sorption on lithium zirconate,” *Environmental Science and Technology* 37 (2003) 1999-2004.
  101. Ida J-I, Xiong R, Lin YS, “Synthesis and CO<sub>2</sub> sorption properties of pure and modified lithium zirconate,” *Sep. Purification Tech.* 36 (2004) 41-51.
  102. Nair BN, Yamaguchi T, Kawamura H, Nakao SI, Nakagawa K, “Processing of lithium zirconate for applications in carbon dioxide separation: structure and properties of the powders,” *Journal of The American Ceramic Society* 87 (2004) 68-74.
  103. Iyer MV, Gupta H, Sakadjian BB, Fan L-S, “Multicyclic study on the simultaneous carbonation and sulfation of high-reactivity CaO,” *Ind. Eng. Chem. Res.* 43 (2004) 3939-3947.
  104. Gupta H, Fan LS, “Carbonation-calcination cycle using high reactivity calcium oxide for

- carbon dioxide separation from flue gas,” *Ind. Eng. Chem. Res.* 41 (2002) 4035-4042.
105. Gupta H, Iyer MV, Sakadjian BB, Fan L-S, “Reactive separation of CO<sub>2</sub> using pressure pelletised limestone,” *International Journal of Environmental Technology and Management* 4 (2004) 3-20.
106. Kuramoto K, Fujimoto S, Morita A, Shibano S, Suzuki Y, Hatano H, Lin S-Y, Harada M, Takarada T, “Repetitive carbonation-calcination reactions of Ca-based sorbents for efficient CO<sub>2</sub> sorption at elevated temperatures and pressures,” *Ind. Eng. Chem. Res.* 42 (2003) 975-981.
107. Abanades JC, “The maximum capture efficiency of CO<sub>2</sub> using a carbonation/calcination cycle of CaO/CaCO<sub>3</sub>,” *Chemical Engineering Journal* 90 (2002) 303-306.
108. Birbara PJ, Nalette TA, “Regenerable supported amine-polyol sorbent,” USP 5,376,614 (1994).
109. Birbara PJ, Filburn TP, Nalette TA, “Regenerable supported amine sorbent,” USP 5,876,488 (1999).
110. Satyapal S, Filburn T, Trela J, Strange J, “Performance and properties of a solid amine sorbent for carbon dioxide removal in space life support applications,” *Energy and Fuels*, 15 (2001) 250-255.
111. Xu XC, Song CS, Andresen JM, et al., “Novel polyethylenimine-modified mesoporous molecular sieve of MCM-41 type as high-capacity adsorbent for CO<sub>2</sub> capture,” *Energy and Fuels* 16 (2002) 1463-1469.
112. Xu XC, Song CS, Andresen JM, et al., “Preparation and characterization of novel CO<sub>2</sub> “molecular basket” adsorbents based on polymer-modified mesoporous molecular sieve MCM-41,” *Micropor. Mesopor. Mater.* 62 (2003) 29-45.
113. Xu XC, Song CS, Miller BG, et al., “Influence of moisture on CO<sub>2</sub> separation from gas mixture by a nanoporous adsorbent based on polyethylenimine-modified molecular sieve MCM-41,” *Ind. Eng. Chem. Res.* 44 (2005) 8113-8119.
114. Robeson, LM, “Polymer membranes for gas separation,” *Cur. Opinion Sol. St. Mater. Sci.* 4 (1999): 549-552.
115. Freeman, BD, “Basis of permeability/selectivity tradeoff relations in polymeric gas separation membranes,” *Macromol.* 32 (1999) 375-380.
116. Stern SA, “Polymers for gas separations - the next decade,” *J. Mem. Sci.* 94 (1994) 1-65.
117. Dai Y, Guiver MD, Robertson, GP, et al., “Preparation and characterization of polysulfones containing both hexafluoroisopropylidene and trimethylsilyl groups as gas separation membrane materials,” *Macromol.* 37 (2004) 1403-1410.
118. Dai Y, Guiver MD, Robertson GP, et al., “Enhancement in the gas permeabilities of novel polysulfones with pendant 4-trimethylsilyl- $\alpha$ -hydroxybenzyl substituents,” *Macromol.* 36 (2003) 6807-6816.
119. Dai Y, Guiver MD, Robertson GP, et al., “Modified polysulfones 5: Synthesis and characterization of tetramethyl polysulfones containing trimethylsilyl groups and their gas transport properties,” *Polymer* 43 (2002) 5369-5378.
120. Lagunas-Fuentes C, Ruiz-Trevino FA, “Syntheses and permselectivity properties of polysulfones based on bisphenol A and 1,1 Bi-2 naphthol,” *J. Polym. Sci. B Polym. Phys.* 42 (2004) 226-231.
121. Ismail AF, Dunkin IR, Gallivan SL, et al., “Production of super selective polysulfone hollow fiber membranes for gas separation,” *Polymer* 40 (1999) 6499-6506.
122. Ismail AF, Ng BC, Rahman WA, “Effects of shear rate and forced convection residence

- time on asymmetric polysulfone membranes structure and gas separation performance,” *Sep. Purif. Technol.* 33 (2003) 255-272.
123. Ismail AF, Lorna W, “Suppression of plasticization in polysulfone membranes for gas separations by heat-treatment technique,” *Sep. Purif. Technol.* 30 (2003) 37-46.
  124. Choi SH, Lee MK, Oh SJ, et al., “Gas sorption and transport of ozone-treated polysulfone,” *J. Mem. Sci.* 221 (2003a) 37-46.
  125. Bhardwaj V, Macintosh A, Sharpe ID, et al., “Polysulfone hollow fiber gas separation membranes filled with submicron particles,” *Ann. NY Acad. Sci.* 984 (2003) 318-328.
  126. Chung TS, Shieh JJ, Lau WWY, et al., “Fabrication of multi-layer composite hollow fiber membranes for gas separation,” *J. Mem. Sci.* 152 (1999) 211-225.
  127. Guiver MD, Le THN, Robertson GP, “Preparation of polysulfone-zeolite composite gas separation membranes,” *USP Appl.* 2002062737 (2002).
  128. Shao L, Chung TS, Goh SH, et al., “Transport properties of cross-linked polyimide membranes induced by different generations of diaminobutane (DAB) dendrimers,” *J. Mem. Sci.* 238 (2004a) 153-163.
  129. Shao L, Chung TS, Pramoda KP, “The evolution of physicochemical and transport properties of 6FDA-durene toward carbon membranes; from polymer, intermediate to carbon,” *Micropor. Mesopor. Mater.* 84 (2005b) 59-68.
  130. Shao L, Chung TS, Goh SH, et al., “The effects of 1,3-cyclohexanebis(methylamine) modification on gas transport and plasticization resistance of polyimide membranes,” *J. Mem. Sci.* 267 (2005a) 78-89.
  131. Ren JH, Wang R, Chung TS, et al., “The effects of chemical modifications on morphology and performance of 6FDA-ODA/ND: A hollow fiber membrane for CO<sub>2</sub>/CH<sub>4</sub> separation,” *J. Mem. Sci.* 222 (2003) 133-147.
  132. Jeong HK, Krych W, Ramanan H, et al., “Fabrication of polymer/selective-flake nanocomposite membranes and their use in gas separation,” *Chem. Mater.* 16 (2004) 3838-3845.
  133. Xiao YC, Chung TS, Chng ML, “Surface characterization, modification chemistry, and separation performance of polyimide and polyamidoamine dendrimer composite films,” *Langmuir* 20 (2004) 8230-8238.
  134. Barsema JN, Kapantaidakis GC, van der Vegt NFA, et al., “Preparation and characterization of highly selective dense and hollow fiber asymmetric membranes based on BTDA-TDI/MDI co-polyimide,” *J. Mem. Sci.* 216 (2003b) 195-205.
  135. Barsema JN, Klijnstra SD, Balster JH, et al., “Intermediate polymer to carbon gas separation membranes based on Matrimid PI,” *J. Mem. Sci.* 238 (2004) 93-102.
  136. Hibshman C, Mager M, Marand E, “Effects of feed pressure on fluorinated polyimide-organosilicate hybrid membranes,” *J. Mem. Sci.* 229 (2004) 73-80.
  137. Hibshman C, Cornelius CJ, Marand E, “The gas separation effects of annealing polyimide-organosilicate hybrid membranes,” *J. Mem. Sci.* 211 (2003) 25-40.
  138. Tin PS, Chung TS, Liu Y, et al., “Separation of CO<sub>2</sub>/CH<sub>4</sub> through carbon molecular sieve membranes derived from P84 polyimide,” *Carbon* 42 (2004a) 3123-3131.
  139. Qin JJ, Chung TS, Cao C, et al., “Effect of temperature on intrinsic permeation properties of 6FDA-Durene/1,3-phenylenediamine (mPDA) copolyimide and fabrication of its hollow fiber membranes for CO<sub>2</sub>/CH<sub>4</sub> separation,” *J. Mem. Sci.* 250 (2005) 95-103.
  140. Xu JW, Chng ML, Chung TS, et al., “Permeability of polyimides derived from non-coplanar diamines and 4,4'-(hexafluoroisopropylidene)diphthalic anhydride,” *Polymer*

- 44 (2003) 4715-4721.
141. Chan SS, Chung TS, Liu Y, et al., "Gas and hydrocarbon (C-2 and C-3) transport properties of co-polyimides synthesized from 6FDA and 1,5-NDA (naphthalene)/Durene diamines," J. Mem. Sci. 218 (2003) 235-245.
142. Cao C, Chung TS, Liu Y, et al., "Chemical cross-linking modification of 6FDA-2,6-DAT hollow fiber membranes for natural gas separation," J. Mem. Sci. 216 (2003) 257-268.
143. Ayala D, Lozano AE, de Abajo J, et al., "Gas separation properties of aromatic polyimides," J. Mem. Sci. 215 (2003) 61-73.
144. Liu Y, Chng ML, Chung TS, et al., "Effects of amidation on gas permeation properties of polyimide membranes," J. Mem. Sci. 214 (2003a) 83-92.
145. Liu Y, Chung TS, Wang R, et al., "Chemical cross-linking modification of polyimide/poly(ether sulfone) dual-layer hollow-fiber membranes for gas separation," Ind. Eng. Chem. Res. 42 (2003d) 1190-1195.
146. Lin WH, Chung TS, "The physical aging phenomenon of 6FDA-durene polyimide hollow fiber membranes," J. Polym. Sci. B Polym. Phys. 38 (2000) 765-775.
147. Lin WH, Chung TS, "Gas permeability, diffusivity, solubility, and aging characteristics of 6FDA-durene polyimide membranes," J. Mem. Sci. 186 (2001) 183-193.
148. Fuertes AB, Nevskiaia DM, Centeno TA, "Carbon composite membranes from Matrimid (R) and Kapton (R) polyimides for gas separation," Micropor. Mesopor. Mater. 33 (1999) 115-125 .
149. Jois YHR, Reale J, "Preparation of supported polyimide membranes for gas separations," USP 5928410 (1999).
150. Baker RW, Wijmans JG, He Z, Pinnau I, "Multiple-bed permselective membrane separation for rejection of nitrogen, carbon dioxide, water, and hydrogen sulfide from natural gas," USP 6565626 (2003).
151. Lee SJ, Kim MS, Chung JG, "Preparation of porous polycarbonate membranes using supercritical CO<sub>2</sub> with enhanced solubility," J. Ind. Eng. Chem. 10 (2004) 877-882.
152. Hacarlioglu P, Toppare L, Yilmaz L, "Effect of preparation parameters on performance of dense homogeneous polycarbonate gas separation membranes," J. Appl. Polym. Sci. 90 (2003) 776-785.
153. Pereira B, Admassu W, "Effects of chemical impurities on gas sorption in polymeric membranes. I. Polycarbonate and polysulfone," Sep. Sci. Technol. 36 (2001) 177-197.
154. Chen SH, Huang SL, Yu KC, et al., "Effect of CO<sub>2</sub> treated polycarbonate membranes on gas transport and sorption properties," J. Mem. Sci. 172 (2000) 105-112.
155. Dai Y, Guiver MD, Robertson GP, et al., "Effect of hexafluoro-2-propanol substituents in polymers on gas permeability and fractional free volume," Macromol. 38 (2005) 9670-9678.
156. Bhole YS, Kharul UK, Somani SP, et al., "Benzoylation of polyphenylene oxide: Characterization and gas permeability investigations," Euro. Polym. J. 41 (2005) 2461-2471.
157. Yoshimune M, Fujiwara I, Suda H, et al., "Novel carbon molecular sieve membranes derived from poly(phenylene oxide) and its derivatives for gas separation," Chem. Let. 34 (2005) 958-959.
158. Li JT, Wang SC, Nagai K, et al., "Effect of polyethyleneglycol (PEG) on gas permeabilities and permselectivities in its cellulose acetate (CA) blend membranes," J. Mem. Sci. 138 (1998) 143-152.

159. Li JT, Nagai K, Nakagawa T, et al., "Preparation of polyethyleneglycol (peg) and cellulose-acetate (ca) blend membranes and their gas permeabilities," *J. Appl. Polym. Sci.*, 58 (1995) 1455-1463.
160. Hamad F, Khulbe KC, Matsuura T, "Comparison of gas separation performance and morphology of homogeneous and composite PPO membranes," *J. Mem. Sci.* 256 (2005a) 29-37.
161. Hamad F, Matsuura T, "Performance of gas separation membranes made from sulfonated brominated high molecular weight poly(2,4-dimethyl-1,6-phenylene oxide)," *J. Mem. Sci.* 253 (2005b) 183-189.
162. Polotskaya G, Biryulin Y, Pientka Z, et al., "Transport properties of fullerene-polyphenylene oxide homogeneous membranes," *Full. Nanotube Carbon Nanos.* 12 (2004) 365-369.
163. Khulbe KC, Hamad F, Feng C, et al., "Characterization of the poly(phenylene oxide) dense membrane prepared at different temperatures," *Sep. Purif. Tech.* 36 (2004) 53-62.
164. Lie JA, Hagg MB, "Carbon membranes from cellulose and metal loaded cellulose," *Carbon* 43 (2005) 2600-2607.
165. Eckelt J, Wolf BA, "Membranes directly prepared from solutions of unsubstituted cellulose," *Macromol. Chem. Phys.* 206 (2005) 227-232.
166. Jie XM, Cao YM, Lin B, et al., "Gas permeation performance of cellulose hollow fiber membranes made from the cellulose/N-methylmorpholine-N-oxide/H<sub>2</sub>O system," *J. Appl. Polym. Sci.* 91 (2004) 1873-1880.
167. Nakabayashi M, Okabe K, Fujisawa E, Hirayama Y, Kazama S, Matsumiya N, Takagi K, Mano H, Haraya K, Kamizawa C, "Carbon-dioxide separation through water-swollen-gel membrane," *Energy Conversion and Management* 36 (1995) 419-422.
168. Riekerink MBO, Engbers GHM, Wessling M, et al., "Tailoring the properties of asymmetric cellulose acetate membranes by gas plasma etching," *J. Col. Interf. Sci.* 245 (2002) 338-348.
169. Banerjee S, Maier G, Dannenberg C, et al., "Gas permeabilities of novel poly(arylene ether)s with terphenyl unit in the main chain," *J. Mem. Sci.* 229 (2004) 63-71.
170. Hao J, Rice PA, Stem SA, "Upgrading low-quality natural gas with H<sub>2</sub>S- and CO<sub>2</sub>-selective polymer membranes Part I. Process design and economics of membrane stages without recycle streams," *J. Mem. Sci.* 209 (2002) 177-206.
171. Queiroz DP, Pinho MN, "Gas permeability of polypropylene oxide/polybutadiene bi-soft segment urethane/urea membranes," *Desal.* 145 (2002) 379-383.
172. Xu ZK, Dannenberg C, Springer J, et al., "Novel poly(arylene ether) as membranes for gas separation," *J. Mem. Sci.* 205 (2002) 23-31.
173. Park HB, Kim JH, Kim JK, et al., "Morphology of a poly(imide siloxane) segmented copolymer/silica hybrid composite," *Macrom. Rapid Comm.* 23 (2002b) 544-550.
174. Wang ZY, Moulinie PR, Handa YP, "Gas transport properties of novel poly(arylene ether ketone)s containing dibenzoylbiphenyl and benzonaphthone moieties," *J. Polym. Sci. B Polym. Phys.* 36 (1998) 425-431.
175. Chatterjee G, Houde AA, Stern SA, "Poly(ether urethane) and poly(ether urethane urea) membranes with high H<sub>2</sub>S/CH<sub>4</sub> selectivity," *J. Mem. Sci.* 135 (1997) 99-106.
176. Simmons, JW "Block polyester-ether gas separation membranes," *USP* 6,860,920 (2005).
177. Lin H, Freeman BD, "Gas solubility, diffusivity and permeability in poly(ethylene oxide)," *J. Mem. Sci.* 239 (2004) 105-117.

178. Koros WJ, Mahajan R, "Pushing the limits on possibilities for large scale gas separation: Which strategies?," J. Mem. Sci. 175 (2000) 181-196.
179. Koros WJ, Mahajan R, "Pushing the limits on possibilities for large scale gas separation: Which strategies?," J. Mem. Sci. 181 (2001) 141-141.
180. Burns RL, Koros WJ, "Structure-property relationships for poly(pyrrolone-imide) gas separation membranes," Macromol. 36 (2003) 2374-2381.
181. Budd PM, McKeown NB, Fritsch D, "Free volume and intrinsic microporosity in polymers," J. Mater. Chem, 15 (2005a) 1977-1986.
182. Budd PM, Msayib KJ, Tattershall CE, et al., "Gas separation membranes from polymers of intrinsic microporosity," J. Mem. Sci., 251 (2005b) 263-269.
183. McKeown NB, Budd PM, Msayib KJ, et al., "Polymers of intrinsic microporosity (PIMs)," Chem.- A Eur. J. 11 (2005) 2610-2620.
184. Zimmerman CM, Koros WJ, "Comparison of gas transport and sorption in the ladder polymer BBL and some semi-ladder polymers," Polymer 40 (1999a) 5655-5664.
185. Zimmerman CM, Koros WJ, "Entropic selectivity analysis of a series of polypyrrolones for gas separation membranes," Macromol. 32 (1999b) 3341-3346.
186. Zimmerman CM, Koros WJ, "Polypyrrolones for membrane gas separations. I. Structural comparison of gas transport and sorption properties," J. Polym. Sci. B Polym. Phys. 37 (1999c) 1235-1249.
187. Zimmerman CM, Koros WJ, "Polypyrrolones for membrane gas separations. II. Activation energies and heats of sorption," J. Polym. Sci. B Polym. Phys. 37 (1999d) 1251-1265.
188. Chung TS, Ren JH, Wang R, et al., "Development of asymmetric 6FDA-2,6DAT hollow fiber membranes for CO<sub>2</sub>/CH<sub>4</sub> separation Part 2. Suppression of plasticization," J. Mem. Sci. 214 (2003) 57-69.
189. Bos A, Punt IGM, Wessling M, et al., "Suppression of CO<sub>2</sub>-plasticization by semi-interpenetrating polymer network formation," J. Polym. Sci. B Polym. Phys., 36 (1998b) 1547-1556.
190. Bos A, Punt IGM, Wessling M, et al., "Plasticization-resistant glassy polyimide membranes for CO<sub>2</sub>/CH<sub>4</sub> separations," Sep. Purif. Technol 14 (1998a) 27-39.
191. Bos A, Punt IGM, Wessling M, et al., "CO<sub>2</sub>-induced plasticization phenomena in glassy polymers," J. Mem. Sci. 155 (1999) 67-78.
192. Bos A, Punt I, Strathmann H, et al., "Suppression of gas separation membrane plasticization by homogeneous polymer blending," AIChE J. 47 (2001): 1088-1093.
193. Shao L, Chung TS, Goh SH, et al., "Polyimide modification by a linear aliphatic diamine to enhance transport performance and plasticization resistance," J. Mem. Sci. 256 (2005dc) 46-56.
194. Wind JD, Paul DR, Koros WJ, "Natural gas permeation in polyimide membranes," J. Mem. Sci. 228 (2004) 227-236.
195. Wind JD, Sirard SM, Paul DR, et al., "Carbon dioxide-induced plasticization of polyimide membranes: Pseudo-equilibrium relationships of diffusion, sorption, and swelling," Macromol. 36 (2003a) 6433-6441.
196. Wind JD, Sirard SM, Paul DR, et al., "Relaxation dynamics of CO<sub>2</sub> diffusion, sorption, and polymer swelling for plasticized polyimide membranes," Macromol. 36 (2003b) 6442-6448.
197. Wind JD, Staudt-Bickel C, Paul DR, et al., "Solid-state covalent cross-linking of

- polyimide membranes for carbon dioxide plasticization reduction,” *Macromol.* 36 (2003c) 1882-1888.
198. Wind JD, Staudt-Bickel C, Paul DR, et al., “The effects of crosslinking chemistry on CO<sub>2</sub> plasticization of polyimide gas separation membranes,” *Ind. Eng. Chem. Res.* 41 (2002) 6139-6148.
  199. Taubert A, Wind JD, Paul DR, et al., “Novel polyimide ionomers: CO<sub>2</sub> plasticization, morphology, and ion distribution,” *Polym.* 44 (2003) 1881-1892.
  200. Krol JJ, Boerrigter M, Koops GH, “Polyimide hollow fiber gas separation membranes: preparation and the suppression of plasticization in propane/propylene environments,” *J. Mem. Sci.* 184 (2001) 275-286.
  201. Staudt-Bickel C, Koros WJ, “Improvement of CO<sub>2</sub>/CH<sub>4</sub> separation characteristics of polyimides by chemical crosslinking,” *J. Mem. Sci.* 155 (1999) 145-154.
  202. Kawakami H, Mikawa M, Nagaoka S, “Gas transport properties in thermally cured aromatic polyimide membranes,” *J. Mem. Sci.* 118 (1996) 223-230.
  203. Liu Y, Wang R, Chung TS, “Chemical cross-linking modification of polyimide membranes for gas separation,” *J. Mem. Sci.* 189 (2001) 231-239.
  204. Hu CC, Tu CY, Wang YC, et al., “Effects of plasma treatment on CO<sub>2</sub> plasticization of poly(methyl methacrylate) gas-separation membranes,” *J. Appl. Polym. Sci.* 93 (2004) 395-401.
  205. Suzuki T, Yamada Y, “Characterization of 6FDA-based hyperbranched and linear polyimide-silica hybrid membranes by gas permeation and Xe-129 NMR measurements,” *J. Polym. Sci. B Polym. Phys.* 44 (2006) 291-298.
  206. Suzuki T, Yamada Y, “Physical and gas transport properties of novel hyperbranched polyimide-silica hybrid membranes,” *Polym. Bull.* 53 (2005) 139-146.
  207. Kim JH, Lee YM, “Gas permeation properties of poly(amide-6-b-ethylene oxide)-silica hybrid membranes,” *J. Mem. Sci.* 193 (2001) 209-225.
  208. Tamaki R, Chujo Y, Kuraoka K, et al., “Application of organic-inorganic polymer hybrids as selective gas permeation membranes,” *J. Mater. Chem.* 9 (1999) 1741-1746.
  209. Park HB, Kim JK, Nam SY, et al., “Imide-siloxane block copolymer/silica hybrid membranes: preparation, characterization and gas separation properties,” *J. Mem. Sci.* 220 (2003) 59-73.
  210. Budd PM, Ghanem BS, Makhseed S, et al., “Polymers of intrinsic microporosity (PIMs) robust, solution-processable, organic nanoporous materials,” *Chem. Comm.* 2 (2004) 230-231.
  211. Shida Y, Sakaguchi T, Shiotsuki M, et al., “Synthesis and properties of membranes of poly(diphenylacetylenes) having fluorines and hydroxyl groups,” *Macromol.* 39 (2006): 569-574.
  212. Shida Y, Sakaguchi T, Shiotsuki M, et al., “Synthesis and properties of poly(diphenylacetylenes) having hydroxyl groups,” *Macromol.* 38 (2005) 4096-4102.
  213. Sakaguchi T, Yumoto K, Shiotsuki M, et al., “Synthesis of poly(diphenylacetylene) membranes by desilylation of various precursor polymers and their properties,” *Macromol.* 38 (2005) 2704-2709.
  214. Sakaguchi T, Kwak G, Masuda T, “Synthesis of poly(1-beta-naphthyl-2-phenylacetylene) membranes through desilylation and their properties,” *Polym.* 43 (2002) 3937-3942.
  215. Raharjo RD, Lee HJ, Freeman BD, et al., “Pure gas and vapor permeation properties of poly[1-phenyl-2-[p-(trimethylsilyl)phenyl]acetylene] (PTMSDPA) and its desilylated

- analog, poly[diphenylacetylene],” (PDPA), *Polym.* 46 (2005) 6316-6324.
216. Hill AJ, Pas SJ, Bastow TJ, et al., “Influence of methanol conditioning and physical aging on carbon spin-lattice relaxation times of poly(1-trimethylsilyl-1-propyne),” *J. Mem. Sci.* 243 (2004) 37-44.
  217. Pinnau I, Toy LG, “Transport of organic vapors through poly(1-trimethylsilyl-1-propyne),” *J. Mem. Sci.* 116 (1996) 199-209.
  218. Pinnau I, He ZJ, Morisato A, “Synthesis and gas permeation properties of poly(dialkylacetylenes) containing isopropyl-terminated side-chains,” *J. Mem. Sci.* 241 (2004) 363-369.
  219. Pinnau I, Morisato A, He ZJ, “Influence of side-chain length on the gas permeation properties of poly(2-alkylacetylenes),” *Macromol.* 37 (2004) 2823-2828.
  220. Merkel TC, Bondar V, Nagai K, et al., “Hydrocarbon and perfluorocarbon gas sorption in poly(dimethylsiloxane), poly(1-trimethylsilyl-1-propyne), and copolymers of tetrafluoroethylene and 2,2-bis(trifluoromethyl)-4,5-difluoro-1,3-dioxole,” *Macromol.* 32 (1999) 370-374.
  221. Merkel TC, Bondar V, Nagai K, et al., “Sorption and transport of hydrocarbon and perfluorocarbon gases in poly(1-trimethylsilyl-1-propyne),” *J. Polym. Sci. B Polym. Phys.* 38 (2000) 273-296.
  222. Merkel TC, Gupta RP, Turk BS, et al., “Mixed-gas permeation of syngas components in poly(dimethylsiloxane) and poly(1-trimethylsilyl-1-propyne) at elevated temperatures,” *J. Mem. Sci.* 191 (2001) 85-94.
  223. Merkel TC, He ZJ, Pinnau I, et al., “Sorption and transport in poly(2,2-bis(trifluoromethyl)-4,5-difluoro-1,3-dioxole-co-tetrafluoroethylene) containing nanoscale fumed silica,” *Macromol.* 36 (2003) 8406-8414.
  224. Nagai K, Freeman BD, Hill AJ, “Effect of physical aging of poly(1-trimethylsilyl-1-propyne) films synthesized with TaCl<sub>5</sub> and NbCl<sub>5</sub> on gas permeability, fractional free volume, and positron annihilation lifetime spectroscopy parameters,” *J. Polym. Sci. B Polym. Phys.* 38 (2000) 1222-1239.
  225. Nagai K, Masuda T, Nakagawa T, et al., “Poly[1-(trimethylsilyl)-1-propyne] and related polymers: synthesis, properties and functions,” *Prog. Polym. Sci.* 26 (2001) 721-798.
  226. Yampolskii YP, Korikov AP, Shantarovich VP, et al., “Gas permeability and free volume of highly branched substituted acetylene polymers,” *Macromol.* 34 (2001) 1788-1796.
  227. Yampolskii YP, Motyakin MV, Wasserman AM, et al., “Study of high permeability polymers by means of the spin probe technique,” *Polymer* 40 (1999) 1745-1752.
  228. Kwak G, Aoki T, Toy LG, et al., “Synthesis, characterization, and oxygen permeability of homo- and copolymers from p-[tris(trimethylsilyl)silyl]-phenylacetylene,” *Polym. Bull.* 45 (2000) 215-221.
  229. Higuchi A, Yoshida T, Imizu T, et al., “Gas permeation of fullerene-dispersed poly(1-trimethylsilyl-1-propyne) membranes,” *J. Polym. Sci. B Polym. Phys.* 38 (2000) 1749-1755.
  230. Morisato A, Pinnau I, “Synthesis and gas permeation properties of poly(4-methyl-2-pentyne),” *J. Mem. Sci.* 121 (1996) 243-250.
  231. Morisato A, Shen, HC, Sankar SS, et al., “Polymer characterization and gas permeability of poly(1-trimethylsilyl-1-propyne) [PTMSP], poly(1-phenyl-1-propyne) [PPP], and PTMSP/PPP blends,” *J. Polym. Sci. B Polym. Phys.* 34 (1996) 2209-2222.
  232. Gomes D, Nunes SP, Peinemann KV, “Membranes for gas separation based on poly(1-



- trimethylsilyl-1-propyne)-silica nanocomposites,” *J. Mem. Sci.* 246 (2005) 13-25.
233. He ZJ, Pinnau I, Morisato A, “Nanostructured poly(4-methyl-2-pentyne)/silica hybrid membranes for gas separation,” *Desalination* 146 (2002) 11-15.
  234. Camera-Roda G, “Performances of filled and unfilled PTMSP membranes in pervaporation,” *Chem Eng. Comm.* 163 (1988) 3-22 1998.
  235. Lin HQ, Van Wagner E, Raharjo R, et al., “High-performance polymer membranes for natural-gas sweetening,” *Adv. Mater.* 18 (2006a) 39-44.
  236. Lin H, Van Wagner E, Freeman BD, Toy LG, Gupta RP, “Plasticization-enhanced hydrogen purification using polymeric membranes,” *Science* 311 (2006) 639-642.
  237. Lin HQ, Freeman BD, “Gas and vapor solubility in cross-linked poly(ethylene glycol diacrylate),” *Macromol.* 38 (2005) 8394-8407.
  238. Lin HQ, Freeman BD, “Materials selection guidelines for membranes that remove CO<sub>2</sub> from gas mixtures,” *J. Mol. Struct.* 739 (2005) 57-74.
  239. Kalakkunnath S, Kalika DS, Lin HQ, et al., “Segmental relaxation characteristics of cross-linked poly(ethylene oxide) copolymer networks,” *Macromol.* 38 (2005) 9679-9687.
  240. Orme CJ, Stewart FF, “Mixed gas hydrogen sulfide permeability and separation using supported polyphosphazene membranes,” *J. Mem. Sci.* 253 (2005) 243-249.
  241. Orme CJ, Klaehn JR, Stewart FF, “Gas permeability and ideal selectivity of poly [bis-(phenoxy)phosphazene], poly [bis-(4-tert-butylphenoxy)phosphazene], and poly [bis-(3,5-di-tert-butylphenoxy)(1.2)(chloro)(0.8)phosphazene],” *J. Mem. Sci.* 238 (2004) 47-55.
  242. a) Patel NP, Spontak RJ, “Gas-transport and thermal properties of a microphase-ordered poly(styrene-*b*-ethylene oxide-*b*-styrene) triblock copolymer and its blends with poly(ethylene glycol),” *Macromol.* 37 (2004) 2829-2838.  
 b) Patel NP, Aberg CM, Sanchez AM, et al., “Morphological, mechanical and gas-transport characteristics of crosslinked poly(propylene glycol) homopolymers, nanocomposites and blends,” *Polymer*, 45 (2004) 5941-5950.  
 c) Patel NP, Zielinski JM, Samseth J, et al., “Effects of pressure and nanoparticle functionality on CO<sub>2</sub>-selective nanocomposites derived from crosslinked poly(ethylene glycol),” *Macromol. Chem. Phys.* 205 (2004) 2409-2419.
  243. a) Patel NP, Hunt MA, Lin-Gibson S, et al., “Tunable CO<sub>2</sub> transport through mixed polyether membranes,” *J. Mem. Sci.* 251 (2005) 51-57.  
 b) Patel NP, Miller AC, Spontak RJ, “Highly CO<sub>2</sub>-permeable and -selective membranes derived from crossfinked poly(ethylene glycol) and its nanocomposites,” *Adv. Func. Mater.* 14 (2004c) 699-707.  
 c) Patel NP, Miller AC, Spontak RJ, “Highly CO<sub>2</sub>-permeable and selective polymer nanocomposite membranes,” *Adv. Mater.* 15 (2003) 729-733.
  244. Metz SJ, van de Ven WJC, Potreck J, et al., “Transport of water vapor and inert gas mixtures through highly selective and highly permeable polymer membranes,” *J. Mem. Sci.* 251 (2005) 29-41.
  245. Metz SJ, Mulder MHV, Wessling M, “Gas-permeation properties of poly(ethylene oxide) poly(butylene terephthalate) block copolymers,” *Macromol.* 37 (2004) 4590-4597.
  246. Metz SJ, Potreck J, Mulder M, et al., “Water vapor and gas transport through a poly(butylene terephthalate) poly(ethylene oxide) block copolymer,” *Desal.* 148 (2002) 303-307.

247. Liu L, Chakma A, Feng X, "Preparation of hollow fiber poly(ether block amide)/polysulfone composite membranes for separation of carbon dioxide from nitrogen," *Chem. Eng. J.* 105 (2004) 43-51.  
Liu L, Chakma A, Feng XS, "A novel method of preparing ultrathin poly(ether block amide) membranes," *J. Mem. Sci.* 235 (2004) 43-52.
248. Balachandra AM, Baker GL, Bruening ML, "Preparation of composite membranes by atom transfer radical polymerization initiated from a porous support," *J. Mem. Sci.* 227 (2003) 1-14.
249. Orme CJ, Stone ML, Benson MT, et al., "Testing of polymer membranes for the selective permeability of hydrogen," *Sep. Sci. Technol.* 38 (2003) 3225-3238.
250. Kim YK, Lee JM, Park HB, et al., "The gas separation properties of carbon molecular sieve membranes derived from polyimides having carboxylic acid groups," *J. Mem. Sci.* 235 (2004) 139-146.
251. Kim JH, Ha SY, Nam SY, et al., "Selective permeation of CO<sub>2</sub> through pore-filled polyacrylonitrile membrane with poly(ethylene glycol)," *J. Mem. Sci.* 186 (2001) 97-107.
252. Bondar VI, Freeman BD, Pinnau I, "Gas transport properties of poly(ether-b-amide) segmented block copolymers," *J. Polym. Sci. B Polym. Phys.* 38 (2000) 2051-2062.
253. Hirayama Y, Kase Y, Tanihara R, et al., "Permeation properties to CO<sub>2</sub> and N<sub>2</sub> of poly(ethylene oxide)-containing and crosslinked polymer films," *J. Mem. Sci.* 160 (1999) 87-99.
254. Kita H, Tabuchi M, Sakai T, "Polyether separation membrane," *USP App.* 2003110947 (2003).
255. Laverty BW, Chowdhury G, Vujosevic R, Deng S, Yao B, Matsuura T, "Manufacture of permeable gas separation materials having good mechanical strength and permselectivity," *PCT Int. App. WO* 9942204 (1999).
256. Senthilkumar U, Rajini R, Reddy BSR, "Gas permeation and sorption properties of non-ionic and cationic amino-hydroxy functionalized poly(dimethylsiloxane) membranes," *J. Mem. Sci.* 254 (2005) 169-177.
257. Senthilkumar U, Reddy BSR, "Structure-gas separation property relationships of non-ionic and cationic amino-hydroxy functionalized poly (dimethylsiloxane) membranes," *J. Mem. Sci.* 232 (2004) 73-83.
258. Queiroz DP, de Pinho MN, "Structural characteristics and gas permeation properties of polydimethylsiloxane/poly(propylene oxide) urethane/urea bi-soft segment membranes," *Polymer* 46 (2005) 2346-2353.
259. Prabhakar RS, Merkel TC, Freeman BD, et al., "Sorption and transport properties of propane and perfluoropropane in poly(dimethylsiloxane) and poly(1-trimethylsilyl-1-propyne)," *Macromol.* 38 (2005) 1899-1910.
260. Pinnau I, He ZJ, "Pure- and mixed-gas permeation properties of polydimethylsiloxane for hydrocarbon/methane and hydrocarbon/hydrogen separation," *J. Mem. Sci.* 244 (2004) 227-233.
261. Abdellah L, Boutevin B, Guida-Pietrasanta F, et al., "Evaluation of photocrosslinkable fluorinated polydimethylsiloxanes as gas permeation membranes," *J. Mem. Sci.* 217 (2003) 295-298.
262. Kuraoka K, Chujo Y, Yazawa T, "Hydrocarbon separation via porous glass membranes surface-modified using organosilane compounds," *J. Mem. Sci.* 182 (2001) 139-149.

263. Matsuyama H, Teramoto M, Hirai K, "Effect of plasma treatment on CO<sub>2</sub> permeability and selectivity of poly(dimethylsiloxane) membrane," J. Mem. Sci. 99 (1995) 139-147.
264. Orme CJ, Harrup MK, Luther TA, et al., "Characterization of gas transport in selected rubbery amorphous polyphosphazene membranes," J. Mem Sci, 186 (2001) 249-256.
265. Nagai K, Freeman BD, Cannon A, et al., "Gas permeability of poly(bis-trifluoroethoxyphosphazene) and blends with adamantane amino/trifluoroethoxy (50/50) polyphosphazene," J. Mem Sci. 172 (2000) 167-176.
266. Barbi V, Funari SS, Gehrke R, et al., "SAXS and the gas transport in polyether-block-polyamide copolymer membranes," Macromol. 36 (2003) 749-758.
267. Yoshino M, Ito K, Kita H, et al., "Effects of hard-segment polymers on CO<sub>2</sub>/N<sub>2</sub> gas-separation properties of poly(ethylene oxide)-segmented copolymers," J. Polym. Sci. B Polym. Phys. 38 (2000) 1707-1715.
268. Okamoto K, Fujii M, Okamoto S, et al., "Gas permeation properties of poly(ether imide) segmented copolymers," Macromol. 28 (1995) 6950-6956.
269. Okamoto K, Umeo N, Okamoto S, et al., "Selective permeation of carbon-dioxide over nitrogen through polyethyleneoxide-containing polyimide membranes," Chem. Let., (1993) 225-228.
270. Kovvali AS, Sirkar KK, "Stable liquid membranes - Recent developments and future directions," Ann. N. Y. Acad. Sci. 984 (2003) 279-288.
271. Chen H, Kovvali AS, Majumdar S, et al., "Selective CO<sub>2</sub> separation from CO<sub>2</sub>-N<sub>2</sub> mixtures by immobilized carbonate-glycerol membranes," Ind. Eng. Chem. Res. 38 (1999) 3489-3498.
272. Chen H, Kovvali AS, Sirkar KK, "Selective CO<sub>2</sub> separation from CO<sub>2</sub>-N<sub>2</sub> mixtures by immobilized glycine-Na-glycerol membranes," Ind. Eng. Chem. Res. 39 (2000) 2447-2458.
273. Chen H, Obuskovic G, Majumdar S, et al., "Immobilized glycerol-based liquid membranes in hollow fibers for selective CO<sub>2</sub> separation from CO<sub>2</sub>-N<sub>2</sub> mixtures," J. Mem Sci. 183 (2001) 75-88.
274. Kovvali AS, Sirkar KK, "Carbon dioxide separation with novel solvents as liquid membranes," Ind. Eng. Chem. Res. 41 (2002) 2287-2295.
275. Kovvali AS, Sirkar KK, "Dendrimer liquid membranes: CO<sub>2</sub> separation from gas mixtures," Industrial & Engineering Chemistry Research, 40 (2001) 2502-2511.
276. Quinn R, Appleby JB, Pez GP, "Hydrogen sulfide separation from gas streams using salt hydrate chemical absorbents and immobilized liquid membranes," Sep. Sci. Technol. 37 (2002) 627-638.
277. Quinn R, Laciak DV, Pez GP, "Polyelectrolyte-salt blend membranes for acid gas separations," J. Mem Sci., 131 (1997) 61-69.
278. Quinn R, Appleby JB, Pez GP, "New facilitated transport membranes for the separation of carbon-dioxide from hydrogen and methane," J. Mem Sci. 104 (1995) 139-146.
279. Quinn R, Laciak DV, Appleby JB, Pez GP, "Polyelectrolyte membranes for the separation of acid gases," USP 5,336,298 (1993).
280. Quinn R, Laciak DV, "Polyelectrolyte membranes for acid gas separations," J. Mem Sci., 131 (1997) 49-60.
281. Quinn R, "A repair technique for acid gas selective polyelectrolyte membranes," J. Mem Sci. 139 (1998) 97-102.
282. Matsuyama H, Teramoto M, Matsui K, et al., "Preparation of poly(acrylic

- acid)/poly(vinyl alcohol) membrane for the facilitated transport of CO<sub>2</sub>,” J. Appl. Pol. Sci. 81 (2001) 936-942.
283. Way JD, Noble RD, Reed DL, et al., “Facilitated transport of CO<sub>2</sub> in ion-exchange membranes,” AIChE J. 33 (1987) 480-487.
  284. Noble RD, Pellegrino JJ, Grosogeat E, et al., “CO<sub>2</sub> separation using facilitated transport ion-exchange membranes,” Sep. Sci. Technol. 23 (1988) 1595-1609.
  285. Eriksen OI, Aksnes E, Dahl IM, “Facilitated transport of ethene through nafion membranes. 1. Water swollen membranes,” J. Mem Sci. 85 (1993) 89-97.
  286. Eriksen OI, Aksnes E, Dahl IM, “Facilitated transport of ethene through nafion membranes. Part II. Glycerin treated, water swollen membranes,” J. Mem Sci. 85 (1993) 99-106.
  287. LeBlanc OH, Ward WJ, Matson SL, Kimura SG, “Facilitated transport in ion-exchange membranes,” J. Mem Sci. 6 (1980) 339-343.
  288. Kim MJ, Park YI, Youm KH, et al., “Gas permeation through water-swollen polysaccharide/poly(vinyl alcohol) membranes,” J. Appl. Pol. Sci. 91 (2004) 3225-3232.
  289. Park YI, Lee KH, “Preparation of water-swollen hydrogel membranes for gas separation,” J. Appl. Pol. Sci., 80 (2001) 1785-1791.
  290. Park YI, Lee KH, “Preparation of water-swollen hydrogel membranes for the separation of carbon dioxide,” J. Ind. Eng. Chem. 5 (1999) 235-239.
  291. Kim MJ, Park YI, Youm KH, et al., “Facilitated transport of CO<sub>2</sub> through ethylenediamine-fixed cation-exchange polysaccharide membranes,” J. Mem Sci. 245 (2004) 79-86.
  292. Zhang Y, Wang Z, Wang SC, “Novel fixed-carrier membranes for CO<sub>2</sub> separation,” J. Appl. Pol. Sci. 86 (2002) 2222-2226.
  293. Zhang Y, Wang Z, Wang SC, “Selective permeation of CO<sub>2</sub> through new facilitated transport membranes,” Desalination 145 (2002) 385-388.
  294. Teramoto M, Kitada S, Ohnishi N, et al., “Separation and concentration of CO<sub>2</sub> by capillary-type facilitated transport membrane module with permeation of carrier solution,” J. Mem Sci. 234 (2004) 83-94.
  295. Teramoto M, Ohnishi N, Takeuchi N, et al., “Separation and enrichment of carbon dioxide by capillary membrane module with permeation of carrier solution,” Sep. Purif. Technol. 30 (2003) 215-227.
  296. Teramoto M, Takeuchi N, Maki T, et al., “Facilitated transport of CO<sub>2</sub> through liquid membrane accompanied by permeation of carrier solution,” Sep. Purif. Technol. 27 (2002) 25-31.
  297. Lagorsse S, Campo MC, Magalhaes FD, et al., “Water adsorption on carbon molecular sieve membranes: Experimental data and isotherm model,” Carbon 43 (2005) 2769-2779.
  298. Lagorsse S, Leite A, Magalhaes FD, et al., “Novel carbon molecular sieve honeycomb membrane module: configuration and membrane characterization,” Carbon 43 (2005) 809-819.
  299. Lagorsse S, Magalhaes FD, Mendes A, “Carbon molecular sieve membranes - Sorption, kinetic and structural characterization,” J. Mem. Sci. 241 (2004) 275-287.
  300. Kim YK, Park HB, Lee YM, “Preparation and characterization of carbon molecular sieve membranes derived from BTDA-ODA polyimide and their gas separation properties,” J. Mem. Sci. 255 (2005) 265-273.
  301. Kim YK, Park HB, Lee YM, “Gas separation properties of carbon molecular sieve

- membranes derived from polyimide/polyvinylpyrrolidone blends: effect of the molecular weight of polyvinylpyrrolidone,” *J. Mem. Sci.* 251 (2005) 159-167.
302. Kim YK, Park HB, Lee YM, “Carbon molecular sieve membranes derived from thermally labile polymer containing blend polymers and their gas separation properties,” *J. Mem. Sci.* 243 (2004) 9-17.
  303. Park HB, Lee SY, Lee YM, “Pyrolytic carbon membranes containing silica: morphological approach on gas transport behavior,” *J. Mol. Struct.* 739 (2005) 179-190.
  304. Park HB, Jung CH, Kim YK, et al., “Pyrolytic carbon membranes containing silica derived from poly(imide siloxane) the effect of siloxane chain length on gas transport behavior and a study on the separation of mixed gases,” *J. Mem. Sci.* 235 (2004) 87-98.
  305. Park HB, Kim YK, Lee JM, et al., “Relationship between chemical structure of aromatic polyimides and gas permeation properties of their carbon molecular sieve membranes,” *J. Mem. Sci.* 229 (2004) 117-127.
  306. Barsema JN, van der Vegt NFA, Koops GH, et al., “Ag-functionalized carbon molecular-sieve membranes based on polyelectrolyte/polyimide blend precursors,” *Adv. Funct. Mater.* 15 (2005) 69-75.
  307. Barsema JN, Balster J, Jordan V, et al., “Functionalized carbon molecular sieve membranes containing Ag-nanoclusters,” *J. Mem. Sci.* 219 (2003) 47-57.
  308. Barsema JN, van der Vegt NFA, Koops GH, et al., “Carbon molecular sieve membranes prepared from porous fiber precursor,” *J. Mem. Sci.* 205 (2002) 239-246.
  309. Tin PS, Chung TS, Hill AJ, “Advanced fabrication of carbon molecular sieve membranes by nonsolvent pretreatment of precursor polymers,” *Ind. Eng. Chem. Res.* 43 (2004) 6476-6483.
  310. Tin PS, Chung TS, “Novel approach to fabricate carbon molecular-sieve membranes based on consideration of interpenetrating networks,” *Macrom. Rapid Comm.* 25 (2004) 1247-1250.
  311. Vu DQ, Koros WJ, Miller SJ, “Effect of condensable impurities in CO<sub>2</sub>/CH<sub>4</sub> gas feeds on carbon molecular sieve hollow-fiber membranes,” *Ind. Eng. Chem. Res.* 42 (2003) 1064-1075.
  312. Fuertes AB, Centeno TA, “Carbon molecular sieve membranes from polyetherimide,” *Micropor. Mesopor. Mater.* 26 (1998) 23-26.
  313. Centeno TA, Fuertes AB, “Supported carbon molecular sieve membranes based on a phenolic resin,” *J. Mem. Sci.* 160 (1999) 201-211.
  314. Shin DW, Hyun SH, Cho CH, et al., “Synthesis and CO<sub>2</sub>/N<sub>2</sub> gas permeation characteristics of ZSM-5 zeolite membranes,” *Micropor. Mesopor. Mater.*, 85 (2005) 313-323.
  315. Li SG, Martinek JG, Falconer JL, et al., “High-pressure CO<sub>2</sub>/CH<sub>4</sub> separation using SAPO-34 membranes,” *Ind. Eng. Chem. Res.* 44 (2005) 3220-3228.
  316. Li SG, Alvarado G, Noble RD, et al., “Effects of impurities on CO<sub>2</sub>/CH<sub>4</sub> separations through SAPO-34 membranes,” *J. Mem. Sci.* 251 (2005) 59-66.
  317. Li SG, Falconer JL, Noble RD, “SAPO-34 membranes for CO<sub>2</sub>/CH<sub>4</sub> separation,” *J. Mem. Sci.* 241 (2004) 121-135.
  318. Xomeritakis G, Tsai CY, Brinker CJ, “Microporous sol-gel derived aminosilicate membrane for enhanced carbon dioxide separation,” *Sep. Purif. Technol.* 42 (2005) 249-257.
  319. Moon JH, Park YJ, Kim MB, et al., “Permeation and separation of a carbon

- dioxide/nitrogen mixture in a methyltriethoxysilane templating silica/alpha-alumina composite membrane," *J. Mem. Sci.* 250 (2005) 195-205.
320. Gu XH, Dong JH, Nenoff TM, "Synthesis of defect-free FAU-type zeolite membranes and separation for dry and moist CO<sub>2</sub>/N<sub>2</sub> mixtures," *Ind. Eng. Chem. Res.* 44 (2005) 937-944.
  321. Zhang LX, Gilbert KE, Baldwin RM, et al., "Preparation and testing of carbon/silicalite-1 composite membranes," *Chem. Eng. Comm.* 191 (2005) 665-681.
  322. Bernal MP, Coronas J, Menendez M, et al., "Separation of CO<sub>2</sub>/N<sub>2</sub> mixtures using MFI-type zeolite membranes," *AIChE J.* 50 (2004) 127-135.
  323. Bernal MP, Coronas J, Menendez M, et al., "On the effect of morphological features on the properties of MFI zeolite membranes," *Micropor. Mesopor. Mater.*, 60 (2003) 99-110.
  324. Poshusta JC, Noble RD, Falconer JL, "Characterization of SAPO-34 membranes by water adsorption," *J. Mem. Sci.* 186 (2001) 25-40.
  325. Poshusta JC, Tuan VA, Pape EA, et al., "Separation of light gas mixtures using SAPO-34 membranes," *AIChE J.* 46 (2000) 779-789.
  326. Poshusta JC, Tuan VA, Falconer JL, et al., "Synthesis and permeation properties of SAPO-34 tubular membranes," *Ind. Eng. Chem. Res.* 37 (1998) 3924-3929.
  327. Kusakabe K, Kuroda T, Uchino K, et al., "Gas permeation properties of ion-exchanged faujasite-type zeolite membranes," *AIChE J.* 45 (1999) 1220-1226.
  328. Kusakabe K, Sakamoto S, Saie T, et al., "Pore structure of silica membranes formed by a sol-gel technique using tetraethoxysilane and alkyltriethoxysilanes," *Sep. Purif. Technol.* 16 (1999) 139-146.
  329. Kusakabe K, Kuroda T, Morooka S, "Separation of carbon dioxide from nitrogen using ion-exchanged faujasite-type zeolite membranes formed on porous support tubes," *J. Mem. Sci.* 148 (1998) 13-23.
  330. van den Broeke LJP, Bakker WJW, Kapteijn F, et al., "Binary permeation through a silicalite-1 membrane," *AIChE J.* 45 (1999) 976-985.
  331. van den Broeke LJP, Bakker WJW, Kapteijn F, et al., "Transport and separation properties of a silicalite-1 membrane - I. Operating conditions," *Chem. Eng. Sci.* 54 (1999) 245-258.
  332. van den Broeke LJP, Kapteijn F, Moulijn JA, "Transport and separation properties of a silicalite-1 membrane - II. Variable separation factor," *Chem. Eng. Sci.* 54 (1999) 259-269.
  333. Masuda T, Fujikata Y, Nishida T, et al., "The influence of acid sites on intracrystalline diffusivities within MFI-type zeolites," *Micropor. Mesopor. Mater.*, 23 (1998) 157-167.
  334. Lovallo MC, Gouzinis A, Tsapatsis M, "Synthesis and characterization of oriented MFI membranes prepared by secondary growth," *AIChE J.* 44 (1998) 1903-1913.
  335. Lovallo MC, Tsapatsis M, "Preferentially oriented submicron silicalite membranes," *AIChE J.* 42 (1996) 3020-3029.
  336. Morooka S, Kuroda T, Kusakabe K, "Carbon dioxide separation from nitrogen using Y-type zeolite membranes," *Stud. Surf. Sci. Cat.* 114 (1998) 665-668.
  337. Cooper CA, Lin YS, "Microstructural and gas separation properties of CVD modified mesoporous gamma-alumina membranes," *J. Mem. Sci.* 195 (2002) 35-50.
  338. Tsai CY, Tam SY, Lu YF, et al., "Dual-layer asymmetric microporous silica membranes," *J. Mem. Sci.* 169 (2000) 255-268.

339. de Vos RM, Maier WF, Verweij H, "Hydrophobic silica membranes for gas separation," *J. Mem. Sci.* 158 (1999) 277-288.
340. de Vos RM, Verweij H, "High-selectivity, high-flux silica membranes for gas separation," *Science*, 279 (1998) 1710-1711.
341. de Vos RM, Verweij H, "Improved performance of silica membranes for gas separation," *J. Mem. Sci.* 143 (1998) 37-51.
342. Sircar S, Rao MB, Thaeron CMA, "Selective surface flow membrane for gas separation," *Sep. Sci. Technol.* 34 (1999) 2081-2093.
343. Sircar S, Waldron WE, Rao MB, et al., "Hydrogen production by hybrid SMR-PSA-SSF membrane system," *Sep. Purif. Technol.* 17 (1999) 11-20.
344. Sircar S, Golden TC, Rao MB, "Activated carbon for gas separation and storage," *Carbon* 34 (1996) 1-12.
345. Thaeron C, Parrillo DJ, Sircar S, et al., "Separation of hydrogen sulfide-methane mixtures by selective surface flow membrane," *Sep. Purif. Technol.* 15 (1999) 121-129.
346. Parrillo DJ, Thaeron C, Sircar S, "Separation of bulk hydrogen sulfide hydrogen mixtures by selective surface flow membrane," *AIChE J.* 43 (1997) 2239-2245.
347. Naheiri T, Ludwig KA, Anand M, et al., "Scale-up of selective surface flow membrane for gas separation," *Sep. Sci. Technol.* 32 (1997) 1589-1602.
348. Anand M, Langsam M, Rao MB, et al., "Multicomponent gas separation by selective surface flow (SSF) and poly-trimethylsilylpropyne (PTMSP) membranes," *J. Mem. Sci.* 123 (1997) 17-25.
349. Rao MB, Sircar S, "Performance and pore characterization of nanoporous carbon membranes for gas separation," *J. Mem. Sci.* 110 (1996) 109-118.
350. Rao MB, Sircar S, Abrardo JM, Baade WF, "Hydrogen recovery by adsorbent membranes," *Eur. Pat. Appl.* EP582184 (1994).
351. Singh RP, Way JD, McCarley KC, "Development of a model surface flow membrane by modification of porous vycor glass with a fluorosilane," *Ind. Eng. Chem. Res.* 43 (2004) 3033-3040.
352. Cui Y, Kita H, Okamoto KI, "Zeolite T membrane: preparation, characterization, pervaporation of water/organic liquid mixtures and acid stability," *J. Mem. Sci.* 236 (2004) 17-27.
353. Cui Y, Kita H, Okamoto KI, "Preparation and gas separation performance of zeolite T membrane," *J. Mater. Chem.* 14 (2004) 924-932.
354. Cui Y, Kita H, Okamoto KI, "Preparation and gas separation properties of zeolite T membrane," *Chem. Comm.* 17 (2003) 2154-2155.
355. Tomita T, Nakayama K, Sakai H, "Gas separation characteristics of DDR type zeolite membrane," *Micropor. Mesopor. Mater.* 68 (2004) 71-75.
356. Centeno TA, Vilas JL, Fuertes AB, "Effects of phenolic resin pyrolysis conditions on carbon membrane performance for gas separation," *J. Mem. Sci.* 228 (2004) 45-54.
357. Kalipcilar H, Bowen TC, Noble RD, et al., "Synthesis and separation performance of SSZ-13 zeolite membranes on tubular supports," *Chem. Mater.* 14 (2002) 3458-3464.
358. McCarley KC, Way JD, "Development of a model surface flow membrane by modification of porous gamma-alumina with octadecyltrichlorosilane," *Sep. Purif. Technol.* 25 (2001) 195-210.
360. Robeson LM, "Correlation of separation factor versus permeability for polymeric membranes," *J. Mem. Sci.* 62 (1991) 165-185.

361. Kim DS, Park HB, Rhim JW, et al., "Preparation and characterization of crosslinked PVA/SiO<sub>2</sub> hybrid membranes containing sulfonic acid groups for direct methanol fuel cell applications," *J. Mem. Sci.* 240 (2004) 37-48.
362. Kim DS, Park HB, Lee YM, et al., "Preparation and characterization of PVDF/silica hybrid membranes containing sulfonic acid groups," *J. Appl. Polym. Sci.* 93 (2004) 209-218.
363. Kim H, Lim C, Hong SI, "Gas permeation properties of organic-inorganic hybrid membranes prepared from hydroxyl-terminated polyether and 3-isocyanatopropyltriethoxysilane," *J. Sol-Gel Sci. Technol.* 36 (2005) 213-221.
364. Jose NM, Prado LASA, Yoshida IVP, "Synthesis, characterization, and permeability evaluation of hybrid organic-inorganic films," *J. Polym. Sci. B Polym. Phys.* 42 (2004) 4281-4292.
365. Lum DS, Shin KH, Park HB, et al., "Preparation and characterization of sulfonated poly(phthalazinone ether sulfone ketone) (SPPESEK)/Silica hybrid membranes for direct methanol fuel cell applications," *Macrom. Res.* 12 (2004) 413-421.
366. Dvornic PR, Li JM, de Leuze-Jallouli AM, et al., "Nanostructured dendrimer-based networks with hydrophilic polyamidoamine and hydrophobic organosilicon domains," *Macromol.* 35 (2002) 9323-9333.
367. West GD, Diamond GG, Holland D, et al., "Gas transport mechanisms through sol-gel derived templated membranes," *J. Mem. Sci.* 203 (2002) 53-69.
368. Cornelius CJ, Marand E, "Hybrid silica-polyimide composite membranes: gas transport properties," *J. Mem. Sci.* 202 (2002) 97-118.
369. Cornelius CJ, Marand E, "Hybrid inorganic-organic materials based on a 6FDA-6FpDA-DABA polyimide and silica: physical characterization studies," *Polymer* 43 (2002) 2385-2400.
370. Cornelius C, Hibshman C, Marand E, "Hybrid organic-inorganic membranes," *Sep. Purif. Technol.* 25 (2001) 181-193.
371. Chujo Y, Tamaki R, "New preparation methods for organic-inorganic polymer hybrids," *MRS Bull.* 26 (2001) 389-392.
372. Ruckenstein E, Yin WS, "SiO<sub>2</sub>-poly(amidoamine) dendrimer inorganic/organic hybrids," *J. Polym. Sci. A Polym. Chem.* 38 (2000) 1443-1449.
373. Joly C, Smaïhi M, Porcar L, et al., "Polyimide-silica composite materials: How does silica influence their microstructure and gas permeation properties?," *Chem. Mater.* 11 (1999) 2331-2338.
374. Joly C, Goizet S, Schrotter JC, et al., "Sol-gel polyimide-silica composite membrane: gas transport properties," *J. Mem. Sci.* 130 (1997) 63-74.
375. Tamaki R, Chujo Y, "Synthesis of poly(vinyl alcohol) silica gel polymer hybrids by in-situ hydrolysis method," *Appl. Organomet. Chem.* 12 (1998) 755-762.
376. Tamaki R, Naka K, Chujo Y, "Synthesis of poly(N,N-dimethylacrylamide) silica gel polymer hybrids by in situ polymerization method," *Polym. J.* 30 (1998) 60-65.
377. Smaïhi M, Schrotter JC, Lesimple C, et al., "Gas separation properties of hybrid imide-siloxane copolymers with various silica contents," *J. Mem. Sci.* 161 (1999) 157-170.
378. Smaïhi M, Jermoumi T, Marignan J, et al., "Organic-inorganic gas separation membranes: Preparation and characterization," *J. Mem. Sci.* 116 (1996) 211-220.
379. Nunes SP, Peinemann KV, Ohlrogge K, et al., "Membranes of poly(ether imide) and nanodispersed silica," *J. Mem. Sci.* 157 (1999) 219-226.



380. Matejka L, Plestil J, Dusek K, "Structure evolution in epoxy-silica hybrids: sol-gel process," *J. Non-Cryst. Sol.* 226 (1998) 114-121.
381. McCarthy DW, Mark JE, Schaefer DW, "Synthesis, structure, and properties of hybrid organic-inorganic composites based on polysiloxanes. I. Poly(dimethylsiloxane) elastomers containing silica," *J. Polym. Sci. B Polym. Phys.* 36 (1998) 1167-1189.
382. Naito M, Nakahira K, Fukuda Y, et al., "Process conditions on the preparation of supported microporous SiO<sub>2</sub> membranes by sol-gel modification techniques," *J. Mem. Sci.* 129 (1997) 263-269.
383. Moaddeb M, Koros WJ, "Gas transport properties of thin polymeric membranes in the presence of silicon dioxide particles," *J. Mem. Sci.* 125 (1997) 143-163.
384. Moaddeb M, Koros WJ, "Effects of colloidal silica incorporation on oxygen nitrogen separation properties of ceramic-supported 6FDA-IPDA thin films," *J. Mem. Sci.* 111 (1996) 283-290.
385. Kusakabe K, Ichiki K, Hayashi J, et al., "Preparation and characterization of silica-polyimide composite membranes coated on porous tubes for CO<sub>2</sub> separation," *J. Mem. Sci.* 115 (1996) 65-75.
386. Raman NK, Brinker CJ, "Organic template approach to molecular-sieving silica membranes," *J. Mem. Sci.* 105 (1995) 273-279.
387. Huang HH, Orlor B, Wilkes GL, "Structure property behavior of new hybrid materials incorporating oligomeric species into sol-gel glasses. 3. Effect of acid content, tetraethoxysilane content, and molecular-weight of poly(dimethylsiloxane)," *Macromol.* 20 (1987) 1322-1330.
388. Hu Q, Marand E, Dhingra S, et al., "Poly(amide-imide)/TiO<sub>2</sub> nano-composite gas separation membranes: Fabrication and characterization," *J. Mem. Sci.* 135 (1997) 65-79.
389. Moore TT, Mahajan R, Vu DQ, et al., "Hybrid membrane materials comprising organic polymers with rigid dispersed phases," *AIChE J.* 50 (2004) 311-321.
390. Vu D, Koros WJ, Miller SJ, "Effect of condensable impurity in CO<sub>2</sub>/CH<sub>4</sub> gas feeds on performance of mixed matrix membranes using carbon molecular sieves," *J. Mem. Sci.* 221 (2003) 233-239.
391. Vu DQ, Koros WJ, Miller SJ, "Mixed matrix membranes using carbon molecular sieves - I. Preparation and experimental results," *J. Mem. Sci.* 211 (2003) 311-334.
392. Vu DQ, Koros WJ, Miller SJ, "Mixed matrix membranes using carbon molecular sieves - II. Modeling permeation behavior," *J. Mem. Sci.* 211 (2003) 335-348.
393. Anson M, Marchese J, Garis E, et al., "ABS copolymer-activated carbon mixed matrix membranes for CO<sub>2</sub>/CH<sub>4</sub> separation," *J. Mem. Sci.* 243 (2004) 19-28.
394. Mahajan R, Burns R, Schaeffer M, et al., "Challenges in forming successful mixed matrix membranes with rigid polymeric materials," *J. Appl. Polym. Sci.* 86 (2002) 881-890.
395. Mahajan R, Koros WJ, "Factors controlling successful formation of mixed-matrix gas separation materials," *Ind. Eng. Chem. Res.* 39 (2000) 2692-2696.
396. Kulprathipanja S, "Mixed matrix membrane development," *Ann. NY Acad. Sci.* 984 (2003) 361-369.
397. Kulprathipanja S, Neuzil RW, Li NN, "Separation of gases by means of mixed matrix membranes," *USP* 5,127,925 (1992).
398. Kulprathipanja S, Neuzil RW, Li NN, "Gas separation by means of mixed matrix membranes," *USP* 4,740,219 (1988).
399. Vankelecom IFJ, VandenBroeck S, Merckx E, et al., "Silylation to improve incorporation

- of zeolites in polyimide films," J. Phys. Chem. 100 (1996) 3753-3758.
400. Vankelecom IFJ, Merckx E, Luts M, et al., "Incorporation of zeolites in polyimide membranes," J. Phys. Chem. 99 (1995) 13187-13192.
  401. Duval JM, Kemperman AJB, Folkers B, et al., "Preparation of zeolite filled glassy polymer membranes," J. Appl. Polym. Sci. 54 (1994) 409-418.
  402. Duval JM, Folkers B, Mulder MHV, et al., "Adsorbent filled membranes for gas separation. Part I. Improvement of the gas separation properties of polymeric membranes by incorporation of microporous adsorbents," J. Mem. Sci. 80 (1993) 189-198.
  403. Suer MG, Bac N, Yilmaz L, "Gas permeation characteristics of polymer-zeolite mixed matrix membranes," J. Mem. Sci. 91 (1994) 77-86.
  404. Jia MD, Peinemann KV, Behling RD, "Ceramic zeolite composite membranes - preparation, characterization and gas permeation," J. Mem. Sci. 82 (1994) 15-26.
  405. Jia MD, Peinemann KV, Behling RD, "Preparation and characterization of thin-film zeolite PDMS composite membranes," J. Mem. Sci. 73 (1992) 119-128.
  406. Jia MD, Peinemann KV, Behling RD, "Molecular-sieving effect of the zeolite-filled silicone-rubber membranes in gas permeation," J. Mem. Sci. 57 (1991) 289-296.
  407. Paul DR, Kemp, DR, "The diffusion time lag in polymer membranes containing adsorptive fillers," J. Polym Sci. 41 (1973) 79-93.
  408. Berry MB, Libby BE, Rose K, et al., "Incorporation of zeolites into composite matrices," Micropor. Mesopor. Mater. 39 (2000) 205-217.
  409. Gur TM, "Permselectivity of zeolite filled polysulfone gas separation membranes," J. Mem. Sci. 93 (1994) 283-289.
  410. Landry CJT, Coltrain BK, Teegarden DM, et al., "Use of organic copolymers as compatibilizers for organic-inorganic composites," Macromol. 29 (1996) 4712-4721.
  411. Zimmerman CM, Singh A, Koros WJ, "Tailoring mixed matrix composite membranes for gas separations," J. Mem. Sci. 137 (1997) 145-154.
  412. Rong, MZ; Zhang, MQ; Zheng, YX; et al., "Structure-property relationships of irradiation grafted nano-inorganic particle filled polypropylene composites," Polymer 42 (2001) 167-183.
  413. Nunes SP, Schultz J, Peinemann KV, "Silicone membranes with silica nanoparticles," J. Mater. Sci. Lett. 15 (1996) 1139-1141.
  414. Zhang Q, Cussler EL, "Microporous hollow fibers for gas-absorption. Part I. Mass-transfer in the liquid," J. Mem Sci. 23 (1985) 321-332.
  415. Zhang Q, Cussler EL, "Microporous hollow fibers for gas-absorption. Part II. Mass-transfer across the membrane," J. Mem Sci. 23 (1985) 333-345.
  416. Dindore VY, Brilman DWF, Versteeg GF, "Modelling of cross-flow membrane contactors: physical mass transfer processes," J. Mem. Sci., 251 (2005) 209-222.
  417. Dindore VY, Brilman DWF, Versteeg GF, "Modelling of cross-flow membrane contactors: physical mass transfer processes," J. Mem. Sci., 251 (2005) 275-289.
  418. Hoff KA, Juliussen O, Falk-Pedersen O, et al., "Modeling and experimental study of carbon dioxide absorption in aqueous alkanolamine solutions using a membrane contactor," Ind. Eng. Chem. Res. 43 (2004) 4908-4921.
  419. Klaassen R, Jansen AE, "The membrane contactor: Environmental applications and possibilities," Environ. Prog. 20 (2001) 37-43.
  420. Klaassen R, Feron PHM, Jansen AE, "Membrane contactors in industrial applications," Chem. Eng. Res. Des. 83 (2005) 234-246.

421. Dindore VY, Brilman DWF, Versteeg GE, "Hollow fiber membrane contactor as a gas-liquid model contactor," *Chem. Eng. Sci.* 60 (2005) 467-479.
422. Dindore VY, Brilman DWF, Feron PHM, et al., "CO<sub>2</sub> absorption at elevated pressures using a hollow fiber membrane contactor," *J. Mem. Sci.* 235 (2004) 99-109.
423. Kumar PS, Hogendoorn JA, Feron PHM, et al., "Approximate solution to predict the enhancement factor for the reactive absorption of a gas in a liquid flowing through a microporous membrane hollow fiber," *J. Mem. Sci.* 213 (2003) 231-245.
424. Kumar PS, Hogendoorn JA, Feron PHM, et al., "New absorption liquids for the removal of CO<sub>2</sub> from dilute gas streams using membrane contactors," *Chem. Eng. Sci.* 57 (2002) 1639-1651.
425. Drioli E, Curcio E, Di Profio G, "State of the art and recent progresses in membrane contactors," *Chem. Eng. Res. Des.* 83 (2005) 223-233.
426. Bocquet S, Torres A, Sanchez J, et al., "Modeling the mass transfer in solvent-extraction processes with hollow-fiber membranes," *AIChE J.* 51 (2005) 1067-1079.
427. Bothun GD, Knutson BL, Strobel HJ, et al., "Mass transfer in hollow fiber membrane contactor extraction using compressed solvents," *J. Mem. Sci.*, 227 (2003) 183-196.
428. Bothun GD, Knutson BL, Strobel HJ, et al., "Compressed solvents for the extraction of fermentation products within a hollow fiber membrane contactor," *J. Supercrit. Fluids* 25 (2003) 119-134.
429. Dindore VY, Versteeg GF, "Gas-liquid mass transfer in a cross-flow hollow fiber module: Analytical model and experimental validation," *Inter. J. Heat Mass Trans.* 48 (2005) 3352-3362.
430. Feron PHM, Jansen AE, "CO<sub>2</sub> separation with polyolefin membrane contactors and dedicated absorption liquids: performances and prospects," *Sep. Purif. Technol.* 27 (2002) 231-242.
431. Gabelman A, Hwang ST, Krantz WB, "Dense gas extraction using a hollow fiber membrane contactor: experimental results versus model predictions," *J. Mem. Sci.* 257 (2005) 11-36.
432. Kang MS, Moon SH, Park YI, Lee KH, "Development of carbon dioxide separation process using continuous hollow-fiber membrane contactor and water-splitting electrodialysis," *Separation Science and Technology* 37 (2002) 1789-1806.
433. Korikov AP, Sirkar KK, "Membrane gas permeance in gas-liquid membrane contactor systems for solutions containing a highly reactive absorbent," *J. Mem. Sci.* 246 (2005) 27-37.
434. Kosaraju P, Kovvali AS, Korikov A, et al., "Hollow fiber membrane contactor based CO<sub>2</sub> absorption-stripping using novel solvents and membranes," *Ind. Eng. Chem. Res.* 44 (2005) 1250-1258.
435. Lu JG, Wang LJ, Sun XY, et al., "Absorption of CO<sub>2</sub> into aqueous solutions of methyldiethanolamine and activated methyldiethanolamine from a gas mixture in a hollow fiber contactor," *Ind. Eng. Chem. Res.* 44 (2005) 9230-9238.
436. Mavroudi M, Kaldis SP, Sakellaropoulos GP, "Reduction of CO<sub>2</sub> emissions by a membrane contacting process," *Fuel*, 82 (2003) 2153-2159.
437. Nishikawa N, Ishibashi M, Ohta H, Akutsu N, Matsumoto H, Kanata T, Kitamura H, "CO<sub>2</sub> removal by hollow-fiber gas-liquid contactor," *Energy Conversion and Management*, 36 (1995) 415-418.
438. Wang R, Zhang HY, Feron PHM, et al., "Influence of membrane wetting on CO<sub>2</sub> capture

- in microporous hollow fiber membrane contactors,” *Sep. Purif. Tech.* 46 (2005) 33-40.
439. Wang R, Li DF, Liang DT, “Modeling of CO<sub>2</sub> capture by three typical amine solutions in hollow fiber membrane contactors,” *Chem. Eng. Process.* 43 (2004) 849-856.
  440. Wang R, Li DF, Zhou C, et al., “Impact of DEA solutions with and without CO<sub>2</sub> loading on porous polypropylene membranes intended for use as contactors,” *J. Mem. Sci.*, 229 (2004) 147-157.
  441. Yeon SH, Lee KS, Sea B, et al., “Application of pilot-scale membrane contactor hybrid system for removal of carbon dioxide from flue gas,” *J. Mem. Sci.* 257 (2005) 156-160.
  442. Yeon SH, Sea B, Park YI, et al., “Absorption of carbon dioxide characterized by using the absorbent composed of piperazine and triethanolamine,” *Sep. Sci. Technol.* 39 (2004) 3281-3300.
  443. Yeon SH, Sea B, Park YI, et al., “Determination of mass transfer rates in PVDF and PTFE hollow fiber membranes for CO<sub>2</sub> absorption,” *Sep. Sci. Technol.* 38 (2003) 271-293.
  444. Zheng JM, Xu YY, Xu ZK, “Shell side mass transfer characteristics in a parallel flow hollow fiber membrane module,” *Sep. Sci. Technol.* 38 (2003) 1247-1267.
  445. Li JL Chen BH, “Review of CO<sub>2</sub> absorption using chemical solvents in hollow fiber membrane contactors,” *Sep. Purif. Tech.* 41 (2005) 109-122.
  446. EPA, “AP 42, Compilation of air pollutant emission factors, Vol. 1: Stationary point and area sources,” 5<sup>th</sup> Ed., <http://www.epa.gov/ttn/chief/ap42/>.
  447. Nolan PS, “Flue gas desulfurization technologies for coal-fired power plants,” presented at the Coal Tech 2000 International Conference, Jakarta, Indonesia (2000).
  448. Alpert SB, “Clean coal technology and advanced coal-based power plants,” *Ann. Rev. Energy Environ.* 16 (1991) 1-23.
  449. DOE, “Inventory of Electric Utility Power Plants in the United States 2000,” DOE/EIA-0095, 2002.
  450. Merichem, “Cleaning up the gasification gas,” <http://www.gtp-merichem.com/news/releases/syngas.php>.
  451. NETL, “Destec Gasifier IGCC Base Cases,” PED-IGCC-98-003, <http://www.netl.doe.gov/technologies/coalpower/gasification/pubs/system-studies.html>, (1998).
  452. Bohm MC, “Capture-ready power plants - Options, technologies and economics,” Mark C, MS Thesis, Massachusetts Institute of Technology (2006) ([http://sequestration.mit.edu/pdf/Mark\\_Bohm\\_Thesis.pdf](http://sequestration.mit.edu/pdf/Mark_Bohm_Thesis.pdf)).
  453. Platts M, “The coke oven by-product plant,” American Iron and Steel Institute, [http://www.energymanagertraining.com/iron\\_steel/coke\\_oven\\_steel.htm](http://www.energymanagertraining.com/iron_steel/coke_oven_steel.htm).
  454. Freitag DW, Richerson DW, “Opportunities for advanced ceramics to meet the needs of the industries of the future,” DOE report DOE/ORO 2076 (1998).
  455. Division of Pollution Prevention and Environmental Assistance, “Primary Metals,” <http://www.p2pays.org/ref/01/text/00778/chapter1.htm>.
  456. Metallurgical Society, “Virtual tour,” <http://www.metsoc.org/virtualtour/default.asp>.
  457. Green Island Cement Holding limited site, “Cement Process,” [http://www.gich.com.hk/Facilities/f\\_main.htm](http://www.gich.com.hk/Facilities/f_main.htm).
  458. Worrell E, Price L, Martin N, Hendriks C, Meida LO, “Carbon dioxide emissions from the global cement industry,” *Annu. Rev. Energy Environ.* 26 (2001) 303-329.
  459. Pletcher D, Walsh FC, “Industrial Electrochemistry,” 2<sup>nd</sup> Ed., Chapman and Hall, London,

- (1995).
460. Bruno MJ, "Aluminum Carbothermic Technology," DOE report Cooperative Agreement Number DE-FC36-00ID13900, <http://www.osti.gov/bridge/servlets/purl/838679-h1h8sh/838679.PDF>.
  461. EPA, "Associated waste report, dehydration and sweetening wastes," (2000).
  462. Ortloff engineers limited, "Sulfur Recovery Process Information," <http://www.ortloff.com/sulfur/sulfinfo.htm>.
  463. EPA, Landfill Methane Outreach Program (LMOP), <http://www.epa.gov/landfill/overview.htm>.
  464. EPA, Coalbed Methane Outreach Program, <http://www.epa.gov/cmop>.
  465. American Coalition for Ethanol, "How is Ethanol Made?," <http://www.ethanol.org/howethanol.html>.
  466. Kintisch E, "Climate change: Along the road from Kyoto," *Science* 311 (2006) 1702-1703.
  467. Webster P, "Canada on Kyoto: What a gas," *Science* 312 (2006) 985.
  468. CCS Tech Lessons Learned (2006).
  469. Tondu Corporation, <http://www.tonducorp.com/IGCC.htm>.
  470. Sekar RC, Parsons JE, Herzog HJ, Jacoby HD, "Future carbon regulations and current investments in alternative coal-fired power plant designs," MIT Report no. 129 (2005).
  471. US DOE NETL, "Pinon Pine IGCC power project: A DOE assessment," DOE/NETL-2003/1183 (2002).
  472. Berzin I, "Synthetic and biologically-derived products produced using biomass produced by photobioreactors configured for mitigation of pollutants in flue gases," USP App. 20050239182 (2005).
  473. Berzin I, "Hydrogen production with photosynthetic organisms and from biomass derived therefrom," USP App. 20050064577 (2005).
  474. DOE International Energy Annual 2004, <http://www.eia.doe.gov/iea/carbon.html>.
  475. UDS DOE, "Emissions of Greenhouse Gases in the U.S. 2005," DOE/EIA-0573 (2005).
  476. Schipper M, "Energy-Related Carbon Dioxide Emissions in U.S. Manufacturing," Special topic of DOE/EIA-0573 (2005).
  477. EPA Report: Inventory of U.S. Greenhouse Gas Emissions and Sinks: 1990 – 2004.
  478. "Hydrocarbon Processing: Gas Processes 2004 and Petrochemical Processes 2003," Gulf Publishing Co.
  479. "Fuel Science and Technology Handbook," 2<sup>nd</sup> edition. Speight JG Ed., Marcel Dekker, New York, Chapters 35 and 36 (1998).
  480. Kohl A, Riesenfeld F, "Gas Purification," 4th edition, Gulf Publishing Company, Houston (1985).
  481. Rameshni P, "State of the art in gas treating," Parsons Energy & Chemical Group, Inc. San Francisco (2000).
  482. Suzuki T, Sakoda A, Suzuki M, Izumi J, "Recovery of carbon dioxide from stack gas by piston-driven ultra-rapid PSA," *J. Chem. Eng. Japan* 30 (1997) 1026-1033.
  483. Gomes VG, Yee KWK, "Pressure swing adsorption for carbon dioxide sequestration from exhaust gases," *Separation and Purification Technology* 28 (2002) 161-171.
  484. Ko D, Siriwardane R, Biegler LT, "Optimization of a pressure swing adsorption process using zeolite 13X for CO<sub>2</sub> sequestration," *Ind. Eng. Chem. Res.* 42 (2003) 339-348.
  485. Ko D, Siriwardane R, Biegler LT, "Optimization of pressure swing adsorption and

- fractionated vacuum pressure swing adsorption processes for CO<sub>2</sub> capture,” *Ind. Eng. Chem. Res.* 44 (2005) 8084-8094.
486. Na B-K, Koo K-K, Eum H-M, Lee H, Song H-K, “CO<sub>2</sub> recovery from flue gas by PSA process using activated carbon,” *Korean J. Chem. Eng.* 18 (2001) 220-227.
  487. Na B-K, Lee H, Koo K-K, Song HK, “Effect of rinse and recycle methods on the pressure swing adsorption process to recover CO<sub>2</sub> from power plant flue gas using activated carbon,” *Ind. Eng. Chem. Res.* 41 (2002) 5498-5503.
  488. Choi W-K, Kwon T-I, Yeo Y-K, Lee H, Song H-K, Na B-K, “Optimal Operation of the Pressure Swing Adsorption (PSA) Process for CO<sub>2</sub> Recovery,” *Korean J. Chem. Eng.* 20 (2003) 617-623.
  489. Chue KT, Kim JN, Yoo YJ, Cho SH, Yang, RT, “Comparison of activated carbon and zeolite 13X for CO<sub>2</sub> adsorption recovery from flue gas by pressure swing adsorption,” *Ind. Eng. Chem. Res.* 34 (1995) 591-598.
  490. Kikkinides ES, Yang RT, Cho SH, “Concentration and recovery of CO<sub>2</sub> from flue gas by pressure swing adsorption,” *Ind. Eng. Chem. Res.* 32 (1993) 2714-2720.
  491. Chou CT, Chen CY, “Carbon dioxide recovery by vacuum swing adsorption,” *Separ. Purif. Technol.* 39 (2004) 51-65.
  492. Rao MB, Sircar S, Golden TC, “Gas separation by adsorbent membranes,” *European Patent*, EP0428052 (2001).
  493. Syrtsova DA, Kharitonov AP, Teplyakov VV, et al., “Improving gas separation properties of polymeric membranes based on glassy polymers by gas phase fluorination,” *Desal.* 163 (2004) 273-279.
  494. Glugla PG, Rickle GK, Smith BL, Bales SE, “Interfacially polymerized polyester films for gas separation membranes and preparation thereof,” *USP* 5,650,479 (1997).
  495. Marek M, Brynda E, Pientka Z, et al., “Gas separation properties of ultra-thin films based on fully cyclized polyimides,” *Macrom. Rapid Comm.* 19 (1998) 53-57.
  496. Pinnau I, Toy LG, “Gas and vapor transport properties of amorphous perfluorinated copolymer membranes based on 2,2-bis(trifluoromethyl)-4,5-difluoro-1,3-dioxole/tetrafluoroethylene,” *J. Mem. Sci.* 109 (1996) 125-133.
  497. Yoshioka T, Nakanishi E, Tsuru T, et al., “Experimental studies of gas permeation through microporous silica membranes,” *AIChE J.* 47 (2001) 2052-2063.

Table 1. 1990 and 2004 Worldwide and U.S. CO<sub>2</sub> emissions (MMt).

|                                                        | 1990      | 2004      |
|--------------------------------------------------------|-----------|-----------|
| <b>Worldwide Emissions [474]</b>                       | 21,426.12 | 27,043.57 |
| <b>U.S. CO<sub>2</sub> Emissions [474]</b>             | 5,013.45  | 5,912.20  |
| <b>U.S. CO<sub>2</sub> Emissions [475]<sup>a</sup></b> | 4,984.80  | 5,923.20  |
| 1. Residential                                         | 953.00    | 1,213.90  |
| 2. Commercial                                          | 780.70    | 1,034.10  |
| 3. Transportation                                      | 1,566.80  | 1,939.20  |
| 4. Industrial                                          | 1,683.60  | 1,736.00  |
| 5. Electric <sup>b</sup>                               | 1,803.10  | 2,309.40  |
| 6. Non-fuel use of fossil fuels <sup>c</sup>           | 98.10     | 111.70    |
| 7. Other sources <sup>d</sup>                          | 88.30     | 105.70    |

<sup>a</sup> Sum of rows 1 to 4, and includes total emissions from energy and non-energy related sources.

<sup>b</sup> Total emissions from electricity needed to power activities in rows 1 to 4.

<sup>c</sup> Emissions in row 6 included in emissions in rows 1 to 4.

<sup>d</sup> Emissions in row 7 not included in emissions in rows 1 to 4, and includes natural gas flaring, CO<sub>2</sub> in natural gas, cement production, other industries, and waste combustion.

Table 2. Summary of 2002 U.S. CO<sub>2</sub> emissions (MMt).

|                                                  | Total                                          | Electricity | Natural gas | Petroleum | Coal     | Other  |                            |                     |        |                    |
|--------------------------------------------------|------------------------------------------------|-------------|-------------|-----------|----------|--------|----------------------------|---------------------|--------|--------------------|
| CO <sub>2</sub> Emissions [475,476] <sup>a</sup> | 5,752.20                                       |             |             |           |          |        |                            |                     |        |                    |
| 1. Residential                                   | 1,186.40                                       | 821.40      | 263.70      | 100.20    | 1.10     | 0.00   |                            |                     |        |                    |
| 2. Comercial                                     | 1,009.40                                       | 782.30      | 170.20      | 48.70     | 8.30     | 0.00   |                            |                     |        |                    |
| 3. Transportation                                | 1,871.70                                       | 3.60        | 37.10       | 1,831.00  | 0.00     | 0.00   |                            |                     |        |                    |
| 4. Industrial                                    | 1,684.70                                       | 642.70      | 450.70      | 400.40    | 190.90   | 0.00   |                            |                     |        |                    |
| 5. Electric <sup>b</sup>                         | 2,250.00                                       | -----       | 305.90      | 77.40     | 1,853.70 | 12.60  |                            |                     |        |                    |
|                                                  |                                                |             |             |           |          |        |                            |                     |        |                    |
| Manufacturing Industry [476] <sup>c</sup>        | Energy Related Fossil Fuels [476] <sup>c</sup> |             |             |           |          |        | Non-Energy Related Sources |                     |        |                    |
|                                                  |                                                |             |             |           |          |        | Total                      |                     | Non-   |                    |
|                                                  | Total                                          | Electricity | Natural Gas | Petroleum | Coal     | Other  | [477] <sup>d</sup>         | Fossil <sup>e</sup> | Fossil |                    |
|                                                  |                                                |             |             |           |          |        |                            |                     | [475]  |                    |
|                                                  | 6. Total manufacturing                         | 1,401.20    | 540.70      | 325.90    | 257.60   | 202.80 | 74.20                      | 177.10 <sup>f</sup> | 89.80  | 87.30 <sup>g</sup> |
|                                                  | 7. Iron and steel industry                     | 126.00      | 35.00       | 22.00     | 1.10     | 66.70  | 1.20                       | 51.30               | 49.90  | 1.40               |
|                                                  | 8. Cement manufacture                          | 39.00       | 8.20        | 1.10      | 6.40     | 23.00  | 0.30                       | 43.00               | 0.00   | 43.00              |
|                                                  | 9. Ammonia                                     | -----       | -----       | -----     | -----    | -----  | -----                      | 18.50               | 18.50  | 0.00               |
|                                                  | 10. Natural gas                                | -----       | -----       | -----     | -----    | -----  | -----                      | 17.90               | 0.00   | 17.90              |
|                                                  | 11. Lime                                       | 10.30       | 1.00        | 0.40      | 2.80     | 6.20   | 0.00                       | 14.10               | 0.00   | 14.10              |
|                                                  | 12. Aluminum production                        | 48.00       | 36.70       | 7.10      | 0.10     | 0.00   | 4.00                       | 4.60                | 0.60   | 4.00               |
|                                                  | 13. Other manufacturing                        | 1,177.90    | 459.80      | 295.30    | 247.20   | 106.90 | 68.70                      | 27.70               | 20.80  | 6.90               |
|                                                  | Other industries and sources [475]             |             |             |           |          |        |                            |                     |        |                    |
|                                                  | 14. Municipal combustion                       | 12.60       | 0.00        | 0.00      | 0.00     | 0.00   | 12.60                      | 6.20                | 0.00   | 6.20               |
|                                                  | 15. Natural gas flaring                        | 0.00        | 0.00        | 0.00      | 0.00     | 0.00   | 0.00                       | 6.00                | 6.00   | 0.00               |
| CO <sub>2</sub> Consumption [475]                | 11.31                                          |             |             |           |          |        |                            |                     |        |                    |

<sup>a</sup> Sum of rows 1 to 4, and includes total emissions from energy and non-energy related sources.

<sup>b</sup> Total emissions from electricity needed to power activities in rows 1 to 4.

<sup>c</sup> Ammonia and natural gas production not mentioned in this report, but emissions expected to be negligible.

<sup>d</sup> Data for municipal combustion and natural gas flaring and production obtained from [475].

<sup>e</sup> Difference between total non-energy related sources and non-fossil sources.

<sup>f</sup> This value includes all values reported in Tables 2 and 3 of [477], including natural gas production reported in row 10 of this table, but excluding those for combustion and natural gas flaring.

<sup>g</sup> This value includes natural gas production reported in row 10 of this table.



Table 3. Average U.S. CO<sub>2</sub> emissions per plant within several industries (MMt).<sup>a</sup>

| <b>Industry</b>           | <b>Year</b> | <b>Number of<br/>Plants</b> | <b>Emissions</b> | <b>Average Plant<br/>Emissions</b> |
|---------------------------|-------------|-----------------------------|------------------|------------------------------------|
| Fossil fuel power plants: |             |                             |                  |                                    |
| Coal                      | 1998        | 1198                        | 1801.1           | 1.50                               |
| Gas                       | 1998        | 3321                        | 249.1            | 0.08                               |
| Petroleum                 | 1998        | 2148                        | 104.1            | 0.05                               |
| Iron and steel industry   | 2004        | 95                          | 51.3             | 0.54                               |
| Cement manufacture        | 2004        | 116                         | 45.6             | 0.39                               |
| Ammonia                   | 2004        | 32                          | 16.9             | 0.53                               |
| Natural gas (absorption)  | 1991        | 460                         | 16.2             | 0.04                               |
| Aluminum production       | 2006        | 400                         | 4.3              | 0.01                               |
| Ethanol industry          | 2006        | 101                         | 3.5              | 0.03                               |

<sup>a</sup> Except for fossil fuel plants, emissions are non-energy related.

Table 4. Number of patents (P) and peer review manuscripts (M) per researcher or research group on CO<sub>2</sub> related separation processes since 1995 and 2002 (in parentheses).

| Main Investigator                                     | Company or Institution                                                  | Membrane |        | Membrane Process |      | Adsorption |      | Absorption |      | Other |   |
|-------------------------------------------------------|-------------------------------------------------------------------------|----------|--------|------------------|------|------------|------|------------|------|-------|---|
|                                                       |                                                                         | P        | M      | P                | M    | P          | M    | P          | M    | P     | M |
| Katsuki Kusakabe, Shigeharu Morooka                   | Kyushu Sangyo University, Japan                                         | 0(0)     | 35(9)  |                  |      |            |      |            |      |       |   |
| Tai S. Chung and Rong Wang                            | National U. of Singapore, Nanyang Technological U., Singapore           | 1(1)     | 37(29) |                  |      |            |      |            |      |       |   |
| William J. Koros                                      | Georgia Institute of Technology, USA                                    | 8(8)     | 42(22) | 2(1)             | 0(0) |            |      |            |      |       |   |
| Ken-ichi Okamoto, Hidetoshi Kita                      | Yamaguchi University, Japan                                             | 1(0)     | 31(25) |                  |      |            |      |            |      |       |   |
| Richard D. Noble and John L. Falconer                 | University of Colorado, USA                                             | 3(0)     | 29(13) |                  |      |            |      |            |      |       |   |
| Kenji Haraya                                          | National Institute of Advanced Industrial Science and Technology, Japan | 1(0)     | 15(6)  |                  |      |            |      |            |      |       |   |
| Hiroyoshi Kawakami                                    | Tokyo Metropolitan University, Japan                                    | 1(0)     | 26(6)  |                  |      |            |      |            |      |       |   |
| Akira Miyamoto, Momoji Kubo                           | Tohoku University, Japan                                                | 0(0)     | 8(1)   |                  |      |            |      |            |      |       |   |
| Matthias Wessling                                     | U. of Twente, the Netherlands                                           | 1(1)     | 23(16) |                  |      |            |      |            |      |       |   |
| Richard W. Baker, Ingo Pinnau                         | Membrane Tech. & Research, Inc., USA                                    | 7(4)     | 14(4)  | 12(5)            | 3(1) |            |      |            |      |       |   |
| Stephen J. Miller, Curtis L. Munson, De Q. Vu         | Chevron USA Inc., USA                                                   | 9(9)     | 6(6)   | 2(2)             | 1(1) | 2(2)       | 3(3) | 3(3)       | 0(0) |       |   |
| Benny D. Freeman                                      | U. of Texas, USA                                                        | 0(0)     | 43(11) |                  |      |            |      |            |      |       |   |
| William D. Dolan                                      | Engelhard Corporation, USA                                              | 5(5)     | 2(2)   |                  |      |            |      |            |      |       |   |
| Raymond Clarke                                        | Landec Corporation, USA                                                 | 4(2)     | 2(1)   |                  |      |            |      |            |      |       |   |
| John W. Simmons                                       | L'air Liquide, France                                                   | 5(5)     | 0(0)   |                  |      |            |      |            |      |       |   |
| Santi Kulprathipanja                                  | UOP LLC, USA                                                            | 2(2)     | 1(1)   |                  |      |            |      |            |      |       |   |
| David J. Hasse, Sudhir S. Kulkarni                    | L'air Liquide, France                                                   | 4(4)     | 2(0)   |                  |      |            |      |            |      |       |   |
| Harry W. Deckman, Donald J. Victory, Eugene R. Thomas | ExxonMobil, USA                                                         | 3(3)     | 0(0)   |                  |      | 1(1)       | 0(0) |            |      |       |   |
| Benjamin Bikson, Joice K. Nelson, Yong Ding           | Praxair Technology, Inc., USA                                           | 6(2)     | 0(0)   |                  |      |            |      |            |      |       |   |
| Gilles P. Robertson, Michael D. Guiver                | Institute for Chemical Process and Environmental Technology, Canada     | 1(1)     | 10(8)  |                  |      |            |      |            |      |       |   |
| Hisao Hachisuka, Tomomi Ohara, Ken-Ichi Ikeda         | Nitto Denko Corporation, Japan                                          | 0(0)     | 5(0)   |                  |      |            |      |            |      |       |   |
| Nikunj P. Patel, Richard J. Spontak                   | North Carolina State University, USA                                    | 0(0)     | 8(6)   |                  |      |            |      |            |      |       |   |
| Liang Hu                                              | Hampton University, USA                                                 | 1(1)     | 6(4)   |                  |      |            |      |            |      |       |   |
| Eva Marand                                            | Virginia Polytechnic I. and State U., USA                               | 1(1)     | 9(6)   |                  |      |            |      |            |      |       |   |
| Yong S. Kang                                          | Korea I. of Science and Tech., South Korea                              | 3(2)     | 2(1)   |                  |      |            |      |            |      |       |   |
| Shigeo T. Oyama                                       | Virginia Polytechnic I. and State U., USA                               | 1(1)     | 12(7)  |                  |      |            |      |            |      |       |   |
| Anthony M. Sammels                                    | Eltron Research Inc. USA                                                | 2(1)     | 2(2)   | 1(0)             | 2(1) |            |      |            |      |       |   |

|                                                         |                                                          |      |        |      |      |      |        |      |      |      |                    |
|---------------------------------------------------------|----------------------------------------------------------|------|--------|------|------|------|--------|------|------|------|--------------------|
| S. Alexander Stern                                      | Gas Research Institute, USA                              | 0(0) | 8(0)   |      |      |      |        |      |      |      |                    |
| Shivaji Sircar, Jeffrey R. Hufton, Madhukar B. Rao      | Air Products and Chemicals, Inc., USA                    | 2(0) | 0(0)   | 3(0) | 2(0) | 7(0) | 5(0)   |      |      |      |                    |
| Charles L. Anderson                                     | L'Air Liquide, France                                    | 2(2) | 0(0)   |      |      |      |        |      |      |      |                    |
| W. H. Winston Ho                                        | ExxonMobil, USA                                          | 4(0) | 0(0)   |      |      |      |        | 9(0) | 5(0) |      |                    |
| Ravi Prasad, Frank Notaro                               | Praxair Technology, Inc., USA                            | 1(1) | 0(0)   |      |      | 4(1) | 0(0)   |      |      |      |                    |
| George P. Sakellaropoulos                               | Aristotle Univ Thessaloniki, Greece                      | 1(0) | 1(1)   | 0(0) | 3(2) | 0(0) | 8(2)   |      |      |      |                    |
| Kang Li, Wah K. Teo, Dongliang Wang                     | National University of Singapore, Singapore              | 1(0) | 10(1)  |      |      |      |        |      |      |      |                    |
| Takeshi Matsuura                                        | U. of Ottawa, Canada                                     | 1(0) | 19(6)  |      |      |      |        |      |      |      |                    |
| Gilbert M. Rios, Stephane Sarrade                       | I. Europeen des Membranes-UM2, France                    | 0(0) | 12(6)  |      |      |      |        |      |      |      |                    |
| Tsutomu Nakagawa                                        | Meiji University, Japan                                  | 0(0) | 21(3)  |      |      |      |        |      |      |      |                    |
| Theodore T.. Tsotsis                                    | U. of Southern California, USA                           | 0(0) | 13(5)  | 0(0) | 3(1) |      |        |      |      |      |                    |
| Antonio B. Fuertes, Teresa A. Centeno                   | Instituto Nacional del Carbon, Spain                     | 0(0) | 11(2)  |      |      |      |        |      |      |      |                    |
| A. F. Ismail                                            | U. Teknologi of Malaysia, Malaysia                       | 0(0) | 9(4)   |      |      |      |        |      |      |      |                    |
| Ho Bum Park, Young Moo Lee                              | Hanyang University, South Korea                          | 0(0) | 19(16) |      |      |      |        |      |      |      |                    |
| S. Ted Oyama                                            | Virginia Polytechnic Institute and State University, USA | 2(1) | 9(5)   |      |      |      |        |      |      |      |                    |
| Zhi Kang Xu                                             | Zhejiang University, China                               | 0(0) | 10(4)  |      |      |      |        |      |      | 0(0) | 2(2) <sup>a</sup>  |
| Enrico Drioli,                                          | U. of Calabria, Italy                                    | 0(0) | 20(12) |      |      |      |        |      |      |      |                    |
| Yong Soo Kang                                           | Korea I. of Science and Tech., South Korea               | 5(4) | 15(6)  |      |      |      |        |      |      |      |                    |
| Ricardo A. F. Machado                                   | U. Federal de Santa Catarina, Brazil                     | 0(0) | 6(5)   |      |      |      |        |      |      |      |                    |
| Henk Verweij                                            | U. of Twente, the Netherlands                            | 0(0) | 5(2)   |      |      |      |        |      |      |      |                    |
| Daniele Fiaschi                                         | U. degli Studi di Firenze, Italy                         | 0(0) | 5(4)   |      |      |      |        |      |      |      |                    |
| Jose Sanchez                                            | Institut Europeen des Membranes, France                  | 0(0) | 15(6)  |      |      |      |        |      |      | 0(0) | 1(1) <sup>a</sup>  |
| Kamalesh K. Sirkar                                      | New Jersey Institute of Technology, USA                  |      |        | 0(0) | 3(1) |      |        |      |      | 3(1) | 14(3) <sup>b</sup> |
| Tomonori Takahashi, Hitoshi Sakai, Toshihiro Tomita     | NGK insulators, Japan                                    |      |        | 4(0) | 2(2) |      |        |      |      |      |                    |
| Paul A. Daus, Charles R. Pauley                         | Messer Griesheim Industries, Inc., Germany               |      |        | 3(0) | 0(0) |      |        |      |      |      |                    |
| Sawas Vasileiadis                                       | Ivatech Corporation, USA                                 |      |        | 2(1) | 2(0) |      |        |      |      |      |                    |
| Ralph T. Yang                                           | U. of Michigan, USA                                      |      |        |      |      | 1(0) | 19(6)  |      |      |      |                    |
| Tsutomu Hirose, Monotobu Goto                           | Kumamoto University, Japan                               |      |        |      |      | 0(0) | 18(4)  |      |      |      |                    |
| Chang Ha Lee                                            | Yonsei University, South Korea                           |      |        |      |      | 0(0) | 19(8)  |      |      |      |                    |
| Angel Linares, Diego Cazorla                            | U. de Alicante, Spain                                    |      |        |      |      | 0(0) | 29(14) |      |      |      |                    |
| Isao Mochida                                            | Kyushu University, Japan                                 |      |        |      |      | 0(0) | 12(2)  |      |      |      |                    |
| Alirio E. Rodrigues                                     | U. de Oporto, Portugal                                   |      |        |      |      | 0(0) | 16(9)  |      |      |      |                    |
| James A. Ritter                                         | U. of South Carolina, USA                                |      |        |      |      | 0(0) | 5(1)   |      |      |      |                    |
| Jia Guo, Aik C. Lua                                     | Fudan University, China                                  |      |        |      |      | 0(0) | 12(6)  |      |      |      |                    |
| Juan M. D. Tascon, Amelia Martinez, Silvia Villar Rodil | Instituto Nacional del Carbon, Spain                     |      |        |      |      | 0(0) | 30(21) |      |      |      |                    |

|                                                                     |                                                                  |  |  |  |  |        |       |        |        |  |  |
|---------------------------------------------------------------------|------------------------------------------------------------------|--|--|--|--|--------|-------|--------|--------|--|--|
| Jose Ortega, Cristina Volzone                                       | Centro de Tecnologia de Recursos Minerales y Ceramica, Argentina |  |  |  |  | 0(0)   | 5(2)  |        |        |  |  |
| F. Handan Tezel                                                     | U. of Ottawa, Canada                                             |  |  |  |  | 0(0)   | 10(4) |        |        |  |  |
| Kenzi Suzuki                                                        | Agency of Industrial Sci.& Tech, Japan                           |  |  |  |  | 0(2)   | 7(0)  |        |        |  |  |
| Martin Bulow                                                        | The BOC Group, Inc., USA                                         |  |  |  |  | 3(12)  | 7(5)  |        |        |  |  |
| Ravi Kumar                                                          | The BOC Group, Inc., USA                                         |  |  |  |  | 4(13)  | 2(1)  |        |        |  |  |
| Akhilesh Kapoor                                                     | The BOC Group, Inc., USA                                         |  |  |  |  | 0(8)   | 0(0)  | 1(0)   | 0(0)   |  |  |
| Ravi Jain                                                           | The BOC Group, Inc., USA                                         |  |  |  |  | 0(7)   | 0(0)  |        |        |  |  |
| Mohamed S. A. Baksh                                                 | Praxair Technology, Inc., USA                                    |  |  |  |  | 2(4)   | 0(0)  |        |        |  |  |
| Roger D. Whitley, Robert L. Chiang                                  | Air Products and Chemicals, Inc., USA                            |  |  |  |  | 4(4)   | 0(0)  |        |        |  |  |
| Norberto O. Lemcoff, Divyanshu R. Acharya                           | The BOC Group, Inc., Canada                                      |  |  |  |  | 2(5)   | 3(1)  |        |        |  |  |
| Bowie G. Keefer                                                     | Questair Technologies, Inc., Canada                              |  |  |  |  | 6(9)   | 0(0)  |        |        |  |  |
| Amitabh Gupta, Shrikar Chakravarti                                  | Praxair Technology, Inc., USA                                    |  |  |  |  | 1(1)   | 0(0)  | 6(1)   | 0(0)   |  |  |
| Timothy C. Golden                                                   | Air Products and Chemicals, Inc, USA                             |  |  |  |  | 11(28) | 1(0)  |        |        |  |  |
| Hans H. Funkel, Dan Fraenkel                                        | Matheson Tri-Gas, Inc., USA                                      |  |  |  |  | 6(7)   | 1(1)  |        |        |  |  |
| Richard K. Lyon                                                     | General Electric Co., USA                                        |  |  |  |  | 5(5)   | 4(0)  |        |        |  |  |
| Omar M. Yaghi                                                       | U. of Michigan, USA                                              |  |  |  |  | 4(5)   | 15(8) |        |        |  |  |
| Robert S. Wegeng                                                    | Battelle Memorial Institute, USA                                 |  |  |  |  | 2(2)   | 0(0)  |        |        |  |  |
| Alan Mather                                                         | U. of Alberta, Canada                                            |  |  |  |  |        |       | 0(0)   | 18(2)  |  |  |
| Sang Wook Park                                                      | Korean Inst. of Chemical Engineers, Korea                        |  |  |  |  |        |       | 0(0)   | 16(16) |  |  |
| Gary T. Rochelle                                                    | U. of Texas, USA                                                 |  |  |  |  |        |       | 2(2)   | 15(10) |  |  |
| Syamalendu S. Bandyopadhyay                                         | Indian I. of Technology, India                                   |  |  |  |  |        |       | 0(0)   | 14(13) |  |  |
| Menghui Li                                                          | Chung Yuan Christian University, Taiwan                          |  |  |  |  |        |       | 0(0)   | 13(6)  |  |  |
| Helmuth Sigel                                                       | U of Basel, Switzerland                                          |  |  |  |  |        |       | 0(0)   | 13(6)  |  |  |
| Fumio Kiyono                                                        | Agency of Industrial Sci.& Tech, Japan                           |  |  |  |  |        |       | 1(0)   | 5(5)   |  |  |
| Arturo Trejo                                                        | Instituto Mexicano de Petroleo, Mexico                           |  |  |  |  |        |       | 1(0)   | 9(5)   |  |  |
| Mohamed K Aroua                                                     | U. of Malaya, Malaysia                                           |  |  |  |  |        |       | 0(0)   | 7(4)   |  |  |
| Gerd Maurer                                                         | U. of Kaiserslautern, Germany                                    |  |  |  |  |        |       | 0(0)   | 8(5)   |  |  |
| Orville C. Sandall                                                  | U. of California Santa Barbara, USA                              |  |  |  |  |        |       | 0(0)   | 8(0)   |  |  |
| Hallvard F. Svendsen                                                | Norwegian Inst. of Science and Tech., Norway                     |  |  |  |  |        |       | 0(0)   | 8(7)   |  |  |
| Takayuki Saito                                                      | Nat. Institute for Res. & Environ., Japan                        |  |  |  |  |        |       | 2(0)   | 8(1)   |  |  |
| Masaki Iijima, Kazuto Kobayashi, Kazuhiro Morita, Shigeaki Mitsuoka | Mitsubishi Heavy Industries, Japan                               |  |  |  |  |        |       | 19(10) | 8(1)   |  |  |
| Paul L. Wallace                                                     | Texaco Development Corp., USA                                    |  |  |  |  |        |       | 3(1)   | 0(0)   |  |  |
| Tofik K. Khanmamedov                                                | TKK Company, USA                                                 |  |  |  |  |        |       | 3(1)   | 1(1)   |  |  |
| Guido Sartori                                                       | ExxonMobil, USA                                                  |  |  |  |  |        |       | 23(0)  | 1(0)   |  |  |
| Bernt H. Torkildsen, Martin Sigmundstad, Harald Linga, Patrick Finn | Den Norske Stats Oljieselskap A.S., Norway                       |  |  |  |  |        |       | 7(0)   | 0(0)   |  |  |
| James E. Critchfield                                                | Hunstmann Petrochemical Corp., USA                               |  |  |  |  |        |       | 2(0)   | 1(0)   |  |  |

|                                                                  |                                                             |  |  |  |  |  |  |  |      |        |      |                       |
|------------------------------------------------------------------|-------------------------------------------------------------|--|--|--|--|--|--|--|------|--------|------|-----------------------|
| Jerry D. Blue                                                    | Alliance, USA                                               |  |  |  |  |  |  |  | 3(1) | 0(0)   |      |                       |
| Fabrice Lecomte                                                  | Institut Francais du Petrole, France                        |  |  |  |  |  |  |  | 3(3) | 3(2)   |      |                       |
| Gary Palmer                                                      | Alberta Limited, Canada                                     |  |  |  |  |  |  |  | 2(2) | 0(0)   |      |                       |
| John Mak                                                         | Fluor Corporation, USA                                      |  |  |  |  |  |  |  | 7(7) | 2(2)   |      |                       |
| Paolo Chiesa                                                     | Politecnico di Milano, Italy                                |  |  |  |  |  |  |  | 0(0) | 5(1)   |      |                       |
| Masahiro Kato                                                    | Toshiba Corporation, Japan                                  |  |  |  |  |  |  |  | 0(0) | 12(4)  |      |                       |
| Paitoon Tontiwachwuthikul,<br>Amornvadee Veawab,<br>Raphael Idem | U. of Regina, Canada                                        |  |  |  |  |  |  |  | 0(0) | 30(18) |      |                       |
| Syamalendus S. Bandyopadhyay                                     | Indian Institute of Technology, India                       |  |  |  |  |  |  |  | 0(0) | 5(2)   |      |                       |
| Cheng Fang Zhang                                                 | Shanghai Jiaotong University, China                         |  |  |  |  |  |  |  | 0(0) | 8(4)   |      |                       |
| Dwain F. Spencer                                                 | Electric Power Research Institute, USA                      |  |  |  |  |  |  |  | 7(1) | 5(2)   |      |                       |
| Frederic Dutil                                                   | CO2 Solution, Inc., Canada                                  |  |  |  |  |  |  |  | 7(7) | 0(0)   |      |                       |
| Joan F. Brennecke                                                | U. of Notre Dame, USA                                       |  |  |  |  |  |  |  | 0(0) | 37(14) | 1(1) | 0(0) <sup>b</sup>     |
| Satish Reddy                                                     | Fluor Corporation, USA                                      |  |  |  |  |  |  |  | 0(0) | 1(1)   | 4(2) | 0(0) <sup>c</sup>     |
| Geert F. Versteeg, Vishwas Y.<br>Dindore                         | Institutt for Kjemisk Prosessteknologi,<br>Norway           |  |  |  |  |  |  |  | 1(1) | 11(7)  | 0(0) | 8(8) <sup>a</sup>     |
| Robert Quinn                                                     | Air Products and Chemicals, Inc., USA                       |  |  |  |  |  |  |  | 0(1) | 6(1)   | 0(0) | 6(1) <sup>b</sup>     |
| Hideto Matsuyama, Masaaki<br>Teramoto                            | Kyoto Institute of Technology, Japan                        |  |  |  |  |  |  |  |      |        | 0(0) | 17(4) <sup>a,b</sup>  |
| Kew-Ho Lee, You-In park                                          | Korea Research Inst. of Chemical Tech.,<br>South Korea      |  |  |  |  |  |  |  |      |        | 0(0) | 18(11) <sup>a,b</sup> |
| Zhi Wang                                                         | Tianjin University, China                                   |  |  |  |  |  |  |  |      |        | 0(0) | 15(9) <sup>b</sup>    |
| Paul H. M. Feron                                                 | TNO Institute of Environmental Sciences,<br>The Netherlands |  |  |  |  |  |  |  |      |        | 2(1) | 16(10) <sup>a</sup>   |
| Zoher M. Meratla                                                 | CDS Research Ltd., USA                                      |  |  |  |  |  |  |  |      |        | 1(0) | 2(0) <sup>d</sup>     |
| Olav Falk-Pedersen                                               | Kvaerner ASA, Norway                                        |  |  |  |  |  |  |  |      |        | 2(0) | 8(4) <sup>a</sup>     |
| Fawzy T. Abdelmalek                                              | Abdelmalek & Associates, Inc., USA                          |  |  |  |  |  |  |  |      |        | 4(0) | 1(0) <sup>c</sup>     |

<sup>a</sup> Membrane contactors

<sup>b</sup> Immobilized liquid and facilitated transport membranes

<sup>c</sup> Autorefrigeration and liquefaction

<sup>d</sup> Cryogenic separation

Table 5. Number of patents per company on CO<sub>2</sub> related separation processes since 1995 and 2002 (in parentheses).

| <b>Company</b>                                         | <b>Membrane</b> | <b>Adsorption</b> | <b>Absorption</b> |
|--------------------------------------------------------|-----------------|-------------------|-------------------|
| Air Products and Chemicals, Inc., USA                  | 11(3)           | 51(18)            | 5(2)              |
| The BOC Group, Inc., USA                               | 3(1)            | 49(15)            | 5(2)              |
| Praxair Technology, Inc., USA                          | 23(7)           | 24(9)             | 10(2)             |
| ExxonMobil, USA                                        | 10(4)           | 2(2)              | 28(1)             |
| UOP LLC, USA                                           | 7(3)            | 17(5)             | 2(0)              |
| Membrane Technology and Research, Inc., USA            | 23(9)           |                   |                   |
| Mitsubishi Heavy Industries, Japan                     | 1(1)            | 2(1)              | 19(10)            |
| L'Air Liquide, France                                  | 11(5)           | 7(3)              | 2(0)              |
| Chevron USA Inc., USA                                  | 9(9)            | 3(3)              | 5(5)              |
| Shell Internationale Research, The Netherlands         | 4(2)            | 3(2)              | 8(7)              |
| Battelle Memorial Institute, USA                       | 4(3)            | 4(3)              | 4(3)              |
| DSM N V, The Netherlands                               |                 |                   | 13(8)             |
| Fluor Corporation, USA                                 |                 | 4(3)              | 8(7)              |
| E.I. Du Pont de Nemours and Company, USA               | 5(0)            | 1(0)              | 5(1)              |
| Engelhard Corporation, USA                             | 6(6)            | 4(4)              |                   |
| General Electric Co., USA                              | 2(2)            | 5(5)              | 3(2)              |
| Norsk Hydro ASA, Norway                                | 6(1)            |                   | 3(0)              |
| Questair Technologies, Inc., Canada                    |                 | 9(6)              |                   |
| Den Norske Stats Oljieselskap A.S., Norway             | 2(0)            |                   | 7(0)              |
| Hamilton Sundstrand Corporation, USA                   | 2(2)            | 4(4)              | 2(2)              |
| Texaco Development Corp., USA                          | 3(0)            |                   | 4(1)              |
| Kvaerner ASA, Norway                                   | 4(1)            |                   | 3(0)              |
| Matheson Tri-Gas, Inc., USA                            |                 | 7(6)              |                   |
| DOW/Corning Corp, USA                                  |                 | 3(0)              | 4(0)              |
| Messer Griesheim Industries, Inc.                      | 3(0)            | 1(0)              | 2(0)              |
| Agency of Industrial Sci.& Tech, Japan                 | 1(0)            | 3(0)              | 2(0)              |
| Korea Institute of Science and Technology, South Korea | 4(3)            | 2(1)              |                   |
| Conoco/Phillips, USA                                   | 2(2)            | 2(1)              | 1(1)              |
| Honeywell International Inc, USA                       | 1(0)            | 3(2)              |                   |
| Hunstmann Petrochemical Corporation, USA               |                 | 1(2)              | 0(2)              |
| BP-Amoco, UK-USA                                       | 4(2)            |                   | 4(3)              |
| Union Carbide, USA                                     |                 |                   | 4(1)              |
| Institut Francais du Petrole, France                   |                 | 1(1)              | 3(3)              |
| Landec Corporation, USA                                | 3(2)            |                   |                   |

Table 6. Licensors of CO<sub>2</sub> separation processes, type of process, production rate, and number of plants worldwide [478].

| Licensor                                            | System                                        | Primary Goal                            | CO <sub>2</sub> in Tailgas | Capacity/unit               | Plants Worldwide |
|-----------------------------------------------------|-----------------------------------------------|-----------------------------------------|----------------------------|-----------------------------|------------------|
| Linde AG                                            | PSA-H <sub>2</sub>                            | 2 (P)                                   | 30-60%                     | 1-100 MMscfd                | 250              |
| Technip                                             | PSA-H <sub>2</sub>                            | H <sub>2</sub> (P)                      | 30-60%                     | -                           | 240              |
| Uhde                                                | PSA-H <sub>2</sub>                            | H <sub>2</sub> (P)                      | 30-60%                     | -110 MMscfd                 | 60               |
| Haldor Topsøe A/S                                   | PSA-H <sub>2</sub>                            | H <sub>2</sub> (P)                      | 30-60%                     | -20 MMscfd                  | 31               |
| UOP LLC (Polybed)                                   | PSA-H <sub>2</sub>                            | H <sub>2</sub> (P)                      | 30-60%                     | -200 MMscfd                 | 700              |
| CB&I Howe-Baker                                     | PSA-H <sub>2</sub>                            | H <sub>2</sub> (P)                      | 30-60%                     | 1- 280 MMscfd               | 170              |
| Foster Wheeler                                      | PSA-H <sub>2</sub>                            | H <sub>2</sub> (P)                      | 30-60%                     | 1- 95 MMscfd                | 100              |
| Lurgi Oel-Gas-Chemie GmbH                           | PSA-H <sub>2</sub>                            | H <sub>2</sub> (P)                      | 30-60%                     | 1-200 MMscfd                | 105              |
| Air Products (PRISM)                                | PSA H <sub>2</sub>                            | 2 (P)                                   | 30-60%                     | 15-120 MMscfd               | 50               |
| Linde AG                                            | PSA-NH <sub>3</sub>                           | H <sub>2</sub> (P)                      | 30-60%                     | 230-1350 mtpd               | 3                |
| Uhde GmbH                                           | PSA-NH <sub>3</sub>                           | 2 (P)                                   | 30-60%                     | 500-1800 mtpd               | 14               |
| Haldor Topsøe                                       | PSA-NH <sub>3</sub>                           | H <sub>2</sub> (P)                      | 30-60%                     | 650-2050 mtpd               | 60               |
| Kellogg Brown & Root, Inc                           | PSA-NH <sub>3</sub>                           | 2 (P)                                   | 30-60%                     | -1850 mtpd                  | 200              |
| Engelhard Corp. (Molecular Gate)                    | Adsorption                                    | CO <sub>2</sub> , H <sub>2</sub> O (R)  | 1-98%                      | 2-10 MMscfd                 | 2                |
| Axens                                               | Adsorption                                    | GC+CO <sub>2</sub> (R)                  | 1-98%                      | -                           | 60               |
| ProPure As (CAP-compact)                            | Scrub (MDEA)                                  | H <sub>2</sub> S (R)                    | -                          | -                           | 2                |
| Shell Global Solutions International B.V (ADIP)     | Scrub (MDEA, DIPA)                            | AG (R)                                  | 1-98%                      | -                           | 400              |
| Shell Global Solutions International B.V (ADIP-X)   | Scrub (MDEA)                                  | AG (R)                                  | 1-98%                      | -                           | 1                |
| Prosernat-IFP Group Tech. (Advanced Amines)         | Scrub (DEA, MDEA)                             | AG (R)                                  | 1-98%                      | 0.3-25.2 Nm <sup>3</sup> /d | 120              |
| BASF AG (aMDEA)                                     | Scrub (MDEA)                                  | AG (R)                                  | 1-98%                      | 3.5-700 MMscfd              | 230              |
| UOP LLC (Amine Guard FS)                            | Scrub (amine)                                 | AG (R)                                  | 1-98%                      | -500 MMscfd                 | 500              |
| Prosernat IFP & Titan SNC Lavalin (ifpex-2)         | Scrub (Methanol)                              | AG (R)                                  | 1-98%                      | -350 MMscfd                 | -                |
| UOP LLC (Benfield)                                  | Scrub (DEA-K <sub>2</sub> CO <sub>3</sub> )   | AG (R)                                  | 1-98%                      | -500 MMscfd                 | 700              |
| Randall Gas Tech, ABB Lummus Global Inc.            | Scrub (MHA)                                   | AG (R)                                  | 1-98%                      | 2700 mtpd                   | 8                |
| Exxon Mobil Research & Eng. Co. (FIEXSORB)          | Scrub (amine)                                 | AG (R)                                  | 1-98%                      | -                           | 49               |
| Fluor Enterprises, Inc. (Econamine)                 | Scrub (DGA)                                   | CO <sub>2</sub> (R)                     | +99%                       | 3-400 MMscfd                | 55               |
| Fluor Enterprises, Inc. (Econamine FG Plus)         | Scrub (MEA)                                   | CO <sub>2</sub> (R)                     | +99%                       | -300 mtpd                   | 24               |
| Fluor Enterprises, Inc. (Improved Econamine )       | Scrub (DGA)                                   | CO <sub>2</sub> (R)                     | +99%                       | 547 MMscfd                  | 7                |
| Fluor Enterprises, Inc. (Fluor Solvent)             | Scrub (fluor solvent+PC)                      | CO <sub>2</sub> (R)                     | +99%                       | -220 MMscfd                 | 13               |
| Advantica Ltd. (LRS-10)                             | Scrub (LRS10-K <sub>2</sub> CO <sub>3</sub> ) | CO <sub>2</sub> (R)                     | +99%                       | -                           | 30               |
| Uhde GmbH (Morphysorb)                              | Scrub (Morphysorb)                            | AG (R)                                  | 1-98%                      | 300 MMscfd                  | 2                |
| Lurgi Oel-Gas-Chemie GmbH (Omnisulf)                | Scrub (Morphysorb)                            | AG (R)                                  | 1-98%                      | -                           | 1                |
| Lurgi Oel-Gas-Chemie GmbH (Purisol)                 | Scrub (NMP)                                   | AG (R)                                  | 1-98%                      | -                           | 7                |
| Lurgi Oel-Gas-Chemie GmbH (Rectisol)                | Scrub (Methanol)                              | AG (R)                                  | 1-98%                      | -                           | 100              |
| UOP LLC (Selexol)                                   | Scrub (DME, PEG)                              | AG (R)                                  | 1-98%                      | -                           | 55               |
| Shell Global Solutions International B.V (Sulfinol) | Scrub (sulfolane, amine)                      | AG (R)                                  | 1-98%                      | -                           | 200              |
| Fluor (CO <sub>2</sub> LDSEP)                       | Liquifaction                                  | CO <sub>2</sub> , H <sub>2</sub> (R, P) | +99%                       | -15 MMscfd                  | -                |
| Costain Oil, Gas & Process Ltd.                     | Liquifaction                                  | CO <sub>2</sub> (P)                     | 100%                       | 5-1200 mtpd                 | 7                |
| Air Liquide (Medal)                                 | Membrane                                      | CO <sub>2</sub> , H <sub>2</sub> O (R)  | 2-70%                      | 1-1000 MMscfd               | several          |
| NATCO Group Inc. (CYNARA)                           | Membrane                                      | CO <sub>2</sub> (R)                     | -95%                       | 5-750 MMscfd                | 30               |
| UOP LLC (Separex)                                   | Membrane                                      | AG (R)                                  | -                          | 1-1000 MMscfd               | 50               |
| Merichem Chem & Refineries Services (AMINEX)        | HFCM                                          | AG (R)                                  | 1-98%                      | -                           | 10               |

PSA = Pressure Swing Adsorption; Mem = membrane; CEL = compression-expansion liquefaction; L = Liquefaction; HFMC = hollow fiber membrane contactor; AG = All acid gases (i.e., H<sub>2</sub>S, COS and CO<sub>2</sub>); P = purification; R = removal; PC = propylene carbonate; GC= Gas contaminants (Hg, As, H<sub>2</sub>O, TBC, NH and Sx)

Table 7. Characteristics of key alkanolamines used in gas treating [479].

| Name                                   |      | Chemical Formula                              | Molecular Weight | Vapor Pressure (mm Hg) | Relative Acid Gas Capacity (%) |
|----------------------------------------|------|-----------------------------------------------|------------------|------------------------|--------------------------------|
| Ethanolamine<br>(Monoethanolamine)     | MEA  | $\text{HO-CH}_2\text{CH}_2\text{-NH}_2$       | 61               | 1.05                   | 100                            |
| Diethanolamine                         | DEA  | $(\text{HO-CH}_2\text{CH}_2)_2\text{-NH}$     | 105              | 0.058                  | 58                             |
| Triethanolamine                        | TEA  | $(\text{HO-CH}_2\text{CH}_2)_3\text{-N}$      | 148              | 0.0063                 | 41                             |
| Hydroxyethanolamine<br>(Diglycolamine) | DGA  | $\text{H-(OCH}_2\text{CH}_2)_2\text{-NH}_2$   | 105              | 0.0160                 | 58                             |
| Diisopropanolamine                     | DIPA | $(\text{CH}_3\text{CH(OH)CH}_2)_2\text{-NH}$  | 133              | 0.010                  | 46                             |
| Methyldiethanolamine                   | MDEA | $(\text{HO-CH}_2\text{CH}_2)_2\text{-N-CH}_3$ | 119              | 0.0061                 | 51                             |



Table 8. Major types of acid gas absorbent processes [479-481].

|                                                         | <u>Chemical Absorption</u>                                                                                                                                                                                                                                                                                                                                                                                                                             |                                                                                                                                                                                                                                                          | <u>Physical Solvent Absorption</u>                                                                                            |
|---------------------------------------------------------|--------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------------------------------------------------|
|                                                         | <u>Alkanolamine</u>                                                                                                                                                                                                                                                                                                                                                                                                                                    | <u>Inorganic Carbonate</u>                                                                                                                                                                                                                               |                                                                                                                               |
| Adsorbents                                              | MEA, DEA, DGA, MDEA, DIPA                                                                                                                                                                                                                                                                                                                                                                                                                              | K <sub>2</sub> CO <sub>3</sub> , K <sub>2</sub> CO <sub>3</sub> -MEA, K <sub>2</sub> CO <sub>3</sub> -DEA                                                                                                                                                | Purisol, Selexol, Rectisol,                                                                                                   |
| CO <sub>2</sub> & H <sub>2</sub> S absorption mechanism | Chemical reaction<br>CO <sub>2</sub> :<br>$2\text{RNH}_2 + \text{CO}_2 + \text{H}_2\text{O} \leftrightarrow (\text{RNH}_3)_2\text{CO}_3$<br>$(\text{RNH}_3)_2\text{CO}_3 + \text{CO}_2 + \text{H}_2\text{O} \leftrightarrow 2\text{RNH}_3\text{HCO}_3$<br>H <sub>2</sub> S:<br>$2\text{RNH}_2 + \text{H}_2\text{S} \leftrightarrow (\text{RNH}_3)_2\text{S}$<br>$(\text{RNH}_3)_2\text{S} + \text{H}_2\text{S} \leftrightarrow 2\text{RNH}_3\text{HS}$ | Chemical reaction<br>CO <sub>2</sub> :<br>$\text{Na}_2\text{CO}_3 + \text{CO}_2 + \text{H}_2\text{O} \leftrightarrow 2\text{NaHCO}_3$<br>H <sub>2</sub> S:<br>$\text{Na}_2\text{CO}_3 + \text{H}_2\text{S} \leftrightarrow \text{NaHS} + \text{NaHCO}_3$ | Physical dissolution                                                                                                          |
| Operating Pressure, psig                                | Insensitive to pressure                                                                                                                                                                                                                                                                                                                                                                                                                                | > 200                                                                                                                                                                                                                                                    | 250-1000                                                                                                                      |
| Operating Temp., °F                                     | 100-400                                                                                                                                                                                                                                                                                                                                                                                                                                                | 200-250                                                                                                                                                                                                                                                  | Ambient temperature                                                                                                           |
| Stripper Gas                                            | Steam                                                                                                                                                                                                                                                                                                                                                                                                                                                  | Steam or air*                                                                                                                                                                                                                                            | Steam or air*                                                                                                                 |
| Absorbent Recovery                                      | Reboiled stripper                                                                                                                                                                                                                                                                                                                                                                                                                                      | Stripper                                                                                                                                                                                                                                                 | Flash, reboiler, or steam stripper                                                                                            |
| Swing variables (Temp. or Pressure)                     | Temperature principally                                                                                                                                                                                                                                                                                                                                                                                                                                | Both, but pressure principally                                                                                                                                                                                                                           | Pressure principally                                                                                                          |
| Selectivity CO <sub>2</sub> vs. H <sub>2</sub> S        | Only MDEA selective for H <sub>2</sub> S                                                                                                                                                                                                                                                                                                                                                                                                               | May be selective for H <sub>2</sub> S                                                                                                                                                                                                                    | Some selectivity for H <sub>2</sub> S                                                                                         |
| Meets ppmv H <sub>2</sub> S                             | Yes                                                                                                                                                                                                                                                                                                                                                                                                                                                    | Yes                                                                                                                                                                                                                                                      | Yes                                                                                                                           |
| Effect of O <sub>2</sub> in Feed                        | Amine degradation products                                                                                                                                                                                                                                                                                                                                                                                                                             | None                                                                                                                                                                                                                                                     | Sulfur (S <sub>8</sub> ) precipitates at low temperatures                                                                     |
| COS and CS <sub>2</sub> Removal and degradation         | MEA – no removal and strong degradation; DEA – slight removal and some degradation; DGA – removes both, strong degradation; DIPA, MDEA – Removes both, no degradation                                                                                                                                                                                                                                                                                  | Converts both into CO <sub>2</sub> and H <sub>2</sub> S, then removes both, no degradation                                                                                                                                                               | Removes both, no degradation                                                                                                  |
| Solvent: solute concentration, wt%                      | H <sub>2</sub> O:<br>MEA, 13-25; DEA, 10-30; DGA, 40-60; MDEA, 33-55                                                                                                                                                                                                                                                                                                                                                                                   | H <sub>2</sub> O:<br>K <sub>2</sub> CO <sub>3</sub> < 30                                                                                                                                                                                                 | <u>N-methyl-2-pyrrolidone</u> (purisol); <u>dimethyl ether of polypropylene glycol</u> (selexol); <u>methanol</u> (rectisol); |
| Operating Problems                                      | Solution degradation, foaming, corrosion, evaporation (MEA)                                                                                                                                                                                                                                                                                                                                                                                            | Column instability, corrosion, erosion                                                                                                                                                                                                                   | Absorption of heavy hydrocarbons                                                                                              |
| Utility Cost                                            | High                                                                                                                                                                                                                                                                                                                                                                                                                                                   | Medium                                                                                                                                                                                                                                                   | Low to medium                                                                                                                 |
| Other comments                                          | MEA limited to COS, CS <sub>2</sub> free streams with low CO <sub>2</sub> and H <sub>2</sub> S concentrations; inhibitors used to control corrosive character of loaded alkanolamines; performance improves: MEA < DEA < DIPA < MDEA                                                                                                                                                                                                                   | Rate enhancers are used to improve low adsorption rates; good for high pressure gases                                                                                                                                                                    | Best for high pressure gases.                                                                                                 |

\* For streams free of sulfur compounds.

Table 9. Number of papers since 2000 containing in the title the indicated alkanolamine and other absorbents for CO<sub>2</sub> removal.

| <b>Absorbent</b>            | <b>#</b> |
|-----------------------------|----------|
| Methyldiethanolamine (MDEA) | 73       |
| Monoethanolamine (MEA)      | 55       |
| Diethanolamine (DEA)        | 38       |
| Piperazine (PZ)             | 33       |
| Potassium Carbonate         | 7        |
| Aminomethylpropano (AMP)    | 6        |
| Triethanolamine (TEA)       | 5        |
| Diglycolamine (DGA)         | 4        |
| Sodium Glycinate            | 4        |
| Dyethylene triamine (DETA)  | 3        |
| Diisopropanolamine (DIPA)   | 2        |

Table 10. Typical capacities of commercial and developmental CO<sub>2</sub> and CO selective adsorbents.

| <b>Adsorbent</b>                       | <b>Adsorbate</b> | <b>T (°C)</b> | <b>P (torr)</b>       | <b>Loading (mol/kg)</b>  | <b>Mode</b> |
|----------------------------------------|------------------|---------------|-----------------------|--------------------------|-------------|
| act. carbon                            | CO <sub>2</sub>  | 25            | 500                   | 1.5-2.0                  | PSA         |
| act. carbon                            | CO <sub>2</sub>  | 250-300       | 500                   | 0.1-0.2                  | PSA         |
| 5A zeolite                             | CO <sub>2</sub>  | 25            | 500                   | ~ 3.0                    | PSA         |
| 5A zeolite                             | CO <sub>2</sub>  | 250           | 500                   | 0.2                      | PSA         |
| titanosilicates                        | CO <sub>2</sub>  | 25-200        | 760-6x10 <sup>5</sup> | proprietary <sup>1</sup> | PSA         |
| titanosilicates                        | N <sub>2</sub>   | 25-200        | 760-6x10 <sup>5</sup> | proprietary <sup>1</sup> | PSA         |
| titanosilicates                        | CH <sub>4</sub>  | 25-200        | 760-6x10 <sup>5</sup> | proprietary <sup>1</sup> | PSA         |
| solid amine<br>(supported PEI)         |                  | 75            | 760                   | 1.5 – 3.0                | PSA         |
| HTlc<br>(K-promoted)                   | CO <sub>2</sub>  | 300-400       | 200-700               | 0.4-0.7                  | PSA         |
| double-layer<br>hydroxides             | CO <sub>2</sub>  | 375           | 230                   | 1.5                      | PSA         |
| alumina<br>(un-doped)                  | CO <sub>2</sub>  | 400           | 500                   | 0.06                     | PSA         |
| alumina<br>(doped w/Li <sub>2</sub> O) | CO <sub>2</sub>  | 400           | 500                   | 0.52                     | PSA         |
| alumina<br>(basic)                     | CO <sub>2</sub>  | 300           | 500                   | 0.3                      | PSA         |
| Li zirconate                           | CO <sub>2</sub>  | 500           | 760                   | 3.4-4.5                  | TSA         |
| CaO                                    | CO <sub>2</sub>  | 500           | 150                   | 4-8                      | TSA         |
| CaO                                    | CO <sub>2</sub>  | 700           | 76                    | 7                        | TSA         |
| Cu(I)<br>(alumina)                     | CO               | 25-30         | 760                   | 0.8-1.2                  | PSA         |
| Cu(I)<br>(alumina)                     | CO               | 30            | 760                   | 0.8                      | PSA         |

<sup>1</sup> Molecular Gate titanosilicates molecular sieves patented by Engelhard Coporation [10].

Table 11. Performances of various PSA cycle configurations investigated for CO<sub>2</sub> concentration from flue gas, with the process performance judged primarily in terms of the CO<sub>2</sub> purity in the heavy product ( $y_{\text{CO}_2,\text{F}}$ ), with the CO<sub>2</sub> recovery ( $R_{\text{CO}_2}$ ) and the feed throughput ( $\theta$ ) being secondary but also important process performance indicators.

| Cycle Configuration | Cycle Step Sequence*                       | Ads** | $P_{\text{H}}$<br>(atm) | $P_{\text{H}}/P_{\text{L}}$<br>y | $\text{CO}_{2,\text{F}}$<br>(%) | $y_{\text{CO}_2,\text{HP}}$<br>(%) | $R_{\text{CO}_2}$<br>(%) | $\theta$<br>(LSTP/hr/kg) | Reference |
|---------------------|--------------------------------------------|-------|-------------------------|----------------------------------|---------------------------------|------------------------------------|--------------------------|--------------------------|-----------|
| 2-bed 2-step        | FP, CnD                                    | Y     | 2.0                     | 2.0                              | 15                              | 18                                 | 90                       | 12,600                   | [482]     |
| 2-bed 4-step        | FP, F, CnD, LR                             | 13X   | 3.0                     | 3.0                              | 8.3                             | --                                 | --                       | 15                       | [483]     |
| 1-bed 4-step        | LPP, F, CnD, LR                            | 13X   | 1.7                     | 1.9                              | 15                              | 24.4                               | 9                        | 17                       | [484]     |
| 2-bed 4-step        | FP, F, CnD, LR                             | 13X   | 1.1                     | 17.2                             | 10                              | 68                                 | 50                       | 507                      | [38]      |
| 1-bed 4-step        | FP, F, CnD, LR                             | 13X   | 14.0                    | 15.9                             | 15                              | 56.4                               | 98                       | 908                      | [485]     |
| 3-bed 8-step        | FP, F, CoD, LEE, HPP or HR-IP, N, CnD, LEE | AC    | 1.5                     | 15                               | 17                              | 99.8                               | 34                       | 331                      | [486]     |
| 3-bed 7-step        | FP, F, LEE, HR-IP, N, CnD, LEE             | AC    | 2.0                     | 20                               | 13                              | 99                                 | 55                       | 156                      | [487]     |
| 3-bed 8-step        | FP, F, LEE, HPP, HR-IP, N, CnD, LEE        | 13X   | 1.5                     | 30                               | 13                              | 99.5                               | 69                       | 228                      | [488]     |
| 3-bed 8-step        | FP, F, CoD, FR, N, HR-IP, CnD, N           | AC    | 1.1                     | 16.6                             | 16                              | 99                                 | 50                       | 610                      | [489]     |
| 4-bed 4-step        | LPP, F+ReC, HR, CnD                        | AC    | 1.2                     | 12                               | 17                              | 99.9+                              | 68                       | 33                       | [490]     |
| 4-bed 8-step        | LPP, N, F, HR, LEE, CnD, LR, LEE           | 13X   | 1.1                     | 11                               | 13                              | 64                                 | 80                       | 120                      | [491]     |
| 3-bed 5-step        | FP, F, HR, CnD, LR                         | 13X   | 1.1                     | 17.2                             | 10                              | 83                                 | 54                       | 338                      | [38]      |
| 2-bed 6-step        | LEE, FP, F, LEE, CnD, LR                   | 13X   | 1.1                     | 17.2                             | 10                              | 82                                 | 57                       | 477                      | [38]      |
| 2-bed 4-step        | HPP, FP, CoD, CnD                          | 13X   | 5.5                     | 110                              | 20                              | 48                                 | 94                       | 426                      | [491]     |
| 2-bed 5-step        | LPP, FP, F, CoD, CnD                       | 13X   | 5.5                     | 110                              | 20                              | 43                                 | 88                       | 426                      | [491]     |
| 3-bed 4-step        | LPP, F, CnD, LR                            | 13X   | 1.5                     | 30                               | 20                              | 58                                 | 75                       | 273                      | [491]     |
| 3-bed 6-step        | LPP, FP, F, HR, CoD, CnD                   | 13X   | 1.5                     | 30                               | 20                              | 63                                 | 70                       | 273                      | [491]     |
| 4-bed 4-step        | LPP, F, CnD, LR                            | HTlc  | 1.4                     | 12                               | 15                              | 63                                 | 75                       | 22                       | [37]      |
| 4-bed 5-step        | LPP, F, CoD, CnD, LR                       | HTlc  | 1.4                     | 12                               | 15                              | 84                                 | 68                       | 15                       | [37]      |
| 5-bed 5-step        | LPP, F, CoD, CnD, LR                       | HTlc  | 1.4                     | 12                               | 15                              | 65                                 | 87                       | 12                       | [37]      |
| 5-bed 5-step        | LPP, F, HR (from CnD), CnD, LR             | HTlc  | 1.4                     | 12                               | 15                              | 72                                 | 82                       | 12                       | [37]      |
| 5-bed 5-step        | LPP, F, HR (from LR), CnD, LR              | HTlc  | 1.4                     | 12                               | 15                              | 76                                 | 49                       | 23                       | [37]      |
| 4-bed 4-step        | LPP, F, HR (from CnD), CnD                 | HTlc  | 1.4                     | 12                               | 15                              | 83                                 | 17                       | 14                       | [37]      |
| 5-bed 5-step        | LPP, F, HR (from LR), CnD, LR              | HTlc  | 1.4                     | 12                               | 15                              | 89                                 | 72                       | 58                       | [61]      |
| 4-bed 4-step        | LPP, F, HR (from CnD), CnD                 | HTlc  | 1.4                     | 12                               | 15                              | 98                                 | 5                        | 202                      | [61]      |

\* CnD = countercurrent depressurization; CoD = cocurrent depressurization; FP = feed pressurization; F = high pressure feed; HPP = heavy product pressurization; HR = heavy reflux; IP = intermediate pressure; LEE = light end equalization; LPP = light product pressurization; LR = light reflux; N = null or delay; ReC = recycle.

\*\* All processes operated at ambient temperature except for HTlc (hydrotalcite like compound), which was done at 575 °K.

Table 12. Permeabilities and permeances of membrane materials used for CO<sub>2</sub> separations.

|                                                                                                                     | * T<br>(°C) | UNITS | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  |      | REFERENCE |
|---------------------------------------------------------------------------------------------------------------------|-------------|-------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|------|-----------|
|                                                                                                                     |             |       | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |      |           |
| ORGANIC MEMBRANES                                                                                                   |             |       |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |      |           |
| Polyacetylenes                                                                                                      |             |       |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |      |           |
| R groups                                                                                                            |             |       |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |      |           |
| D = H, R' = C(CH <sub>3</sub> ) <sub>4</sub>                                                                        | S           | 25    | Barrer                        | 180            | 300            | 43             | 130             | 85              | 560                 | 3.11                            | 1.87                            | 13.02                            | 6.59 | [230]     |
| D = CH <sub>3</sub> , R' = CH(CH <sub>3</sub> ) <sub>2</sub> (PMP)                                                  | S           | 25    | Barrer                        | 2630           | 5800           | 1330           | 2700            | 2900            | 10700               | 4.07                            | 1.84                            | 8.05                             | 3.69 | [230]     |
| D = CH <sub>3</sub> , R' = CH(CH <sub>3</sub> ) <sub>2</sub> (PMP)                                                  | S           | 35    | Barrer                        | 2650           | 5640           | 1250           | 2460            | 2690            | 9090                | 3.43                            | 1.61                            | 7.27                             | 3.38 | [219]     |
| D = CH <sub>3</sub> , R' = CH <sub>2</sub> CH(CH <sub>3</sub> ) <sub>2</sub> (P5M2H)                                | S           | 35    | Barrer                        | 460            | 750            | 93             | 245             | 190             | 900                 | 1.96                            | 1.20                            | 9.68                             | 4.74 | [219]     |
| D = CH <sub>3</sub> , R' = CH <sub>2</sub> CH <sub>2</sub> CH(CH <sub>3</sub> ) <sub>2</sub> (P6M2H)                | S           | 35    | Barrer                        | 240            | 370            | 51             | 130             | 112             | 390                 | 1.63                            | 1.05                            | 7.65                             | 3.48 | [219]     |
| D = CH <sub>3</sub> , R' = SiMe <sub>3</sub> (PTMSP)                                                                | S           | 25    | Barrer                        |                | 18000          | 7000           | 11000           |                 | 41000               |                                 | 2.28                            | 5.86                             |      | [231]     |
| D = CH <sub>3</sub> , R' = SiMe <sub>3</sub> (PTMSP)                                                                | M           | 23    | Barrer                        |                | 11800          | 5700           |                 |                 | 18200               |                                 | 1.54                            | 3.19                             |      | [222]     |
| D = CH <sub>3</sub> , R' = SiMe <sub>3</sub> (PTMSP)                                                                | S           | 35    | Barrer                        | 5080           |                | 4970           | 7730            | 13000           | 28000               | 5.51                            |                                 | 5.63                             | 2.15 | [116]     |
| D = CH <sub>3</sub> , R' = SiMe <sub>3</sub> (PTMSP)                                                                | S           | 25    | Barrer                        | 2200           | 5200           | 1800           | 3000            | 4300            | 19000               | 8.64                            | 3.65                            | 10.56                            | 4.42 | [116]     |
| D = H, R' = t-Bu                                                                                                    | S           | 25    | Barrer                        | 180            | 300            | 43             | 130             | 85              | 560                 | 3.11                            | 1.87                            | 13.02                            | 6.59 | [116]     |
| D = H, D' = CH <sub>3</sub> , 'Poly(cis-isoprene)                                                                   | S           | 35    | Barrer                        | 100            |                | 35.9           | 91              | 150             | 520                 | 5.20                            |                                 | 14.48                            | 3.47 | [116]     |
| D = CH <sub>3</sub> , R' = Si(CH <sub>3</sub> ) <sub>2</sub> CH <sub>2</sub> Si(CH <sub>3</sub> ) <sub>3</sub>      | S           | 25    | Barrer                        | 180            | 270            | 21             | 75              | 45              | 310                 | 1.72                            | 1.15                            | 14.76                            | 6.89 | [116]     |
| D = H, R' = o-C <sub>6</sub> H <sub>4</sub> Si(CH <sub>3</sub> ) <sub>3</sub>                                       | S           | 25    | Barrer                        | 170            | 290            | 24             | 78              | 38              | 290                 | 1.71                            | 1.00                            | 12.08                            | 7.63 | [116]     |
| D = CH <sub>3</sub> , R' = n-C <sub>5</sub> H <sub>11</sub>                                                         | S           | 35    | Barrer                        |                | 150            | 21             | 57              | 51              | 200                 |                                 | 1.33                            | 9.52                             | 3.92 | [218]     |
| D = CH <sub>3</sub> , R' = n-C <sub>6</sub> H <sub>13</sub>                                                         | S           | 35    | Barrer                        |                | 140            | 23             | 60              | 64              | 230                 |                                 | 1.64                            | 10.00                            | 3.59 | [218]     |
| D = CH <sub>3</sub> , R' = n-C <sub>7</sub> H <sub>15</sub>                                                         | S           | 35    | Barrer                        |                | 150            | 29             | 74              | 84              | 290                 |                                 | 1.93                            | 10.00                            | 3.45 | [218]     |
| D = CH <sub>3</sub> , R' = n-C <sub>8</sub> H <sub>17</sub>                                                         | S           | 35    | Barrer                        |                | 140            | 29             | 71              | 83              | 290                 |                                 | 2.07                            | 10.00                            | 3.49 | [218]     |
| D = CH <sub>3</sub> , R' = n-C <sub>7</sub> H <sub>15</sub>                                                         | S           | 25    | Barrer                        | 48             | 76             | 14             | 35              | 40              | 130                 | 2.71                            | 1.71                            | 9.29                             | 3.25 | [116]     |
| D = Cl, R' = n-C <sub>6</sub> H <sub>13</sub>                                                                       | S           | 25    | Barrer                        | 43             | 76             | 16             | 47              | 46              | 170                 | 3.95                            | 2.24                            | 10.63                            | 3.70 | [116]     |
| D = Cl, R' = n-C <sub>4</sub> H <sub>9</sub>                                                                        | S           | 25    | Barrer                        | 41             | 66             | 11             | 32              | 33              | 130                 | 3.17                            | 1.97                            | 11.82                            | 3.94 | [116]     |
| D = Cl, R' = n-C <sub>8</sub> H <sub>19</sub>                                                                       | S           | 25    | Barrer                        | 59             | 100            | 10             | 35              | 30              | 180                 | 3.05                            | 1.80                            | 18.00                            | 6.00 | [116]     |
| D = H, R' = CH(n-C <sub>5</sub> H <sub>11</sub> )Si(CH <sub>3</sub> ) <sub>3</sub>                                  | S           | 25    | Barrer                        | 60             | 84             | 8              | 27              | 21              | 120                 | 2.00                            | 1.43                            | 15.00                            | 5.71 | [116]     |
| D = H, R' = CH(n-C <sub>3</sub> H <sub>7</sub> )Si(CH <sub>3</sub> ) <sub>2</sub> -n-C <sub>6</sub> H <sub>13</sub> | S           | 25    | Barrer                        | 58             | 42             | 6.3            | 19              | 17              | 70                  | 1.21                            | 1.67                            | 11.11                            | 4.12 | [116]     |
| D = D <sub>6</sub> , D' = n-C <sub>6</sub> H <sub>13</sub>                                                          | S           | 25    | Barrer                        | 30             | 45             | 5.5            | 14              | 14              | 48                  | 1.60                            | 1.07                            | 8.73                             | 3.43 | [116]     |
| D = H, R' = CH(n-C <sub>3</sub> H <sub>7</sub> )Si(CH <sub>3</sub> ) <sub>2</sub> Ph                                | S           | 25    | Barrer                        | 25             | 29             | 2.5            | 9.5             | 7               | 54                  | 2.16                            | 1.86                            | 21.60                            | 7.71 | [116]     |

|                                                                                                                                | * | T     | UNITS  | PERMEANCES AND PERMEABILITIES |                |              |              |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |
|--------------------------------------------------------------------------------------------------------------------------------|---|-------|--------|-------------------------------|----------------|--------------|--------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|
|                                                                                                                                |   | (°C)  |        | He                            | H <sub>2</sub> | <sub>2</sub> | <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
|                                                                                                                                |   |       |        |                               | N              | O            |              |                 |                 |                     |                                 |                                 |                                  |           |
| Polyacetylenes (Cont'd.)                                                                                                       |   |       |        |                               |                |              |              |                 |                 |                     |                                 |                                 |                                  |           |
| R = CH <sub>3</sub> ; R' = Si(CH <sub>3</sub> ) <sub>2</sub> CH <sub>2</sub> CH <sub>2</sub> Si(CH <sub>3</sub> ) <sub>3</sub> |   | 25    | Barrer | 130                           | 180            | 14           | 50           | 28              | 150             | 1.15                | 0.83                            | 10.71                           | 5.36                             | [116]     |
| R = CH <sub>3</sub> ; R' = n-C <sub>3</sub> H <sub>7</sub>                                                                     | S | 35    | Barrer |                               | 160            | 12           | 39           | 21              | 120             |                     | 0.75                            | 10.00                           | 5.71                             | [218]     |
| R = H;<br>R' = o-C <sub>6</sub> H <sub>4</sub> CF <sub>3</sub>                                                                 | S | 25    | Barrer | 130                           | 140            | 7.3          | 25           | 6.6             | 130             | 1.00                | 0.93                            | 17.81                           | 19.70                            | [116]     |
| R = Ph; R' = (CH <sub>3</sub> ) <sub>3</sub> (PPP)                                                                             | S | 25    | Barrer | 30                            | 43             | 2.2          | 6.3          | 2.8             | 25              | 0.83                | 0.58                            | 11.36                           | 8.93                             | [116]     |
| R = Ph; R' = Et                                                                                                                | S | 25    | Barrer | 40                            | 57             | 4.5          | 12           | 4.4             | 40              | 1.00                | 0.70                            | 8.89                            | 9.09                             | [116]     |
| R = Ph; R' = Cl                                                                                                                | S | 25    | Barrer | 23                            | 29             | 1            | 5.1          | 1.3             | 23              | 1.00                | 0.79                            | 23.00                           | 17.69                            | [116]     |
| R = H;<br>R' = o-C <sub>6</sub> H <sub>4</sub> (CH <sub>3</sub> ) <sub>3</sub>                                                 | S | 25    | Barrer | 29                            | 39             | 3            | 8.1          | 3               | 15              | 0.52                | 0.38                            | 5.00                            | 5.00                             | [116]     |
| R = (CH <sub>3</sub> ) <sub>3</sub> ; R' = Ph (PPP)                                                                            | S | 25    | Barrer |                               | 280            | 20           | 58           |                 | 260             |                     | 0.93                            | 13.00                           |                                  | [231]     |
| Polyolefins                                                                                                                    |   |       |        |                               |                |              |              |                 |                 |                     |                                 |                                 |                                  |           |
| Polystyrene                                                                                                                    | S | 35    | Barrer | 22.4                          |                | 0.52         | 2.9          | 0.78            | 12.4            | 0.55                |                                 | 23.85                           | 15.90                            | [116]     |
| Polytetrafluoroethylene (PTFE)                                                                                                 | M | 25    | Barrer |                               | 9.8            |              |              |                 | 11.7            |                     | 1.19                            |                                 |                                  | [492]     |
| Polyethylene                                                                                                                   | S | 30    | Barrer |                               | 17.3           | 4.2          | 6.3          | 7.7             | 17.9            |                     | 1.03                            | 4.26                            | 2.32                             | [249]     |
| Polystyrene                                                                                                                    | S | 30    | Barrer |                               | 23.8           | 0.6          | 2.4          | 0.8             | 10.4            |                     | 0.44                            | 17.33                           | 13.00                            | [249]     |
| Polybenzylmethacrylate                                                                                                         | S | 30    | Barrer |                               | 11             |              |              | 1.4             | 7.9             |                     | 0.72                            |                                 | 5.64                             | [249]     |
| Polymethylmethacrylate                                                                                                         | S | 30    | Barrer |                               | 2.4            | 1.2          | 3.3          | 0.6             | 0.6             |                     | 0.25                            | 0.50                            | 1.00                             | [249]     |
| Polyvinylacetate                                                                                                               | S | 30    | Barrer |                               | 15.1           | 1.3          | 2.3          | 0.9             | 13.1            |                     | 0.87                            | 10.08                           | 14.56                            | [249]     |
| Polyethylene:Polyvinylalcohol                                                                                                  | S | 30    | Barrer |                               | 0.5            | 0.3          | 0.2          | 0.2             | 0.2             |                     | 0.40                            | 0.67                            | 1.00                             | [249]     |
| Polyvinylidene fluoride                                                                                                        | S | 30    | Barrer |                               | 2.4            | 0.7          | 1.4          | 1.3             | 1.2             |                     | 0.50                            | 1.71                            | 0.92                             | [249]     |
| Polyvinyltrimethylsilane (PVTMS)                                                                                               | S | 25    | Barrer |                               | 200            | 11           | 44           | 14              | 200             |                     | 1.00                            | 18.18                           | 14.29                            | [116]     |
| Polyvinylacetate                                                                                                               | S | 35    | Barrer | 15.1                          |                | 0.089        | 0.53         |                 | 3.1             | 0.21                |                                 | 34.83                           |                                  | [359]     |
| Poly(ethyl methacrylate)                                                                                                       | S | 35    | Barrer | 23.8                          |                | 0.33         | 1.9          | 0.35            | 7.01            | 0.29                |                                 | 21.24                           | 20.03                            | [116]     |
| Poly(methyl methacrylate)                                                                                                      | S | 35    | Barrer | 8.4                           |                | 0.02         | 0.14         | 0.0052          | 0.62            | 0.07                |                                 | 31.00                           | 119.23                           | [116]     |
| PVTMS                                                                                                                          | S | 20-25 | GPU    | 762                           |                | 138          |              | 156             | 746             | 0.98                |                                 | 5.41                            | 4.78                             | [493]     |
| PVTMS (silicone coated)                                                                                                        | S | 20-25 | GPU    | 473                           |                | 52           |              | 90              | 450             | 0.95                |                                 | 8.65                            | 5.00                             | [493]     |
| PVTMS (silicone coated & fluorinated)                                                                                          | S | 20-25 | GPU    | 120                           |                | 3.4          |              | 1               | 110             | 0.92                |                                 | 32.35                           | 110.00                           | [493]     |
| Poly(2-hydroxyethyl methacrylate)/alumina                                                                                      | S | room  | Barrer | 15                            | 23             | 7.9          | 7.2          | 10.6            | 7               | 0.47                | 0.30                            | 0.89                            | 0.66                             | [248]     |

|                                                                                                                       | * | T    | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |
|-----------------------------------------------------------------------------------------------------------------------|---|------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|
|                                                                                                                       |   | (°C) |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
| <b>Polydienes</b>                                                                                                     |   |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Polychloroprene                                                                                                       | M | 25   | Barrer |                               | 13.6           |                |                |                 | 25.8            |                     | 1.90                            |                                 |                                  | [492]     |
| Polybutadiene                                                                                                         | M | 25   | Barrer |                               | 42             |                |                |                 | 138             |                     | 3.29                            |                                 |                                  | [492]     |
| <b>Silicones</b>                                                                                                      |   |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Poly(dimethylsiloxane)                                                                                                | M | 23   | Barrer |                               | 950            | 380            |                | 850             | 3200            |                     | 3.37                            | 8.42                            | 3.76                             | [222]     |
| Poly(dimethylsiloxane)                                                                                                | S | 30   | Barrer |                               | 375            | 299            | 540            | 600             | 1300            |                     | 3.47                            | 4.35                            | 2.17                             | [249]     |
| PDMS                                                                                                                  | S | 23   | Barrer |                               | 890            | 400            | 800            | 1200            | 3800            |                     | 4.27                            | 9.50                            | 3.17                             | [364]     |
| Poly(dimethylsiloxane) (PDMS)                                                                                         | S | 35   | Barrer | 590                           |                | 351            | 781            | 1430            | 4550            | 7.71                |                                 | 12.96                           | 3.18                             | [116]     |
| Poly(methylpropylsiloxane)                                                                                            | S | 35   | Barrer |                               |                |                |                | 531             | 1520            |                     |                                 |                                 | 2.86                             | [116]     |
| Poly(methyloctylsiloxane)                                                                                             | S | 35   | Barrer |                               |                |                |                | 314             | 917             |                     |                                 |                                 | 2.92                             | [116]     |
| Poly(trifluoropropylmethylsiloxane)                                                                                   | S | 35   | Barrer |                               |                |                |                | 201             | 1210            |                     |                                 |                                 | 6.02                             | [116]     |
| Poly(benzilmethylsiloxane)                                                                                            | S | 35   | Barrer |                               |                |                |                | 36.3            | 226             |                     |                                 |                                 | 6.23                             | [116]     |
| [(CH <sub>3</sub> ) <sub>2</sub> Si(CH <sub>2</sub> ) <sub>6</sub> Si(CH <sub>3</sub> ) <sub>2</sub> O] <sub>x</sub>  | S | 35   | Barrer |                               |                |                |                | 395             | 1310            |                     |                                 |                                 | 3.32                             | [116]     |
| [(CH <sub>3</sub> ) <sub>2</sub> SiCH <sub>2</sub> ] <sub>x</sub>                                                     | S | 35   | Barrer |                               |                |                |                | 130             | 542             |                     |                                 |                                 | 4.17                             | [116]     |
| [(CH <sub>3</sub> ) <sub>2</sub> Si-p-C <sub>6</sub> H <sub>4</sub> Si(CH <sub>3</sub> ) <sub>2</sub> O] <sub>x</sub> | S | 35   | Barrer |                               |                |                |                | 10.4            | 52.3            |                     |                                 |                                 | 5.03                             | [116]     |
| <b>Polyethers</b>                                                                                                     |   |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Pol(ethylene oxide) PEO                                                                                               | S | 25   | Barrer |                               | 0.81           | 0.07           | 0.26           | 0.19            | 9.5             |                     | 11.73                           | 135.71                          | 50.00                            | [177]     |
| Pol(ethylene oxide) PEO                                                                                               | S | 35   | Barrer |                               | 1.8            | 0.24           | 0.68           | 0.7             | 17              |                     | 9.44                            | 70.83                           | 24.29                            | [177]     |
| PPO                                                                                                                   | S | 35   | Barrer |                               | 10             | 2              |                |                 | 100             |                     | 10.00                           | 50.00                           |                                  | [254]     |
| Poly (phenylene oxide) (PPO)                                                                                          | S | room | Barrer |                               |                | 3.52           | 16.71          | 4.59            | 80.1            |                     |                                 | 22.76                           | 17.45                            | [255]     |
| PPO 20% brominated                                                                                                    | S | room | Barrer |                               |                | 3.62           | 18.24          | 3.98            | 88.69           |                     |                                 | 24.50                           | 22.28                            | [255]     |
| PPO 40% brominated                                                                                                    | S | room | Barrer |                               |                | 5.03           | 23.13          | 5.33            | 118.42          |                     |                                 | 23.54                           | 22.22                            | [255]     |
| PPO 60% brominated                                                                                                    | S | room | Barrer |                               |                | 4.88           | 24.57          | 5.7             | 139.3           |                     |                                 | 28.55                           | 24.44                            | [255]     |
| sulfonated PPO                                                                                                        | S | room | Barrer |                               |                |                | 4.1            |                 | 33.6            |                     |                                 |                                 |                                  | [255]     |
| sulfonated PPO 20% brominated                                                                                         | S | room | Barrer |                               |                | 1.53           | 9.09           | 0.67            | 39.8            |                     |                                 | 26.01                           | 59.40                            | [255]     |
| sulfonated PPO 40% brominated                                                                                         | S | room | Barrer |                               |                | 0.79           | 5.17           | 0.53            | 27.22           |                     |                                 | 34.46                           | 51.36                            | [255]     |
| sulfonated PPO 60% brominated                                                                                         | S | room | Barrer |                               |                | 2.92           | 15.96          | 3.83            | 112.5           |                     |                                 | 38.53                           | 29.37                            | [255]     |

|                                          | *      | T    | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |
|------------------------------------------|--------|------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|
|                                          |        | (°C) |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
| Polysulfones                             |        |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Bisphenol-A polysulfone (PSf)            | S      | 35   | Barrer |                               | N 14           | O 1.4          |                |                 | 5.6             |                     | 0.40                            | 4.00                            |                                  | [254]     |
| PSf                                      | S      | 30   | Barrer |                               | 12.1           | 0.8            | 1.7            | 0.4             | 6.1             |                     | 0.50                            | 7.63                            | 15.25                            | [249]     |
| PSf                                      | S      | 35   | Barrer | 10.8                          |                | 0.19           | 1.2            | 0.18            | 4.6             | 0.43                |                                 | 24.21                           | 25.56                            | [116]     |
| PSf                                      | S      | 25   | Barrer |                               |                |                |                | 5.3-8.8         | 23.7-68.7       |                     |                                 |                                 | 5.00-8.00                        | [121]     |
| PSf                                      | S      | 25   | Barrer |                               |                |                |                | 0.95-1.4        | 38.1-58.1       |                     |                                 |                                 | 40.00                            | [121]     |
| PSf                                      | S      | 25   | Barrer |                               |                |                |                | 0.36-1.06       | 13.7-35.7       |                     |                                 |                                 | 35.00                            | [121]     |
| PSf                                      | S      | 25   | Barrer |                               |                |                |                | 0.38-0.81       | 20.8-43.4       |                     |                                 |                                 | 55.00                            | [121]     |
| PSf                                      | S      | 22   | Barrer |                               | 5.8-23.8       |                |                |                 | 3.6-8.5         |                     | 0.65                            |                                 |                                  | [127]     |
| PSf aldehyde (PSFCHO)                    | S      | 22   | Barrer |                               | 6.7-8.2        |                |                |                 | 3.8-4.3         |                     | 0.55                            |                                 |                                  | [127]     |
| PSFCHO/3A zeolite                        | S      | 22   | Barrer |                               | 14.2-136       |                |                |                 | 5.0-10.7        |                     | 0.35                            |                                 |                                  | [127]     |
| PSFCHO/5A zeolite                        | S      | 22   | Barrer |                               | 32.6           |                |                |                 | 11.9            |                     | 0.37                            |                                 |                                  | [127]     |
| Polyvinylacetate/diverse inorg. supports | S      | 35   | Barrer | 10.6-20.9                     |                |                | 0.53-0.77      | 0.08-0.1        | 2.4-5.1         | 0.23                |                                 |                                 | 30.0-51.0                        | [359]     |
| Polyaryleneethers                        |        |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| 6FPT-6FBPA                               | S      | 35   | Barrer |                               | 41.9           | 2.18           | 6.96           | 1.58            | 25.29           |                     | 0.60                            | 11.60                           | 16.01                            | [172]     |
| 6FPT-BPA                                 | S      | 35   | Barrer |                               | 28.8           | 1.37           | 4.76           | 1.41            | 18.53           |                     | 0.64                            | 13.53                           | 13.14                            | [172]     |
| 6FPPy-6FBPA                              | S      | 35   | Barrer |                               | 50.1           | 2.39           | 7.9            | 1.92            | 29.46           |                     | 0.59                            | 12.33                           | 15.34                            | [172]     |
| 6FPPy-BPA                                | S      | 35   | Barrer |                               | 41.2           | 1.7            | 5.6            | 1.78            | 21.44           |                     | 0.52                            | 12.61                           | 12.04                            | [172]     |
| Polyesters                               |        |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| BisA w/High KOH conc.                    | M room | GPU  |        | 5.5                           |                |                |                | 0.545           | 12.00           | 2.18                |                                 |                                 | 22.00                            | [494]     |
| DHBP w/High KOH conc.                    | M room | GPU  |        | 2                             |                |                |                | 0.075           | 2.40            | 1.20                |                                 |                                 | 32.00                            | [494]     |
| DHDPE w/High KOH conc.                   | M room | GPU  |        | 4.3                           |                |                |                | 0.390           | 8.20            | 1.91                |                                 |                                 | 21.00                            | [494]     |
| TBBA w/High KOH conc.                    | M room | GPU  |        | 3                             |                |                |                | 0.480           | 12.00           | 4.00                |                                 |                                 | 25.00                            | [494]     |
| TCHFBA w/High KOH conc.                  | M room | GPU  |        | 69                            |                |                |                | 10.952          | 230.00          | 3.33                |                                 |                                 | 21.00                            | [494]     |
| TDP w/High KOH conc.                     | M room | GPU  |        | 4.3                           |                |                |                | 0.319           | 8.60            | 2.00                |                                 |                                 | 27.00                            | [494]     |
| TMBA w/High KOH conc.                    | M room | GPU  |        | 6.8                           |                |                |                | 0.486           | 17.00           | 2.50                |                                 |                                 | 35.00                            | [494]     |
| BisF w/Low KOH conc.                     | M room | GPU  |        | 32                            |                |                |                | 31.667          | 38.00           | 1.19                |                                 |                                 | 1.20                             | [494]     |
| BisA w/Low KOH conc.                     | M room | GPU  |        | 2.8                           |                |                |                | 0.061           | 2.00            | 0.71                |                                 |                                 | 33.00                            | [494]     |
| DHBP w/Low KOH conc.                     | M room | GPU  |        | 2                             |                |                |                | 0.034           | 1.80            | 0.90                |                                 |                                 | 53.00                            | [494]     |
| DHDPE w/Low KOH conc.                    | M room | GPU  |        | 22                            |                |                |                | 17.500          | 21.00           | 0.95                |                                 |                                 | 1.20                             | [494]     |



|                             | * | T<br>(°C) | UNITS  | PERMEANCES AND PERMEABILITIES |                |              |              |                 |                 | SELECTIVITIES       |                     |                                 |                                  | REFERENCE |
|-----------------------------|---|-----------|--------|-------------------------------|----------------|--------------|--------------|-----------------|-----------------|---------------------|---------------------|---------------------------------|----------------------------------|-----------|
|                             |   |           |        | He                            | H <sub>2</sub> | <sub>2</sub> | <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H2 | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
|                             |   |           |        |                               | N              |              | O            |                 |                 |                     |                     |                                 |                                  |           |
| Polyesters (Cont'd.)        |   |           |        |                               |                |              |              |                 |                 |                     |                     |                                 |                                  |           |
| BHPF w/High KOH conc.       | M | room      | GPU    | 1.9                           |                |              |              | 0.072           | 1.80            | 0.95                |                     |                                 | 25.00                            | [494]     |
| TBBA w/Low KOH conc.        | M | room      | GPU    | 1.9                           |                |              |              | 0.038           | 1.80            | 0.95                |                     |                                 | 48.00                            | [494]     |
| TDP w/Low KOH conc.         | M | room      | GPU    | 4.2                           |                |              |              | 0.065           | 2.00            | 0.48                |                     |                                 | 31.00                            | [494]     |
| TMBA w/Low KOH conc.        | M | room      | GPU    | 2.2                           |                |              |              | 0.067           | 1.00            | 0.45                |                     |                                 | 15.00                            | [494]     |
| SDP w/Low KOH conc.         | M | room      | GPU    | 11                            |                |              |              | 3.296           | 8.9             | 0.81                |                     |                                 | 2.70                             | [494]     |
| Polycarbonates              |   |           |        |                               |                |              |              |                 |                 |                     |                     |                                 |                                  |           |
| Bisphenol-A polycarbonate   | S | 35        | Barrer | 13                            |                | 0.38         | 1.6          | 0.36            | 6.8             | 0.52                |                     | 17.89                           | 18.89                            | [116]     |
| Polysilmethylenes           |   |           |        |                               |                |              |              |                 |                 |                     |                     |                                 |                                  |           |
| Poly(dimethyl silmethylene) | S | 35        | Barrer | 43.4                          |                | 14.5         | 37.5         | 47.4            | 191             | 4.40                |                     | 13.17                           | 4.03                             | [116]     |
| Cellulose based             |   |           |        |                               |                |              |              |                 |                 |                     |                     |                                 |                                  |           |
| Ethyl cellulose             | S | 35        | Barrer | 39.8                          |                | 3.4          | 12.4         | 6.8             | 75              | 1.88                |                     | 22.06                           | 11.03                            | [116]     |
| Cellulose acetate           | M | 25        | Barrer |                               | 3.5            |              |              |                 | 22.7            |                     | 6.49                |                                 |                                  | [492]     |
| Cellulose acetate           | M | -20       | Barrer |                               | 3.5            |              |              |                 | 22.6            |                     | 6.46                |                                 |                                  | [492]     |
| Cellulose acetate           | S | 35        | Barrer | 16                            |                | 0.15         | 0.82         | 0.15            | 4.75            | 0.30                |                     | 31.67                           | 31.67                            | [116]     |
| Polyimides                  |   |           |        |                               |                |              |              |                 |                 |                     |                     |                                 |                                  |           |
| PI-1/PTMSP                  | S | 25        | GPU    |                               | 30.1           | 4.2          | 11.9         |                 | 60.9            |                     | 2.02                | 14.50                           |                                  | [495]     |
| PI-1/PTMSP                  | S | 25        | GPU    |                               | 7.2            | 0.64         | 2.27         |                 | 12.3            |                     | 1.71                | 19.22                           |                                  | [495]     |
| PI-2/PTMSP                  | S | 25        | GPU    |                               | 2.76           | 0.28         | 0.91         |                 | 5.02            |                     | 1.82                | 17.93                           |                                  | [495]     |
| PI-3/PTMSP                  | S | 25        | GPU    |                               | 2.39           | 0.25         | 0.84         |                 | 4.35            |                     | 1.82                | 17.40                           |                                  | [495]     |
| BDCDA-MPD                   | S | 30        | Barrer |                               | 15.4           | 0.13         | 1            | 0.1             | 3.7             |                     | 0.24                | 28.46                           | 37.00                            | [143]     |
| BDCDA-DDSO                  | S | 30        | Barrer |                               | 12.9           | 0.14         | 0.93         | 0.12            | 4.2             |                     | 0.33                | 30.00                           | 35.00                            | [143]     |
| HDCDA-6F                    | S | 30        | Barrer |                               | 23.1           | 0.12         | 1.06         | 0.1             | 4.1             |                     | 0.18                | 34.17                           | 41.00                            | [143]     |
| PDCDA-6F                    | S | 30        | Barrer |                               | 25             | 0.18         | 1.2          | 0.16            | 5               |                     | 0.20                | 27.78                           | 31.25                            | [143]     |
| BDCDA-6F                    | S | 30        | Barrer |                               | 41.5           | 0.64         | 3.8          | 0.4             | 15.6            |                     | 0.38                | 24.38                           | 39.00                            | [143]     |
| PMDA-ODA                    | S | 35        | Barrer | 8                             |                | 0.1          | 0.61         | 0.059           | 2.71            | 0.34                |                     | 27.10                           | 45.93                            | [116]     |
| PMDA-MDA                    | S | 35        | Barrer | 9.4                           |                |              | 0.98         | 0.1             | 4.03            | 0.43                |                     |                                 | 40.30                            | [116]     |
| PMDA-IPDA                   | S | 35        | Barrer | 37.1                          |                |              | 7.1          | 0.9             | 26.8            | 0.72                |                     |                                 | 29.78                            | [116]     |

|                                             | * | T<br>(°C) | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |
|---------------------------------------------|---|-----------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|
|                                             |   |           |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
| Polyimides (Cont'd.)                        |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| 6FDA-ODA                                    | S | 35        | Barrer | 51.5                          | N              | O              | 4.34           | 0.38            | 23              | 0.45                |                                 |                                 | 60.53                            | [116]     |
| 6FDA-MDA                                    | S | 35        | Barrer | 50                            |                |                | 4.6            | 0.43            | 24.2            | 0.48                |                                 |                                 | 56.28                            | [116]     |
| 6FDA-IPDA                                   | S | 35        | Barrer | 71.2                          |                |                | 7.53           | 0.7             | 30              | 0.42                |                                 |                                 | 42.86                            | [116]     |
| 6FDA-DAF                                    | S | 35        | Barrer | 98.5                          |                |                | 7.85           |                 | 32.2            | 0.33                |                                 |                                 |                                  | [116]     |
| PMDA-m'pODA                                 | S | 35        | Barrer |                               | 5.92           | 0.045          | 0.31           | 0.0258          | 1.18            |                     | 0.20                            | 25.99                           | 45.74                            | [116]     |
| PMDA-p'pODA                                 | S | 35        | Barrer |                               | 10.6           | 0.145          | 0.825          | 0.0937          | 3.55            |                     | 0.33                            | 24.48                           | 37.89                            | [116]     |
| PMDA-BAPHF                                  | S | 35        | Barrer |                               | 34.3           | 0.943          | 4.98           | 0.638           | 17.6            |                     | 0.51                            | 18.66                           | 27.59                            | [116]     |
| PMDA-BATPHF                                 | S | 35        | Barrer |                               | 50.4           | 1.5            | 7.06           | 0.937           | 24.6            |                     | 0.49                            | 16.40                           | 26.25                            | [116]     |
| BPDA-p'pODA                                 | S | 35        | Barrer |                               | 3.68           |                |                | 0.0099          | 0.642           |                     | 0.17                            |                                 | 64.85                            | [116]     |
| BPDA-BAPHF                                  | S | 35        | Barrer |                               | 17.3           | 0.245          | 1.54           | 0.145           | 4.96            |                     | 0.29                            | 20.24                           | 34.21                            | [116]     |
| BPDA-BATPHF                                 | S | 35        | Barrer |                               | 30.6           | 0.563          | 3.11           | 0.279           | 9.15            |                     | 0.30                            | 16.25                           | 32.80                            | [116]     |
| BPDA-BAHF                                   | S | 35        | Barrer |                               | 59.1           | 1.39           | 7.1            | 0.78            | 27.7            |                     | 0.47                            | 19.93                           | 35.51                            | [116]     |
| BTDA-p'pODA                                 | S | 35        | Barrer |                               | 4.79           | 0.024          | 0.191          | 0.0109          | 0.625           |                     | 0.13                            | 26.48                           | 57.34                            | [116]     |
| BTDA-BAPHF                                  | S | 35        | Barrer |                               | 16.1           | 0.195          | 1.14           | 0.105           | 4.37            |                     | 0.27                            | 22.41                           | 41.62                            | [116]     |
| BTDA-BATPHF                                 | S | 35        | Barrer |                               | 24.6           | 0.37           | 2.17           | 0.189           | 6.94            |                     | 0.28                            | 18.76                           | 36.72                            | [116]     |
| BTDA-BAHF                                   | S | 35        | Barrer |                               | 30.8           | 0.45           | 2.5            | 0.226           | 10.1            |                     | 0.33                            | 22.44                           | 44.69                            | [116]     |
| 6FDA-m'pODA                                 | S | 35        | Barrer |                               | 23.7           | 0.259          | 1.57           | 0.125           | 6.11            |                     | 0.26                            | 23.59                           | 48.88                            | [116]     |
| 6FDA-APAP                                   | S | 35        | Barrer |                               | 38.2           | 0.473          | 2.89           | 0.217           | 10.7            |                     | 0.28                            | 22.62                           | 49.31                            | [116]     |
| 6FDA-p'pODA                                 | S | 35        | Barrer |                               | 40.7           | 0.733          | 3.88           | 0.341           | 16.7            |                     | 0.41                            | 22.78                           | 48.97                            | [116]     |
| 6FDA-BAPHF                                  | S | 35        | Barrer |                               | 47.4           | 0.981          | 5.13           | 0.52            | 19.1            |                     | 0.40                            | 19.47                           | 36.73                            | [116]     |
| 6FDA-BATPHF                                 | S | 35        | Barrer |                               | 55.4           | 1.3            | 6.5            | 0.703           | 22.8            |                     | 0.41                            | 17.54                           | 32.43                            | [116]     |
| 6FDA-BAHF                                   | S | 35        | Barrer |                               | 108            | 3.11           | 14.2           | 1.34            | 51.2            |                     | 0.47                            | 16.46                           | 38.21                            | [116]     |
| 6FDA-TADPO (polypyrrolone)                  | S | 35        | Barrer | 89                            |                |                | 4.34           |                 | 23              | 0.26                |                                 |                                 |                                  |           |
| 6FDA-HAB                                    | S | 35        | Barrer |                               |                |                |                | 0.071           | 7.83            |                     |                                 |                                 | 110.28                           | [149]     |
| 6FDA-durene                                 | S | 35        | Barrer | 490                           | 786            | 55.4           | 186            | 45.1            | 612             | 1.25                | 0.78                            | 11.05                           | 13.57                            | [132]     |
| 6FDA-6FpDA-8%-DABA                          | S | 30        | Barrer | 178                           |                | 10             | 36             | 6               | 84              | 0.47                |                                 | 8.40                            | 14.00                            | [132]     |
| 6FDA-6FpDA-8%-DABA:Aluminophoshate(95:5)    | S | 30        | Barrer | 148                           |                | 6.2            | 24             | 3.6             | 66              | 0.45                |                                 | 10.65                           | 18.33                            | [132]     |
| 6FDA-6FpDA-8%-DABA:Aluminophoshate(90:10),1 | S | 30        | Barrer | 94.4                          |                | 2.1            | 18.5           | 1.3             | 51              | 0.54                |                                 | 24.29                           | 39.23                            | [132]     |
| 6FDA-6FpDA-8%-DABA:Aluminophoshate(90:10),2 | S | 30        | Barrer | 67.5                          |                | 1.2            | 9.3            | 0.7             | 28.3            | 0.42                |                                 | 23.58                           | 40.43                            | [132]     |
| Matrimid 5218                               | S | 35        | Barrer |                               |                | 0.32           | 2.12           | 0.28            | 10              |                     |                                 | 31.25                           | 35.71                            | [311]     |
| Matrimid 5218                               | M | 20-25     | GPU    | 83.2                          |                |                |                | 0.57            | 28.5            | 0.34                |                                 |                                 | 50.00                            | [493]     |
| Matrimid 5218 (Fluorinated)                 | M | 20-25     | GPU    | 77                            |                |                |                | 0.2             | 18.7            | 0.24                |                                 |                                 | 93.50                            | [493]     |

|                                                                             | * | T<br>(°C) | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  |       | REFERENCE |
|-----------------------------------------------------------------------------|---|-----------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-------|-----------|
|                                                                             |   |           |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |       |           |
| <b>Polyphosphazenes</b>                                                     |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| Pendant groups: 2-(2-methoxyethoxy)ethanol : 4Methoxyphenol : 2-Allylphenol |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| 6:75:19                                                                     | S | 30        | Barrer | 4.7                           | 4.2            | 0.3            | 1.7            | 1.4             | 9.3             | 1.98                | 2.21                            | 31.00                           | 6.64                             | [264] |           |
| 23:72:5                                                                     | S | 30        | Barrer | 9.7                           | 13.4           | 1.8            | 4.8            | 3.6             | 38.9            | 4.01                | 2.90                            | 21.61                           | 10.81                            | [264] |           |
| 25:59:16                                                                    | S | 30        | Barrer | 15.1                          | 19.4           | 2.8            | 7.7            | 7.1             | 81.9            | 5.42                | 4.22                            | 29.25                           | 11.54                            | [264] |           |
| 38:46:16                                                                    | S | 30        | Barrer | 16.8                          | 25.6           | 3.9            | 10.2           | 13.9            | 107.7           | 6.41                | 4.21                            | 27.62                           | 7.75                             | [264] |           |
| 48:48:4                                                                     | S | 30        | Barrer | 16.6                          | 23.7           | 8.3            | 14.8           | 16              | 115.9           | 6.98                | 4.89                            | 13.96                           | 7.24                             | [264] |           |
| 74:24:2                                                                     | S | 30        | Barrer | 21.9                          | 28.8           | 10.2           | 18             | 19.2            | 226.7           | 10.35               | 7.87                            | 22.23                           | 11.81                            | [264] |           |
| 100:0:0                                                                     | S | 30        | Barrer | 17                            | 25             | 4              | 7              | 11              | 250             | 14.71               | 10.00                           | 62.50                           | 22.73                            | [264] |           |
| R Group                                                                     |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| PPOP                                                                        | S | 30        | Barrer |                               | 7.5            | 1.3            | 2.1            | 1.2             | 4.8             |                     | 0.64                            | 3.69                            | 4.00                             | [241] |           |
| PTBP                                                                        | S | 30        | Barrer |                               | 23             | 2.4            | 8.2            | 1.7             | 17              |                     | 0.74                            | 7.08                            | 10.00                            | [241] |           |
| PBTBP:Cl (20:80)                                                            | S | 30        | Barrer |                               | 75             | 3              | 11             | 5               | 27              |                     | 0.36                            | 9.00                            | 5.40                             | [241] |           |
| <b>Other Polymers</b>                                                       |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| Cytop                                                                       | S | 35        | Barrer | 1270                          | 620            | 34             | 130            | 11              | 300             | 0.24                | 0.48                            | 8.82                            | 27.27                            | [150] |           |
| Poly(3-(2-acetoxyethyl)thiophene) (P3AcET)                                  | S | 20        | Barrer |                               |                | 22             | 111            | 36              | 668             |                     |                                 | 30.36                           | 18.56                            | [150] |           |
| Poly(3-(2-hydroxyethyl)thiophene) (P3AcET),1                                | S | 20        | Barrer |                               |                | 5              | 63             | 14              | 281             |                     |                                 | 56.20                           | 20.07                            | [150] |           |
| Poly(3-(2-hydroxyethyl)thiophene) (P3AcET),2                                | S | 20        | Barrer |                               |                | 5              | 60             | 8               | 336             |                     |                                 | 67.20                           | 42.00                            | [150] |           |
| <b>Copolymers</b>                                                           |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| <b>Ether-Olefin</b>                                                         |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| Poly(propylene glycol) diacrylate (PPGDA) 540                               | S | 23        | Barrer |                               | 15             | 2              | 5              |                 | 30              |                     | 2.00                            | 15.00                           |                                  | [242] |           |
| PPGDA900                                                                    | S | 23        | Barrer |                               | 33             | 7              | 15             |                 | 110             |                     | 3.33                            | 15.71                           |                                  | [242] |           |
| Poly(ethylene glycol) diacrylate (PEGDA) 575                                | S | 23        | Barrer |                               | 7.2            |                | 1.8            | 0.73            | 39              |                     | 5.42                            |                                 | 53.42                            | [242] |           |
| PEGDA575 + 10 wt% fumed silica                                              | S | 23        | Barrer |                               | 5.3            |                | 1.4            | 0.6             | 32              |                     | 6.04                            |                                 | 53.33                            | [242] |           |
| PEGDA700                                                                    | S | 23        | Barrer |                               | 8.5            |                | 3              | 1               | 72              |                     | 8.47                            |                                 | 72.00                            | [242] |           |
| PEGDA700 + 10 wt% fumed silica                                              | S | 23        | Barrer |                               | 7.2            |                | 3.1            | 0.9             | 68              |                     | 9.44                            |                                 | 75.56                            | [242] |           |
| PEGDMA/alumina                                                              | S | room      | Barrer | 6.7                           | 7.5            | 1              | 1.5            | 1.1             | 19              | 2.84                | 2.53                            | 19.00                           | 17.27                            | [248] |           |
| poly(tetramethylene oxide) (PTMEO):nylon (PEA)12 (80:20)                    | S | 35        | Barrer |                               | 59.73          | 9.44           |                |                 | 221             |                     | 3.70                            | 23.40                           |                                  | [252] |           |
| PTMEO:PEA12(53:47)                                                          | S | 35        | Barrer |                               | 32.29          | 5.54           |                |                 | 113             |                     | 3.50                            | 20.40                           |                                  | [252] |           |
| PEO:PA6(55:45)                                                              | S | 35        | Barrer |                               | 12.24          | 2.33           |                |                 | 120             |                     | 9.80                            | 51.40                           |                                  | [252] |           |

|                                                                      | * T<br>(°C) | UNITS | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |       |
|----------------------------------------------------------------------|-------------|-------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|-------|
|                                                                      |             |       | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |       |
| Copolymers (Cont'd.)                                                 |             |       |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |       |
| PEO:PA12(57:43)                                                      | S           | 35    | Barrer                        |                | 8.46           | 1.17           |                 |                 | 66                  |                                 | 7.80                            | 56.40                            |           | [252] |
| Methoxy PEG acrylate (MePEGA)0/Polyacrylonitrile (PAN)               | S           | 30    | GPU                           |                |                | 0.658          |                 |                 | 6.45                |                                 |                                 | 9.80                             |           | [251] |
| MePEGA2/PAN                                                          | S           | 30    | GPU                           |                |                | 0.186          |                 |                 | 6.14                |                                 |                                 | 33.00                            |           | [251] |
| MePEGA4/PAN                                                          | S           | 30    | GPU                           |                |                | 0.159          |                 |                 | 5.4                 |                                 |                                 | 34.00                            |           | [251] |
| MePEGA6/PAN                                                          | S           | 30    | GPU                           |                |                | 0.174          |                 |                 | 5.65                |                                 |                                 | 32.40                            |           | [251] |
| MePEGA8/PAN                                                          | S           | 30    | GPU                           |                |                | 0.180          |                 |                 | 5.87                |                                 |                                 | 32.60                            |           | [251] |
| MePEGA10/PAN                                                         | S           | 30    | GPU                           |                |                | 0.206          |                 |                 | 6.36                |                                 |                                 | 30.90                            |           | [251] |
| MePEGA12/PAN                                                         | S           | 30    | GPU                           |                |                | 0.239          |                 |                 | 7.06                |                                 |                                 | 29.50                            |           | [251] |
| MePEGA14/PAN                                                         | S           | 30    | GPU                           |                |                | 0.684          |                 |                 | 7.52                |                                 |                                 | 11.00                            |           | [251] |
| MePEGA16/PAN                                                         | S           | 30    | GPU                           |                |                | 1.532          |                 |                 | 9.04                |                                 |                                 | 5.90                             |           | [251] |
| MePEGA18/PAN                                                         | S           | 30    | GPU                           |                |                | 3.570          |                 |                 | 9.64                |                                 |                                 | 2.70                             |           | [251] |
| PEGDA/Poly(ethylene glycol) methyl ether acrylate (PEGMEA)           | S           | 35    | Barrer                        |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |       |
| (100:0)                                                              |             |       |                               |                |                | 2.15           |                 |                 | 112                 |                                 |                                 | 52.00                            |           | [237] |
| PEGDA/PEGMEA(80:20)                                                  | S           | 35    | Barrer                        |                |                | 2.59           |                 |                 | 150                 |                                 |                                 | 58.00                            |           | [237] |
| PEGDA/PEGMEA(50:50)                                                  | S           | 35    | Barrer                        |                |                | 6.10           |                 |                 | 250                 |                                 |                                 | 41.00                            |           | [237] |
| PEGDA/PEGMEA(30:70)                                                  | S           | 35    | Barrer                        |                |                | 6.81           |                 |                 | 320                 |                                 |                                 | 47.00                            |           | [237] |
| PEGDA/PEGMEA(9:91)                                                   | S           | 35    | Barrer                        |                |                | 12.68          |                 |                 | 520                 |                                 |                                 | 41.00                            |           | [237] |
| PEGDA/PEGMEA(1:99)                                                   | S           | 35    | Barrer                        |                |                | 13.90          |                 |                 | 570                 |                                 |                                 | 41.00                            |           | [237] |
| PEG dimethacrylate(DM)14:PEG methyl ether methacrylate (MM)9 (100:0) | S           | 35    | Barrer                        |                |                | 1.23           |                 |                 | 65                  |                                 |                                 | 53.00                            |           | [253] |
| DM14:MM9 (90:10)                                                     | S           | 35    | Barrer                        |                |                | 1.57           |                 |                 | 85                  |                                 |                                 | 54.00                            |           | [253] |
| DM14:MM9 (70:30)                                                     | S           | 35    | Barrer                        |                |                | 2.53           |                 |                 | 129                 |                                 |                                 | 51.00                            |           | [253] |
| DM14:MM9 (50:50)                                                     | S           | 35    | Barrer                        |                |                | 3.70           |                 |                 | 185                 |                                 |                                 | 50.00                            |           | [253] |
| DM14:MM9 (30:70)                                                     | S           | 35    | Barrer                        |                |                | 5.42           |                 |                 | 260                 |                                 |                                 | 48.00                            |           | [253] |
| DM9:MM9 (90:10)                                                      | S           | 35    | Barrer                        |                |                | 0.53           |                 |                 | 28                  |                                 |                                 | 53.00                            |           | [253] |
| DM23:MM9 (90:10)                                                     | S           | 35    | Barrer                        |                |                | 3.73           |                 |                 | 194                 |                                 |                                 | 52.00                            |           | [253] |
| 2,2-bis(4-methacryloxy polyethoxy phenyl)propane (DB)30:MM9          | S           | 35    | Barrer                        |                |                | 2.61           |                 |                 | 128                 |                                 |                                 | 49.00                            |           | [253] |
| (100:0)                                                              |             |       |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |       |
| DB30:MM9 (90:10)                                                     | S           | 35    | Barrer                        |                |                | 2.80           |                 |                 | 140                 |                                 |                                 | 50.00                            |           | [253] |
| DB30:MM9 (70:30)                                                     | S           | 35    | Barrer                        |                |                | 3.63           |                 |                 | 185                 |                                 |                                 | 51.00                            |           | [253] |
| DB30:MM9 (50:50)                                                     | S           | 35    | Barrer                        |                |                | 4.81           |                 |                 | 231                 |                                 |                                 | 48.00                            |           | [253] |
| DB30:MM9 (30:70)                                                     | S           | 35    | Barrer                        |                |                | 6.55           |                 |                 | 308                 |                                 |                                 | 47.00                            |           | [253] |
| DB10:MM9 (90:10)                                                     | S           | 35    | Barrer                        |                |                | 0.25           |                 |                 | 12                  |                                 |                                 | 48.00                            |           | [253] |

|                                                                                      | * | T<br>(°C) | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  |       | REFERENCE |
|--------------------------------------------------------------------------------------|---|-----------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-------|-----------|
|                                                                                      |   |           |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |       |           |
| Copolymers (Cont'd.)                                                                 |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| Ether-Ether                                                                          |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| EO:2-(2-methoxyethoxy)ethyl glycidyl ether(EM-2):allyl glycidyl ether (AGE) (94:4:2) | S | 35        | Barrer |                               | 20             | 4              |                |                 | 250             |                     | 12.50                           | 62.50                           |                                  | [254] |           |
| Ethylene oxide (EO):propylene oxide(PO):AGE (83:16:1)                                | S | 35        | Barrer |                               | 30             | 5              |                |                 | 220             |                     | 7.33                            | 44.00                           |                                  | [254] |           |
| EO:epichlorohydrin(EP):AGE (56:39:5)                                                 | S | 35        | Barrer |                               | 30             | 6              |                |                 | 260             |                     | 8.67                            | 43.33                           |                                  | [254] |           |
| PO:EP:3-glycidoxypropyltrimethoxysilane (GPTMS) (35:63:2)                            | S | 35        | Barrer |                               | 30             | 6              |                |                 | 270             |                     | 9.00                            | 45.00                           |                                  | [254] |           |
| EO:AGE (92:8)                                                                        | S | 35        | Barrer |                               | 30             | 5              |                |                 | 350             |                     | 11.67                           | 70.00                           |                                  | [254] |           |
| EP:AGE (94:6)                                                                        | S | 35        | Barrer |                               | 20             | 6              |                |                 | 250             |                     | 12.50                           | 41.67                           |                                  | [254] |           |
| EO:GPTMS (95:5)                                                                      | S | 35        | Barrer |                               | 40             | 6              |                |                 | 380             |                     | 9.50                            | 63.33                           |                                  | [254] |           |
| EO:PO (90:10)                                                                        | S | 35        | Barrer |                               | 45             | 6              |                |                 | 400             |                     | 8.89                            | 66.67                           |                                  | [254] |           |
| EO:EM-2 (78:22)                                                                      | S | 35        | Barrer |                               | 38             | 7              |                |                 | 610             |                     | 16.05                           | 87.14                           |                                  | [254] |           |
| Ester-Ether                                                                          |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| PEG-1500:1,4-butanediol:DMT                                                          | S | 35        | Barrer |                               | 28.2           |                |                |                 | 262             |                     | 9.29                            |                                 |                                  | [176] |           |
| PEG-1500:1,4-butanediol:2,6 DMN                                                      | S | 33        | Barrer |                               | 30.6           |                |                |                 | 333             |                     | 10.88                           |                                 |                                  | [176] |           |
| PEG-1500:1,3-propanediol:DMCH                                                        | S | 33.5      | Barrer |                               | 35.8           |                |                |                 | 353             |                     | 9.86                            |                                 |                                  | [176] |           |
| PEG-1500:1,3-propanediol:SBMB                                                        | S | 36        | Barrer |                               | 23.1           |                |                |                 | 237             |                     | 10.26                           |                                 |                                  | [176] |           |
| PEG-1500:1,3-propanediol:DMBPD                                                       | S | 33        | Barrer |                               | 45.3           |                |                |                 | 322             |                     | 7.11                            |                                 |                                  | [176] |           |
| PEG-2000:1,2-ethyleneglycol:2,6-DMN                                                  | S | 33        | Barrer |                               | 5.6            |                |                |                 | 59.3            |                     | 10.59                           |                                 |                                  | [176] |           |
| Diene-Olefin                                                                         |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| Poly(butadiene-styrene)                                                              | S | 35        | Barrer | 32.9                          |                | 10.3           | 32.9           | 34.2            | 171             | 5.20                |                                 | 16.60                           | 5.00                             | [116] |           |
| Polyvinyl-butadiene                                                                  | S | 30        | Barrer |                               | 7.9            | 1.8            | 0.6            | 2.5             | 15.3            |                     | 1.94                            | 8.50                            | 6.12                             | [249] |           |
| Poly(acrylonitrile-butadiene)                                                        | M | 25        | Barrer |                               | 25.2           |                |                |                 | 63.1            |                     | 2.50                            |                                 |                                  | [492] |           |
| Ether-Urethane                                                                       |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| PU1                                                                                  | M | 35        | Barrer |                               |                |                |                | 8.1-11.2        | 77.5-55.8       |                     |                                 |                                 | 5.0-9.                           | [175] |           |
| PU3                                                                                  | M | 35        | Barrer |                               |                |                |                | 4.7-5.1         | 58.8-62.2       |                     |                                 |                                 | 12.2-12.5                        | [175] |           |
| Ether-Urethane urea                                                                  |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| PU2                                                                                  | M | 35        | Barrer |                               |                |                |                | 32.5-34.7       | 195-197         |                     |                                 |                                 | 5.6-6.0                          | [175] |           |
| PU4                                                                                  | M | 35        | Barrer |                               |                |                |                | 2.7-3.4         | 44.7-50.8       |                     |                                 |                                 | 15.0-16.6                        | [175] |           |
| Copolyimides                                                                         |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |       |           |
| Teflon AF2400 (Hyflon AD87)                                                          | S | 25        | Barrer | 3600                          | 3400           | 780            | 1600           | 600             | 3900            | 1.08                | 1.15                            | 5.00                            | 6.50                             | [496] |           |
| BTDA-TDI/MDI (80:20) (P84)                                                           | S | 25        | Barrer | 7.2                           |                | 0.024          | 0.24           | 0.0246          | 0.99            | 0.14                |                                 | 41.25                           | 40.24                            | [134] |           |

|                                                            | * | T<br>(°C) | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                     |                                 |                                  | REFERENCE |
|------------------------------------------------------------|---|-----------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------|---------------------------------|----------------------------------|-----------|
|                                                            |   |           |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H2 | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
| Copolymers (Cont'd.)                                       |   |           |        |                               |                |                |                |                 |                 |                     |                     |                                 |                                  |           |
| Hyflon AD60                                                | S | 35        | Barrer | 1360                          | 790            | 52             | 180            | 17.6            | 433             | 0.32                | 0.55                | 8.33                            | 24.60                            | [153]     |
| Hyflon AD60                                                | S | 22        | Barrer |                               |                |                |                | 27              | 460             |                     |                     |                                 | 17.04                            | [153]     |
| Hyflon AD80                                                | S | 22        | Barrer |                               |                |                |                | 125             | 1620            |                     |                     |                                 | 12.96                            | [153]     |
| Polysulfone:poly(4-vnylpyridine):Silcon Rubber (25:0.1:3)  | S | 25        | GPU    |                               | 140            | 1.3            | 8.1            | 0.77            | 40              |                     | 0.29                | 30.77                           | 51.95                            | [126]     |
| Polysulfone:poly(4-vnylpyridine):Silcon Rubber (25:0.2:3)  | S | 25        | GPU    |                               | 90             | 0.92           | 6.7            | 0.48            | 40              |                     | 0.44                | 43.48                           | 83.33                            | [126]     |
| Polysulfone:poly(4-vnylpyridine):Silcon Rubber (25:0.5:3)  | S | 25        | GPU    |                               | 74             | 0.65           | 4.9            | 0.44            | 24              |                     | 0.32                | 36.92                           | 54.55                            | [126]     |
| Polysulfone:poly(4-vnylpyridine):Silcon Rubber (25:1.0:3)  | S | 25        | GPU    |                               | 54             | 0.59           | 3.4            | 0.36            | 16              |                     | 0.30                | 27.12                           | 44.44                            | [126]     |
| Polysulfone:poly(4-vnylpyridine):Silcon Rubber (23:0.2:3)  | S | 25        | GPU    |                               | 132            | 1.3            | 8.6            | 0.87            | 51              |                     | 0.39                | 39.23                           | 58.62                            | [126]     |
| Polysulfone:poly(4-vnylpyridine):Silcon Rubber (21:0.5:3)  | S | 25        | GPU    |                               | 96             | 1.6            | 7.5            | 1.8             | 40              |                     | 0.42                | 25.00                           | 22.22                            | [126]     |
| Polysulfone:poly(4-vnylpyridine):Silcon Rubber (21:1.0:3)  | S | 25        | GPU    |                               | 81             | 1.1            | 5.3            | 0.99            | 28              |                     | 0.35                | 25.45                           | 28.28                            | [126]     |
| Polysulfone:poly(4-vnylpyridine):Silcon Rubber (21:2.0:3)  | S | 25        | GPU    |                               | 20             | 0.4            | 2.1            | 0.26            | 8.8             |                     | 0.44                | 22.00                           | 33.85                            | [126]     |
| Polysulfone:poly(4-vnylpyridine):Silcon Rubber (17:2.0:3)  | S | 25        | GPU    |                               | 54             | 3              | 5.2            | 1.9             | 16              |                     | 0.30                | 5.33                            | 8.42                             | [126]     |
| FACILITATED TRANSPORT                                      |   |           |        |                               |                |                |                |                 |                 |                     |                     |                                 |                                  |           |
| Solid-Polyelectrolyte                                      |   |           |        |                               |                |                |                |                 |                 |                     |                     |                                 |                                  |           |
| Polyvinylpyrrolidone (hydrolyzed)/polysulfone              | S | 26        | GPU    |                               |                |                |                | 0.3-3.5         | 25-800          |                     |                     |                                 |                                  | [292,293] |
| PVBTAf:poly(diallyldimethylammonium fluoride)              | M | 23        | Barrer |                               | 0.276          |                |                | 0.0417          | 7.51            |                     | 27.21               |                                 | 180.10                           | [281]     |
| Poly(vinylbenzyltrimethylammonium fluoride) (PVBTAf)       | M | 23        | GPU    |                               | 0.0751         |                |                | 0.0128          | 3.57            |                     | 47.54               |                                 | 278.91                           | [281]     |
| PVBTAf/poly(diallyldimethylammonium fluoride)              | M | 23        | GPU    |                               | 0.0443         |                |                | 0.00636         | 4.83            |                     | 109.03              |                                 | 759.43                           | [281]     |
| PVBTAf-nCesiumFluoride,n=4                                 | M | 23        | GPU    |                               | 0.20-0.3       |                |                | 0.035-0.044     | 13-25.7         |                     | 43-126              |                                 | 371-587                          | [277]     |
| PVBTAf-nCesiumFluoride-1cholineFluoride,n=3                | M | 23        | GPU    |                               |                |                |                | 0.109-0.061     | 19.31-24.39     |                     |                     |                                 | 178-400                          | [277]     |
| PDMS/poly(diallyl-dimethylammoniumfluoride) (PDADMAF)/PDMS | M | 23        | GPU    |                               | 0.016-0.023    |                |                | 0.007           | 0.87-1.83       |                     | 53-81               |                                 | 120-239                          | [279]     |
| PTMSP/PDADMAF/PTMSP                                        | M | 23        | GPU    |                               | 0.065          |                |                | 0.007           | 1.1-2.84        |                     | 17-44               |                                 | 150-380                          | [279]     |
| PTMSP/PDADMAF/microporous polymer                          | M | 23        | GPU    |                               | 0.112-0.163    |                |                | 0.023-0.025     | 1.96-2.69       |                     | 12-24               |                                 | 78-118                           | [279]     |
| PTMSP/PVBTAf/microporous polymer                           | M | 23        | GPU    |                               | 0.006          |                |                | 0.068           | 2.88-6.02       |                     | 490-10000           |                                 | 43-87                            | [279]     |
| Poly(vyvilbenzyltrimethylammonium fluoride) PVBTAf,#1      | M | 23        | GPU    |                               | 0.07-0.10      |                |                | 0.00586         | 2.88-6.02       |                     | 42-64               |                                 | 4910-10270                       | [280]     |
| Poly(vyvilbenzyltrimethylammonium fluoride) PVBTAf,#2      | M | 23        | GPU    |                               |                | 0.011          | 0.026-0.022    |                 | 7.17-9.02       |                     |                     | 629-835                         |                                  | [280]     |
| Polyvinylamine (PVAm)/poly(ether sulfone)                  | S | 25        | GPU    |                               |                |                |                | 0.221           | 1.437           |                     |                     |                                 | 6.50                             | [288]     |
| Polyvinylamine (PVAm)/polyacrylonitrile                    | S | 25        | GPU    |                               |                |                |                | 2.375           | 12.111          |                     |                     |                                 | 5.10                             | [288]     |
| Polyvinylamine (PVAm)/celullose acetate                    | S | 25        | GPU    |                               |                |                |                | 2.119           | 36.67           |                     |                     |                                 | 17.31                            | [288]     |
| Polyvinylamine (PVAm)/polysulfone                          | S | 25        | GPU    |                               |                |                |                | 0.003-0.087     | 2.33-3.1        |                     |                     |                                 | 36-778                           | [288]     |

|                                                                                    | * | T    | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |
|------------------------------------------------------------------------------------|---|------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|
|                                                                                    |   | (°C) |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
| FACILITATED TRANSPORT (Cont'd.)                                                    |   |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Immobilized liquid                                                                 |   |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Glycerol-Na <sub>2</sub> CO <sub>3</sub> in poly(vinylidene fluoride) (PVDF) (dry) | M | 23   | Barrer |                               |                |                |                |                 | 1.24            | 2.79                |                                 |                                 | 2.25                             | [272]     |
| Glycerol-Na <sub>2</sub> CO <sub>3</sub> in PVDF (100 RH)                          | M | 23   | Barrer |                               |                |                |                |                 | 1.56            | 1770                |                                 |                                 | 1135                             | [272]     |
| Glycerol carbonate in PVDF (dry)                                                   | M | 23   | Barrer |                               |                |                |                |                 | 1.1             | 100                 |                                 |                                 | 90.91                            | [274]     |
| Glycerol carbonate in PVDF (humid)                                                 | M | 23   | Barrer |                               |                |                |                |                 | 3.7             | 320                 |                                 |                                 | 86.49                            | [274]     |
| Glycerol carbonate in Celgard 2500 (dry)                                           | M | 23   | Barrer |                               |                |                |                |                 | 4.4             | 260                 |                                 |                                 | 59.09                            | [274]     |
| Glycerol carbonate in Celgard 2500 (humid)                                         | M | 23   | Barrer |                               |                |                |                |                 | 3.5             | 160                 |                                 |                                 | 45.71                            | [274]     |
| 44% dendrimer (generation 0) in glycerol in PVDF (dry)                             | M | 23   | Barrer |                               |                |                |                |                 | 7.54            | 17                  |                                 |                                 | 2.25                             | [275]     |
| 44% dendrimer (generation 0) in glycerol in PVDF (humid)                           | M | 23   | Barrer |                               |                |                |                |                 | 0.94            | 900                 |                                 |                                 | 957                              | [275]     |
| 75% dendrimer (generation 0) in glycerol in PVDF (dry)                             | M | 23   | Barrer |                               |                |                |                |                 | 860             | 5800                |                                 |                                 | 6.74                             | [275]     |
| 75% dendrimer (generation 0) in glycerol in PVDF (humid)                           | M | 23   | Barrer |                               |                |                |                |                 | 0.19            | 3200                |                                 |                                 | 16842                            | [275]     |
| Pure dendrimer in PVDF by impregnation (dry)                                       | M | 23   | Barrer |                               |                |                |                |                 | 930             | 4700                |                                 |                                 | 5.05                             | [275]     |
| Pure dendrimer in PVDF by impregnation (humid)                                     | M | 23   | Barrer |                               |                |                |                |                 | 0.17            | 3600                |                                 |                                 | 21176                            | [275]     |
| INORGANIC MEMBRANES                                                                |   |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Zeolites                                                                           |   |      |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Fau-type,1                                                                         | S | 50   | GPU    |                               |                | 717.44         |                |                 | 567.97          |                     |                                 | 0.79                            |                                  | [320]     |
| Fau-type,2                                                                         | S | 50   | GPU    |                               |                | 777.23         |                |                 | 627.76          |                     |                                 | 0.81                            |                                  | [320]     |
| Fau-type,3                                                                         | S | 50   | GPU    |                               |                | 161.42         |                |                 | 388.61          |                     |                                 | 2.41                            |                                  | [320]     |
| Fau-type,4                                                                         | S | 50   | GPU    |                               |                | 47.83          |                |                 | 358.72          |                     |                                 | 7.50                            |                                  | [320]     |
| Fau-type,5                                                                         | S | 50   | GPU    |                               |                | 14.65          |                |                 | 233.17          |                     |                                 | 15.92                           |                                  | [320]     |
| Fau-type,6                                                                         | S | 50   | GPU    |                               |                | 5.98           |                |                 | 116.58          |                     |                                 | 19.50                           |                                  | [320]     |
| Fau-type,7                                                                         | S | 50   | GPU    |                               |                | 38.86          |                |                 | 275.02          |                     |                                 | 7.08                            |                                  | [320]     |
| Fau-type,8                                                                         | S | 50   | GPU    |                               |                | 23.62          |                |                 | 230.18          |                     |                                 | 9.75                            |                                  | [320]     |
| ZSM-5                                                                              | S | 25   | GPU    |                               |                | 2.27           |                |                 | 104.63          |                     |                                 | 46.00                           |                                  | [314]     |
| ZSM-5                                                                              | S | 25   | GPU    |                               |                | 30.45          |                |                 | 1644.13         |                     |                                 | 54.00                           |                                  | [314]     |
| Na-Y                                                                               | M | 30   | GPU    |                               |                | 4.48           |                |                 | 448.40          |                     |                                 | 100.00                          |                                  | [329]     |
| K-Y                                                                                | M | 40   | GPU    |                               |                | 177.58         |                |                 | 5380.80         |                     |                                 | 30.30                           |                                  | [327]     |
| Silicalite                                                                         | M | 180  | GPU    |                               |                | 2.54           |                |                 | 50.82           |                     |                                 | 20.00                           |                                  | [334]     |

|                                               | * | T    | UNITS  | PERMEANCES AND PERMEABILITIES |                |              |              |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |
|-----------------------------------------------|---|------|--------|-------------------------------|----------------|--------------|--------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|
|                                               |   | (°C) |        | He                            | H <sub>2</sub> | <sub>2</sub> | <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
| Zeolites (Cont'd.)                            |   |      |        |                               | N              | O            |              |                 |                 |                     |                                 |                                 |                                  |           |
| Silicalite                                    | M | 30   | GPU    |                               |                | 38.05        |              |                 | 209.25          |                     |                                 | 5.50                            |                                  | [330]     |
| K-ZSM-5                                       | M | 50   | GPU    |                               |                | 67.26        |              |                 | 134.52          |                     |                                 | 2.00                            |                                  | [333]     |
| B-ZSM-5                                       | M | 27   | GPU    |                               |                | 45.08        |              |                 | 567.97          |                     |                                 | 12.60                           |                                  | [322]     |
| Na-ZSM-5                                      | M | 27   | GPU    |                               |                | 567.32       |              |                 | 7772.27         |                     |                                 | 13.70                           |                                  | [322]     |
| Sapo-34,1                                     | S | 24   | GPU    |                               |                |              |              | 12.26           | 328.83          |                     |                                 |                                 | 26.83                            | [315]     |
| Sapo-34,2                                     | S | 24   | GPU    |                               |                |              |              | 7.47            | 418.51          |                     |                                 |                                 | 56.00                            | [315]     |
| Sapo-34,3                                     | S | 24   | GPU    |                               |                |              |              | 4.78            | 418.51          |                     |                                 |                                 | 87.50                            | [315]     |
| Sapo-34                                       | M | 22   | GPU    |                               |                |              |              | 15.51           | 573.95          |                     |                                 |                                 | 37.00                            | [316]     |
| Sapo-34                                       | M | 22   | GPU    |                               |                |              |              | 17.58           | 298.93          |                     |                                 |                                 | 17.00                            | [316]     |
| Carbon-Silicalite composite                   | S | 27   | GPU    | 22.12                         |                | 0.54         | 1.91         |                 | 32.88           | 1.49                |                                 | 61.11                           |                                  | [321]     |
| Sapo-34,1                                     | S | 25   | GPU    |                               | 203.27         | 37.37        |              | 110.61          | 179.36          |                     | 0.88                            | 4.80                            | 1.62                             | [325]     |
| Sapo-34,2                                     | S | 25   | GPU    |                               | 179.36         | 32.88        |              | 50.82           | 158.43          |                     | 0.88                            | 4.82                            | 3.12                             | [325]     |
| Silicas                                       |   |      |        |                               |                |              |              |                 |                 |                     |                                 |                                 |                                  |           |
| Silica,1                                      | S | 20   | GPU    |                               |                | 0.38         |              |                 | 6.40            |                     |                                 | 17                              |                                  | [317]     |
| Silica,2                                      | S | 20   | GPU    |                               |                | 0.54         |              |                 | 3.89            |                     |                                 | 7.2                             |                                  | [317]     |
| Aminosilicate,1                               | S | 22   | GPU    |                               |                | 5.83         |              |                 | 304.82          |                     |                                 | 52.3                            |                                  | [318]     |
| Aminosilicate,2                               | S | 22   | GPU    |                               |                | 1.16         |              |                 | 72.37           |                     |                                 | 62.6                            |                                  | [318]     |
| Aminosilicate,3                               | S | 22   | GPU    |                               |                | 3.76         |              |                 | 225.88          |                     |                                 | 60.1                            |                                  | [318]     |
| Aminosilicate,4                               | S | 22   | GPU    |                               |                | 0.64         |              |                 | 63.60           |                     |                                 | 100                             |                                  | [318]     |
| Aminosilicate,5                               | S | 22   | GPU    |                               |                | 2.75         |              |                 | 212.72          |                     |                                 | 77.3                            |                                  | [318]     |
| Aminosilicate,6                               | S | 22   | GPU    |                               |                | 1.23         |              |                 | 50.44           |                     |                                 | 41                              |                                  | [318]     |
| Aminosilicate,7                               | S | 22   | GPU    |                               |                | 2.33         |              |                 | 116.23          |                     |                                 | 49.9                            |                                  | [318]     |
| Aminosilicate,8                               | S | 22   | GPU    |                               |                | 1.19         |              |                 | 83.33           |                     |                                 | 70.2                            |                                  | [318]     |
| Aminosilicate,9                               | S | 22   | GPU    |                               |                | 0.40         |              |                 | 30.70           |                     |                                 | 76.8                            |                                  | [318]     |
| Aminosilicate,10                              | S | 22   | GPU    |                               |                | 1.33         |              |                 | 70.18           |                     |                                 | 52.9                            |                                  | [318]     |
| Microporous Silica                            | S | 50   | GPU    | 8968                          | 14049          | 2989         | 419          |                 | 10164           | 1.13                | 0.72                            | 3.40                            |                                  | [318]     |
| Microporous Silica                            | S | 50   | GPU    | 5381                          | 5380           | 1494         | 50.8         |                 | 2391            | 0.44                | 0.44                            | 1.60                            |                                  | [497]     |
| Carbon Molecular Sieves (precursors)          |   |      |        |                               |                |              |              |                 |                 |                     |                                 |                                 |                                  | [497]     |
| BTDA-TDI/MDI                                  | S | 25   | GPU    | 400                           | 1250           | 120          | 400          | 80              | 2000            | 5.00                | 1.60                            | 16.67                           | 25.00                            | [308]     |
| BTDA-TDI/MDI (80:20) (P84)                    | S | 25   | Barrer | 58.5                          |                | 2.8          | 3            |                 | 3.3             | 0.06                |                                 | 1.18                            |                                  | [306]     |
| BTDA-TDI/MDI (80:20) (P84):AgSPEEK (95:5)     | S | 25   | Barrer | 161                           |                | 4.6          | 27.5         |                 | 83.3            | 0.52                |                                 | 18.11                           |                                  | [306]     |
| BTDA-TDI/MDI (80:20) (P84):AgSPEEK (90.9:9.1) | S | 25   | Barrer | 465                           |                | 10.3         | 91.8         |                 | 366             | 0.79                |                                 | 35.53                           |                                  | [306]     |



|                                                | * T  | UNITS | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |
|------------------------------------------------|------|-------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|
|                                                | (°C) |       | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
| Carbon Molecular Sieves (precursors) (Cont'd.) |      |       |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
|                                                |      |       |                               | N              | O              |                |                 |                 |                     |                                 |                                 |                                  |           |
| BTDA-TDI/MDI (80:20) (P84):AgSPEEK (83.3:16.7) | S    | 25    | Barrer                        | 361            | 3.9            | 52.7           |                 | 191             | 0.53                |                                 | 48.97                           |                                  | [306]     |
| BTDA-TDI/MDI (80:20) (P84):AgNO3 (94:6)        | S    | 25    | Barrer                        | 169            | 0.19           | 3              |                 | 12.4            | 0.07                |                                 | 65.26                           |                                  | [306]     |
| Matrimid 5218                                  | S    | 35    | Barrer                        |                | 1.65           | 22             | 0.22            | 44              |                     |                                 | 26.67                           | 200.00                           | [390]     |
| Matrimid 5218,1                                | S    | 25    | Barrer                        | 18             | 0.8            | 4.5            | 0.37            | 12              | 0.67                |                                 | 15.00                           | 32.43                            | [148]     |
| Matrimid 5218,2                                | S    | 25    | Barrer                        | 70             | 2.5            | 7.5            | 2               | 10              | 0.14                |                                 | 4.00                            | 5.00                             | [148]     |
| Matrimid 5218,3                                | S    | 25    | Barrer                        | 22             | 0.72           | 3.1            | 0.72            | 8.5             | 0.39                |                                 | 11.81                           | 11.81                            | [148]     |
| Kapton                                         | S    | 25    | Barrer                        | 9              | 0.15           | 1.15           | 0.15            | 2               | 0.22                |                                 | 13.33                           | 13.33                            | [148]     |
| PMDA-ODA-PDM (Poly(imide-siloxane:PIS),1       |      | 25    | Barrer                        | 315            | 0.3            | 8              |                 | 21              | 0.07                |                                 | 70.00                           |                                  | [304]     |
| PMDA-ODA-PDM (Poly(imide-siloxane:PIS),2       |      | 25    | Barrer                        | 3416           | 8216           | 27             | 326             | 1068            | 0.31                | 0.13                            | 39.56                           |                                  | [304]     |
| PMDA-ODA-PDM (Poly(imide-siloxane:PIS),3       |      | 25    | Barrer                        | 610            |                | 1.4            | 30              | 84              | 0.14                |                                 | 60.00                           |                                  | [304]     |
| PMDA-ODA-PDM (Poly(imide-siloxane:PIS),4       |      | 25    | Barrer                        | 4245           | 9518           | 40             | 399             | 1509            | 0.36                | 0.16                            | 37.73                           |                                  | [304]     |
| PMDA-ODA-PDM (Poly(imide-siloxane:PIS),5S      |      | 25    | Barrer                        | 1258           |                | 8.5            | 111             | 386             | 0.31                |                                 | 45.41                           |                                  | [304]     |
| PMDA-ODA-PDM (Poly(imide-siloxane:PIS),6S      |      | 25    | Barrer                        | 7319           | 12598          | 69             | 595             | 2526            | 0.35                | 0.20                            | 36.61                           |                                  | [304]     |
| BTDA-ODA (PI)-(PVP) blend (10:10:0),1          | S    | 25    | Barrer                        | 1700           |                | 47             | 500             | 1500            | 0.88                |                                 | 31.91                           |                                  | [302]     |
| BTDA-ODA (PI)-(PVP) blend (10:10:0),2          | S    | 25    | Barrer                        | 1100           |                | 9              | 140             | 350             | 0.32                |                                 | 38.89                           |                                  | [302]     |
| BTDA-ODA (PI)-(PVP) blend (10:10:5),1          | S    | 25    | Barrer                        | 2000           |                | 57             | 550             | 1800            | 0.90                |                                 | 31.58                           |                                  | [302]     |
| BTDA-ODA (PI)-(PVP) blend (10:10:5),2          | S    | 25    | Barrer                        | 1250           |                | 13             | 160             | 400             | 0.32                |                                 | 30.77                           |                                  | [302]     |
| BTDA-ODA (PI)-(PVP) blend (10:10:10),1         | S    | 25    | Barrer                        | 2200           |                | 66             | 640             | 1950            | 0.89                |                                 | 29.55                           |                                  | [302]     |
| BTDA-ODA (PI)-(PVP) blend (10:10:10),2         | S    | 25    | Barrer                        | 1700           |                | 17             | 230             | 550             | 0.32                |                                 | 32.35                           |                                  | [302]     |
| Matrimid 5218                                  | S    | 35    | Barrer                        |                | 30.3           | 227            | 10              | 611             |                     |                                 | 20.17                           | 200.00                           | [309]     |
| Matrimid 5218, MeOH pretreat                   | S    | 35    | Barrer                        |                | 15.8           | 138            | 4.8             | 423             |                     |                                 | 26.77                           | 88.13                            | [309]     |
| Matrimid 5218, EtOH pretreat                   | S    | 35    | Barrer                        |                | 6.3            | 75.4           | 1.1             | 191             |                     |                                 | 30.32                           | 173.64                           | [309]     |
| Matrimid 5218, PrOH pretreat                   | S    | 35    | Barrer                        |                | 24.1           | 204            | 6.7             | 565             |                     |                                 | 23.44                           | 84.33                            | [309]     |
| Matrimid 5218, BuOH pretreat                   | S    | 35    | Barrer                        |                | 21             | 186            | 7               | 547             |                     |                                 | 26.05                           | 78.14                            | [309]     |
| P84                                            | S    | 35    | Barrer                        |                | 17.8           | 158            | 5.6             | 499             |                     |                                 | 28.03                           | 201.00                           | [309]     |
| P84, MeOH pretreat                             | S    | 35    | Barrer                        |                | 13.6           | 132            | 3.7             | 402             |                     |                                 | 29.56                           | 108.65                           | [309]     |
| P84, EtOH pretreat                             | S    | 35    | Barrer                        |                | 9              | 101            | 2               | 278             |                     |                                 | 30.89                           | 139.00                           | [309]     |
| P84, PrOH pretreat                             | S    | 35    | Barrer                        |                | 14.6           | 144            | 3.9             | 428             |                     |                                 | 29.32                           | 109.74                           | [309]     |
| BTDA-ODA-mPDA-DBA (10:8:2:0)                   | S    | 25    | Barrer                        | 2763           |                | 24             | 256             | 829             | 0.30                |                                 | 34.54                           |                                  | [250]     |
| BTDA-ODA-mPDA-DBA (10:8:0:2)                   | S    | 25    | Barrer                        | 3208           |                | 49             | 501             | 1674            | 0.52                |                                 | 34.16                           |                                  | [250]     |
| BTDA-ODA-mPDA-DBA (10:8:0:5)                   | S    | 25    | Barrer                        | 4193           |                | 83             | 707             | 2863            | 0.68                |                                 | 34.49                           |                                  | [250]     |

|                                                                                               | * | T<br>(°C) | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  |           | REFERENCE |
|-----------------------------------------------------------------------------------------------|---|-----------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|-----------|
|                                                                                               |   |           |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |           |
| Carbon Molecular Sieves (precursors) (Cont'd.)                                                |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |           |
| CMSM,1                                                                                        | S | 20        | GPU    |                               | N 2160.00      | O 10.40        | 86.27          |                 | 486.67          |                     | 0.23                            | 46.79                           |                                  | [297,298] |           |
| CMSM,2                                                                                        | S | 20        | GPU    |                               | 1680.00        | 7.47           | 63.33          |                 | 288.00          |                     | 0.17                            | 38.57                           |                                  | [297,298] |           |
| CMSM,3                                                                                        | S | 20        | GPU    |                               | 2093.33        | 13.33          | 141.33         |                 | 792.00          |                     | 0.38                            | 59.40                           |                                  | [297,298] |           |
| CMSM,4                                                                                        | S | 20        | GPU    |                               | 1893.33        | 8.13           | 97.33          |                 | 530.67          |                     | 0.28                            | 65.25                           |                                  | [297,298] |           |
| CMSM,5                                                                                        | S | 20        | GPU    |                               | 1130.67        | 4.40           | 58.53          |                 | 317.33          |                     | 0.28                            | 72.12                           |                                  | [297,298] |           |
| Surface Flow (adsorption Selective membranes)                                                 |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |           |
| Carbonized latex-graphite, MI                                                                 | M | 25        | Barrer |                               |                |                |                |                 | 350             | 1130                |                                 |                                 | 3.23                             | [492]     |           |
| Carbonized latex-graphite, MI                                                                 | M | -20       | Barrer |                               |                |                |                |                 | 240             | 1080                |                                 |                                 | 4.50                             | [492]     |           |
| Carbonized latex-graphite, MII                                                                | M | 25        | Barrer |                               |                |                |                |                 | 250             | 1800                |                                 |                                 | 7.20                             | [492]     |           |
| Carbonized latex-graphite, MII                                                                | M | -15       | Barrer |                               |                |                |                |                 | 58              | 1500                |                                 |                                 | 25.86                            | [492]     |           |
| Carbonized latex-graphite, MIIIA                                                              | S | 22        | Barrer | 22                            | 150            |                |                | 335             | 631             | 28.68               | 4.21                            |                                 | 1.88                             | [492]     |           |
| Carbonized latex-graphite, MIIIB                                                              | S | 22        | Barrer | 31                            | 129            |                |                | 663             | 1054            | 34.00               | 8.17                            |                                 | 1.59                             | [492]     |           |
| Carbonized latex-graphite, MIIIC                                                              | S | 22        | Barrer | 28                            | 145            |                |                | 551             | 973             | 34.75               | 6.71                            |                                 | 1.77                             | [492]     |           |
| Carbonized phenolic resin                                                                     | S | 25        | GPU    | 239                           |                | 329            | 448            | 836             | 1195            | 5.00                |                                 | 3.64                            | 1.43                             | [356]     |           |
| HDFS in Vycor                                                                                 | S | 20        | GPU    | 1.01                          | 0.52           | 0.34           |                | 0.56            | 2.1             | 2.07                | 4.03                            | 6.12                            | 3.74                             | [351]     |           |
| ODS in g-Alumina                                                                              | S | 20        | GPU    |                               | 38             | 11             |                | 17              | 60              |                     | 1.58                            | 5.45                            | 3.53                             | [358]     |           |
| C <sub>n</sub> H <sub>2n+1</sub> (CH <sub>3</sub> ) <sub>2</sub> SiCl in porous glass, n = 18 | S | 25        | GPU    | 0.051                         |                | 0.028          |                |                 | 0.284           | 5.59                |                                 | 10.00                           |                                  | [262]     |           |
| C <sub>n</sub> H <sub>2n+1</sub> (CH <sub>3</sub> ) <sub>2</sub> SiCl in porous glass, n = 8  | S | 25        | GPU    | 0.358                         |                | 0.299          |                |                 | 0.538           | 1.50                |                                 | 1.80                            |                                  | [262]     |           |
| C <sub>n</sub> H <sub>2n+1</sub> (CH <sub>3</sub> ) <sub>2</sub> SiCl in porous glass, n = 3  | S | 25        | GPU    | 3.58                          |                | 2.09           |                |                 | 2.69            | 0.75                |                                 | 1.29                            |                                  | [262]     |           |
| C <sub>n</sub> H <sub>2n+1</sub> (CH <sub>3</sub> ) <sub>2</sub> SiCl in porous glass, n = 1  | S | 25        | GPU    | 5.38                          |                | 2.99           |                |                 | 3.88            | 0.72                |                                 | 1.30                            |                                  | [262]     |           |
| Novolak-phenolic resin-N-methyl-2-pyrrolidone,1                                               | S | 25        | GPU    |                               | 151.86         | 39.04          |                | 68.51           | 335.70          |                     | 2.21                            | 8.60                            | 4.90                             | [356]     |           |
| Novolak-phenolic resin-N-methyl-2-pyrrolidone,1                                               | S | 25        | GPU    |                               | 216.73         | 311.05         |                | 677.00          | 1150.89         |                     | 5.31                            | 3.70                            | 1.70                             | [356]     |           |
| Novolak-phenolic resin-N-methyl-2-pyrrolidone,1                                               | S | 25        | GPU    |                               | 70.25          | 47.10          |                | 150.02          | 405.05          |                     | 5.77                            | 8.60                            | 2.70                             | [356]     |           |
| Novolak-phenolic resin-N-methyl-2-pyrrolidone,1                                               | S | 25        | GPU    |                               | 248.11         | 83.93          |                | 134.64          | 646.29          |                     | 2.60                            | 7.70                            | 4.80                             | [356]     |           |
| Novolak-phenolic resin-N-methyl-2-pyrrolidone,1                                               | S | 25        | GPU    |                               | 322.55         | 55.98          |                | 48.87           | 615.80          |                     | 1.91                            | 11                              | 12.6                             | [356]     |           |
| Zeolite-T                                                                                     | S | 35        | GPU    | 10.46                         | 23.91          | 5.38           |                | 0.42            | 89.68           | 8.57                | 3.75                            | 16.67                           | 214.29                           | [352,353] |           |
| DDR-zeolite                                                                                   | S | 18        | GPU    | 29.89                         | 119.57         | 14.95          | 26.90          | 0.34            | 239.15          | 8.00                | 2.00                            | 16.00                           | 703.37                           | [355]     |           |
| Sapo-34,3                                                                                     | S | 25        | GPU    | 119.57                        | 248.11         | 65.77          |                | 20.93           | 448.40          | 3.75                | 1.81                            | 6.82                            | 21.43                            | [325]     |           |
| SSZ-13 Zeolite,1                                                                              | S | 25        | GPU    |                               | 403.56         | 89.68          |                | 44.84           | 478.29          |                     | 1.19                            | 5.33                            | 10.67                            | [357]     |           |
| SSZ-13 Zeolite,2                                                                              | S | 25        | GPU    |                               | 388.61         | 134.52         |                | 80.71           | 627.76          |                     | 1.62                            | 4.67                            | 7.78                             | [357]     |           |
| SSZ-13 Zeolite,3                                                                              | S | 25        | GPU    |                               | 553.03         | 107.62         |                | 113.59          | 702.49          |                     | 1.27                            | 6.53                            | 6.18                             | [357]     |           |

|                                                               | * | T<br>(°C) | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |
|---------------------------------------------------------------|---|-----------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|
|                                                               |   |           |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
| Surface Flow (adsorption Selective membranes) (Cont'd.)       |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| SSZ-13 Zeolite,4                                              | S | 25        | GPU    |                               | 463.35         | 134.52         |                | 89.68           | 553.03          |                     | 1.19                            | 4.11                            | 6.17                             | [357]     |
| SSZ-13 Zeolite,5                                              | S | 25        | GPU    |                               | 463.35         | 134.52         |                | 74.73           | 702.49          |                     | 1.52                            | 5.22                            | 9.40                             | [357]     |
| HYBRID ORGANIC-INORGANIC MEMBRANES                            |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Poly(amide-6-b ethylene oxide)(PEBAX)-Silica                  |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  | [207]     |
| PEBAX:Silica(100:0)                                           | S | 25        | Barrer | 18.6                          |                | 1.71           | 5.84           |                 | 122             | 6.56                |                                 | 71.35                           |                                  | [207]     |
| PEBAX:Silica(90:10)                                           | S | 25        | Barrer | 21.4                          |                | 2.13           | 6.82           |                 | 154             | 7.20                |                                 | 72.30                           |                                  | [207]     |
| PEBAX:Silica(81:19)                                           | S | 25        | Barrer | 25.5                          |                | 1.73           | 8.74           |                 | 205             | 8.04                |                                 | 118.50                          |                                  | [207]     |
| PEBAX:Silica(73:27)                                           | S | 25        | Barrer | 32.2                          |                | 3.52           | 11.3           |                 | 277             | 8.60                |                                 | 78.69                           |                                  | [207]     |
| PDMS-pentaerythritol triacrylate (PETA)-Silica                |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  | [364]     |
| PDMS:PETA:Silica (11:89:0)                                    | S | 23        | Barrer |                               | 479            | 206            | 441            | 648             | 1154            |                     | 2.41                            | 5.60                            | 1.78                             | [364]     |
| PDMS:PETA:Silica (10:85:5)                                    | S | 23        | Barrer |                               | 647            | 381            | 665            | 1246            | 4511            |                     | 6.97                            | 11.84                           | 3.62                             | [364]     |
| PDMS:PETA:Silica (10:80:10)                                   | S | 23        | Barrer |                               | 285            | 156            | 341            | 466             | 1422            |                     | 4.99                            | 9.12                            | 3.05                             | [364]     |
| Poly(ethylene glycol)(PEG)-Silica                             |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  | [363]     |
| PEG600:Silica                                                 | S | 30        | Barrer |                               |                | 0.52           | 1.51           | 1.48            | 23.92           |                     |                                 | 46.00                           | 16.16                            | [363]     |
| PEG1000:Silica                                                | S | 30        | Barrer |                               |                | 1.16           | 2.68           | 3.12            | 49.3            |                     |                                 | 42.50                           | 15.80                            | [363]     |
| PEG2000:Silica                                                | S | 30        | Barrer |                               |                | 2.46           | 5.56           | 6.01            | 94.2            |                     |                                 | 38.29                           | 15.67                            | [363]     |
| Poly(propylene glycol)(PPG)-Silica                            |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  | [363]     |
| PPG600:Silica                                                 | S | 30        | Barrer |                               |                | 1.69           | 5              | 4.99            | 33.91           |                     |                                 | 20.07                           | 6.80                             | [363]     |
| PPG1000:Silica                                                | S | 30        | Barrer |                               |                | 2.54           | 6.73           | 7.3             | 48.37           |                     |                                 | 19.04                           | 6.63                             | [363]     |
| PPG2000:Silica                                                | S | 30        | Barrer |                               |                | 3.81           | 9.24           | 10.95           | 72.26           |                     |                                 | 18.97                           | 6.60                             | [363]     |
| (PEG-PPG-PEG) (PEPG)-Silica                                   |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  | [363]     |
| PEPG2000:Silica                                               | S | 30        | Barrer |                               |                | 3.2            | 8.1            | 10.1            | 83.64           |                     |                                 | 26.14                           | 8.28                             | [363]     |
| PEPG2700:Silica                                               | S | 30        | Barrer |                               |                | 4.39           | 10.6           | 13.6            | 110             |                     |                                 | 25.06                           | 8.09                             | [363]     |
| PEPG3300:Silica                                               | S | 30        | Barrer |                               |                | 6.59           | 15.76          | 20.18           | 132.3           |                     |                                 | 20.08                           | 6.56                             | [363]     |
| Acrylonitrile-butadiene-styrene (ABS)/Activated carbon 1(AC1) | S | 20        | Barrer |                               |                |                |                | 0.162-0.315     | 4.31-10.81      |                     |                                 |                                 | 26.6-34.3                        | [393]     |
| ABS/AC2                                                       | S | 20        | Barrer |                               |                |                |                | 0.264-0.406     | 7.49-20.50      |                     |                                 |                                 | 28.4-50.5                        | [393]     |
| 6FDA-TAPOB hyperbranched polyimide (HBPI)-Silica              |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  | [206]     |
| HBPI-Silica(100:0)                                            | S | 25        | Barrer |                               |                | 0.22           | 1.5            | 0.098           | 7.4             |                     |                                 | 26.67                           | 75.51                            | [206]     |
| HBPI-Silica(90:10)                                            | S | 25        | Barrer |                               |                | 0.31           | 2              | 0.092           | 10              |                     |                                 | 32.26                           | 108.70                           | [206]     |
| HBPI-Silica(80:20)                                            | S | 25        | Barrer |                               |                | 0.32           | 2.1            | 0.08            | 12              |                     |                                 | 37.50                           | 150.00                           | [206]     |
| HBPI-Silica(100:30)                                           | S | 25        | Barrer |                               |                | 0.46           | 3              | 0.08            | 19              |                     |                                 | 41.30                           | 237.50                           | [206]     |

|                                             | * | T<br>(°C) | UNITS  | PERMEANCES AND PERMEABILITIES |                |                |                |                 |                 | SELECTIVITIES       |                                 |                                 |                                  | REFERENCE |
|---------------------------------------------|---|-----------|--------|-------------------------------|----------------|----------------|----------------|-----------------|-----------------|---------------------|---------------------------------|---------------------------------|----------------------------------|-----------|
|                                             |   |           |        | He                            | H <sub>2</sub> | N <sub>2</sub> | O <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO <sub>2</sub> /He | CO <sub>2</sub> /H <sub>2</sub> | CO <sub>2</sub> /N <sub>2</sub> | CO <sub>2</sub> /CH <sub>4</sub> |           |
| HYBRID ORGANIC-INORGANIC MEMBRANES (Cont’)  |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Polysulfone (PSF)-Carbon Black(CB)          |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
|                                             | S | 25        | GPU    |                               | 2.05           | 12.21          |                | 2.1             | 86.12           |                     |                                 | 26.67                           | 41.01                            | [125]     |
| PSF:CB (100:0)                              | S | 25        | GPU    |                               | 1.94           | 12.65          |                | 2.16            | 76.25           |                     |                                 | 39.30                           | 35.30                            | [125]     |
| PSF:CB (98:2)                               | S | 25        | GPU    |                               | 2.81           | 12.78          |                | 4.77            | 68.72           |                     |                                 | 24.46                           | 14.41                            | [125]     |
| PSF:CB (95:5)                               | S | 25        | GPU    |                               | 2.25           | 11.89          |                | 2.44            | 75.13           |                     |                                 | 33.39                           | 30.79                            | [125]     |
| PSF:CB (90:10)                              | S | 25        | GPU    |                               | 3.95           | 12.63          |                | 5.52            | 57.12           |                     |                                 | 26.67                           | 10.35                            | [125]     |
| PSF-Vapor grown carbon fibers (VGVF)        | S | 25        | GPU    |                               | 3.17           | 14.7           |                | 3.67            | 89.56           |                     |                                 | 28.25                           | 24.40                            | [125]     |
| PSF-Titania                                 |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Matrimid® 5218-Carbon molecular sieve (CMS) |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Matrimid® 5218:CMS (100:0)                  | S | 35        | Barrer |                               | 0.32           | 2.12           |                | 0.28            | 10              |                     |                                 | 26.67                           | 35.71                            | [390,391] |
| Matrimid® 5218:CMS (83:17)                  | S | 35        | Barrer |                               | 0.29           | 2.08           |                | 0.23            | 10.3            |                     |                                 | 35.52                           | 44.78                            | [390,391] |
| Matrimid® 5218:CMS (81:19)                  | S | 35        | Barrer |                               | 0.35           | 2.41           |                | 0.23            | 10.6            |                     |                                 | 30.29                           | 46.09                            | [390,391] |
| Matrimid® 5218:CMS (67:33)                  | S | 35        | Barrer |                               | 0.38           | 2.7            |                | 0.24            | 11.5            |                     |                                 | 30.26                           | 47.92                            | [390,391] |
| Matrimid® 5218:CMS (64:36)                  | S | 35        | Barrer |                               | 0.38           | 3              |                | 0.24            | 12.6            |                     |                                 | 33.16                           | 52.50                            | [390,391] |
| Matrimid® 5218:CMS (0:100)                  | S | 35        | Barrer |                               | 1.65           | 22             |                | 0.22            | 44              |                     |                                 | 26.67                           | 200.00                           | [390,391] |
| Ultem® 1000-Carbon molecular sieve (CMS)    |   |           |        |                               |                |                |                |                 |                 |                     |                                 |                                 |                                  |           |
| Ultem® 1000:CMS (100:0)                     | S | 35        | Barrer |                               | 0.052          | 0.38           |                | 0.037           | 1.45            |                     |                                 | 27.88                           | 39.19                            | [390,391] |
| Ultem® 1000:CMS (84:16)                     | S | 35        | Barrer |                               | 0.071          | 0.56           |                | 0.058           | 2.51            |                     |                                 | 35.35                           | 43.28                            | [390,391] |
| Ultem® 1000:CMS (80:20)                     | S | 35        | Barrer |                               | 0.09           | 0.71           |                | 0.06            | 2.9             |                     |                                 | 26.67                           | 48.33                            | [390,391] |
| Ultem® 1000:CMS (65:35)                     | S | 35        | Barrer |                               | 0.136          | 1.09           |                | 0.083           | 4.48            |                     |                                 | 32.94                           | 53.98                            | [390,391] |
| Ultem® 1000:CMS (0:100)                     | S | 35        | Barrer |                               | 1.65           | 22             |                | 0.22            | 44              |                     |                                 | 26.67                           | 200.00                           | [390,391] |

\* S: Data based on single gas experiments; M: Data based on mix-gas experiments; Barrer:  $10^{-10} \text{ cm}^3 \text{ (STP) cm cm}^{-2} \text{ s}^{-1} \text{ cmHg}^{-1}$ ; GPU:  $10^{-6} \text{ cm}^3 \text{ (STP) cm}^{-2} \text{ s}^{-1} \text{ cmHg}^{-1}$ . To convert values in GPU into  $\text{mol m}^{-2} \text{ s}^{-1} \text{ Pa}^{-1}$ , multiply the value by  $5.95 \cdot 10^{-4}$ . Cells in gray show materials with preference of CO<sub>2</sub> over H<sub>2</sub>.

Table 13. Trans-membrane flux (mmol/m<sup>2</sup>s) for different capillary hollow fiber membrane contactors reported in the literature. The parameters reported include number, internal diameter, length and surface area of the fibers (i.e., No, d<sub>i</sub>, L, a), concentration of absorbent (wt%), and feed temperature, pressure, concentration and flow (i.e., T<sub>F</sub>, P<sub>F</sub>, y<sub>CO2</sub>, F<sub>CO2</sub>).

| Authors | Membrane  |      |                      |         |                                     | Solvent (Conc., loading <sup>a</sup> ) | Conditions             |                         |                                      |                          |                            | CO <sub>2</sub>                 |             | Stability <sup>b</sup> |
|---------|-----------|------|----------------------|---------|-------------------------------------|----------------------------------------|------------------------|-------------------------|--------------------------------------|--------------------------|----------------------------|---------------------------------|-------------|------------------------|
|         | Mat.      | No   | d <sub>i</sub><br>mm | L<br>cm | a<br>m <sup>2</sup> /m <sup>3</sup> |                                        | T <sub>F</sub><br>(°C) | P <sub>F</sub><br>(kPa) | y <sub>CO2</sub><br>(%) <sup>e</sup> | V <sub>L</sub><br>(cm/s) | F <sub>CO2</sub><br>(SLPM) | Flux<br>(mmol/m <sup>2</sup> s) | Eff.<br>(%) |                        |
| [418]   | PTFE      | 28   | 3.00                 | 43.0    | 416                                 | MEA(30wt%)                             | 40                     | NA                      | 1.5*                                 | 1.68                     | NA <sup>c</sup>            | 1.910                           | NA          | NA                     |
|         |           |      |                      |         |                                     |                                        | 40                     | NA                      | 7.5*                                 | 1.68                     | NA                         | 3.360                           | NA          |                        |
|         |           |      |                      |         |                                     | MEA(30wt%, 0.150)                      | 40                     | NA                      | 1.0*                                 | 1.68                     | NA                         | 1.180                           | NA          |                        |
|         |           |      |                      |         |                                     |                                        | 40                     | NA                      | 9.0*                                 | 1.68                     | NA                         | 2.450                           | NA          |                        |
|         |           |      |                      |         |                                     | MEA(30wt%, 0.068)                      | 40                     | NA                      | 5.0*                                 | 0.84                     | NA                         | 2.270                           | NA          |                        |
|         |           |      |                      |         |                                     |                                        | 40                     | NA                      | 5.0*                                 | 3.37                     | NA                         | 2.910                           | NA          |                        |
|         |           |      |                      |         |                                     | MEA(30wt%, 0.043)                      | 25                     | NA                      | 5.0*                                 | 1.68                     | NA                         | 3.180                           | NA          |                        |
|         |           |      |                      |         |                                     |                                        | 55                     | NA                      | 5.0*                                 | 1.68                     | NA                         | 2.000                           | NA          |                        |
| [444]   | PVDF 2050 | 0.83 | 52.0                 | 1542    |                                     | MEA(5wt%)+TEA(5wt%)                    | 40                     | NA                      | 11.0                                 | 0.90                     | 2.200                      | 0.580                           | 99          | +80 h                  |
|         |           |      |                      |         |                                     |                                        | 40                     | NA                      | 11.0                                 | 0.90                     | 3.300                      | 0.760                           | 86          |                        |
|         |           |      |                      |         |                                     |                                        | 40                     | NA                      | 11.0                                 | 2.70                     | 2.750                      | 0.730                           | 100         |                        |
|         |           |      |                      |         |                                     |                                        | 40                     | NA                      | 11.0                                 | 2.70                     | 4.400                      | 1.120                           | 95          |                        |
| [442]   | PVDF 130  | 0.83 | 23.0                 | 1391    |                                     | Piperazine (PZ) (5wt%)                 | 40                     | NA                      | 20.0                                 | 0.47                     | 0.010                      | 0.100                           | 100         | <2 h                   |
|         |           |      |                      |         |                                     |                                        | 40                     | NA                      | 20.0                                 | 0.47                     | 0.070                      | 0.230                           | 35          |                        |
|         |           |      |                      |         |                                     | TEA(5wt%)                              | 40                     | NA                      | 20.0                                 | 0.47                     | 0.070                      | 0.670                           | 100         |                        |
|         |           |      |                      |         |                                     |                                        | 40                     | NA                      | 20.0                                 | 0.47                     | 0.090                      | 0.750                           | 88          |                        |
|         |           |      |                      |         |                                     | PZ(5wt%)+TEA(5wt%)                     | 40                     | NA                      | 20.0                                 | 0.47                     | 0.080                      | 0.760                           | 100         |                        |
|         |           |      |                      |         |                                     |                                        | 40                     | NA                      | 20.0                                 | 0.47                     | 0.120                      | 1.090                           | 95          |                        |
| [429]   | PP        | 4900 | 0.60                 | 10.0    | 924                                 | Pure water                             | 22                     | 137.8                   | 30.0                                 | 1.20                     | 4.212                      | 0.044                           | 1           | NA                     |
|         |           |      |                      |         |                                     |                                        | 22                     | 137.8                   | 30.0                                 | 8.30                     | 4.212                      | 0.212                           | 6           |                        |
|         |           |      |                      |         |                                     |                                        | 22                     | 115.5                   | 70.0                                 | 1.20                     | 14.190                     | 0.313                           | 3           |                        |
|         |           |      |                      |         |                                     |                                        | 22                     | 115.5                   | 70.0                                 | 8.30                     | 14.190                     | 0.765                           | 7           |                        |
|         |           |      |                      |         |                                     |                                        | 22                     | 116.5                   | 2.5                                  | 6.60                     | 0.017                      | 0.030                           | 17          |                        |
|         | PP        | 400  | 0.60                 | 10.0    | 471                                 | Pure water                             | 20                     | 116.5                   | 2.5                                  | 9.60                     | 0.017                      | 0.034                           | 19          | NA                     |
|         |           |      |                      |         |                                     |                                        | 22                     | 119.6                   | 30.0                                 | 1.00                     | 0.125                      | 0.086                           | 7           |                        |
|         |           |      |                      |         |                                     |                                        | 22                     | 119.6                   | 30.0                                 | 10.00                    | 0.125                      | 0.255                           | 20          |                        |
|         |           |      |                      |         |                                     |                                        | 22                     | 144.9                   | 87.5                                 | 0.50                     | 0.417                      | 0.354                           | 8           |                        |
|         |           |      |                      |         |                                     |                                        | 22                     | 144.9                   | 87.5                                 | 8.50                     | 0.417                      | 1.133                           | 27          |                        |

| Authors | Membrane |     |                      |         |                                     | Solvent (Conc., loading <sup>a</sup> ) | Conditions             |                         |                                      |                          |                            | CO <sub>2</sub>                 |             | Stability <sup>b</sup> |
|---------|----------|-----|----------------------|---------|-------------------------------------|----------------------------------------|------------------------|-------------------------|--------------------------------------|--------------------------|----------------------------|---------------------------------|-------------|------------------------|
|         | Mat.     | No  | d <sub>i</sub><br>mm | L<br>cm | a<br>m <sup>2</sup> /m <sup>3</sup> |                                        | T <sub>F</sub><br>(°C) | P <sub>F</sub><br>(kPa) | y <sub>CO2</sub><br>(%) <sup>c</sup> | V <sub>L</sub><br>(cm/s) | F <sub>CO2</sub><br>(SLPM) | Flux<br>(mmol/m <sup>2</sup> s) | Eff.<br>(%) |                        |
| [443]   | PVDF     | 139 | 0.83                 | 23.0    | 1488                                | MEA(5wt%)                              | 40                     | NA                      | 25.0                                 | 0.27                     | 0.110                      | 0.530                           | 55          | NA                     |
|         | PTFE     | 70  | 1.00                 | 23.0    | 1340                                | MEA(5wt%)                              | 40                     | NA                      | 25.0                                 | 0.55                     | 0.110                      | 0.950                           | 100         | NA                     |
| [422]   | PP       | 1   | 0.60                 | 15.0    | -                                   | Propylene Carbonate                    | 40                     | NA                      | 25.0                                 | 0.36                     | 0.045                      | 0.450                           | 66          | Short                  |
|         |          |     |                      |         |                                     |                                        | 40                     | NA                      | 25.0                                 | 0.76                     | 0.045                      | 0.680                           | 100         |                        |
|         |          |     |                      |         |                                     |                                        | 20                     | 172.3                   | 100.0                                | 2.50                     | NA                         | 1.700                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 20                     | 172.3                   | 100.0                                | 9.00                     | NA                         | 3.000                           | NA          |                        |
|         | PP       | 1   | 0.60                 | 13.0    | -                                   | Propylene Carbonate                    | 20                     | 202.7                   | 100.0                                | 4.00                     | NA                         | 2.700                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 20                     | 202.7                   | 100.0                                | 14.50                    | NA                         | 4.200                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 425.6                   | 100.0                                | 0.50                     | NA                         | 2.200                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 425.6                   | 100.0                                | 9.50                     | NA                         | 9.300                           | NA          |                        |
|         | PP       | 1   | 0.60                 | 11.5    | -                                   | Propylene Carbonate                    | 25                     | 810.6                   | 100.0                                | 2.00                     | NA                         | 9.200                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 810.6                   | 100.0                                | 8.50                     | NA                         | 17.000                          | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 1013.3                  | 100.0                                | 1.50                     | NA                         | 11.000                          | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 1013.3                  | 100.0                                | 9.00                     | NA                         | 24.000                          | NA          |                        |
|         | PP       | 1   | 0.60                 | 13.5    | -                                   | Propylene Carbonate                    | 25                     | 1519.9                  | 100.0                                | 3.00                     | NA                         | 20.000                          | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 1519.9                  | 100.0                                | 12.00                    | NA                         | 38.000                          | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 2026.5                  | 100.0                                | 3.00                     | NA                         | 25.000                          | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 2026.5                  | 100.0                                | 13.00                    | NA                         | 56.000                          | NA          |                        |
|         | PP       | 1   | 0.60                 | 13.0    | -                                   | Propylene Carbonate                    | 25                     | 405.6                   | 10.3                                 | 2.00                     | NA                         | 0.500                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 405.6                   | 10.3                                 | 10.00                    | NA                         | 0.950                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 405.6                   | 22.5                                 | 2.00                     | NA                         | 1.000                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 405.6                   | 22.5                                 | 8.00                     | NA                         | 2.050                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 810.6                   | 8.6                                  | 2.00                     | NA                         | 0.800                           | NA          |                        |
|         |          |     |                      |         |                                     |                                        | 25                     | 810.6                   | 8.6                                  | 10.00                    | NA                         | 1.500                           | NA          |                        |
| 24      |          |     |                      |         |                                     |                                        | 101.3                  | 32.6                    | 1.00                                 | 14.90                    | 0.540                      | NA                              |             |                        |
| 24      |          |     |                      |         |                                     |                                        | 101.3                  | 32.6                    | 10.00                                | 14.90                    | 0.760                      | NA                              |             |                        |
| [422]   | PP       | 400 | 0.60                 | 10.0    | 471                                 | K <sub>2</sub> CO <sub>3</sub> (0.25M) | 24                     | 101.3                   | 32.6                                 | 1.00                     | 19.50                      | 0.640                           | NA          |                        |
|         |          |     |                      |         |                                     | K <sub>2</sub> CO <sub>3</sub> (0.50M) | 24                     | 101.3                   | 32.6                                 | 1.00                     | 19.50                      | 0.640                           | NA          |                        |
|         |          |     |                      |         |                                     | K <sub>2</sub> CO <sub>3</sub> (0.25M) | 24                     | 101.3                   | 32.6                                 | 1.00                     | 19.50                      | 0.640                           | NA          |                        |
|         |          |     |                      |         |                                     | K <sub>2</sub> CO <sub>3</sub> (0.50M) | 24                     | 101.3                   | 32.6                                 | 1.00                     | 19.50                      | 0.920                           | NA          |                        |

<sup>a</sup> Loading is shown in some results and is evaluated as mol of CO<sub>2</sub> absorbed per mol of active absorbent (water excluded).

<sup>b</sup> NA: not available or cannot be elucidated from data provided.

Table 14. Typical molar fraction concentrations in each of the streams listed in Figures 4 to 14.

| Process <sup>a</sup> | Stream | N <sub>2</sub> | O <sub>2</sub> | H <sub>2</sub> | CH <sub>4</sub> | CO <sub>2</sub> | CO    | H <sub>2</sub> S | SO <sub>2</sub> | C2+ | H <sub>2</sub> O | Other Emissions*         | Temp (°C) | Press (atm) |
|----------------------|--------|----------------|----------------|----------------|-----------------|-----------------|-------|------------------|-----------------|-----|------------------|--------------------------|-----------|-------------|
| 1                    | 1      | 76             | 5              | -              | -               | 16              | <0.05 | -                | <0.05           | -   | 8                | NOX,Hg,VOC, HCl          | 1000      | 1           |
| 1                    | 2      | 70             | 5              | -              | -               | 16              | -     | -                | -               | -   | -                | -                        | <100      | 1           |
| 2                    | 1      | <0.5           | -              | 38             | <0.3            | 19              | 42    | -                | -               | -   | <10              | -                        | <100      | 20-60       |
| 2                    | 2      | <0.5           | -              | 38             | <0.3            | 19              | 42    | -                | <0.05           | -   | 20               | COS,CS <sub>2</sub>      | 1000      | 20-80       |
| 3                    | 1      | <0.5           | -              | 38             | <0.3            | 19              | 42    | -                | -               | -   | <10              | -                        | <100      | 20-60       |
| 3                    | 2      | <0.5           | -              | 58             | <0.3            | 40              | <1    | -                | -               | -   | <10              | -                        | <100      | 20-60       |
| 4                    | 1      | 4              | -              | 50             | 30              | 2               | 8     | <1               | -               | 2   | 55               | VOC, PAH                 | 1000      | 1           |
| 4                    | 2      | 51             | <1             | 5              | <1              | 20              | 22    | -                | ~               | -   | 7                | NOX,VOC                  | 1000      | 1           |
| 4                    | 3      | 10             | -              | 2              | -               | 15              | 70    | -                | -               | -   | -                | VOC                      | 1000      | 1           |
| 4                    | 4      | 55             | -              | 4              | -               | 12              | 28    | -                | ~               | -   | <1               | NOX,VOC                  | 1000      | 1           |
| 5                    | 1      | 70             | 9              | -              | -               | 22              | -     | -                | <1              | -   | 13               | NOX,VOC                  | 1000      | 1           |
| 6                    | 1      | -              | -              | 72             | 6               | 12              | 8     | -                | -               | -   | >70              | -                        | 1000      | 20-30       |
| 6                    | 2      | -              | -              | 42             | 15              | 37              | 7     | -                | -               | -   | -                | -                        | 20-50     | 20-30       |
| 6                    | 3      | -              | -              | 39             | 12              | 48              | <1    | -                | -               | -   | -                | -                        | 20-50     | 20-30       |
| 6                    | 4      | -              | -              | -              | -               | >99             | -     | -                | -               | -   | -                | -                        | <100      | 1           |
| 7                    | 1      | 4              | -              | -              | 91              | <1*             | -     | <1*              | -               | 6   | -                | COS,CS <sub>2</sub> ,HCN |           | >30         |
| 8                    | 1      | -              | -              | -              | -               | 99              | -     | -                | <0.5            | -   | -                | PFCs,VOC                 | 1000      | 1           |
| 8                    | 2      | -              | -              | -              | -               | -               | 99    | -                | ~               | -   | -                | -                        | 1000      | 1           |
| 9                    | 1      | <0.5           | -              | -              | -               | 36              | -     | 60               | <1.0            | <2  | -                | COS,CS <sub>2</sub>      | <100      | <1          |
| 9                    | 2      | 75             | -              | <3             | -               | 23              | <2    | <1               | <0.5            | <2  | 10               | COS,CS <sub>2</sub>      |           | 1           |
| 9                    | 3      | 75             | -              | <3             | -               | 23              | <2    | <0.05            | -               | <2  | 10               | -                        | <100      | 1           |
| 10a                  | 1      | <10            | <1             | -              | 45              | 40              | -     | -                | -               | -   | <5               | VOC, Sx, Clx             | 20-40     | 1           |
| 10b                  | 1      | 40             | 7              | -              | 50              | 3               | -     | -                | -               | -   | <5               | -                        | <100      |             |
| 11                   | 1      | -              | -              | -              | -               | >99.9           | -     | -                | -               | -   | >0.1             | -                        | <100      | 30-40       |

<sup>a</sup> Figure number in the text. Estimations based on dry basis. NO<sub>x</sub>: NO<sub>x</sub>, NO; VOC: volatile organic compounds; PAH: Polycyclic aromatic hydrocarbons; PFC: perfluorocarbons; Sx, Clx, S- and Cl-bearing compounds.

Table 15. Typical capacities and gas flows for processes in Figures 4 to 14.

| Process <sup>a</sup> |                                                             | Capacities                                                                                                       | Gas Production                                                                          |
|----------------------|-------------------------------------------------------------|------------------------------------------------------------------------------------------------------------------|-----------------------------------------------------------------------------------------|
| <b>1</b>             | 1. Pulverized Coal Power Plant                              | -7.84 t Coal/MW power<br>-10-1000 MW plants                                                                      | 0.4-0.5 MMscf gas /t coal                                                               |
| <b>2-3</b>           | 1. IGCC                                                     | -7.52 t Coal/MW power<br>-300-4000 MW plants                                                                     | 0.060-0.065 MMscf CO <sub>2</sub> /t coal                                               |
| <b>4</b>             | 1. Coke Oven Battery:<br>10-105 ovens, usually > 45 ovens   | -10-45 t coal/charge/oven<br>-0.8 t coke/t coal<br>-Coking time: 18-22 h<br>-Battery capacities: 0.18-0.90 MMtpa | -9,500-11,500 scf gas/t coal                                                            |
|                      | 2. Blast Furnace                                            | -2,000-8,000 Mtpd of pig iron prod.<br>-0.5 t Coke/t of pig iron prod.                                           | -70,000-80,000 scf gas/t pig iron prod.                                                 |
|                      | 3. Basic Oxygen Furnace                                     | -1.00 -5.50 MMtpa steel prod.                                                                                    | -3,200 scf gas/t steel prod.                                                            |
|                      | 4. Electric Arc Furnace                                     | -0.60 -0.85 MMtpa steel prod.                                                                                    | -3,800 scf gas/t steel prod.                                                            |
| <b>5</b>             | 1. Kiln                                                     | -0.5-2.0 MMtpa per kiln                                                                                          | -1.0-1.2 t CO <sub>2</sub> /t cement or lime<br>-75,000-85,000 scf gas/t cement or lime |
| <b>6</b>             | 1. Hydrogen/Ammonia Plants                                  | 1-270 MMscfd H <sub>2</sub> (7.5-2000 Mtpd NH <sub>3</sub> )                                                     | 1.5 t CO <sub>2</sub> /t NH <sub>3</sub>                                                |
| <b>7</b>             | 1. Natural Gas Wells                                        |                                                                                                                  | -.05-2.5 MMscfd                                                                         |
| <b>8</b>             | 1. Hall Heroult Process<br>1-3 potlines of 50-200 pots each | -66,000-110,000 Mtpa per potline                                                                                 | -1.83 t CO <sub>2</sub> /t Al<br>-33500 scf gas/t Al                                    |
| <b>9</b>             | 1. Claus Process                                            | 3-4000 t Sulphur/day                                                                                             | -5-50 mol% SBC in gas steam                                                             |
|                      | 2. Scot Process                                             | 0.3-400 t Sulphur/day                                                                                            | <1 mol% SBC in gas steam                                                                |
| <b>10</b>            | 1. Coal Bed Wells                                           |                                                                                                                  | -0.1-2.0 MMscfd                                                                         |
|                      | 2. Landfills                                                | Sizes 1.0t -100MMt (average 3.8 MMt; 50% 1-10 MMt)                                                               | -220 scfa gas/t landfill<br>-0.7-1.0 t landfill/person/year                             |
| <b>11</b>            | 1. Fermenter                                                | -14-15 Ga ethanol/gal of batch fermenter<br>-20 MGa-140 MGa ethanol/plant                                        | -2.8 kg CO <sub>2</sub> /gal ethanol<br>-50 scf/gal ethanol                             |

<sup>a</sup> Figure number in the text. Acronyms: Mtpa: metric tons per annum; MMtpa: million Mtpa; Mtpd: metric tons per day; Ga: gallons per annum, MGa: megagallons per annum; scf: standard cubic feet; MMscf: Million scf; scfd: scf per day; scfa: scf per annum; MW: Megawatt; SBC: sulfur bearing compounds.



Table 16. Largest IGCC and NGCC plants in the world as of January 2000.

| Owner                        | Location       | Technology    | Output (MW <sub>th</sub> )* | Year Online | Feedstock          | Products                     |
|------------------------------|----------------|---------------|-----------------------------|-------------|--------------------|------------------------------|
| Sasol-II                     | South Africa   | Lurgi Dry Ash | 4,130                       | 1977        | Subbit. coal       | FT liquids                   |
| Sasol-III                    | South Africa   | Lurgi Dry Ash | 4,130                       | 1982        | Subbit. coal       | FT liquids                   |
| Repsol/Iberdrola             | Spain          | GE Energy     | 1,654                       | 2004a       | Vac. Res           | Electricity                  |
| Dakota Gasification Co.      | U.S.           | Lurgi Dry Ash | 1,545                       | 1984        | Lignite & ref res  | Syngas                       |
| SARLUX srl                   | Italy          | GE Energy     | 1,067                       | 2000b       | Visbreaker res     | Electricity & H <sub>2</sub> |
| Shell MDS                    | Malaysia       | Shell         | 1,032                       | 1993        | Natural gas        | Mid-distillates              |
| Linde AG                     | Germany        | Shell         | 984                         | 1997        | Visbreaker res     | H <sub>2</sub> & methanol    |
| ISAB Energy                  | Italy          | GE Energy     | 982                         | 1999b       | Asphalt            | Electricity & H <sub>2</sub> |
| Sasol-1                      | South Africa   | Lurgi Dry Ash | 911                         | 1955        | Subbit. coal       | FT                           |
| Total France/edf/GE Energy   | France         | GE Energy     | 895                         | 2003a       | Fuel oil           | Electricity & H <sub>2</sub> |
| Shell Nederland              | Netherlands    | Shell         | 637                         | 1997        | Visbreaker res     | Electricity & H <sub>2</sub> |
| SUV/EGT                      | Czech Republic | Lurgi Dry Ash | 636                         | 1996        | Coal               | Elec. & steam                |
| Chinese Pet Corp             | Taiwan         | GE Energy     | 621                         | 1984        | Bitumen            | H <sub>2</sub> & CO          |
| Hydro Agri Brunsbutt         | Germany        | Shell         | 615                         | 1978        | Hvy vac res        | Ammonia                      |
| Global Energy                | U.S.           | E-gas         | 591                         | 1995        | Bit. coal/pet coke | Electricity                  |
| VEBA Chemie AG               | Germany        | Shell         | 588                         | 1973        | Vac. Res           | Ammonia & methanol           |
| Elcogas SA                   | Spain          | PRENFLO       | 588                         | 1997        | Coal & pet coke    | Electricity                  |
| Motiva Enterprises           | U.S.           | GE Energy     | 558                         | 1999b       | Fluid petcoke      | Electricity                  |
| API Raffineria               | Italy          | GE Energy     | 496                         | 1999b       | Visbreaker res     | Electricity                  |
| Chemopetrol                  | Czech Republic | Shell         | 492                         | 1971        | Vac. Res           | Methanol & Ammonia           |
| NUON                         | Netherlands    | Shell         | 466                         | 1994        | Bit coal           | Electricity                  |
| Tampa Electric               | U.S.           | GE Energy     | 455                         | 1996        | Coal               | Electricity                  |
| Ultrafertil                  | Brazil         | Shell         | 451                         | 1979        | Asphalt res        | Ammonia                      |
| Shanghai Pacific Chem. Corp. | China          | GE Energy     | 439                         | 1995        | Anthracite coal    | Methanol & Town gas          |
| Exxon USA                    | U.S.           | GE Energy     | 436                         | 2000b       | Petcoke            | Electricity & Syngas         |
| Shanghai Pacific Chem. Corp. | China          | IGT U-Gas     | 410                         | 1994        | Bit coal           | Fuel gas & Town gas          |
| Gujarat National Fertilizer  | India          | GE Energy     | 405                         | 1982        | Ref residue        | Methanol & Ammonia           |
| Esso Singapore               | Singapore      | GE Energy     | 364                         | 2000        | Residual oil       | Electricity & H <sub>2</sub> |
| Quimigal Adubos              | Portugal       | Shell         | 328                         | 1984        | Vac. Res           | Ammonia                      |

<sup>a</sup> Plant was in advanced engineering at time of survey.

<sup>b</sup> Plant was under construction at time of survey.

\* MW<sub>th</sub> is a measure of syngas thermal energy.

Source: NETL/Gasification Technology Council, "Gasification: Worldwide Use and Acceptance," Jan. 2000, p. 7.

**Vision 2020 for the Chemical Industry Separations Committee Members**

**Francis Via – Chair**  
**Fairfield Resources International, Inc.**

**Sharon Robinson – Vice Chair**  
**Oak Ridge National Laboratory**

**Linda Curran**  
**BP**

**Timothy C. Frank**  
**Patrick H. Au-Yeung**  
**John G. Pendergast, Jr.**  
**Dow**

**Scott Barnicki**  
**Eastman Chemical**

**Hans Wijmans**  
**Membranes Research & Technology, Inc.**

**Krish R. Krishnamurthy**  
**Stevan Jovanovic**  
**BOC**

**Charles G. Scouten**  
**The Fusheld Group**

**Dante Bonaquist**  
**Neil Stephenson**  
**Praxair Inc.**

**Santi Kulprathipanja**  
**UOP**

**Dilip Kalthod**  
**Air Products and Chemicals, Inc**

**Brendan Murray**  
**Shell**

**Greg Chambers**  
**GE**

## Glossary

|       |                                        |
|-------|----------------------------------------|
| Å     | Angstrom unit                          |
| BFLM  | Bulk flow liquid membrane              |
| BOF   | Basic oxygen furnace                   |
| CARP  | Carbothermic advanced reactor process  |
| DEA   | Diethanolamine                         |
| DGA   | Diglycolamine                          |
| DIPA  | Diisopropanolamine                     |
| EAF   | Electric arc furnace                   |
| EOR   | Enhanced oil recovery                  |
| FCM   | Fixed carrier membrane                 |
| FTM   | Facilitated transport membrane         |
| HGCU  | Hot gas cleanup unit                   |
| HTlc  | Hydrotalcite                           |
| IEM   | Ionic exchange membrane                |
| IGCC  | Integrated gasification combined cycle |
| ILM   | Immobilized liquid membrane            |
| MDEA  | Methyldiethanolamine                   |
| MEA   | Monoethanolamine                       |
| MMt   | Million metric tons                    |
| NGCC  | Natural gas combined cycle             |
| PC    | Pulverized coal                        |
| PDMS  | Poly(dimethylsiloxane)                 |
| PEI   | Polyethyleneimine                      |
| PSA   | Pressure swing adsorption              |
| Psig  | Pounds per Square Inch Gauge           |
| PTFE  | Polytetrafluoroethylene                |
| PTMSP | Poly(1-trimethylsilyl-1-propyne)       |
| SCOT  | Shell-Claus offgas treating            |
| SERP  | Sorption enhanced reaction processes   |
| SMR   | Steam methane reforming                |
| SSF   | Selective surface flow                 |
| TEA   | Triethanolamine                        |
| TSA   | Temperature swing adsorption           |
| VOC   | Volatile organic compound              |
| WGS   | Water gas shift reaction               |