

# Overview of the U.S. DOE Fast Reactor Fuel Development Program

**International Conference on Fast Reactors  
and Related Fuel Cycles: Next Generation  
Nuclear Systems for Sustainable  
Development (FR17)**

W. J. Carmack, S. L. Hayes, J. M. Harp,  
R. S. Fielding, S. A. Maloy, T. A. Saleh

February 2017

The INL is a  
U.S. Department of Energy  
National Laboratory  
operated by  
Battelle Energy Alliance



This is a preprint of a paper intended for publication in a journal or proceedings. Since changes may be made before publication, this preprint should not be cited or reproduced without permission of the author. This document was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, or any of their employees, makes any warranty, expressed or implied, or assumes any legal liability or responsibility for any third party's use, or the results of such use, of any information, apparatus, product or process disclosed in this report, or represents that its use by such third party would not infringe privately owned rights. The views expressed in this paper are not necessarily those of the United States Government or the sponsoring agency.

## Overview of the U.S. DOE Fast Reactor Fuel Development Program

W. J. Carmack<sup>1</sup>, S. L. Hayes<sup>1</sup>, J. M. Harp<sup>1</sup>, R. S. Fielding<sup>1</sup>, S. A. Maloy<sup>2</sup>, T. A. Saleh<sup>2</sup>

<sup>1</sup>Idaho National Laboratory, P. O. Box 1625, Idaho Falls, ID USA

<sup>2</sup>Los Alamos National Laboratory, Los Alamos, NM, USA

*E-mail contact of main author: [jon.carmack@inl.gov](mailto:jon.carmack@inl.gov)*

**Abstract.** Research and development activities on fast reactor fuels in the United States is focused on their potential use for actinide transmutation in future sodium fast reactors. As part of this application, there is a desire to demonstrate a multifold increase in burnup potential in the fuel and high dose capability cladding.

A number of fuel design innovations are under investigation with a view toward significantly increasing the burnup potential of fuels, since higher discharge burnups equate to lower potential actinide losses during recycle. Promising innovations under investigation include: 1) lowering the fuel smeared density in order to accommodate the additional swelling expected as burnups increase, 2) utilizing an annular fuel geometry for better geometrical stability at low smeared densities, as well as the potential to eliminate the need for a sodium bond, and 3) minor alloy additions to immobilize lanthanide fission products inside the metallic fuel matrix and prevent their transport to the cladding resulting in fuel-cladding chemical interaction.

This paper presents results from these efforts to advance fuel and cladding technology in support of high burnup and actinide transmutation objectives. Highlights include examples of fabrication of low smeared density annular metallic fuels, experiments to identify alloy additions effective in immobilizing lanthanide fission products, and early postirradiation examinations of annular metallic fuels having low smeared densities and palladium additions for fission product immobilization. Advanced cladding development activities include the investigation of high dose tolerant steel alloys. An overview of the U.S. Department of Energy fast reactor fuel research and development activities will be provided.

**Key Words:** Fuel development, metallic

### 1. Introduction

Metallic fuels have a history of use that spans the entire nuclear age, especially in association with the development of the LMFBR. Initially, metallic fuels were employed due to their ease of fabrication and high heavy metal density (which led to the most favorable breeding efficiencies in fast reactors). During subsequent decades of use, metallic fuel technology has matured significantly, leading to the realization of major benefits in the areas of fuel reliability and burnup, proliferation-resistant recycling, remote fabrication, and passive reactor safety. Such characteristics continue to make metallic fuels a highly attractive technology, especially for use with future sodium fast reactors.

Current research and development activities on metallic fuels in DOE's Advanced Fuels Campaign are focused on their potential use for actinide transmutation in advanced SFRs. In such a mission, metallic fuels would be employed as part of a closed fuel cycle in which plutonium and minor actinides (Am, Np) recovered from spent fuel would be incorporated. All actinides in this metallic fuel would be fissioned or transmuted in a fast reactor to eliminate the extremely long-lived, heat-producing actinides in order to reduce the volume, heat load, and radio-toxicity burden on a future geological repository. Thus, the need exists to demonstrate reliable performance of metallic fuels with Pu and minor actinide constituents to very high burnup. As part of this application, there is also a need for a near zero-loss

fabrication process, since losses during fuel fabrication are a potential source of long-lived actinides destined for geologic disposal. This paper presents the current state and future direction of the development of metallic fuels for actinide transmutation in the United States.

## 2. Fabrication Development

The incorporation of Am and Np into traditional U-Pu-Zr metallic fuel alloys was attempted during the IFR Program in the early 1990's. However, the conventional counter gravity injection casting method performed under vacuum, previously used to fabricate these metallic fuel alloys for EBR-II, was not optimized for mitigating loss of the volatile Am constituent in the casting charge; as a result, approximately 40% of the Am casting charge failed to be incorporated into the as-cast fuel alloys. In addition, the counter gravity method was inherently inefficient, as a significant fraction (typically 30-40%) of the melted charge remained as a heel in the crucible after casting. Limited recycle of the heel into subsequent casting batches was possible. However, interaction of the molten fuel alloy with crucible wash materials (typically a  $\text{Y}_2\text{O}_3$  slurry) and quartz molds increasingly introduced impurities into the fuel alloy, eventually making continued recycle undesirable; discarded heels became a significant actinide waste stream. Furthermore, the use of one-time, disposable quartz molds gave rise to yet another actinide waste stream.<sup>1</sup> There existed a need for an advanced casting system to address these issues.

Fabrication development efforts of the recent past have pursued an optimized bottom-pour (gravity) casting method to increase utilization of the melted charge to near 100%, a differential pressure casting approach, performed under an argon overpressure, to mitigate Am volatilization during fabrication, and the use of permanent molds. A small, experimental casting furnace was designed, fabricated, and installed in a radiological fume hood in order to evaluate the proposed casting changes relative to melt utilization, loss of volatile constituents, and mold performance. It was operated for several years for casting experiments on U-10Zr and using Mn as a volatile constituent with properties reasonably similar to Am. These experiments indicated that excellent improvement could be achieved in every respect using this casting approach.<sup>2</sup>

The next step was to design and build a casting system that could be installed into a glovebox in order to demonstrate these improvements using actual U-Pu-Am-Np-Zr fuel alloys. The new furnace, designated the Glovebox Advanced Casting System, became operational near the end of 2013. A solid model of the GACS and photograph of its glovebox installation are shown in Fig. 1.

A series of three experiments have been performed using the GACS. The first set tested the operability and feasibility of using the furnace for minor actinide fuel fabrication by simultaneously casting three U-TRU-Zr pins of 4.2mm in diameter. The next two sets of experiments focused on retention of Am in the fuel melt during a prototypic heating cycle.

In the experiment which attempted to simultaneously cast three U-TRU-Zr fuel pins, the crucible was charged with U, a Pu-Am-Zr alloy, and Zr feed materials and heated to a casting temperature of 1450°C. The casting produced two pins of approximately 100 mm in length and a third pin of approximately 75 mm in length. The cast fuel pins appeared to be sound and free of substantial surface flaws. A photograph of the three as-cast fuel pins is shown in Fig. 2.

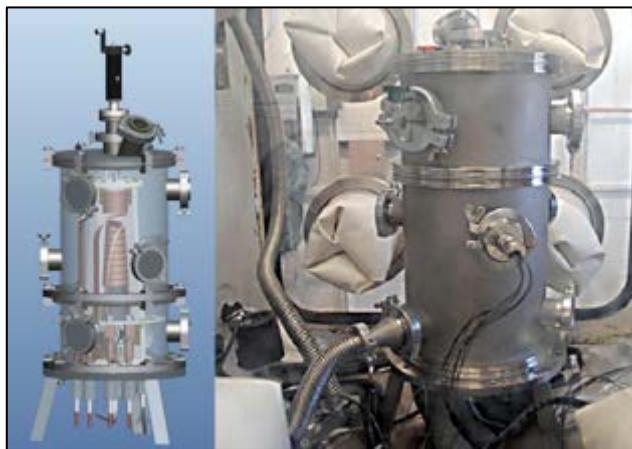


FIG. 1. Schematic and photo of the installed GACS.

In the set of experiments investigating Am volatility, the three previously cast pins were broken up, loaded in the crucible, and heated to 1450°C for 15 minutes under a constant purge of approximately 0.2 m<sup>3</sup>/hr of argon, then allowed to cool. The resulting ingot was sampled, and the remainder of the ingot was re-melted according to the same procedure. This second ingot was again sampled. Chemical analyses of these two ingots are shown in Table I, with a reported uncertainty in the analyses of 5% (2 $\sigma$ ). As seen in the table, the Am content appears to be fairly consistent between the two ingots and the initial charge.



FIG. 2. U-TRU-Zr pins simultaneously cast in the GACS (calipers set at 25.4 mm).

TABLE I: CHEMICAL ANALYSES FROM VOLATILITY EXPERIMENTS.

Material	Initial Charge* (wt.%)	After Run 1 (wt.%)	After Run 2 (wt.%)
U	80.96	81.90	81.10
Pu	6.05	7.66	7.54
Am	1.21	1.18	1.18
Zr	8.86	9.97	11.1

\*Analysis resulted in 2.92% undissolved/unknown material.

Certainly much additional experimentation, testing, and optimization of the casting process is needed. However, these initial results demonstrate essentially no loss of Am due to volatilization during fabrication. In short, a path toward zero-loss fabrication of metallic fuels including minor actinides appears to be feasible.

### 3. Irradiation Testing

In the early 2000's the Advanced Fuels Campaign renewed the development of metallic fuels for actinide transmutation in future fast reactors, but it was hindered by the fact that there was no longer a domestic (U.S.) fast reactor available for irradiation testing of fuels. Since early metallic fuels were developed using experiments in thermal test reactors (such as the Materials Test Reactor in Idaho or CP-5 in Chicago), an irradiation test program was developed for implementation in the Advanced Test Reactor in Idaho.

Irradiation testing of advanced metallic fuels in the ATR has been underway since 2003. Testing in the ATR is performed inside of cadmium-shrouded experiment positions to remove >99% of the thermal flux incident on the test fuels, resulting in an epi-thermal driven fuel test that is free from gross flux depression<sup>3</sup> and produces an essentially prototypic radial temperature profile inside fuel rodlets (i.e., miniature test rods).

To date, two ATR test series (AFC-1, 2) on transmutation fuels have been completed. Almost 20 different metallic fuel alloys have been tested to burnups as high as 30% with constituent compositions of Pu up to 30%, Am up to 12%, Np up to 10%, and Zr between 10 and 60%. In general, the performance of all of these substantially disparate metallic fuel alloys has been observed to be excellent, and their irradiation behaviors are generally consistent with historic norms for metallic fuels without minor actinide additions and having lower Pu or Zr contents.<sup>4</sup>

Although irradiation of these transmutation fuels inside the cadmium-shrouded experiment positions in ATR generally achieve temperature conditions that are fairly prototypic of fast reactor conditions, the test fuels do not experience neutron damage conditions prototypic of a fast-spectrum reactor. For this reason, cladding performance is not genuinely being challenged in these tests. Furthermore, even the fuel performance under these non-prototypic irradiation conditions must be validated. To this end, two metallic fuel compositions (Pu-12Am-40Zr and U-29Pu-4Am-2Np-30Zr) were irradiated for 235 EFPDs to approximately 12% burnup in the Phénix fast reactor as part of the FUTURIX-FTA experiment.<sup>5</sup> Postirradiation examination of these test pins is underway. Comparison of these Phénix irradiated metallic fuels with identical compositions irradiated under nominally the same conditions in ATR will be an important part of the validation process. Fig. 3 provides metallography photomicrographs of metallic alloy fuels irradiated in the ATR (AFC-1H R4) and Phenix (DOE-1) reactors. Irradiated at similar temperatures and to similar burnups, the fuel regions have relatively comparable microstructures with discernable constituent and fission product migration. A full comparison of the fast reactor fuel irradiation experiments in ATR epi-thermal environment with prototypic fast reactor condition irradiations is currently underway in the United States.

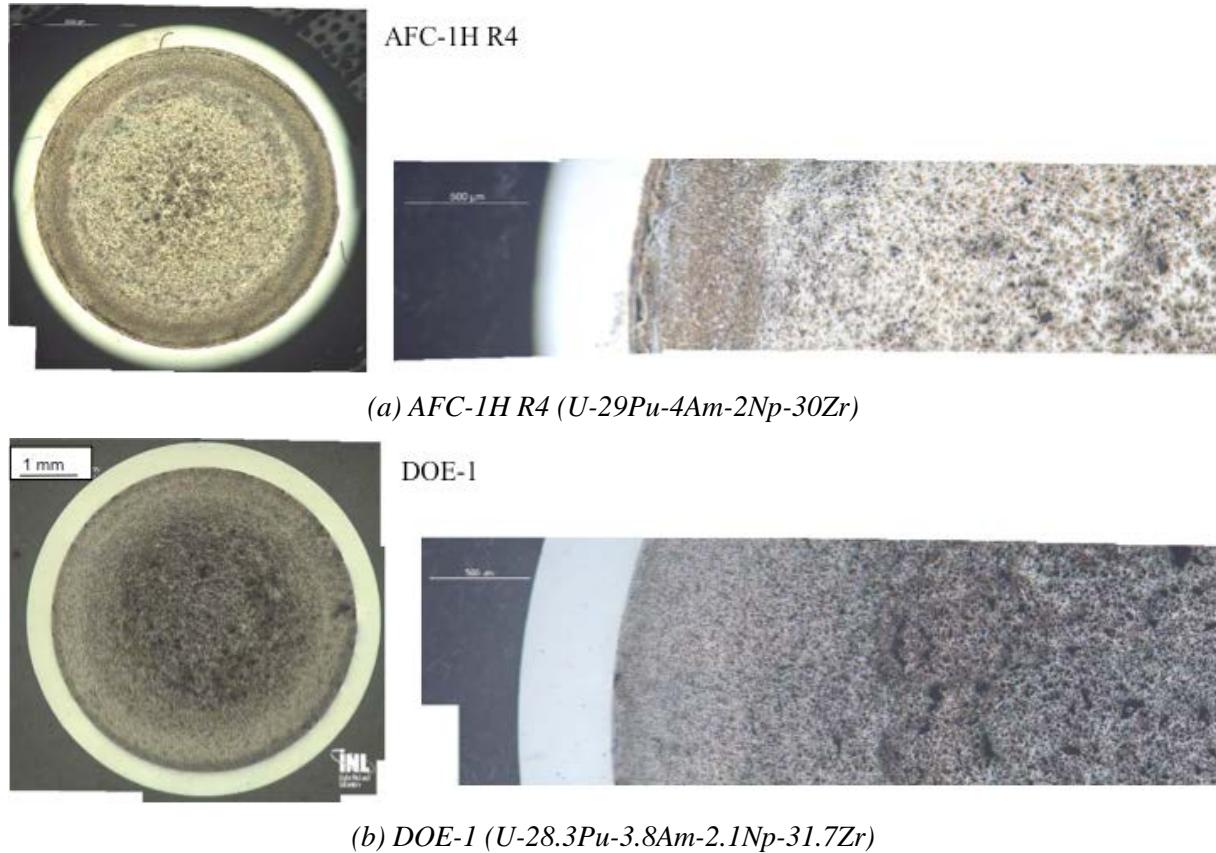


FIG. 3. Metallography photomicrographs of metallic alloy fuels irradiated in ATR (AFC-1H R4) and Phenix (DOE-1).

#### 4. Fast Reactor Cladding Development

Fast reactor cladding development programs have been underway for many years in the United States and have performed significant development of steel alloys. Since the mid-1990s fast reactor design and fuel performance goals have driven core component and cladding materials development to develop steel alloys capable of higher temperature operation with high burnup capability. As indicated in Fig. 4, the ferritic-martensitic HT-9 alloy accommodates operation in the 500°C range up to doses of 200 dpa. Above this temperature and damage range other alloys must be investigated. The United States bases much of its fast reactor cladding development for near term reactor designs on the fabrication and performance of the HT-9 alloy and is also conducting research of advanced ODS steels for use at higher temperature and higher doses. Fig. 4. Shows a photograph of the FCRD-NFA1 developmental ODS alloy drawn to bar stock in preparation for tubing formation and drawing. It is hoped that advanced ODS alloy fabrication and joining technology can be developed such that the ODS alloys will allow the potential for fast reactor operation at higher temperature and doses.

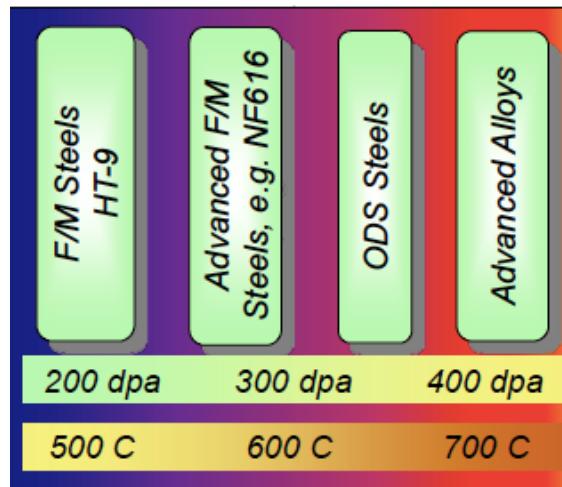


FIG. 4. *Near term cladding focused on HT-9 FM Steel with higher dpa research investigating ODS Steels.*



FIG. 5. *FCRD-NFA1 ODS Steel bar stock.*

## 5. Future Direction of R&D

Future work is being undertaken with a view toward increasing the burnup potential of metallic fuels even more. Design innovations under investigation include: 1) lowering the fuel smear density below the traditional 75% in order to accommodate more swelling, 2) an annular fuel geometry in intimate contact with the cladding to eliminate the need for a sodium bond (with the central hole accommodating fuel swelling), 3) coatings/liners on the cladding inner surface to mitigate fuel-cladding chemical interaction and enable higher temperature operation, 4) alternative major alloying elements to Zr that can stabilize the gamma phase of uranium under irradiation conditions, while increasing fuel alloy melting temperatures or offering other fuel performance benefits, and 5) minor alloy additions to immobilize lanthanide fission products where produced inside the fuel and prevent their transport to the cladding where they make up the primary species responsible for FCCI.

### 5.1. Alternative Metallic Fuel Alloy Systems

As the TRU content of a metallic transmutation fuel alloy increases, the fuel alloy melting temperature (solidus) decreases below that of U-10Zr or even U-20Pu-10Zr. This decrease can be offset by increasing the Zr content above 10 wt.%. As can be seen in Table II, metallic fuels with much higher Zr contents have been the subject of extensive testing. While the performance of these high Zr content metallic fuels has been observed to be very good, it comes as the price of a decreasing actinide (i.e., fissile) density in the fuel. As an alternative to dramatically increasing the Zr content, other major alloying element(s) are

under investigation. Two such alloy systems that are showing potential are Mo-Ti-Zr and Ta.

For example, although U and Ta are immiscible, success in alloying U-Zr-Ta has been achieved. Fig. 6 shows an SEM micrograph of a U-10Zr-5Ta as-cast alloy with the chemical compositions of all phases present determined by EDX (Table II). Modest additions of Ta could significantly increase the fuel alloy solidus while stabilizing the gamma phase of U to even lower temperatures than are achieved by Zr alone.

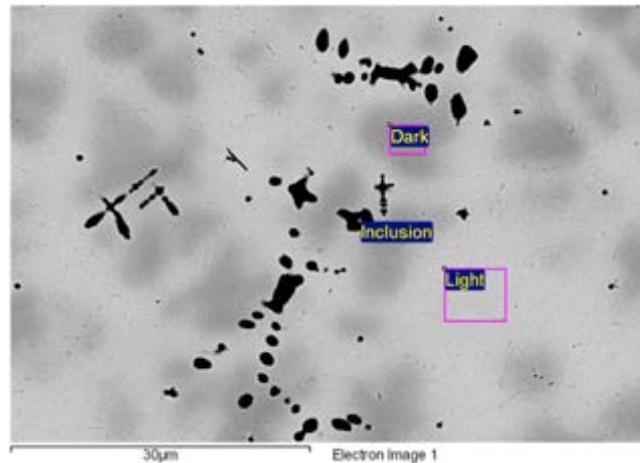


FIG. 6. SEM micrograph of U-10Zr-5Ta alloy.

TABLE II. CHEMICAL COMPOSITIONS OF PHASES IN U-10ZR-5TA ALLOY.

Phase	U (wt.%)	Zr (wt.%)	Ta (wt.%)
Light	93.13	4.88	1.99
Dark	70.07	18.61	11.31
Inclusion	3.98	83.94	12.08

## 5.2. Minor Alloy Additions to Immobilize Lanthanides

In U-Zr and U-Pu-Zr metallic fuels, lanthanide fission products migrate to the fuel periphery and become the primary species responsible for fuel-cladding chemical interaction. FCCI thins the cladding wall, increasing cladding stress. The rate of FCCI attack increases with temperature. As a result, FCCI caused by the lanthanide fission products (on stainless steel cladding) limits cladding temperatures to approximately 600°C. Development of coatings/liners (e.g., Zr, V, TiN, Cr) that could be applied to the inner surface of the cladding to act as a diffusion barrier, mitigating FCCI, are under investigation. However, a more elegant solution to the FCCI issue would be the addition of a minor alloying element that would react with the lanthanide fission products *in situ*, immobilizing them in the fuel matrix and preventing their migration to the cladding. Preliminary alloy casting and interdiffusion experiments suggest that palladium may be able to achieve the desired effect in relatively small quantities. In casting studies in which both Pd and lanthanide elements were included in the fuel alloy, Pd reacted with the lanthanides to form a separate, stable intermetallic

phase.<sup>6</sup> In separate experiments, diffusion couple studies showed that although Pd and Fe (the major constituent in stainless steel cladding) strongly react, including liquefaction, at 700°C, a Pd-Nd intermetallic (i.e., 1:1 atomic ratio) showed no reaction with Fe at the same temperature<sup>7</sup> (see Fig. 7).

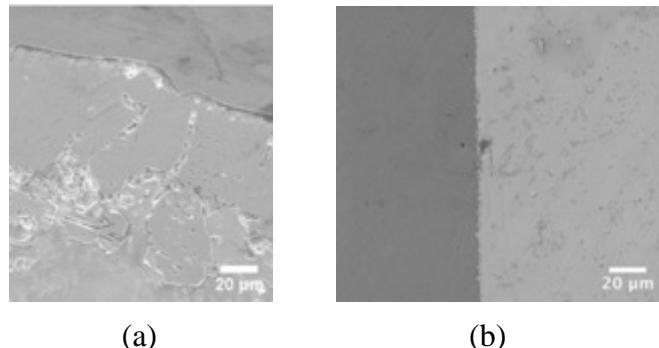


Fig. 7. (a) Liquification of Nd-Fe diffusion couple at 700°C; (b) no reaction between Nd/Pd-Fe diffusion couple at 700°C.

Thermodynamic calculations suggest that 2 wt.% Pd would be needed in the metallic fuel alloy to stabilize the lanthanide fission products produced per 10% burnup. Metallic fuel alloys with Pd additions are currently under irradiation in the ATR.

## 6. Conclusions

Metallic fuels have had a long history of use in sodium-cooled fast reactors. Continued research, development, and design innovation over a period of decades have demonstrated this fuel technology to be safe and reliable to extremely high burnups over a wide range of compositions. Their simple fabrication has historically given them a significant economic advantage over other fuel forms. Research and development on metallic fuels continues, with particular emphasis on showing that this fuel technology can incorporate significant quantities of plutonium and minor actinides for the purpose of efficiently and economically transmuting these elements in a fast-spectrum reactor. New fabrication methods to improve retention of the volatile fuel constituents during the casting process (and reduce waste generation), are being developed. Irradiation testing of the new metallic fuels has so far indicated that the new compositions, although differing significantly both in the quantities of Pu and minor actinides included and in the Zr alloying addition, perform as a function of fission density very analogously to the historic U-Zr and U-Pu-Zr fuels.

In the next few years it is anticipated that a new casting furnace prototype will demonstrate that these new metallic fuel alloys can be fabricated at engineering scale, in a remote environment, with no significant fuel loss or waste generation. Irradiation tests currently underway will provide the performance data needed to assess fuel reliability/burnup capability and identify any unique behaviors that are a result of the new compositions. If these future results are consistent with the intermediate data available at present, metallic fuels are expected to continue to be a strong contender for the fuel technology choice of future fast reactors. The following papers contain additional detailed technical presentation of work conducted under the DOE Advanced Fuel Campaign with respect to fast reactor fuel and cladding development and are included in this meeting.

Paper 73 - Controlling FCCI with Pd in Metallic Fuel - Michael T. Benson, James A. King, Jason M. Harp

Paper 370 - Americium Retention During Metallic Fuel Fabrication, Randall Fielding.

Paper 523 - Review of Transient Testing of Fast Reactor Fuels in the Transient REActor Test Facility (TREAT), Colby Jensen, Daniel Wachs, Jon Carmack, Nicolas Woolstenhulme.

Paper 215 - Status of development of the BISON code for fast reactor fuel performance modeling, Pavel Medvedev, Stephen Novascone, Russel Gardner, Albert Casagrande.

Paper 366 - BISON for Metallic Fuels Modeling, C. Matthews, J. Galloway, C. Unal, S. Novascone, R. Williamson.

Paper 350 - Modeling of Lanthanide Transport in Metallic Fuels: Recent Progresses, C. Unal, X. Li, J. Isler, S. Abid, J. Zhang, C. Matthews, C. Arnold, J. Galloway, N. Carlson, R. Mariani.

Paper 362 - Mechanical Properties of Irradiated Cladding Material from BOR-60 Irradiations, Tarik Saleh.

## 7. Acknowledgement

This manuscript has been authored by a contractor of the U.S. Government for the U.S. Department of Energy, Office of Nuclear Energy, Science, and Technology (NE), under DOE-NE Idaho Operations Office Contract DEAC0705ID14517. Accordingly, the U.S. Government retains a nonexclusive, royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for U.S. Government purposes.

## 8. Nomenclature

ATR Advanced Test Reactor

DOE Department of Energy

EDX Energy Dispersive X-ray Spectroscopy

FCCI Fuel-cladding Chemical Interaction

GACS Glovebox Advanced Casting System

LMFBR Liquid Metal Fast Breeder Reactor

LWR Light Water Reactor

SEM Scanning Electron Microscope

SFR Sodium Fast Reactor

TRU Transuranic

## 9. References

- [1] CRAWFORD, D.C., et al., "Performance of U-Pu-Zr Fuel Cast into Zirconium Molds," *J. Nucl. Mater.*, **204**, 157-164 (1993).
- [2] FIELDING, R., et al., "Advanced Bench-scale Metal Fuel Castings System Development," *Tran. Am. Nucl. Soc.*, Vol. 99, pp. 305-306, American Nuclear Society, Reno, NV, USA (2008).

- [3] CHANG, G.S. and AMBROSEK, R.G., "Hardening Neutron Spectrum for Advanced Actinide Transmutation Experiments in the ATR," *Rad. Prot. Dos.*, **115**, 63-38 (2005).
- [4] HILTON, B.A. et al., "Irradiation Tests and Postirradiation Examination of Metallic Alloy and Nitride Based Transmutation Fuels," *Proceedings of the 12th International Conference on Nuclear Engineering*, American Society of Mechanical Engineers, Arlington, VA, USA (2004).
- [5] CHICHESTER, H.J.M. et al., "Overview of the FUTURIX-FTA Irradiation Experiment in the Phénix Reactor," GLOBAL 2015, Société Français d'Energie Nucléaire, Paris, France (2015).
- [6] MARIANI, R.D. et al., "Metallic Fuels: The EBR-II Legacy and Recent Advances," *Proc. Chem.*, **7**, 513-520 (2012).
- [7] EGELAND, G.W. et al., "Reducing Fuel-Cladding Chemical Interaction: The Effect of Palladium on the Reactivity of Neodymium on Iron in Diffusion Couples", *J. Nucl. Mater.*, **432**, 539-544 (2013).