



LAWRENCE
LIVERMORE
NATIONAL
LABORATORY

LLNL-JRNL-716617

Analysis of High-Power Diode Laser Heating Effects on HY-80 Steel for Laser Assisted Friction Stir Welding Applications

M. E. Wiechec, B. W. Baker, T. R. McNelley, M. J. Matthews, A. M. Rubenchik, M. D. Rotter, R. J. Beach, S. S. Wu

January 4, 2017

World Journal of Engineering and Technology

Disclaimer

This document was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor Lawrence Livermore National Security, LLC, nor any of their employees makes any warranty, expressed or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or Lawrence Livermore National Security, LLC. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or Lawrence Livermore National Security, LLC, and shall not be used for advertising or product endorsement purposes.

***Analysis of High-Power Diode Laser Heating Effects on HY-80 Steel for
Laser Assisted Friction Stir Welding Applications***

M. E. Wiechec¹ (maxwiechec@gmail.com) , B.W. Baker^{1*} (bbaker@usna.edu) ,
T. R. McNelley² (tmcnelley@nps.edu) , M. J. Matthews³
(matthews11@llnl.gov) , A. M. Rubenchik³ (rubenchik1@llnl.gov) , M. D.
Rotter (rotter1@llnl.gov) , R. J. Beach (beach2@llnl.gov) and S. S. Wu³
(wu31@llnl.gov)

¹United States Naval Academy, Annapolis, MD

²Naval Postgraduate School, Monterey, CA

³Lawrence Livermore National Laboratory, Livermore, CA

* corresponding author

Abstract

In this research, several conditions of high power diode laser heated HY-80 steel were characterized to determine the viability of using such lasers as a preheating source before friction stir welding in order to reduce frictional forces thereby reducing tool wear and increasing welding speeds. Differences in microstructures within heat affected zones were identified at specific laser powers and traverse speeds. Vickers hardness values were recorded and analyzed to validate the formation of additional martensite in diode laser heated regions of HY-80 steel. Conditions that produced little to no additional martensite were identified and relationships between high power diode laser power, traverse speed, and martensite formation were determined. The development of heat affected zones, change in grain structure, and creation of additional martensite in HY-80 can be prevented through the optimization of laser amperage and transverse speed.

Keywords

Mechanical characterization, martensite, welding, martensitic transformations

LLNL-JRNL-716617

1. Introduction

Friction stir welding (FSW) is a modern solid-state joining technique that is energy efficient, environmentally friendly, and versatile which has been in use for over two decades on both soft alloys such as aluminum and harder alloys such as steels [1-3]. Some of the advantages of FSW over conventional joining techniques include usage of no filler material, expenditure of no shielding gas to the environment, and consumption of considerably less energy than conventional welding methods. The superiority of FSW welds is evident in the low distortion of the workpiece, good dimensional stability, no loss of alloying elements, excellent material properties in the joint area, refinement of microstructure, and absence of solidification and hot cracking all of which arise from the fact that FSW is a solid-state joining process [3]. Despite these positive attributes, FSW does have some disadvantages related to the nature of frictional heating and the forces between tool and the workpiece which have limited its use across a wider range of industrially-relevant materials.

Wear of tools used during FSW is a critical issue and is discussed in detail by several authors [3-6]. For softer metals such as aluminum, frictional forces between the tool and workpiece are relatively low, leading to less tool wear and thereby allowing the use of simpler tool designs that can have a long useful lifetime. FSW on harder materials such as steel alloys results in significantly larger frictional forces causing reduced tool life and requiring stronger, more expensive tools to compensate. The combination of increased tool cost, tool wear, and reduced welding speeds is one of the primary industrial limitations of FSW on steels.

As an alternative to hardening tool material to minimize tool wear, softening of the base metal prior to FSW is a viable

solution to increase tool life, and several hybrid FSW methods involving workpiece preheating have been proposed [7-13]. Many of the original hybrid FSW techniques used traditional fusion welding heat input mechanisms, but more recently laser-based hybrid FSW concepts have been proposed that offer simple, effective, and controllable means of preheating [14-17]. Frictional forces are directly related to the downward force of the tool as well as the shear force once the tool is rotating [3, 18, 19]. Softening of high strength materials below their recrystallization temperature moments before being friction stir welded should reduce tool wear while also causing minimal change to the workpiece. As an example, Ferrando confirmed that electronically-assisted friction stir welding (EAWSW) does reduce the downward force required for proper metal joining [7]. Unfortunately, since EAWSW requires additional contact with the workpiece and relies on energy transfer through the workpiece to the weld area, it is highly application and material dependent and therefore may not be viable for a broad range of applications. Similarly, Kohn demonstrated that a fiber-coupled Nd:YAG laser could be used to locally preheat the workpiece without physical contact, showing the potential behind laser assisted friction stir welding (LAFSW) in reducing tool wear and increasing welding speeds [14].

Unlike the large and generally complex Nd:YAG or CO₂ lasers and the comparatively more expensive Yb fiber lasers proposed in current LAFSW systems, high-power diode lasers (HPDL) are compact, less expensive, more efficient, safer and comparatively easier to operate. The advantages and potential applications of HPDL systems are discussed in detail in reviews by Li [20], Chen [21], and Bachmann [22]. Additionally, HPDLs can have adjustable wavelengths allowing for increased absorption and efficiency further adding to their flexibility [17]. Assisting FSW with the

use of HPDL systems was initially proposed as Diode Laser Assisted Friction Stir Welding (DLAFSW), where the flexibility of HPDL systems was a key consideration for controlling preheating and post FSW cooling on hardenable steels [17]. This research aims to add to that proposal by characterizing the microstructural changes due to laser heating with HPDLs alone.

In order to demonstrate the effect of laser heating on typical hardenable steels, the tempered martensitic steel HY-80 was selected as a candidate workpiece. HY-80 steel is a high-strength low-carbon steel best known for its use in ship construction and military applications. Having a high tensile and yield strength, HY-80 is used extensively for hulls of Naval vessels and submarines. The Naval lineage of HY-80 is discussed in detail by Heller [23], Stewart [24], and Young [25]. HY-80 is primarily used in a quenched and tempered condition that results in a tempered martensitic microstructure which produces the desirable strength and hardness.

When used on HY-80, a HPDL will be able to provide a highly controllable heating source required for FSW of hardenable steels. With control over the laser parameters, the temperature at the heating location can be regulated, controlling the phase transformation that traditionally complicates the welding process of hardenable steels. With the location and precise amount of heat under control, it is anticipated that heating will be in a confined area, thus preserving the mechanical properties of the base metal. Additionally, the precision of HPDL systems may allow for heating below phase transition temperatures.

Although not desirable for pre-weld treatment in DLAFSW, the use of HPDL systems on hardenable steels offers a separate possibility of surface hardening. As opposed to softening prior to FSW, a HPDL can be used to locally raise the surface

temperature of a workpiece to promote the formation of martensite without applying energy throughout the material. Because of its low cost, a HPDL is a cost effective means for large area processing and therefore could be used to harden a large area. Shi et al. found that lasers are ideal tools for surface hardening below the melting temperature of steel, producing a hardened depth of around 1 mm using a 600 W laser with a beam diameter of 5 mm [26]. Thus, aside from preheating to soften the workpiece, surface hardening with HPDL arrays can be considered for future research as there are many applications for localized and efficient hardening; however, such applications will not be discussed in detail in this research.

If controllable heating using HPDLs proves successful, DLAFSW could be used to provide higher quality welds with a smaller heat affected zone (HAZ) producing more desirable material joints. Additionally, conventional FSW is already used extensively on aluminum alloys for newer Naval ships, and DLAFSW could have great potential in improving these joints as well [27]. Finally, since future nuclear reactor designs use high strength superalloys which cannot be joined by typical joining methods, FSW has been proposed as a joining method for these alloys in nuclear applications.

This research analyzes HPDL heated HY-80 samples for the optimum laser settings before FSW. Ideally, no additional martensite will have formed, grain size through the heated region will be consistent with the base material, and hardness will be uniform. If HY-80 is heated past its transition temperature, additional martensite will form, creating a HAZ with undesirable brittleness, stiffness, and low toughness. As a result of this research, the laser heating effects of HPDLs on HY-80 for DLAFSW applications, and the possibility of laser hardening, will be explored using microstructure and material

characterization based on high resolution microscopy and hardness measurements.

2. Experimental Procedure

HY-80 was selected for this study based on previous FSW experience and its similarity to other hardenable steels. In this study we used rolled plates of HY-80 (MIL-S-16216) which were 6.4 mm (0.25 inches) thick and of varying widths and lengths. As discussed previously, HY-80 is a low carbon steel (0.12 - 0.18 wt% carbon) used in Naval applications as well as some pressure vessels and acquires its strength and toughness through quenching and tempering treatments. Table I gives the composition limits for HY-80 steel according to MIL-S-16216 as well as the composition of the HY-80 used in this research as determined by energy dispersive spectroscopy (EDS). For the EDS results presented in this research, the compositional values for carbon were not included due to the inaccuracies associated with the low energy characteristic x-rays of carbon. Additionally, impurities such as sulfur and phosphorous were not included since their composition were well below 0.1 wt% and within specification.

Previous research on FSW of HY-80 has shown that peak temperatures in the stir zone are sufficient to create austenite which upon cooling will become tempered or untempered martensite based on the cooling rates [28]. Depending on the intended application, the formation of martensite in the weld nugget can be beneficial or detrimental, but in most applications requiring toughness, the formation of an untempered martensite phase is undesirable so consideration must be given to cooling rates following joining in order to establish a tempered martensitic microstructure. Although considered and established as a future

research goal, no specific post welding heat treatment was applied in this research.

Several plates of HY-80 were laser heated in accordance to the procedure discussed in related research [17]. The HPDL used was a 5 kW Northrup Grumman diode array that emits partially-coherent light at a wavelength of 795 nm. Over a drive current range of 20 to 50 amps, the array generates optical powers between 160 and 2100 W, thus allowing for wide range of temperatures on the workpiece. Fig. 1 shows a series of experimental runs to measure of beam profile and establish the operating conditions of the HPDL array [17].

Fig. 1 shows that increasing the laser current causes a change in the beam profile (Fig. 1a) as well as a linear increase in power above a lasing threshold of ~17 amps (Fig. 1b). Increasing the beam current causes a proportionally larger expansion of the beam in the axis corresponding to the direction perpendicular to the laser and proposed welding path ('slow' axis of the laser diode emission) and relates closely to the width of laser scarring found on the heated plates (Fig. 2). Increasing the beam current clearly causes an increase in the width of the visibly heated area as suggested by the beam dump analysis shown in Fig. 1a.

Parameters for testing were chosen based on predicted optimum FSW conditions on HY-80 by Young et al.: 400 revolutions per minute (RPM) for rotational speed and 100 millimeters per minute (MMPM) for traverse or scan speed [25]. Since this research focuses solely on laser effects on HY-80, only the traverse speed recommended by Young is relevant. The rotational speed will become important when the two components of FSW and HPDL heating are combined in DLAFSW research. Based on initial laser heating trials and estimates reported in related research, the optimal current conditions were determined to be between 25

amps and 30 amps [17]. Additionally, all runs were performed on bead-blasted surfaces to eliminate variability in absorptivity across runs. Workpiece surface preparation does have a significant impact on laser absorptivity and a resultant impact on heating. Analysis of different surface preparations will be reported in a separate report. The major conditions analyzed in this research are summarized in Table II.

In addition to the conditions listed in Table II, optimum conditions may include varying the current of the laser shortly after movement begins. Preheating without movement at a current below 25 amps may be considered for additional workpiece heating without passing the austenitic transition temperature. Experiments based on these variable heating conditions were performed and an image of the laser heated plate can be found in Fig. 3; however, no characterization was performed on this specific plate in this research since an analysis of steady state heating conditions was desirable. Nonetheless, these results demonstrate the effect of near instantaneous (<1 ms) laser heating changes on surface treatment and the associated responsiveness. Fig. 3 also shows the nominal surface temperature of the heated plate using thermally sensitive lacquers applied across the heated path.

For this research, two plates with three runs each were the primary focus with important conditions summarized in Table II. Specimens were cut, polished, and mounted in conductive resin for subsequent analysis. All samples used in this research were mounted such that the transvers side would be visible from the mount for inspection of the laser effects below the surface of the metal. Specimens were not subjected to any additional heating during sample preparation.

Samples were prepared with SiC papers and diamond polishing solutions. Samples for microscopy were etched with 2% Nital and

were analyzed in an optical microscope and a field emission gun scanning electron microscope (SEM) at 15 keV. EDS was also performed on the base material and the HAZ to determine if any change in composition of an element in any particular area.

After imaging, the hardness of transverse specimens was measured using a micro-indenter on a Vickers scale. Indentations were made with a 500 gram load and 15 second dwell time. Hardness measurements were taken with a separation distance of 3-5 times the indentation width to prevent interference due to strain hardening from nearby indentations. Hardness measurements were recorded in representative areas of the base metal and heat affected zones for each test specimen.

3. Results

3.1 Base Metal

The microstructure in the base material is tempered martensite as shown in Fig. 4. The grains are comparatively larger than the grains in the HAZ following laser heating and their shape resembles that of prior austenitic grains that transformed into tempered martensite during the original production processing of HY-80. Similar grain structures were observed using a SEM, as seen Fig. 4b. Results for the base material from all conditions were consistent and images were similar. The hardness of the base material was experimentally determined to be 240 HV_{0.5} throughout all samples.

3.2 Heat affected zone

3.2.1 High heat input (30 amp, 807 W)

The microstructure in the HAZ for the 30 amp condition is coarse tempered martensite as shown in Fig. 5. The grains are smaller than those found in the base material and the fraction of martensite is noticeably increased as evidenced by smaller

grain size (Fig. 5 compared to Fig. 4). Hardness testing within the HAZ of the 30A specimen resulted in a 43% increase in hardness when compared to the base material.

3.2.2 Moderate heat input (27 amp, 612 W)

The microstructure in the HAZ for the 27 amp condition is also coarse tempered martensite. These results are not shown for brevity, but the microstructure of the 27 amp condition was very similar to the 30 amp condition. The grains are smaller than those in the base material and the fraction of martensite is noticeably increased. Hardness testing within the HAZ of the 27 amp specimen resulted in a 42% increase in hardness when compared to the base material which was virtually identical to the hardness results of the 30 amp condition. There is no major notable difference in either the microstructure or hardness of the 27 amp condition over the 30 amp condition suggesting that there is a threshold condition above which little change in of the workpiece occurs.

3.2.3 Low heat input (25 amp, 483 W)

Unlike in the previous specimen conditions, the microstructure in the HAZ for the 25A amp condition did not appear to deviate from the base material as shown in Fig. 6. The grains are similar to those of normal tempered martensite as found in Fig. 4. Hardness testing within the near-surface heated region of the 25 amp sample shows no significant increase in hardness due to laser heating.

4. Discussion

The formation of martensite occurs when a ferrous material is raised beyond the austenite transition (A1) temperature and then is rapidly cooled or quenched. For HY-80 this transition

temperature is approximately 727°C. The transformation of ferrite to austenite and to martensite upon cooling is well established [29] and more recently the specifics of these transformations in low-carbon steels following laser heating or joining has also been established [30, 31]. Based on the results from the 25 amp specimens, temperature within the workpiece during the 25 amp condition did not rise above the A1 temperature.

In previously reported results [17], modelling results of the 25 amp condition showed that temperature remained below the A1 transition temperature which is consistent with the metallographic results shown here (Fig. 6). In this report, the temperature analysis has been extended to the 30 amp condition and the modeling results predicted a temperature profile that includes a HAZ above the A1 transition temperature (Fig. 7). The modeling results shown in Fig. 7 show the longitudinal temperature profile along the laser path and show the higher temperature behind the laser and lower temperature ahead of the laser (hence the asymmetric shape of the profile in Fig. 7). The depth of the temperature profile can be compared to the visible HAZ (shown in later Figures).

Results from this research suggest that a current at or above 27 amp and a scan rate of 100 MMPM does cause HY-80 to rise above the A1 temperature, resulting in visible hardened HAZ regions discussed earlier. When scan rate was held constant at 100 MMPM and HPDL current was varied from 25 amp to 30 amp on a bead-blasted plate, a clear difference in HAZ size as a function of current became evident. Fig. 8 compares three transverse sections heated with three different amperages at the same transverse speed. As discussed previously, the 25 amp sample showed no signs of a HAZ, while the 27 amp and 30 amp experienced significant HAZ development. The HAZ for the 30 amp

sample was over three times deeper than that the 27 amp condition and over 1.5 times wider. This suggests that small changes in amperage results in dramatic changes in temperature of the work piece and corresponding phase changes. HAZ dimensions for each condition are summarized in Table III. The depth of the HAZ in the 30 amp condition is also notably similar (approximately 1200 μm or 1.2 mm) to that predicted in Fig. 7.

Within a single condition, very distinct transitions between the HAZ and base material were observable using microscopy and hardness analysis. Fig. 9 shows three micrographs corresponding to the regions labeled in the macrograph for the 30 amp condition at 100 MMPM . Increased martensite is easily identifiable when comparing the base metal and the HAZ by the increased needle-like structure and martensitic grain density. Additionally, the transition zone image provides a clear distinction between the base tempered martensite and the HAZ coarse tempered martensite.

Although the primary goal of DLAFSW is a reduction in tool wear due to workpiece softening, another possible alternative is increased welding speed for a given frictional loading. Because of this, additional traverse speeds were analyzed for the high heat input condition of 30 amps. As expected, increasing the traverse rated reduced the size of the HAZ considerably, as shown in Fig. 10. Since the laser array spent less time transferring energy to the workpiece, the HAZ was seven times smaller when the speed was doubled. Although the HAZ was not eliminated, the depth was reduced enough to not affect a significant portion of the material. Future research should focus on whether appropriate softening can take place in conjunction of these increased rates since the minimized HAZ is desirable along with increased welding speeds.

Finally, change in hardness was determined to be directly related to the formation of martensite in the material. Fig. 11 is a consolidated plot of hardness versus position for all three laser amperage conditions and clearly shows that the additional formation of martensite due to laser heating above 25 amps causes a marked increase in hardness. The results also show that the relative increase in hardness is the same for both the high heat condition (30 amp) and the moderate heat condition (27 amp) suggesting that increase in hardness is only due to the formation of martensite above the A₁ temperature not any other grain coarsening effect. Fig. 11 also shows that the nominal HAZ for the 27 amp condition is smaller in width than the 30 amp condition in the same manner that Fig. 11 shows that the depth of the HAZ is smaller for the same comparison. A summary of hardness results from this research can be found in Table IV.

5. Conclusions

Using HPDLs in conjunction with FSW can provide a unique and powerful application for high energy lasers. The improved efficiency, compact size, safety and simplicity of operation of HPDLs make them good candidates for use during machining and surface treatment of steels and in conjunction with a traditional FSW system to make a DLAFSW system. Several conditions of HPDL parameters for use in DLAFSW were analyzed in this research for optimization on HY-80 steel. The following conclusions were made:

- Laser operation at less than 27 amps results in no noticeable change in microstructure at a steady traverse speed of 100 MMPM. Conversely, laser operation at 27 amps or greater causes a noticeable HAZ and change in microstructure.

- The HAZ of laser heated HY-80 rises above the A1 temperature and experiences approximately 40% increase in hardness when compared to the base metal after cooling. This increase in hardness is directly due to increased martensite formation.
- An increase in traverse rate significantly reduces the size of the HAZ which may allow for faster manufacturing.
- The formation of a HAZ and additional brittle martensite in HY-80 can be prevented through the optimization of laser amperage and transverse speed.

Acknowledgements:

The authors are eternally grateful to have received guidance from and worked with the late Dr. W. Howard Lowdermilk, to whom this article is dedicated. This work was funded through a Laboratory Directed Research and Development grant 15-ERD-037 and performed under the auspices of the U.S. Department of Energy by Lawrence Livermore National Laboratory under contract DE-AC52-07NA27344.

References

- [1] W.M. Thomas, E.D. Nicholas, J.C. Needham, M.G. Murch, P. Templesmith, C.J. Dawes, 1991.
- [2] W.M. Thomas, P.L. Threadgill, E.D. Nicholas, *Sci. Technol. Weld. Joining*, 4 (1999) 365-372.
- [3] R.S. Mishra, Z.Y. Ma, *Mater. Sci. Eng., R*, 50 (2005) 1-78.
- [4] R. Nandan, T. DebRoy, H.K.D.H. Bhadeshia, *Prog. Mater Sci.*, 53 (2008) 980-1023.
- [5] A. Steuwer, S.J. Barnes, J. Altenkirch, R. Johnson, P.J. Withers, *Metallurgical and Materials Transactions a-Physical Metallurgy and Materials Science*, 43A (2012) 2356-2365.
- [6] R.A. Prado, L.E. Murr, D.J. Shindo, K.F. Soto, *Scripta Mater.*, 45 (2001) 75-80.
- [7] W.A. Ferrando, in: N.S.W.C.C. Division (Ed.), West Bethesda, MD, 2008.
- [8] H. Montazerolghaem, M. Badrossamay, A.F. Tehrani, *Investigation of Vibration Assisted Friction Stir Welding*, in: M. Merklein, H. Hagenah (Eds.) *Material Forming - Esaform 2012*, Pts 1 & 2, 2012, pp. 741-746.
- [9] P.C. Sinclair, W.R. Longhurst, C.D. Cox, D.H. Lammlein, A.M. Strauss, G.E. Cook, *Mater. Manuf. Processes*, 25 (2010) 1283-1291.
- [10] H. Bang, H. Bang, G. Jeon, I. Oh, C. Ro, *Materials & Design*, 37 (2012) 48-55.
- [11] B. HanSur, B. HeeSeon, S. HyunJong, J. SungMin, *Materials & Design*, 51 (2013) 544-551.
- [12] E. Scutelnicu, D. Birsan, R. Cojocaru, *Proceedings of the 4th International Conference on Manufacturing Engineering, Quality and Production Systems (MEQAPS 2011). Recent Advances in Manufacturing Engineering*, (2011) 97-102.
- [13] B.M. Tweedy, W. Arbegast, C. Allen, *Friction Stir Welding Processing III*, (2005) 97-104.
- [14] G. Kohn, Y. Greenberg, I. Makover, A. Munitz, *Welding Journal*, 81 (2002) 46-48.
- [15] G. Casalino, S. Campanelli, A.D. Ludovico, N. Contuzzi, A. Angelastro, *High Power Laser Materials Processing: Lasers, Beam Delivery, Diagnostics, and Applications*, 8239 (2012).
- [16] M. Merklein, A. Giera, *International Journal of Material Forming*, 1 (2008) 1299-1302.
- [17] B.W. Baker, T.R. McNelley, M.J. Matthews, M. Rotter, A. Rubenchik, S. Wu, *Use of High-Power Diode Laser Array for Pre- and Post- Weld Heating During Friciton Stir Welding of Steels*, in: R.S. Mishra (Ed.) *Friction Stir Welding and Processing VIII*, Wiley, 2015.
- [18] A.P. Reynolds, W. Tang, M. Posada, J. DeLoach, *Sci. Technol. Weld. Joining*, 8 (2003) 455-460.
- [19] B. Baker, E.S. Menon, T. McNelley, L. Brewer, B. El-Dasher, J. Farmer, S. Torres, M. Mahoney, S. Sanderson, *Metall. Trans. E*, (2014) 1-13.
- [20] L. Li, *Optics and Lasers in Engineering*, 34 (2000) 231-253.
- [21] W.Q. Chen, C.S. Roychoudhuri, C.M. Banas, *Optical Engineering*, 33 (1994) 3662-3669.
- [22] F. Bachmann, *Appl. Surf. Sci.*, 208 (2003) 125-136.
- [23] S.R. Heller, I. Fioriti, J. Vasta, *Naval Engineers Journal*, (1965) 29-44.
- [24] W.C. Stewart, *Mechanical and Aerospace Engineering*, Naval Postgraduate School, Monterey, CA, 2011.
- [25] G.W. Young, *Mechanical and Aerospace Engineering Department*, Naval Postgraduate School, Monterey, CA, 2012.
- [26] B. Shi, H. Attia, *Journal of Manufacturing Science and Engineering-Transactions of the Asme*, 135 (2013).
- [27] B.H. Halverson, John F., *Journal of Ship Production*, 23 (2007) 3.
- [28] C. Cheng, H. Lin, J. Lin, *Science and Technology of Welding and Joining*, 15 (2010) 5.
- [29] D. Koistinen, R. Marburger, *Acta Metall.*, 7 (1959) 59-60.

[30] K.H. Lo, F.T. Cheng, H.C. Man, *Surf. Coat. Technol.*, 173 (2003) 96-104.
[31] M. Xia, E. Biro, Z. Tian, Y.N. Zhou, *ISIJ Int.*, 48 (2008) 809-814.

Figure Captions:

Figure 1. (a) High power diode laser (HPDL) beam profile at varying currents (measured on a beam dump not the HY-80 workpiece) and (b) power versus current of the HPDL array. Slow and fast axis refer to divergence of the laser diode array. The fast axis is the axis perpendicular to the plane of the diode waveguide and corresponds to steeper divergence.

Figure 2. Top view of example HY-80 plate with three different laser preheating runs showing the size and shape of the heated area with respect to laser amperage. The size and shape of the heated area is similar to the path of a typical friction stir welding tool.

Figure 3. Proposed condition with increasing laser current to 30 amps followed by reduction in current to 25 amps at the end of the laser run. Temperature sensitive lacquers with transition temperature shown were applied prior to heating to indicate nominal surface temperature.

Figure 4. (a) Optical micrograph and (b) scanning electron microscope secondary electron image from transverse view of base material exhibiting tempered martensitic microstructure. Images (a) and (b) are not from the same exact location but are both taken from representative areas of the base material.

Figure 5. (a) Optical micrograph and (b) scanning electron microscope secondary electron image from transverse view of 30 amp heat affected zone exhibiting coarse martensitic microstructure. Images (a) and (b) are not from the same exact location but are both taken from representative areas of the heat affected zone.

Figure 6. Figure 6. Optical micrograph of (a) 25 amp heat affected zone and (b) base metal showing no significant change in microstructure at low power.

Figure 7. Figure 7. Longitudinal cross-section view of the theoretical temperature field during a steady state portion of a 30A run at 100 MMPM.

Figure 8. Comparison of 25, 27, and 30A heat affected zone dimensions at 100 MMPM scan rate.

Figure 9. Visible transitions within 30A 100 MMPM transverse HY-80 specimen.

Figure 10. Effect on increasing traverse speed of 30 amp high power diode laser on HY-80.

Figure 11. Hardness profiles across heat affected zones for all amperage conditions at normal traverse speeds (100 MMPM). A representative macrograph of the 30 amp condition is shown for reference. Lower amperages produce smaller (in both width and depth) heat affected zones compared to the 30 amp condition.

Table I. Chemical composition for HY-80 (in wt%).

Element	HY80 nominal composition	Base Material	Heat Affected Zone
C	0.12 – 0.18	-	-
Si	0.15 – 0.35	0.18	0.18
Mo	0.20 – 0.60	0.31	0.21
Cr	1.00 – 1.8	1.24	1.38
Ni	2.00 – 3.25	1.91	1.69
Cu	0.25 max	0.29	0.19
Fe	balance	95.0	95.4

Table II. Summary of laser heating conditions analyzed consisting of three current conditions and three different traverse speeds.

Current (Amps)	Power (W)	Nominal Heat Input	Traverse Speed (MMPM)
30	800	High heat input	200
30	800	High heat input	150
30	800	High heat input	100
27	612	Moderate heat input	100
25	158	Low heat input	100

Table III. Summary of heated affected zone (HAZ) dimensions.

Current (Amps)	Traverse Speed (MMPM)	HAZ Depth (mm)	HAZ Width (mm)
30	200	0.17	6.73
30	150	0.60	9.30
30	100	1.20	10.9
27	100	0.35	6.60
25	100	None	None

Table IV. Summary of hardness results.

Current (Amps)	Traverse Speed (MMPM)	Percent Increase in Hardness	
		HAZ	Transition Zone
30	200	40%	20%
30	150	42%	23%
30	100	46%	21%
27	100	42%	24%
25	100	None	None

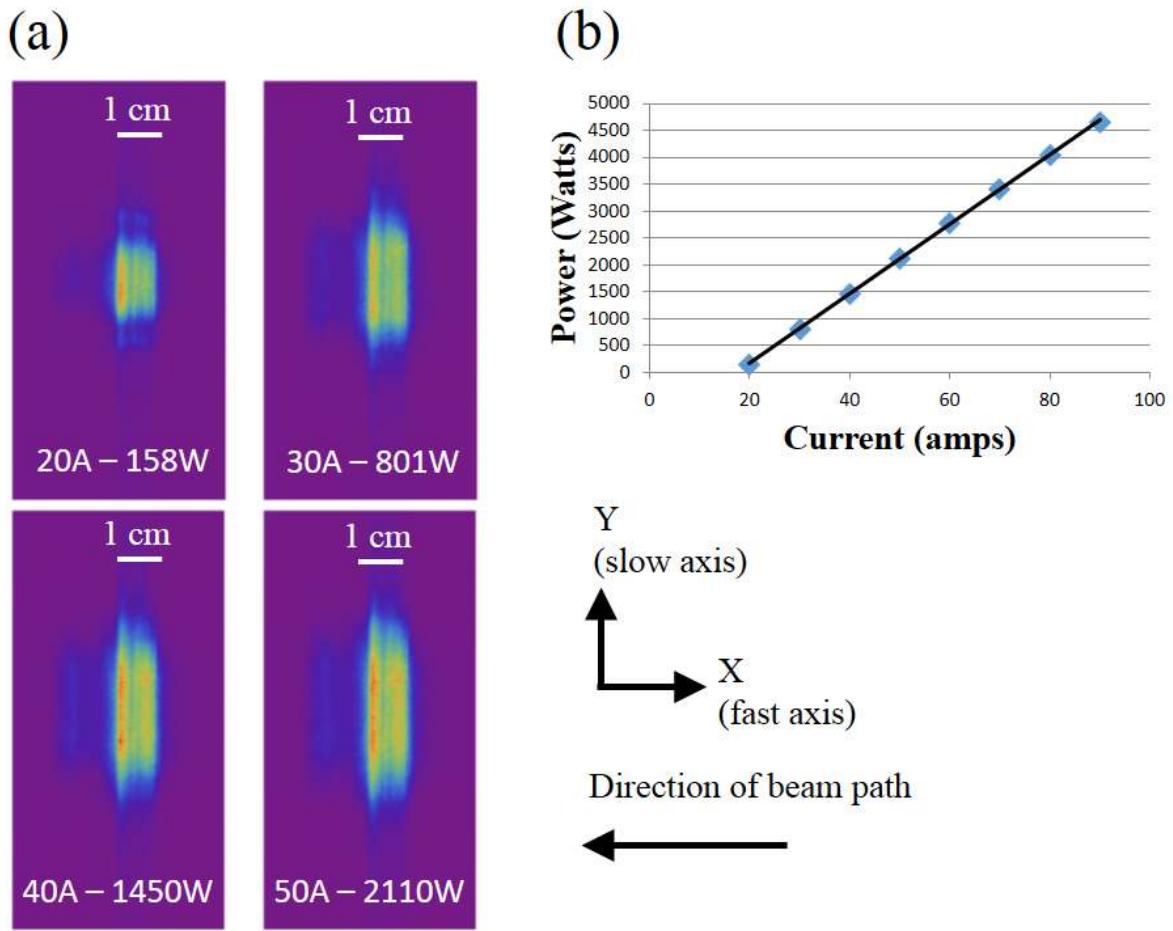


Figure 1. (a) High power diode laser (HPDL) beam profile at varying currents (measured on a beam dump not the HY-80 workpiece) and (b) power versus current of the HPDL array. Slow and fast axis refer to divergence of the laser diode array. The fast axis is the axis perpendicular to the plane of the diode waveguide and corresponds to steeper divergence.

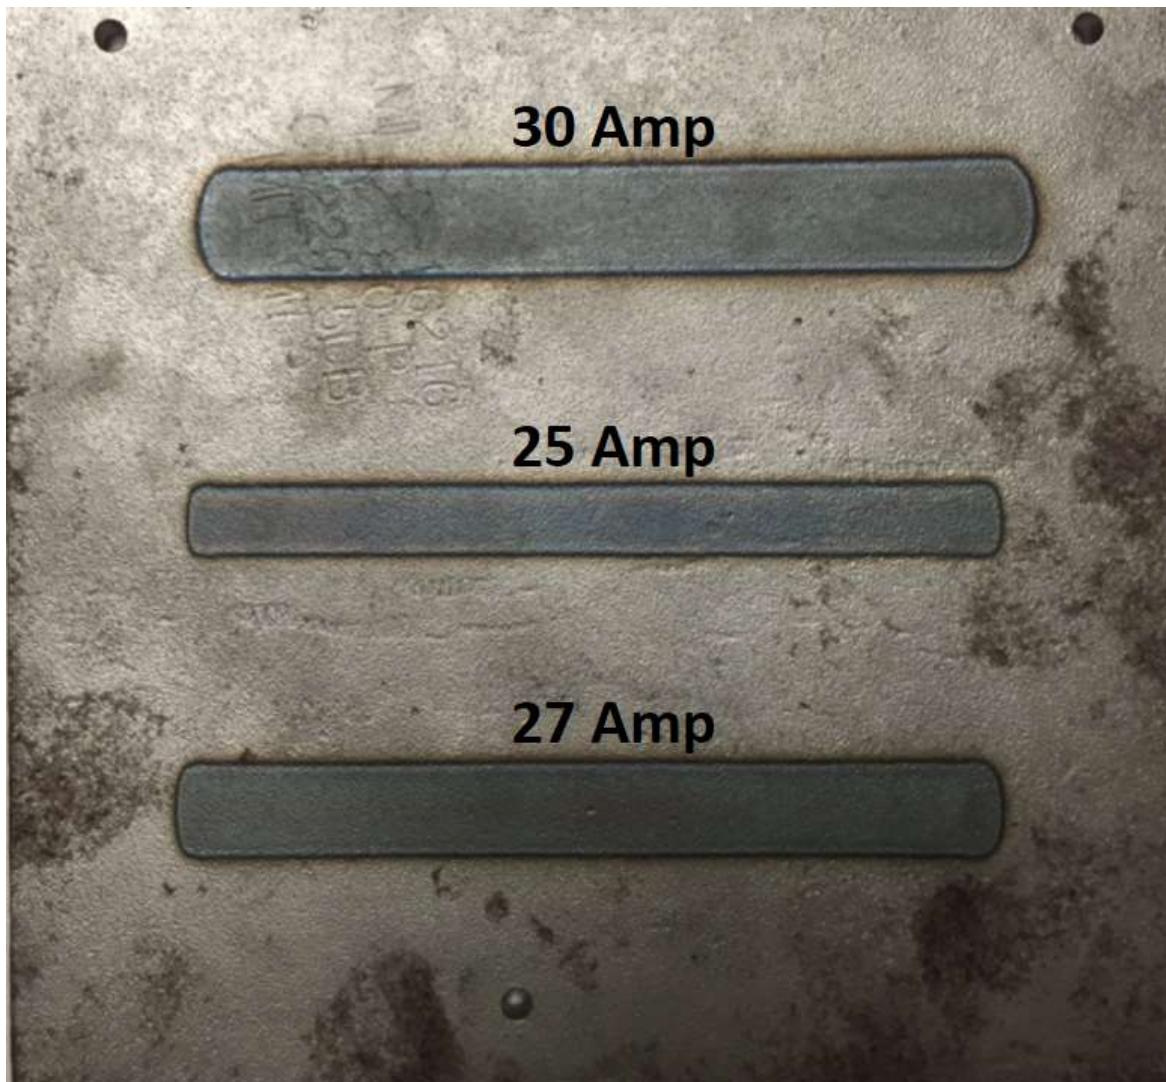


Figure 2. Top view of example HY-80 plate with three different laser preheating runs showing the size and shape of the heated area with respect to laser amperage. The size and shape of the heated area is similar to the path of a typical friction stir welding tool.

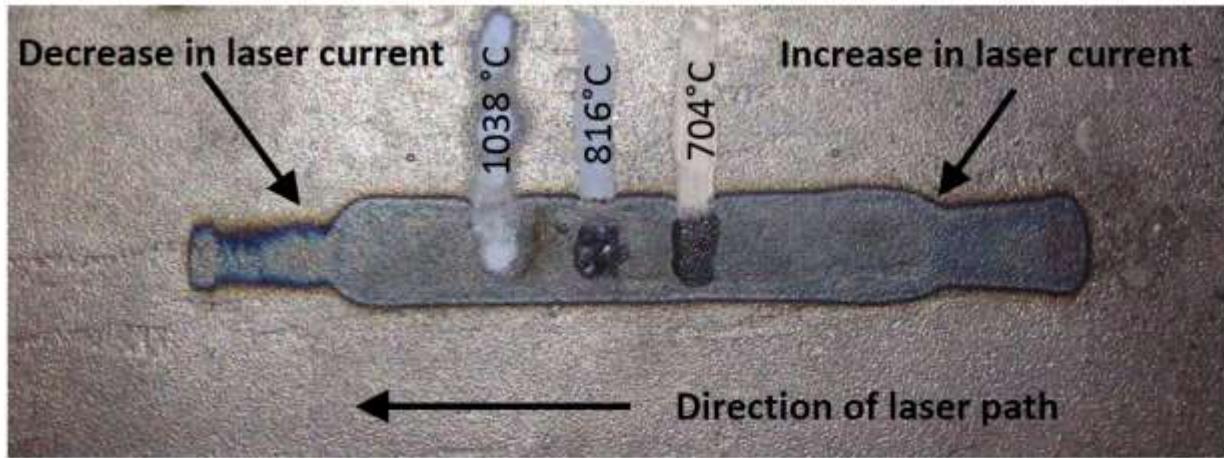


Figure 3. Proposed condition with increasing laser current to 30 amps followed by reduction in current to 25 amps at the end of the laser run. Temperature sensitive lacquers with transition temperature shown were applied prior to heating to indicate nominal surface temperature.

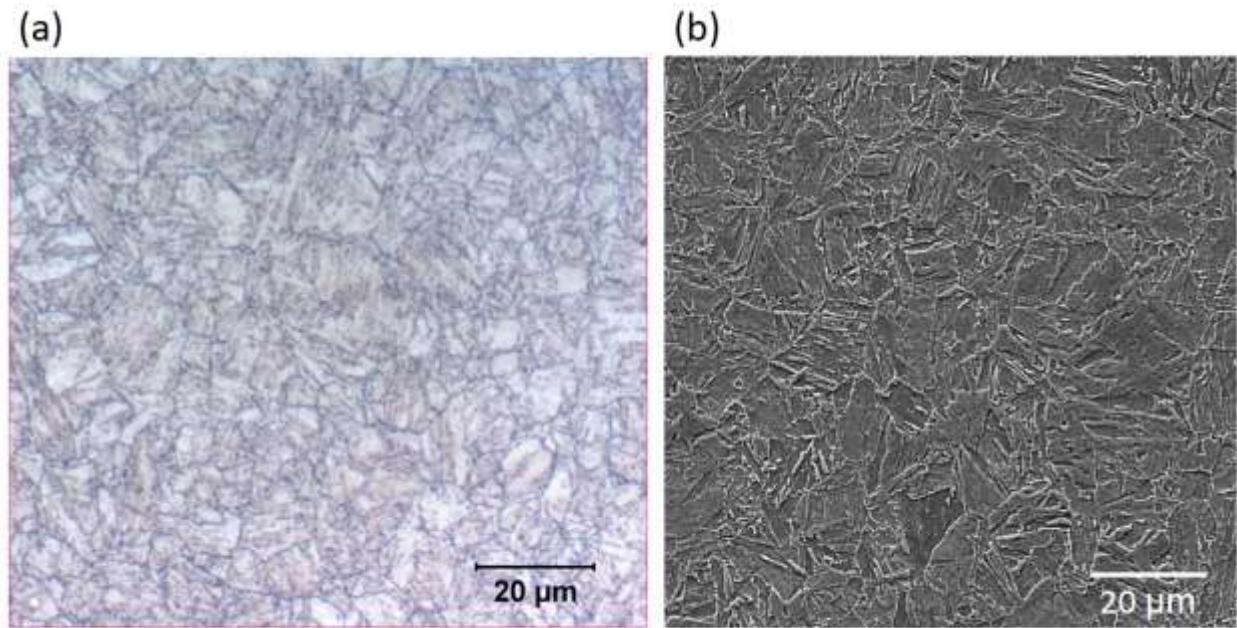


Figure 4. (a) Optical micrograph and (b) scanning electron microscope secondary electron image from transverse view of base material exhibiting tempered martensitic microstructure. Images (a) and (b) are not from the same exact location but are both taken from representative areas of the base material.

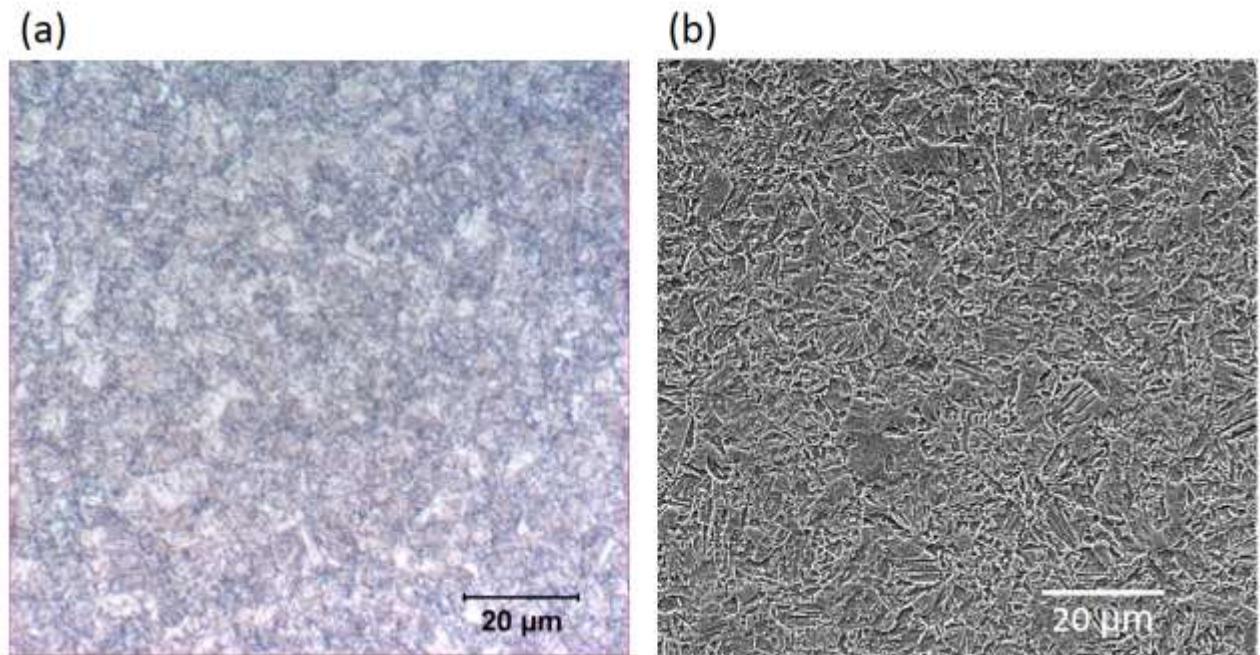


Figure 5. (a) Optical micrograph and (b) scanning electron microscope secondary electron image from transverse view of 30 amp heat affected zone exhibiting coarse martensitic microstructure. Images (a) and (b) are not from the same exact location but are both taken from representative areas of the heat affected zone.

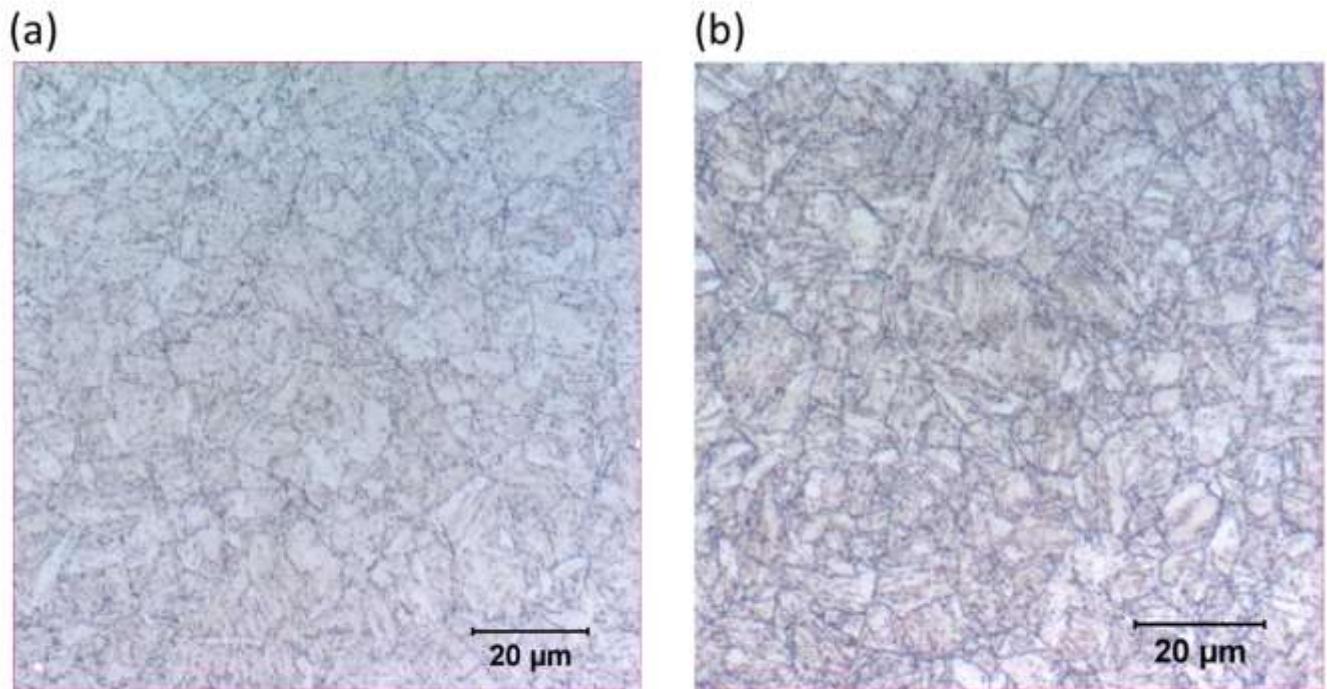


Figure 6. Optical micrograph of (a) 25 amp heat affected zone and (b) base metal showing no significant change in microstructure at low power.

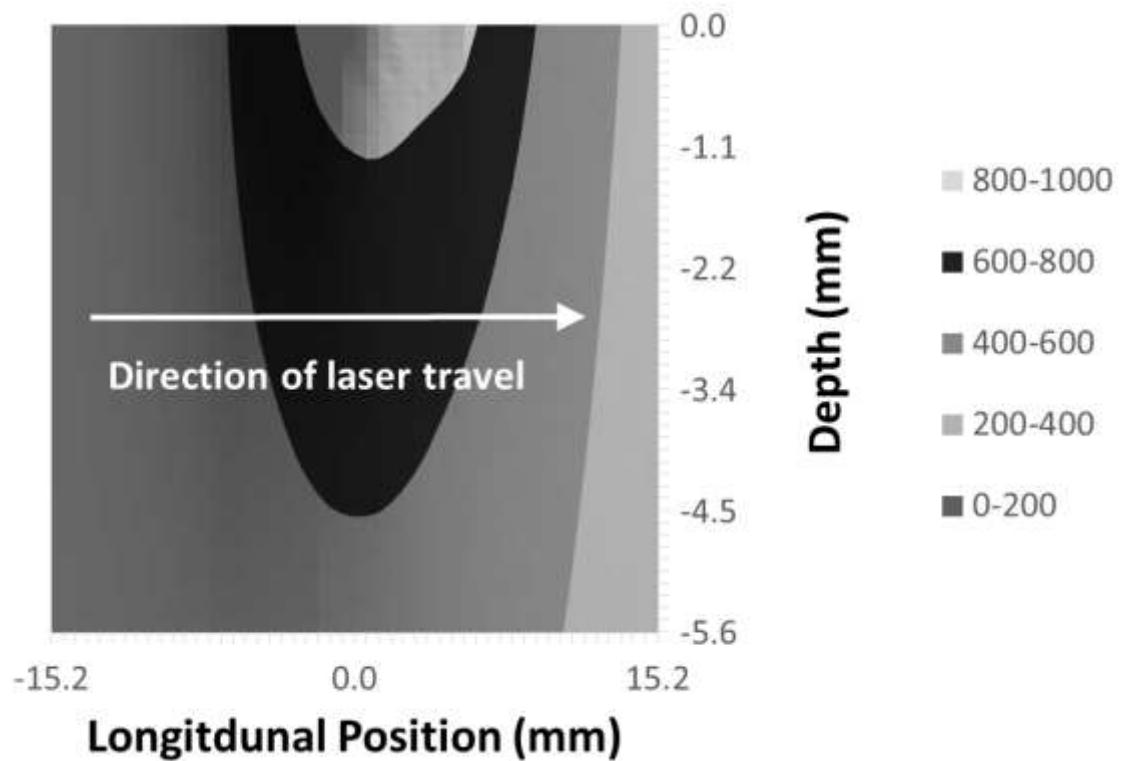


Figure 7. Longitudinal cross-section view of the theoretical temperature field during a steady state portion of a 30A run at 100 MMPM.

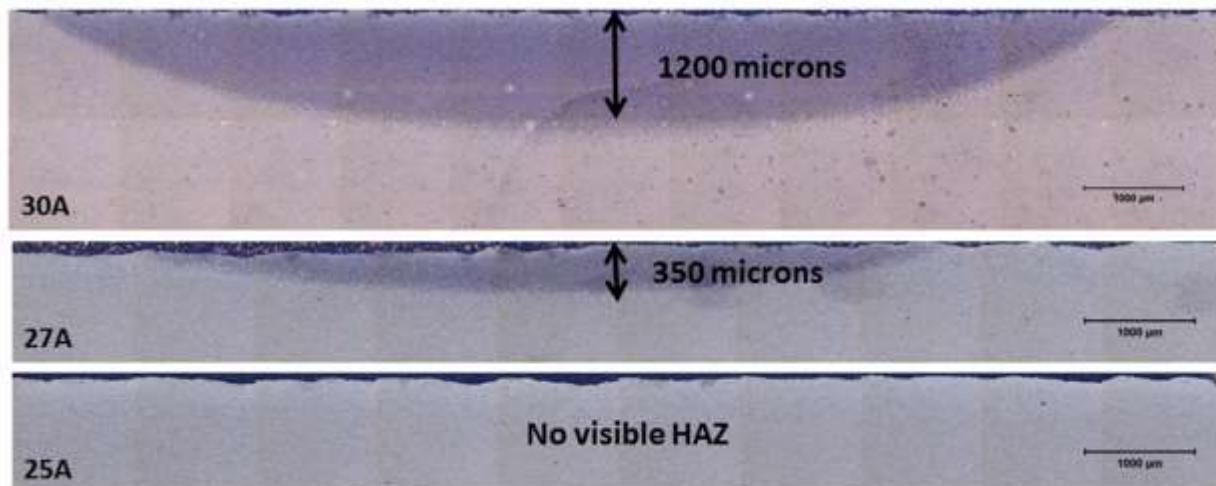


Figure 8. Comparison of 25, 27, and 30A heat affected zone dimensions at 100 MMPM scan rate.

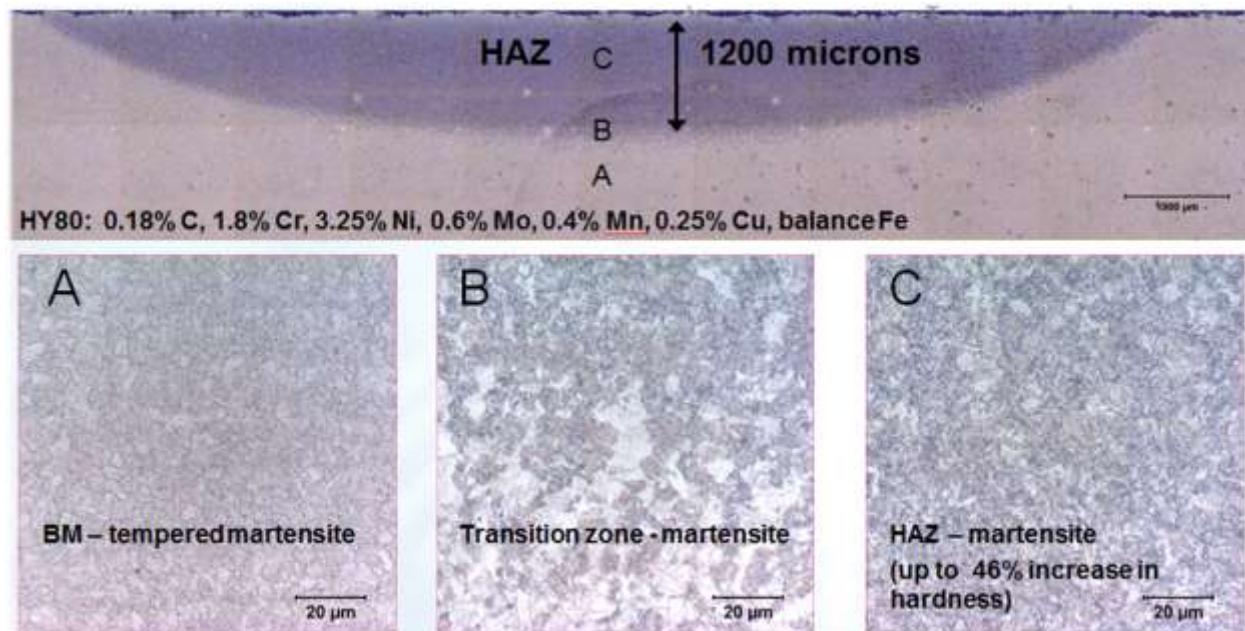


Figure 9. Visible transitions within 30A 100 MMPM transverse HY-80 specimen.

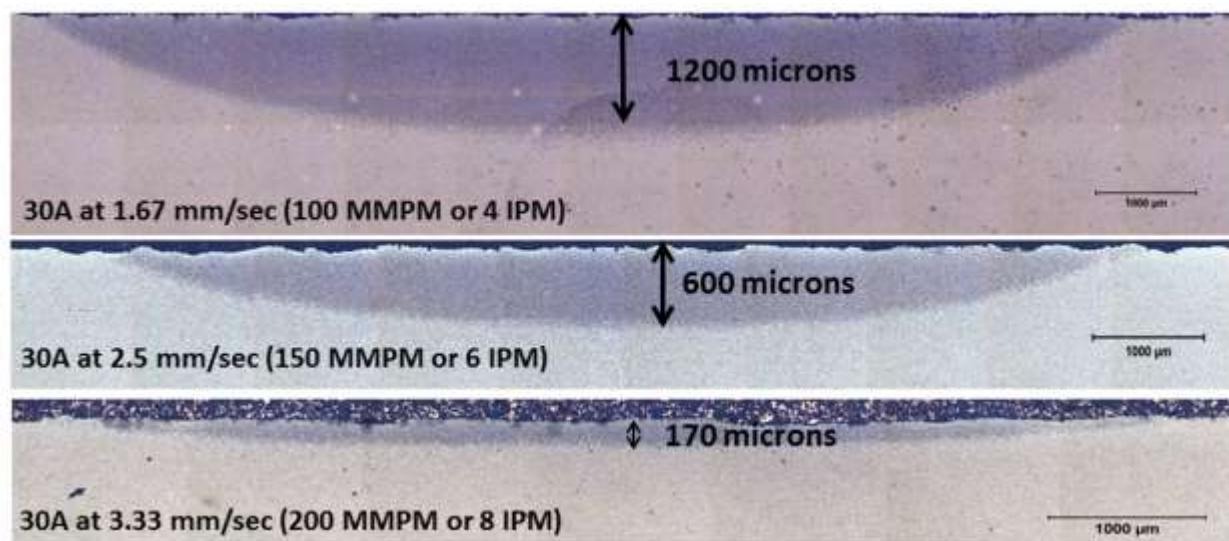


Figure 10. Effect on increasing traverse speed of 30 amp high power diode laser on HY-80.

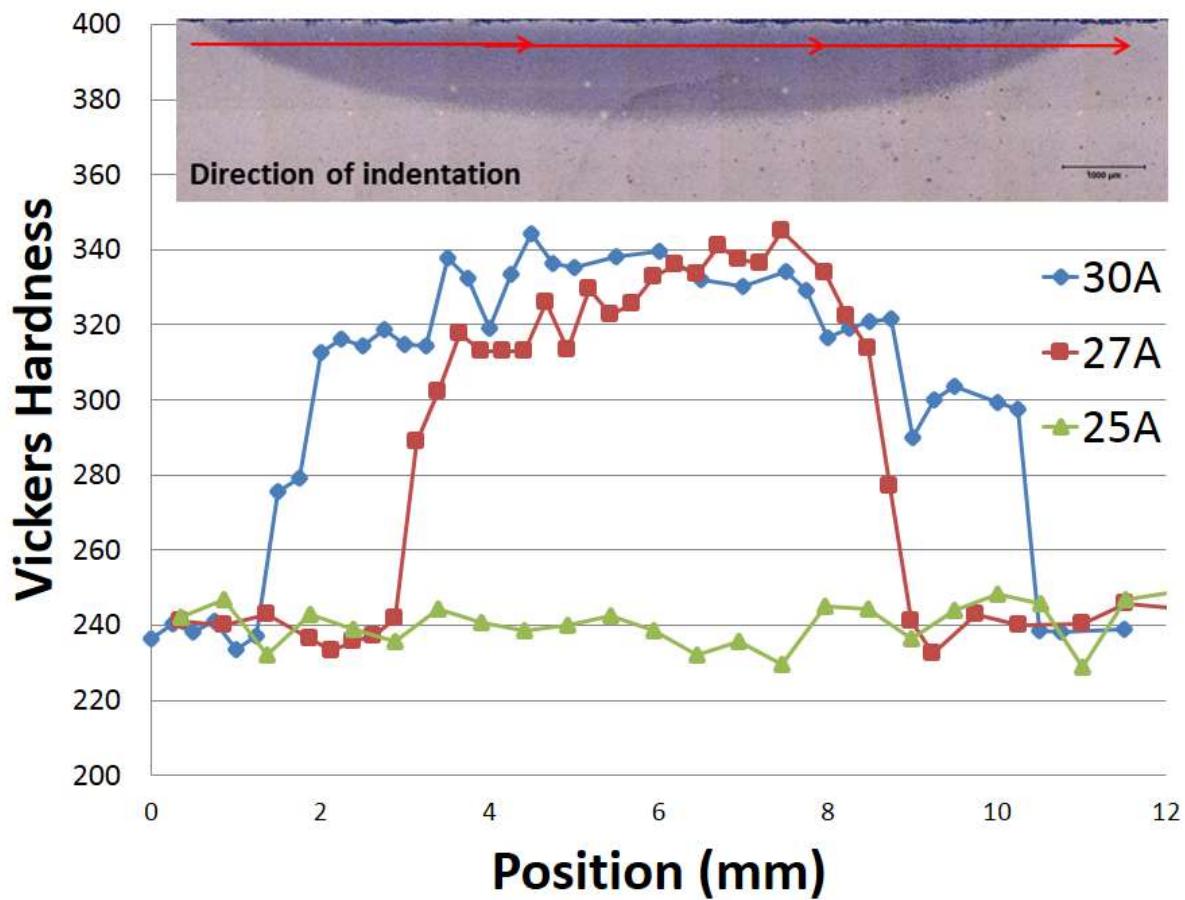


Figure 11. Hardness profiles across heat affected zones for all amperage conditions at normal traverse speeds (100 MMPM). A representative macrograph of the 30 amp condition is shown for reference. Lower amperages produce smaller (in both width and depth) heat affected zones compared to the 30 amp condition.