

Final Report

High Temperature Tribology Performance of Ni alloys under Helium Environment for Very High Temperature Gas Cooled Reactors (VHTRs)

Andreas A. Polycarpou (PI)

Department of Mechanical Engineering, Texas A&M University, College Station, TX, 77843, USA

Xinghang Zhang (Co-PI)

School of Materials Engineering, Purdue University, West Lafayette, IN, 47907, USA

Ali Beheshti (Co-PI)

Department of Mechanical Engineering, George Mason University, Fairfax, VA, 22030, USA

U.S. Department of Energy

Office of Nuclear Energy, Nuclear Energy University Program (NEUP)

Project No. NEUP 16-10732

Contract No. DOE DE-NE0008549

Project Period: October 2016 to September 2019

Contents

Executive summary.....	v
Acknowledgement	vii
Supported and Contributing Students	viii
Incomplete List of Publications	ix
1 Introduction and overview	1-1
1.1. Introduction	1-1
1.2. Report Overview	1-2
2 Materials, Aging Process, Tribology Testing and Analysis	2-5
2.1. Materials and Samples	2-5
2.2. Helium coolant	2-6
2.3. Aging Process.....	2-7
2.4. High temperature tribometer (for Helium)	2-9
2.5. Tribology Experimental conditions.....	2-12
2.6. Tribo-Chemical analysis	2-13
3 Tribology of Inconel 617	3-16
3.1. Effect of temperature and normal load.....	3-17
3.2. Effect of the environment.....	3-20
3.3. Effect of sliding velocity	3-21
3.4. Effect of sliding distance.....	3-23
3.5. Oscillational (Fretting) Experiments.....	3-23
3.6. Characterization and discussion	3-25
3.6.1. Surface morphology.....	3-25
3.6.2. SEM/EDS.....	3-27
3.7. Summary	3-32
4 Tribology of Alloy 800HT	4-33
4.1. Effect of Temperature and Normal Load	4-34
4.2. Effect of Environment.....	4-36
4.3. Effect of Sliding Velocity	4-38
4.4. Effect of Sliding Distance	4-39
4.5. Oscillational(fretting) Experiments.....	4-40

4.6.	Characterization and Discussion	4-42
4.6.1.	Surface Morphology	4-42
4.6.2.	SEM/EDS.....	4-45
4.7.	Summary	4-50
5	Tribo-Chemical analysis of Inconel 617	5-51
5.1.	Surface Morphology.....	5-52
5.2.	XRD Analysis	5-56
5.3.	Raman analysis.....	5-57
5.4.	TOF-SIMS depth profiling.....	5-59
5.5.	Summary	5-59
6	Tribo-Chemical analysis of Alloy 800HT	6-61
6.1.	Surface Morphology.....	6-62
6.2.	XRD Analysis	6-66
6.3.	Raman Spectroscopy studies.....	6-67
6.4.	TOF-SIMS depth profiling.....	6-69
6.5.	Summary	6-71
7	High temperature Nano-mechanical property characterization.....	7-72
7.1.	Nano/Micro Indentation	7-73
7.1.1.	Sample preparation	7-75
7.1.2.	Instrumented Nanoindentation.....	7-76
7.1.3.	High temperature parameter modifications	7-77
7.1.4.	Numerical Modeling	7-80
7.1.5.	Optimization Algorithm.....	7-81
7.1.6.	Results and discussion	7-83
7.1.7.	Challenges.....	7-89
7.1.8.	Nanoindentation summary	7-92
7.2.	Nano/micro-scratch Tests.....	7-93
7.2.1.	Experimental results.....	7-95
7.2.2.	Nano/micro-scratch summary	7-100
8	Contact Creep and Friction Modeling of Nickel Alloys at High Temperatures.....	8-101
8.1.	Numerical modeling.....	8-102
8.2.	Contact model verification	8-104

8.3.	Creep model verification.....	8-105
8.4.	Results and discussion.....	8-106
8.5.	Summary	8-113
9	Self-welding of Ni alloys.....	9-115
9.1.	Experimental Procedure	9-116
9.1.1.	Muffle furnace and tensile stage	9-116
9.1.2.	Materials and samples.....	9-117
9.1.3.	Experimental conditions	9-118
9.2.	Results and discussion.....	9-118
9.3.	Challenges	9-121
9.4.	Summary	9-123
10	Tribological Property enhancement.....	10-124
10.1.	Coating preparation	10-125
10.2.	Nano-tribological properties.....	10-126
10.3.	Macro tribological experiments.....	10-131
10.4.	Alternative surface treatment approach.....	10-133
10.5.	Summary.....	10-134
11	Optimum design/operating conditions.....	11-135
12	Conclusion	12-138
	References.....	12-142

EXECUTIVE SUMMARY

Currently the health and well-being of the global society are affected by energy source efficiency, reliability and environmental impact. Nuclear power is one of the reliable energy resources with low greenhouse gas emissions per unit energy generated. Findings from the current research directly result in more reliable and efficient nuclear power plants.

This project systematically studied the tribological (friction and wear) response of alloy 800H and Inconel 617 at very high temperatures and in the presence of helium coolant. The project targeted to address the need for mitigating the scarcity of available knowledge on the tribological performance of these alloys operating under relevant advanced reactor environments, as well as further enhancements in their tribological performance and durability.

In this project, a comprehensive experimental investigation was performed to study and compare the friction, surface damage (wear, self-welding, oxidation) and contact response of tribo-pairs consisting of alloys 800H and 617 in simulated helium and also in air up to 950 °C. The results generated here contribute to the design and licensing of high temperature gas cooled reactors (HTGR) and very high temperature gas cooled reactors (VHTR) in Nuclear Regulatory Commission (NRC), especially with the forthcoming addition of Alloy 617 to the ASME Code. In addition, micro/nano-mechanical testing and material characterization were performed in high temperatures along with analytical/numerical modeling to obtain a fundamental knowledge of the failure mechanisms and tribological response, as well as to develop predictive models. The research project also investigated different solutions such as identification of optimized operating conditions and surface modifications to alleviate tribological problems with these materials under HTGR/VHTR conditions.

The fundamental knowledge in high temperature tribology, especially in controlled gas atmosphere is limited, mainly due to complexity of experimental tests and analytical/numerical methods. The present work is pushing the boundaries of in-situ multiscale (nano/micro/macro) characterization of tribological materials in air/non-air ambient conditions at very high temperatures through novel experimental setups (e.g., very high temperature tribometer and very high temperature nano-indenter, under controlled Helium conditions). Also, comprehensive surface layer composition studies using advanced electron microscopy and other material

characterization techniques, provide insight into the prevention and failure mechanisms. In addition, this research impacts the surface engineering science community through identification of solutions to mitigate tribological problems under very high temperature conditions.

Despite its importance, the field of tribology has not been acknowledged appropriately in different communities. The expansion of tribological science especially in the fields that deal directly with society health, wealth, and comfort can provide tangible examples of engineering impact as well as useful and applicable science for the expert societies. This work provides new knowledge in the form of scientific papers, technical reports, and presentations that benefits a wide range of communities, and individuals. In addition, students active in the project had the opportunity to improve their hands-on skills on tribological testing, surface characterization, and nano-indentation measurements and simulations at high temperatures. Most importantly this work is showcasing the important tribological issues encountered in future state-of-the-art nuclear reactors. Also, through close collaboration between three research universities and through effective integration of the research into graduate and undergraduate classes, the benefit of the current project have reached several members of the society.

ACKNOWLEDGEMENT

This work was supported by the US DOE Office of Nuclear Energy's Nuclear Energy University Program (NEUP) under Contract No. DE- NE0008549.

The materials, Inconel 617 and alloy 800HT were provided by Idaho National Laboratory (INL) and Oak Ridge National Laboratory (ORNL), respectively.

We would like to thank Dr. Richard Wright of INL, Dr. Sam Sham of ANL and Dr. Yanli Wang of ORNL useful data as well as helpful discussions. We are thankful to Dr. S. Verkhoturov of Texas A&M University for the TOF-SIMS data. SEM, EDS, SIMS, Raman characterizations were performed at Materials Characterization Facility (MCF) at Texas A&M University.

SUPPORTED AND CONTRIBUTING STUDENTS

Texas A&M University

- Md Saifur Rahman, Graduate Student (PhD candidate)
- Yong Zheng, Graduate Student (PhD candidate)
- Hugo Rivera Alessio, Undergraduate student
- Jevon Phandi, Graduate Student (Currently at Schlumberger)

Purdue University

- Jie Ding, Graduate Student (PhD candidate)

George Mason University

- Sepehr Salari, Graduate Student (PhD candidate)
- Manisha Tripathy, Graduate Student (PhD candidate)

INCOMPLETE LIST OF PUBLICATIONS

Peer-Reviewed Journals

1	M.S. Rahman, J. Ding, A. Beheshti, X. Zhang, A.A. Polycarpou, Elevated temperature tribology of Ni alloys under helium environment for nuclear reactor applications, <i>Tribol. Int.</i> 123 (2018) 372–384. doi:10.1016/j.triboint.2018.03.021
2	M.S. Rahman, J. Ding, A. Beheshti, X. Zhang, A.A. Polycarpou, "Helium Tribology of Inconel 617 at Elevated Temperatures up to 950° C: Parametric Study." <i>Nuclear Science and Engineering</i> (2019): 1-15. https://doi.org/10.1080/00295639.2019.1582315
3	M.S. Rahman, Kyriaki Polychronopoulou., A.A. Polycarpou, Tribochemistry of Inconel 617 during sliding contact at 950 °C Under Helium Environment, <i>Journal of Nuclear Materials</i> (2019) https://doi.org/10.1016/j.jnucmat.2019.04.032
4	M.S. Rahman, J. Ding, A. Beheshti, X. Zhang, A.A. Polycarpou. Tribology of Incoloy 800HT for nuclear reactors under helium environment at elevated temperatures. <i>Wear</i> 2019;436–437:203022. doi:10.1016/j.wear.2019.203022.
5	M.S. Rahman, Kyriaki Polychronopoulou., A.A. Polycarpou, Tribochemical change of Alloy 800HT under sliding contact at elevated temperature in impure Helium Environment. <i>J. of Alloys and Comp.</i> 2019 (Under Review)

Manuscripts in Preparation

6	S. Salari, M.S. Rahman, A. Beheshti, A.A. Polycarpou. Elevated Temperature Mechanical Property of Inconel 617 Surface Oxide through Instrumented Nanoindentation. 2020
7	M.S. Rahman, A.A. Polycarpou, Challenges in high temperature nanoindentation of Ni-based superalloy-Inconel 617. 2020
8	M.S. Rahman, A. Beheshti, A.A. Polycarpou, Static to Kinetic Friction Transition study of Nickel Alloys at Elevated Temperature under Helium Atmosphere. 2020
9	M.S. Rahman, A.A. Polycarpou, Nano-tribological properties of oxide layers of Ni based superalloy by nanoscratch. 2020
10	S. Salari, A. Beheshti, A.A. Polycarpou. Contact Creep and Friction Modeling of Alloy Inconel 617 at High Temperatures. 2020
11	Y. Zhang, M.S. Rahman, A.A. Polycarpou, Diffusion bonding behavior of Ni-alloy at elevated temperature under Helium atmosphere. 2020
12	M.S. Rahman, A.A. Polycarpou, Effect of Layer thickness on mechanical and nano-tribological properties of Ni-Cr multilayer coatings at elevated temperature. 2020

Conference Proceedings, Poster and Presentation

1	Presented poster on "High-Temperature sliding wear behavior of Ni alloys under Helium environment" at the Society of Tribologists and Lubrication Engineers (STLE) conference, Atlanta, May 2017, won best student poster presentation award [Platinum] of STLE 2017.
2	"Hot Nanoindentation of Ni alloys" presented at the Society of Tribologists and Lubrication Engineers (STLE) conference, Atlanta, May 2017.
3	"High-Temperature sliding wear behavior of Ni alloys under Helium environment" presented at the 2017 ANS Winter Meeting and Nuclear Technology Expo, Washington DC and was published in ANS Transaction 2017.
4	"High-Temperature Nanoindentation of Ni Alloys Under Helium Environment" presented at 2017 ANS Winter Meeting and Nuclear Technology Expo, Washington DC and was published in ANS Transaction 2017.
5	"Hot nanoindentation modeling of high temperature Ni alloys under Helium environment" presented in November at the 2017 ASME IMECE in Tampa, FL.
6	"High-Temperature Sliding Wear Behavior of Ni Alloys Under Helium Environment" presented at the STLE Tribology Frontiers Conference, Chicago, October 2018.
7	"High-Temperature Nano-Indentation/Scratch of Ni Alloys Oxide Layer Under Helium Environment" presented at the STLE Tribology Frontiers Conference, Chicago, October 2018.
8	"Elevated Temperature Sliding Wear Behavior of Ni Alloys Under Helium Environment" presented at 2018 ANS Winter Meeting and Nuclear Technology Expo, Orlando and was published in ANS Transaction 2018.
9	"Adhesion, Self-Welding and Static Friction Coefficient of Ni Alloys at Elevated Temperature" - presented at the Society of Tribologists and Lubrication Engineers (STLE) conference, May 2019.
10	"Elevated Temperature Nanomechanical and Nanotribological Behaviors of Ni Alloys Surface Oxides: Part I-Experimental Study" - presented at the Society of Tribologists and Lubrication Engineers (STLE) conference, May 2019.
11	"Elevated Temperature Nanomechanical and Nanotribological Behaviors of Ni Alloys Surface Oxides: Part II-Finite Element Study" - presented at the Society of Tribologists and Lubrication Engineers (STLE) conference, May 2019.
12	"Self-welding Behavior of Ni-alloys at High Temperature under Helium Environment" - presented at the Society of Tribologists and Lubrication Engineers (STLE) conference, May 2019.
13	"Helium Tribology of Ni-Based Alloys at High Temperature Up to 950°C" – is accepted and will be presented at the Society of Tribologists and Lubrication Engineers (STLE) conference, May 2020.
14	"High-Temperature Nanomechanical Behavior of Inconel 617 Surface Oxides" – is accepted and will be presented at the Society of Tribologists and Lubrication Engineers (STLE) conference, May 2020.
15	"High-Temperature Contact Creep and Friction of Inconel 617 Surface Oxides" – is accepted and will be presented at the Society of Tribologists and Lubrication Engineers (STLE) conference, May 2020.

1 INTRODUCTION AND OVERVIEW

1.1. INTRODUCTION

The cost of energy generated from fossil fuels and their detrimental environmental effects has mandated major steps to escalate energy production from alternate sources more extensively and efficiently. One such energy resource is nuclear power with low greenhouse gas emissions per unit energy generated. Operating at high temperature (HT) is critical for nuclear reactors as it results in substantial thermal efficiency improvement. Therefore, in view of design demands, materials that can withstand HTs and harsh environment are deemed necessary for reliable and effective nuclear reactor operation. Alloy 800HT and Inconel 617 are principal candidates in high temperature gas cooled reactors (HTGR) and very high temperature gas cooled reactors (VHTR) with outlet temperatures of 700-950°C, which should be licensed for a 60-year life [1–3]. Of course, not all of the designed components can be targeted for such a long period of time; nonetheless, time intervals between two replacements should be sufficiently long and more importantly lifetime should be estimated as accurate as possible. Thus, there is no surprise that significant efforts have been made to characterize and predict the behaviors of these alloys. The literature is relatively abundant with works pertaining to mechanical behavior studies (mostly fatigue, fracture, and creep) [4–8] as well as oxidation and corrosion [2,3,9–14], for 800HT, Inconel 617 and other nickel alloys. Yet, before this study and similar projects funded by the Department of Energy in 2016, tribological studies of alloy 800HT and Inconel 617 interfaces were limited [15,16].

Sliding motion and its consequent friction and wear between metallic components at elevated temperatures can lead to severe surface damage and are important considerations for the effective performance of moving parts in nuclear reactors and power generation components. HT tribology is challenging on its own, and in the case of nuclear reactor conditions, the complexity is further compounded by the fact that the interface between metallic surfaces at HT remains non-lubricated with low water or oxygen partial pressure in the presence of Helium (He) and other minor gaseous ingredients [17]. Tribo-pairs in HTGR mainly include valves, valve seats, valve shafts, He circulator shaft and bearings, and control rods [18]. For these rubbing surfaces, accelerated friction and surface damage (mostly wear and small motion fretting wear) can have detrimental effects on

component performance and life. Besides, owing to the HT inert operating conditions along with extended dwell times, static/kinetic friction transition as well as self-welding are major concerns in moving components. During steady-state operation in HTGR/VHTR, the He coolant contains low levels of impurities including H₂, O₂, H₂O, CH₄, CO, CO₂, and N₂. Due to the presence of these impurities, the structural alloys used in the reactors can experience significant long-term corrosion involving oxidation, carburization or decarburization depending on temperature, oxygen partial pressure, carbon activity, and alloy composition at elevated temperatures.

The objective of this research project is to systematically evaluate the tribological response of 800HT and 617 alloys at relevant reactor operating temperatures (700-950 °C) and in the presence of He coolant. This research aims to address the need for a clear and inclusive understanding of the tribological performance of Ni based alloys in HT gas cooled reactors HTGR/VHTR operational environment as well as a further enhancement in HT durability and environmental compatibility of tribological components operating in HT He-coolant. This report is a summary of the work carried out by the interdisciplinary research team from Texas A&M University, Purdue University and George Mason University, USA, investigating the tribological behavior of Ni-based alloy, Inconel 617 and 800HT in simulated HTGR/VHTR atmosphere of He. Texas A&M University conducted the nano/micro and macro tribological experiment in a novel HT tribology setup. Purdue University team performed microscopy characterization and development of wear protective coatings, and George Mason University developed and executed the numerical simulations to extract mechanical properties, and further study scratch and frictional behavior at HTs (including creep effects).

1.2. REPORT OVERVIEW

Two alloy blocks of Alloy 800HT and Inconel 617 were provided by Idaho National laboratory (INL) and Oak Ridge National Laboratory (ORNL) to perform the experimental studies. This report describes the contact response of tribo-pairs including friction, wear, self-welding, oxidation, chemical and nanomechanical property measurements of the alloys surface at HT (up to 950°C) in simulated HTGR/VHTR He (and also in air, for comparison). In addition, experimental and numerical simulations for the micro/nano scale properties characterization of alloy surfaces and their oxide layers under HT, are presented through nano/micro indentation and scratch studies. The research project also investigated different solutions such as optimizing the

operating conditions, and surface modifications, such as surface treatments, and HT super hard coatings to mitigate tribological problems under HTGR/VHTR conditions. Detailed description of the experiments, materials development and modification and simulations, along with their results and discussion are presented in the following chapters of this final report. The focus of the chapters can be summarized as the following:

- **HT aging and testing process (Chapter 2):** The effect of long exposure to HT was by aging the samples inside a furnace. The as-received materials were exposed to HT condition of HTGR/VHTR to investigate the effect of oxidation on the surfaces of the samples. The HTGR/VHTR He condition was simulated in a vacuum furnace to prepare the aged samples to be used in the tribological experiments.
- **HT unidirectional and oscillatory tribology experiments (Chapter 3-4):** The response time as well as the capability to control the stroke of reactor's elements such as control rods/bearings and valves is highly critical for safety and reliable performance of nuclear reactors. This is mainly controlled by the state of friction between the component's interfaces. Hence, the values of kinetic and static coefficient of friction (COF) and the transitional COF from static to kinetic sliding are of a great concern for the tribo-pairs in contact. Unidirectional and oscillatory (fretting) macro tribological experiments were carried out in a custom made high-temperature tribometer (HTT) which simulates the reactors operating conditions. Tests were carried out for temperatures up to 950 °C for different normal loads and sliding velocities to study static/kinetic friction as well as wear volume.
- **Tribo-Chemical analysis (Chapter 5-6):** To understand the underlying mechanisms behind the friction and wear behaviors of the alloys in He HT, it is essential to investigate the complex tribo-chemical activity at the contact. The as-received, aged and tested samples were investigated thoroughly using techniques such as, cross section SEM/EDS, XRD, Raman, SIMS and nanoindentation to analyze the surface topography, tribo-chemical changes and their effects on the tribological behavior of the alloys.
- **HT nano/micro indentation and scratch (Chapter 7):** The nano-mechanical properties of the bulk and oxide surfaces of aged samples were investigated using HT nano/micro indentation and scratch techniques. Finite Element (FE) models for indentation and scratch were also developed and calibrated using the experimental data and used to extract the

mechanical properties of the alloy surface and to further study the contact and frictional behavior.

- **Friction Model (Chapter 8):** An asperity friction model was developed to study and predict static friction (sliding inception) of junctions due to HT creep at several loads and dwell times.
- **Self-welding (Chapter 9):** Surfaces with slight movement and static contact in nuclear reactors, can weld themselves together (via diffusion bonding). This phenomenon occurs by the exchange of metal atoms when metallic crystals of two virgin (oxide-free) surfaces come in direct contact for a sufficiently long time under loading, especially at HT. The intermittent motion of moving parts in HTGR/VHTR environment at HT promotes the possibility of self-welding and affect the performance. Accordingly, diffusion bonding of the alloys was investigated under different contact pressures and durations.
- **Tribological response enhancements (Chapter 10):** To improve the friction and wear properties of alloy 800HT and Inconel 617, multiple combinations of Ni/Cr multilayer coatings were developed and investigated, where the hardness values of the multilayers were tailored effectively by varying the individual layer thickness. Several other alternatives to coatings for alloy 800HT and Inconel 617 were searched in the literature and Laser Shock Peening (LSP) was selected as a potential promising remedy. Nano/macro-tribology investigation was performed on Ni/Cr multilayer coatings using both nanoscratch and macro tribology experiments at very HTs. In addition, LSPed alloys were tested at HT using the macro tribometer to investigate the tribological benefits of the treatment process.

2 MATERIALS, AGING PROCESS, TRIBOLOGY TESTING AND ANALYSIS

2.1. MATERIALS AND SAMPLES

The materials used in this study, Inconel 617 and alloy 800HT were received from Idaho National Laboratory (INL) and Oak Ridge National Laboratory, respectively. The chemical composition of the as-received alloys, given by the manufacturer, are shown in Table 1. Alloy 617 is strengthened by solid solution hardening provided by chromium, cobalt, and molybdenum as well as by intra and inter-granular carbide precipitates. The high-temperature oxidation resistance of the alloy is due to the high nickel and chromium content. Alloy 800HT was solution annealed at 1150°C and has a yield strength of 90 MPa at 750 °C, while Inconel 617 has a yield strength of 189 MPa at 800°C.

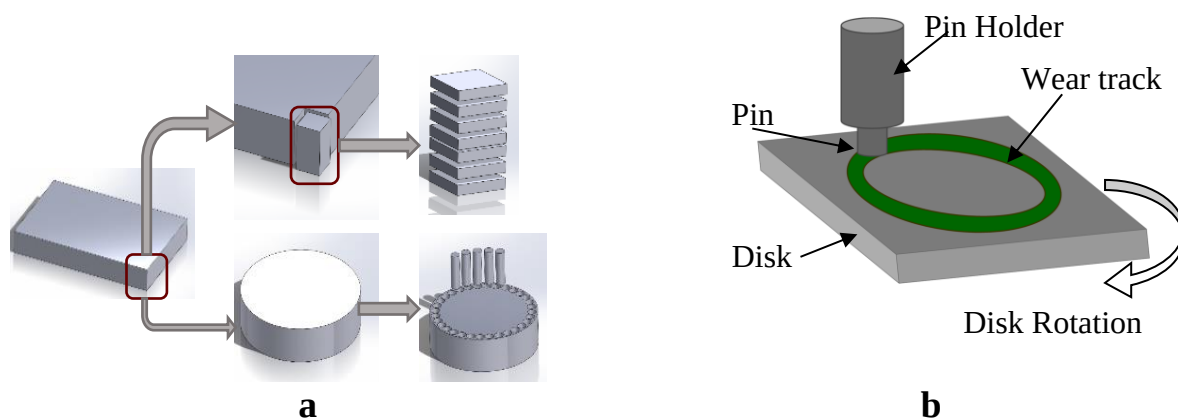


Fig. 1. (a) Sample preparation process, (b) Schematic of flat pin-on disk experimental configuration.

Fig. 1 shows the sample preparation and testing schematic of the pin-on-disk configuration. The material was received in the form of a rectangular bar and then machined to desired specifications. The disk samples (25.4mm x 25.4mm x 3.8mm) and flat cylindrical pins (6.3mm diameter and 19mm length) were machined using wire EDM (Electric Discharge Machining) process from the bulk material. The disk and pin contact surfaces were then polished to reach a surface roughness of approximately 0.3 μm (root-mean-square) for the unidirectional tribological experiments. For the nanoindentation experiments at HT, the surface was polished with 400, 600 and 800 grit SiC paper and then by mechanical polishing with 3 μm diamond grits to have 30-40nm rms values.

Fig. 2a shows the microstructure of the as-received Inconel 617 disk where it is evident that the grain size is not homogenous, and the inhomogeneous distribution of carbide is present. The average grain size is around 30-40 μm , which agrees with the findings of Ref. [3]. The microstructure of the as-received alloy 800HT, etched by 1:3 solution of nitric acid and hydrochloric acid is shown in Fig. 2b. The grain size is generally not homogenous, where twinning is observed.

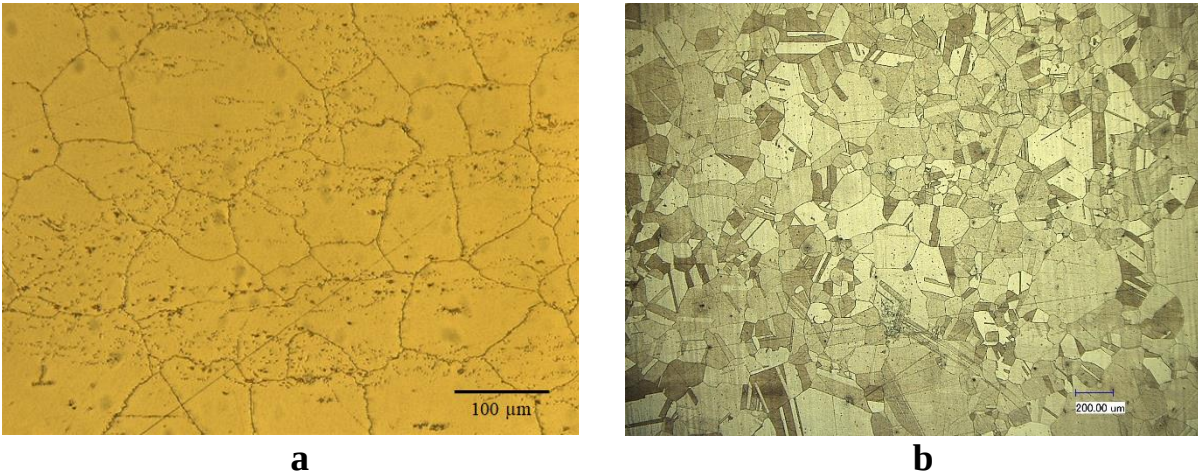


Fig. 2. Optical micrograph illustrating carbide distribution and grain size in as-received (a) Inconel 617, and (b) Alloy 800HT.

Table 1

Chemical composition of Inconel 617 and 800HT (in wt%)

Element	C	Mn	Fe	S	Si	Cu	Ni	Cr	Al	Ti	Co	Mo	P	B
Inc 617	0.08	0.23	1.46	0.001	0.2	0.02	53.27	22.02	1.10	0.32	11.91	9.38	0.005	0.002
800HT	0.061	1.27	46.24	0.001	0.42	0.2	30.65	19.7	0.56	0.54	0.1	-	0.024	-

2.2. HELIUM COOLANT

All high-temperature reactor systems operated to date using He coolant, have had extensive gas cleanup systems to keep the total impurity level in He typically below 10 ppm [2]. To create similar VHTR environment, three impurity combinations of He have been used in this study: 99.99% (*He3*), 99.999% (*He2*), and 99.9999% (*He1*) purity. He gas was injected during the He environment wear experiments as well as aging in HT furnace. The composition of He gas used in

the current project and the impurity levels reported for the steady-state operation for several of the VHTR are given in Table 2 [2,3]. During the initial comparative study, no significant difference was observed on the tribological behavior for the alloys in these three categories of He. So, the detailed study on the alloys has been performed using *He2*. Hereafter in this document anywhere mentioning He will refer to *He2* unless mentioned otherwise.

Table 2
Composition of impurities in Helium (in ppm by volume) [2,3]

	He	O ₂	H ₂ O	CH ₄	CO	CO ₂	H ₂	N ₂
Present research <i>He1</i>	Bal	0.5	0.2	0.1	0.1	0.1	-	0.5
Present research <i>He2</i>	Bal.	1	1	0.5	1	1	-	5
Present research <i>He3</i>	Bal	-	-	10	-	20	200	-
Dragon	Bal.	0.1	0.1	0.1	0.05	0.02	0.1	0.05
Peach Bottom	Bal.	-	0.5	1	0.5	<0.05	10	0.5
Fort St. Vrain	Bal.	-	1	0.1	3	1	7	-
AVR	Bal.	-	0.15	1	45	0.25	9	22
THTR	Bal.	-	<0.01	0.1	0.4	0.2	0.8	0.1

2.3. AGING PROCESS

An atmosphere-controlled furnace, GFC1400 was used for the aging of the samples in air and He environments. The furnace is capable of reaching a maximum temperature of 1400 °C. Before the He aging experiments, the furnace was purged with He after achieving -14.4 psi vacuum pressure in the chamber and the process was repeated three times. Then, a constant He flow rate was maintained at 5 scfh. The furnace is heated up to the test temperature in 2 hours while during cool down (at the completion of the experiments) the cooling rate is maintained at 1 °C/min or lower. Digital weighing balance (Satorius-CPA225D) of 0.01 mg accuracy was used for the weight measurements for all the samples before and after the experiments to measure the oxidation and wear rate. In this study, to simulate VHTR environment, 99.999% pure He is used in furnace aging. The supplied He contains very small amounts of impurities in (ppm): O₂(1), H₂O(1), CO₂(1),


CH₄(0.5), CO(1), N₂(5), which is similar to VHTR operational environments (refer to Table 2). The purging protocol ensured minimum (~35ppm) presence of oxygen content in the chamber. The oxidation rate is calculated as weight gain per unit surface area (g/m²), using the following equation:

$$\Delta W/S = (W - W_o)/S_o \quad (2.1)$$


where W_o is the weight before oxidation, W is the weight after oxidation, and S_o is the surface area before oxidation.

As shown in Fig. 3a, for Inconel 617, the weight gain follows a parabolic curve as a function of time at 950 °C as reported in the literature [11] (note that it is linear with respect to square root of time). Oxidation rate is almost similar to what was presented by Kim et al. at 1000 °C in two different types of He environments [13]. In the current study, higher initial oxidation weight gain is indicated by the short time aging of 1 hr and 10 hrs. The oxidation rate is higher than what the trend line indicated. The main reason can be the presence of oxygen as impurity in the current He environment, whereas none of the He environment had O₂ content in the work of Kim et al. at. Although O₂ and H₂O contents are significantly different in air and He environments, the weight gain behavior in air follows the same trend line as He.

As shown in Fig. 3b, the weight gain of alloy 800HT at 750 °C in air and He also followed a parabolic trend over time for both He and air environments. Unlike Inconel 617, the rate of weight gain in air is higher than in He for alloy 800HT. The weight change curves follow a parabolic law of oxidation governed by a relationship of the type $\Delta W/S = k^{1/2}t^{1/2}$ where k is the parabolic rate constant, and t is the oxidation time in hours. The parabolic rate constants were calculated from the fitting oxidation data sets to straight lines. The parabolic rate constants for alloy 800HT in air and He conditions are 1.23×10^{-12} and $3.87 \times 10^{-13} \text{ g}^2 \text{ cm}^{-4} \text{ s}^{-1}$, respectively. For Inconel 617, the rates are 2.27×10^{-12} and $2.31 \times 10^{-12} \text{ g}^2 \text{ cm}^{-4} \text{ s}^{-1}$ in He and air respectively for aging in 950 °C.

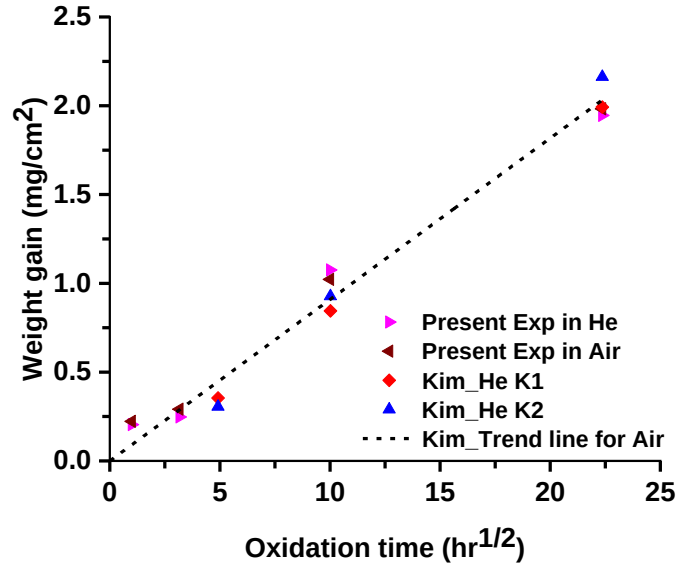

a

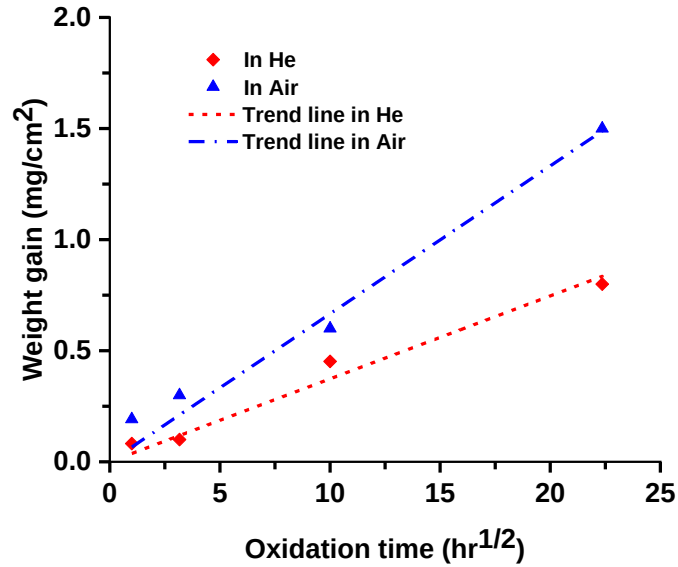

b

Fig. 3. (a) Weight gain with oxidation time for Inconel 617 in He at 950 °C and comparison with oxidation behavior at 1000 °C by Kim et. al. [13] with impurities of H₂, H₂O, CO, C₂O, CH₄ (He K1) and H₂O, CO, C₂O (He K2); (b) Weight gain in He and air over oxidation time of Alloy 800HT at 750 °C.

2.4. HIGH TEMPERATURE TRIBOMETER (FOR HELIUM)

A custom-built high temperature tribometer (HTT) is modified to perform unidirectional HT tribological experiments for alloy 800HT and alloy 617 in controlled environments (e.g., He with impurities). The HTT mimics the complex environmental conditions of nuclear reactors, and is capable of exploring the tribological characteristics of the alloys in HT gas cooled HTGR/VHTR operational environments.

The HTT is a specialized tribometer (shown in Fig. 4a) with pin-on-disk (ball-on-disk, flat pin-on-disk, and cylinder pin-on-disk) configurations that can perform wear and friction experiments for samples with a diameter up to 95 mm. The tribometer has the capability of unidirectional and oscillatory motions: rotational speeds up to 1000 rpm and oscillation frequencies up to 5 Hertz. The force transducer records the in situ normal (up to 45 N) and friction forces and uses them to calculate the in-situ COF. It has an enclosed chamber (Fig. 4b), which enables the control of the test atmosphere. Using a vacuum pump and ports, the chamber can be evacuated and then gas (e.g., He with different impurities) can be introduced. It is equipped with a “Transparent Furnace” based on the invention of Thomas Reed in 1970, which uses the infrared radiation to heat up the sample by reflecting substantially all infrared radiation on a thin gold coated quartz tube (Fig. 4c). Yet, sufficient visible radiation is transmitted so that the inside of the furnace can be viewed from the outside [19].

Fig. 4c shows a schematic view of the furnace with section views taken parallel and vertical to the rotational axis of the furnace. The outermost quartz muffle is a transparent quartz enclosure coated on the inner side with a thin gold film. The gold film enables the attainment of high operating temperatures as it has high reflectance for infrared radiation, while being thin allows visible light transmittance. The transparent furnace has the capability of reaching 1000 °C in reasonably short period of time with efficiency, comparable to the conventional infrared heated muffle furnace encased by conventional packed insulation, with the additional advantage of visibility. Beside the outermost quartz tube mentioned above, the furnace consists of an innermost clear quartz muffle in which the tribo-pair is inserted. These two quartz tubes are concentric creating a 4 mm annular space in-between, called the dead air space. The heating elements are located in the annular space wrapped around five alumina tubes in helical formation. Two ends of the heating wire are connected to the power source, well-protected from the metal body by alumina tubes. The heating wires are passed through slots on the alumina tubes to avoid reduction in the resistance of the heating element and effectiveness of the furnace due to heating wires connecting each other during operation. A ferritic iron-chromium-aluminum alloy (Fe-Cr-Al alloy) is used as the heating wire which is an advanced powder metallurgical, dispersion strengthened alloy with melting temperature of 1500 °C. Although originally 1 mm diameter heating wire was used in the furnace, as we seek to reach temperatures as high as 950 °C, especially in the presence of He coolant, the heating wire diameter was increased to 1.2 mm. A third quartz clear tube is placed in between the

2-10

heating elements and the outer gold-coated quartz tube to avoid contact and damage to the gold coating.

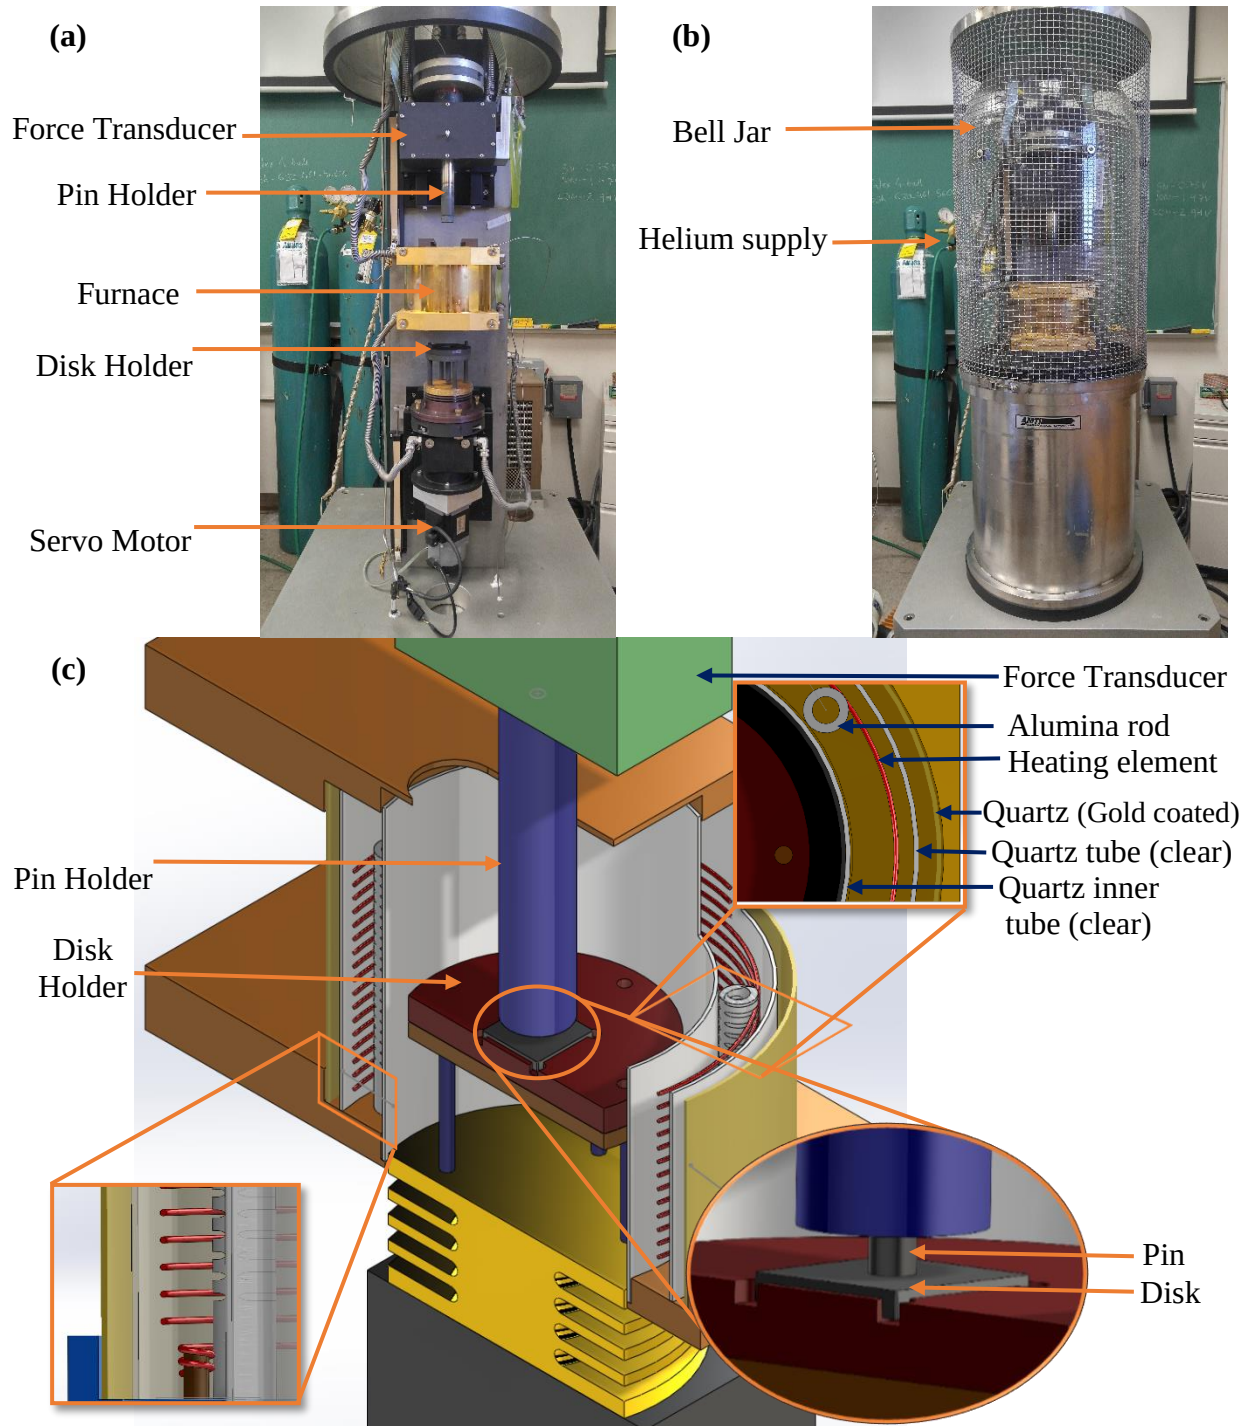


Fig. 4. High temperature tribometer (a) Tribometer setup, (b) Bell jar chamber for vacuum and controlled environment, (c) Furnace construction.

The disk holder is placed on the plate supported by four pins connected to the rotating shaft of the servo motor which is surrounded by a jacket of cooling fluid to ensure safe operation of the servo motor at HTs. The shaft near the furnace also has fins to increase heat transfer during rotation. The whole setup of the disk holder and motor (lower part) has vertical movement capability using another servo motor to move the sample in and out of the furnace. The pin is connected to the upper unit consisting of a pin holder made of Inconel 625, which is connected to a two-axis force transducer. The entire upper setup is mounted on a jack screw drive system and a servo motor to control the normal load and movement into and out of the furnace. Additionally, to have a precision control of the normal load, an electromagnetic actuator is placed in between the force transducer and the servo system bringing the resolution control of the normal load to 0.05 N. The force transducer is also jacketed by a cooling fluid to ensure correct measurement of forces at HTs. It is possible to measure and record the in-situ friction and normal loads along with the COF with the data acquisition system at 100 Hz.

2.5. TRIBOLOGY EXPERIMENTAL CONDITIONS

The experimental conditions for unidirectional sliding are summarized in Table 3. Two different tribo-pairs, Inconel 617 pin sliding on Inconel 617 disk and 800HT pin sliding on 800HT disk and two different gas environmental conditions (air and He) were selected for each tribo-pair. The HT tribological study was carried out at three different temperatures with the highest being 950 °C for Inconel 617. However, for alloy 800HT, the highest temperature was 750 °C as its mechanical properties degrade drastically beyond 800°C [4,7]. All the experiments were performed at three different normal loads and three sliding velocities along a circular path with 17.5 mm mean diameter. The tests were performed for a duration of 600 seconds with 24 m sliding distance.

Table 3
Tribology experimental conditions

Disk	Pin	Ambient	Temperature (°C)	Normal Force (N) [MPa]	Sliding velocity (m/s)
Inc 617 800HT	Inc 617 800HT	Air, He	25, 500, 950 25, 500, 750	5 [0.16], 10 [0.32], 20 [0.64]	0.04, 0.1, 0.15

For all of the experiments in He environment, the exact same experimental protocol was followed as described in Table 4. Before each HT test, the bell jar needs to be full of He and free of air.

Accordingly, the ball jar chamber was vacuumed to -14.3 ± 0.1 psi and then followed by flushing He in the chamber until the chamber has a positive pressure. To assure minimum possible amount of air in the bell jar chamber, the vacuum and flushing process were carried out three times. The He pressure in the chamber was maintained at 0.1 psi during heating up, during the experiment, and during the cooling down processes.

Table 4
Protocol for HTT experiments with Helium flow

Time (min)	State	He volume flow rate (l/min)	Relative Pressure (psi)
0	Initial condition	0	0
1-5	Test chamber vacuumed	0	-14.0 ~ -14.3
6-15	Helium flushed the test chamber	~25	0.1 ± 0.02
16-45	Vacuum and flushing of He (Two times)	~25	-14.3 / 0.1
46-55	Create positive pressure and execute test	~60 (Full Open)	0.1 ± 0.05
56-85	Heating the chamber	5-10	0.1 ± 0.02
86-95	Test	5-10	0.1 ± 0.02
96-185	Cooling	5-10	0.15 ± 0.02

2.6. TRIBO-CHEMICAL ANALYSIS

Sliding contact under HT conditions is influenced by both mechanical and chemical changes of the surfaces coming in contact, as well as the bulk material properties. The tribological behavior is further affected by the environment and gaseous content present during the HT contact. There are several studies which showed the chemical changes under He impurity at HT (thermal load only) [10,11,20] but there is none showing the effect of simultaneous presence of tribological action and gas atmosphere on the chemical changes of Inconel 617 and 800HT (co-presence of thermal/chemical/mechanical load). The present study focuses on the tribo-chemical changes taking place at the surface/interface contact of Inconel 617 under He and air atmospheres at HT of 950 °C, and 800HT at 750 °C. Subsequently we explain how these changes may have affected the tribological behavior of the alloys. To deconvolute the contribution of wear and temperature, characterization study has been performed on the aged samples as well. Following the tribological studies, the surfaces inside and outside the wear tracks of the alloy were studied using detailed

characterization tools including Scanning Electron Microscopy (SEM), Energy Dispersive Spectroscopy (EDS), X-ray Diffraction (XRD), Raman spectroscopy, and Secondary Ions Mass Spectroscopy (SIMS) and nanoindentation.

SEM and EDS

SEM and EDS were performed on the disk sample surfaces along with optical microscopy. For the cross-sectional EDS analysis, a layer of Nickel (Ni) coating, deposited using electrodeposition technique, was used on some of the sample's surface to protect the oxide layer from delaminating during grinding. SEM and EDS analyses were performed in a JEOL JSM-7500F that was equipped with EDS and BSE detectors. All the SEM images and the EDS scans have been taken using 5 KV and 20 KV operational voltages, respectively.

X-ray diffraction

X-ray diffraction spectroscopy (XRD) was performed using a Bruker D8 Discover having Copper sealed tube X-ray source with angular resolution of 0.01° . The energy of the incident X-ray beam used was 40 keV, 40 mA ($\lambda=1.54056 \text{ \AA}$) with collimator of 0.5 mm and step size of 0.005° on an area of 1 mm^2 .

Weight changes during oxidation

Digital weighing balance Mettler Toledo-AG245 with 0.01 mg accuracy was used for the weight measurements for all the samples, before and after the experiments, to measure the oxidation and correlate with the wear rate.

Raman Spectroscopy

Horiba Jobin-Yvon LabRam HR Raman is used as a complementary method for chemical characterization of the surface materials. It is equipped with an Olympus BX 41 confocal microscope and two different wavelength laser sources of 633 nm and 785 nm. For the current research, 633 nm wavelength laser was used for the Raman shift range of $100 - 2000 \text{ cm}^{-1}$.

Secondary Ion Mass Spectroscopy (SIMS)

A CAMECA IMS 4f ion microprobe was used in the dynamic mode, for identification of materials through the depth of the oxide layers inside and outside of the wear tracks. Profiling was performed with 14.5 keV Cs¹ ion beam (raster $50 \times 50 \text{ }\mu\text{m}^2$, image collimation diameter of $50 \text{ }\mu\text{m}$, and

variable sputtering rate from 2.73 nm/s to 3.73 nm/s). Time-of-Flight (ToF) SIMS spectra were collected over selected samples.

3 TRIBOLOGY OF INCONEL 617

The results presented in this chapter have been published in two journal papers and one additional journal paper is in preparation:

- “Elevated temperature tribology of Ni alloys under helium environment for nuclear reactor applications”, *Tribol. Int.* 123 (2018) 372–384.
<https://doi.org/10.1016/j.triboint.2018.03.021>
- “Helium Tribology of Inconel 617 at Elevated Temperatures up to 950° C: Parametric Study." *Nuclear Science and Engineering* (2019): 1-15.
<https://doi.org/10.1080/00295639.2019.1582315>
- “Static to Kinetic Friction Transition study of Nickel Alloys at Elevated Temperature under Helium Atmosphere,” to be submitted in summer 2020.

3.1. EFFECT OF TEMPERATURE AND NORMAL LOAD

Fig. 5 depicts the COF of Inconel 617 tribopair in He environment as a function of sliding time and temperature. Every experiment discussed, hereinafter, has been carried out at least twice to assure repeatability. All the mean COF values reported were obtained from the stable average of the in-situ results during the last 40% portion of the runtime. As seen, the COF values at RT and HT in He are all generally high and stable. In He environment, the COF is 1.42 at 950 °C, which is significantly higher than at 500 °C (0.85) and RT (1.09) under 5 N normal load (nominal contact pressure of 0.16 MPa). As shown in Fig. 5b, the tribopair exhibits the lowest COF at 500 °C in He environment while the COF values at 800 °C and 950 °C are higher. Interestingly no considerable change is observed comparing the COFs at 800 °C and 950 °C, implying the same mechanisms at very HT from 800 °C to 950 °C. It is noted that with the rise of temperature, the fluctuation of the COF increases under He environment (Fig. 5a) which is also seen in the increasing trend for the standard deviation values depicted in Fig. 5b.

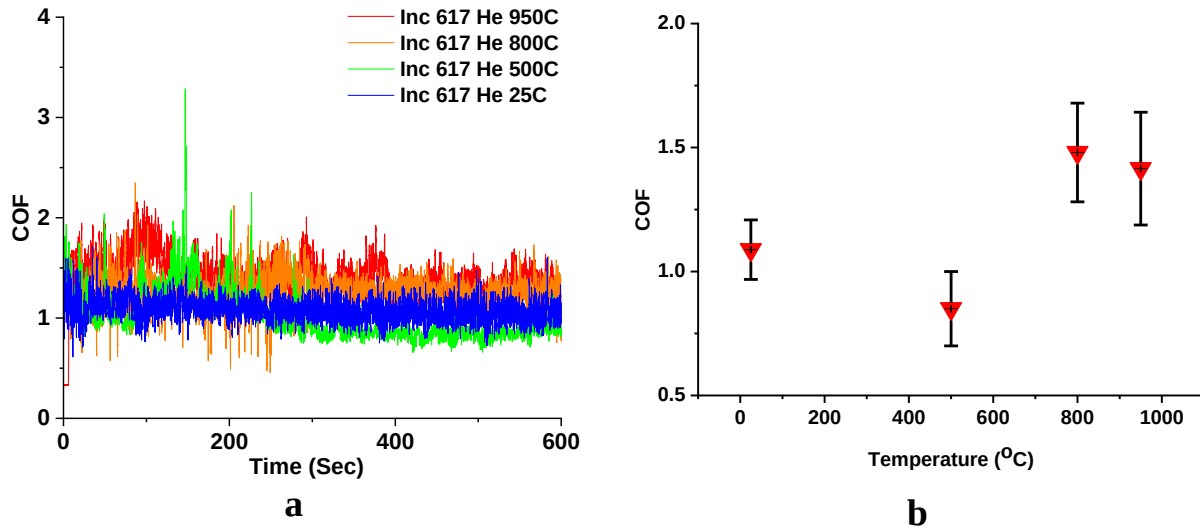


Fig. 5. Inconel 617 in He under 5 N normal load (0.16 MPa) and sliding velocity of 0.04 m/s (a) In situ COF, (b) average COF versus temperature showing ± 1 standard deviation.

Fig. 6 shows the dependency of the COF on the contact pressure (normal load) at three different temperatures under He conditions. The COF is minimum under the intermediate load of 10 N at all temperatures. The COF is highest at 950 °C for all loads, while minimum COF values are observed at the intermediate temperature. At the intermediate temperature of 500 °C, the alloy starts to become softer and very small oxide layer starts to form, that also can be confirmed by the

change in the color of the surface to brownish yellow. This is also observed in previous studies and it is suggested that the COF is lowest at the intermediate temperature during when mechanically mixed layer (MML) starts to form [21,22]. On the other hand, in previous studies on Ni-Cr alloys it is found that at this intermediate temperature NiO is dominant, whereas Cr₂O and NiCr₂O₄ was found to be the reason of lower COF at 600 °C and above temperatures [23]. Lower melting temperature of NiO could enable softening under the contact pressure at intermediate temperature which can be attributed to the formation of a more stable tribolayer or MML by chemical reaction with the impurities present in He, during the experiments at the intermediate temperature. At HT (800 °C and above), however, the formation of more brittle and harder composite layer can lead to COF increase. Moreover, adhesive wear strongly depends upon interfacial bonding between the solids. In the case of two metals in contact, they can overlap, leading to large electron exchange interactions [24]. The adhesion between the pin and the bare metal surface on the wear track in He environment is considerably higher than the adhesion force with the thicker oxide layer (see Section 3.5) in air atmosphere.

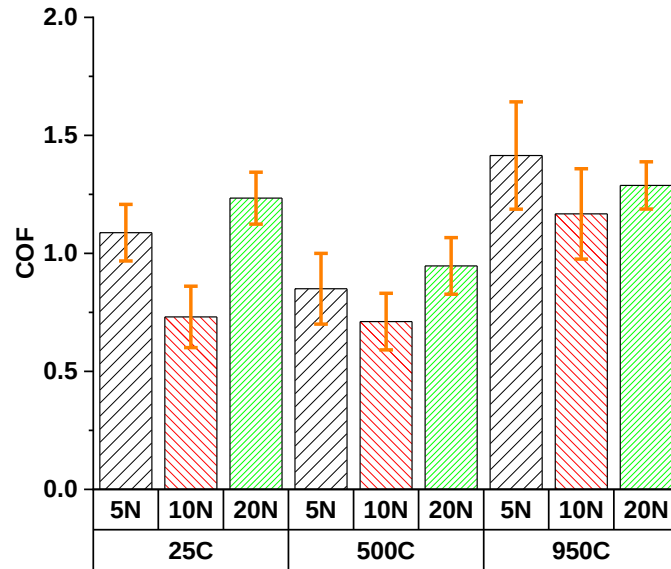


Fig. 6. Average COF at sliding velocity of 0.04 m/s for various normal loads in He (the nominal contact pressures are 0.16. 0.32. 0.64 MPa for 5, 10, 20 N, respectively).

The influence of temperature and normal load on the wear rate in He atmosphere is shown in Fig. 7. Under He environment, at all temperature conditions, the wear rate increases with applied normal load. The wear rate also increases with the rise of temperature under all contact pressures. At RT the wear loss is mostly through adhesive-abrasive burnishing by the metallic contact

between the pin and disk. During testing, periodic evaluation of the contacting surfaces sliding at RT confirmed no sign of material transfer or layer formation. At 500 °C, oxidation and transfer of wear debris to the pin from the disk wear track increases the wear rate. At 950 °C, high oxidation and formation of a composite layer on the wear track accelerated the wear rate at the beginning of the sliding period and continued at a steady rate afterward by high plastic deformation, crack nucleation and propagation in more brittle rubbing surfaces. The wear rate at the intermediate temperature of 500 °C is slightly higher than that of the RT experiments under all loads, while it increases significantly at 950 °C. The wear mechanisms at 500 °C He remains similar as RT with powdery abrasive wear particles whereas, at 950 °C the wear is mostly adhesive generating larger delaminated oxidized wear particles. But due to the presence of higher temperature of 500 °C, the particles are oxidized and increased hardness ratio of oxide to metal substrate might have slightly raised the wear rate [21,22,25,26]. On the other hand, the presence of very fine powdery wear particle in the contact kept the COF lower. Although similar behavior is observed by several investigators as mentioned before, for better understanding of this phenomenon of low friction-high wear rate at intermediate temperatures, further in-depth study is required. Specific wear rate values (wear rate normalized by the normal load) in Fig. 7b show an increase in the wear volume for high load of 20 N. Like typical metallic wear phenomena where specific wear rate does not change considerably with load, here the values are close to each other at RT and 500 °C. At HT the trend changes which can be attributed to the formation of a brittle substrate that is more prone to cracking damage under high contact pressure.

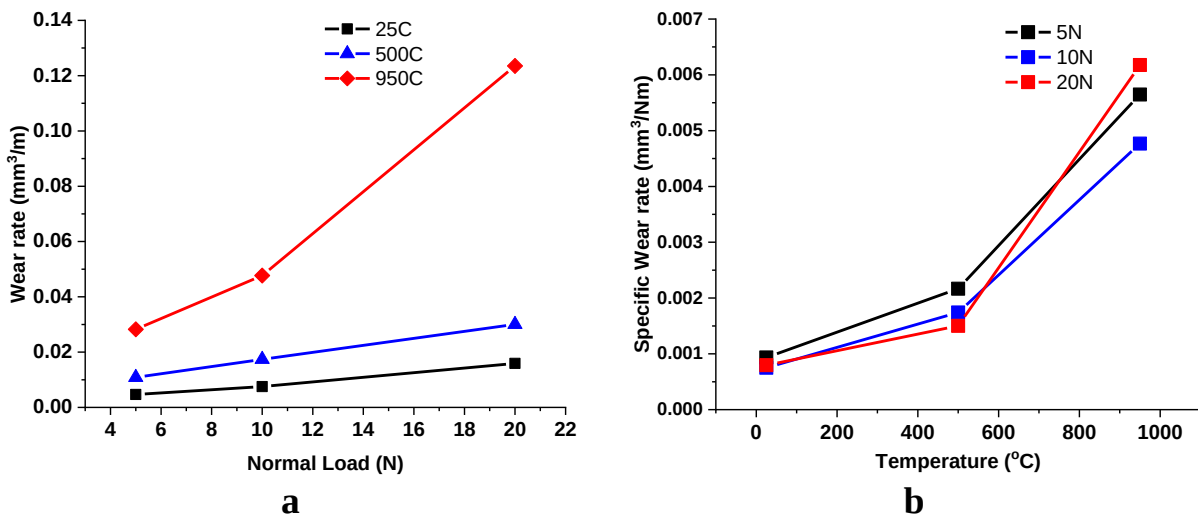


Fig. 7. (a) Average wear rate versus normal load and (b) specific wear rate versus temperature (In He at 0.04 m/s).

3.2. EFFECT OF THE ENVIRONMENT

To understand the effect of the He environment on the sliding wear, experiments were carried out under similar loading and temperature conditions in air. Fig. 8 shows the in-situ COF at different temperatures in air environment and also the average COF values as a function of temperature under different normal loads. At 950 °C in air, the COF drops significantly (about 60% reduction) after few cycles and it is stabilized at lower values as also observed in previous studies [15,27]. Contrary to He environment, in air atmosphere, as the temperature increases, the steady-state COF monotonically decreases from 0.69 at 25 °C to 0.45 at 950 °C, which is similar to the behavior shown at 800 °C and in Ref. [16]. The COF value at 10N at RT and 500 °C in air environment remains almost in the same range and standard deviation. The reason behind not having lower COF at 10N like other loads, is still not clear and further investigation is required in future. The COF decreases with the increase in temperature for all loads (with exception of 10N at 500 °C) due to the stable protective glazed layer generated by compaction of the wear debris trapped in the contact area. At HT in air, the oxide layer becomes softer and at higher loads, the glazed layer becomes relatively more consistent along the wear track. However, in He environment, no such layer was observed even at higher load, which eventually led to higher observed COF and wear.

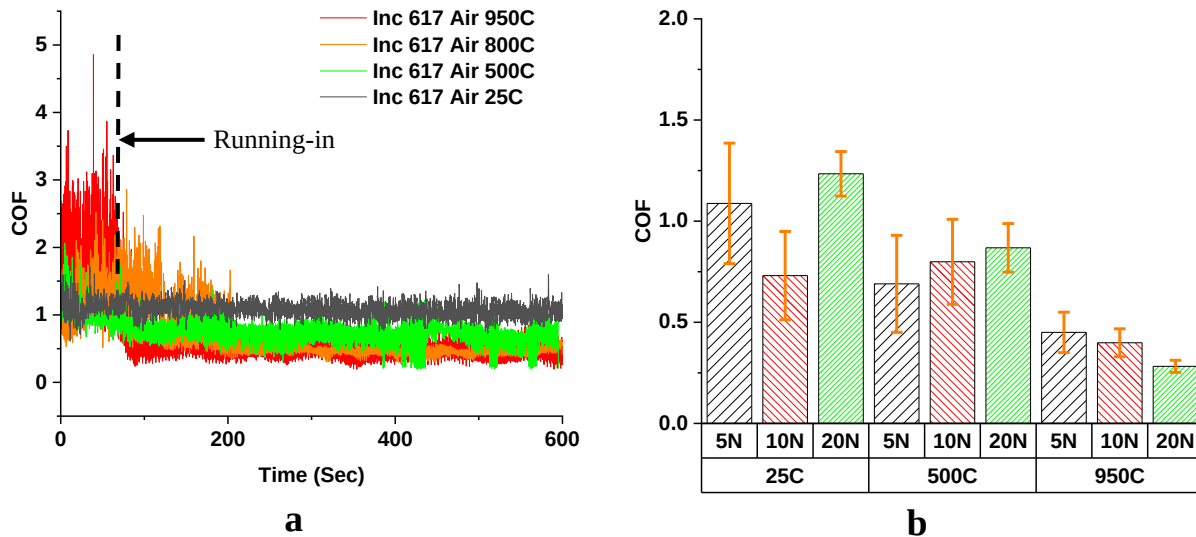


Fig. 8. (a) In-situ COF for 5 N load, (b) average COF at sliding velocity of 0.04 m/s for various normal loads in air.

Fig. 9 compares the wear rates in both air and He environments at 950 °C. At all loading conditions, the wear rate in He is higher than in air, which is in line with the observed frictional behavior.

Although the wear rate, similar to He environment, increases at almost constant rate with load in air, the rate of increment is much lower and consistent between different loads, implying the same specific wear rate (wear coefficient) and the same wear mechanism. The wear rate in HT air is dominated by the initial running in period of the experiment (high COF values for 950 °C in Fig. 8a) where the metal pin slides on the oxidized surface breaking into wear particles. Subsequently, some portion of the wear debris and the newly oxidized surface create the compacted glaze load bearing layer protecting the surface, which leads to reduced friction and wear. Such transitional period (running-in) was not observed for the test carried out in He environment. The wear at HT air is also affected by the reduction in the mechanical properties such as hardness and modulus of elasticity, as the maximum elastic contact strength drops significantly with temperature [28].

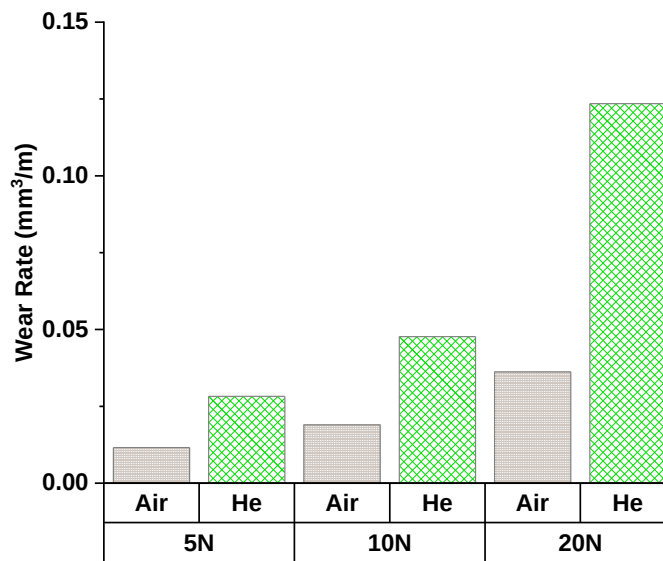


Fig. 9 Wear rate in Air and He environments at 950 °C for different normal loads at 0.04 m/s.

3.3. EFFECT OF SLIDING VELOCITY

Fig. 10 presents the effect of sliding velocity on the COF and wear rate under 5 N normal load at 950 °C, in He and air environments. Both in air and He environments, the COF remains similar at all sliding velocities, although, in He the standard deviation decreased with the increase in sliding speed. In the case of air, although stable COF values, the transition to achieve stable COF increases with sliding velocity (see Fig. 10c). As compared to the situation in air, for samples tested in He, no difference or transition was observed at any velocity. The interaction time between the pin and any point on the disk wear track is inversely proportional to the velocity. Hence, as the sliding

velocity increases the interaction time decreases. At low velocity, the surface has more time to get oxidized and thus the compacted layer is formed earlier than at high velocity. Moreover at higher velocity, there is a higher probability of removing the wear debris out of the wear track that is required to form the protective layer. The wear rate of Inconel 617 is somewhat independent of velocity, and significantly lower in air.

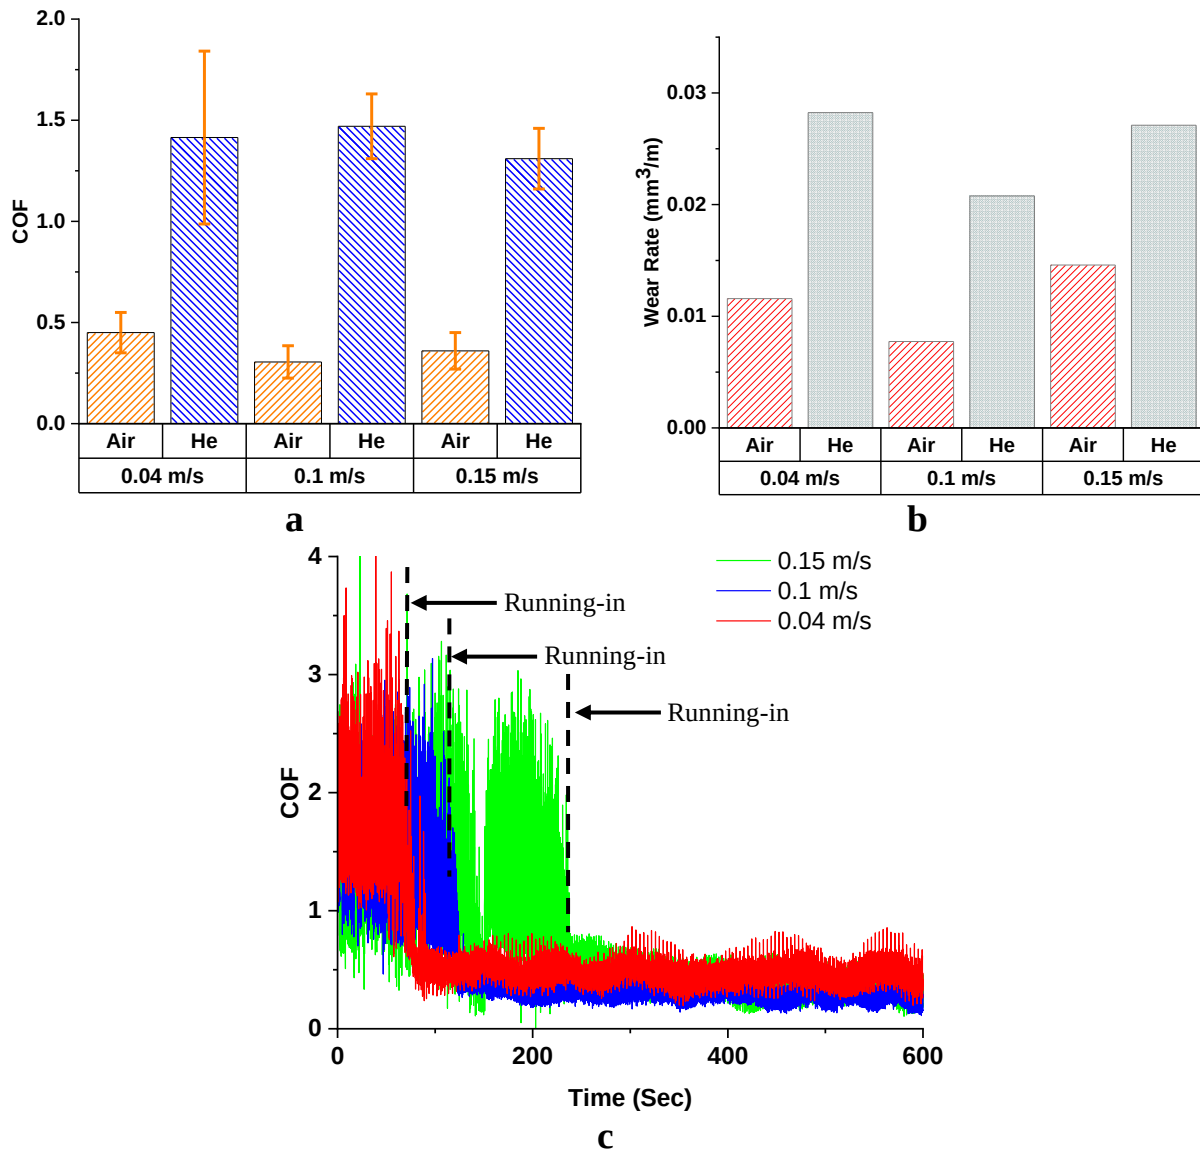


Fig. 10 Effect of sliding velocity at 950 °C under 5 N load and duration of 10 minutes: (a) COF, (b) wear rate, (c) in situ COF in air.

3.4. EFFECT OF SLIDING DISTANCE

Fig. 11 shows the experimental results of Inconel 617 for different sliding distance values with the same constant load of 10 N under He, 950 °C and 0.04 m/s. The average COF is reported for the final 200 s of the experiment, where the COF is stabilized. The 500-cycle experiment exhibits almost the same average COF as 1400 and 2700 cycles. This is in line with the fact that unlike experiments performed in air, no considerable transitional (running-in) period was observed during sliding of the Inconel tribo-pair in He. The 500-cycle experiments are sufficient to investigate the friction/ wear behavior under nuclear HT He conditions. The wear rate at HT He is constant at 0.04 mm³/m. Although the wear rates are fairly close for all test durations, their standard deviation decreases with increasing number of cycles. This is expected as the initial oxidation and removal of oxide layers, although has marginal effect on the average values, they impact the variability of the wear rate. It is noted that despite exhibiting very high COF, Inconel 617 has very low wear rate showing strength retention capability as well as the oxide stability at HT He atmosphere.

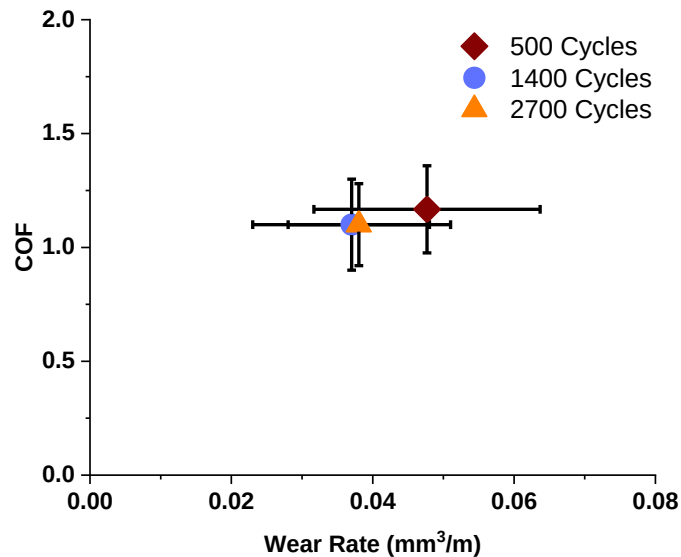


Fig. 11 Comparison of COF and wear rate for Inconel 617 under 10 N at 950 °C in He and 0.04 m/s.

3.5. OSCILLATIONAL (FRETTING) EXPERIMENTS

The HT oscillation (fretting) study was carried out at 950 °C for Inconel 617 using the same specialized high-temperature tribometer (HTT). All experiments were performed at 10 N normal loads (contact pressure of 204 MPa) with an oscillation angle of 120° and max sliding speed of 0.025 m/s along a circular path of 17.5 mm mean diameter. In this configuration, one complete cycle is completed in two seconds, which allows us to obtain enough data to accurately capture

the static COF. Data acquisition was collected at 120 Hz for all the tests performed for 10 and 100 cycle oscillations.

All conditions are repeated for at least two experiments to ensure consistency. Similar to unidirectional experiments presented above, at RT, the static COF is lower than the static COF at HT He environment. The COF value remains almost the same for both 10 and 100 cycles. The static COF in HT He atmosphere for Inconel 617 is 2.13 ± 0.22 during the 10 cycle experiments, whereas it is 2.28 ± 0.26 during the 100 cycle experiments. All the data reported here for 100 cycle experiments are taken by averaging the value of the final 10 oscillations. The spherical pin with 55.3 mm radius curvature was used in these experiments to ensure better contact. The final contact area on the pin increases with oscillations and is larger after 100 oscillations. But the consistency of the static COF at RT proves that the contact area does not have a considerable effect on the COF in this case. In the case of HT experiments, the contact area is larger than its corresponding RT experiments for all conditions.

Fig. 12 shows the average static COF values for Inconel 617 under 10 N normal load. It shows higher static COF values at HT He condition, similar to the dynamic COF. It is noted that the static COF is around 1.5 to 2.5 times higher than the dynamic COF reported in the previous sections for unidirectional experiments. The dynamic COF values during these oscillation experiments are within the error limits reported, which will stabilize over time as mentioned in the previous sections. According to the static COF values reported here, Inconel 617 has better agreement with the previously reported dynamic COF values.

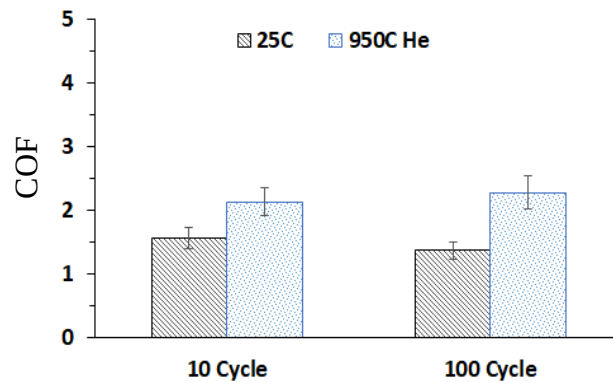


Fig. 12 Average static COF in RT and HT He environment for Inconel 617.

3.6. CHARACTERIZATION AND DISCUSSION

3.6.1. *Surface morphology*

The SEM images in Fig. 13 show the morphology of the oxides formed on the matrix surface as well as in the wear track under different magnifications at 950 °C in both air and He. The thicker yellow arrows in the middle micrographs indicate the sliding direction. The SEM images reveal that the oxides formed on the matrix surface in air (Fig.13a) and He (Fig.13c) atmospheres have similar morphologies. On the wear track, however, the compacted glazed layer of oxide debris is more continuous and clearly visible on the wear track of the disk at 950 °C in air (Fig. 13b), whereas no such layer is observed under He environment. This clearly explains the higher COF and wear values observed for He. A closer look in the wear track reveals areas with two different surface morphologies under both air and He. Designated area-I exhibits a more continuous contact with the counter surface and eventually carrying most of the contact pressure, which made the surface “cleaner” and smoother. This is the result of the initial material transfer to the pin surface in He, and the “glazed” layer formed by compacted oxide debris in air. Designated area-II shows a rougher surface with partially compacted adhesive wear debris, which is also a transitional phase towards Area-I. Area-II on the wear track in He (Fig. 13d) shows similar morphology as on the surface outside the wear track and fewer signs of adhesive wear than in Area-I, which indicates reduced contact with the counter surface.

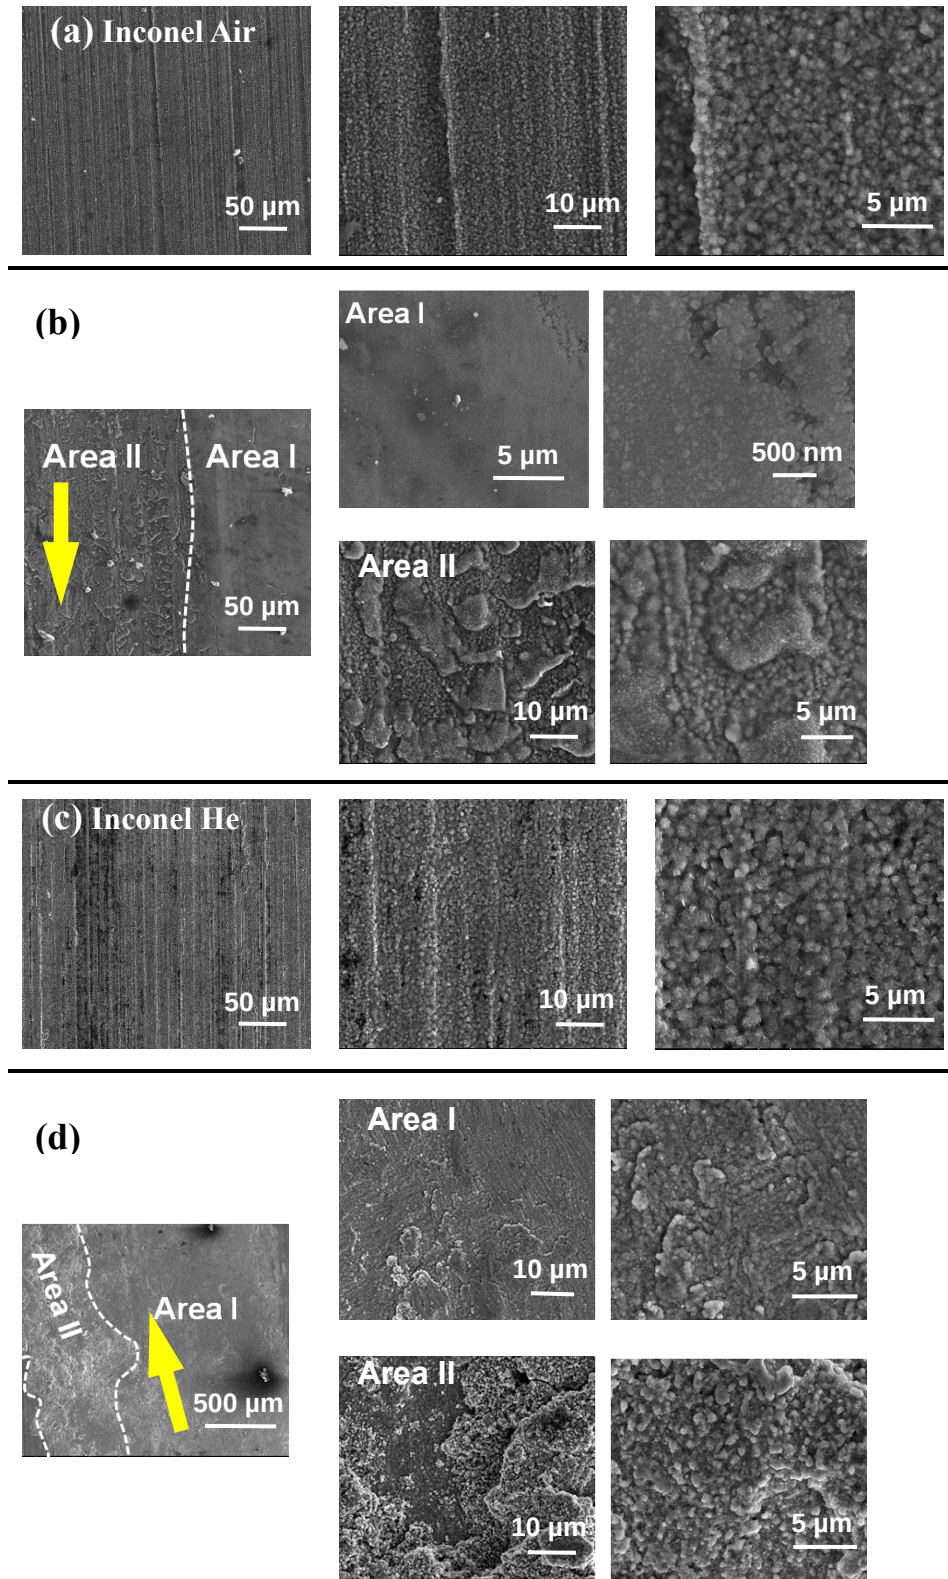


Fig. 13. SEM images of samples under 5 N normal load, 950 °C, 0.04 m/s; in air (a) outside the wear track (matrix) and (b) inside the wear track; in He (c) outside the wear track (matrix) and (d) inside the wear track.

The XRD technique was also performed on samples exposed in He and air at 950 °C and both samples show peaks for Cr₂O₃ as well as the metal substrate of Inconel 617 (Fig. 14). The peaks of the oxides in air are further developed and sharp, implying that the oxide is more crystalline and also the size of the particles is larger, compared to the oxide developed in He, which is in agreement with the observations from the SEM images, Fig. 13.

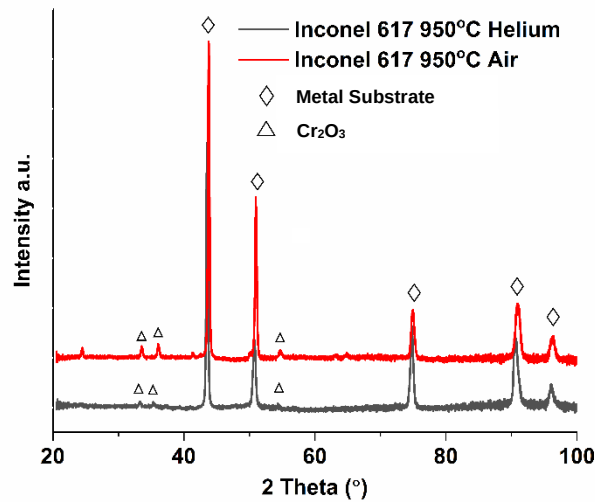



Fig. 14. XRD data outside the wear track for Inconel 617 at 950 °C, 0.04 m/s in He and Air.

3.6.2. SEM/EDS

Cross section SEM and EDS analyses for the samples tested at 950 °C show a surface oxide reach of Cr with the presence of subsurface oxides of Aluminum (Fig. 15) [29]. From the cross-section SEM images of the matrix outside the wear track, it is evident that the oxide layer thickness exposed in air is higher than the samples tested in He. Also, the surface oxide in air is relatively rougher than in He. Once pressurized in the contact region, this thick and stable layer of compacted oxides in HT air protects the Inconel surface from excessive wear.

According to Fig. 15, the oxide layer thickness outside the wear track is approximately 4 µm in air at 950 °C, but it should be noted that it varies depending on location and could be up to 10 µm thick. Nonetheless, outside the wear track in He the oxide layer thickness is only around 1.5 to 2 µm. For the wear tracks at 950 °C, the cross section EDS results show that the thickness of the mechanically mixed layer varies between 1 to 10 µm in both air and He environments depending

on the area (I and II) of the wear track. The EDS maps on the wear track in Fig. 15 reveal the layer in HT air to be a mixture of Cr-Ni-Co-Mo with a higher concentration of Cr. However, in the case of the mixed layer in HT He, it mostly consists of high concentration of Cr at the top layers with a small trace of Ni, Co and Mo. Significant amount of molybdenum and aluminum traces are found at the inner edge in the interface of the mechanically mixed layer and the bulk. At 950 °C air, complete recrystallization occurs and $M_{23}C_6$ carbide precipitates, rich in chromium and molybdenum are found on the surface and along the grain and subgrain boundaries [11,30]. The presence of Mo in the MML and moisture in the air can help the formation of compact layers and reduce the COF and wear at HT air environment.

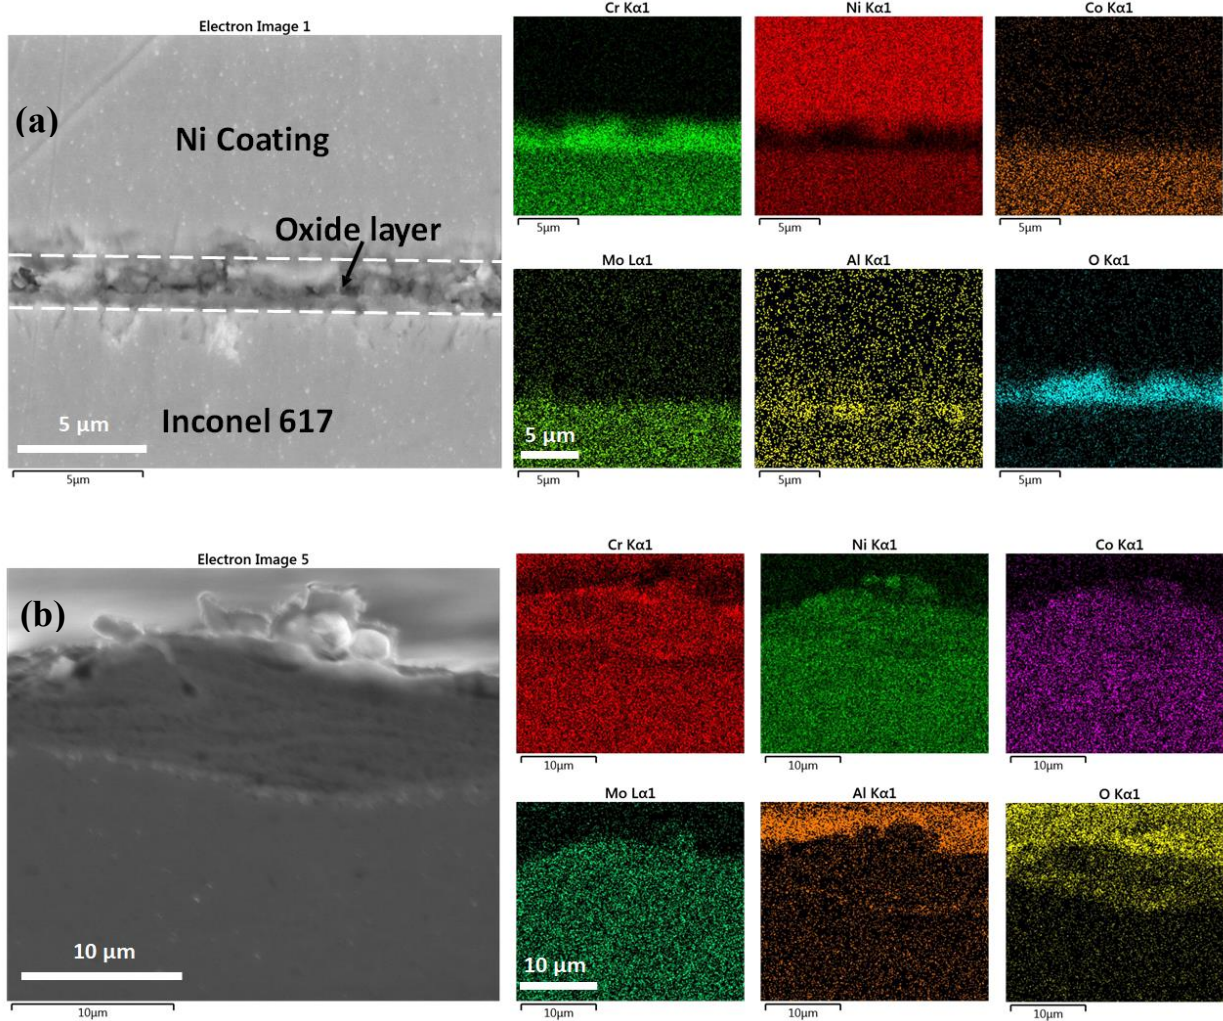

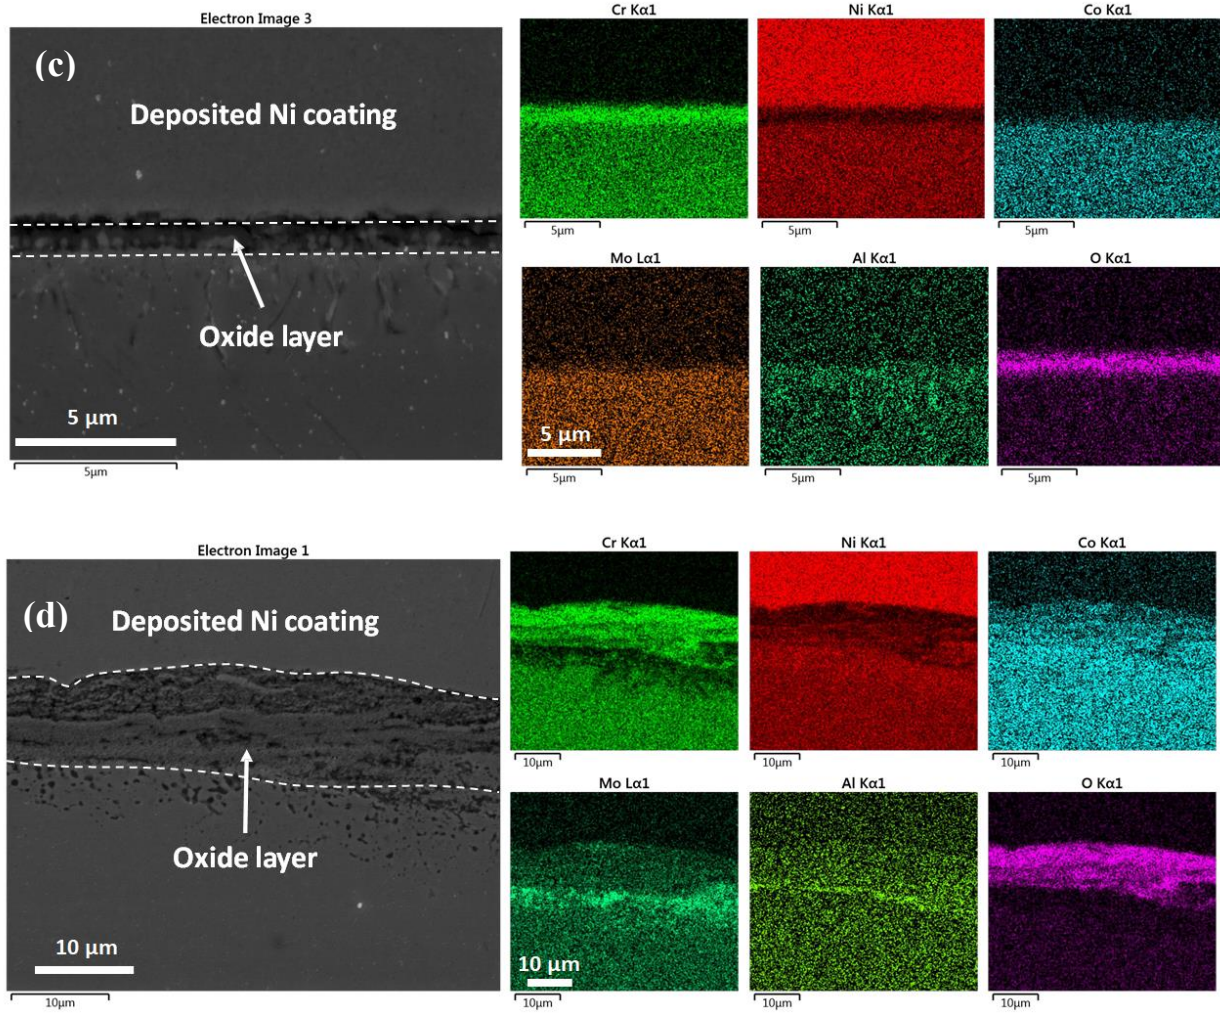


Fig. 15. Cross section SEM images and EDS maps of Inconel 617 at 950 °C under 5N load, (a) Air outside the wear track, (b) Air inside the wear track, (c) He outside the wear track and (d) He inside the wear track.

At a lower load of 5 N, patches of “glazed” layer are observed on the wear track in HT air (Fig. 13), whereas at higher loads the glazed layer becomes consistent and continues along the wear track (see SEM images shown in Fig. 16a, b, c). It should be emphasized that in He, no such layer is present at any condition. At higher load, the wear track is clear of any wear debris particles and shows only small patches of adhesive contacts which eventually lead to higher COF and wear (Fig. 16d, e, f). With increasing load in HT He, the higher contact pressure easily generates and propagates cracks through the mixed layer at a higher rate than its formation and eventually, the thickness of the mixed layer reduces. This observation is further supported by the EDS line scans presented in Fig. 16(g, h) for the sample cross section under 10 N and 20 N loads.

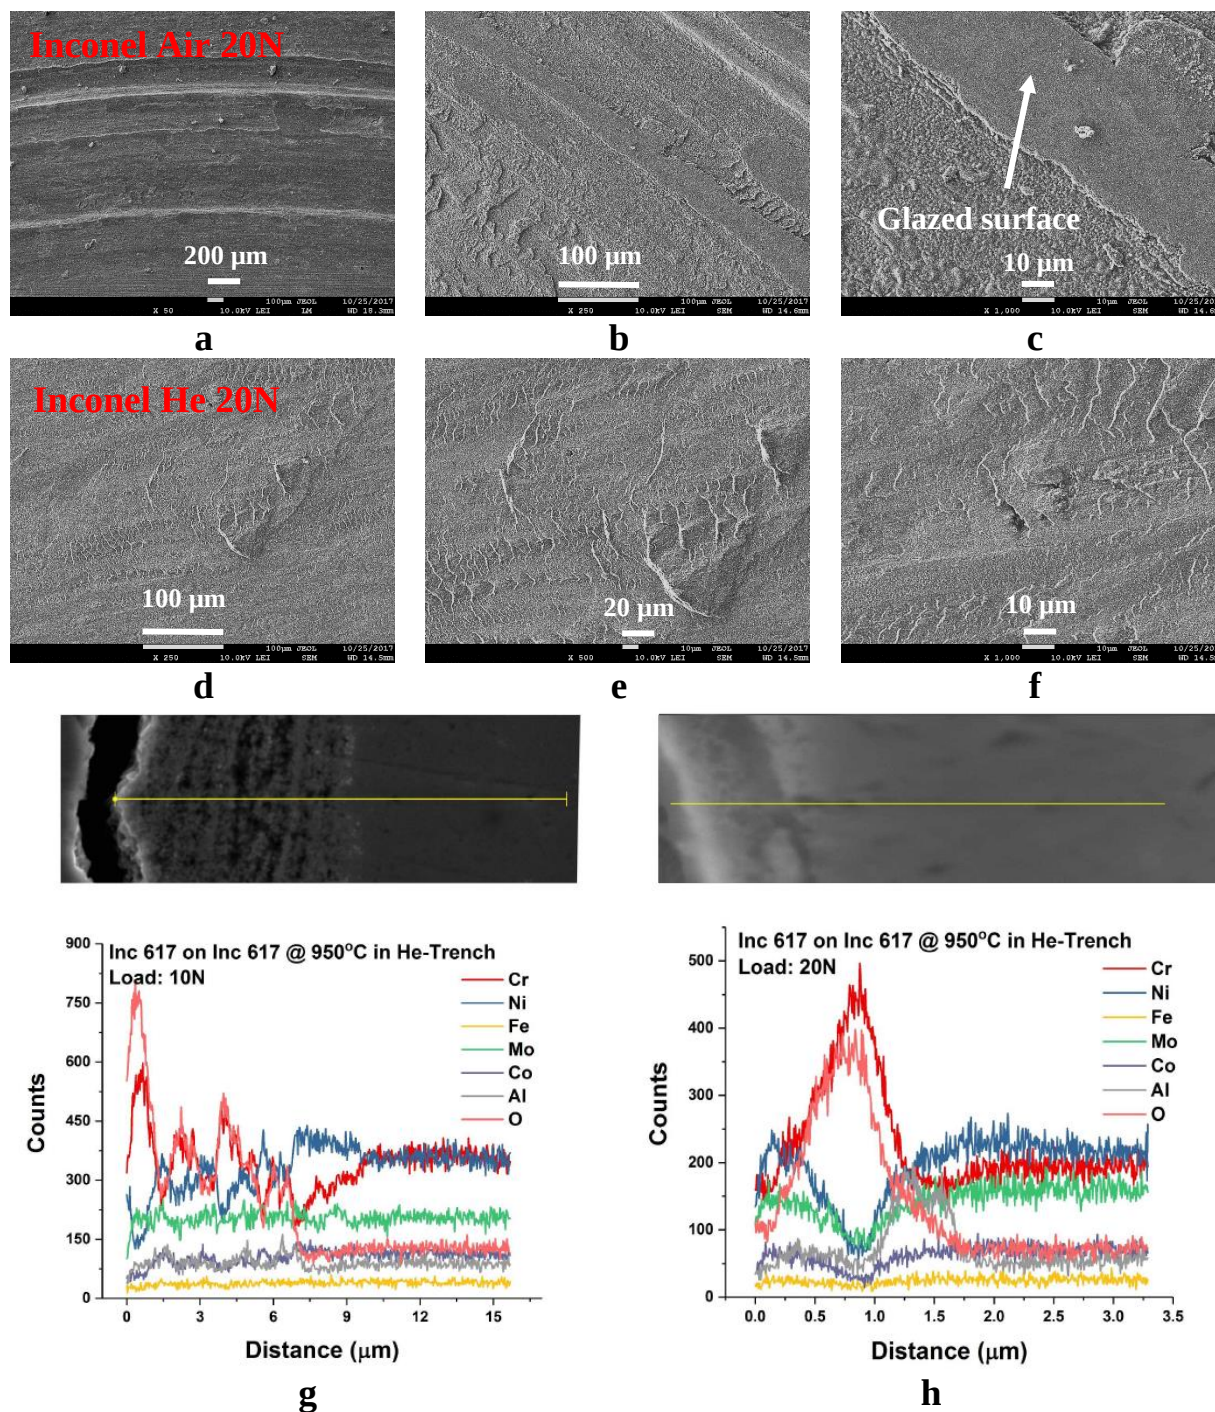


Fig. 16. SEM images of 20 N, 0.04 m/s samples (a, b, c) at 950 °C, air; (d, e, f) 950 °C, He. EDS line scan on the cross section of the wear track at 950 °C in He (g) 10 N load sample, (h) 20 N load sample.

Obvious differences are observed between the worn surface and the wear debris produced in HT He and air environments. The amount and size of the wear debris produced in He at 950 °C is larger than in air, under similar loading conditions. To further evaluate the wear particles, debris

produced during the experiments were examined by SEM and EDS techniques and the results are shown in Fig. 17. At the temperature of 500 °C as well as RT at both environments, the size of the wear particles is small in the range of 20-100 μm , and particles are flake-like. However, at 950 °C in He, the quantity of wear debris increases drastically with larger chunky particles up to 300 μm . The size of the debris particles is defined by both mechanical and chemical effects during sliding, and also the partial pressure of oxygen has a significant influence on their size.

It has been shown experimentally by Soda et al. that the diameter of the wear debris particles increases with the decrease in oxygen partial pressure [31,32], which is in agreement with this work. The chemical activity of the gases was systematically investigated by Mishina to correlate the influence of atmosphere on the wear of metals [33]. Three categories of wear behavior were identified based on chemisorption affinity for metals and, accordingly, a correlation between the wear debris size/ quantity and gas pressure was established. The wear behavior is classified as Type I: gases with high chemisorption affinity of metals, Type II: gases with low chemisorption affinity of metals and Type III where chemisorption of gases on metal surfaces does not occur. In the case of type I, at the low-pressure end, strong adhesion and metal transfer occurs. With the increase in gas pressure, the wear debris particle size decreases. According to the observation of wear debris produced here, the wear behavior can be classified as Type I. The generation of rolling fine wear debris particles promotes faster agglomeration and formation of wear-protective layer in HT air environment, whereas the larger particles in He are not suitable and jump out of the wear track, or go through further plastic deformation under contact and can potentially lead to harder substances and may even result in more abrasive wear.

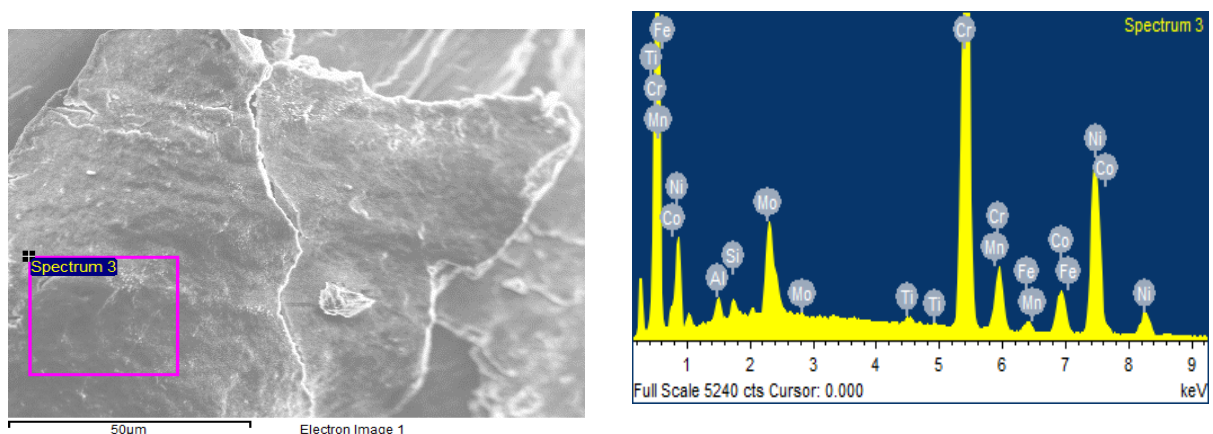


Fig. 17 SEM and EDS of typical wear debris at 950 °C in He, 5 N, 0.04 m/s.

3.7. SUMMARY

The friction and wear behavior of Inconel 617 was investigated using a custom-built HT tribometer simulating He cooled reactor environments up to 950 °C. Understanding the complete tribological behavior of Inconel 617 requires experiments covering multiple variables affecting the results. Interestingly, even though the alloy exhibits very large COF values (>1), high wear resistance was observed for the alloy at HT, which demonstrates the strength resilience of the alloy even at HT He environments. The following conclusions could be drawn from this work:

- (1) In air, as temperature increases, friction decreases due to the formation of a protective glazed layer on the tribo-surface, formed by wear debris compaction;
- (2) In HT He, friction and wear are higher than in air due to the instability of the surface oxide layer and crack initiation/propagation in low oxygen partial pressures, generating larger size wear debris;
- (3) Under different contact pressures, the wear rate increases linearly with pressure, while the COF is almost independent of pressure;
- (4) Sliding velocity (in the range of nuclear reactor applications) does not have a significant effect on the wear rate and COF values in both air or He environments. However, the transition time in HT air increases with increasing velocity;
- (5) At HT air, Cr-rich oxide layer is present with a mixture of CO-Ni-Mo. The thickness of the oxide layer outside the wear track varies significantly between 1 to 10 μm .
- (6) At HT He, the oxide is Cr-rich with minor presence of CO-Ni-Mo and the thickness of the oxide layer outside the wear track remains almost the same; and
- (7) The thickness of the mechanically mixed layers inside the wear track varies for both He and air, and two different areas with very different properties and topographies are observed.

4 TRIBOLOGY OF ALLOY 800HT

The results presented in this chapter have been published in *Wear* in 2019:

- “Tribology of Incoloy 800HT for nuclear reactors under helium environment at elevated temperatures”, *Wear* 2019;436–437:203022, <https://doi.org/10.1016/j.wear.2019.203022>.)

4.1. EFFECT OF TEMPERATURE AND NORMAL LOAD

Fig. 18 shows the COF results in He atmosphere as a function of temperature and sliding time (distance). The error bars presented in Fig. 18b were obtained from experiments carried out under the same condition repeated for at least two times to assure repeatability, as well as to determine the range of variation which is true for all the data hereinafter. The steady-state runtime of the in-situ results is considered to obtain all the mean COF values. In He environment, the COF values at all temperatures (RT and HTs) are high and generally stable, albeit with fluctuations. In He atmosphere, the COF is 1.65 at 750 °C, which is considerably higher than at both 500 °C (0.97) and RT (1.28) under 5 N normal load equivalent to 0.16 MPa nominal contact pressure. The tribo-pair demonstrates the lowest COF value at 500 °C in He. Similarly, from the in-situ COF data in Fig. 18a it is noted that the fluctuation of the COF is highest at 750 °C and lowest at 500 °C, under He environment, which can also be inferred by the standard deviation values depicted in Fig. 18b. Generally, with the increase in temperature and in the absence of major oxidation, the material becomes softer and is expected to have lower resistance to sizable deformation and thus, lower COF values. Here, the sample surface color changes to brownish yellow at 500 °C, confirming oxidation phenomena. However, further investigation showed that the oxide layer is very thin and not even detectable under cross sectional EDS. At this temperature, the alloy is softer compared to RT which in the absence of major oxidation leads to lower COF. This trend is also observed in previous reports for HT alloy [23,24]. At HT (750 °C), nonetheless, the formation of a harder, brittle and thicker composite layer and its frequent failure leads to an increase in the COF [21].

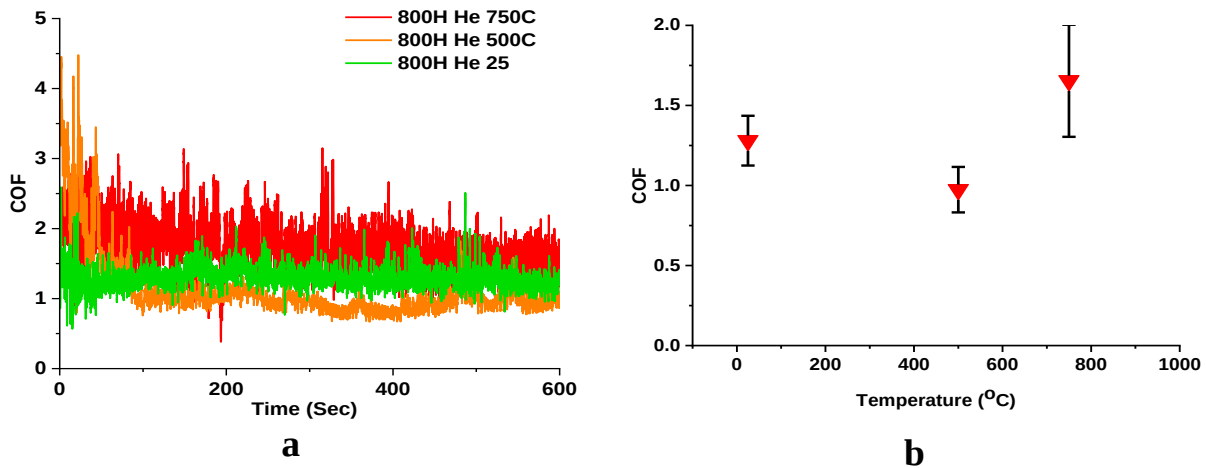


Fig. 18. Alloy 800HT (a) In situ and (b) average COF values for different temperatures in He environment and under 0.04 m/s sliding velocity and 5 N normal load (0.16 MPa).

Fig. 19 shows the average COF values for different normal loads in He condition and under three different temperatures. No specific trend can be concluded for the variation of COF with load (contact pressure), especially taking the standard deviation into consideration. Although the COF is minimum for the middle load of 10 N at RT, it is the maximum at the same load at a high temperature of 750 °C, while at an intermediate temperature of 500 °C the average COF is almost in the same range for all load conditions. Still, the COF has the highest values at 750 °C for all loads, whereas lowest values are measured at the temperature of 500 °C. The reduction of the COF values at 500 °C, compared to RT for 5 N and 20 N load is noticeable. At 750 °C, the COF behavior becomes more extreme where with the combination of higher adhesive wear debris generation and surface roughness on the wear track, the COF at 10 N is the highest. This behavior at 750 °C can be attributed to a mechanically mixed composite layer formation from a brittle oxide layer generated by chemical reaction with the impurities present in He during the experiments at HT. This composite layer starts breaking and delaminating with continuous unidirectional motion leading to higher roughness on the wear track.

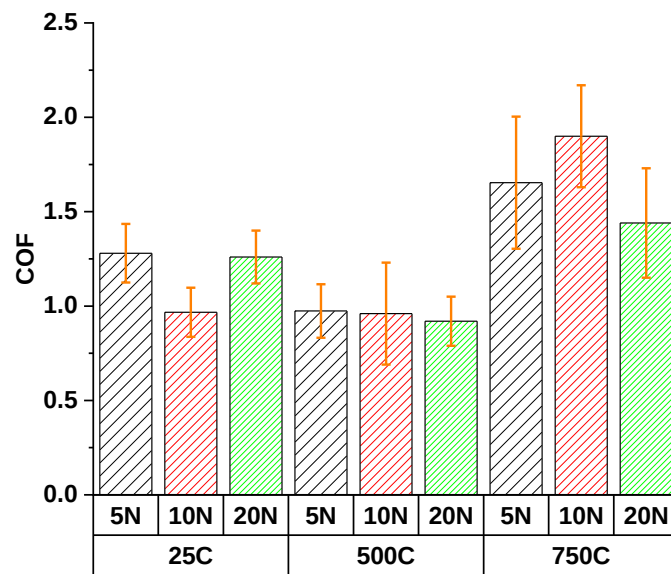


Fig. 19. Average COF for different normal loads in He (sliding velocity of 0.04 m/s, normal contact loads of 5, 10, 20 are equal to 0.16, 0.32, 0.64 MPa, respectively).

The effect of normal load as well as temperature on the wear rate is illustrated in Fig. 20, under He atmosphere. The results clearly show wear rate increase with the increase in applied normal load, as expected. Under this condition and for all contact pressures, the wear rate increases with

temperature. Adhesive-abrasive burnishing wear, caused through the disk and pin metallic surface interactions, is predominant at RT. During the RT experiment, no sign of layer formation or material transfer was observed which is confirmed by periodic assessment of sliding surfaces. The wear at 500 °C in He becomes larger slightly since the material softens compared to RT while retaining the COF value lower with the generation of similar type of finer wear debris. At 750 °C, high oxidation rate, and formation and delamination failure of the composite oxide layer on the wear track resulted in enhanced surface wear during the running-in period. The wear rate is then continued with high steady value through large plastic deformation, as well as nucleation and propagation of cracks in more brittle surfaces. The change in wear rate under 10 N is slightly steeper than that of other loads at 750 °C, which is also more pronounced from the values of wear rate normalized by normal load (specific wear rate), shown in Fig. 20b. The reported values are for 500 cycle experiments and the steep change in wear rate for 10 N load is investigated for higher cycles in a later section.

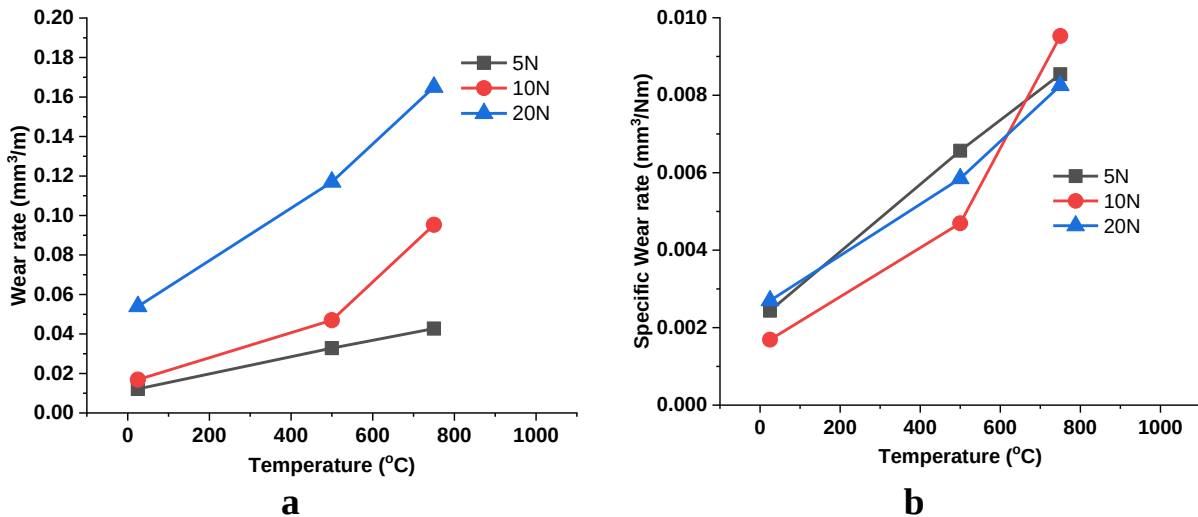


Fig. 20 (a) Average and (b) specific wear rates for different temperatures (0.04 m/s, He, 500 cycles).

4.2. EFFECT OF ENVIRONMENT

The influence of He environment on the sliding wear can be better explained through comparing the He environment data with experiments carried out in air under the same loading and temperature conditions. Fig. 21a depicts the in-situ COF values at three different temperatures in air under 5 N normal load, whereas the average COF values at 750 °C under different normal loads at sliding speed of 0.04 m/s are compared with He atmosphere in Fig. 21b. The in-situ data suggests

that the COF stabilizes around the same range of values for both 500 °C and 750 °C in air for 5 N normal load with a longer period of running-in at 750 °C. At 500 °C, the average COF values reduce in a similar fashion to He environment, but the COF values in air are slightly lower compared to He. Under 5 N load, the COF in air 500 °C is 0.71 whereas in He, the value was 0.97. At 750 °C in air, the COF continues dropping after several cycles (running-in period) and stabilizes at 0.66 for 5 N load. Although this trend in air is not observed in He, similar behavior was, in fact, observed in air according to Refs. [15,16] for nickel alloys. On the contrary, for higher loads of 10 N and 20 N in air, such significant reduction was not identified. The reduction of COF with the increase in temperature for 5 N load is attributed to the glazed layer formed by compacting the wear debris under contact pressure. At HT in air and under higher contact pressures, the glazed layer becomes unstable, cannot sustain the high contact pressure and fails to provide effective wear resistance, which leads to higher COF and wear.

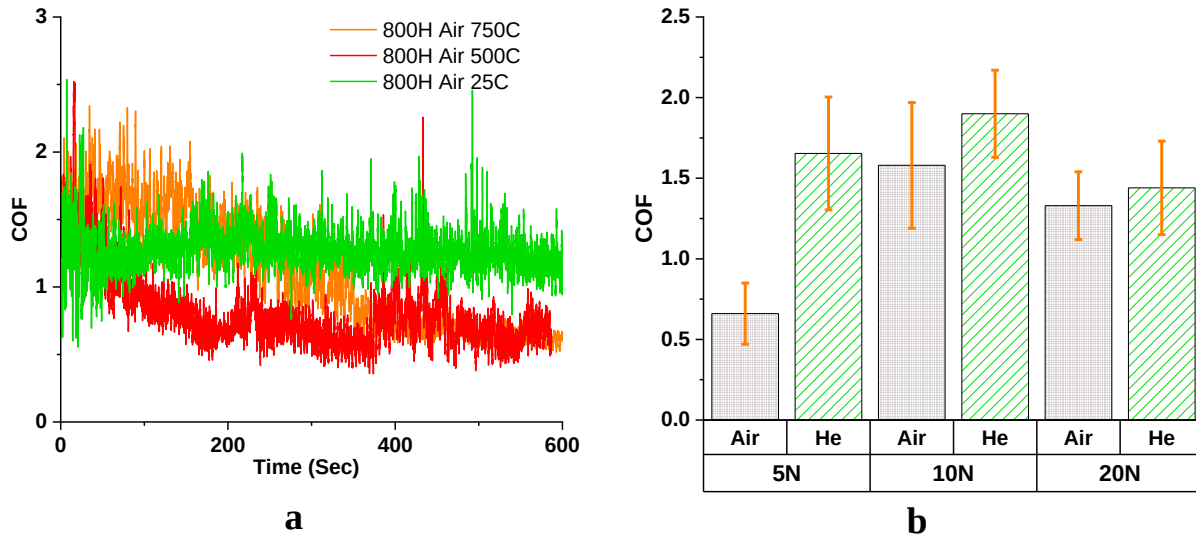


Fig. 21 (a) In-situ COF values in air for 5 N load and sliding velocity of 0.04 m/s, (b) average COF at 0.04 m/s for different normal loads in air compared with He at 750 °C.

The comparisons of the wear rates in air and He environments are presented in Fig. 22a for the temperature of 750 °C at 0.04 m/s sliding speed for different normal loads. A typical 3D confocal optical profiling image of a wear track is shown in Fig. 22b. The wear rate steadily increases with load at 750 °C, irrespective of the atmosphere. Interestingly, under all normal loading conditions, the wear rate values are in very close proximity in He and air, which indicates similar oxidative adhesive wear mechanism in action. The wear rate in HT is dominated by adhesion, crack

propagation and delamination of the mechanically mixed oxide layer. The layer on the wear track in both environments shows brittle behavior with low adherence to the bulk metal leading to higher wear rate at higher temperatures.

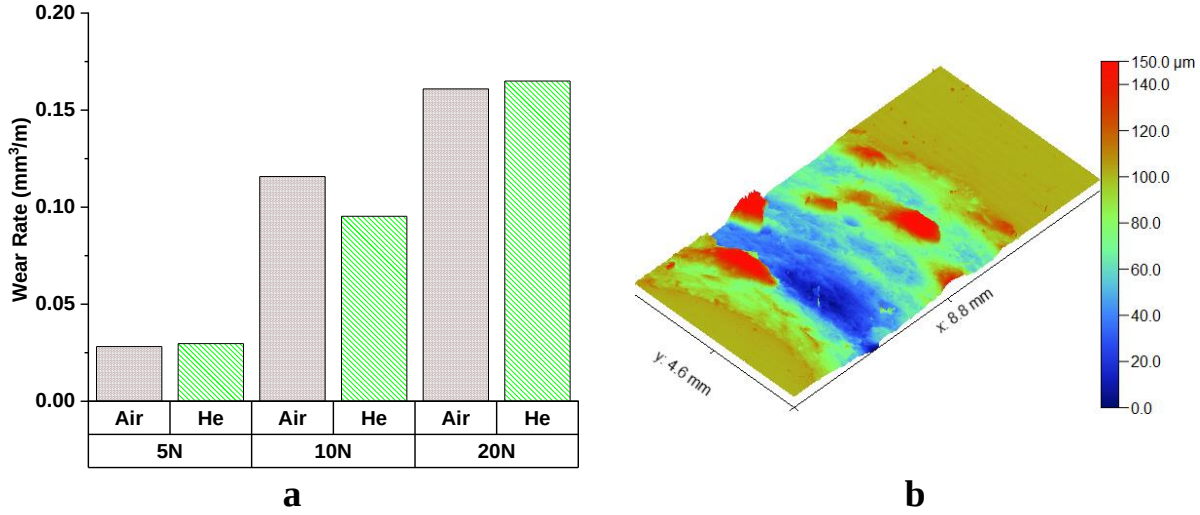


Fig. 22 (a) Wear rate in Air and He environments at 750 °C for various normal loads at 0.04 m/s, 500 cycles, (b) Confocal optical profiling images of wear track in He under 10N, 0.04m/s at 750 °C.

4.3. EFFECT OF SLIDING VELOCITY

Fig. 23 presents COF values as a function of sliding velocity under all normal loading conditions at 750 °C, in both He and air conditions. In HT air atmosphere the COF settles to a lower average value for 5 N load in 0.04 m/s sliding speed, but cannot maintain this value for the higher loads. As shown in Fig. 23a, a similar trend is observed for the sliding speed of 0.1 m/s where the COF is low for 5 N but higher for other load conditions. However, at a higher sliding speed of 0.15 m/s, change in the behavior is observed with lower COF for both 5 N and 10 N, and higher COF under 20 N load. In He, as shown in Fig. 23b, the COF still remains in the higher range above 1.0 for all conditions but shows a slight steady decreasing trend at a high load of 20 N with the increase of sliding speed, and remains in the same range for the other two loading conditions without showing any specific trend.

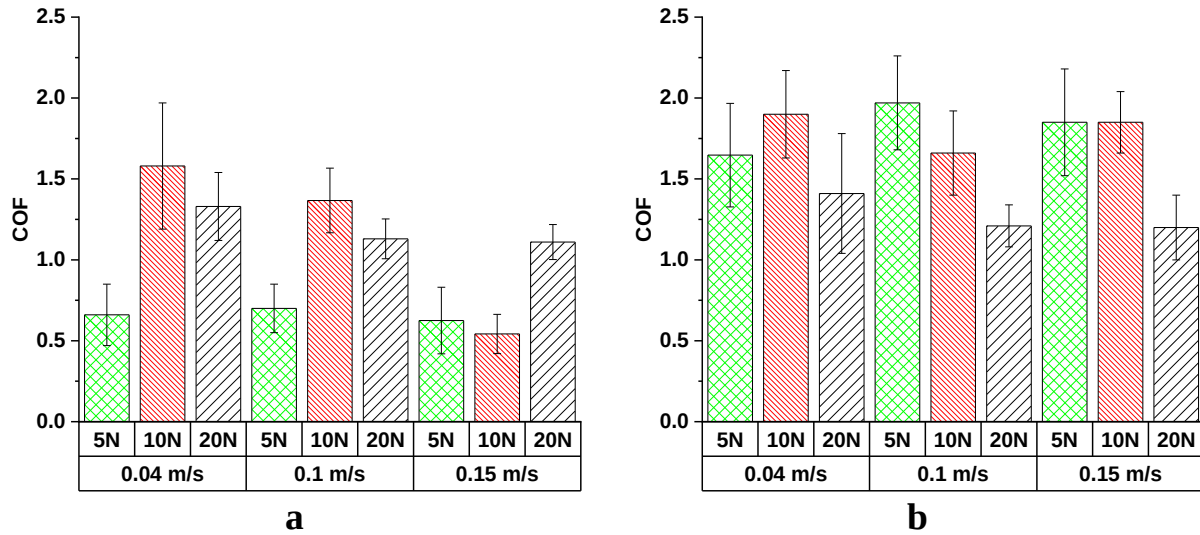


Fig. 23 Effect of sliding velocity on COF at 750 °C for 500 cycle experiments: (a) in air, (b) in He.

4.4. EFFECT OF SLIDING DISTANCE

Experiments were performed for three different test durations in He, while other parameters were kept constant at normal load of 10 N, temperature of 750 °C, and sliding speed of 0.04 m/s. The average COF is calculated for the final 30% of the experimental duration, when the COF value is stabilized and is shown in Fig. 24. The 500-cycle test demonstrates almost similar value for average COF as the 1400 and 2700 cycle experiments. In fact, unlike the tests performed in air, the experiments in He atmosphere do not show any clear running-in period with sudden change in COF. Considering the constant and stable test conditions, where COF and wear rate values are stabilized, one can conclude that from a tribological perspective, 500 cycles is adequate duration to accurately quantify and understand the steady-state sliding friction behavior of alloy 800HT at the current experimental conditions.

Nonetheless, specific applications in reactors might involve contacting surfaces in idle conditions for long duration followed by few slow sliding movements. In view of such scenario, it is then worth mentioning that it might never be possible to reach the steady state condition and, therefore, in some practical applications (viz. nuclear reactors) aging is an important factor. In fact, aging over time changes the top layer of material surface influencing its short-term tribological behavior. Particularly, when a long idle duration is followed by limited number of slow sliding movements, the system can always stay in running-in mode. Aging is not the focus of the current investigation, however, a separate investigation looking into the frictional behavior of samples aged for different

durations in He atmosphere is sought in future studies. The wear rate shows a high standard deviation at 500 cycle experiments with a higher average value of $0.09 \text{ mm}^3/\text{m}$, compared to other test durations. However, this by itself does not contradict the conclusion of steady-state conditions for 500 cycles. This, in fact, is due to the inclusion of the running-in period (initial oxidation and oxide layer removal) in the total wear rate calculation. As seen, with the increase in the experimental cycles, the deviation in wear rate diminishes as steady-state wear rate gradually overshadows the running-in effect.

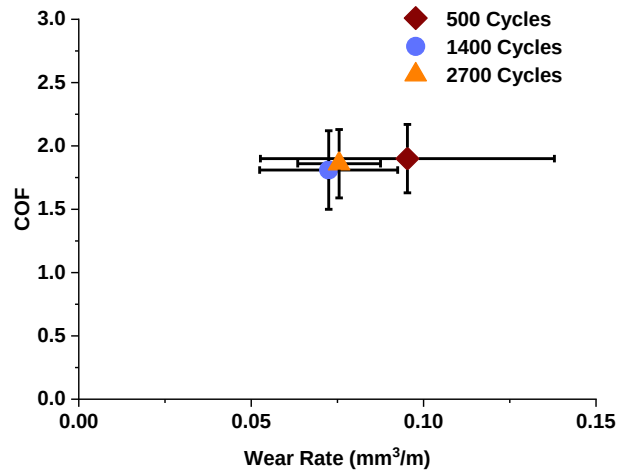


Fig. 24 COF and wear rate comparison under 10 N at 750 °C in He and 0.04 m/s.

4.5. OSCILLATIONAL(FRETTING) EXPERIMENTS

The HT oscillation experiments were carried out at 750 °C for alloy 800HT using the HTT, which has the capability of unidirectional and oscillatory motions: rotational speeds up to 1000 rpm and oscillation frequencies up to 5 Hertz. Similar to Inconel 617, all experiments were performed at 10 N normal loads (contact pressure of 204 MPa) with an oscillation angle of 120° and max sliding speed of 0.025 m/s along a circular path of 17.5 mm mean diameter. Data acquisition was collected at 120 Hz for all the tests performed for 10 and 100 cycle oscillations.

Fig. 25 shows representative in-situ COF for the oscillation experiment for an 800HT pin against 800HT disk in both room temperature (RT) and HT under He environment. All conditions are repeated for at least two experiments to ensure consistency. Similar to unidirectional experiments, presented above, at RT, the static COF is lower than the static COF at HT He environment. The COF value remains almost the same for both 10 and 100 cycles (Fig. 25a). In the case of HT He atmosphere, the static COF of alloy 800HT increases with time over the 100 cycles. The static

COF in HT He atmosphere for 800HT is 2.98 ± 0.38 during the 10 cycle experiments, whereas it is 3.74 ± 0.59 for 800HT during 100 cycle experiments. All the data reported here for 100 cycle experiments are taken by averaging the value of the final 10 oscillations. The spherical pin with 55.3 mm radius curvature was used in these experiments to ensure better contact. The final contact area on the pin increases with oscillations and is larger after 100 oscillations. But the consistency of the static COF in RT proves that contact area does not have a considerable effect on the COF in this case. The final contact width after 100 oscillations is approximately 1.5 mm at RT and 3 mm at 750 °C. Fig. 25b and c show the optical images of the wear tracks on the disk and pin at HT, respectively. The image shows the presence of adhered wear debris on the wear surface of both pin and disk, which is not seen on the surface of the RT wear track.

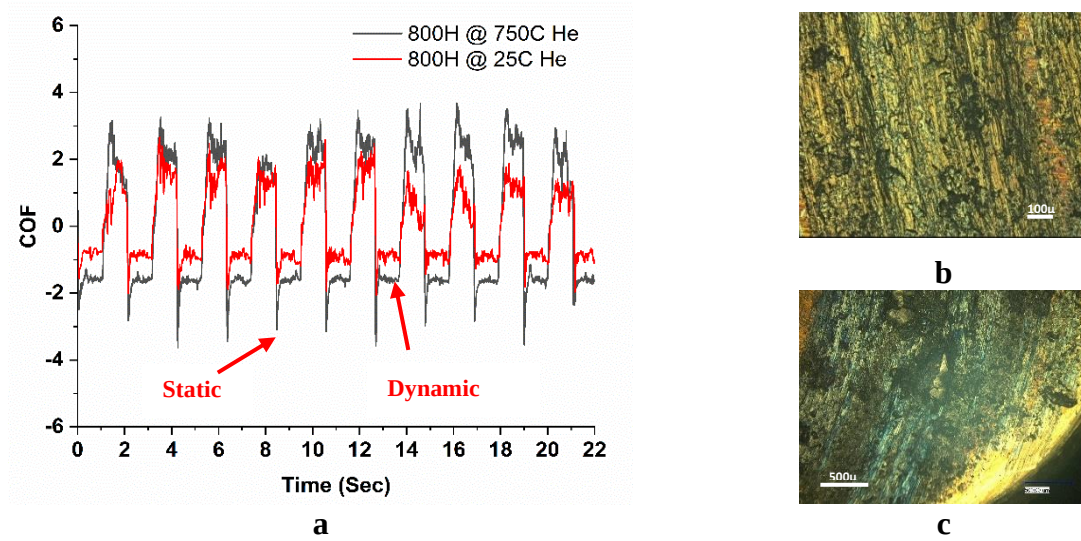


Fig. 25 (a) In-situ oscillation experiment data of alloy 800HT, Alloy 800HT disk (b) and pin (c) surface after 750 °C He experiment.

The SEM images shown in Fig. 26 show the wear track of both RT and HT experiments. The HT wear track shows higher adhesive contact features with a lower amount of loose debris than in RT. The increase in adhesive force between the pin and disk surface at HT along with the increase in contact area could be the reason for the higher static COF in HT He environment [34]. The contact depth at HT He for 800HT is around 25 μm, and 6 μm at RT. The higher contact depth also increases the resistance to sliding and accordingly the static COF.

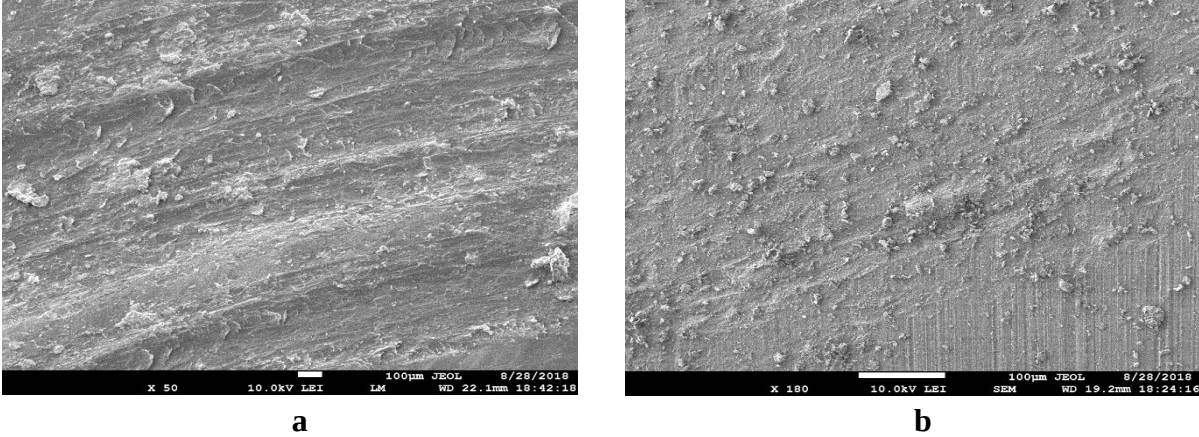


Fig. 26 SEM images of alloy 800HT wear track (a) At 750 °C He (b) At room temperature.

Fig. 27 shows the average static COF for alloy 800HT under 10 N normal load. The possible reason for the increase in the static COF at HT He environment for alloy 800HT could be the higher wear rate leading to higher contact depth and increased plowing resistance. It is noted that the static COF of both alloys is around 1.5 to 2.5 times higher than the dynamic COF reported above for unidirectional experiments. The dynamic COF values during these oscillation experiments are within the error limits reported, which will stabilize over time as mentioned earlier. According to the static COF reported here and in section 3.5, Inconel 617 has proven its superior performance over alloy 800HT.

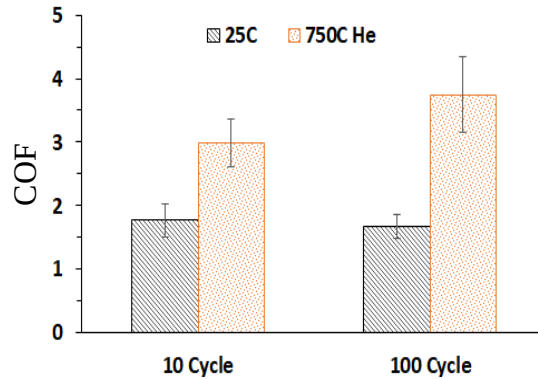


Fig. 27 Average static COF in RT and HT He environment for Alloy 800HT.

4.6. CHARACTERIZATION AND DISCUSSION

4.6.1. Surface Morphology

Fig. 28 shows the SEM images of the surface oxides on the sample surface as well as on the wear track (at different magnifications) in both air and He at 750 °C (10 N normal force and 0.15 m/s sliding speed). The arrows on the micrographs denote the sliding direction. The SEM pictures

show the matrix oxide surfaces with fairly analogous morphologies in air (Fig.28c) and He (Fig.28i) atmospheres except that the surface oxide particles in air are more crystalline and larger in size, as compared to the oxide formed in He. A scattered and discontinuous compacted glazed layer formed by oxide debris is found (Fig. 28d, e, f) on the wear track in HT air. Similar patches of the compacted glazed layer are seen on the pin surface which resulted in lowering the COF even with discontinuous glazed layer on the disk.

This form of compacted surface is found only on the samples showing lower COF in HT air atmosphere, namely for 5 N load at all three speed conditions and for 10 N load at 0.15 m/s sliding velocity. Therefore, the observed compacted oxide layer seems to be the key factor to reduce the COF on alloy 800HT at HT environments. For other loads and sliding velocities, the conditions are not favorable to generate a compacted oxide that can support the contact pressure, as explained in section 3.3. The wear track surface morphology of these conditions is similar to the HT He samples, as shown in Fig. 28(j, k, l) where no such layer is observed. The clear presence of adhesive wear patches are seen on the wear track with the surface almost free of wear particles, implying the dominance of adhesive wear mechanism for successive process of repeated sliding [35,36].

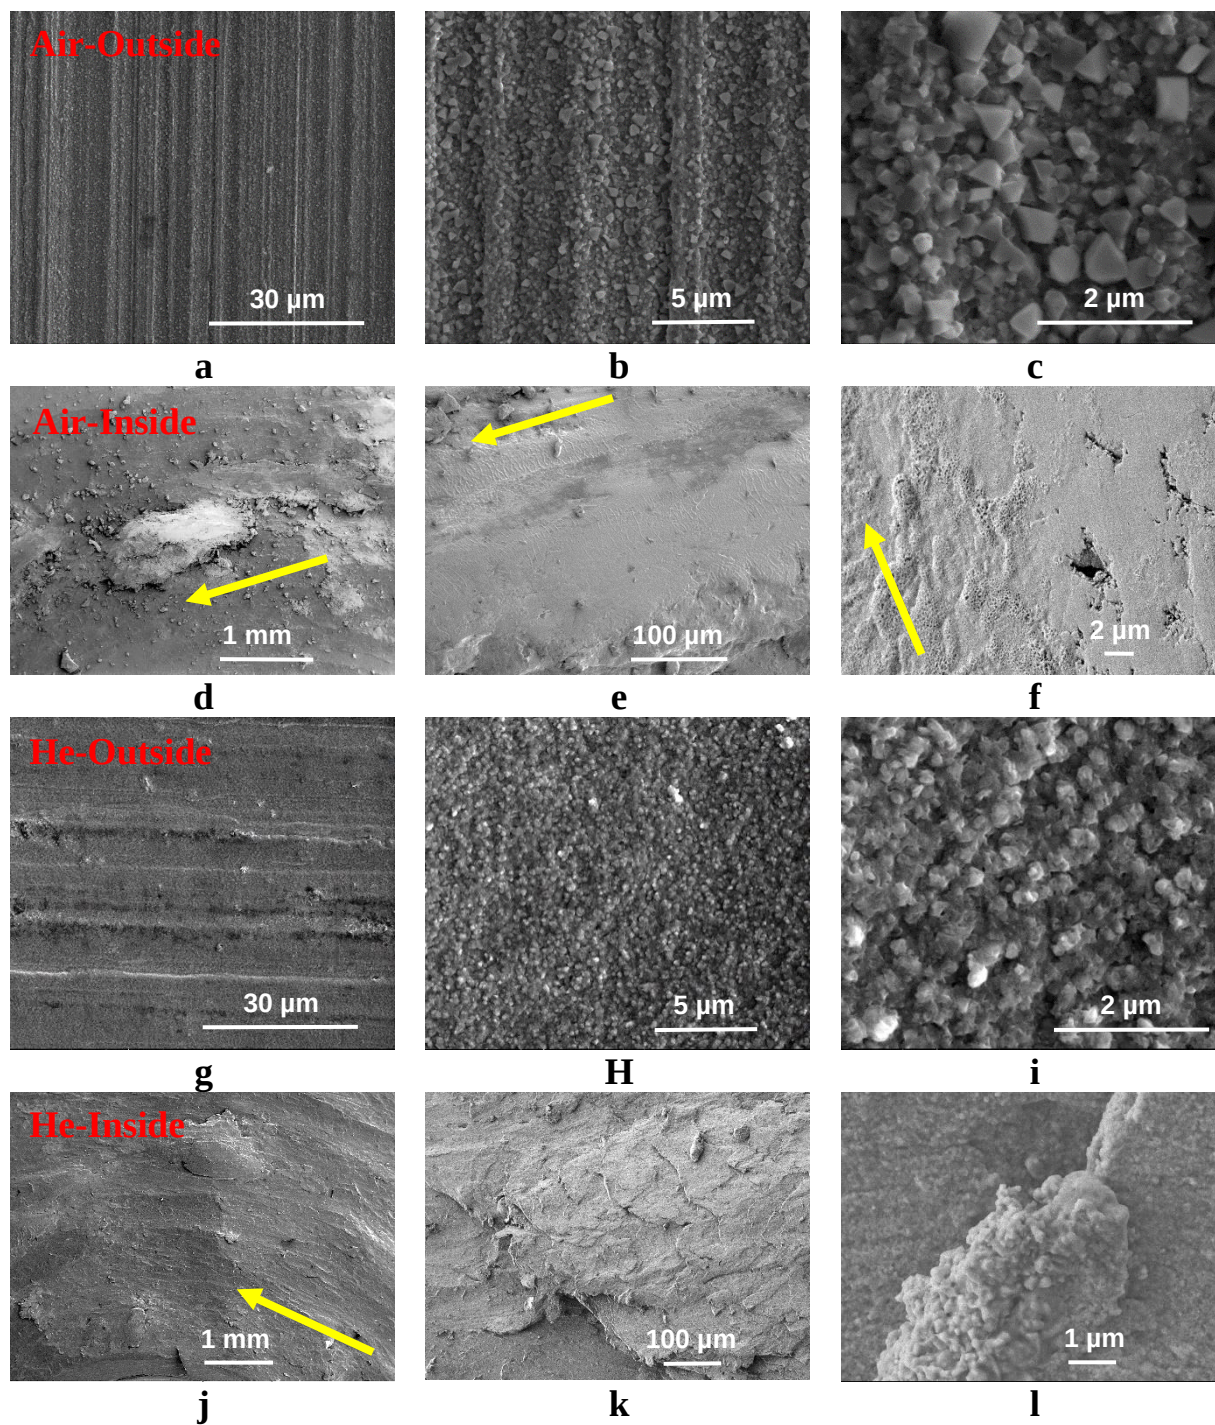


Fig. 28 SEM images of specimens at 750 °C under 10 N load at 0.15 m/s sliding speed (a, b, c) in air outside the wear track (matrix), (d, e, f) in air inside wear track, (g, h, i) in He outside the wear track, (j, k, l) in He inside wear track.

4.6.2. SEM/EDS

Examining the wear track cross-section SEM images shown in Fig. 29, it is clear that for the same duration experiments, the mixed oxide layer generated in air is thicker than the one in He ($\sim 10.0\ \mu\text{m}$ in air and $\sim 4.0\ \mu\text{m}$ in He). Note that layer thickness varies from point to point depending on the location of the wear track, as the surface is changing during sliding. The mixed layer thickness is observed to vary from $1\ \mu\text{m}$ to $20\ \mu\text{m}$ in air and from $0.8\ \mu\text{m}$ to $10\ \mu\text{m}$ in He. The lamellar formation of the metal bulk and oxide mixed layer is evident for both He and air conditions in Fig. 29, which happens mainly due to the repeated unidirectional sliding under adhesive contact. The formation of cracks under the layer is also visible in both conditions. The initial wear of the surface is dominated by abrasive wear mechanism at HT, caused by crack nucleation, and propagation in the hard and brittle oxide layers. Removal of the oxide layer increases the adhesive contact between the bare metal surfaces and consequently, adhesive wear becomes dominant. Tangential shear during sliding motion and under compression at the strongly bonded adhesive contact generates flake-like particles followed by nucleation and propagation of cracks in combined compression and shear fracture modes [35]. The subsurface crack seen in Fig. 29 a, c is an example of crack propagation after continuous sliding under compressive and shear load.

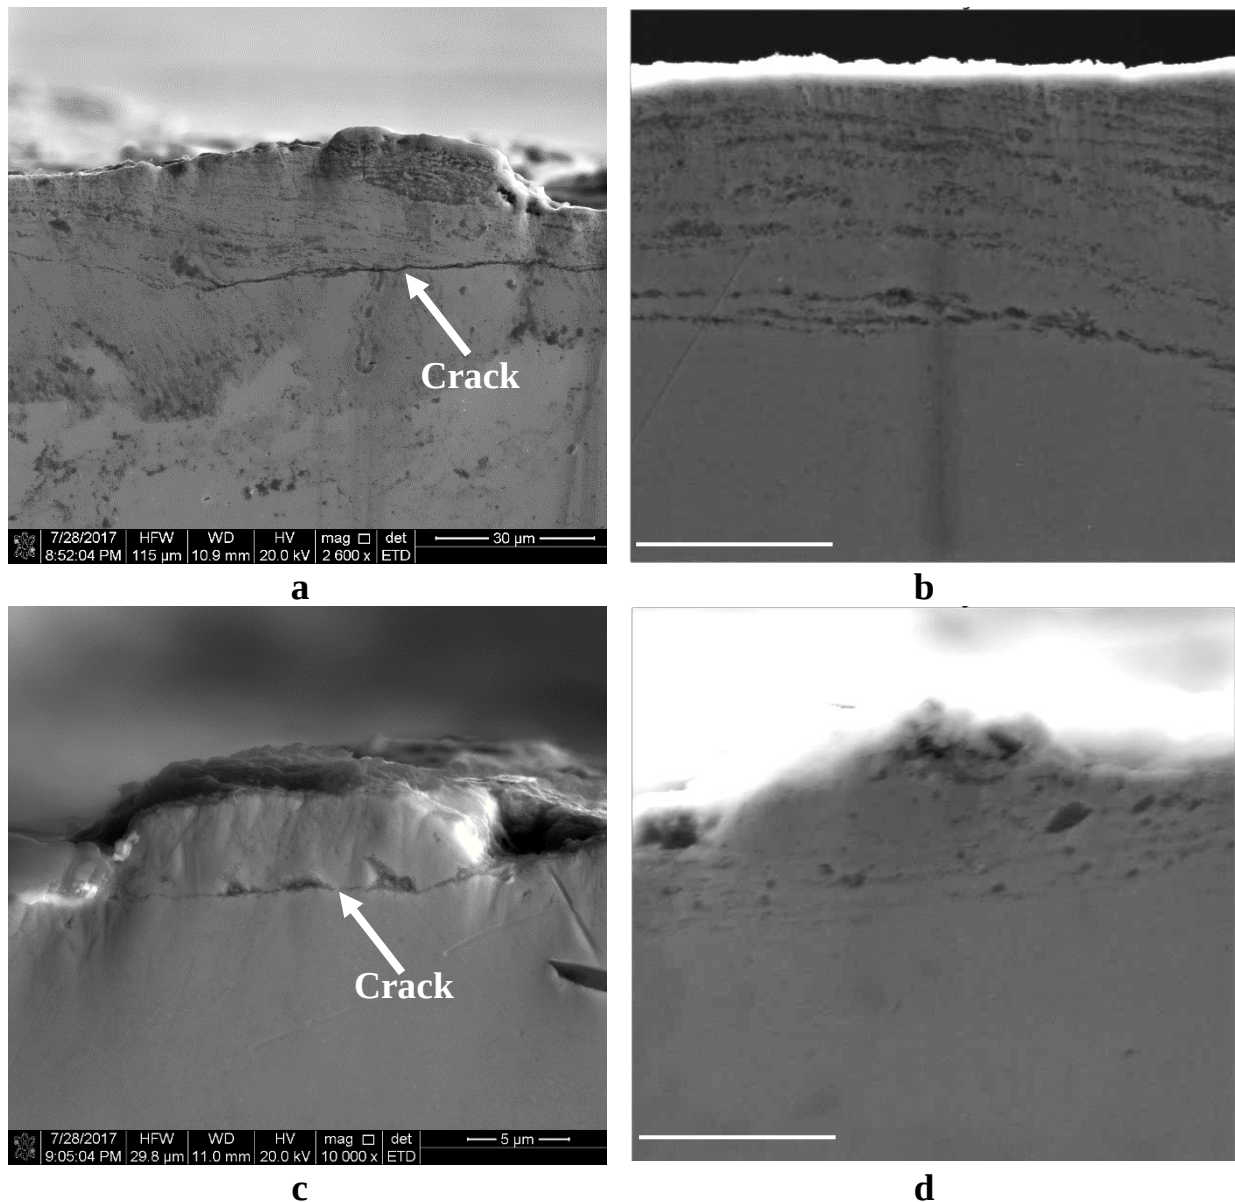
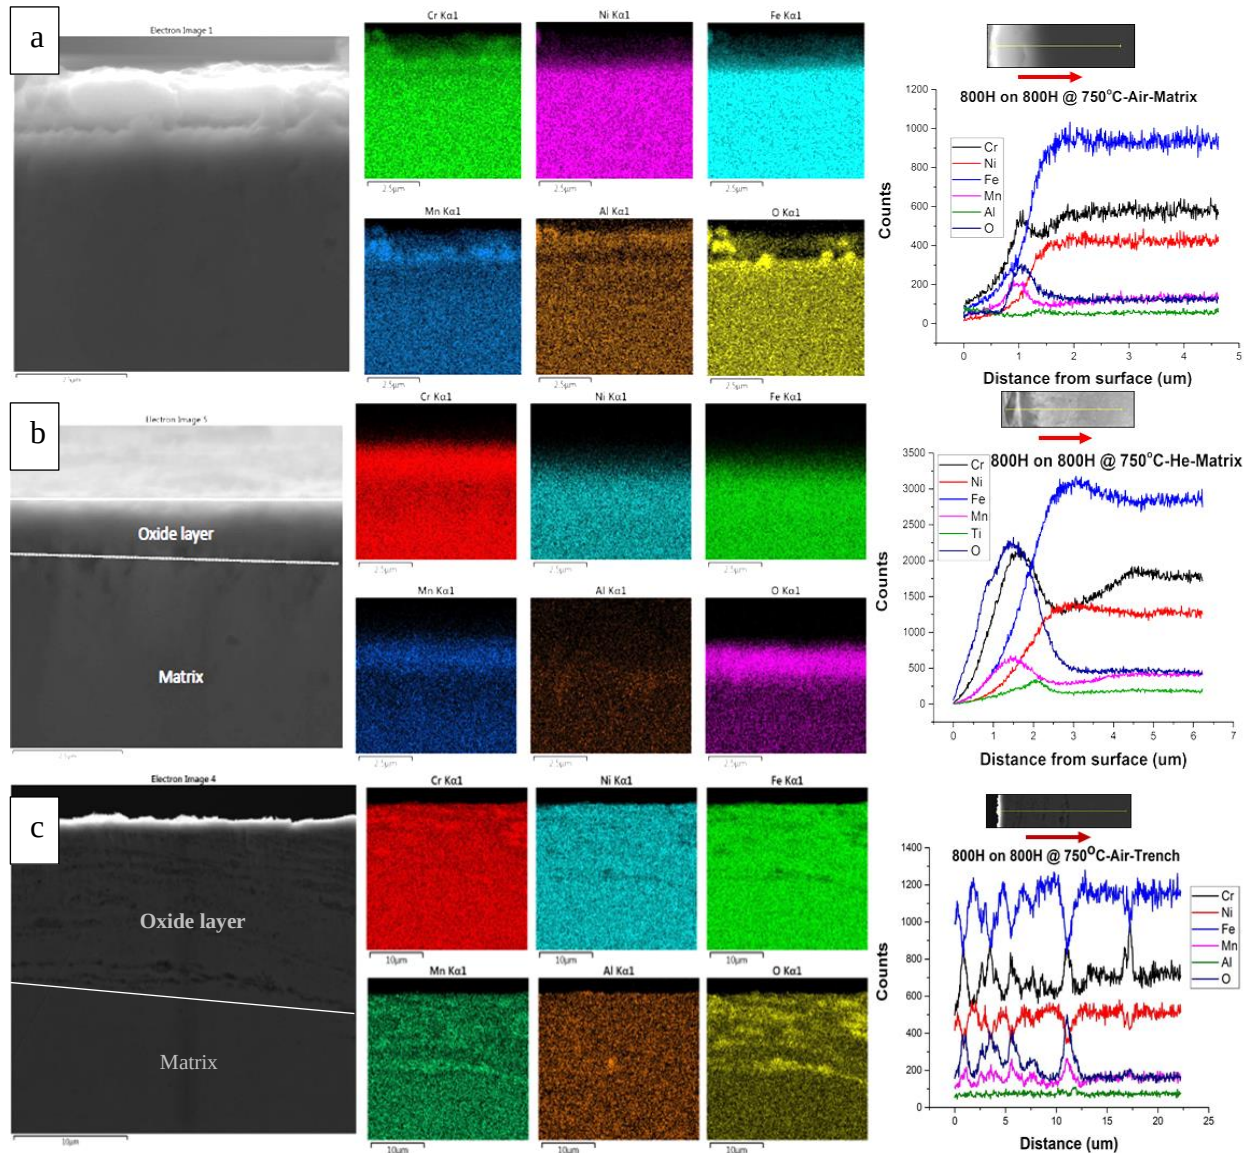


Fig. 29 Cross section SEM images on the wear track at 750 °C, 5 N, 0.04 m/s (a, b) air, (c, d) He.

The EDS results at the cross-section of the wear tracks show thicker oxide penetration in air at HT, compared to He environment. The cross-section SEM images in Fig. 30 show the top surface of the wear track which is a mixing zone of oxides and alloy elements creating non-uniform layers. This mixing zone is referred to as mechanically mixed layer (MML) [21,37]. The thickness of this MML for alloy 800HT at 750 °C under 5N normal load is 18 μm and is observed only in air, whereas in He environment more brittle composite layer (CL) is observed. The MML has better interface strength with the substrate, as compared to CL and, therefore, CL has the tendency to get

detached from the wear surface leading to higher wear rates [21]. This diffused adhesive interface of MML and ability to transfer the load to the substrate reduces the wear rate. The quick removal of the oxide debris from the wear track in He at 750 °C is likely the reason of higher thickness of oxygen penetration depth on alloy 800HT wear track.





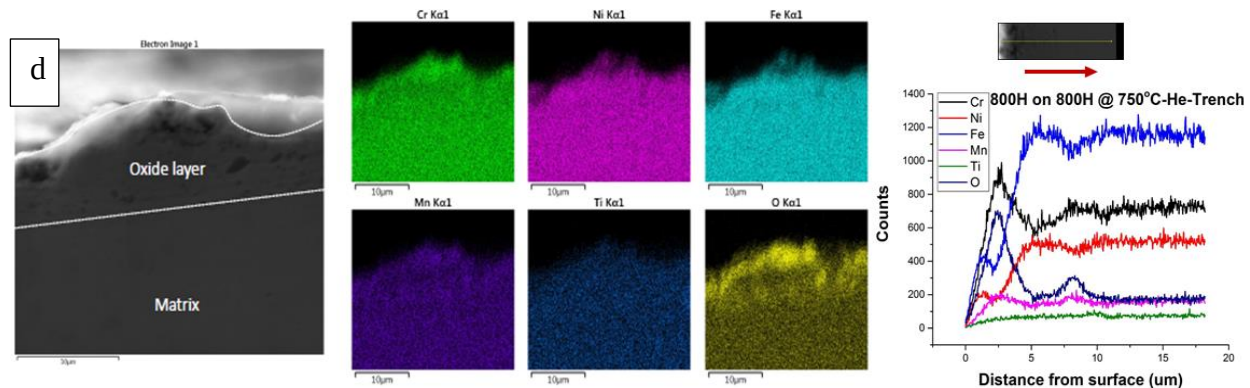




Fig. 30. Cross section SEM images and EDS map of alloy 800HT at 750 °C, (a) Air outside wear track, (b) He outside wear track, (c) Air on wear track and (d) He on wear track.

EDS analysis was performed on different areas of the wear track and surfaces outside the wear track to investigate the chemical composition of the oxide layers (see Fig. 31 for the case of 750 °C, 5N, 0.04 m/s). The EDS analysis on the area outside the wear track shows evidence of the oxide layer enriched by Fe, Cr and Ni in both air and He atmospheres. The chemical composition of the surface oxide layer in air inside and outside the wear track areas are similar, except a slight increase of the oxygen content. This is indicative of the oxide formed on the parallel distributed needle-like phases outside the wear track and the compacted debris in the trench as seen in Fig. 28c, f. For the samples tested in He, the composition remained similar both inside and outside the wear track surfaces, except for the wear debris scattered over the track. Inside the wear track surface in He, the oxygen content is found to be reduced, compared to some areas outside the wear track. At some of the points on the area outside the wear track, high amount of titanium is also found which is believed to be the titanium oxide generated in the grain boundaries. Comparing the wear surfaces in air and He in Fig 31(b, d) it is seen that the compacted oxide debris on the surface in air has higher oxygen content, confirming the retention of oxide on the track, resulting in lower COF values observed in air.

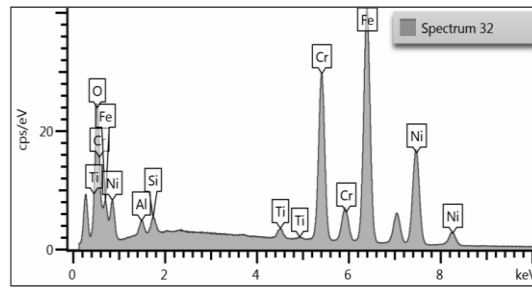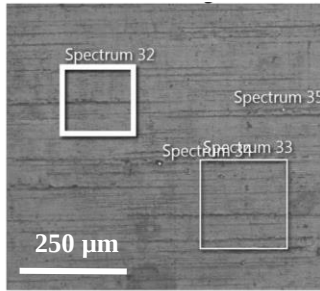



Element	Wt%	Wt% Sigma	Atomic %
O	10.17	0.12	27.75
Al	1.14	0.03	1.84
Si	1.02	0.03	1.59
Ti	0.87	0.03	0.79
Cr	20.14	0.07	16.91
Fe	41.30	0.10	32.28
Ni	25.35	0.09	18.85
Total:	100.0		100.0

a

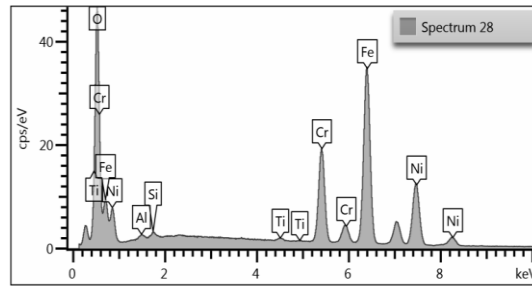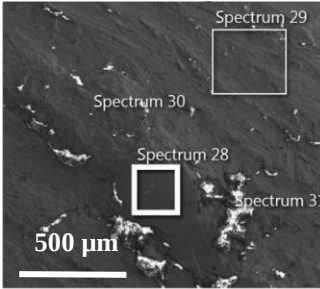



Element	Wt%	Wt% Sigma	Atomic %
O	24.54	0.13	52.87
Al	0.41	0.03	0.52
Si	0.37	0.02	0.46
Ti	0.31	0.02	0.22
Cr	14.18	0.06	9.40
Fe	39.33	0.11	24.28
Ni	20.86	0.09	12.25
Total:	100.0		100.0

b

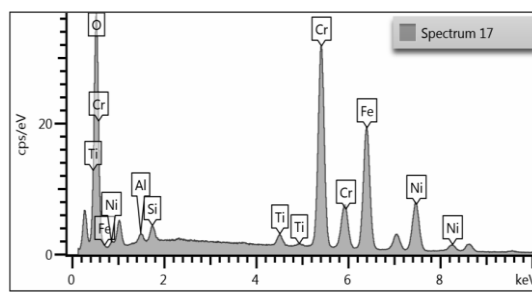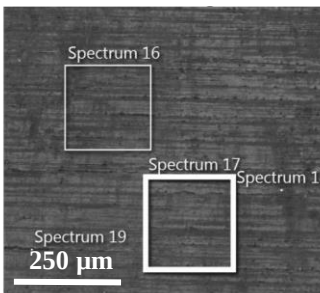

Element	Wt%	Wt% Sigma	Atomic %
O	22.10	0.14	48.60
Al	0.81	0.03	1.06
Si	1.12	0.03	1.41
Ti	1.21	0.03	0.89
Cr	31.21	0.10	21.11
Fe	27.68	0.10	17.44
Ni	15.86	0.10	9.50
Total:	100.0		100.0

c

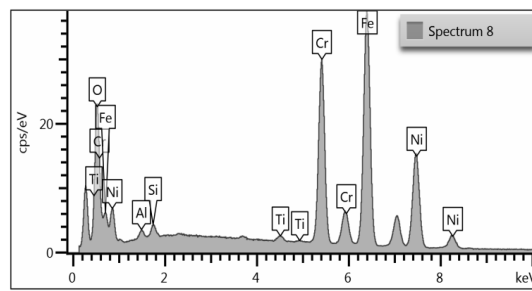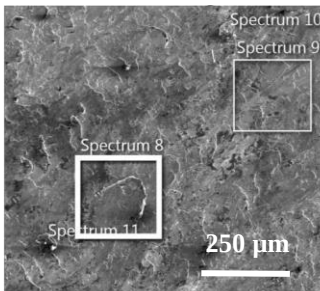

Element	Wt%	Wt% Sigma	Atomic %
O	10.52	0.12	28.66
Al	0.68	0.03	1.10
Si	0.77	0.03	1.19
Ti	0.49	0.02	0.45
Cr	21.63	0.07	18.13
Fe	41.05	0.10	32.03
Ni	24.86	0.10	18.45
Total:	100.0		100.0

d

Fig. 31. SEM pictures and EDS analysis of samples (a) in air and outside wear track, (b) in air and inside wear track, (c) in He and outside wear track, (d) in He and inside wear track (750 °C, 5N, 0.04m/s).

4.7. SUMMARY

A comprehensive study of the tribological performance of superalloy 800HT in the complicated environment of VHTR requires covering multiple variables in the experimental tests. The conditions evaluated in this study may not cover the whole spectrum of applications but provide helpful guidelines in finding optimum operating conditions for nuclear reactor applications. The following conclusion can be drawn from this study:

- (1) In air and with the increase in temperature, the formation of a protective glazed layer in conjunction with the increase in material softness results in lower friction. This is true only for lower contact pressures, while the layer fails at higher contact pressures. The stability of this protective layer increases at higher sliding speed;
- (2) At 500 °C and 750 °C He, friction and wear stay high for all conditions due to the surface oxide instability, its brittleness and subsequent crack initiation/propagation through oxide layer in low oxygen partial pressure, resulting in the generation of larger size wear debris;
- (3) In He atmosphere, under all contact loads studied here, the specific wear rate shows a linear increasing trend with load, while the COF does not show any specific correlation with contact force;
- (4) No significant change in wear rate or COF values in He atmosphere is observed for the sliding velocities examined here (in the range of typical VHTR applications). However, in air environment, higher sliding velocities influence the formation of the compacted glaze layer and as a result, reduce friction and wear; and
- (5) At 500 °C and 750 °C in both air and He, Fe-Cr-Ni rich oxide layer is present. The variation of the mixed oxide layer thickness is significant under the wear track (between 1 to 20 μm) independent of the environment for the 500 cycle experiments.

5 TRIBO-CHEMICAL ANALYSIS OF INCONEL 617

The results presented in this chapter have been published in the Journal of Nuclear Materials in 2019.

- “Tribo Chemistry of Inconel 617 during sliding contact at 950 °C Under Helium Environment, *Journal of Nuclear Materials* (2019);
<https://doi.org/10.1016/j.jnucmat.2019.04.032>

5.1. SURFACE MORPHOLOGY

Fig. 32a shows an optical image of the microstructure of as-received Inconel 617. Figs. 32b-d show the microstructure evolution (SEM) images due to oxidation in air and He environments. The average grain size in the as-received material is 30-40 μm , in agreement with Ref. [3]. The samples were polished to 30-40 nm root-mean-square roughness, before the oxidation experiments. The roughness of the sample surfaces was measured using a Tencor P-6 stylus profilometer. Formation of grain boundary ridges is observed on the oxidized samples, both in air and He atmospheres. The rate of growth is different in He, compared to air, which is evident from Figs. 32c and 32d. Specifically, the grain boundary ridges are more evident in air than in He, after 100 hr. On the other hand, the width of the ridges is wider in He. After 500 hr of oxidation, the width of the ridges increases further and the amount of grain boundary visible in a specific area has also been reduced, compared to the 100 hr aged sample.

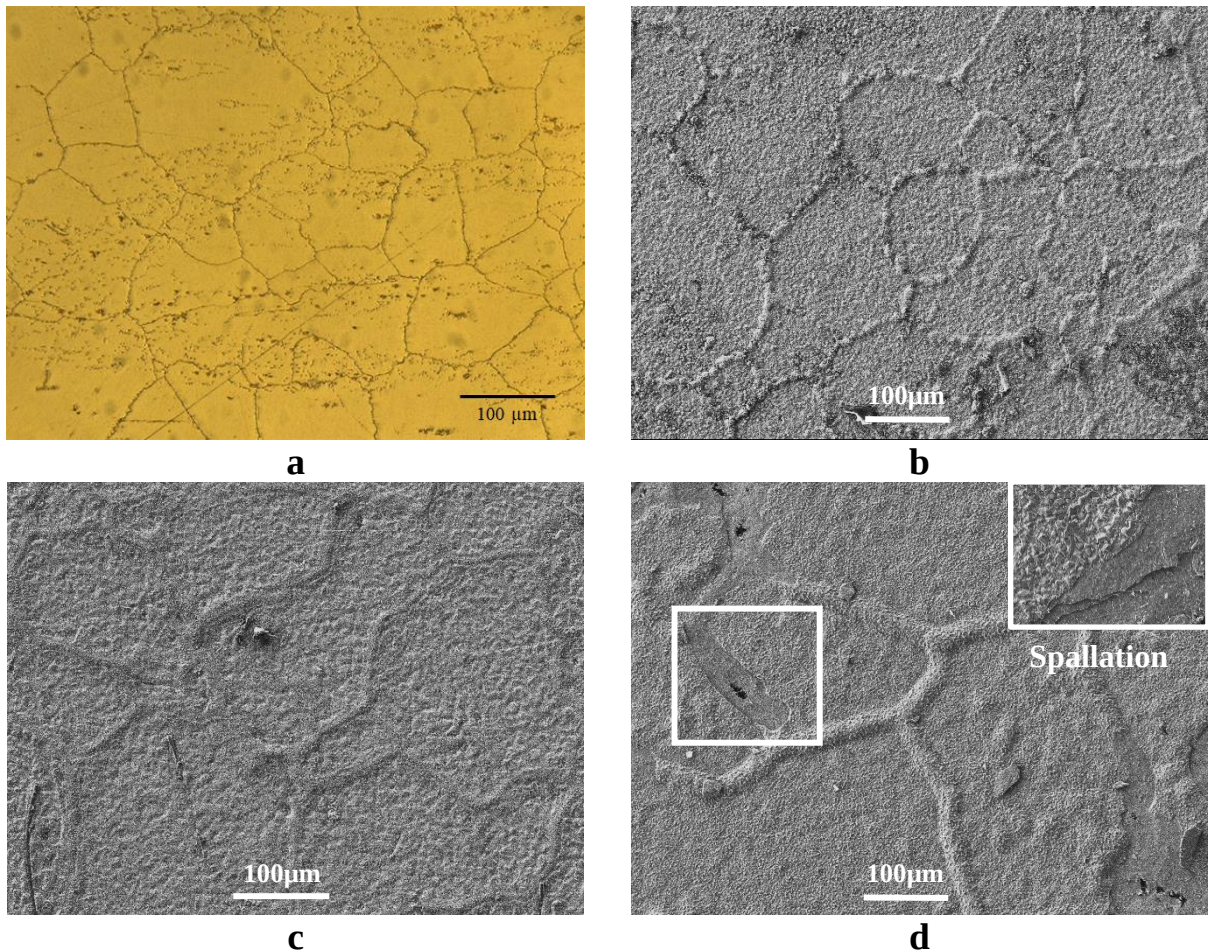


Fig. 32. Microstructure evolution of Inconel 617: (a) optical image of virgin sample; SEM images of samples aged at 950 °C (b) 100 hr air, (c) 100 hr He, (d) 500 hr He. All images obtained at the same magnification.

From the EDS analysis it is found that the grain boundary ridge is mainly formed by Ti-oxide along with Cr-oxide. It is also limited by the amount of Ti available until depletion. It is believed that, over time, some of the grain boundary ridge growth slowed down and got covered by the Cr-oxide, and only few of the grain boundary ridges grew to be visible. For the case of the 500 hr aged sample, spallation of oxide is observed on few places near the grain boundary regions (Fig. 32d inset), which might have occurred during the cooling process due to the difference in thermal expansion of metal compared with oxide, and the internal stress difference between the oxide on the grain boundary and the nearby surface. Spallation reveals the presence of dense Cr-oxide in layer formation below the irregular morphology on the surface, as shown in the inset of Fig. 32d.

Fig. 33 shows magnified surface morphologies inside and outside the grain boundary ridges. At HT air atmosphere after 100 hr, the presence of high oxygen content helps the formation of larger nodular grains of oxides on the surface. On the grain boundary, the oxide shows the presence of more porosity than the other areas. At low oxygen partial pressure of He atmosphere, the formation of oxide is influenced greatly by the chemistry of impurities present. SEM image of the 100 hr aged samples in He (Fig. 33d) shows the presence of less nodules and less crystalized regions, compared to the surface exposed in air environment. The surface oxide shows the presence of few larger nodules on an oxide layer with mode intergranular gaps. The grain boundary shows comparatively larger crystalized oxide. The presence of minute quantities of CO₂ and H₂O in He is believed to be the control parameter of creating nodular oxide particles facilitating the crystallization of oxides, as discussed in Refs. [38–41]. The 500 hr aged samples in Fig. 33g-i show growth in the crystal size and is similar to what is observed for the 100 hr aged samples in air. Both grain boundary and surface show similar morphology and crystal size with no intergranular gaps.

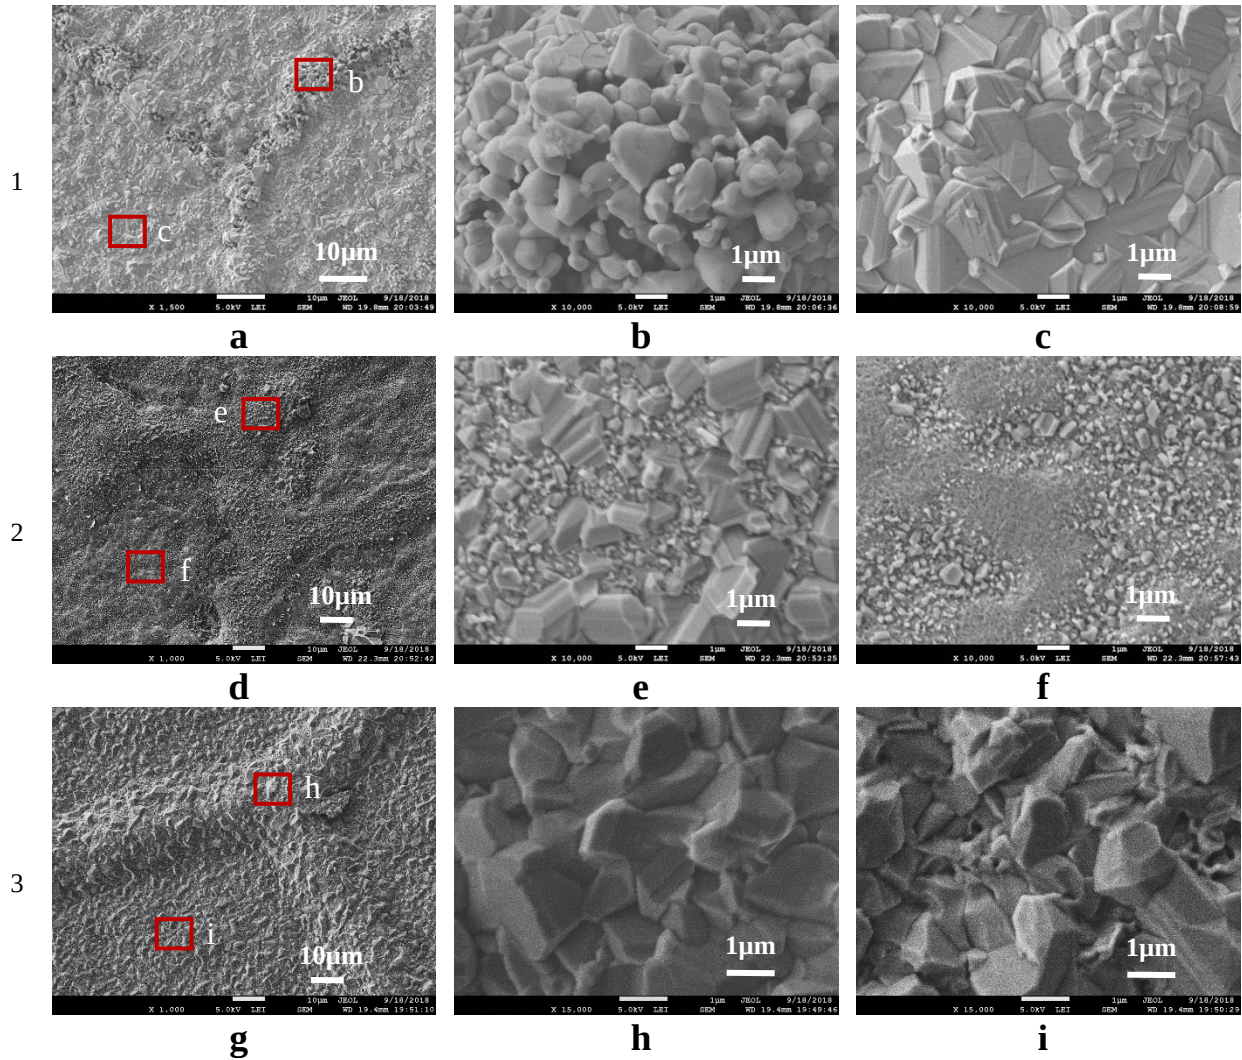


Fig.33. Surface morphologies after oxidation for Inconel 617 at 950 °C: (1) 100 hr air, (2) 100 hr He, (3) 500 hr He. Images shown in (b,e,h) are taken on the grain boundary ridges, and (c,f,i) are taken on the surface.

Cross-section backscatter (BS) SEM images in Fig. 34 show the presence of internal oxidation of aluminum along the grain boundary, and Cr-oxide on the surface. Fig. 35 shows the cross-section SEM and EDS line scans for the samples undergone tribological experiments. The EDS line scan in Fig. 35b, which is along the grain boundary, shows a spike of Ti on the surface, which is in line with the EDS data on the grain boundary. On the other hand, EDS on the cross section of the samples following HT tribological experiments in both air and He atmospheres reveal the presence of Cr-rich oxides on the wear track, with internal oxidation of aluminum. On the wear track, the thickness of the oxide layer varies between 1 – 10 μm. In case of air atmosphere, at the end of the oxide layers there is high concentration of Mo, whereas in He atmosphere the concentration is the same as the matrix after the oxide layer.

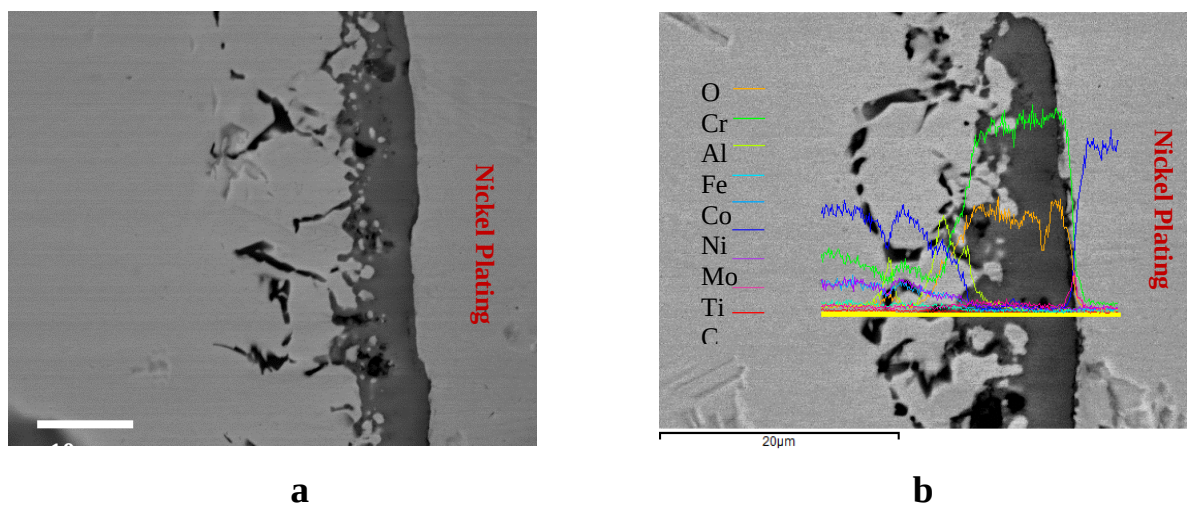


Fig. 34. (a) BS SEM image and (b) EDS line scan on the cross section of Inconel 617, aged 100 hr in He at 950 °C.

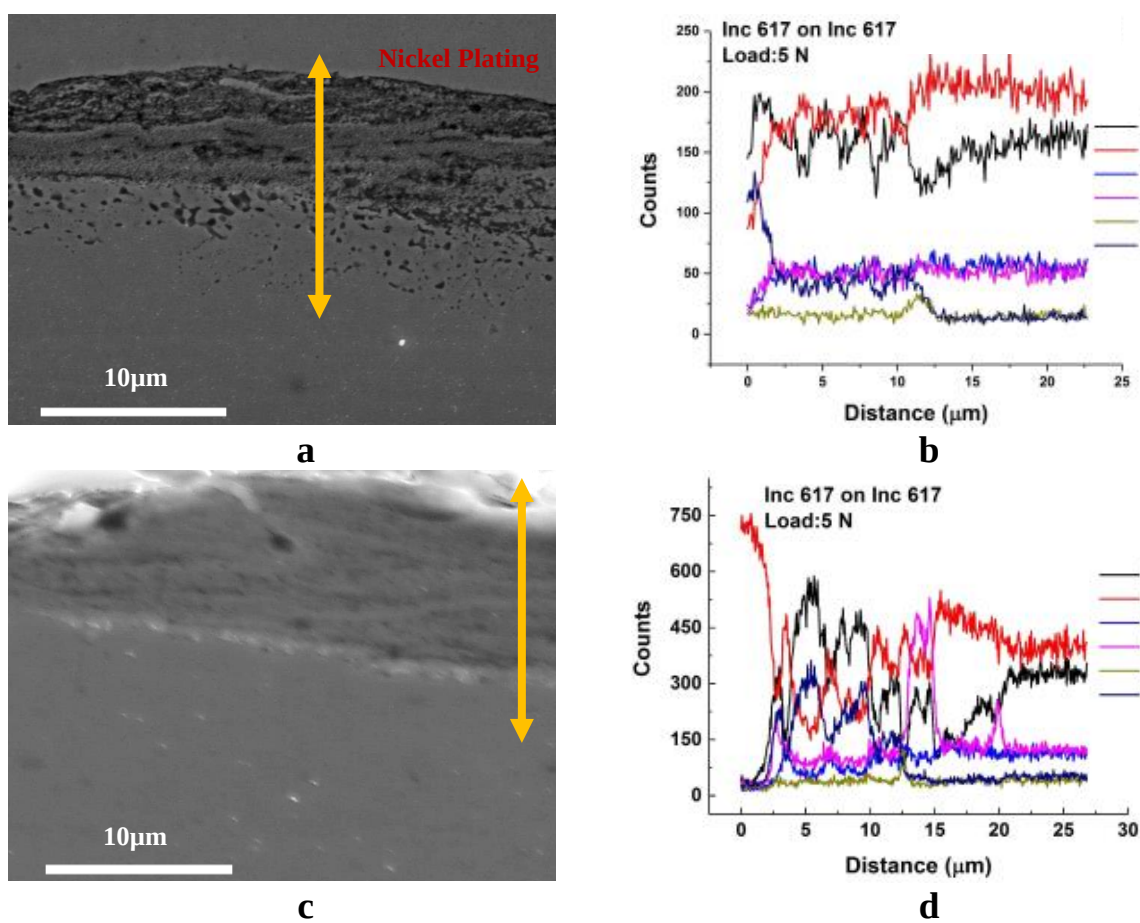


Fig. 35. Cross section SEM images and EDS line scans of Inconel 617 at 950 °C under 5N load inside the wear tracks: (a, b) He, (c, d) Air.

5.2. XRD ANALYSIS

Fig. 36a presents the XRD patterns obtained over the 100 hr aged Inconel 617 samples. X-ray diffraction patterns are collected over a 1 mm² area for 30 min duration using an X-ray beam energy of 40 keV 40mA ($\lambda=1.54056$ Å) and step size of 0.005°. The X-ray patterns indicate that the diffraction peaks for the underlying metal substrate are clearly noticed for all samples. This means that X-rays completely penetrate the oxide layer thickness, and all the oxide phases are detected. Inconel 617 at 500 °C in He or air atmospheres, did not show any prominent peaks other than the substrate. Some of the previous works indicated the presence of small amount of Cr₂O₃ and (Ni/Mn)Cr₂O₄ spinel close to the substrate peaks [42–44]. The oxide scales of Inconel 617 at 950 °C in Fig. 33a are strongly composed of Cr₂O₃ and (Ni/Mn)Cr₂O₄, whereas other oxides such as TiO₂ and MnTiO₃ are clearly detected in He, but weakly detected in air.

In contrast to the previous results in air [10], NiO peaks are not detected. Fig. 36b presents the XRD patterns obtained over the Inconel 617 specimen following the tribotesting under different conditions as described above. X-ray diffraction patterns are collected inside and outside the wear tracks. By comparing the XRD patterns obtained inside and outside the wear track at 500 °C, no changes are observed under He. On the contrary, when the testing is performed at 950 °C drastic differences can be observed. The diffraction peaks that are observed outside the wear track corresponding to the Cr₂O₃ are not present in the diffraction patterns inside the wear track. This can be understood on the basis of Cr₂O₃ being a sacrificing mediator to contribute to reduce or increase the COF. The easy cracking and removal of oxide indicates that the oxides in He have lower shear strength compared to the oxides generated in air.

At 500 °C, there is neither sign of significant formation of Cr₂O₃ (likely due to the slower kinetics of oxidation), nor any other oxide on the surface, which indicates that the reduced COF is the result of only thermal softening. Also, inside the wear track, the XRD pattern appears shifted to higher diffraction angles, a result that implies that the lattice of Inconel 617 phase has contracted under compressive stresses. On the contrary, under air, Cr₂O₃ particles are continuously formed and thus replacing the ones that have been exhausted and retained on the wear track, as compacted layer. Thus, Cr₂O₃ particle XRD peaks can still be traced at the end of the experiments. This can be the reason for the lower COF of 0.45 in the case of air, compared to 1.4 in He.

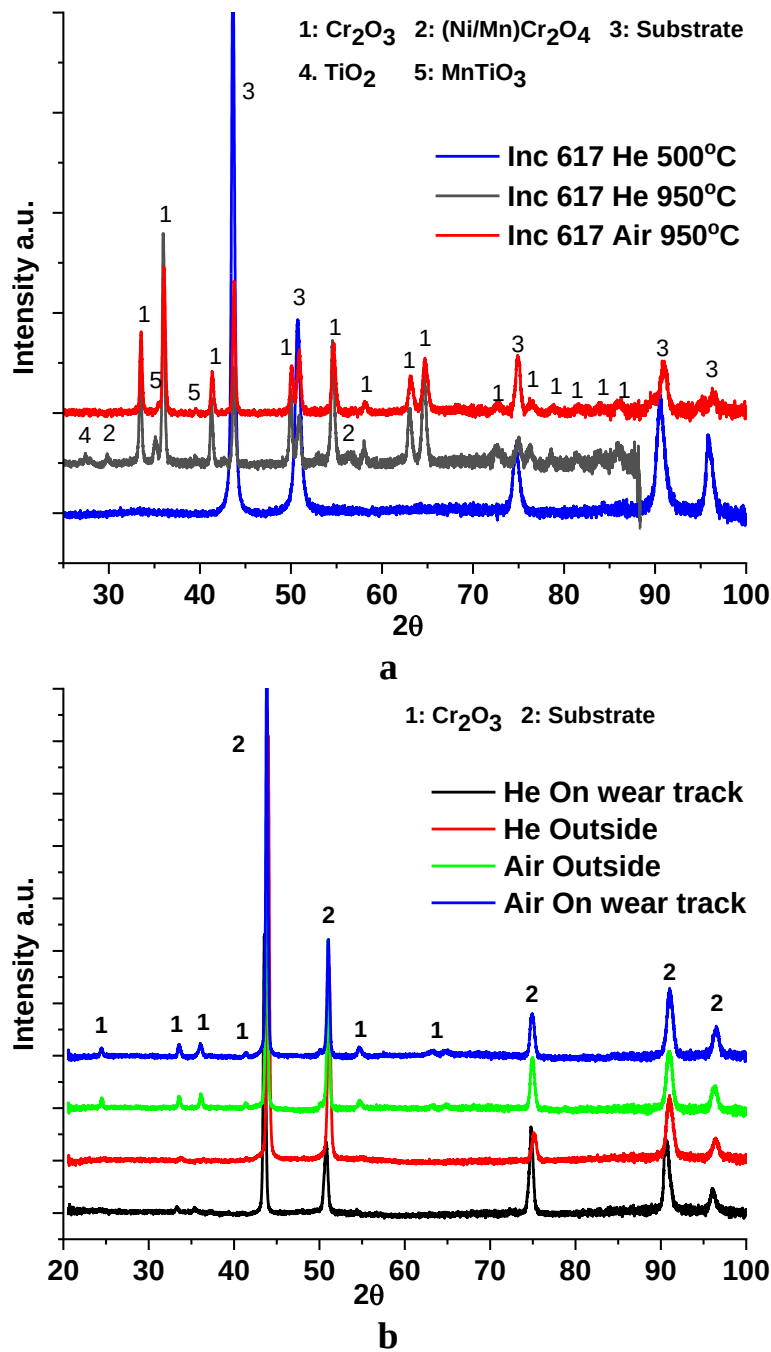


Fig. 36. XRD data on (a) samples aged for 100 hr; (b) inside the wear tracks created at 950 °C tribotesting.

5.3. RAMAN ANALYSIS

Raman spectroscopy is a unique tool to investigate the oxygen sublattice and provide complimentary structure information to the XRD analysis. Fig. 37a presents the Raman spectra acquired over the specimens received from the above described tribotesting, under different gas and temperature conditions. Fig. 37b presents the Raman spectra of samples aged in He over

different durations of time. Referring to Fig. 37a, the Raman bands at 554 cm^{-1} , 616 cm^{-1} and 685 cm^{-1} include contributions from formed phases, such as Cr_2O_3 , NiCr_2O_4 , FeCr_2O_4 spinels, and/or $(\text{Ni/Fe})\text{Cr}_2\text{O}_4$ mixed spinel phase. As the duration of tribotesting is increased, the crystallization/formation of the spinel type oxides is becoming more developed [45,46]. This is expected as a spinel solid solution requires more time to be formed. The spinel disordering is obvious based on the asymmetry of the bands (e.g., band at 685 cm^{-1}). A possible reason for this disordering can be the presence of oxygen vacant sites as the metal oxides are mixed towards the formation of the spinel structure, as well as the short duration of the experiment, compared to the time scale of formation of the spinel structure.

Given that the tribotesting and the aging tests were both conducted in He at 950 $^{\circ}\text{C}$, by comparing Figs. 37a and 37b there is a clear effect of the wear mechanism in the phases formed. The latter is clear based on the differences on the peaks at $<1000 \text{ cm}^{-1}$ (different population of oxides) and on the peaks at high wavenumber ($>1200 \text{ cm}^{-1}$). Also, in Fig. 37a, a red shift can be observed in the Raman spectra as the aging is prolonged.

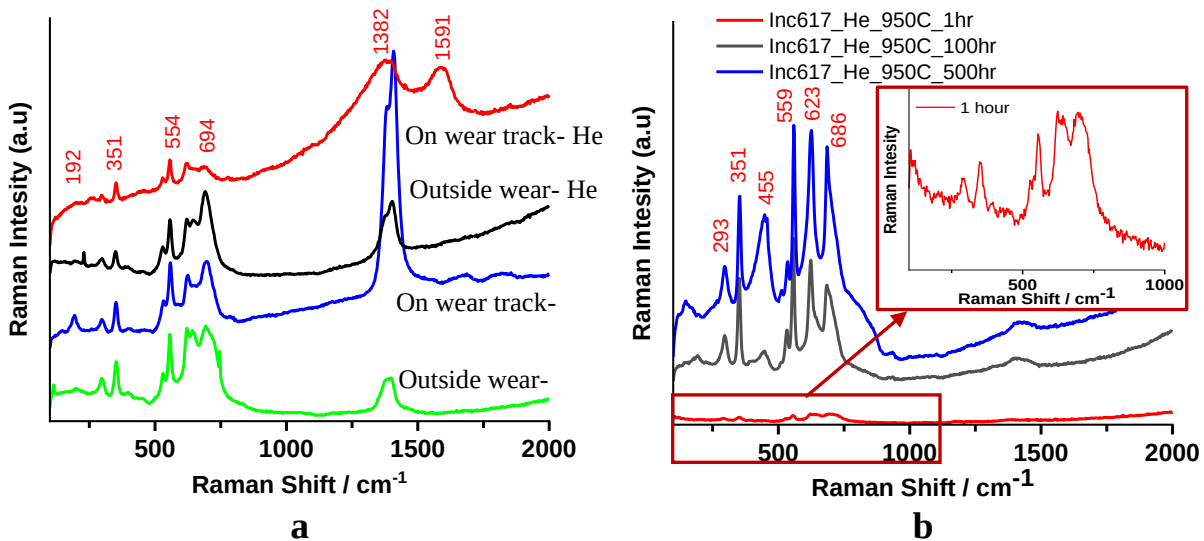


Fig. 37. Raman spectroscopy data on (a) tribotested samples, (b) He 950 $^{\circ}\text{C}$ aging samples of Inconel 617.


5.4. TOF-SIMS DEPTH PROFILING

Fig. 38 presents the TOF-SIMS depth profiles that were acquired over the Inconel 617 specimens, following tribotesting under He and air environmental conditions, both outside and inside the wear tracks. Outside the wear tracks of Inconel 617 (in He atmosphere), the presence of high Cr and O concentration was noticed, which corroborates for a Cr_2O_3 -rich surface, in agreement with the XRD and Raman results. At intermediate depths (sub-surface), Cr_2O_3 depletion is noticed, where Ni and Co-rich oxides start revealing. This behavior of the outward diffusion, temperature-driven of Cr, is in agreement with the literature for Inconel 617 [11]. Inside the wear track, the profiles are different, as Cr_2O_3 and CoO are observed. The latter is most likely diffused on the surface from greater depths.


Similar trend with CoO, is observed for NiO. The diffusion profile with depth explains the coexistence and concomitant formation of the mixed spinel structures observed using Raman spectroscopy. It is interesting to note that Cr_2O_3 depletion rate, as we move to sub-surface, follows fast kinetics inside the wear track under He, whereas in air the depletion is lower. This suggests that while performing the tribo-experiments under air, the Cr_2O_3 has formed in greater depths as well, and thus can be detected. Under air, on the very top surface of the oxide, enrichment of Ni and Co-based oxides was observed, along with dominant Cr_2O_3 at a very thin layer.

5.5. SUMMARY


The combined mechanical and chemical changes of Inconel 617 surfaces are uncoupled through designed tribological (mechanical and chemical) and aging (chemical only) experiments. From the tribological experiments, both the COF and wear rate values were higher in He environment, compared to air atmosphere. The aging studies highlighted the oxidation processes and how they contributed to the evolution of different types of oxides (e.g., spinels and simple oxides). An evolution from asymmetric to more symmetric Raman peaks, demonstrated the transition to less disordered spinels. As metal oxides are vital in the tribological behavior their depth distribution was measured using TOF-SIMS. Cr_2O_3 was predominant on the surface, while in sub-surface Ni/Co/Cr oxides were found. Cr_2O_3 depletion rate follows fast kinetics in the sub-surface inside the wear track under He, whereas in air the depletion is lower.

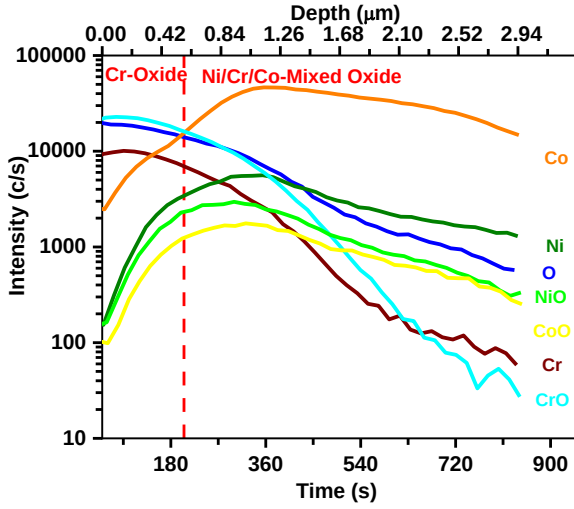


a

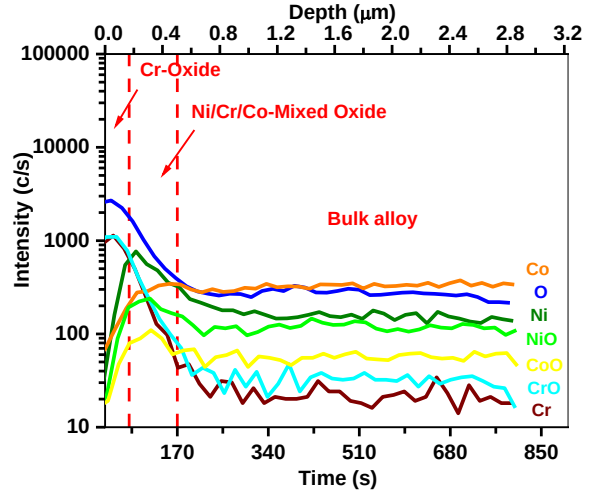

b

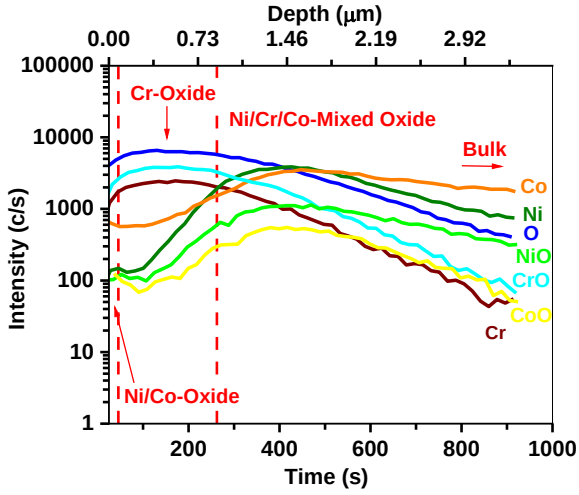

c

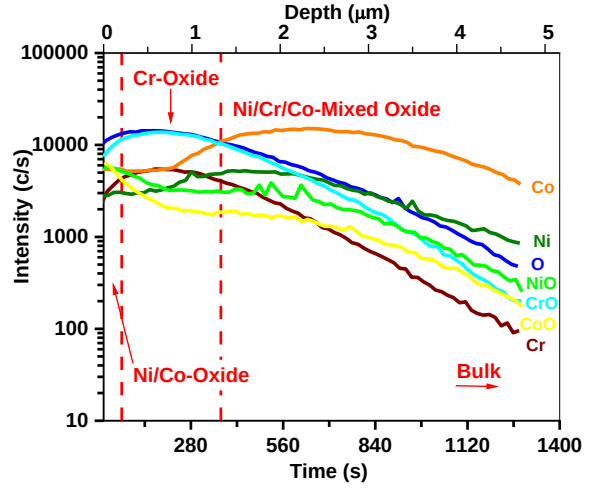

d

Fig. 38. TOF-SIMS elemental depth profiles of Inconel 617 tribotested samples at 950 °C (a) He outside wear track, (b) He inside wear track; (c) Air outside wear track, (d) Air inside wear track.

6 TRIBO-CHEMICAL ANALYSIS OF ALLOY 800HT

The results presented in this chapter have been submitted to Journal of Alloys and Compounds in December 2019.

- “Tribo Chemical change of Alloy 800HT under sliding contact at elevated temperature in impure Helium Environment”, *Journal of Alloys and Compounds*, Under Review.

6.1. SURFACE MORPHOLOGY

The surface morphology of the alloy aged in He and air environments for 100 hours is shown in the SEM images of Fig. 39. Two very different ways of the grain boundary (GB) ridge evolution is observed for He and air environments. From Fig. 39a (air atmosphere), it is clearly visible that the area on the GB is lower in height, compared to the surrounding surface. On the other hand, under He atmosphere, the GB ridge rises higher than the surrounding area. The surface of the oxide in air, other than the GB, shows multiple number of holes on the surface of different size and shape (Fig. 39c). These openings are believed to be the result of gaseous product discharge during the formation of the oxide. The grain boundary valley does not show similar structure. The surface is mostly covered by nodular-like structures with several larger openings, as seen in Fig. 39b.

The oxide generated on the surface in He does not show any such formation of openings at the investigated magnification of SEM. The surface in He, as seen in Fig. 39f, is more homogeneous with nodules of around 1 μm size created by small oxide crystals attached together shown by red dashed square. The nodules might have gaps between them, and two or more nodules can merge together to generate larger (aggregated) nodules over time. The surface on the GB shows oxides with merged nodules. The crystals on the GB are larger compared to the surface oxide crystals.

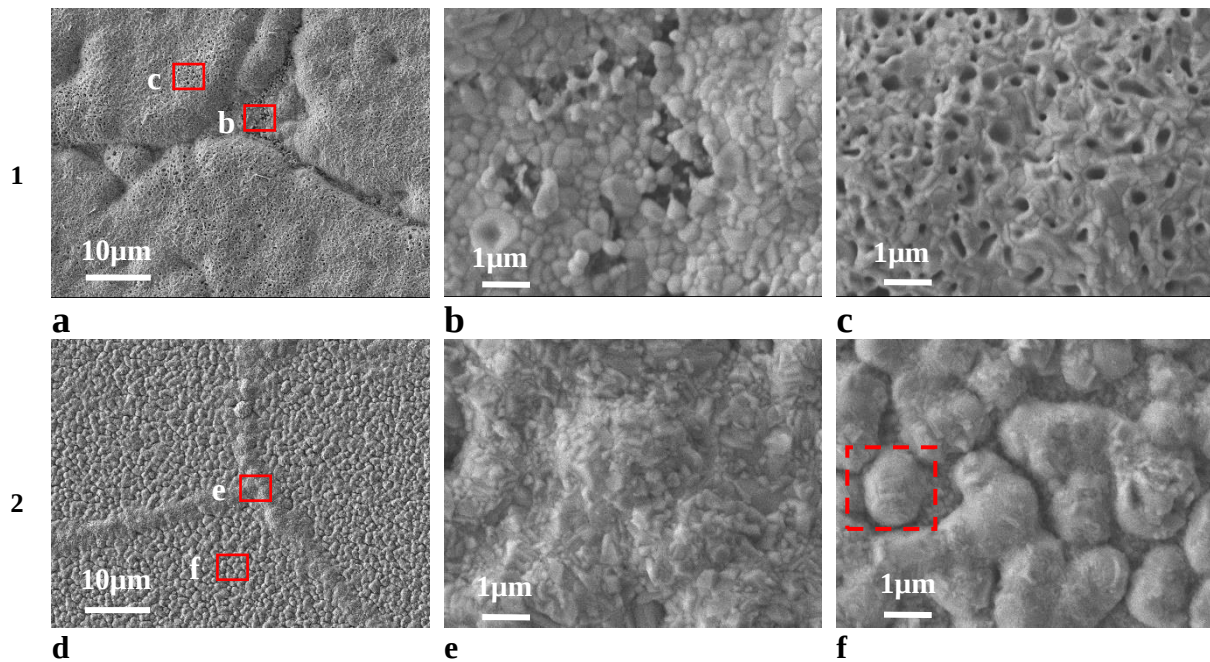


Fig. 39. SEM surface morphologies after oxidation of Alloy 800HT at 750 °C: (1) 100 hr air, (2) 100 hr He. Images shown in (b and e) are taken on the grain boundary ridges, and (c and f) are taken on the surface. The red dashed square in (f) is showing the nodule like structure of oxide.

Fig. 40 depicts the EDS map performed on the GB and surrounding surface of 100 hour aged samples showing the dominant elemental distribution. The elemental distribution map in Fig. 40a, for the sample in air confirms the presence of oxygen on the GB region with a rich presence of chromium (Cr), titanium (Ti), manganese (Mn), and nickel (Ni), compared to the surrounding surface. The surface other than the GB is mostly covered by iron-rich oxide along with Mn. Ni is found all over the sample surface but with very small concentration.

The EDS map analysis of the sample in He shows different qualitative elemental presence. The presence of oxygen is found all over the sample surface and with slightly higher concentration on the GB region, indicating higher oxidation in the area which could be the reason of height gain of the GB. The GB shows high concentration of Cr with presence of Ti and Mn, but minimum presence of Fe. The rich presence of Ti on the GB, compared to the surface, is evidence that the GB is rich with Ti-based oxide. The surface oxide in He shows presence of Fe and Cr with Mn and Ni. The surface map in He shows comparatively higher amount of Ni present than in air.

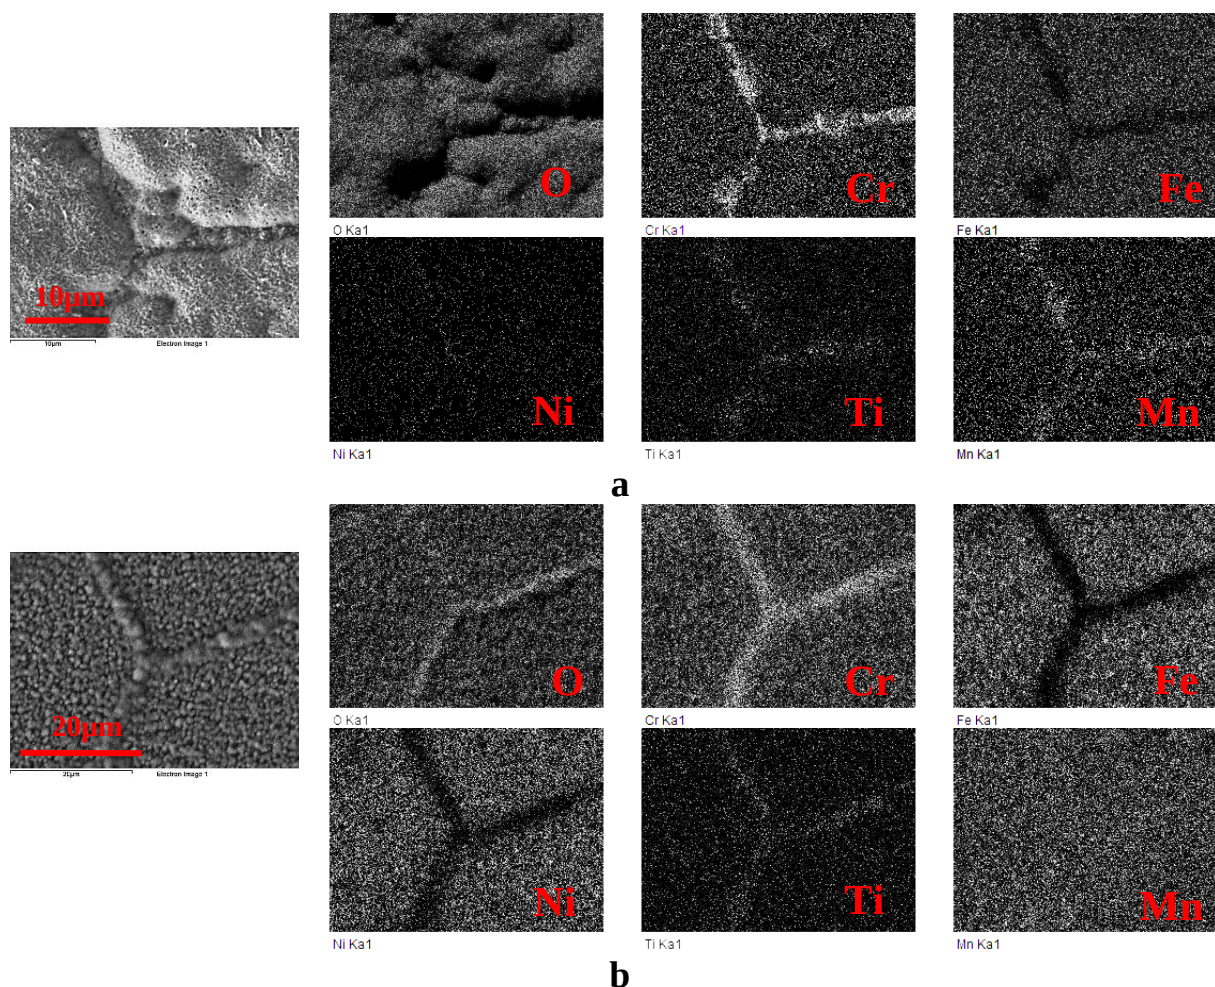


Fig. 40. SEM images and EDS analysis of samples aged at 750 °C for 100 hr: (a) in air, (b) in He.

For more insight, quantitative EDS analysis is performed on and outside the GB locations showed in Fig. 41 and the outcomes are listed in Table 5. As expected during EDS map, in air, Iron (Fe) is more dominant on the surrounding areas with 56.87 wt.%, whereas on the GB it is only 27 wt.%. On the other hand, composition of Cr jumped to 22 wt.% on the GB, whereas it is only 4% on the surrounding area. Wt.% of Ni is also increased on the GB with traces of Ti, Si, and Al, which is not found on the areas other than GB. For the sample aged in He, the oxygen wt.% is about 44% on the GB and 29% on the surrounding surface. The surface oxide is rich with Fe (23.89%) and Cr (25.76%) with the presence of Ni, Mn and Ti whereas, the GB oxide is mostly Cr rich (44.2%) with presence of Ti. So, the major difference between the GB oxide in air and He is the composition of Fe, Cr and Ti.

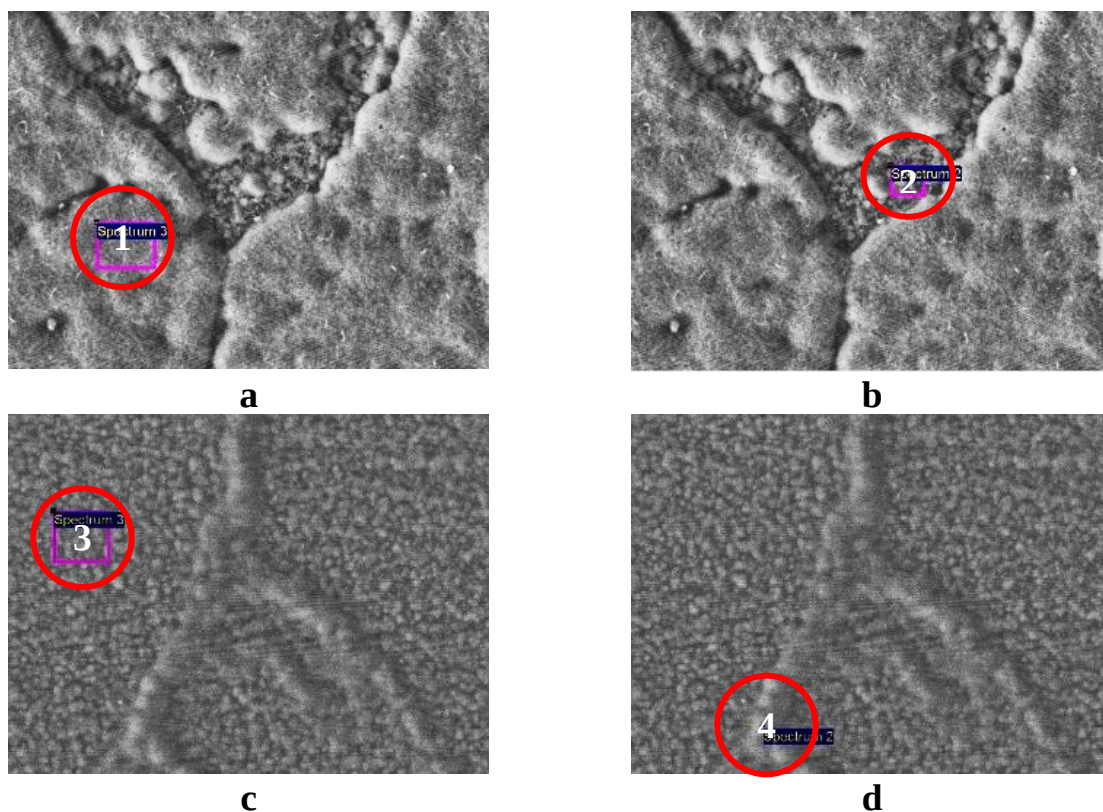


Fig. 41. SEM images showing quantitative EDS analysis locations of samples aged at 750 °C for 100 hr: (a) outside grain boundary in air, (b) on grain boundary in air, (c) outside grain boundary in He, (d) on grain boundary in He.

Table 5

Quantitative EDS analysis of Alloy 800HT aged at 750 °C for 100 hr on locations showed in Fig. 41

Location (Fig. 41)	1	2	3	4
Composition (wt%)				
O	33.48	32.59	29.12	44.33
Al	-	0.45	0.86	-
Si	-	0.81	1.06	-
Ti	-	1.33	0.69	4.34
Cr	4.45	22.10	25.76	44.20
Mn	1.51	4.31	4.50	2.71
Fe	56.87	27.72	23.89	2.97
Ni	3.10	10.02	14.11	1.45
Cu	0.59	0.67	-	-
Total	100	100	100	100

6.2. XRD ANALYSIS

Fig. 42a presents the XRD patterns obtained over the 100 hr aged samples. The X-ray patterns clearly show the diffraction peaks for the underlying metal substrate for all samples, indicating the complete penetration of the X-ray through the oxide layer thickness, and all the oxide phases are detected. Comparison of the XRD data acquired following oxidation in He at 500 °C, He at 750 °C and air at 750 °C is shown in Fig. 42a. It demonstrates that phases only from the substrate can be observed when the experiments were performed at 500 °C (mild conditions), whereas temperature raise to 750 °C caused acceleration of oxidation and thus Cr_2O_3 , Fe_2O_3 and other spinel phases peaks emerged. Previous studies on alloy 800H oxidation, in supercritical water, superheated steam and in He, mentioned the presence of Fe-Ni spinel and Cr_2O_3 [42,44,47–49].

In the case of the samples after tribo-experimentation under air at 750 °C, the oxidation was more pronounced as it can be seen by the sharper peaks. In Fig. 42b, the 20-100 2theta diffraction patterns can be seen for the cases where the experiments were run under, He and air, for both inside and outside the wear tracks. In Fig. 42c and 42d, a zoom in for the peaks at 43° and 51° of Fig. 41b is presented. For the experiment under air, it is seen that the peak at 43° is shifted to lower angles inside the track, whereas in He the opposite is valid. This type of shift is associated with the different type of stresses, tensile or compressive developed during the thermal treatments, respectively. Tensile stresses are due to the oxides' formation and lattice volume expansion favored in the air atmosphere. The oxide-related phases were noticed only outside the wear track. It seems that inside the wear track during the contact/sliding the oxides formed were purged away under He atmosphere. This coincides with the higher COF measured under He atmosphere and the known role of oxides in tribo-chemistry and lubrication (decrease of the COF) [50]. On the contrary, in the case of air the purged-out oxide is being replenished.

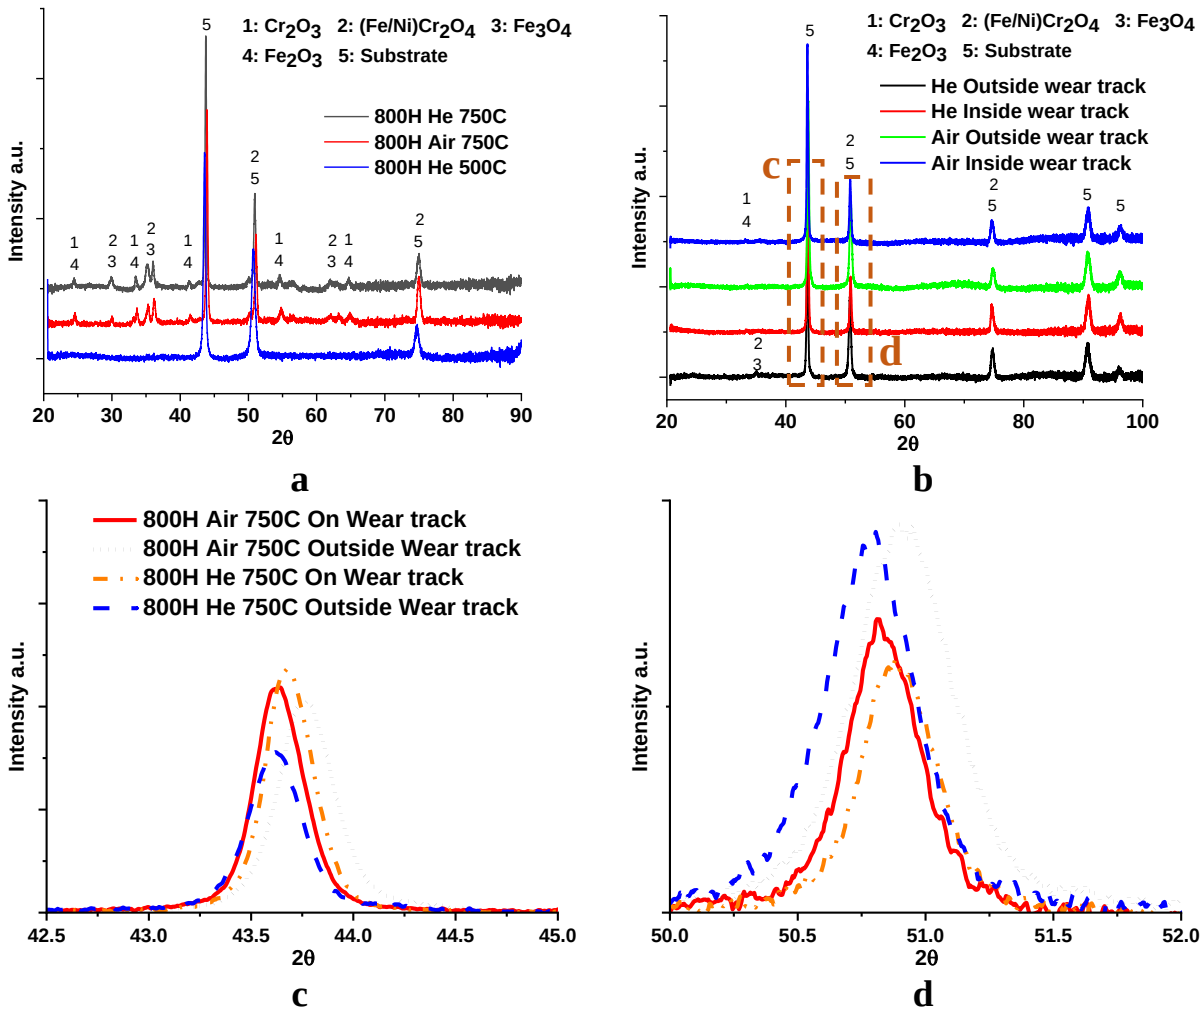


Fig. 42. XRD data on (a) samples aged for 100 hr; (b) inside and outside the wear tracks after tribotesting at 750 °C; (c and d) zoomed-in XRD data from the wear track showing the shift of peaks.

6.3. RAMAN SPECTROSCOPY STUDIES

Raman spectroscopy is a unique tool to investigate the oxygen sublattice and provides complimentary structural information to the XRD analysis. Fig. 43a presents the Raman spectra for samples oxidized (aged) at different conditions (He and air) for 100 hr and also at two different temperatures, namely 500 °C and 750 °C. Literature suggests identical Raman shifts at around 550-556 cm⁻¹ for Cr₂O₃, at 295 and 408-414 cm⁻¹ for Fe₂O₃, at 671 cm⁻¹ for Fe₃O₄, at 693-707 cm⁻¹ for NiFe₂O₄, and at around 686 cm⁻¹ for FeCr₂O₄[51–57]. The main Raman shift of (Fe,Cr)₃O₄ or Fe_{3-x}Cr_xO₄ spinel oxide varies from 671 cm⁻¹ to 686 cm⁻¹ and (Fe,Cr)₂O₃ or Fe_{2-x}Cr_xO₃ corundum oxide varies from 502 cm⁻¹ to 553 cm⁻¹ based on the x-value in between 0.0 to 2.0 [58].

As showed in Fig. 43, characteristic peaks corresponding to Cr_2O_3 were found; namely at 353 and 558 cm^{-1} . Furthermore, for the mixed spinel $(\text{Fe,Ni})\text{Cr}_3\text{O}_4$ the characteristic peak was found at 683 cm^{-1} . It seems that the temperature affects dramatically the kinetics of metal oxides formation (500 vs. 750). In particular, during aging, the crystallization/ formation of the spinel type oxides is becoming more developed/increased under air at the extreme conditions of temperature ($750\text{ }^\circ\text{C}$) [46,59]. The sample aged at $500\text{ }^\circ\text{C}$ shows the characteristic peaks of Fe_2O_3 at 219 cm^{-1} , 289 cm^{-1} and 408 cm^{-1} along with the $(\text{Fe,Ni})\text{Cr}_3\text{O}_4$ spinel but not the Cr_2O_3 peaks. There is presence of $(\text{Fe,Cr})_2\text{O}_3$ corundum peak in 512 cm^{-1} to 538 cm^{-1} for both 100 hr aged sample in He and air at $750\text{ }^\circ\text{C}$. The formation of spinel is more dominant and under He at the extreme temperature of $750\text{ }^\circ\text{C}$ it is more pronounced. This is expected as a spinel solid solution requires more time to be formed. The spinel disordering is obviously based on the asymmetry of the peaks (e.g., band at 683 cm^{-1}). A possible reason for this disordering can be the presence of oxygen vacant sites as the metal oxides are mixed towards the formation of the spinel structure, as well as the short duration of the experiment, compared to the time scale of formation of the spinel structure. Fig. 43b presents the Raman spectra obtained under He and air inside and outside the wear track. In the presence of He, at $750\text{ }^\circ\text{C}$ some of the oxides have been ‘spent’ during the sliding (e.g., the double peak in the region $1000\text{-}1600\text{ cm}^{-1}$). These peaks correspond to some type of carbonization that took place in the presence of impurities in He gas. In the presence of air, under sliding conditions new oxide phases are formed as indicated by the emerged peaks at $<500\text{ cm}^{-1}$ and $1250\text{-}1500\text{ cm}^{-1}$, which is identical to the Raman peaks of Fe_2O_3 (at 222 cm^{-1} , 289 cm^{-1} , 414 cm^{-1} and 1333 cm^{-1}).

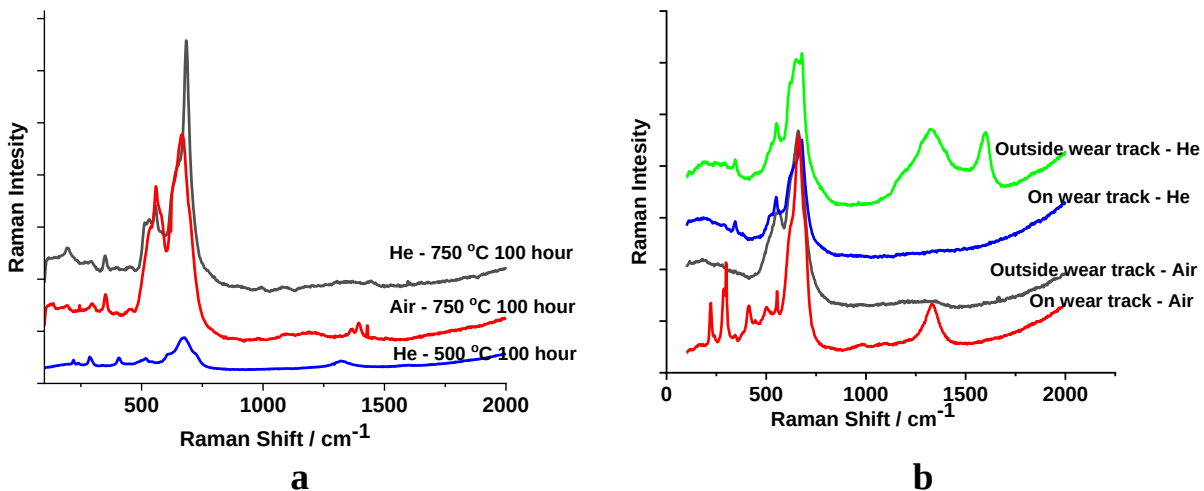


Fig. 43. Raman spectroscopy data on (a) 100 hour aged samples at $750\text{ }^\circ\text{C}$, (b) tribo-tested samples at $750\text{ }^\circ\text{C}$ under 5 N normal load.

6.4. TOF-SIMS DEPTH PROFILING

Fig. 44 presents the TOF-SIMS depth profiles that were acquired over the 800HT specimen, following tribotesting at 750 °C in He (a and b) and air (c and d) environments on both outside and inside the wear tracks. The profile depths in (a) and (b) show that under He, outside the wear track the surface has a very thin layer of Fe-rich oxide with a peak of Mn. Afterward, Cr peaks immediately indicating Cr₂O₃ rich zone (simultaneous high O and Cr concentrations), which are in agreement with the XRD, and Raman studies. At intermediate depths, Fe/Mn and FeO depletion can be noticed, whereas NiO start revealing. This phenomenon is linked with a temperature-driven diffusion. At the inner layer, before the bulk, a combined peak of Ni-Fe with a decreasing layer of Cr indicating a mixed oxide layer.

Inside the wear track (Fig. 44b) the FeO/Mn depletion is more intense. It is interesting to notice that the Fe/Ni/Cr depletion follows fast kinetics as we move to greater depths inside the wear track (Fig. 44b). This is not the case inside the wear track under air (Fig. 44d). It is believed that the rubbing process during the sliding in air caused accumulation of oxide debris on the wear track, which did not happen in He condition. That is why the depth profile up to 600 nm could not reach the bulk of the alloy. The formation of this accumulated oxide is the reason for lower COF in HT air condition.

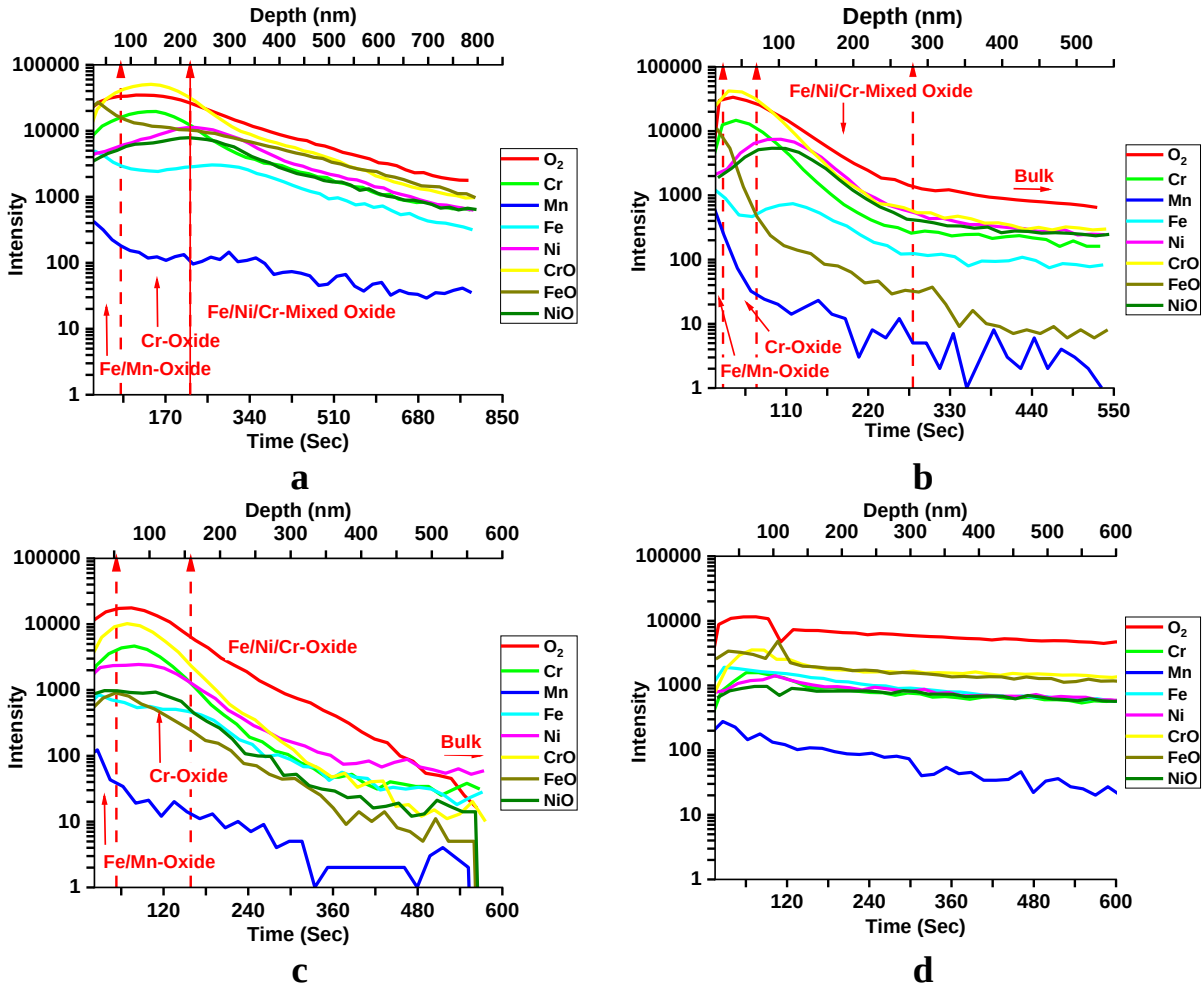


Fig. 44. SIMS elemental depth profiles of tribotested samples at 750 °C (a) He outside wear track, (b) He inside wear track; (c) Air outside wear track, (d) Air inside wear track.

Different metal oxides were formed as a result of the oxidation of the constituent elements in the alloy under investigation. The weight-gain due to the oxidation proceeded at different rates due to the different atmospheres (i.e., He vs. air), with air being moisture and oxygen-rich environment. Based on the XRD and Raman studies the oxide phases were identified, such as Cr_2O_3 , $(\text{Fe,Ni})\text{Cr}_3\text{O}_4$ and $(\text{Fe,Cr})_2\text{O}_3$. Raman showed stronger corundum signals with the dominant spinel peaks in air-aged sample, which is again more clarified from the Raman spectra on the wear track showing multiple strong corundum peaks on the surface of wear track in air. This is in line with the known fact that higher oxygen content favors formation of Fe_2O_3 and oxygen deficiency favors that of Fe_3O_4 [25]. Similar multilayered oxide structure was described in the literature for 800HT in a separate study for oxidation in dry and wet (5% water) oxygen at 850 °C for 50 hours [60]. In that study, the outer layer shows the presence of Cr_2O_3 and Fe_3O_4 whereas, the inner layer had

Cr₂O₃ and Cr-rich (Fe,Cr)₃O₄ in dry oxygen. On the other hand in wet oxygen, the top layer showed presence of Cr-rich (Fe,Cr)₃O₄ and the inner layer had Cr-rich (Fe,Cr)₂O₃, which is in line with our findings in this work.

The thickness of the formed oxide layers is different in He vs. air atmosphere as it can be seen by comparing the TOF-SIMS results (Fig. 44a and 44c). Also, TOF-SIMS studies proved that the oxide layers are continuously consumed under He sliding conditions, whereas they are replenished in the case of air atmosphere (Fig. 44b and 44d). Some first evidence about this finding was discussed earlier in the Raman studies by comparing the spectra inside and outside the wear track. Also, from the TOF-SIMS, the formation of some internal oxides is observed (depth >100 nm). The formation of these oxides is facilitated by the voids of the thin surface oxides, the latter being incapable to protect the structure against oxidation. The TOF-SIMS profiles under air have a higher increase slope (outside the wear track) up to 150 nm depth as the changes in the oxide layers are expected to be steeper due to the much abundant oxygen and its diffusion through the layer. Following this trend and beyond 200 nm, drop of oxides can be noticed in air atmosphere, due to possible spallation or oxides evaporation, whereas in He atmosphere due to much slower kinetics of oxidation (less abundant oxygen) oxide layers keep taking place even beyond 200 nm depth.

6.5. SUMMARY

The chemical changes in alloy 800HT during HT oxidation in He compared to air atmosphere during tribocontact are decoupled through multiple analyses techniques. The oxidation study exposed the evolution of oxides on the surface at different temperature, exposure time, and atmosphere. SEM/EDS analysis showed the formation of Cr-Ti rich oxide on the grain boundary. In addition, XRD and Raman spectroscopy confirmed the presence of oxides, some of them in spinel structures, the disordering of which is dependent on the oxygen level and the presence of tribocontact. SIMS depth profiling confirmed the presence of Fe-rich thin layer of oxide on the top surface with a thicker Cr-rich oxide and a mixed spinel-based inner layer on the bulk. The wear track in air showed the presence of thicker oxide, whereas in He the oxide depleted from the wear track. TOF-SIMS profiles in air and He atmospheres exhibited a distinct difference in their slope (different layer composition as the depth is increasing) due to the oxygen abundance in air and different diffusion rates.

7 HIGH TEMPERATURE NANO-MECHANICAL PROPERTY CHARACTERIZATION

The results presented in this chapter is in process of being submitted to journal papers, as follows:

- “Elevated Temperature Mechanical Property of Inconel 617 Surface Oxide through Instrumented Nanoindentation.” In preparation, to be submitted in February 2020.
- “Challenges in high temperature nanoindentation of Ni-based superalloy-Inconel 617.” In preparation, to be submitted in March 2020.
- “Nano-tribological properties of oxide layers of Ni based superalloy by nanoscratch.” In preparation, to be submitted in April 2020.

7.1. NANO/MICRO INDENTATION

Operating at HT is vital for several types of emerging and highly efficient nuclear reactors including HTGR) and VHTR. The main coolant of HTGR/ VHTR reactors is He which contains low levels of impurities including H₂, O₂, H₂O, CH₄, CO, CO₂ and N₂ [61]. Due to the presence of these impurities, the metallic alloys can develop inevitable and unique surface oxides that are highly controlled with temperature, oxygen partial pressure, carbon activity, and alloy composition. The presence of this oxide can highly influence surface friction, wear and contact properties which in turn impacts the performance of the components. For example, the precise motion of the control rods is mission-critical for reactors' performance and safety. Control rods surface can be affected by the high-temperature contact creep and self-welding during long idle intervals resulting in unpredictable high static friction and often surface damage [62]. In general, contact, friction, wear and adhesion behavior of control rods' surfaces, as well as other tribo-pairs in HTGR/VHTR, are governed by the oxide layer properties and it is thus imperative to understand and quantify their nanomechanical responses/properties.

Instrumented nanoindentation has become a common method of measuring mechanical properties of thin films [63] and oxides [64] with the ability of measuring several material time independent [63–69] and time dependent behaviors [70–73]. Interpreting and measuring mechanical properties at HT through instrumented nanoindentation is, however, very challenging due to the temperature effect on the compliance of the system, thermal expansion of the tip, tip damage as well as complexity of the contact at HT. Hence studies at HT and especially over 500 °C are scarce with limited measured mechanical properties [70–76]. For instance, Gibson et al. used high HT to measure effect of He implantation on tungsten hardness at temperatures up to 750°C [74]. Due to the hardening effect of He, implanted tungsten retains its hardness at HTs, which was contributed to pinning effect of trapped He in small vacancies. Wang et al. measured temperature dependent mechanical properties of additively manufactured Inconel 718 up to 650°C where HT nanoindentation was used to measure hardness, Young's modulus and creep stress exponent [75]. Zhang et al. reported elastic modulus, hardness, indentation creep exponent, and thermal activation of Inconel 617 bulk at HT using instrumented nanoindentation. They observed slight decrease in elastic modulus and significant reduction in indentation hardness as temperature increases [76].

Applying high loads, Zhang's study was focused on the bulk rather the oxide layer, and more importantly, oxidation in their study, if any, formed in air for a short period of time.

Generally, constitutive equations of creep based on uniaxial tests cannot be directly used for nanoindentation parameters requiring systematic modifications. This is due to the complicated stress/strain status during indentation, contact evolution, and continuously changing stress and strain fields in indentation tests resulting in inaccurate estimation of creep properties. Theoretical modeling, numerical simulation, and experiments, when performed collectively, can resolve some of the issues and more importantly can be used to measure time dependent mechanical properties at HT by relating the strain-stress during the creep of indentation to the uniaxial test [70,73–75,77–79].

Su et al. build up a correlation between nanoindentation creep parameters and uniaxial tests using an analytical model of Bower et al. [79] and improved it to include conical indenters using iterations of finite element analysis with varying half angles of the indenter. The improved model validated by the results of amorphous selenium at room temperature (RT) [70]. Nonetheless, the verification was performed with selenium having elastic-creep behavior only at RT. The problem gets more complex when plasticity and creep are both involved. Kang et al. combined the experimental indentation data at HT and corresponding FEA to find the elastic-plastic and creep parameters of P91 steel and XN40F at 600 °C and 900 °C, respectively [72]. There are also other iterative use of FEA to measure yield strength, work hardening rate and creep parameters [80–82]. However, these measurements are only applicable for specific creep mechanisms and should be implemented with care when used for unknown material e.g., metal oxides. It also required precise measurements of the indented surface which is difficult at HTs.

The current study systematically evaluates and compares the HT mechanical properties of the bulk and the oxide built after aging of Inconel 617 through nanoindentation. Combined experimental and optimization algorithms are used to find the time independent properties, elastic modulus and yielding of the oxide layer, along with time dependent properties of creep exponent, creep coefficient and activation energy. A novel dual optimization method based on Kang et al. and FEA simulations is also introduced to accurately find the material properties [72]. These properties are important to understand and highlight the main contributors to static and kinematic COF of Inconel 617 at HT and to predict the top layer frictional behavior.

7.1.1. Sample preparation

As received samples are mechanically polished to reduce the roughness and remove initial oxides on the surface. The polished samples are then cleaned with acetone and iso-propyl alcohol in an ultrasonic cleaner and dried. To simulate the effect of the He-cooled reactor environment, the samples are then placed in a He filled furnace at 950 °C and aged for 100 hours. The samples are then cut where the nanoindentation tests are performed on the oxide from the cross section of the aged samples (called Aged Inconel 617 and symbolized as AIN, hereinafter). Nanoindentation on the cross section is highly beneficial compared to the surface, mainly, due to the high roughness of the surface oxide surface after aging, and also it prevents the ambiguity of having bulk substrate effect on the extracted property. For the cross-sectional sample preparation, a layer of Ni coating is deposited using the electrodeposition technique on the samples' surface to protect the oxide layer from delaminating during grinding (Fig. 45). A small section is cut and polished from the AIN gradually to get a mirror polished surface with approximate roughness (R_q) of 40 nm. Cross-section SEM image in Fig. 45b shows the oxide layer formed on bulk IN617. The oxide thickness of AIN after 100 hr of aging in He is around 6 to 10 μm , and attests to the fact that the contact mechanics of aged IN617 depends mainly on the oxide properties.

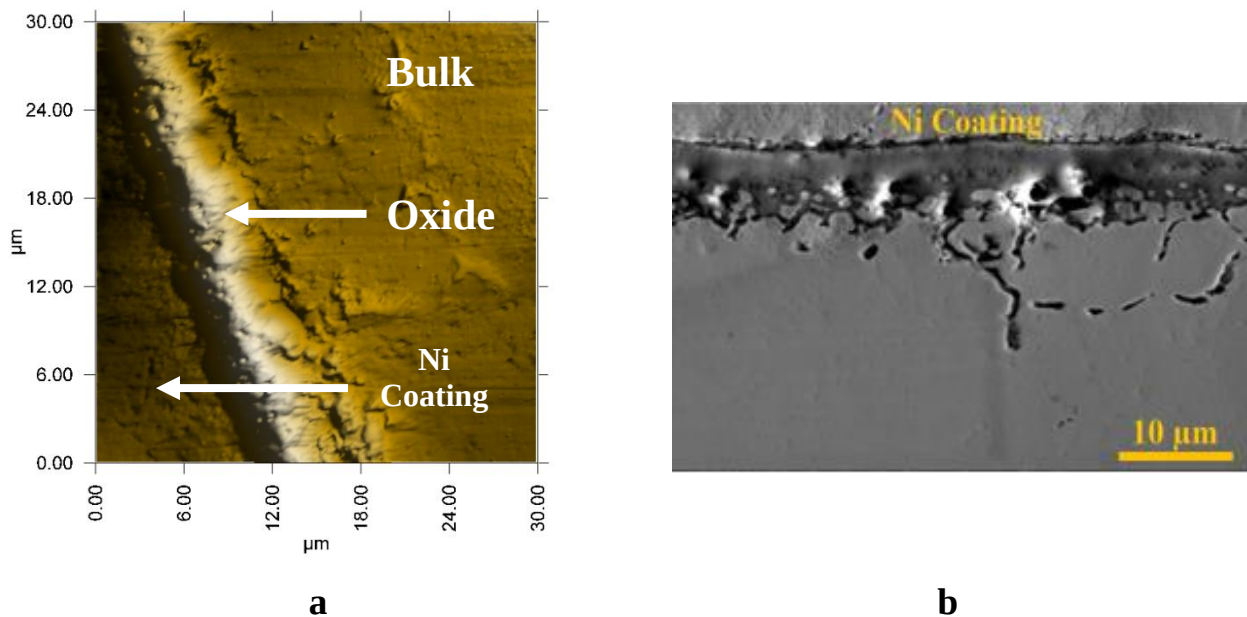


Fig. 45(a) SPM image, and (b) SEM image of aged Inconel 617 at cross section.

7.1.2. Instrumented Nanoindentation

Nanoindentation experiments were conducted using a commercial nanoindenter (Triboindenter TI Premier, Bruker) shown in Fig. 46. Indentation tests are performed at RT, 200 °C, 400 °C and 600 °C, on the oxide cross-section of AlN samples. Fig. 46 shows the indenter with the HT chamber, which is heated by two sets of heating elements on the top and bottom of the sample holder. A constant flow of 95% Argon and 5% Hydrogen is introduced through the hot chamber as cover gas, which acts as the convective heat transfer medium to achieve thermal equilibrium. The cover gas also protects the tip from oxidative damage and further oxidation to the sample.

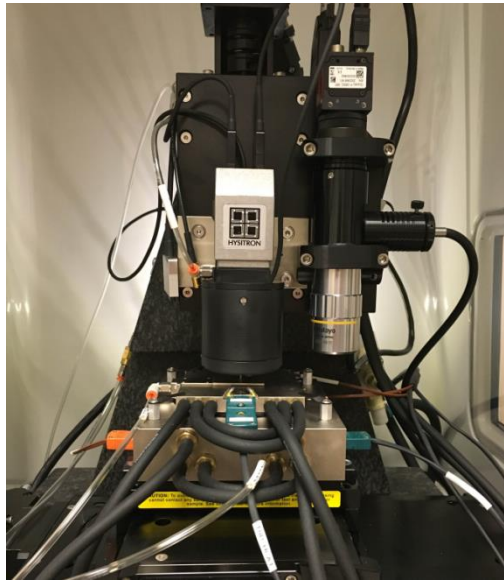


Fig. 46 Bruker-Hysitron TI Premier nanoindenter with high temperature stage.

In the current work, a Berkovich type indenter probe made of diamond is used for nanoindentation tests up to 400 °C and a Berkovich cBN (Cubic Boron Nitride) probe is used for 600 °C tests. The load is ramped from zero to the peak load at 0.5 mN/s rate before it is held at peak load for 100s (for indentation creep measurements) and then it is unloaded at 1.0 mN/s rate. A maximum load of 6 mN is used for experiments up to 400 °C, and 500 μ N is used for 600 °C due to softening of the oxidized sample. The load and holding time are selected after evaluating nanoindentation test results for different holding stages, maximum loads and load patterns. Indentations are repeated 5 times at each temperature.

7.1.3. High temperature parameter modifications

To obtain an accurate result for elastic modulus and hardness at high temperatures, the effect of machine compliance, thermal drift and samples creep should be eliminated from the raw results. Compliance of the machine is calculated by integrated software at the beginning of each test through calibrating in air and standard Fused Quartz sample. During unloading the load is held for 120s at 10% of its peak for 120s to calculate thermal drift correction from the fraction of displacement [83–85]. It should be mentioned that for high temperature indentations, the sample and the probe are held at high temperature for half an hour to achieve thermal stability.

Creep influence on hardness depends on the loading pattern used to measure the creep properties. The common technique, also used in this research, is constant load and hold (CLH) which is loading to a maximum load and maintaining the load for a specific time. Phani et al. shows this method of loading limits the range of depth during creep which reduces its influence on hardness and at the same time can cover a wide range of creep strain rates. In fact, it is shown that the creep displacement during holding time in CLH is closer to real uniaxial creep tests in comparison to other loading patterns [85].

Hardness is measured using the maximum load as well as the associated projected area of the contact and is given by:

$$H = \frac{P_{max}}{A} \quad (7.1)$$

where P_{max} is the maximum indentation load and A is an area function at the contact depth, h_c . The area function can be estimated by the following function:

$$A(h_c) = C_0 h_c^2 + C_1 h_c + C_2 h_c^{1/2} + C_3 h_c^{1/4} + C_4 h_c^{1/8} + C_5 h_c^{1/16} \quad (7.2)$$

where C_0 represents a constant, which is a function of tip geometry and for a perfect Berkovich tip equals to 24.5 and coefficients C_1 - C_5 account for the geometrical imperfection and are calculated based on known properties of fused quartz standard sample. Contact depth h_c , can be defined as [65]:

$$h_c = h_{max} - \varepsilon \frac{P_{max}}{S_u} \quad (7.3)$$

where h_{max} is the maximum depth at the end of loading step, ε denotes the geometry correction factor which is 0.75 for Berkovich tip and S_u is the contact stiffness at the onset of unloading.

Following Oliver-Pharr method, the reduced elastic modulus E_r can be calculated through measurement of contact stiffness, S_u , and projected contact area [86]:

$$E_r = \frac{\sqrt{\pi} S_u}{2\sqrt{A}} \quad (7.4)$$

Using reduced elastic modulus from Eq. 4, and known mechanical properties of the diamond tip (E_i, ν_i), elastic modulus of oxide at the cross section of the samples can be calculated based on:

$$\frac{1}{E_r} = \left(\frac{1 - \nu_i^2}{E_i} + \frac{1 - \nu_s^2}{E_s} \right) \quad (7.5)$$

where E_s and ν_s are elastic modulus and Poisson' ratio of oxide, respectively.

The creep influence on elastic modulus can be eliminated following Feng et al. method [87]. Feng et al. suggested a correction for Oliver-Pharr method (Eq. 4) to exclude the effect of creep on elastic modulus [87] by introducing a modified stiffness parameter, S_m , given by:

$$\frac{1}{S_m} = \frac{1}{S_u} + \frac{\dot{h}_h^c}{|\dot{P}|} \quad (7.6)$$

where $\dot{h}_h^c$ represents indenter's creep rate at the end of the load hold stage, and $\dot{P}$ is the unloading rate at the beginning of the unloading stage. Following Feng et al.'s suggestion, in the current study, the unloading stiffness, S_u , is replaced by S_m in Eq. 3 and 4 to mitigate the effect of creep at higher temperatures.

Implementing these corrections to calculate the true mechanical properties at HT is essential, however, they can only be used when specific criteria is satisfied. [70,87]. Accordingly, Feng et al. introduced a creep factor, C , and a threshold for unloading rate, $\dot{P}$, in which Eq. 6 is valid and can be used to eliminate the creep influence on elastic modulus [87]. The factor defined as:

$$C = \frac{\dot{h}_h^c}{|\dot{P}|} < 0.1 \quad (7.7)$$

Here, for measuring the Young's modulus and hardness of IN617, unloading rate of indenter is kept constant at 1 mN/s . Considering indenter displacement rate at the end of load holding stage

for each tests and temperatures, the maximum creep factor calculated as $C = 0.027 < 0.1$. This condition shows that Eq. 6 can be used to calculate Young's modulus and the proposed holding time is sufficient even at elevated temperatures to effectively reduce the creep influence [87]. Su et al. also defined a threshold for minimum creep displacement (or similarly time during holding stage), below which the elastic modulus can significantly influence steady state creep strain rate and named it elastic transient. Elastic transient related to strain propagation through unyielded material below the indenter postponing the steady state section of creep. This is important since creep rates measured at this stage (Fig. 46, holding stage) and should be surpassed to reduce its effect on creep parameters. Su et al. suggested a minimum indentation depth beyond which the results are not affected by the elastic transient and it is given by [70]:

$$h_{\min} = 10 \sqrt{\frac{\pi P_{\max}}{2E_r \tan \theta}} \quad (7.8)$$

where θ is half angle of the indenter (70.3° for Berkovich) [70]. The calculated elastic transient for the current indentation tests is between 15 to 20 nm based on the maximum load and reduced elastic modulus for all the tested temperatures. Here, the measured creep displacements are beyond the elastic transient and hence minimal influence of elastic transient on creep displacement is expected.

Indentation load-displacement curve for the oxide on AlN cross-section is presented in Fig. 47a at different temperatures where creep displacement is taken out from the holding period at maximum load (Fig. 47b). Thermal drift graphs of nanoindentation test are depicted at 400 °C and 600 °C as it is insignificant in other temperatures. At this temperatures, the thermal drift rate is 0.11-0.24 nm/s which is relatively low and similar to what is reported in Ref. [88] for fused silica.

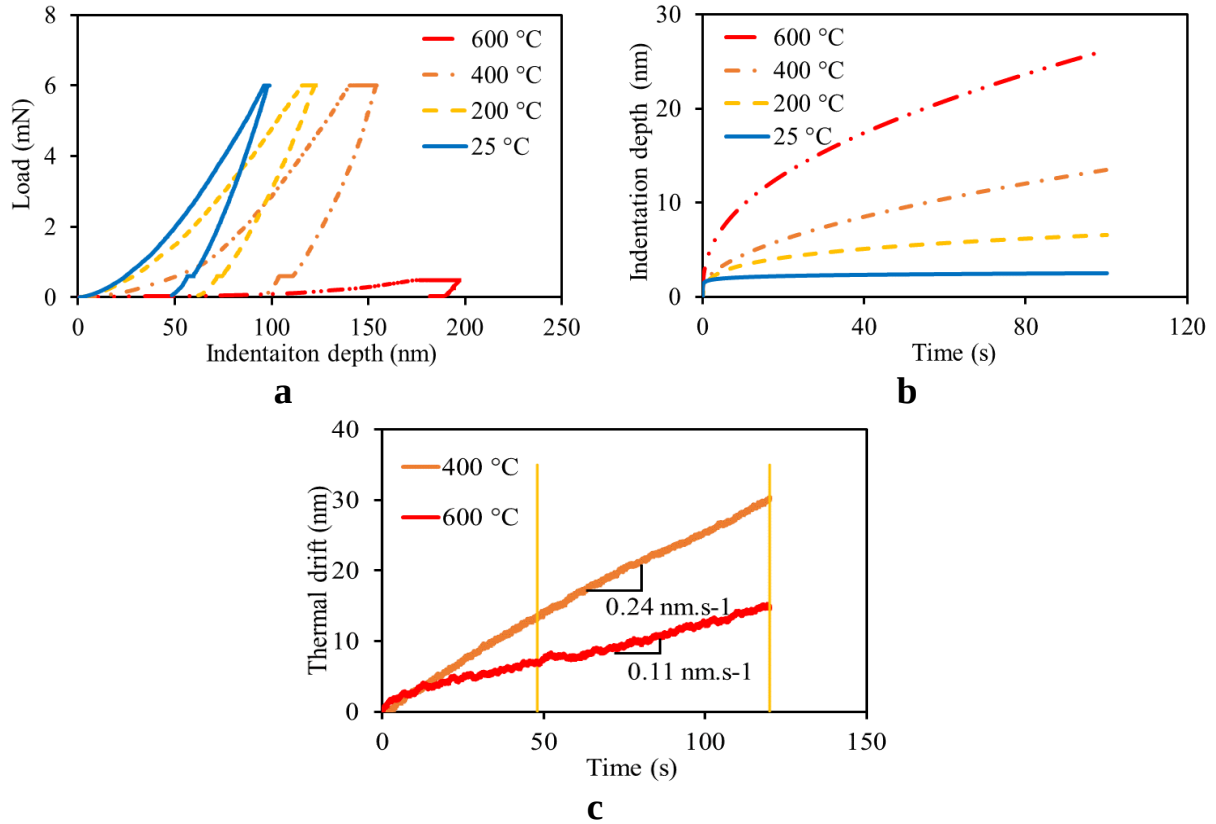


Fig. 47 Average results of 5 indentations for (a) load displacement and (b) creep displacement at the holding time and maximum load of 6 mN for RT to 400 °C and 500 μ N for 600 °C, and (c) thermal drift of oxide on AlN at RT - 600°C. It is noted that at higher temperature of 600 ° the thermal drift is lower compared to 400 °C. It can be attributed to cBN material having lower thermal conductivity, $\sim 700 \text{ W/m}^\circ\text{K}$, compare to Diamond, $2000 \text{ W/m}^\circ\text{K}$ [89]

7.1.4. Numerical Modeling

Finite element model

A FE analysis, simulating the indentation process associated with an regression method, based on iteration of the FE simulations, is developed to determine the mechanical properties of IN617 using load-displacement results of nanoindentation tests. The FE model consists of an indenter with similar materials and dimensions to the original indenters [88] and a deformable sample modeled as an axisymmetric body (Fig. 48a). It is worth mentioning that the maximum load is sufficiently high to indent the material with its pyramidal sides, so the indentation can be modeled with axisymmetric geometry. The rigid indenter is modeled as a conical indenter with a half-included angle of 70.3 equivalent to the Berkovich tip used for the nanoindentation experiments. The deformable sample is modeled using 16940, CAX4R, elements with very fine elements near the contact (Fig. 48b) to be able to capture stress/strain field with high resolution. An incremental load

is applied on the rigid body in three steps: loading, holding and unloading similar to the experimental steps.

To model the creep behavior of AIN at elevated temperatures a power-law creep with strain hardening is selected in ABAQUS™ [72,90,91]. The strain hardening considered here is defined by a power-law hardening beyond the elastic region expressed as:

$$\sigma_p = \sigma_y \left(1 + \frac{E_s \times \varepsilon_p}{\sigma_y} \right)^{n_1} \quad (7.9)$$

where σ_p is the plastic stress, n_1 represents the strain hardening exponent, and σ_y and ε_p denote the yield strength and plastic strain, respectively. The time-independent properties, yield strength and strain hardening exponent (Eq. 9) and time-dependent properties, creep coefficient and creep exponent are selected and modified based on the optimization algorithm described in the next section.

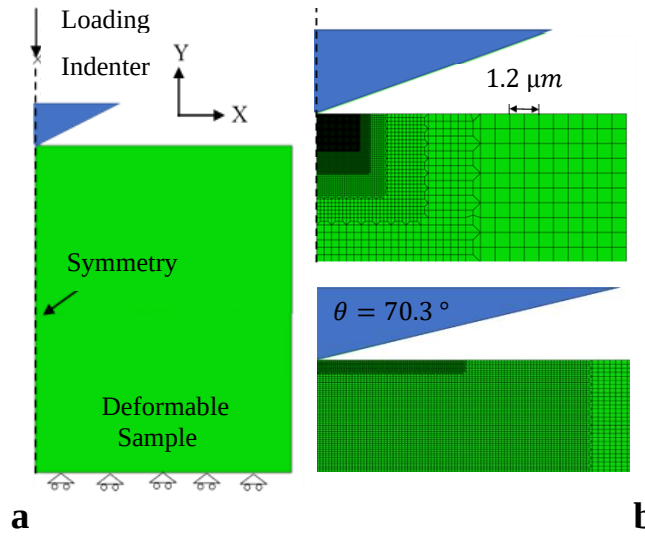


Fig. 48 Schematic representation of (a) indenter and the test sample, with the boundary conditions used for the axisymmetric model, (b) local mesh near the contact area of the deformable body

7.1.5. Optimization Algorithm

A double non-linear optimization (DNLO) procedure is developed with MATLAB, using least-squares optimization function (LASQNONLIN) to minimize the objective function $F(x)$ defined as:

$$F(x) = \frac{1}{2} \sum_{i=1}^N [D(x)_i^{FE} - D(x)_i^{exp}]^2 \rightarrow \min \quad (7.10)$$

$$x \in R^n$$

where x is the desired material properties, and $D(x)_i^{FE}, D(x)_i^{exp}$ are displacement functions (output) of FE simulations, and experimental results, respectively, at each load increment (i). The analysis uses initial estimation of material properties for unknown (time-dependent and independent) properties (x in Eq.10) and tries to fit the FE curves to the experimental load-displacement/creep-time results by systematically changing, iterating through the properties and minimizing the objective function.

Variable x contains elastic/plastic/viscoplastic properties of the desired material including: yield strength (σ_y), work hardening (n_1), creep coefficient (A), and creep exponent (n_2) which are the output of the optimization procedure (total variables: $n = 4$). To reduce the computer cost, Poisson's ratio of the oxide is considered as 0.25 similar to what is reported for chromium oxide coating [67,92]. Using Eqs. 4-6, the elastic modulus of AIN is calculated and used together with Poisson's ratio as input variables for the numerical calculations.

The DNLO consists of two steps, first fitting FE results with the load-displacement (Fig. 49a) where the time-independent properties are dominant and then implement the converged material properties (x) of the first step into the second step and fit the results to the experimental creep displacement-time where creep properties are dominant (Fig. 49b). This dual procedure is repeated till both fitting processes converge. Fig. 49 shows the representative FE simulation fitted graphs to the experimental results of the two steps for 400 °C. It is worth mentioning that the converged results are totally independent of the initial values [31]. The FE simulation and the numerical algorithm are verified against available numerical results of Kang et al [72]. To further validate the method, a nanoindentation test is performed on IN617 at RT and extracted parameters are compared with available uniaxial data for the alloy. Table 6 presents the extracted parameters by the method in comparison with uniaxial tensile tests of IN617 available in literature [37,38].

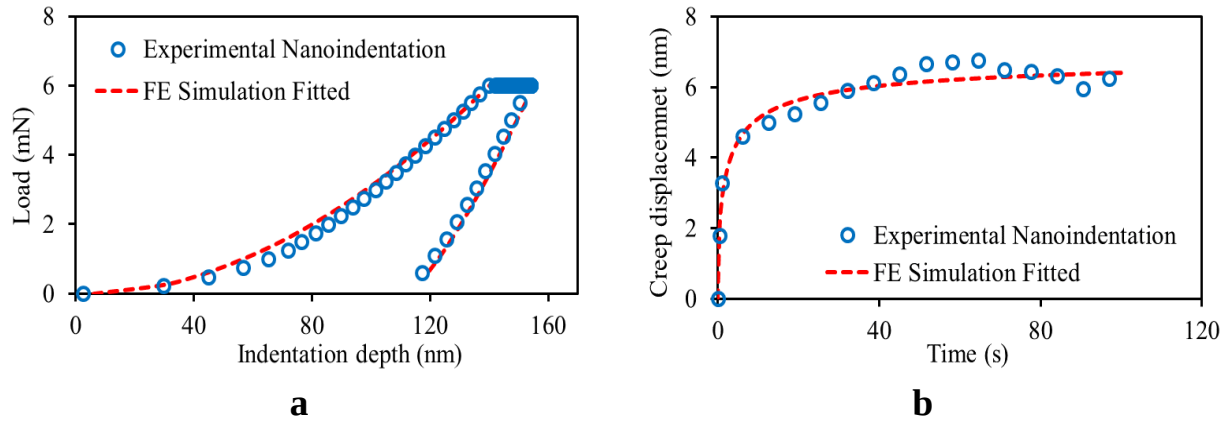


Fig. 49 FE simulation fitting graphs to the experimental results of (a) load-displacement and (b) creep displacement at the holding step.

Table 6

Validating extracted parameters using the optimization method with uniaxial results at RT[93,94]

Material properties	IN617 (FEA fitted)	Experimental Uniaxial tests	Error (%)
Young's modulus (GPa)	227	211	7.05
Yield strength (MPa)	305	322	5.57

7.1.6. Results and discussion

Fig. 50 shows the indentation hardness and elastic modulus (after considering and excluding creep influence on the stiffness) for bulk virgin IN617 at 25 °C to 800 °C. Nanoindentation results are compared with the recently published macro indentation results from Zhang et al. on the IN617, where the indentation depths were very high around 2 to 3 μm using high loads of 200 mN to 400 mN. The nanoindentation results are higher (27-51%) than the published data which may resulted from indentation size effect and also surface treatment effect as the samples used in this research were not electropolished to remove the polishing effect on the surface.

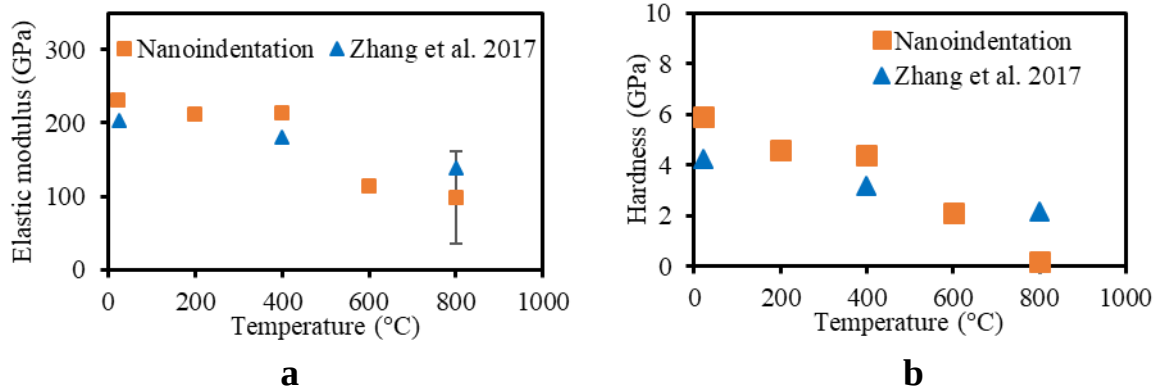


Fig. 50 Results of nanoindentation for (a) hardness (b) elastic modulus calculated from Eqn. 6 in comparison with Zhang et al. 2007 results of IN617 at different temperatures

Fig. 51 shows hardness of the cross section of IN617 at different distances from the surface. There is a sudden drop through the top oxide layer to the bulk of the material. It is interesting that the hardness of the cross section is close to the hardness of the bulk of chromium oxide. The size effects as well as the preparation process which compact the oxides at the cross section may result in higher hardness values similar to chromium oxide packed coat [67].

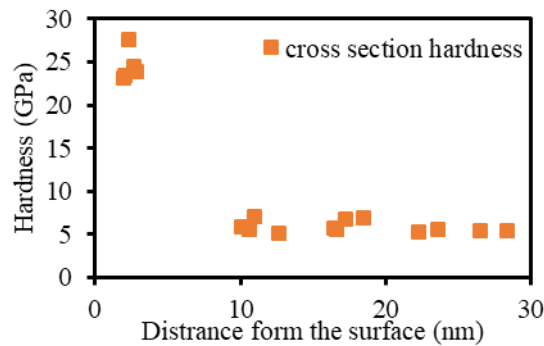


Fig. 51 Hardness of the cross section of IN617 at different distances from the surface

Fig. 52 shows Young's modulus and hardness (excluding creep influence) for oxide layer at 25 °C and up to 600 °C along with those obtained by Zhang et al for bulk IN617. They used high loads of 200 mN to 400 mN on the surface after heating the sample in air for 8 hours, which indented the surface down to the depth of 3 μm including around 400 nm of oxide [76]. Therefore, the results are represented as the properties of the bulk of IN617 (BIN) at 25 °C and 400 °C as tested by Zhang et al. [76]. Young's modulus of the oxide layer is 1.4 times of BIN [76] at RT to 400 °C

and closer to Young's modulus of similar metal oxides (Table. 7). However, hardness is 8 times of BIN at RT which decrease significantly to 3 times of hardness of BIN at 400 °C. This may due to softening at elevated temperatures and/or diffusion of other metal ions into the surface. Hardness and Young's modulus of BIN were only measured for RT, 400 °C and 800 °C in [76]. Table 7 compares the Young's modulus, hardness and yield strength of manufactured metal oxides which build up the oxide on AlN. It shows that despite having different morphologies and scales, nanoindentation results are comparable with similar metal oxides. Based on the EDS results in chapter 6, the oxide mostly consist of Cr_2O_3 validating the high yield strength and elastic modulus of the AlN.

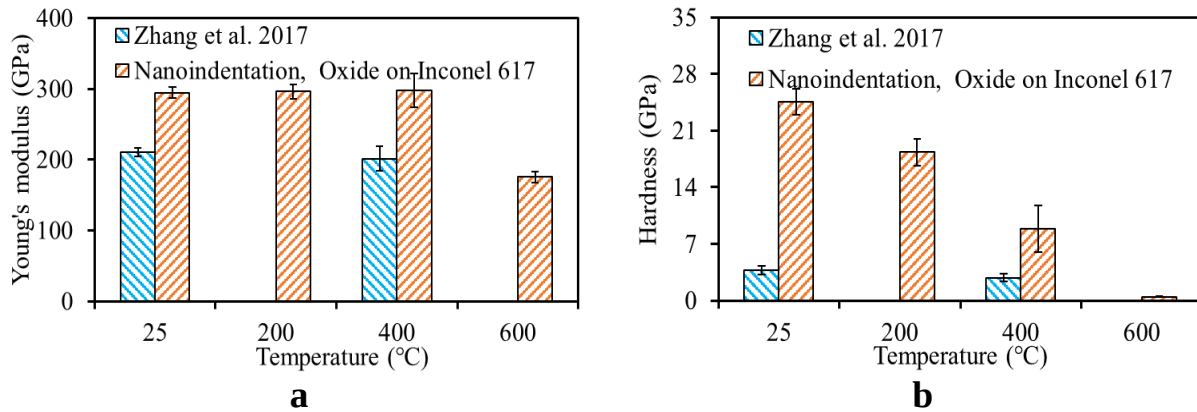


Fig. 52 Results of nanoindentation for (a) elastic modulus (b) hardness calculated from Eq. 6 in comparison with Zhang et al. 2017 results of BIN at different temperatures

Table 7

Comparing mechanical properties of main oxides exist in oxide of AlN

Oxide	E (GPa)	σ_y (GPa)	Hardness (GPa)	Description	Reference
Al_2O_3	344-408	15.4	19.6-25.5	Single crystal	[95,96]
Cr_2O_3	260-370	10-14.5	20-30	Coatings	[67,92]

Fig. 53 shows hardness of AlN from the cross section at different distances from the surface at RT. There is a sudden drop when indentation pass the top oxide layer to the bulk of the material. It is interesting that the hardness of the top of the cross section is close to the hardness of chromium oxide coatings measured by nanoindentation reported in [92] at RT.

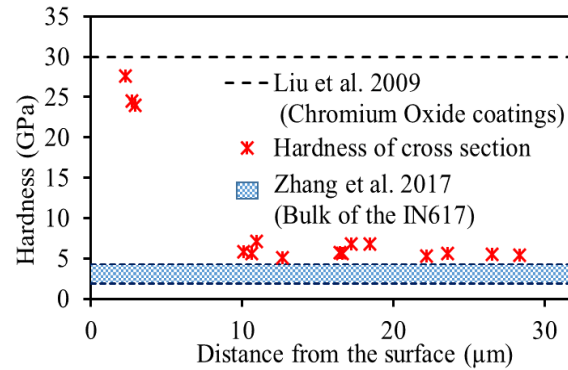


Fig. 53 Hardness of the cross section of IN617 at different distances from the surface

Fig. 54 shows the results of the yield strength of the oxide at RT extracted with the optimization algorithm in comparison with yield strength of the bulk of IN617 measured with uniaxial test and the known yield strength of oxides from Table 7 based on [67,92–98]. The yield strength of oxide is in the same order of constitutive oxide's yield strength. As the temperature increase the yield strength of the oxide decrease similar to semi-linear decrease of strain hardening showing more slip systems are activated and the effect of work hardening decreased (Fig. 55a&b). Based on the results of Young's modulus (Fig. 52) and yield strength, plastic deformation rate is changing, showing activation of more dislocations from 400 °C to 600 °C. Hardness to yield strength ratio of the oxide is plotted in Fig. 55a which shows an increase as the temperature increase. This shows that dependence of yield strength to temperature's change is more than hardness which may due to hydrostatic stresses under the indenter. This behavior also reported for alumina till 700 °C in [99]

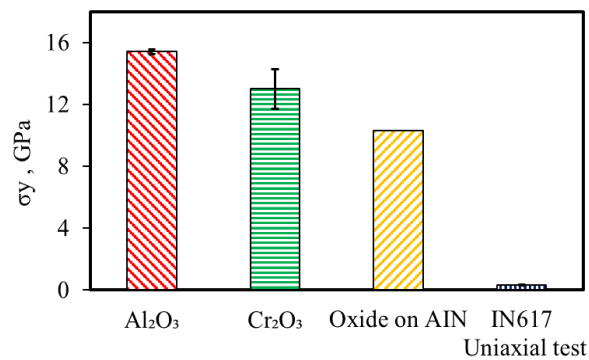


Fig. 54 Yield strength of oxides Al₂O₃, Cr₂O₃ in comparison to extracted yield strength of oxide and IN617 measured by uniaxial test [93,94]

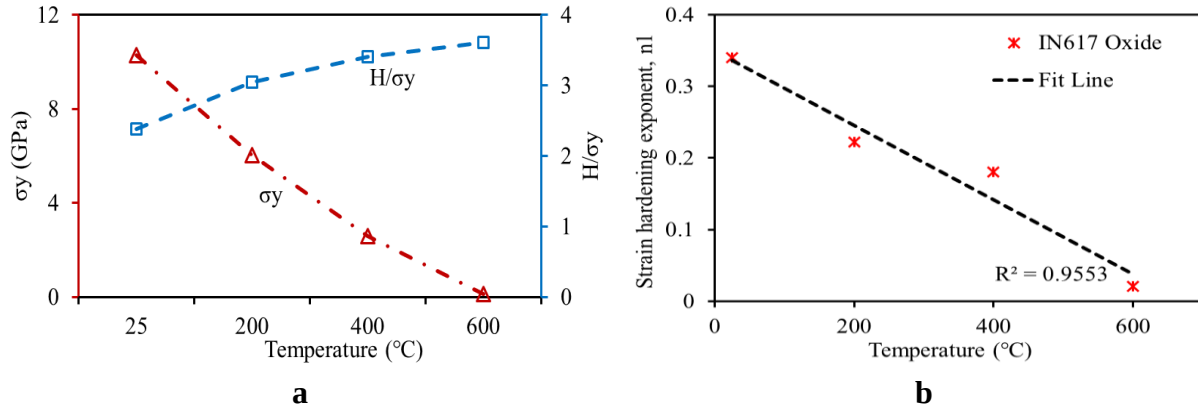


Fig. 55 (a) Evolution of yield strength and hardness to yield strength ratio and (b) strain hardening exponent for oxide of aged IN617 from 25 °C to 600 °C

Fig. 56 presents a comparison of creep stress exponent of BIN from reference [76] and oxide at the cross section of AIN from current study. The stress exponent above 5 generally shows that the main mechanism of creep for BIN is dislocation climb [76], however, for the oxide layer, the lower creep exponent, $n \approx 2$, showing that creep deformation is dominated by diffusion through the grains [100,101]. Diffusional creep is reported to be the main creep mechanism of Al_2O_3 and Cr_2O_3 [78], though, diffusion through the grain is dominant for lower stresses and temperatures $T < 0.5 T_m$ [78]. It is believed that due to complex stress/strain below the indenter and elastic transient during creep, the shear stress drops and creep is dominant by diffusion through boundary (Fig. 57). Surface heat treating in order to have coarser grains can increase the creep resistance of the surface since creep rate varies with inverse of square of grain size [100]. This can be further studied with surface heat treatment and modifying the grain size of the oxide.

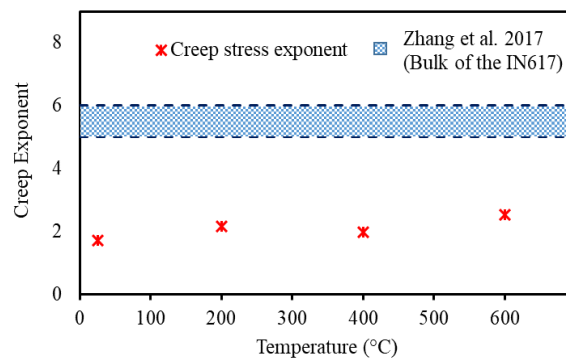


Fig. 56 Comparison of creep stress exponent of oxide on AIN with Zhang's study [76]

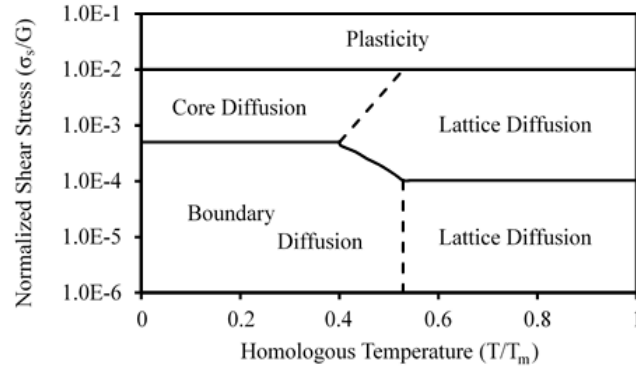


Fig. 57 Deformation mechanism map of creep based on normalized shear stress, σ_s/G , with shear modulus versus homogenous temperature, T/T_m ($T_m=2435$ °C for Cr_2O_3) [78]

Another important parameter in creep deformation is activation energy, Q . An Arrhenius equation for creep strain rate during steady state creep of oxide is presented by:

$$\dot{\epsilon} = \dot{A} \exp(-Q/kT) \sigma^n \quad (7.11)$$

where $\dot{\epsilon}$ symbolizes the steady state creep rate, $\dot{A}$ is a material constant, σ represents the creep stress, n is the stress creep exponent, Q denotes the activation energy, k is the universal gas constant, and T is thermodynamic temperature in the unit of kelvin. Activation energy can be calculated by gradient of logarithm of creep strain vs $1/T$ based on Eq. 11. Results (Fig. 58) show slope remain mostly constant over the tested temperature providing that the creep mechanism is not changing and for oxide on the AIN is $\sim 23 \text{ kJ/mole}$. This activation energy is much lower than 291 kJ/mole reported by [76] for IN617, however, it is close to the boundary creep mechanism in which less energy is needed to move through the boundaries [100,102]. Also, similar activation energy (29 kJ/mole) calculated from creep coefficient, A . At high temperatures, creep rate is controlled by the slowest species in solids which in the case of metal oxides is controlled by the oxygen activity [103].

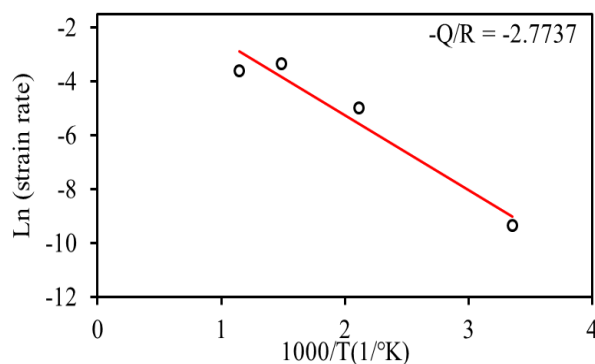


Fig. 58 Depiction of how activation energy calculated from the gradient

7.1.7. Challenges

Elevated temperature nanoindentation on a complex multi element alloy like Inconel 617 presents with the challenge of tip material and alloy reactivity along with the most common and well-known challenges of instrumented nanoindentation: thermal drift and indenter damage due to oxidation. Diamond is the obvious choice for tip material with the highest hardness, but it loses its effectiveness at higher temperature above 400°C due to graphitization. It is popular indentation and scratch probe material up to 400 °C, although oxidation can be avoided in high vacuum technique even for higher temperature. The next choice is cBN for its high hardness, and it requires 700 °C to oxidize and create a B_2O_3 layer. On the other hand, sapphire is popular as it is inert at high temperature. Both this material has been successfully used at high temperature for indentation in several cases.

The diamond tip is successfully used on Inconel 617 up to 400 °C without any major damage to the tip. When the tips were used above 400 °C, the exhibited severe damage although the indentation were performed in Argon gas environment. As shown in Fig. 59a, the first diamond tip was corroded and broken off during indentation at 800 °C. The second tip in Fig. 59b shows a chunk of material adhered on the tip. The first tip in Fig. 59a was used at 800 °C and then it was used to indent on standard FQ to check the status as per the HT indentation protocol explained earlier. But for the second tip, it was imaged under SEM before indenting on FQ. It is assumed that the similar material adhesion might have occurred on the first tip after indentation at 800 °C and afterward during the indentation on FQ at room temperature the portion of the tip might broke off that had adhered material.

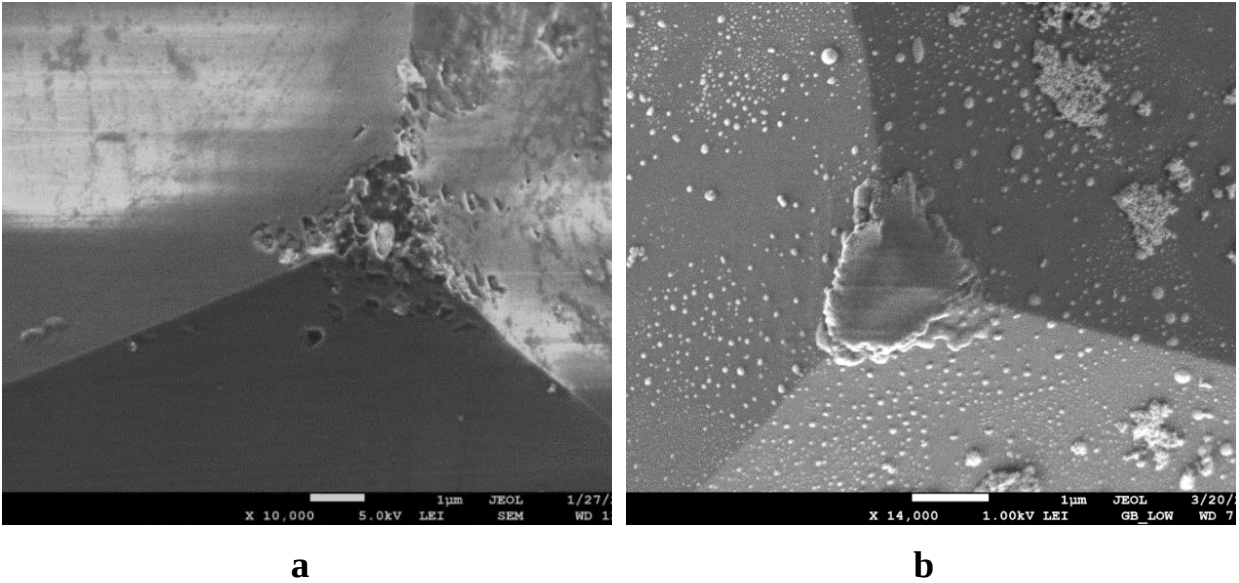


Fig. 59 SEM images of damaged diamond Berkovich probes after indenting on Inconel 617 at 800 °C.

The cBN tip was then used to perform the indentations at HT. Although the indentations at 600 °C were successfully executed with very little damage to the tip, it produced similar result at 800 °C as diamond. Fig. 60a shows the cBN tip after 600 °C indents, where the tip is mostly clear of material. But after 800C indents, in the SEM images the tip is found to be covered with the transfer material. The sapphire probe is used on Inconel 617 at 800 °C resulted in similar outcome. Fig. 61a and 61b shows the SEM images of the tip before and after performing the HT indentations on Inconel 617.

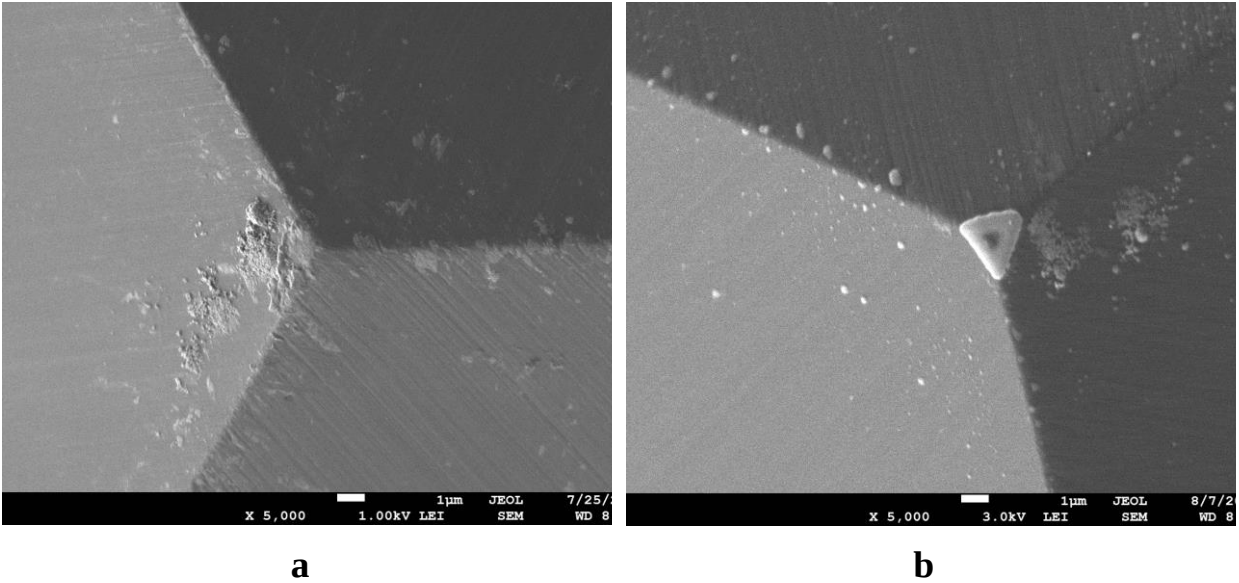


Fig. 60 SEM images of cBN Berkovich probes after indenting on Inconel 617 at (a)600 °C; (b) 800 °C.

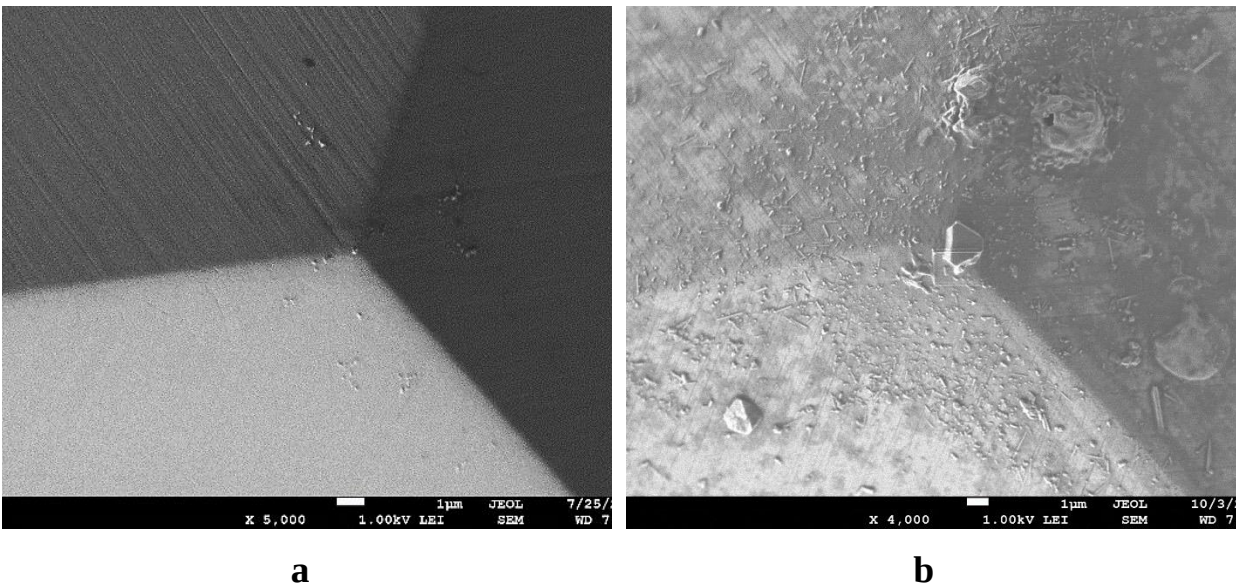


Fig. 61 SEM images of sapphire Berkovich probe (a)before; (b)after indentation on Inconel 617 at 800 °C.

The combination of these experiments suggests, although the tip material is protected from oxidation, the indenter-sample interaction/reactivity poses the highest challenge. Carbon is known to be dissolved in elements like Cr, Ni, Mn, Co, Fe and other early transition metals at high temperature. cBN and sapphire is also prone to be dissolved or reduced to oxides, borides or

nitrides in presence of the Cr or Ni at HT. This reactivity does not only depend on the environment but also the increased diffusion at HT. This highly reactive interaction at HT caused the adherence of material on the tips. This type of material transfer during indentation has been reported before even at room temperature while in-situ TEM indentation of copper by sharp tungsten tip[104]. The adhesion property between the tip and sample is responsible for the material transfer[105].

7.1.8. Nanoindentation summary

In this study experimental nanoindentation tests are performed to investigate the mechanical response of top layer oxide of Inconel 617 which is one of the main candidates for components such as heat exchanger, control rods and valves in HTGR/VHTR. Elevated temperature nanoindentation is performed on the cross section of oxide after aging Inconel 617 for 100hrs at 950 °C environment filled with He. The results are further investigated with an optimization algorithm to fit the FEA data and extract the time independent and dependent constants. Oxide exhibits different mechanical properties than the bulk of Inconel 617 at RT to 600 °C. The following conclusive remarks can also be made:

- (1) Young's modulus of the oxides is 1.3-1.6 times of IN617 and closer to metal oxides. Hardness of the oxide layer at the top most layer of IN617 is much higher than that of the bulk of Inconel 617. This is due to formation of several hard oxide layers on top of Inconel 617 during aged process.
- (2) The yield strength through of the oxide of aged Inconel is 10 GPa at RT and reduced to 120 MPa at 600 °C. The high yield strength at RT is close to other metal oxides at RT.
- (3) Activation energy of oxide is much lower than the bulk of Inconel as less energy is needed for ion/voids to move through the boundaries.
- (4) Creep deformation at high temperature is dependent on diffusion through the grain rather than dislocation climb dominant for the bulk of Inconel 617 and depend on oxygen diffusivity in the oxide.
- (5) Based on the extracted properties, mechanical properties of the bulk cannot be used to measure the tribological response of the surface which oxidized during holding stages.

The success of instrumented high temperature indentation on complex alloy like Inconel 617 is limited by the tip material available at this moment. Other tip material like, SiC and WC can be

explored, but dissolution of SiC in presence of metals (Fe, Ni, Mn, Co) and loosing carbon through diffusion is well known. So, it is imperative to explore for a suitable tip material to produce successful, reliable and reproducible HT instrumented nanoindentation data.

7.2. NANO/MICRO-SCRATCH TESTS

Nanoscratch experiments are conducted using the same commercial nanoindenter for nanoindentation test. A conospherical shaped diamond probe with radius 870 nm was used to conduct the nanoscratch tests at room temperature while for all high temperature nanoscratch test, a conospherical shaped diamond probe with radius 5 μm was used. The system has the capability of supplying gas in the chamber to create the required inert environment. All the high temperature nanoscratch tests were performed under the cover of 95% Argon and 5% Hydrogen gas mixture to protect the diamond tip at high temperatures. For nanoscratch testing, the virgin alloy samples were prepared to have roughness values of 0.03 μm to 0.04 μm achieved through mechanical polishing. The samples were then cleaned using acetone in an ultrasonic cleaner and dried before placing inside the nanoindenter. The aged samples were prepared in a vacuum furnace at high temperature (Inconel 617 at 950 $^{\circ}\text{C}$ and 800HT at 750 $^{\circ}\text{C}$) under He gas environment for 100 hours. The roughness of the samples surface was measured using both AFM and stylus profiler and found to be around 0.45 μm for Inconel 617 aged sample and 0.77 μm for 800HT aged samples (see Figs. 62a,b). Due to the observed high roughness of the samples surface, it is generally better to use higher load ranges and probes with larger radius. Using SEM imaging shown in Figs. 62c,d, the oxide layer thickness of the sample after 100hr of aging in He was found to be around 10 μm for Inconel 617 and 8 μm for 800HT.

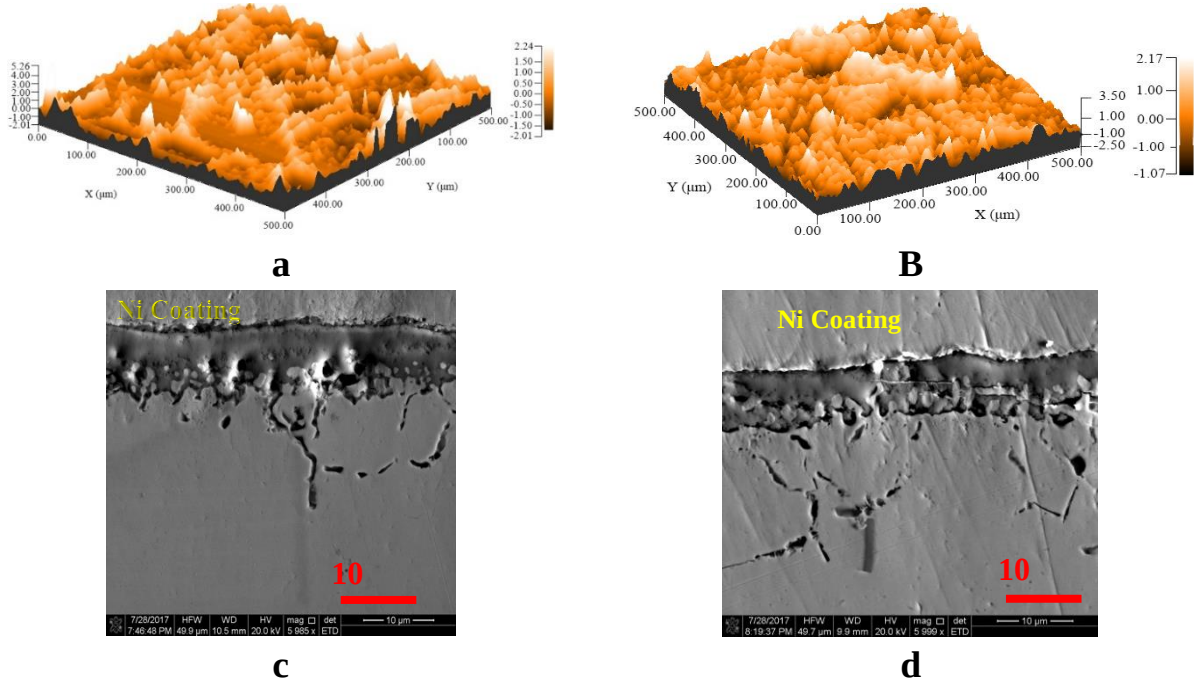


Fig. 62 3D surface topography image of (a) Aged Inconel 617 (b) Aged 800HT. All dimensions are given in micron; Cross section SEM image of (c) Aged Inconel 617 and (d) Aged 800HT.

For room temperature experiments, the tests were performed with two different sets of constant normal loads – Low load (100 – 500 μN) and High load (1 – 5 mN). The low load normal load set were repeated with varying sliding velocities in the range of 0.3 – 1.2 $\mu\text{m/s}$ to study the effect of sliding velocity and potential frictional heating. The nanoscratch test done at high temperature were limited to only lower normal load set due to higher penetration depth. All scratch lengths were kept constant at 10 μm . The normal force, friction force, normal displacement and lateral displacement were recorded during the scratch tests. A trace and retrace scan were performed using low load of 2 μN before and after the scratch test to be able to do tilt correction and calculate the residual depth due to the scratch. The overall drift rate including the thermal drift was recorded and was kept less than 0.5 nm/s. The system also has a scanning probe microscopy (SPM) capability through which in-situ surface topography can be measured using a low contact force of 2 μN . Table 8 summarizes the experimental conditions and test parameters.

Table 8

Experimental conditions for the nanoscratch experiments


Sample	Temperature (°C)	Normal force (μN)	Sliding velocity (m/s)
Virgin Inc 617, Virgin 800HT, Aged Inc 617, Aged 800HT	25	100 – 500 1000 - 5000	0.3, 0.4, 0.6, 0.85, 1.2
Aged Inc 617, Aged 800HT	200, 400	100 - 500	0.3

7.2.1. Experimental results


Load dependency of friction

The frictional behavior for both virgin and aged samples was studied at different loads in the range of 100 – 500 μN with constant sliding velocity of 0.3 $\mu\text{m/s}$. The variation of average friction coefficient as a function of normal load are shown in Fig. 63 where the error bars designate the standard deviation obtained from three independent measurements. The micro-friction of Inconel 617 (0.13 – 0.23) is slightly lower than 800HT (0.15 – 0.26) in all load conditions. For both materials, the COF shows an increasing trend with higher normal load. The increase in friction force with normal load is an indicator of the larger plowing (deformation) part of friction coefficient [106]. In addition, here, the nanoscratch resistance of the surfaces can be evaluated quantitatively by observing the differences in the residual scratch depth in Fig. 64. At lower load of 500 μN the residual depth on virgin 800HT is slightly higher than on virgin Inconel 617 while significant higher scratch resistance of Inconel 617 can be seen for the aged samples with the oxide layers on top. Since no considerable residual scratch depth was observed on the aged samples using low load (500 μN), higher load (e.g., 5 mN) was used for the aged samples. As shown in Fig. 63c,d, the residual scratch depth on the oxide layer of Inconel 617 is around 179 nm whereas on aged 800HT is around 717 nm.

It should be mentioned that the COF reported here were calculated as an average of entire scratch scan length, although the maximum COF during the scratch can be much higher. At high load of 5mN, some of the scratch experiments was abandoned in midway as it crossed the maximum limit of lateral force and normal displacement of the system.

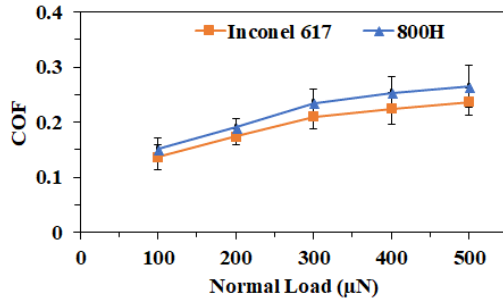


a

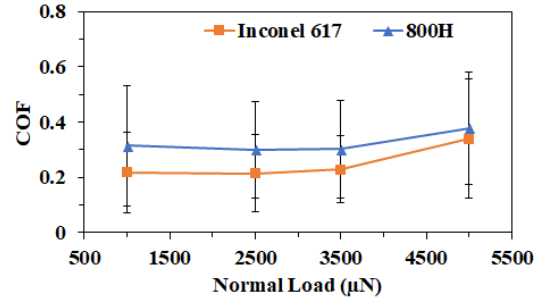


b


Fig. 63 Variation of COF with normal load at sliding velocity of 0.3 $\mu\text{m/s}$ on (a) virgin (b) aged samples.

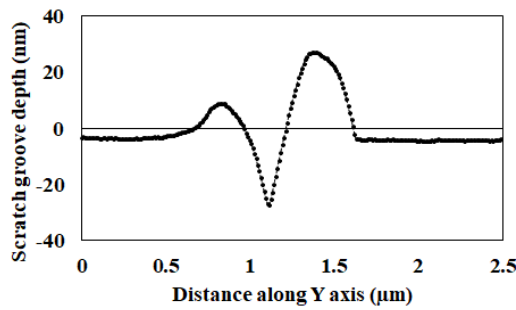


a

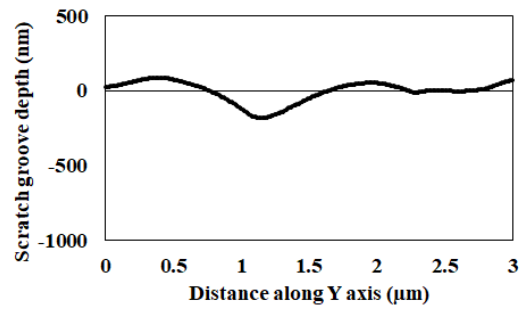

c

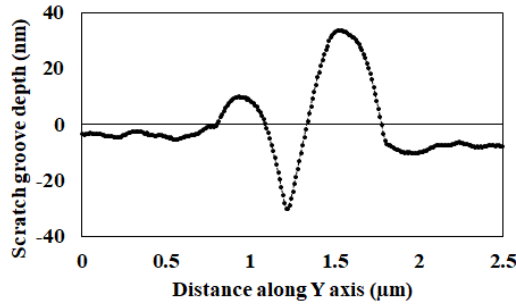

b

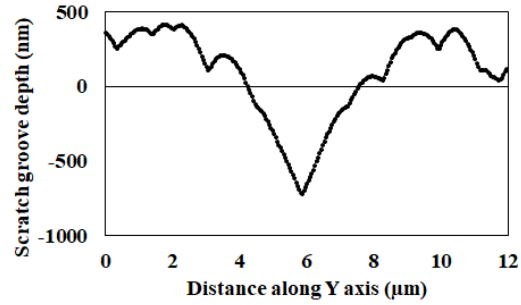

d

Fig. 64 Residual scratch groove depth under normal load of 500 μN on virgin samples (a) Inconel 617 (b) 800HT; Residual scratch groove depth under normal load of 5000 μN on aged samples (c) Inconel 617 (d) 800HT.

Sliding velocity dependence of friction

To investigate the effect of sliding velocity and potential associated frictional heating, scratch experiments were performed at different sliding velocity and at constant normal load. Fig. 65a depicts the variation of COF with varying sliding velocity in the range of 0.3 – 1.2 $\mu\text{m/s}$ at a constant normal load of 500 μN . accordingly, Fig. 65b shows the SPM image of the residual

scratches of the experiments. Both alloys show no significant dependence of COF on sliding velocity.

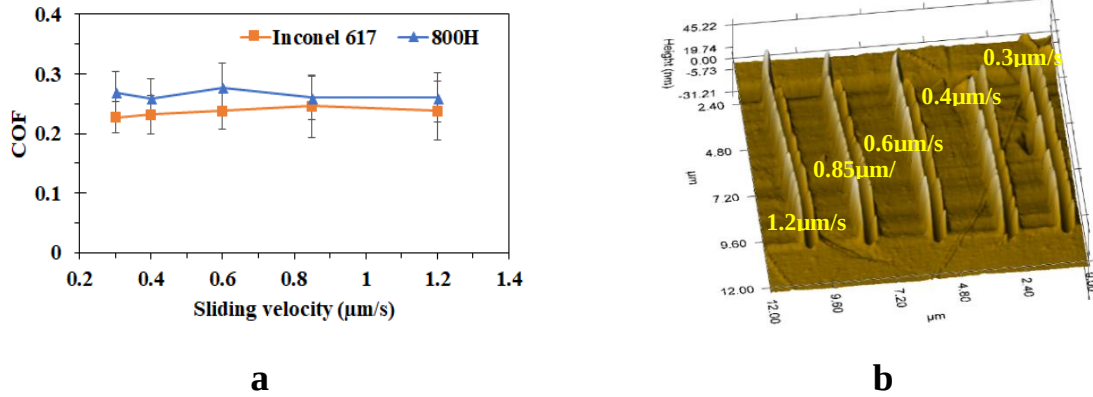


Fig. 65 (a) Variation of COF with sliding velocity at normal load of 500 μN on polished virgin samples. (b) SPM image of residual scratches on Inconel 617.

Effect of temperature on friction

High temperature frictional behavior of the aged samples for both materials was observed by conducting HT nanoscratch experiment at 200°C and 400°C with varying normal load in the range of 100 – 500 μN . Depicted in Fig. 66 is the COF of the oxide layers at HT for aged Inconel 617 and 800HT. For both materials and at all normal loads, COF increases with increased temperature which can be attributed to the effect of combined increased adhesion and more importantly the plowing component due to higher scratch depth on softer oxide layer at higher temperature. On the other hand, both material at 200°C and 400°C shows a lower friction at the load of 500 μN . This variation can also be explained by the dominance of adhesion component of friction at this load [63]. At high temperature, oxide layer of the aged Inconel 617 shows better frictional behavior and scratch resistance property as compared to 800HT. At 200°C, COF for Inconel 617 is in between 0.09 and 0.2 whereas for 800HT it is in the range of 0.23 – 0.37. For 400°C, COF is in the range of 0.29 to 0.38 and 0.37 – 0.51 for Inconel 617 and 800HT respectively. This, in fact, is aligned with our previous findings for high temperature macro-friction of Inconel 617 and 800HT in chapter 3 & 4. In addition, higher resistance of Inconel 617 is evident as at 400°C under normal load of 500 μN , the residual depth on the oxide of Inconel 617 is around 763 nm, nearly 30% lower than that of 800HT (residual depth of 1063 nm).

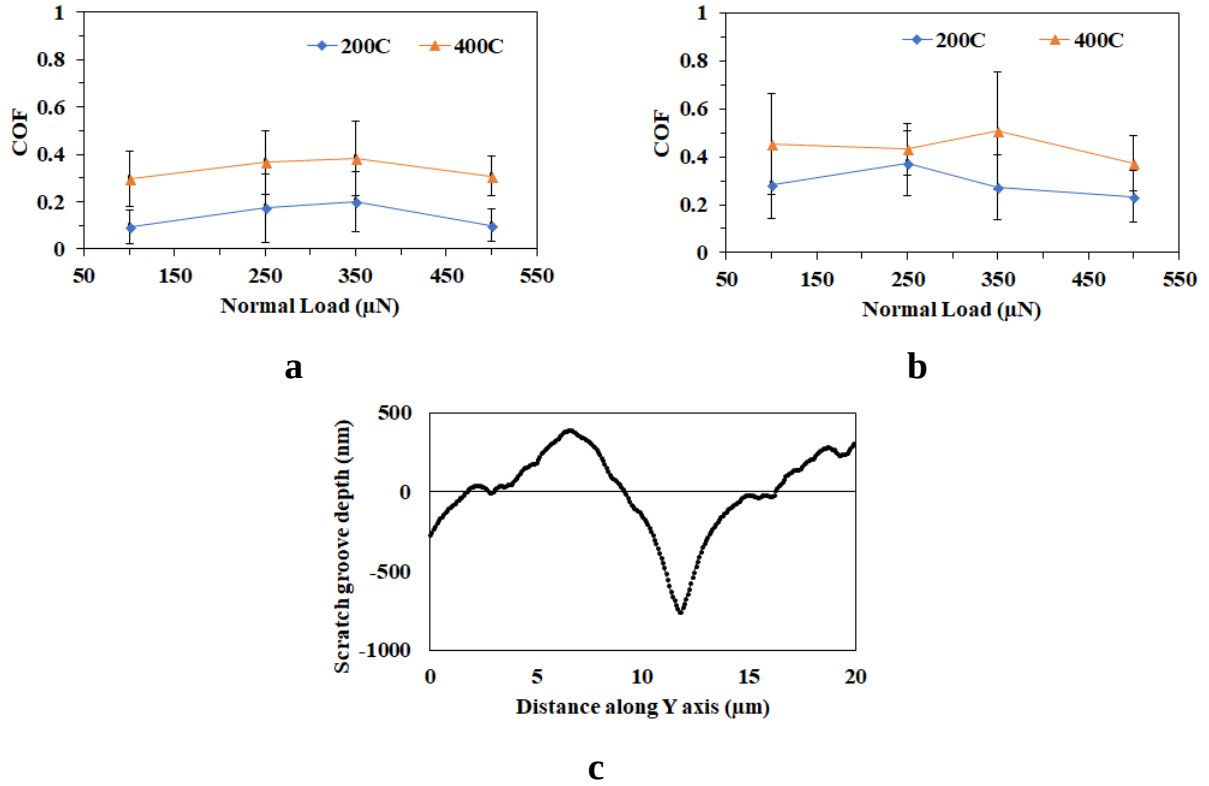


Fig. 66 Variation of COF with Normal load at elevated temperature at sliding velocity of 0.2 $\mu\text{m/s}$ on (a) Aged Inconel 617 (b) Aged 800HT; (c) Residual scratch groove depth under normal load of 500 μN at 400°C on aged Inconel 617.

Finite element simulation

The derived material properties of the nanoindentation section were used as input values in the finite element simulations of scratch (Fig. 67a). The model was verified and validated using a previous model [63] (Fig. 67b) for the residual groove depth (along the z axis). Simulations were performed for different loadings and oxide thickness from 1-10 μm . The thickness range was selected based on the previous results for oxide layer on top of the Inconel 617 in previous chapters. For the scratch simulations, only Inconel 617 is considered as the experimental nanoindentation of alloy 800HT and the extraction of its mechanical properties is under progress. Fig. 68a shows the stress/strain distribution for the deformed virgin Inconel 617 under the maximum load of 500 μN and likewise Fig. 68(b) demonstrates stress/strain distribution for the oxidized Inconel 617 having 10 μm thick oxide under the maximum load of 5 mN. Higher load is selected since both experimental and simulation results showed that under 500 μN no significant scratch depth can be obtained for the oxide layer.

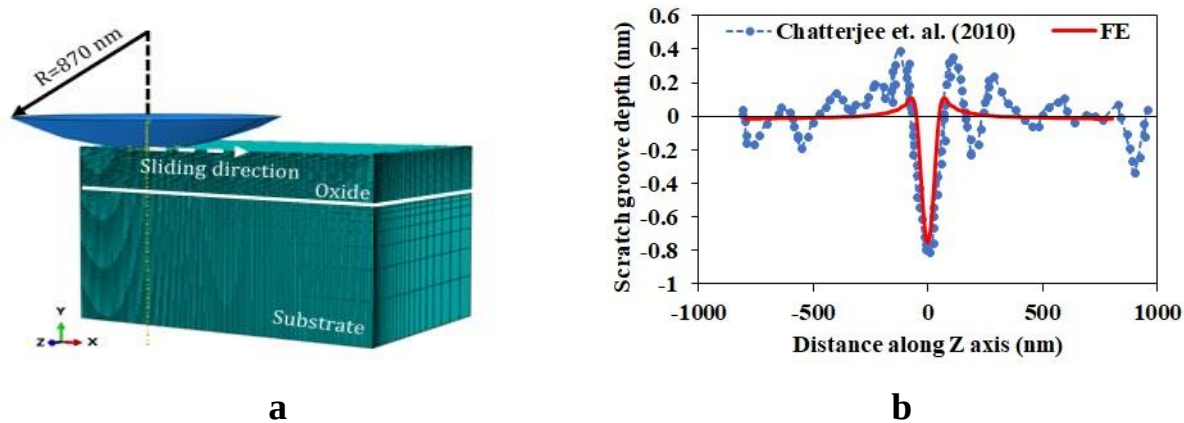


Fig. 67 (a) Model for the scratch test built with ABAQUS, (b) comparison of scratch groove depth along the z axis predicted by finite element simulation and experimental results for thin film HfB_2 on silicon.

The results show that all the stress contours are restrained in the oxide layer (within 100 nm) due to oxide high yield strength (12.85 GPa) and thickness as compared to the contact geometry, so the oxide failure due to the scratch is not associated with significant delamination as also evident by the experimental results. This layer deformed under 21 GPa contact pressure (compare to 659 MPa for virgin Inconel 617) with the onset of yielding at 0.1-0.15 μm below the surface. Von Mises stresses are much higher for the oxide layer due to higher elastic modulus and yield strength. Fig. 68(c) shows the groove depth along the Z axis compared with the experimental results. It should be mentioned that the oxide elastic modulus and yield strength are very high. Also due to the oxidation ductility of the surface diminishes and more imperfections are introduced, which could explain the difference between the simulated results and the experimental measurements. More nanoindentation/scratch simulations as well as experiments are underway to understand the scratch behaviors of both alloys.

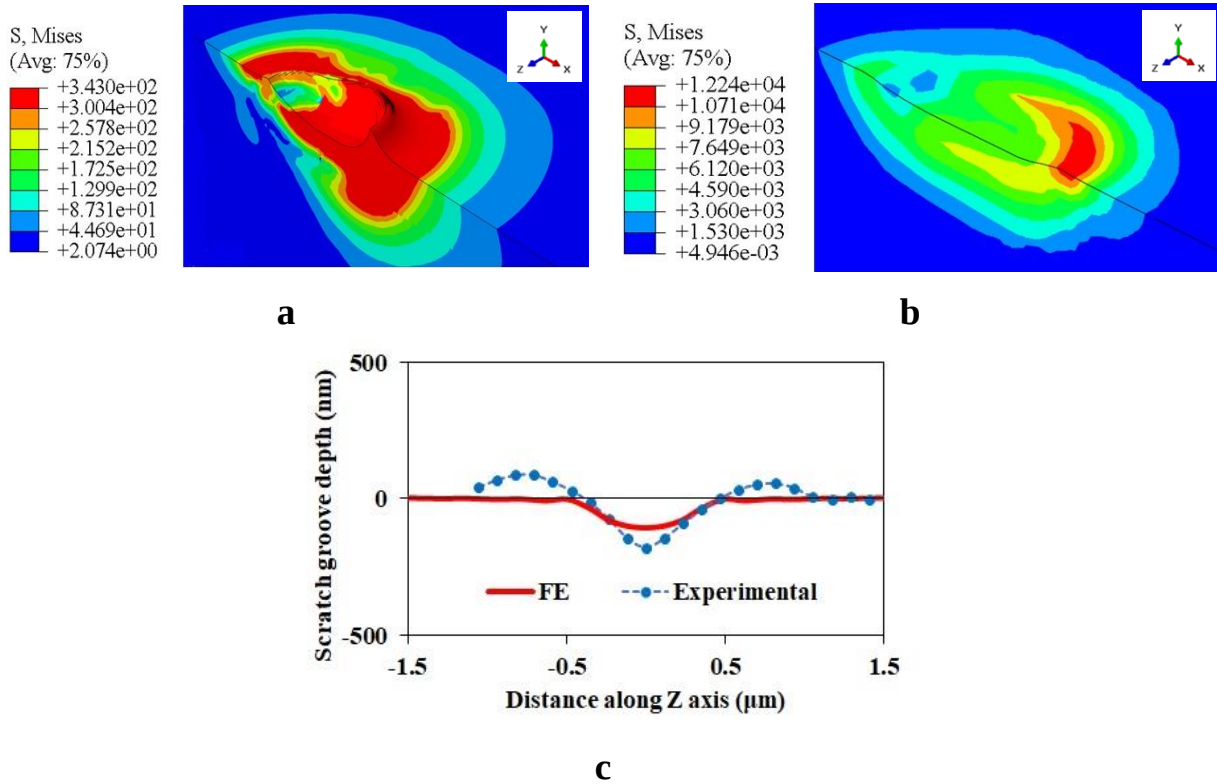


Fig. 68 (a) stress/strain distributions of the virgin Inconel 617 compared with (b) oxide layer on top; (c) scratch groove depth of oxide layer along the Z axis.

7.2.2. Nano/micro-scratch summary

- Nanoscratch experiments is conducted with a 870 nm radius conospherical diamond tip at room temperature on virgin samples at high temperature in He. Inconel 617 show lower COF as compared to 800HT.
- HT nanoscratch on the oxidized aged sample is performed with a 5 μm radius conospherical tip under Argon gas environment. Similar to virgin samples, Inconel 617 show lower COF as compared to 800HT.
- None of the material shows significant dependence on sliding velocity at room temperature.
- Although virgin samples show almost identical scratch resistance, the oxide layer on Inconel 617 exhibits much better scratch resistance over 800HT.
- Numerical results show that for the current loading condition and geometry the critical stresses remain in the oxide layer with the onset of yielding around 100 nm below the surface. Much higher stresses are observed for the oxide as compared to the virgin sample due to its higher yield strength and elastic modulus.

8 CONTACT CREEP AND FRICTION MODELING OF NICKEL ALLOYS AT HIGH TEMPERATURES

The results presented in this chapter is in process of being submitted as a journal paper.

- “Contact Creep and Friction Modeling of Alloy Inconel 617 at High Temperatures”. In preparation, to be submitted in March 2020.

Nickel alloys Inconel 617 is to be used in controlling rods, valves and other contacting pairs in HTGR/VHTRs. Sliding parts of these components should move smoothly with great precision. Their movement is of course highly dependent on the COF. The static friction is of particular concern since the material pairs experience high temperatures, high loads, and long idle intervals, significantly affecting static COF. In the authors' previous study (see chapter 7), Inconel 617 was aged for 100hrs at 950 °C in a vacuum furnace filled with He to simulate the effect of He-cooled reactors and build up similar oxide. Mechanical properties of the oxide were extracted using HT nanoindentation experiments and simulations. Particularly, creep characterization of the oxide under indentation is investigated. Material properties obtained before was used here to understand and predict oxide contact and frictional properties at elevated temperatures. In the current chapter, the effect of temperature, load, and dwell time on the COF and contact growth of an asperity junction is presented. Accordingly, a static friction model for several dwell times and temperatures is developed.

8.1. NUMERICAL MODELING

To get better insight into the friction and area evolution of the surface of IN617 at high temperatures, a numerical finite element solution is developed for one asperity. The asperity is considered as a three-dimensional deformable hemispherical having an elastic-plastic-viscoelastic property and in contact with a rigid flat surface under combined normal and tangential loads. To reduce the computer cost only half of the hemispherical model is used with a radius of $R = 1 \text{ mm}$. The deformable part is meshed gradually with a total of 75k to 100k elements of reduced eight-node hexahedral, C3D8R, as shown in Fig. 69. The number of meshes is optimized based on the temperature and yield strength of the hemisphere. The sphere is divided into 6 zones ($Z_1, Z_2, \dots, Z_6$) with Z_1 near the contact having the finest elements of the regions ($\frac{Z_1}{Z_6} = 4E^{-3}$) and contain 60% of total elements. This is to get high stress/strain resolution at the contact. A ramping load in a range of $P^* = L/L_c = 0.5$ to 16, is applied on the deformable body. P^* represents the non-dimensional normal load and calculated through dividing applied normal load L by critical load L_c . The critical load refers to the load at which the first plastic yielding occurs based on Hertzian calculations. L_c as well as the corresponding critical interference, ω_c , and corresponding critical contact area are given by:

$$L_c = \frac{4}{3} E^* R^{0.5} \omega_c^{1.5} \quad (8.1)$$

$$\omega_c = \left(\frac{\pi K H}{2 E^*} \right)^2 R \quad (8.2)$$

$$K \approx 0.55 \text{ (for } \nu = 0.25 \text{)}$$

$$A_c = \pi R \omega_c \quad (8.3)$$

where E^* is the effective Young's modulus, R is the radius of the sphere (here it is 1 mm), H represents the hardness and ν is the Poisson's ratio. After applying the ramping load, a range of different dwell times, t_d , from 0 (instantaneous) to 1000 minutes is used to study contact creep. At this step the load is constant where stress/strain under the contact change due to the increase in contact area. Third step is increasing displacement U_x in the tangential direction (Fig. 69). The friction for the normal load is negligible [107], however, for the tangential displacement a large friction coefficient is considered following Wu et al.'s approach [108] where maximum frictional shear stress is used as the criterion for the local sliding inception. This is hypothesized as the shear stress of the deformable body and set as $\sigma_y / \sqrt{3}$, where σ_y here is the yield strength of the oxide on top of IN617 at tested temperatures extracted from the nanoindentation experiments and simulations (Chapter 7). This model with shear stress criterion is selected since it gives more friction results that are valid in wider range and generally more accurate compared to full stick model of Brizmer [109]. This is also beneficial in view of interfacial junctions that might grow considerably and even become welded together at HT. A standard/implicit solver is used to analyze the contact, friction and stress/strain behaviors in all three steps. Note that using explicit solver, elastic slip is considered as infinity, however, it should be adjusted for implicit solvers. Elastic slip (ES) is an elastic displacement during the stick period with default value of 0.005 in the software that may induce additional elastic slip during tangential loading.

To find a correct value for ES, simulations similar to the works of Wu et al. and Malamut et al. for multiple loads and displacements are performed [108,110]. Based on the results, a value of 0.002 is selected for ES. COF and friction force are calculated and falls within 5% of Refs. [108,110]. It should be mentioned that lower values give accurate results in cost of increasing computer cost significantly.

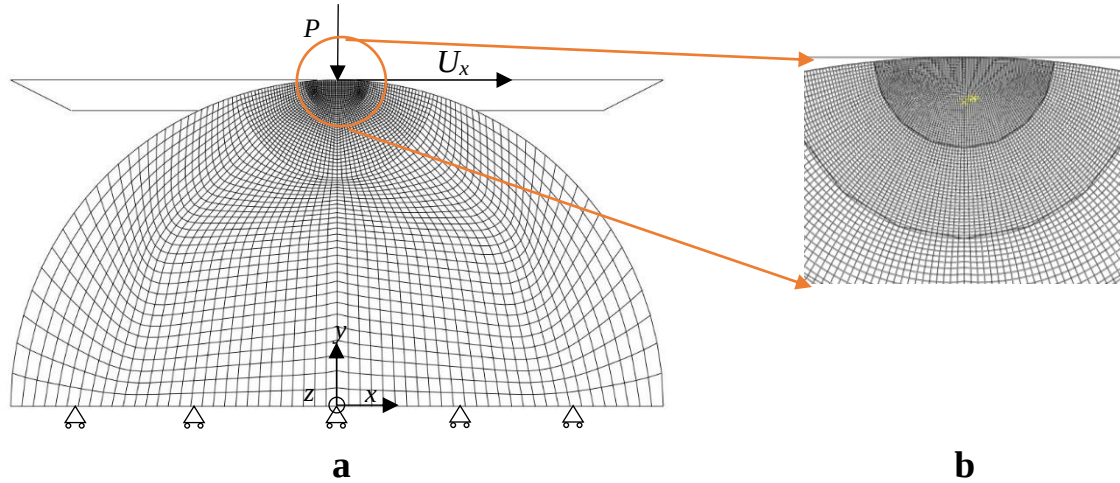


Fig. 69 Schematic of (a) mesh and boundary condition and (b) a close-up view of the fine mesh at the contact region

8.2. CONTACT MODEL VERIFICATION

Fig. 70 illustrates the verification of the current model showing dimensionless tangential force, Q/L_c versus the dimensionless tangential displacement, U_x/ω_c , where Q is the tangential (lateral) force and U_x is the tangential displacement. The graphs show a maximum of 2.42% difference mostly at higher indentations depth. Wu et al.'s model is based on explicit while the simulated model here is based on static/implicit to be able to introduce creep later. As the indentation increases the computer cost increases significantly.

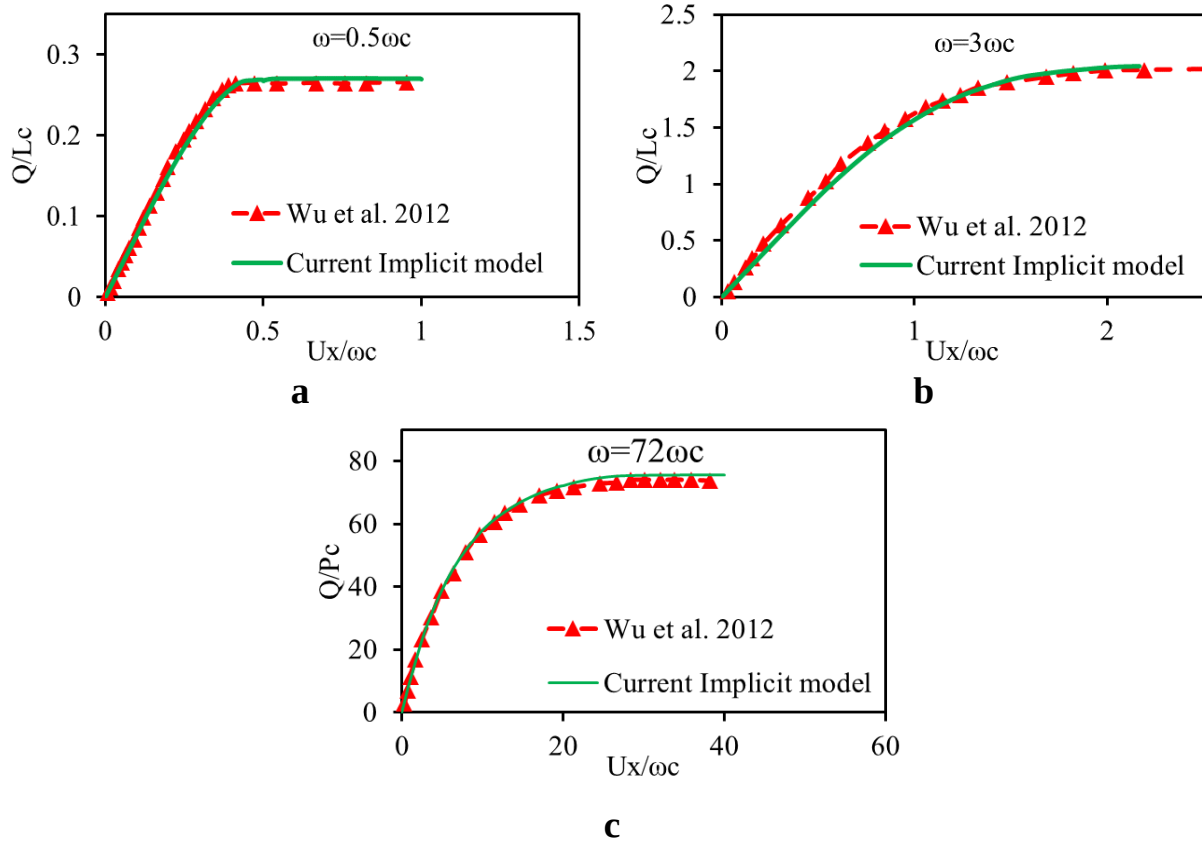


Fig. 70 Dimensionless tangential force vs. dimensionless tangential displacement for different normal interferences

8.3. CREEP MODEL VERIFICATION

To the best of authors' knowledge, there exist no reported work on the HT frictional creep of a metallic asperity in the literature while few reports available for polymer or other geometries (see Ref. [110] for example). To further verify our model focusing on creep, properties of PTFE are introduced to the model and results are compared with those of Malamut et al. Similar to the Malamut et al. model, three holding times, 0, 60, 600 second is selected to measure the influence of creep on friction coefficient. Fig. 71a represents current numerical simulation of dimensionless maximum friction force during creep, $(Q_{max}^*)_{cr}$, versus dwell times along with Malamut et al. results. The $(Q_{max}^*)_{cr}$ is calculated as:

$$(Q_{max}^*)_{cr} = (Q_{max} - (Q_{max})_0)/L_c \quad (8.4)$$

where Q_{max} is the maximum tangential force when the surface reaches the designated shear stress and $(Q_{max})_0$ is the instantaneous maximum tangential force without holding period for creep. Fig.

71b shows the friction coefficient evolution during tangential displacement with dimensionless

tangential displacement, U_x/ω_0 , for a high load of $P^* = L/L_c = 15.75$, where ω_0 is the indentation before creep initiation.

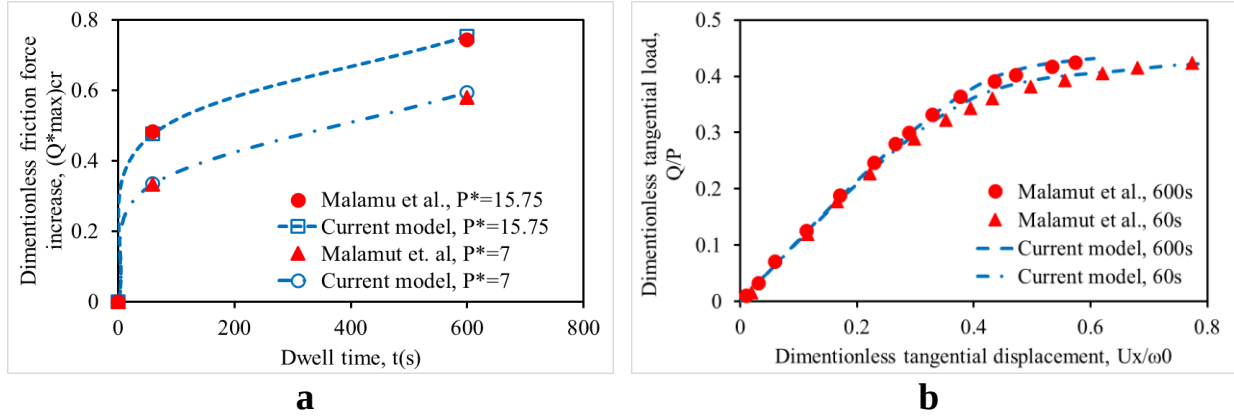


Fig. 71 (a) Dimensionless creep component of the friction force vs. dwell time under different normal loads and (b) dimensionless tangential load versus dimensional tangential displacement for two dwell times of 60 s and 600 s under a high dimensionless normal load of $P^* = 15.75$.

8.4. RESULTS AND DISCUSSION

Numerical solutions are performed based on the mechanical properties extracted by the previous study for oxide surface of IN617 aged for 100 hrs at 950 °C in a vacuum furnace filled with He (Chapter 7) and listed in Table 9. Youngs' modulus, Poisson's ratio, yield strength and strain work hardening exponent evolution through temperature are shown with E , ν , σ_y , and n_1 , respectively. Time-dependent properties, based on power-law creep, are creep coefficient and creep stress exponent displayed as A and n_2 in Table 9. The range of dimensional normal loads varied with the material properties and temperature between 0.7 mN to 2.38 kN. This range is selected to cover a wide range of elastic-plastic loads. It should be noted when the contact radius reaches 0.4, simulations are stopped. At this critical point, asperity deforms such that the contact is no more limited to the asperity tip and, hence, results for single asperity are not extendable for a statistical model of rough surfaces based on Greenwood and Williamson [111,112].

Table 9
Mechanical properties of oxide on aged IN617

Temperature (°C)	E (GPa)	ν	σ_y (GPa)	n_1	A	n_2
25	278.32	0.25	10.28	0.34	3.13E-13	1.71
200	298.02	0.25	6.02	0.22	5.33E-13	1.97
400	323.65	0.25	2.60	0.18	4.75E-12	2.14
600	227.46	0.25	0.13	0.02	1.32E-09	3.51

Fig. 72 shows the effect of dwell time on the evolution of dimensionless contact area, A/A_0 , where A_0 is the contact area right after the normal load application. It shows that by temperature increase, the difference between dimensionless contact areas for different loadings increase. This is more significant when comparing loads of $P^* = 0.5$ to 2 at 25 °C to 600 °C, showing creep influence on contact at high temperature are more significant than room temperature as the load increase. Also, contact evolution is changed from a semi-linear relation with time to a power shape in which the rate of change reaches a constant after short time of approximately 100 minutes.

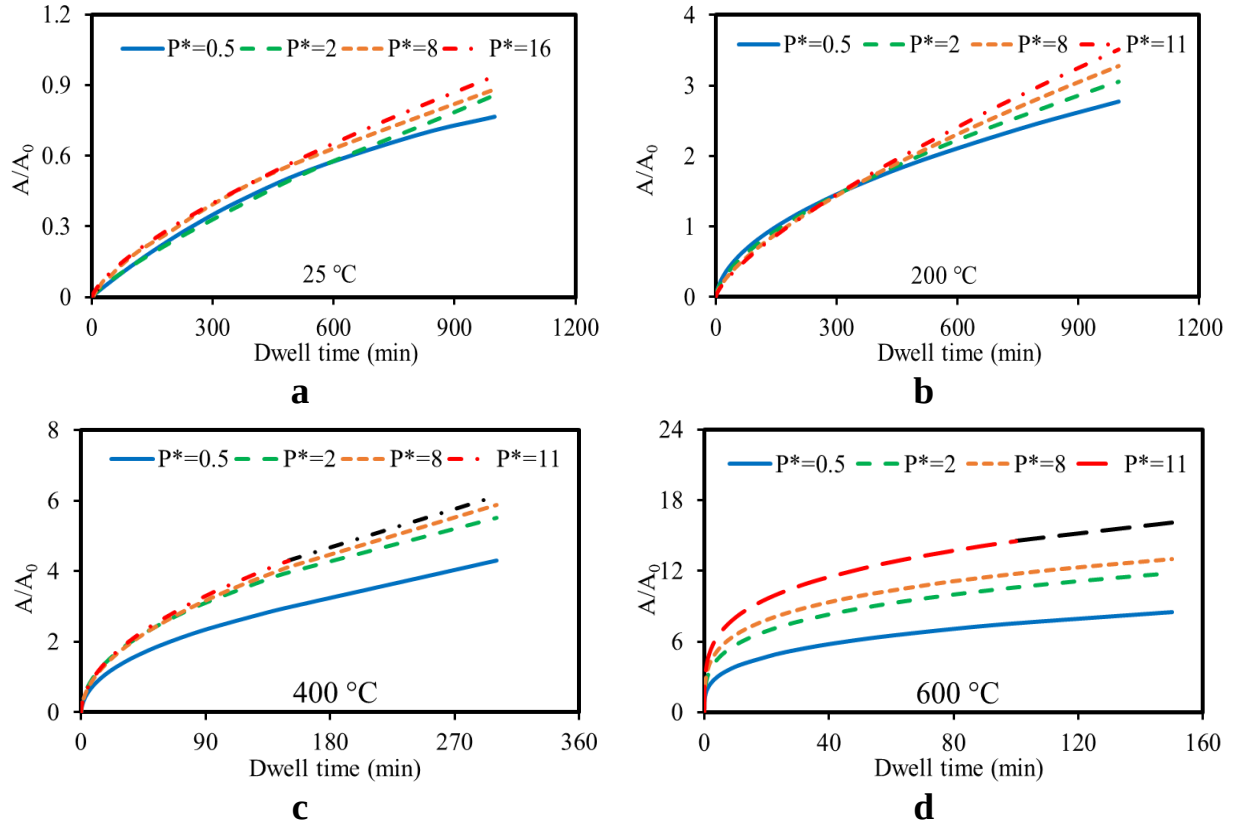


Fig. 72 Evolution of contact area during dwell time for different loads and at different temperatures. As the dimensionless radius of contact ratio, a/R , reaches 0.4 simulations are stopped and results are showed by black line

At high temperatures, the contact area even after a short period of time is larger than the initial contact area resulting in stress relaxation near the contact and higher tangential loading at the sliding inception in comparison to zero dwell time. Fig. 73 shows the evolution of von Mises stress near the contact area which is initially fully plastic under a load of $P^* = 11$ (Fig. 73a) where after dwell time of 10 minutes the high stress region completely disappears (Fig. 73b). This implies that not only the area under creep is increased significantly, but also equivalent stress at the contact falls below yield stress and hence even more tangential load is needed to initiate sliding and reach the same equivalent stress required for initiation of sliding, $\sigma_y/\sqrt{3}$, (Fig. 73c).

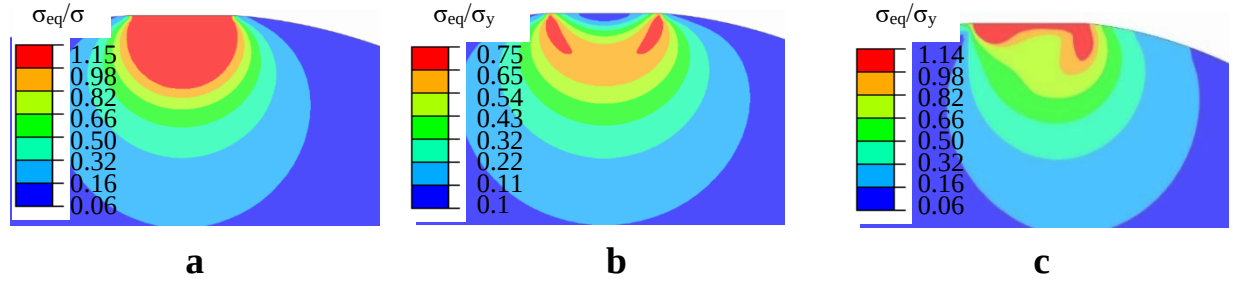


Fig. 73 Contours of equivalent Von Misses stresses at (a) $t = 0$, (b) $t = 10$ min and (c) at sliding inception, under a normal load of $P^*=11$ for IN617 at 600 °C

To compare the effect of temperatures and dwell times on sliding friction, dimensionless load of $P^* = 8$ is selected with dwell times up to 150 minutes. This load is selected as for these parameters, simulated model converge for all the tested temperatures where contact radius is less than 0.4 [111]. Fig. 74 shows evolution of Q/P vs dimensionless displacement, U_x/ω_c . The maximum amount of Q/P or the flat part of the graph here represents the COF. In all the temperatures with the increase of load, COF increase which is more significant at high temperatures. Here, with only 10 minutes of holding, single asperity COF increases by 6 times at 600 °C. This difference is much higher than lower temperatures as in 25 °C by dwell time of 150 min, friction coefficient increases by only 13% times. The overall comparison for COF values is presented in Fig. 75 showing by increasing the dwell time, the total COF will increase. For temperatures higher than 200 °C the effect of creep is more significant which is due to the increase in creep parameters causing stress relaxation increase and contact area growth at higher temperatures.

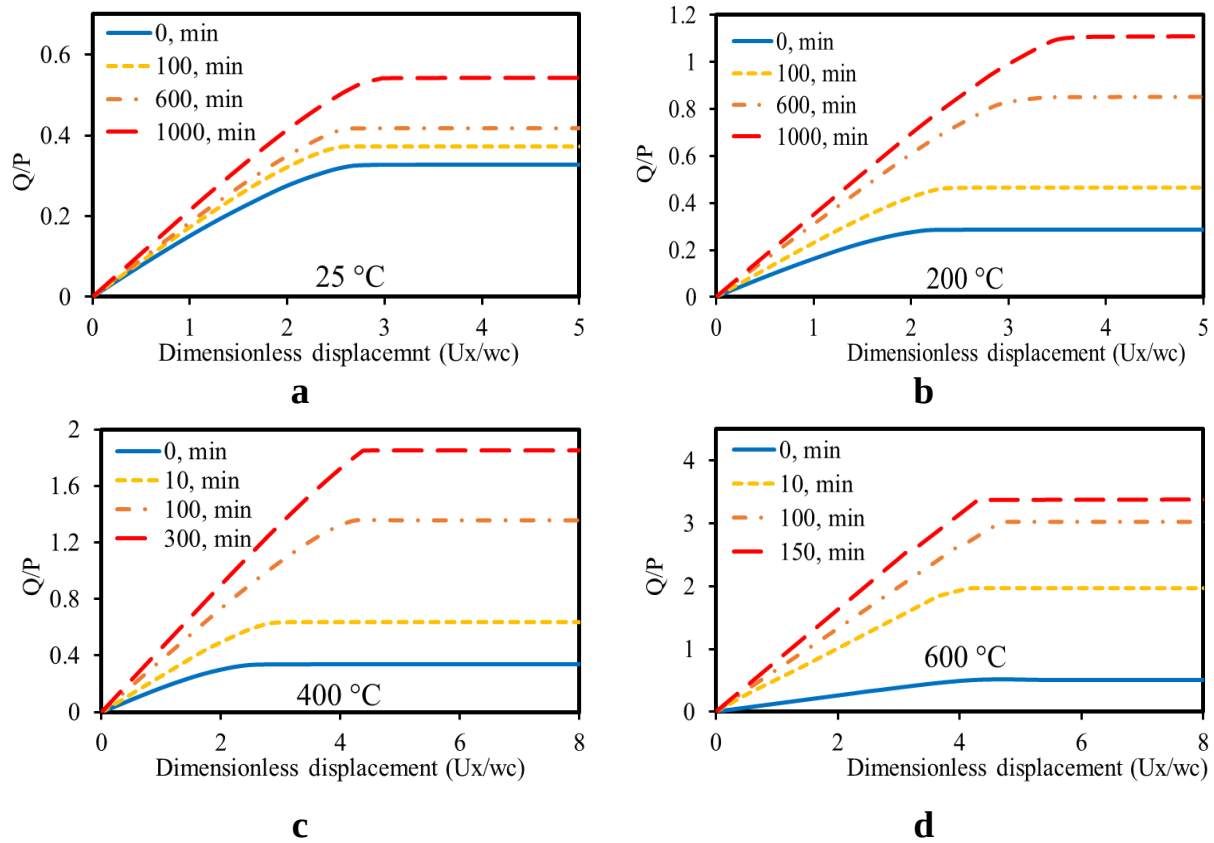


Fig. 74 Dimensionless tangential force vs. dimensionless tangential displacement for different dwell times and temperatures for the reference load of $P^* = 8$.

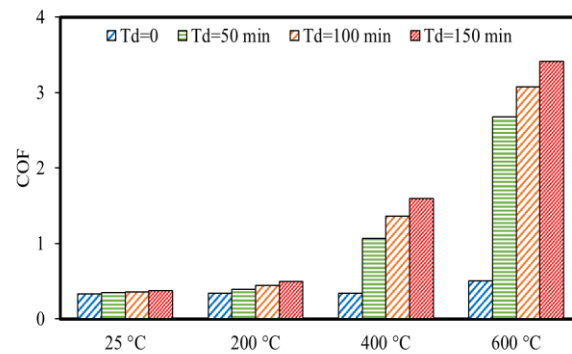


Fig. 75. COF up to 150 minutes of dwell time (T_d) at different temperatures.

To better understand the effect of dwell time on COF of oxide on aged IN617, first the instantaneous (zero dwell time) friction coefficient, μ_0 , are compared for selected temperatures in Fig. 76. As can be seen with increasing normal load the instantaneous friction coefficient decrease for all the temperatures. This behavior is similar to the results of Brizmer et al. and Malamut et al.

[109,110] showing at lower normal loads the contact is more elastic and needs more tangential load to reach the critical point for initiation of sliding. Interestingly, below 400 °C all the oxide graphs merge to one as their E/σ_y are in the same order but for 600 °C the order increased to 10^3 which is close to metals and can be fitted to Brizmer et al. [109] with less than 7% difference. The best fit for the static friction coefficient for temperatures till 400 °C and zero dwell time can be approximated with:

$$\mu_0 = 0.59 - 0.12LN(P^*) \quad (8.5)$$

and for 600 °C, following Brizmer et al. model:

$$\mu_0 = 0.27 \coth(0.27P^{*0.35}) \quad (8.6)$$

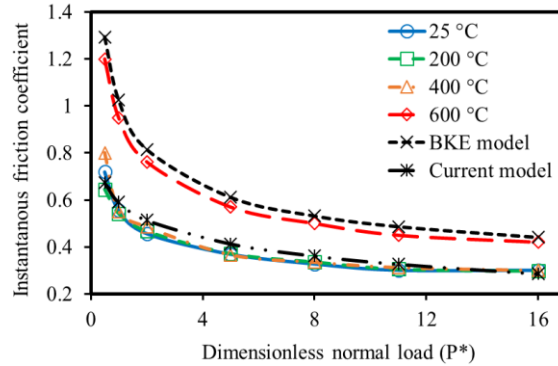


Fig. 76 Instantaneous COF versus dimensionless tangential displacement for IN617 for different loads and temperatures and their best fits

The effect of COF increase due to creep is shown in Fig. 77 for the selected temperature showing an increasing trend for COF increase with temperature. Generally, at higher loads, however, equivalent stress at contact and plastic region is high enough which decrease further deformation of the contact due to creep [84,85,110]. Dependence on load decreases as the temperature increase with 600 °C showing almost same increase for each load.

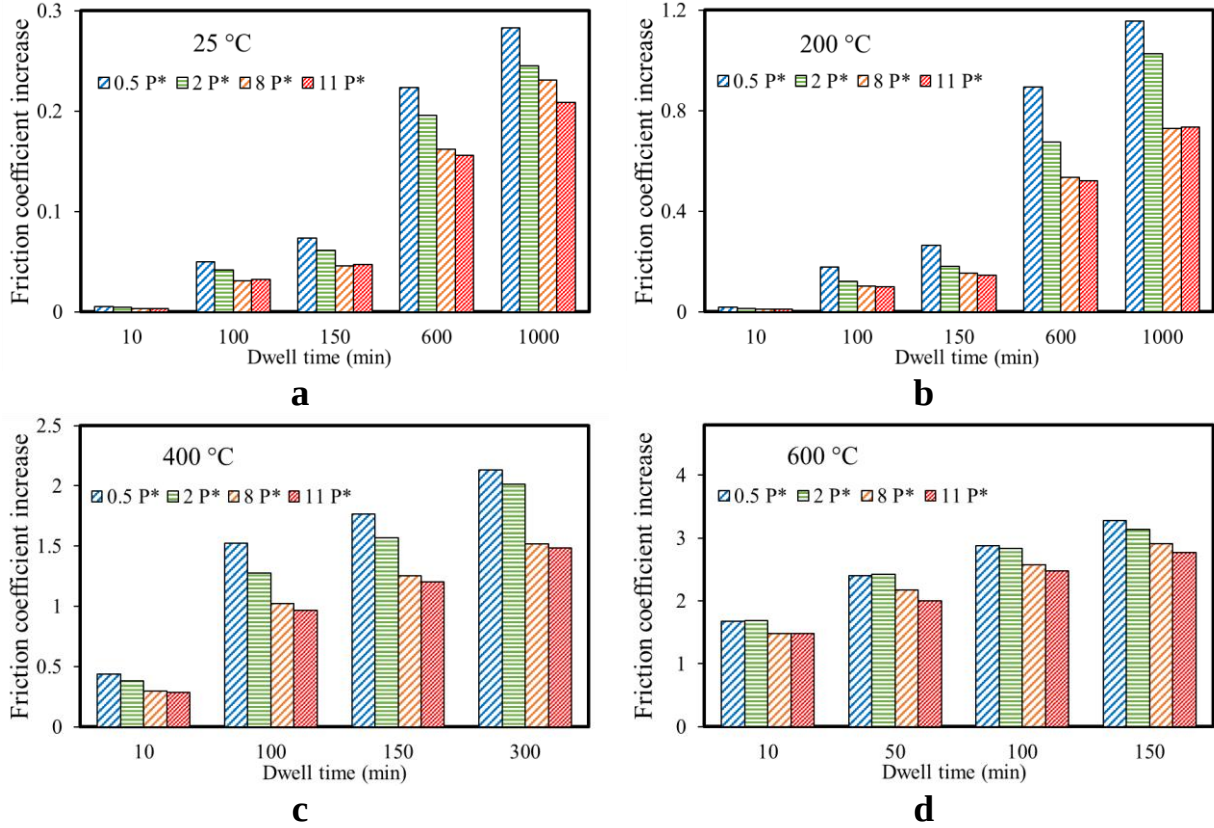


Fig. 77 COF increase due to creep during dwell time for oxide of aged IN617 at different dwell times, temperatures and maximum loads.

It is clear here that after dwell time the asperity COF increases considerably due to the stress relaxation in the contact as well as evolution of contact area during the creep. The total static COF versus the dimensionless normal load for different temperatures is presented in Fig. 78. It can be seen that as the load increase for each dwell time the total friction coefficient reaches a plateau and becomes constant beyond certain load. This COF is called as ultimate COF here and shown for the reference parameter in Fig. 79.

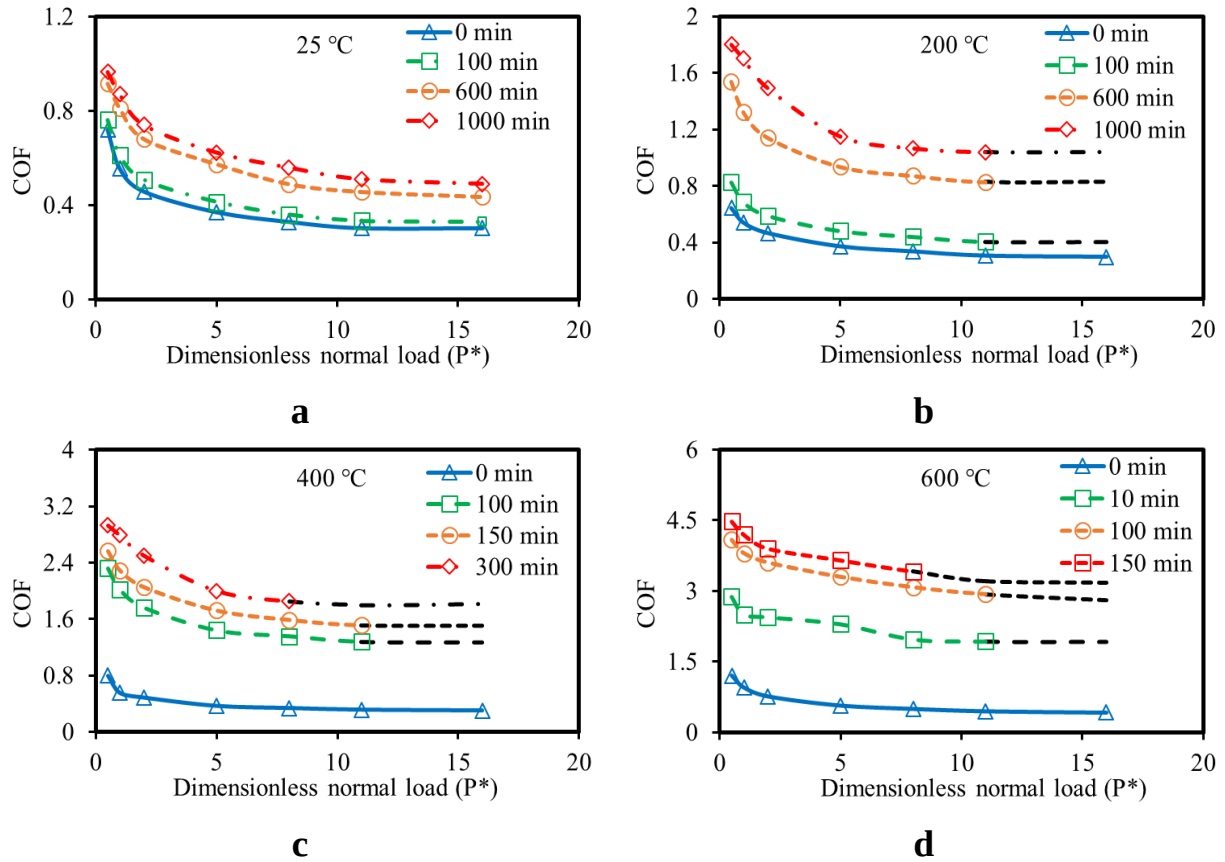


Fig. 78 Total static friction coefficient versus the dimensionless normal load for (a) 25 °C (b) 200 °C (c) 400 °C (d) 600 °C

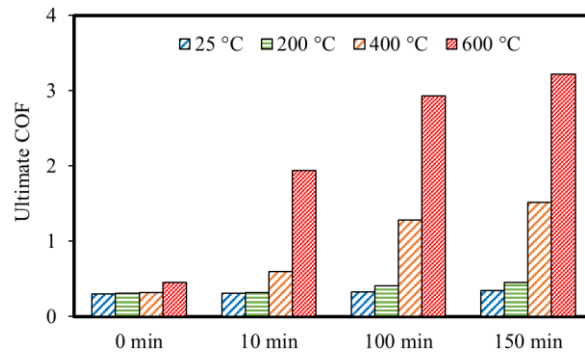


Fig. 79 Ultimate COF for the reference parameters vs dwell times till 150 min

8.5. SUMMARY

By using the extracted materials of IN617 for high temperatures up to 600 °C through previous study, the effect of temperature, load, and dwell time on the COF and contact growth of one

asperity is examined. A new friction model considering HT creep and interfacial junctions' growth is developed and verified with previous models in literature and a relationship for the creep COF is introduced. Finite element simulations shows a significant single asperity COF increase due to the creep for IN617 which is not noticeable for instantaneous (zero dwell time) simulations. As the temperature increases the effect of creep on friction coefficient gets more significant. For example, only 10 min of holding, increases COF by 6 times at 600 °C. This difference is much higher than lower temperatures where in 25 °C by dwell time of 150 min, COF increases by only 1.13 times. Increasing normal contact load, decreases the COF especially at higher temperatures and for all dwell times which follows general observations for single asperity static friction coefficient. The results here, show the significant effect of contact creep on static friction and explain the observation of high COF for nickel alloys surfaces at high temperature after idle times.

9 SELF-WELDING OF NI ALLOYS

The results presented in this chapter are in the process of being submitted as a journal paper:

- “Diffusion bonding behavior of Ni-alloy at elevated temperature under Helium atmosphere.” In preparation, to be submitted in May 2020.

For nuclear reactors, interface between metallic surfaces at high temperatures remains non-lubricated with low water or very small oxygen pressure in the presence of He coolant. Interatomic and intermolecular forces of attraction come into play when two surfaces are mated and come into close contact promoting intense adhesion especially at elevated temperatures [4]. The general objective of this section of research is to systematically evaluate the tribological response of 800HT and 617 alloys at relevant reactor operating temperatures (700-950 °C) and in the presence of He coolant. This chapter focuses on the high temperature self-welding characteristics of Ni-based alloys, as a function of contact pressure and aging duration.


9.1. EXPERIMENTAL PROCEDURE

9.1.1. Muffle furnace and tensile stage

To perform high temperature self-welding tests, a muffle furnace with controlled atmosphere capability was utilized (Fig. 80a). The furnace provides a controllable environment with designated temperature and atmosphere (e.g., gas environment). The built-in 28-segment PID digital temperature controller enables accurate temperature monitoring and consistency. To measure the bonding strength of the self-welded Nickel alloys pairs, a tensile stage, depicted in Fig. 80b, was used. The device accurately measures the force required to detached self-welded test samples after aging process.



a

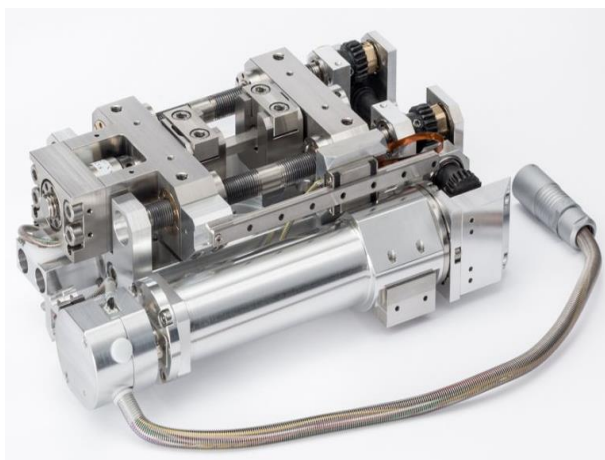

b

Fig. 80 (a) Controlled atmosphere muffle furnace, (b) Tensile stage for bonding strength measurement

9.1.2. Materials and samples

Fig. 81 shows the dimensions of samples made for self-welding tests, as well as the assembly used for the experiments. The material was received in the form of a rectangular bar and machined into required dimensions, using wire Electric Discharge Machining (EDM) process. The overall dimensions of samples tested were 25 mm x 10 mm x 5 mm with maximum testing area of 15 mm x 10 mm and the grip section (for the measurements with tensile stage) of 10 mm x 10 mm. A step was designed to separate the testing surface from the grip. The contacting surfaces were ground to reach surface roughness of approximately 0.4 μm . Pure He (99.999%) was used to simulate the VHTR environment during all of the experiments.

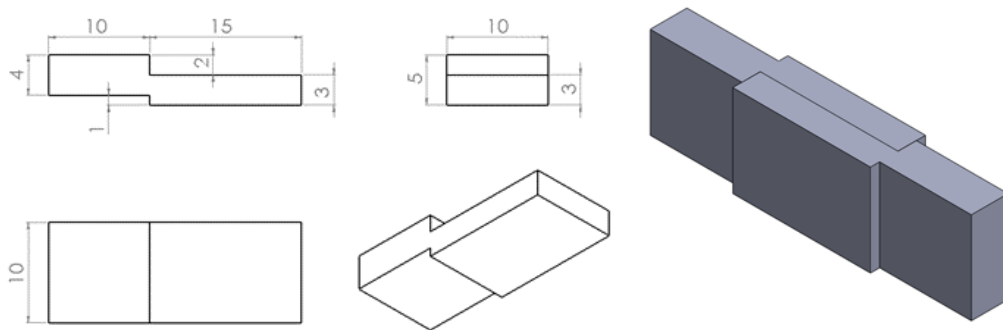


Fig. 81 Test sample for self-welding experiments.

Fig. 82a illustrates the self-welding rig setup. A ceramic disk with machined slots were used to ensure better alignment and effective loading (Fig. 82b). In each experiment, 3 pairs of samples were placed inside the slots. The length of each slot was designed to be able to obtain three different contact areas for the test pieces through various extensions of the contacting upper and bottom samples along the slot walls.

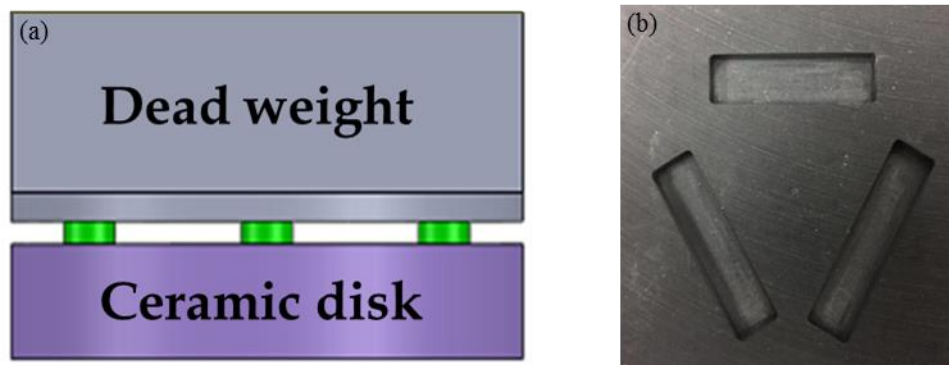


Fig. 82 (a) Setup for self-welding experiments, (b) Lower ceramic disk with slots.

9.1.3. Experimental conditions

The experimental conditions are summarized in Table 10. The Inconel 617 on Inconel 617 tribo-pairs were tested. All of the self-welding tests were carried out in He environment with different aging durations at 950 °C. The experiments were performed under three different contact areas resulted in three contact pressure conditions. The exact same experimental protocol was followed for all of the experiments. Before each self-welding test, the furnace chamber needed to be full of He and free of air. To this end, the furnace chamber was vacuumed to -14.4 ± 0.1 psi and then followed by flushing He in the chamber for a duration of 1 minute, during which obvious increase in the chamber pressure was observed. To minimize the possible residual amount of air in the furnace chamber, the vacuum and flushing process were carried out three times. He pressure in the chamber was maintained at 0.5 psi during all heating up, constant elevated temperature experiment and cooling down processes.

Table 10
Experimental conditions

Disk	Pin	Ambient	Temperature (°C)	Contact pressure (MPa)	Aging duration (hour)
Inconel 617	Inconel 617	Helium	950	0.166, 0.248, 0.341	50, 100

9.2. RESULTS AND DISCUSSION

The self-welding bonding strength for each sample pair was measured using the tensile stage by pulling the two pieces of welded joint apart until the welding breaks, which is referred to as ‘breaking force’, hereinafter. Fig. 83(a) shows the measured breaking force versus contact pressure for samples aged in He for a duration of 50 and 100 hours, respectively. For 50-hour aging duration, as contact pressure increases from 0.166 MPa to 0.341 MPa, the breaking force monotonically increases from 48 N to 4114 N. For 100-hour aging in He, the breaking force for contact pressure of 0.166 MPa and 0.248 MPa is 341 N and 3813 N, respectively, which is significantly higher than the values obtained from 50-hour aging experiment (48 N for 0.166 MPa, 925 N for 0.248 MPa), implying that a longer aging duration results in much stronger self-welding strength as reported previously [5-7]. The low breaking force of 48 N under a contact pressure of 0.166 MPa after 50-hour aging indicates that, under a certain contact pressure, a minimum duration

of aging may be needed for a sample pair of Inconel 617 to start self-welding process. Obviously, the increase in contact pressure accelerates the process. Yokota et al found that for a constant temperature and contact period, the breaking shear stress is proportional to the contact pressure [7-8], which is similar to our case for the samples 50-hour aged samples for all three contact pressures. However, the samples tested at the highest contact pressure of 0.341 MPa for 100 hours, surprisingly do not follow the same trend. For the both tested sample pairs under contact pressure of 0.341 MPa with 100-hour aging, the breaking force is 1976 N and 2306 N, neither of which is higher than 4114 N obtained under the same contact pressure for a shorter duration of 50-hour aging. It is also lower than the breaking force required under lower contact pressure of 0.248 MPa. This discrepancy calls for another mechanism involved which can explain the behavior. Accordingly, normalized bonding area is introduced here which is the ratio of welded contact area over apparent contact area. Although the surfaces were prepared to have consistent and sufficient surface roughness and flatness values, real contact area is much lower than the apparent contact area. More importantly, real contact area and its discrete distribution over the apparent contact area can introduce discrepancy in the results with a margin of error. Therefore, calculating the real bonded area provides a better understanding of the self-welding behavior. Analysis on the area that get effectively welded (real bonding area) was performed using microscope and software ImageJ. Fig. 83b depicts the relationship between the breaking force and normalized bonding area. As seen, for both aging durations, the breaking force increases monotonically with the normalized bonding area. For the 100-hour aging test under contact pressure of 0.341 MPa, the normalized bonding area is lower than expected even for the repeated experiments, which in turn explains the observed lower breaking force. Further analysis on the real contact and subsequently self-welded area suggests a fairly consistent relationship between the measured breaking forces and normalized bonding area, for both the 50-hour aging and 100-hour aging experiments. It should be noted that with a longer duration of aging, sample pairs with almost the same normalized bonding area demonstrated significantly higher breaking force, which shows much stronger bonding strength per area.

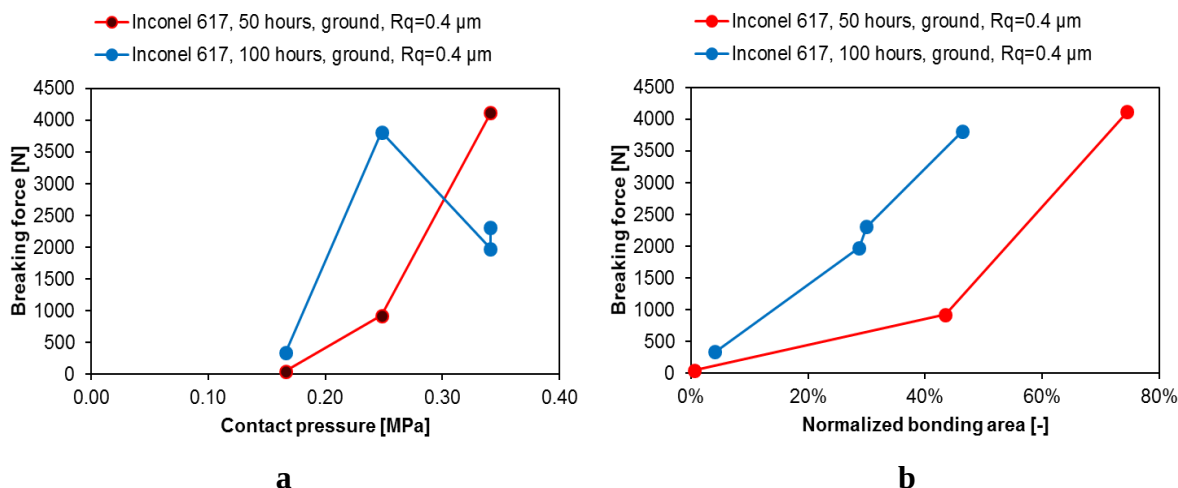


Fig. 83 Self-welding strength of Inconel 617 after 50 and 100 hours of aging at 950 °C in He (a) Breaking force vs. contact pressure; (b) Breaking force vs. normalized bonding area.

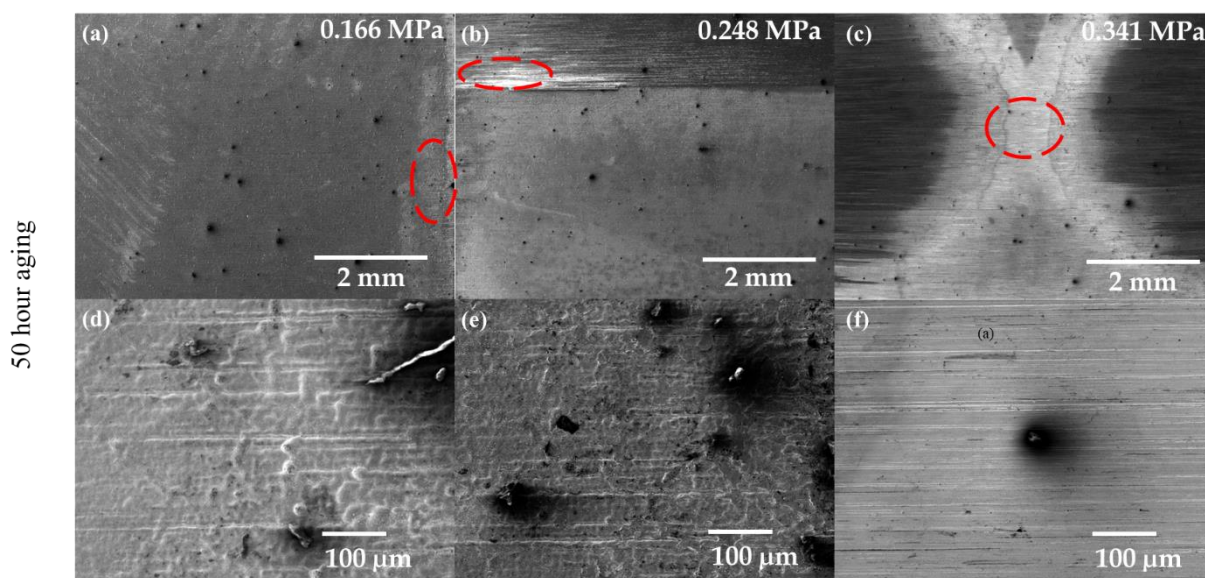


Fig. 84 SEM images of Inconel 617 showing surface damage in self-welded region after 50-hour aging at 950 °C in He.

Fig. 84 illustrates the scanning electron microscopy (SEM) images of the debonded surfaces of self-welded Inconel 617 pair after 50-hour aging in He at 950 °C. Fig. 84(a-c) shows the contact surfaces for samples tested under a contact pressure of 0.166, 0.248 and 0.341 MPa, respectively, whereas, Fig. 84(d-f) shows the SEM images of the same contact surfaces with a higher magnification. As indicated, for the same aging duration, the area of damaged surface increases along with the contact pressure, indicating self-welding behavior at a larger contact area and

stronger bonding strength due to self-welding. Similarly, Fig. 85 shows the SEM images of the contact surfaces of the self-welded sample after 100-hour aging. Similar trend can be observed for the damaged areas and their severity at higher contact pressures. Also, comparing Fig. 84 and Fig.85 one can conclude that under the same contact pressure, doubling the aging duration from 50 hours to 100 hours results in severe damage to the contact surface due to self-welding, as also confirmed by the high increase in breaking force shown in Fig. 83.

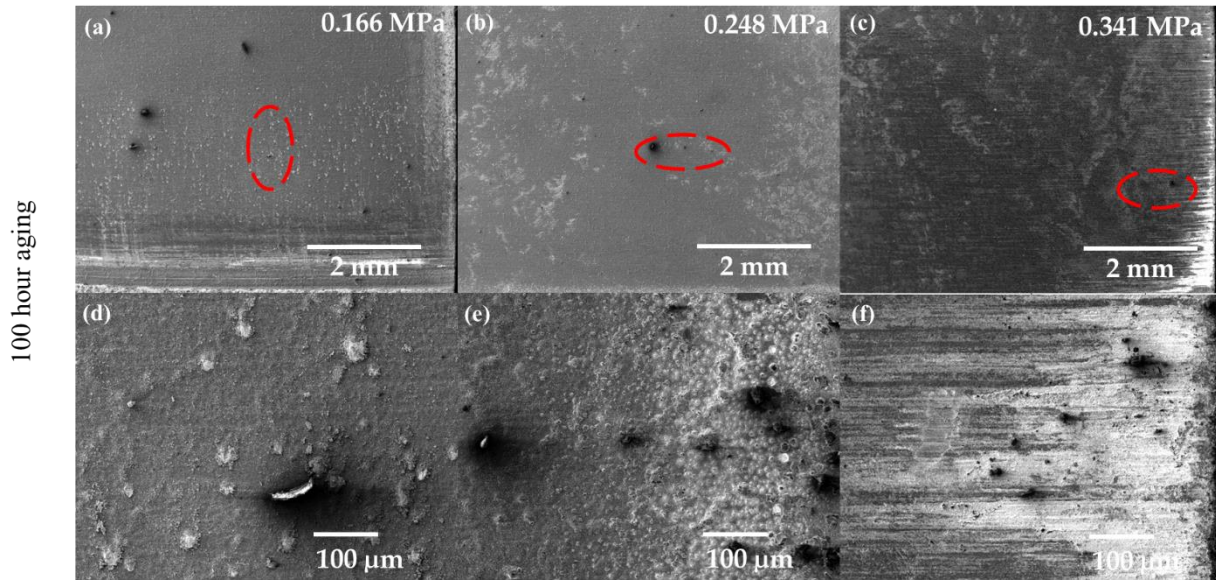


Fig. 85 SEM images of Inconel 617 showing surface damage in self-welded region after 100-hour aging at 950 °C in He.

9.3. CHALLENGES

One of the most challenging part of this study was to have alignment and consistent contact area between the surfaces. Initial experiments without the slotted setup mentioned in the previous section resulted in inconsistency in data. Fig. 86 shows the measured force required to pull the pairs of Inconel 617 apart. The samples were aged under contact pressure in He for a duration of 10 and 50 hours, respectively. The measured maximum breaking force required to pull apart self-welded Inconel 617, after 10-hour aging in He, was 89.5 N under the lowest contact pressure of 0.166 MPa, whereas after 50 hours under same contact pressure the samples did not get bonded. Moreover, the other two pairs under higher apparent contact pressure (0.248 and 0.341 MPa) for the 10-hour aging actually did not get self-welded at all, suggesting that the samples might not have been effectively loaded or evenly distributed among these tests. This can be further viewed from the micro images in Fig. 87 which does not show any apparent bonding area for the contact

pressures of 0.248 and 0.341 MPa for 10 hours aging samples. Nonetheless, bonding is easily visible in all other samples. The challenge was mostly resolved by the aforementioned setup.

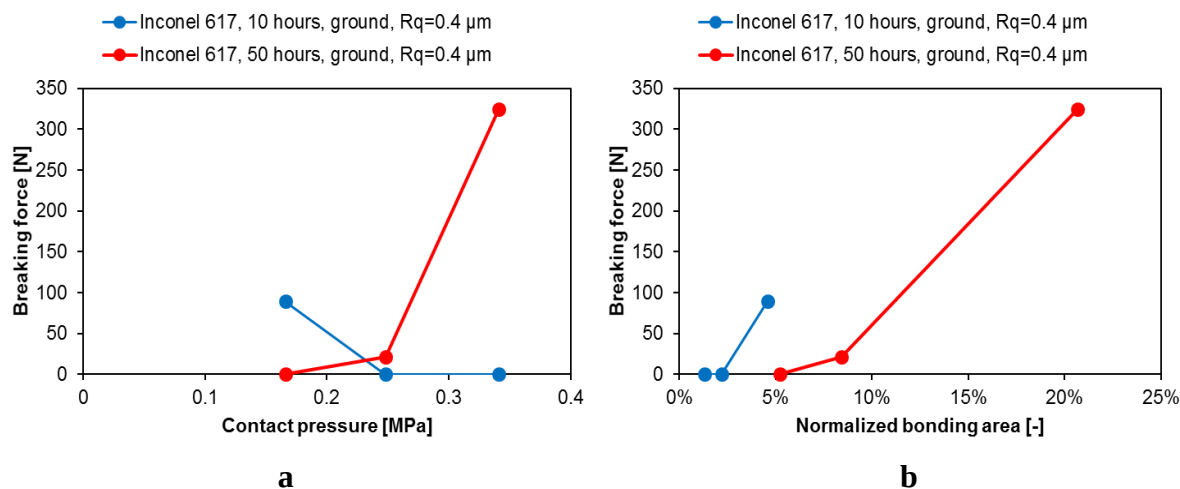


Fig. 86 Self-welding strength of Inconel 617 after 10 and 50 hours of aging at 950 °C in He. (a) Breaking force vs. contact pressure; (b) Breaking force vs. normalized bonding area.

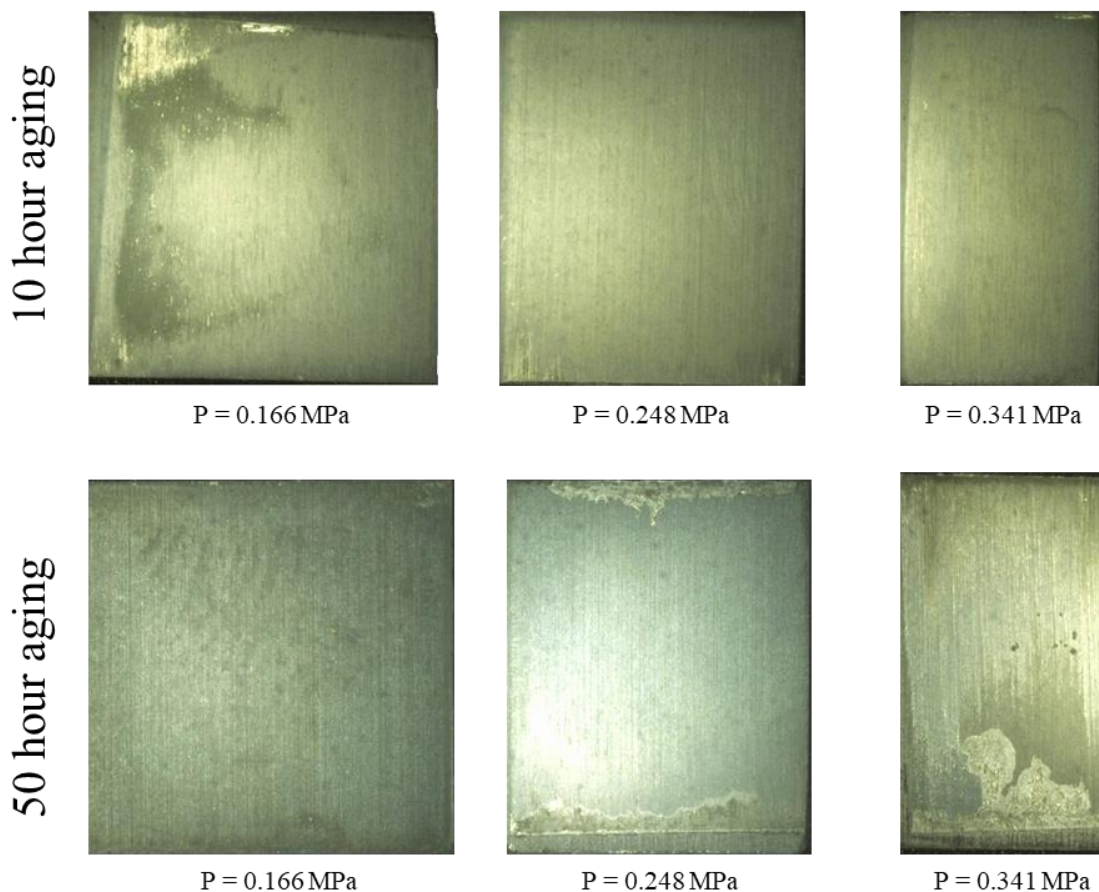


Fig. 87 Micro imaging of Inconel 617 after 10 and 50 hours of aging at 950 °C in He.

9.4. SUMMARY

The following summary of the conclusions can be drawn based on the test results and analysis:

- In He environment and under high temperature of 950 °C, Inconel 617 demonstrates the tendency to get self-welded.
- A minimum aging duration and contact pressure are required for the Nickel alloy to get self-welded at high temperatures in the environment of He.
- Under the same aging duration and temperature, higher contact pressure accelerates the welding process and results in higher self-welding strength. In addition, under the same contact pressure and temperature, longer aging duration results in drastic increase in self-welding strength.
- A potential relationship was observed between the self-welding strength and the normalized bonding area. This relationship is almost linear for the same aging duration where, self-welding strength increases along with the normalized bonding area.

10 TRIBOLOGICAL PROPERTY ENHANCEMENT

The results presented in this chapter is in process of being submitted as a journal paper:

- “Effect of Layer thickness on mechanical and nano-tribological properties of Ni-Cr multilayer coatings at elevated temperature”. In preparation, to be submitted in June 2020.

Coatings have been used in several applications to improve the contact performance and increase the service life of components. Metallic multilayers with various individual layer thickness have drawn considerable attention from the community for their promising mechanical properties and surface enhancement capabilities [1–5]. Recent studies have shown that certain metallic multilayers with nanoscale individual constituent layer thickness exhibit extremely high strength close to their theoretical values [4–10]. To mitigate the observed high friction of alloy 800HT and Inconel 617, multiple combinations of Ni/Cr multilayer coatings were investigated where the hardness of multilayers were tailored effectively by varying the individual layer thickness [11-12]. Nano/micro-scratch was utilized for the study of thin films and surface layers to help explain the tribological behavior with correlation to the properties extracted by the nanoindentation. Nanoscratch at high temperature also helped in the selection of the most suitable coating to be deposited on the Ni-alloy surface. This report presents the nano/macro-tribology of Ni/Cr multilayer coatings on Ni-alloys (Inconel 617 and 800HT) at high temperature using both nanoscratch and macro tribology experiments at very high temperatures.

10.1. COATING PREPARATION

Ni/Cr multilayers with individual layer thickness of $h = 50$ nm and $h = 200$ nm were deposited on Si 110 and SiO₂ substrates for the preliminary nanomechanical and microstructural property study. The 50 nm layered coating (noted as NiCr50 hereinafter) has individual Ni and Cr layer of 50 nm thickness reaching to 1.5 μ m total thickness, whereas the 200 nm layered coating (noted as NiCr200 hereinafter) has individual layer thickness of 200 nm and total film thickness of 4.0 μ m.

For the macro-tribology experiments, NiCr50 and NiCr200 coatings were then deposited on Inconel 617 and 800HT nickel-based alloy substrates by direct current magnetron sputtering at room temperature. Before sputtering, the alloy substrates were mechanically ground and polished, followed by ultrasonic cleaning using ethanol. The sputtering chamber was evacuated to a base pressure of less than 5×10^{-8} torr before deposition. The total film thickness was kept similar, ~ 1.6 μ m for both Ni-based alloy specimens. For this multilayered structure, the first layer is always Cr and the topmost layer is always Ni.

10.2. NANO-TRIBOLOGICAL PROPERTIES

A bright-field XTEM micrograph of NiCr50 multilayer coating (on Si 110 substrate) is shown in Fig. 88a. The inset selected area diffraction (SAD) pattern clearly demonstrates the formation of polycrystalline structure after deposition and no preferable texture is observed. The EDS mapping results (Fig. 88b) and its corresponding line profiles (Fig.88c) verify the chemically alternating layer structure.

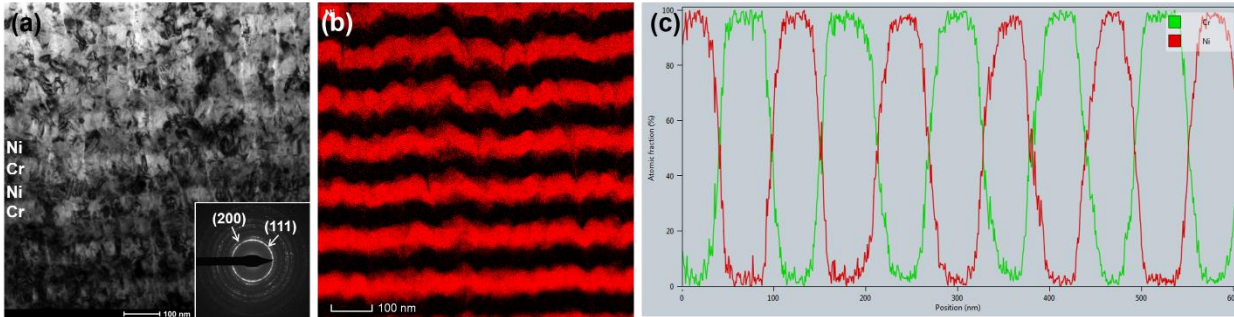


Fig. 88 An XTEM micrograph of Ni/Cr 50 nm multilayer showing the polycrystalline structure. (b) EDS mapping result of Ni and (c) the corresponding line profiles verify the chemically modulated multilayer structure.

The coatings grown on SiO₂ substrate were tested by nanoindentation and nanoscratch. The SPM images in Fig. 89 shows the clear difference in asperity distribution of the coating surfaces. The roughness values, R_{rms} of 5.41 nm and 10.94 nm is calculated from the images for NiCr50 and NiCr200 coatings, respectively.

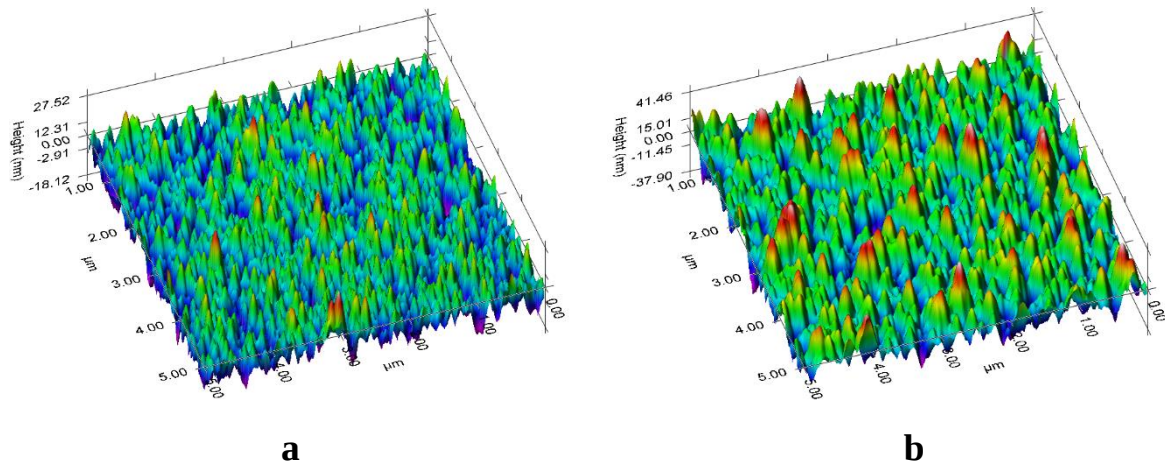


Fig. 89 SPM images of (a) NiCr50 and (b) NiCr200

The high temperature indentation and scratch experiments were performed using the Tribo Premier nanoindenter by Bruker (Hysitron) under cover gas of 95% Argon and 5% Hydrogen. The indentations were performed using a Berkovich geometry probe having a tip radius of around 180 nm. The indentation depth range for the data presented here and was in between 50 and 300 nm, which is within 20% of the total coating thickness. For each loading condition the indentation was repeated at least four times. The indentation results showed that the average hardness values were 6.00 GPa and 3.57 GPa for NiCr50 and NiCr200, respectively at room temperature, where the reduced elastic modulus for both coatings stabilizes around 150 GPa. These results are summarized in Table 11, where it should be noted that these values are the composite properties of the multilayer coating, not the individual layers. To identify the individual layer properties, pure Ni and pure Cr coatings of 1.0 μm thickness were also deposited on the same substrate. Pure Cr coating exhibits higher hardness and reduced modulus compared to pure Ni coating, as listed in Table 11.

Table 11

Film parameters measured prior to nanotribological testing

Coatings ID	Layer Thickness (nm)	Total thickness (μm)	R_{rms} (nm)	H (GPa)	E_r (GPa)
Pure Ni	1000	1.0	19.66	2.09 ± 0.67	142.94 ± 19.26
Pure Cr	1000	1.0	2.95	5.44 ± 0.56	153.94 ± 6.75
NiCr50	50	1.5	5.41	6.02 ± 0.67	150.22 ± 7.7
NiCr200	200	4.0	10.94	3.57 ± 0.30	158.96 ± 12.02

Similar indentations were repeated at elevated temperatures of 200 °C and 400 °C, shown in Fig. 90. The hardness value for NiCr50 reduces gradually by a small amount. The average hardness at 400 °C was found to be 4.92 GPa, which is 18% lower than the RT hardness. The effective modulus reduces insignificantly and remains almost in the same range. On the other hand, for NiCr200 coating, the hardness and reduced modulus show reduction at 200 °C, but it increases again at 400 °C, which could be attributed to the generation of oxide on the surface.

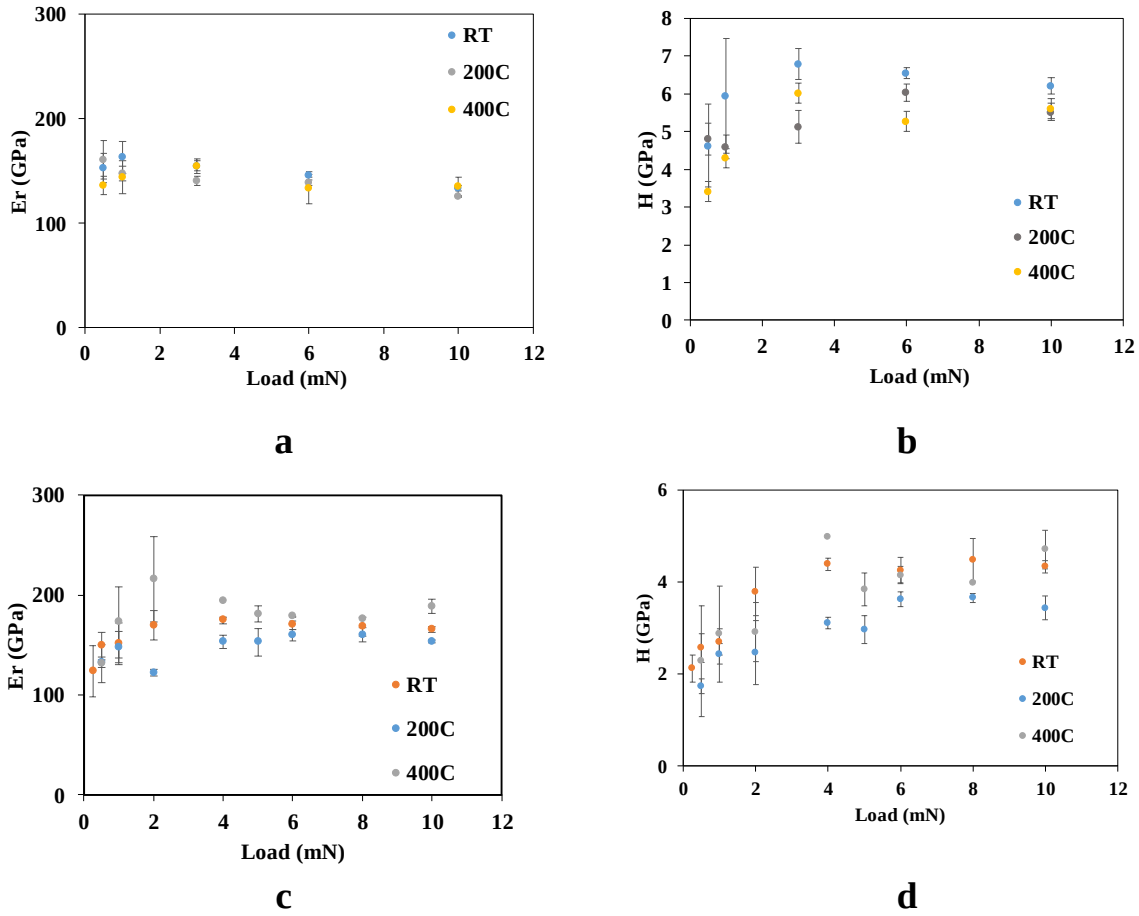


Fig. 90 Extracted nanoindentation properties of (a) reduced modulus of NiCr50; (b) hardness of NiCr50; (c) reduced modulus of NiCr200; (d) hardness of NiCr200 at different temperatures.

The friction behavior was studied at different normal loads (10–100 μN) keeping the sliding velocity and scratch length constant. The variations of COF with temperature and normal load are shown in Fig. 91. The COF of NiCr50 films does not vary much with load up to 200 $^{\circ}\text{C}$, however it starts to increase beyond that point. For NiCr200 coating, the average COF value at different load remains almost constant, showing minimum effect from normal load up to 300 $^{\circ}\text{C}$, but shows fluctuation at 400 $^{\circ}\text{C}$. Fig. 91a also indicates that lower normal load resulted in higher COF at higher temperature, which can be attributed to the higher dependency of COF on adhesion at higher temperatures (and lower normal loads).

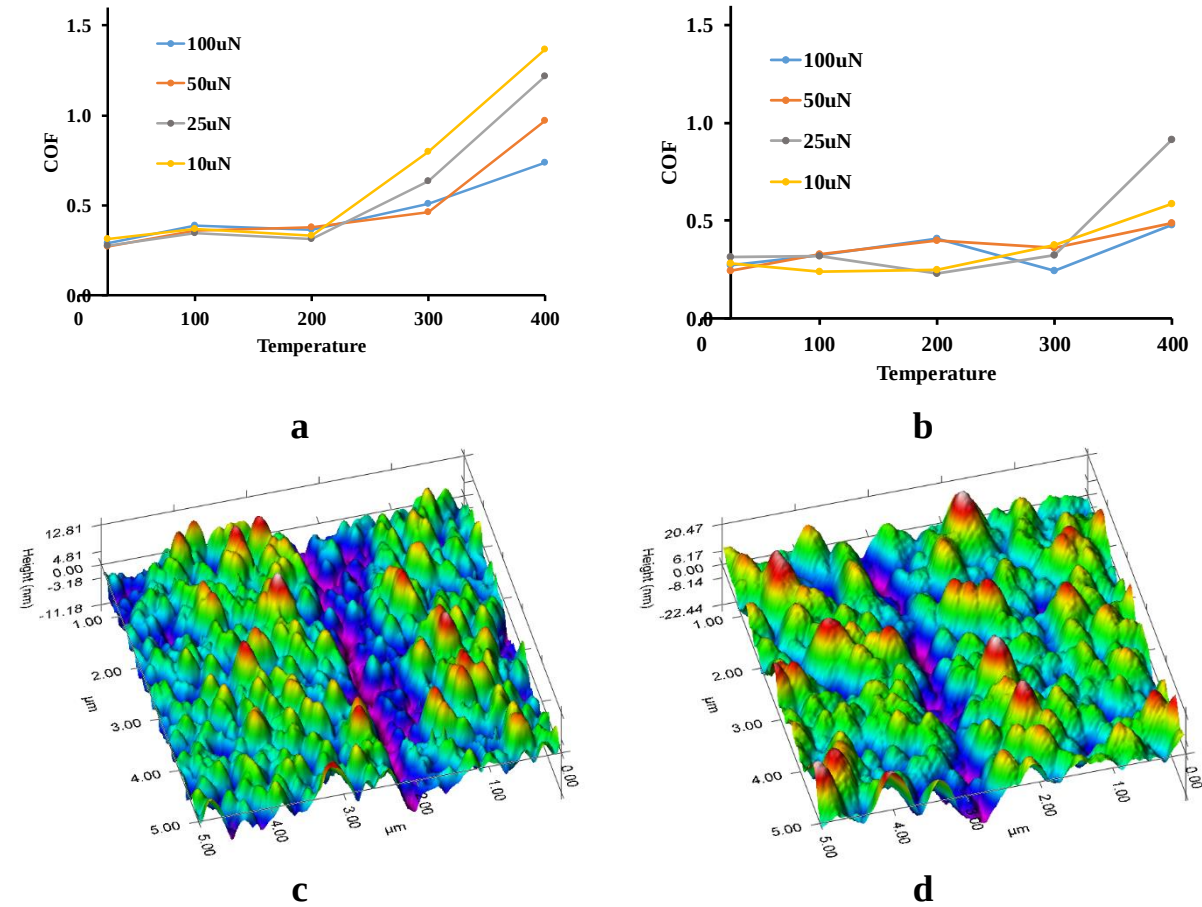


Fig. 91 Variation of COF with normal load and temperature at sliding velocity of 0.6 $\mu\text{m/s}$, for 6 μm scratch length (a) NiCr50, (b) NiCr200; 3D SPM image (using the same tip as for the scratch) of the post-scratch surface at 400 $^{\circ}\text{C}$ (c) NiCr50, (d) NiCr200.

Fig. 92 shows the normal displacement for 100 μN constant normal force scratch experiments for different temperatures during pre-scratch, in-situ, and post scratch conditions for NiCr200. The residual scratch depths were measured using the post scratch scans by the same tip. All the data is presented in Table 12. From the data, the average in-situ scratch depth values are similar with a slight increase with temperature for both coatings. However, the COF increases with the temperature, especially for coating NiCr50. This increase in COF could be the effect of increased adhesion portion of the friction. In simplified form the total COF can be written as [13]:

$$\text{Total friction coefficient } (\mu) \approx \mu_a + \mu_d \quad (10.1)$$

where μ_a is the adhesion friction coefficient, which is the inherent part dependent on the material and adjacent conditions. Plowing (deformation) friction takes place when a harder asperity plows

a softer surface. Using a spherical asperity geometry scratching a flat surface, ploughing friction coefficient (μ_d) can be simplified as [13]:

$$\text{Ploughing friction coefficient } (\mu_d) = 0.6 \times \sqrt{\frac{h}{R}} \quad (10.2)$$

where R is the tip radius (here $R \approx 900$ nm) and h is the in-situ scratch depth. All the measured and calculated data is shown in Table 12. For NiCr200 the ploughing portion of friction ranges from 0.102 at RT to 0.113 at 400 °C, whereas the total COF increases from 0.27 to 0.47 and is much higher than the ploughing friction for the normal load of 100 μ N. This suggests that the adhesive friction has higher impact on the total COF for these coatings. Comparing the two coatings, NiCr50 has better scratch resistance and recovery than NiCr200, but the total COF is much higher at 400 °C for NiCr50.

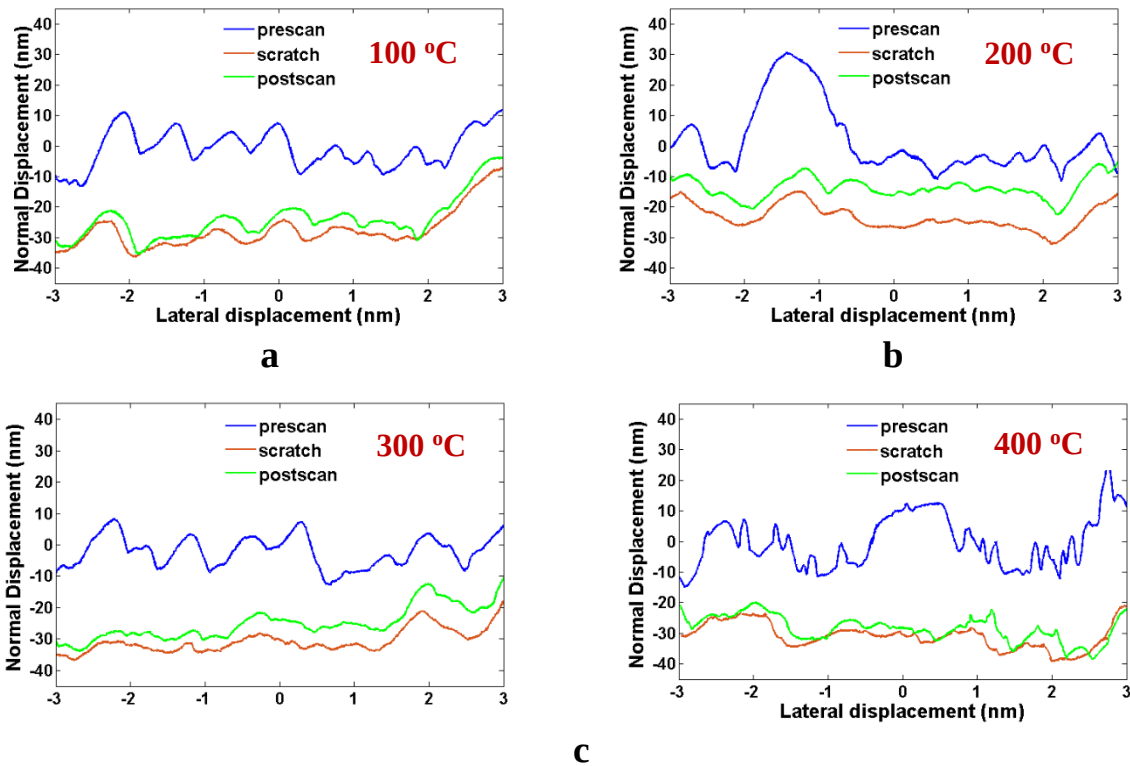


Fig. 92 Scratch profile of NiCr200 with a normal load of 100 μ N at (a) 100 °C, (b) 200 °C, (c) 300 °C, (d) 400 °C.

Table 12
100 μ N Constant Load Scratch Experiments

Coating	Temperature (°C)	In-situ scratch Depth (nm)	Residual Depth (nm)	Recovery (%)	COF, μ	μ_d
NiCr50	25	13.873	10.102	27	0.287	0.074
	200	15.723	11.382	28	0.362	0.079
	300	18.262	12.837	30	0.509	0.085
	400	20.03	14.767	26	0.736	0.09
NiCr200	25	25.933	21.884	16	0.270	0.102
	200	21.305	15.804	26	0.408	0.092
	300	28.361	23.049	19	0.343	0.107
	400	31.946	27.465	14	0.476	0.113

10.3. MACRO TRIBOLOGICAL EXPERIMENTS

The same NiCr50 and NiCr200 Ni/Cr multilayer coatings of 1.6 μ m total thickness were deposited on the surface of alloy 800HT and Inconel 617. The surface was prepared by electropolishing before the coating was deposited. The pin-on-disk tribo experiments were conducted in the specialized high temperature tribometer (HTT) simulating VHTR He environmental conditions. For the counterpart a 55.3 mm diameter spherical pin made out of 800HT (against coating surface with 800HT substrate disk) and Inconel 617 (against coating surface with Inconel 617 substrate disk) were used. The surface of the pins was prepared by polishing to have roughness (R_q) in the range of 30 to 40 nm. The experiments were conducted at 750 °C for 800HT and 800 °C for Inconel 617 in He close to the representative environments for HTGR/VHTR. The tribo-experiments were performed under 5 N normal load and at a sliding velocity of 0.04 m/s.

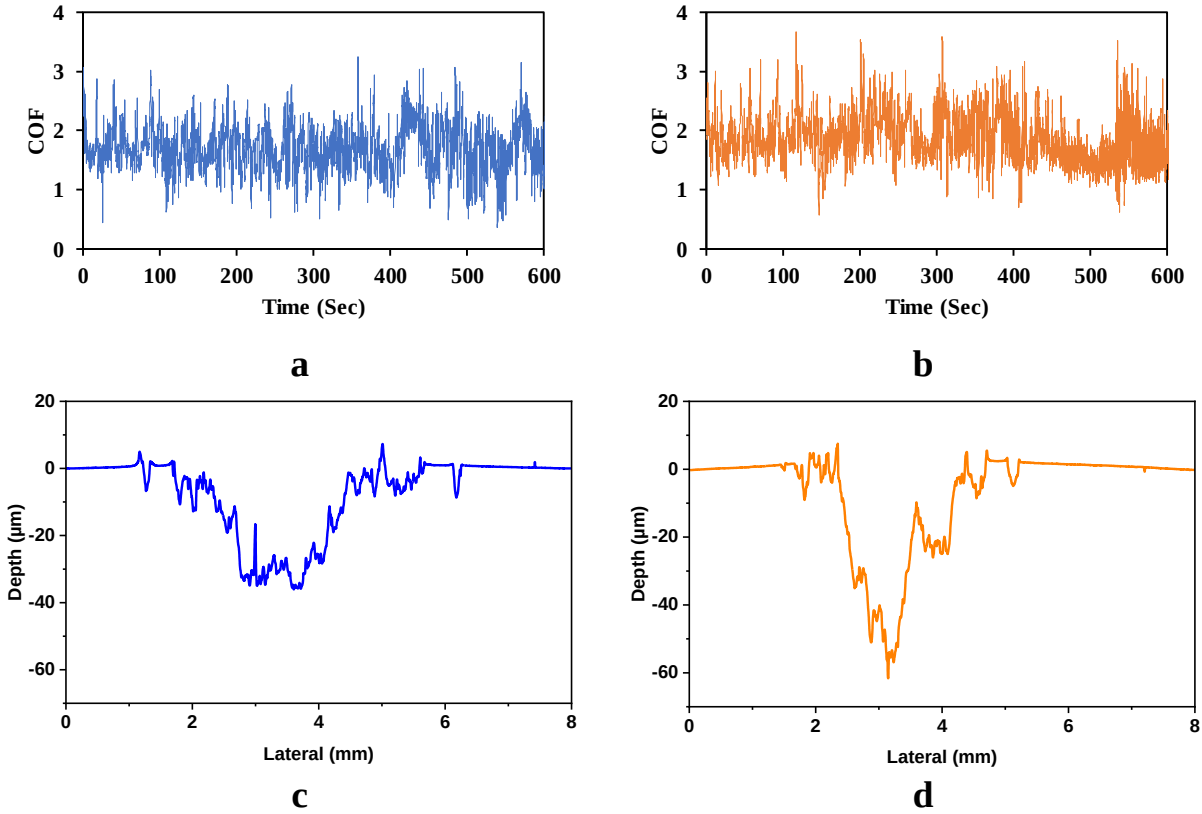


Fig. 93 In-situ COF of (a) NiCr50, (b) NiCr200 in He at 750 °C under 5 N normal load and sliding velocity of 0.04 m/s; Representative wear track line profiles of (c) NiCr50, (d) NiCr200.

Fig. 93 a&b depict the in-situ COF of alloy 800HT coated by multilayer Ni/Cr. The average COF for the NiCr50 coated disk was found to be 1.69 and for NiCr200 to be 1.8. Comparing to COF of untreated surfaces (which was 1.66), this indicates that the coatings were unable to improve the tribological properties of the alloy. The wear tracks were scanned using a contact-based stylus profiler and depicted in Fig. 93c&d. The graphs show clear penetration through the coating and into the substrate for both coatings. Although the coatings survived the scratch experiments at 400 °C under high contact pressure, it could not provide any resistance at 750 °C under macro-scale conditions. Similar results were also observed with the coated samples of Inconel 617 resulting in average COF of 1.36 for NiCr50 and 1.5 for NiCr200. The findings for Inconel 617 are summarized along with those of 800HT in Fig. 94.

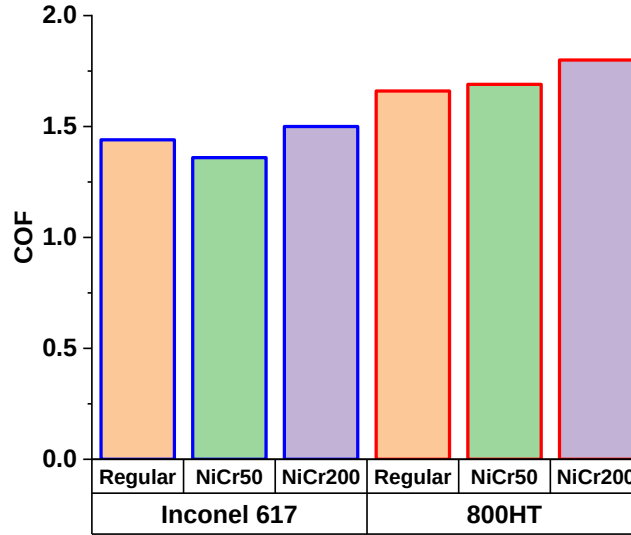


Fig. 94 Average COF of NiCr50 and NiCr200 coated Inconel 617 at 800 °C and alloy 800HT at 750 °C compared with uncoated (designated as “regular”) samples.

10.4. ALTERNATIVE SURFACE TREATMENT APPROACH

Several other alternatives to coatings for alloy 800HT and Inconel 617 were searched in the literature and Laser Shock Peening (LSP) was selected as a potential promising remedy. LSP utilizes short intensive laser pulses to create a plasma in a confined geometry. This results in a very high strain rate plastic deformation leading to a significant increase in the dislocation density through formation of dislocation entanglements and slip bands associated with compressive residual stress and low amount of cold work. The compressive stress field is usually accompanied with increased hardness along with the modified microstructure with a high density of dislocations. The enhanced microstructure creates a shield at the surface where a crack will need much more energy to initiate and propagate. To investigate the effect of LSP on the tribological property of Ni-based alloys in VHTR environment, Inconel 617 samples were LSPed three times and then tested in He at 800°C under 5N normal load, 0.04 m/s sliding velocity and against flat regular (untreated) Inconel 617 pin. Remarkably, the preliminary results show more than 30% reduction in COF and 70% reduction in wear due to LSP process itself, as shown in Fig. 95. This proves LSP to be a promising technique for enhancing tribological properties of these Ni-based super alloys in future nuclear reactors. This of course opens a new path of research focused on LSP of Ni-based alloys for high temperature tribological applications.

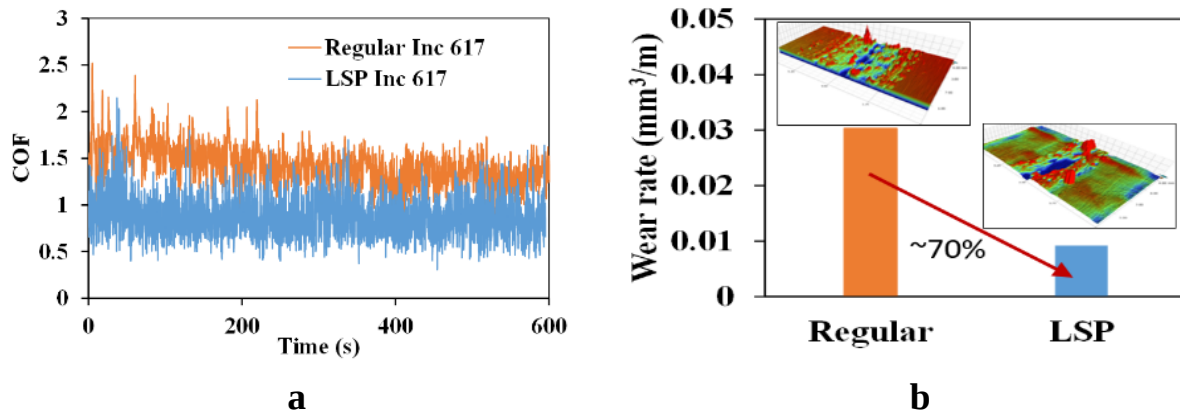


Fig. 95 COF and wear results of untreated and LSPed Inconel 617 in 800°C He atmosphere under 5N load.

10.5. SUMMARY

The objectives of minor milestone #8 were achieved by depositing Ni/Cr multilayer coatings and then subjected to nanoscratch and macro tribological experiments at elevated temperatures. In addition, a relatively new technique to improve the tribological properties at relevant nuclear reactor conditions was investigated showing promising results. The following conclusions can be drawn based on the observations and analysis:

- The developed Ni/Cr multilayer coatings exhibited acceptable performance up to 400 °C under nanomechanical and nano-tribological experiments.
- The same coatings on alloy substrates 800HT and Inconel 617, however, could not protect the surface or improve the tribological properties under macro tribological experiment in realistic VHTR conditions.
- A fairly new surface treatment technique, LSP was applied on Inconel 617 surface. The LSPed samples resulted in 30% reduction in COF and 70% reduction in wear performance, indicating a promising path for the future.

11 OPTIMUM DESIGN/OPERATING CONDITIONS

The general objective was to systematically evaluate the tribological response of 800HT and 617 alloys at relevant reactor operating temperatures (700-950 °C) and in the presence of He coolant. Accordingly, the detailed tribological study of both alloys, Inconel 617 and 800HT, in simulated VHTR operating conditions was performed. This detailed study revealed the friction and wear behavior of the alloys at high temperature (HT) reactor conditions at several varying parameters, including temperature, normal load (contact pressure), sliding velocity, surface roughness and impurity in He. The parameter ranges were selected based on real VHTR/HTGR operating conditions.

The specific objective of this report includes identifying relevant optimum parameters influencing the tribo-pairs performance in reactors. Here, we summarize the overall effect of all these parameters to help in design and material/operating condition selections.

Temperature:

Both alloys exhibited the lowest COF at the intermediate temperature of approximately 500°C and the highest at very high temperatures of 800°C and higher for Inconel 617 and 750°C for alloy 800HT. Maximum temperatures were selected based on the suggested operating temperature range of VHTR. According to several experiments at both air and He environments, Inconel 617 exhibits higher tribological stability with lower COF and wear rate at 950 °C compared to alloy 800HT at 750 °C. These findings suggest Inconel 617 as the favorable choice over alloy 800HT for HTGR/VHTR applications.

Contact Pressure

The study has been conducted in between 5 N to 20N normal load, which corresponds to 0.16 MPa and 0.64 MPa nominal contact pressures. In the case of Inconel 617 in He condition at 950 °C, the change in contact pressure did not have any effect on the gross behavior of the friction. The intermediate load, 10N exhibited the lowest COF consistently and also the specific wear rate. However, for alloy 800HT, the intermediate load of 10 N resulted in the highest COF and specific wear rate. Alloy 800HT exhibited the lowest COF and wear rate at the highest normal load of 20

N at HT of 750 °C in He condition. Experimental observations show that for relative HTGR/VHTR conditions tribo-contact consisting of Inconel 617 performs best around 0.32 MPa at 950 °C and alloy 800HT around 0.64 MPa nominal contact pressure at 750 °C. However, since the variation are minimal and overall COF is generally more than 1.0, the effect of contact pressure is concluded to be insignificant.

Sliding velocity

The sliding velocity range was selected based on the sliding speed calculated for the valve operating in the He pipeline. During the study it is observed that Inconel 617 does not show any dependency on sliding velocity in the investigated range (0.04 m/s to 0.15 m/s). Similarly, for alloy 800HT, sliding velocity did not show any effect on the tribo-contact behavior up to intermediate 0.32 MPa contact pressure. However, as the contact pressure increased to 0.64 MPa, the COF showed a decreasing trend with the raise of sliding velocity, whereas minimal change in wear rate was observed. This generally indicates that alloy 800HT performance increases under higher contact pressure and sliding speed, but for Inconel 617, sliding velocity effect is concluded to be minimal.

Surface roughness

The tribo-study has been conducted for two surface roughness values: R_q 0.3 μm and 0.04 μm . Both alloys did not show any variation in friction/wear behavior with surface roughness. This is due to the high impact of thick surface oxide layer on tribological behavior which is formed/reformed during running-in as well as steady state conditions at high temperatures. Generally, the steady-state condition and the oxide layer morphology/chemistry/thickness was not influenced by initial roughness and therefore, long-term friction/wear behavior showed no dependency on initial roughness.

Helium impurity

To study the effect of the impurities, present in the coolant He, the experiments were performed using three different combinations of impurities which were kept aligned with the reported impurities in the VHTR/HTGR test facilities.

He1 -99.9999% pure (ppm): N₂(0.5), H₂O(0.2), O₂(0.5), CO(0.1), CO₂(0.1), CH₄(0.1)

He2 -99.999% pure (ppm): N₂(5), H₂O(1), O₂(1), CO(1), CO₂(1), CH₄(0.5)

He3 – 99.99% pure (ppm): H₂(200), CO(20), CH₄(10)

Majority of studies here, were focused on He2, whereas He1 and He3 were used as the two other combination of impurities were found before in the test facilities. None of the impurity combinations resulted in better tribological behavior for any of the alloys. Both He1 and He3 resulted in slightly higher COF at high temperature. Therefore, it can be concluded that the investigated impurity combination within the current range of HTGR/VHTR does not have considerable effect on the tribological behavior of the studied alloys.

Surface modification – Coating/LSP

Coating

To improve the tribological properties of the alloy, a Ni/Cr multilayer coating of different layer thickness were deposited on the alloy surface and tested under VHTR simulated tribometer. Although the coatings performed well under high temperature nanoindentation and scratch experiments, they could not offer any improvement to the alloys while under sliding contact in tribometer resulted in similar COF and wear as untreated surfaces. Accordingly, Ni/Cr layered coating is not suggested for the VHTR condition application.

LSP

Several other surface treatment alternatives for alloy 800HT and Inconel 617 were searched and laser shock peening (LSP) was selected and utilized on Inconel 617 surface. The samples were then tested in He at 800°C under 5N normal load and 0.04 m/s sliding velocity and against flat regular Inconel 617 pin. Interestingly, the preliminary results show more than 30% reduction in COF and 70% reduction in wear. *This proves LSP to be a promising technique to enhance tribological properties of these Ni-based super alloys in future nuclear reactors, however, in-depth analysis concentrated on LSP is required for several operating conditions. This, of course, opens a new path of research focused on LSP of Ni-based alloys for high temperature tribological applications.*

12 CONCLUSION

This research project systematically evaluated the tribological response of 800H and 617 alloys at relevant reactor operating temperatures (700-950°C) and in the presence of He coolant. The project aimed to address the need for a clear and inclusive understanding of the tribological performance of Ni based alloys in high temperature gas cooled reactors HTGR/VHTR operational environment as well as a further enhancement in HT durability and environmental compatibility of tribological components operating in HTGR-He coolant.

Under current project a comprehensive experimental plan was performed to investigate and compare the friction, surface damage (wear, self-welding, oxidation) and contact response of tribo-pairs consisting of alloys 800H and 617 in simulated HTGR He and also in air (room and high temperatures). The results generated here contributes to the design and licensing of HTGR/VHTR in Nuclear Regulatory Commission (NRC) especially with the forthcoming addition of Alloy 617 to the ASME Code for HTGR/VHTR. Besides, micro/nano-mechanical testing and material characterization were performed in high temperatures along with analytical/numerical modeling to obtain a fundamental knowledge of failure mechanisms and tribological response as well as to develop predictive models. The research project also investigated different solutions such as optimizing the operating conditions, and surface modifications, such as surface treatments (e.g., LSP), and HT super hard coatings to mitigate tribological problems with these materials under HTGR/VHTR conditions. The following conclusions have been drawn:

- The oxidation behavior of the alloy 800HT and Inconel 617 was investigated under VHTR operating condition and compared with ambient condition. Both alloys follow parabolic trend of oxidation over time for the investigated temperatures and time under both air and He atmosphere. Inconel 617 has almost same oxidation rate in He and air at 950 °C, whereas alloy 800HT has lower rate of oxidation in He at 750 °C. The parabolic rate constants for alloy 800HT in air and He conditions are 1.23×10^{-12} and $3.87 \times 10^{-13} \text{ g}^2 \text{ cm}^{-4} \text{ s}^{-1}$, respectively. For Inconel 617, the rates are 2.27×10^{-12} and $2.31 \times 10^{-12} \text{ g}^2 \text{ cm}^{-4} \text{ s}^{-1}$ in He and air respectively for aging in 950 °C.
- In HTGR/VHTR condition at high temperatures, both alloys exhibit very high friction. Inconel 617 at 950 °C in He shows static coefficient of friction of around 2.28 and steady

state sliding friction coefficient of 1.42 under 5N load and 0.04 m/s sliding velocity. Normal load has minimal effect on the friction behavior under the investigated sliding velocity range (corresponding to VHTR application). In HT He, friction and wear are higher than in air due to the instability of the surface oxide layer and crack initiation/propagation in low oxygen partial pressures, generating larger size wear debris. In air, as temperature increases, friction decreases due to the formation of a protective glazed layer on the tribosurface, formed by wear debris compaction.

- Cr-rich oxide is dominant on the surface of Inconel 617 in both air and He. In He, Cr-oxide, namely Cr_2O_3 is being found on the top surface above Ni-Cr mixed spinel oxide layer. On the other hand, in air, a very thin Ni-Co mixed oxide is found on the very top surface above the Cr_2O_3 and Ni-Cr mixed spinel oxide layer.
- Alloy 800HT at 750 °C in He showed very high COF of 1.66 during sliding whereas the static COF is found to be 3.74, which is around 2.5 times higher than the dynamic COF. At 500 °C and 750 °C He, friction and wear stay high for all conditions due to the surface oxide instability, its brittleness and subsequent crack initiation/propagation through oxide layer in low oxygen partial pressure, resulting in the generation of larger size wear debris. In He atmosphere, under all contact loads studied here, the specific wear rate shows a linear increasing trend with load, while the COF does not show any specific correlation with contact force. No significant change in wear rate or COF values in He atmosphere is observed for the sliding velocities examined here. However, in air environment, higher sliding velocities influence the formation of the compacted glaze layer and as a result, reduce friction and wear.
- On the surface of alloy 800HT, Fe-rich oxide $[(\text{Fe},\text{Ni})\text{Cr}_3\text{O}_4, \text{Fe}_3\text{O}_4]$ is found to be dominant with Cr_2O_3 . The very top surface in He and air is more Fe-rich. Although on the surface in He wear track $(\text{Fe},\text{Ni})\text{Cr}_3\text{O}_4$ spinel is found, on the wear track surface in air $(\text{Fe},\text{Ni})\text{Cr}_2\text{O}_3$ corundum is observed.
- Hardness of the oxide layer is much higher than that of the bulk of Inconel 617. This is due to formation of several hard oxide layers on top of Inconel 617 during aged process. The yield strength through of the oxide of aged Inconel is 10 GPa at RT reducing dramatically to 120 MPa at 600 °C. The high yield strength at RT is close to other metal oxides at RT.

Activation energy of oxide is much lower than the bulk of Inconel as less energy is needed for ion/voids to move through the boundaries. Creep deformation at high temperature is dependent on diffusion through the grain rather than dislocation climb dominant for the bulk of Inconel 617 and depend on oxygen diffusivity in the oxide. Based on the extracted properties, mechanical properties of the bulk cannot be used to measure and predict the tribological response of the surface which oxidized during holding stages.

- In He environment and under high temperature, both alloys demonstrated the tendency to get self-welded. A minimum aging duration and contact pressure are required for the alloys to get self-welded at high temperatures in the environment of He, which is in between 1 to 10 hours of static contact. Under the same aging duration and temperature, higher contact pressure accelerates the welding process and results in higher self-welding strength. In addition, under the same contact pressure and temperature, longer aging duration results in drastic increase in self-welding strength. A linear relationship is observed between the self-welding strength and the normalized bonding area for the same aging duration where, self-welding strength increases along with the normalized bonding area.
- In general, Inconel 617 exhibits higher tribological stability with lower COF and wear rate at 950 °C compared to alloy 800HT at 750 °C under the investigated contact pressures. Alloy 800HT shows slightly improved frictional performance under higher contact pressure and sliding speed, especially in air. But for Inconel 617, contact pressure or sliding velocity effect is concluded to be minimal.
- Both alloys did not show any variation in friction/wear behavior with surface roughness (R_q 0.3 and 0.04 μm) as well as three impurity concentrations He.
- The developed Ni/Cr multilayer coatings exhibited acceptable performance up to 400 °C under nanomechanical and nano-tribological experiments. But the same coatings on alloy substrates 800HT and Inconel 617 cannot protect the surface or improve the tribological properties under macro tribological experiment in realistic VHTR conditions.
- A fairly new surface treatment technique, laser shock peening (LSP) was applied on Inconel 617 surface. The LSPed samples resulted in 30% reduction in COF and 70% reduction in wear performance, indicating a promising path for the Inconel 617 surface property enhancement that needs in-depth study in the future.

- Overall, comparing Inconel 617 and alloy 800HT at their peak temperature, both exhibited very high friction but relatively low wear rate. Especially Inconel 617, being investigated under 950 °C exhibited well wear resistant performance with lower COF compared to 800HT. *The static and dynamic COF values and low wear rate of Inconel 617, make it more favorable than alloy 800HT for the HTGR/VHTR applications.*

REFERENCES

- [1] Cabet C, Terlain A, Lett P, Guétaz L, Gentzbittel JM. High temperature corrosion of structural materials under gas-cooled reactor helium. *Mater Corros* 2006;57:147–53. doi:10.1002/maco.200503901.
- [2] Richard N W. Kinetics of Gas Reactions and Environmental Degradation in NGNP Helium. 2006. doi:10.2172/911710.
- [3] Wright RN. Summary of Studies of Aging and Environmental Effects on Inconel 617 and Haynes 230 2006;27. doi:10.2172/911722.
- [4] Roy AK, Virupaksha V. Performance of alloy 800H for high-temperature heat exchanger applications. *Mater Sci Eng A* 2007;452–453:665–72. doi:10.1016/j.msea.2006.11.082.
- [5] Natesan K, Purohit A, Tam SW. Materials Behavior in HTGR Environments. 2003. doi:NUREG/CR-6824.
- [6] Hasan MH. Effects of mechanical and metallurgical variables on creep , fracture toughness and crack growth behavior of Alloy 617 2009;163.
- [7] Ren W, Swindeman R. A Review of Alloy 800H for Applications in the Gen IV Nuclear Energy Systems. ASME 2010 Press. Vessel. Pip. Conf. Vol. 6, Parts A B, ASME; 2010, p. 821–36. doi:10.1115/PVP2010-25278.
- [8] Wright JK, Lybeck NJ, Wright RN. Tensile Properties of Alloy 617 Bar Stock 2013.
- [9] Quadackers WJ, Schuster H. Corrosion of High Temperature Alloys in the Primary Circuit Helium of High Temperature Gas Cooled Reactors. -Part I: Theroetical Backround 1985;150:141–50.
- [10] Kim D, Jang C, Ryu WS. Oxidation characteristics and oxide layer evolution of Alloy 617 and Haynes 230 at 900 °c and 1100 °c. *Oxid Met* 2009;71:271–93. doi:10.1007/s11085-009-9142-5.
- [11] Jang C, Lee D, Kim D. Oxidation behaviour of an Alloy 617 in very high-temperature air and helium environments. *Int J Press Vessel Pip* 2008;85:368–77. doi:10.1016/j.ijpvp.2007.11.010.
- [12] Christ HJ, Künecke U, Meyer K, Sockel HG. High temperature corrosion of the nickel-based alloy Inconel 617 in helium containing small amounts of impurities. *Mater Sci Eng* 1987;87:161–8. doi:10.1016/0025-5416(87)90374-0.
- [13] Kim D, Sah I, Kim D, Ryu W, Jang C. High Temperature Oxidation Behavior of Alloy 617 and Haynes 230 in Impurity-Controlled Helium Environments. *Oxid Met* 2011;75:103–19. doi:10.1007/s11085-010-9223-5.
- [14] Langevoort JC, Sutherland I, Hanekamp LJ, Gellings PJ. On the oxide formation on stainless steels AISI 304 and incoloy 800H investigated with XPS. *Appl Surf Sci* 1987;28:167–79. doi:10.1016/0169-4332(87)90062-6.
- [15] Birol Y. High temperature sliding wear behaviour of Inconel 617 and Stellite 6 alloys. *Wear* 2010;269:664–71. doi:10.1016/j.wear.2010.07.005.
- [16] Birol Y. Inconel 617 and Stellite 6 alloys for tooling in thixoforming of steels. *Trans Nonferrous Met Soc China (English Ed)* 2010;20:1656–62. doi:10.1016/S1003-6326(09)60354-X.
- [17] Beech DJ, May R. Gas Reactor and Associated Nuclear Experience in The UK Relevant to High Temperature Reactor Engineering. *Proceedings, Oecd* 1999:57.
- [18] Corwin W. Nuclear Energy University Programs (NEUP) Fiscal Year (FY) 2015 Annual Planning Webinar-Advanced Structural Materials (RC-3) 2014:5.
- [19] Reed TB. Transparent Furnace. 3626154, 1971.
- [20] Rouillard F, Cabet C, Wolski K, Terlain A, Tabarant M, Pijolat M, et al. High temperature corrosion of a nickel base alloy by helium impurities. *J Nucl Mater* 2007;362:248–52. doi:10.1016/j.jnucmat.2007.01.049.
- [21] Pauschitz A, Roy M, Franek F. Mechanisms of sliding wear of metals and alloys at elevated temperatures. *Tribol Int* 2008;41:584–602. doi:10.1016/j.triboint.2007.10.003.

- [22] Inman IA, Rose SR, Datta PK. Development of a simple ‘ temperature versus sliding speed ’ wear map for the sliding wear behaviour of dissimilar metallic interfaces 2006;260:919–32. doi:10.1016/j.wear.2005.06.008.
- [23] Stott FH, Lin DS, Wood GC, Stevenson CW. The tribological behaviour of nickel and nickel-chromium alloys at temperatures from 20° to 800 °C. Wear 1976;36:147–74. doi:10.1016/0043-1648(76)90002-8.
- [24] Buckley DH. Adhesion and Wear Resistance of Materials. 1986. doi:NASA-TM-87239.
- [25] Zum Gahr K-H. Microstructure and wear of materials. Elsevier B.V; 1987.
- [26] Buckley DH. Friction, Wear, And Lubrication in Vavuum. NATIONAL AERONAUTICS AND SPACE ADMINISTRATION; 1971.
- [27] Stott FH, Lin DS, Wood GC, Stevenson CW. The Tribological Behavior of Nickel and Nickel-Chromium Alloys At Temperature From 20 to 800°C. Wear 1976;36:147–74.
- [28] Blau PJ. Elevated-temperature tribology of metallic materials. Tribol Int 2010;43:1203–8. doi:10.1016/j.triboint.2010.01.003.
- [29] Crone W, Cao G, Sridhara K. Assessment of Embrittlement of VHTR Structural Alloys in Impure Helium Environments. 2013. doi:10.2172/1087120.
- [30] Hrutkay K. Evolution of Microstructure of Haynes 230 and Inconel 617 Under Mechanical Testing At High Temperatures. University of South Carolina, 2013.
- [31] Jiang J, Stott FH, Stack MM. The effect of partial pressure of oxygen on the tribological behaviour of a nickel-based alloy, N80A, at elevated temperatures. Wear 1997;203–204:615–25. doi:10.1016/S0043-1648(96)07421-2.
- [32] Soda N, Kimura Y, Tanaka A. Wear of some F.C.C. metals during unlubricated sliding part IV: Effects of atmospheric pressure on wear. Wear 1977;43:165–74. doi:10.1016/0043-1648(77)90111-9.
- [33] Mishina H. Atmospheric characteristics in friction and wear of metals. Wear 1992;152:99–110. doi:10.1016/0043-1648(92)90207-O.
- [34] Yoshizawa H, Chen Y, Israelachililo J. Fundamental Mecbanisms of Interfacial Friction . 1 . Relation between Adbesion and Friction. Methods 1993;4128–40.
- [35] Kato K, Adachi K. Wear Mechanisms. 2001. doi:10.1201/9780849377877.ch7.
- [36] Chen LH, Rigney DA. Transfer during unlubricated sliding wear of selected metal systems. Wear 1985;105:47–61. doi:10.1016/0043-1648(85)90005-5.
- [37] A Pauschitz, M Roy FF. Identification of the Mechanisms of Wear during Sliding of Metallic Materials at Elevated 2004:721–30.
- [38] Cabet C, Chapovaloff J, Rouillard F, Girardin G, Kaczorowski D, Wolski K, et al. High temperature reactivity of two chromium-containing alloys in impure helium. J Nucl Mater 2008;375:173–84. doi:10.1016/j.jnucmat.2007.11.006.
- [39] Meschter PJ, Grabke HJ. Kinetics of the water-gas shift reaction on an “FeO” surface. Metall Trans B 1979;10:323–9. doi:10.1007/BF02652502.
- [40] M. Hansel, W. J. Quadackers DJY. Role of water vapor in chromia-scale growth at low oxygen partial pressure. Oxid Met 2003;59:285–300. doi:10.1023/A:1023040010859.
- [41] Pieraggi B, Rolland C, Bruckel P. Morphological characteristics of oxide scales grown on H11 steel oxidised in dry or wet air. Mater High Temp 2005;22:61–8. doi:10.1179/mht.2005.007.
- [42] Choudhry KI, Mahboubi S, Botton GA, Kish JR, Svishchev IM. Corrosion of engineering materials in a supercritical water cooled reactor: Characterization of oxide scales on Alloy 800H and stainless steel 316. Corros Sci 2015;100:222–30. doi:10.1016/j.corsci.2015.07.035.
- [43] Bsat S, Huang X. Corrosion Behaviour of Alloy 800H in Low Density Superheated Steam. ISIJ Int 2016;56:1067–75. doi:10.2355/isijinternational.ISIJINT-2015-651.
- [44] Behnamian Y, Mostafaei A, Kohandehghan A, Amirkhiz BS, Serate D, Sun Y, et al. A comparative study of oxide scales grown on stainless steel and nickel-based superalloys in ultra-high temperature supercritical water at 800 °C. Corros Sci 2016;106:188–207. doi:10.1016/j.corsci.2016.02.004.

- [45] Zeng Z, Natesan K, Grimsditch M. Effect of Oxide Scale Compositions on Metal Dusting Corrosion of Fe-Based Alloys. *CORROSION* 2004;60:632–42. doi:10.5006/1.3287838.
- [46] Wang W, Ding Z, Zhao X, Wu S, Li F, Ming Yue, et al. Microstructure and magnetic properties of MFe_2O_4 ($M = Co, Ni, \text{ and } Mn$) ferrite nanocrystals prepared using colloid mill and hydrothermal method. *J Appl Phys* 2015;117:1–5. doi:10.1063/1.4917463.
- [47] Bates HGA. Corrosion behavior of high-temperature alloys during exposure for times up to 10,000 h in prototype nuclear process helium at 700 to 900 °C. *Nucl Technol* 1984;66:415–28. doi:10.13182/NT84-A33444.
- [48] Cappelaere M, Perrot M, Sannier J. Behavior of Metallic Materials Between 550 and 870°C in High-Temperature Gas-Cooled Reactor Helium Under Pressures of 2 and 50 bar. *Nucl Technol* 1984;66:465–78. doi:10.13182/NT84-A33447.
- [49] Tan L, Allen TR, Yang Y. Corrosion behavior of alloy 800H ($Fe - 21Cr - 32Ni$) in supercritical water. *Corros Sci* 2011;53:703–11. doi:10.1016/j.corsci.2010.10.021.
- [50] Erdemir A. A crystal-chemical approach to lubrication by solid oxides. *Tribol Lett* 2000;8:97–102. doi:10.1023/A:1019183101329.
- [51] Srisrual A. Photoelectrochemical characterization of thermal oxide developed on metal and model alloys Caractérisation photoélectrochimique d ' oxydes thermiques développés sur métaux et alliages modèles 2015.
- [52] Srisrual A, Coindeau S, Galerie A, Petit JP, Wouters Y. Identification by photoelectrochemistry of oxide phases grown during the initial stages of thermal oxidation of AISI 441 ferritic stainless steel in air or in water vapour. *Corros Sci* 2009;51:562–8. doi:10.1016/j.corsci.2008.12.002.
- [53] Renusch D. Transient oxidation in Fe-Cr-Ni alloys: A raman-scattering study. *Oxid Met* 1996;46:365–81. doi:10.1007/BF01048636.
- [54] Srisrual A, Petit JP, Wouters Y, Galerie A. The effect of water vapor on thermal oxide grown on inconel 690. *Appl Mech Mater* 2014;670–671:74–81. doi:10.4028/www.scientific.net/AMM.670-671.74.
- [55] Srisrual A, Petit JP, Wouters Y, Pascal C, Galerie A. Photoelectrochemical investigations on individual ferritic and austenitic grains of a duplex stainless steel oxidized in water vapour. *Mater High Temp* 2011;28:349–54. doi:10.3184/096034011X13190163136192.
- [56] Edwards MW, McIntyre NS. Gas phase initial oxidation of incoloy 800 surfaces. *Oxid Met* 2013;79:179–200. doi:10.1007/s11085-012-9316-4.
- [57] Abraham GJ, Bhambroo R, Kain V, Shekhar R, Dey GK, Raja VS. Electrochemical characterization of oxide film formed at high temperature on Alloy 690. *Nucl Eng Des* 2012;243:69–75. doi:10.1016/j.nucengdes.2011.11.018.
- [58] McCarty KF, Boehme DR. A Raman study of the systems $Fe_{3-x}Cr_xO_4$ and $Fe_{2-x}Cr_xO_3$. *J Solid State Chem* 1989. doi:10.1016/0022-4596(89)90245-4.
- [59] Zeng Z, Natesan K, Grimsditch M. Effect of Oxide Scale Compositions on Metal Dusting Corrosion of Fe-Based Alloys 2004:632–42.
- [60] Srisrual A, Pitaksakorn K, Promdirek P. Influence of Water Vapor on Oxide Scale Morphology of Incoloy800HT at 850°C. *Appl Mech Mater* 2018;875:36–40. doi:10.4028/www.scientific.net/amm.875.36.
- [61] Sakaba N, Hamamoto S, Takeda Y. Helium chemistry for very high temperature reactors. *J Nucl Sci Technol* 2010;47:269–77.
- [62] Stanford MK. A Review of Tribomaterial Technology for Space Nuclear Power Systems. Program 2007.
- [63] Chatterjee A, Polycarpou AA, Abelson JR, Bellon P. Nanoscratch study of hard HfB_2 thin films using experimental and finite element techniques. *Wear* 2010;268:677–85. doi:10.1016/j.wear.2009.11.001.
- [64] Chechenin NG, Bøttiger J, Krog JP. Nanoindentation of amorphous aluminum oxide films I. The influence of the substrate on the plastic properties. *Thin Solid Films* 1995;261:219–27.

- [65] Pharr GM, Oliver WC. Measurement of thin film mechanical properties using nanoindentation. *Mrs Bull* 1992;17:28–33.
- [66] Humood M, Beheshti A, Meyer JL, Polycarpou AA. Normal impact of sand particles with solar panel glass surfaces. *Tribol Int* 2016;102:237–48.
- [67] Pang X, Gao K, Volinsky AA. Microstructure and mechanical properties of chromium oxide coatings. *J Mater Res* 2007;22:3531–7.
- [68] Humood M, Beheshti A, Polycarpou AA. Surface reliability of annealed and tempered solar protective glasses: Indentation and scratch behavior. *Sol Energy* 2017;142:13–25. doi:10.1016/j.solener.2016.12.011.
- [69] Lee J, Beheshti A, Polycarpou AA. Rough Surface Normal Nanocontact Stiffness: Experimental Measurements and Rough Surface Contact Model Predictions. *J Appl Mech Trans ASME* 2017;84. doi:10.1115/1.4035524.
- [70] Su C, Herbert EG, Sohn S, LaManna JA, Oliver WC, Pharr GM. Measurement of power-law creep parameters by instrumented indentation methods. *J Mech Phys Solids* 2013;61:517–36. doi:10.1016/j.jmps.2012.09.009.
- [71] Cordova ME, Shen Y-L. Indentation versus uniaxial power-law creep: a numerical assessment. *J Mater Sci* 2015;50:1394–400.
- [72] Kang J, Becker AA, Sun W. Determination of elastic and viscoplastic material properties obtained from indentation tests using a combined finite element analysis and optimization approach. *Proc Inst Mech Eng Part L J Mater Des Appl* 2015;229:175–88.
- [73] Takagi H, Dao M, Fujiwara M. Prediction of the constitutive equation for uniaxial creep of a power-law material through instrumented microindentation testing and modeling. *Mater Trans* 2014;55:275–84.
- [74] Gibson JS-L, Roberts SG, Armstrong DEJ. High temperature indentation of helium-implanted tungsten. *Mater Sci Eng A* 2015;625:380–4.
- [75] Wang H, Dhiman A, Ostergaard HE, Zhang Y, Siegmund T, Kruzic JJ, et al. Nanoindentation based properties of Inconel 718 at elevated temperatures: A comparison of conventional versus additively manufactured samples. *Int J Plast* 2019;120:380–94. doi:10.1016/j.ijplas.2019.04.018.
- [76] Zhang Y, Mohanty DP, Seiler P, Siegmund T, Kruzic JJ, Tomar V. High temperature indentation based property measurements of IN-617. *Int J Plast* 2017;96:264–81. doi:10.1016/j.ijplas.2017.05.007.
- [77] Wu ZF, Wang XD, Cao QP, Zhao GH, Li JX, Zhang DX, et al. Microstructure characterization of $\text{Al}_x\text{Co}_1\text{Cr}_1\text{Cu}_1\text{Fe}_1\text{Ni}_1(x = 0 \text{ and } 2.5)$ high-entropy alloy films. *J Alloys Compd* 2014;609:137–42. doi:10.1016/j.jallcom.2014.04.094.
- [78] Frost HJ, Ashby MF. Deformation mechanism maps: the plasticity and creep of metals and ceramics. Pergamon press; 1982.
- [79] Bower AF, Fleck NA, Needleman A, Ogbonna N. Indentation of a power law creeping solid. *Proc R Soc Lond A* 1993;441:97–124.
- [80] Dean J, Bradbury A, Aldrich-Smith G, Clyne TW. A procedure for extracting primary and secondary creep parameters from nanoindentation data. *Mech Mater* 2013;65:124–34.
- [81] Dean J, Wheeler JM, Clyne TW. Use of quasi-static nanoindentation data to obtain stress--strain characteristics for metallic materials. *Acta Mater* 2010;58:3613–23.
- [82] Palma T, Munther M, Damasus P, Salari S, Beheshti A, Davami K. Multiscale mechanical and tribological characterizations of additively manufactured polyamide 12 parts with different print orientations. *J Manuf Process* 2019;40:76–83.
- [83] Monclús MA, Lotfian S, Molina-Aldareguía JM. Tip shape effect on hot nanoindentation hardness and modulus measurements. *Int J Precis Eng Manuf* 2014;15:1513–9. doi:10.1007/s12541-014-0499-2.
- [84] Phani PS, Oliver WC, Pharr GM. On the Measurement of Power Law Creep Parameters from Instrumented Indentation. *JOM* 2017;69:2229–36.

- [85] Phani PS, Oliver WC. A direct comparison of high temperature nanoindentation creep and uniaxial creep measurements for commercial purity aluminum. *Acta Mater* 2016;111:31–8. doi:10.1016/j.actamat.2016.03.032.
- [86] Oliver WC, Pharr GM. An improved technique for determining hardness and elastic modulus using load and displacement sensing indentation experiments. *J Mater Res* 1992;7:1564–83.
- [87] Feng G, Ngan AHW. Effects of creep and thermal drift on modulus measurement using depth-sensing indentation. *J Mater Res* 2002;17:660–8.
- [88] Lee H, Chen Y, Claisse A, Schuh CA. Finite element simulation of hot nanoindentation in vacuum. *Exp Mech* 2013;53:1201–11.
- [89] Wheeler JM, Armstrong DEJ, Heinz W, Schwaiger R. High temperature nanoindentation: The state of the art and future challenges. *Curr Opin Solid State Mater Sci* 2015;19:354–66. doi:10.1016/j.cossms.2015.02.002.
- [90] Smith M. ABAQUS/Standard User's Manual, Version 2017. Simulia; 2017.
- [91] Kichenin J. Comportement thermomécanique du polyéthylène. Application aux structures gazières. Palaiseau, Ecole polytechnique, 1992.
- [92] Liu H, Tao J, Xu J, Chen Z, Gao Q. Corrosion and tribological behaviors of chromium oxide coatings prepared by the glow-discharge plasma technique. *Surf Coatings Technol* 2009;204:28–36. doi:10.1016/j.surfcoat.2009.06.020.
- [93] Smith GD, Yates DH. Optimization of the Fatigue Properties of INCONEL alloy 617. ASME 1991 Int. Gas Turbine Aeroengine Congr. Expo., 1991, p. V005T12A009--V005T12A009.
- [94] Corporation SM. Inconel Alloy 617. *Spec Met* 2015:Inconel Alloy 617.
- [95] Shackelford JF, Han Y-H, Kim S, Kwon S-H. CRC materials science and engineering handbook. CRC press; 2016.
- [96] Petersen KE. Silicon as a mechanical material. *Proc IEEE* 1982;70:420–57.
- [97] Sakamoto S, Yoshinaka M, Hirota K, Yamaguchi O. Fabrication, mechanical properties, and electrical conductivity of Co₃O₄ ceramics. *J Am Ceram Soc* 1997;80:267–8.
- [98] Varghese B, Zhang Y, Dai L, Tan VBC, Lim CT, Sow C-H. Structure-mechanical property of individual cobalt oxide nanowires. *Nano Lett* 2008;8:3226–32.
- [99] Evans B, Goetze C. The temperature variation of hardness of olivine and its implication for polycrystalline yield stress. *J Geophys Res Solid Earth* 1979;84:5505–24.
- [100] Coble RL. A model for boundary diffusion controlled creep in polycrystalline materials. *J Appl Phys* 1963;34:1679–82. doi:10.1063/1.1702656.
- [101] Lifshitz IM. On the theory of diffusion-viscous flow of polycrystalline bodies. *Sov Phys JETP* 1963;17:909.
- [102] Lau JH. Solder joint reliability: theory and applications. Springer Science & Business Media; 1991.
- [103] Schneider K, Rekas M. High Temperature Creep of Metal Oxides. *Creep* 2018. doi:10.5772/intechopen.70876.
- [104] Bobji MS, Ramanujan CS, Pethica JB, Inkson BJ. A miniaturized TEM nanoindenter for studying material deformation in situ. *Meas Sci Technol* 2006;17:1324–9. doi:10.1088/0957-0233/17/6/006.
- [105] Anantheshwara K. In situ transmission electron microscope triboprobe for tribological studies of materials at nanoscale. Indian Institute of Science, 2011. doi:10.1.1.629.6462.
- [106] Moschi S, Grau P, Berg G. Nanotribological Measurements on Sol-Gel Derived Silica Films. *MRS Proc* 1998;522:415. doi:10.1557/PROC-522-415.
- [107] Eriten M, Polycarpou AA, Bergman LA. A physics-based friction model and integration to a simple dynamical system. *J Vib Acoust Trans ASME* 2012;134:1–9. doi:10.1115/1.4006182.
- [108] Wu A, Shi X, Polycarpou AA. An elastic-plastic spherical contact model under combined normal and tangential loading. *J Appl Mech* 2012;79:51001.
- [109] Brizmer V, Kligerman Y, Etsion I. Elastic--plastic spherical contact under combined normal and tangential loading in full stick. *Tribol Lett* 2007;25:61–70.
- [110] Malamut S, Kligerman Y, Etsion I. The effect of dwell time on the static friction in creeping elastic-

- plastic polymer spherical contact. *Tribol Lett* 2009;35:159–70.
- [111] Jackson RL, Green I. A statistical model of elasto-plastic asperity contact between rough surfaces. *Tribol Int* 2006;39:906–14. doi:10.1016/j.triboint.2005.09.001.
- [112] Greenwood JA, Williamson JBP. Contact of nominally flat surfaces. *Proc R Soc London Ser A Math Phys Sci* 1966;295:300–19. doi:10.1098/rspa.1966.0242.