




# Corrosion of the 304L stainless steel produced by the laser engineered net shape (LENS) technique

Michael A. Melia, Rebecca F. Schaller, Hai-Duy A. Nguyen, Jason M. Taylor, Jeffrey Rodelas, and Eric J. Schindelholz

## Abstract

In recent years a desire to rapidly prototype complex metallic parts has driven the advancement of metal additive manufacturing (AM). Powder bed selective laser melting (SLM) and laser engineered net shape (LENS) have emerged as prevalent techniques for producing a wide range of complex metal components. The microstructure and surfaces of these materials are considerably different than their conventionally processed counterparts, resultant from rapid, directional solidification, and dynamic thermal cycling associated with layer-wise melting. This presentation will investigate and compare the corrosion behavior of 304L stainless steel produced by typical processes (wrought) and two varieties of LENS processes, high power LENS (HPLENS) and low power LENS (LPLENS). An emphasis will be on understanding the relationship between characteristic microstructural features of the AM materials and localized corrosion behavior in chloride media.

## Background: The LENS technique

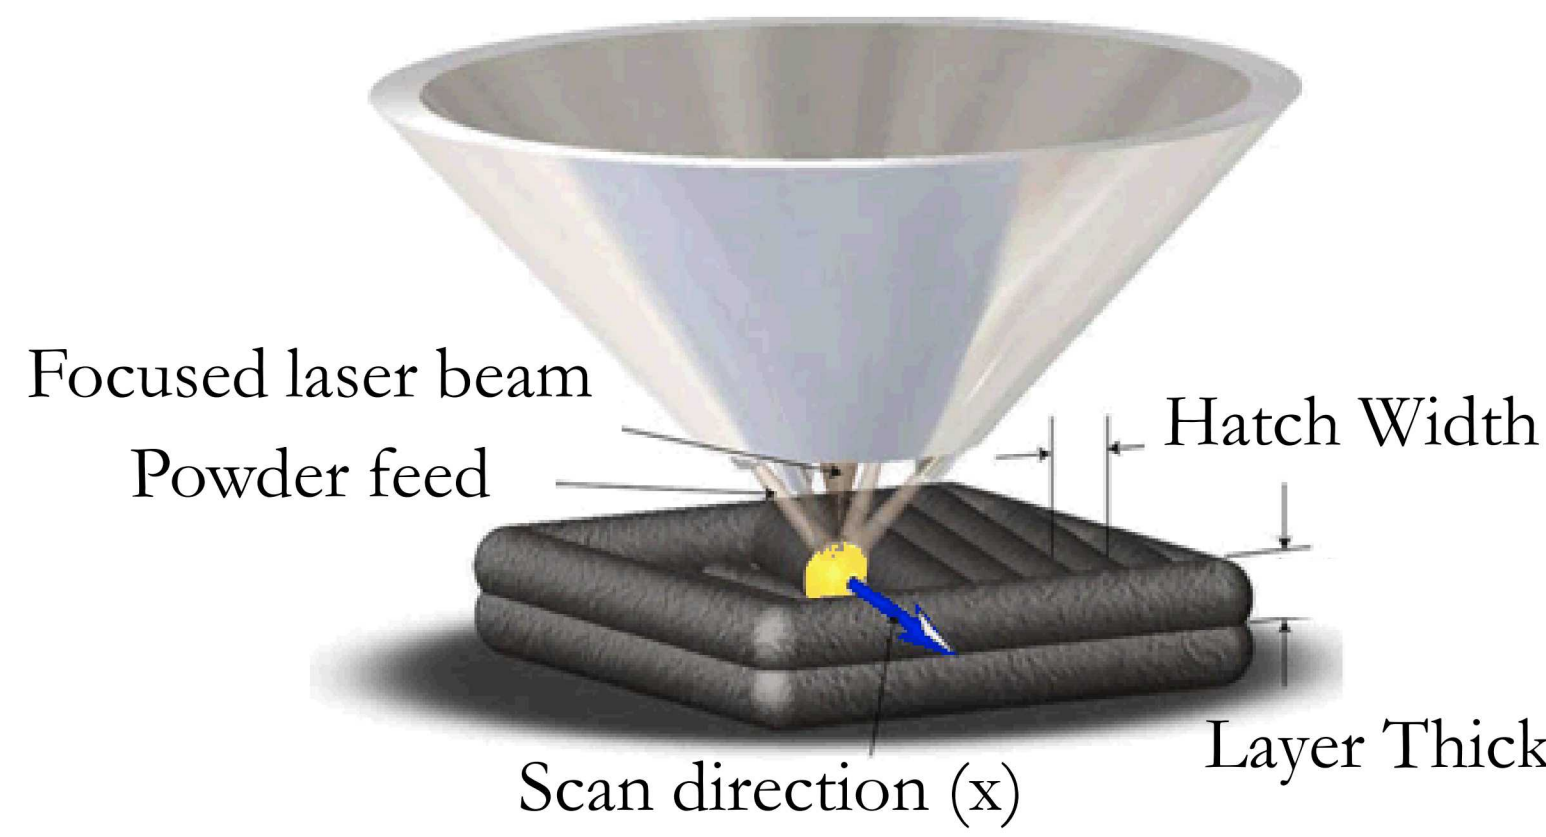


Parameter	380 (LPLENS)	3800 (HPLENS)
Laser Power (W)	380 (LPLENS)	3800 (HPLENS)
Travel Speed (mm/min)	762	508
Powder Feed Rate (g/min)	6.3	23
Hatch Spacing (mm)	0.46	2
Layer Thickness (mm)	0.3	1.25

**Starting Powder**  
Ø = 45-90 µm  
N<sub>2</sub>-atomized single use (not recycled)


HPLENS

LPLENS

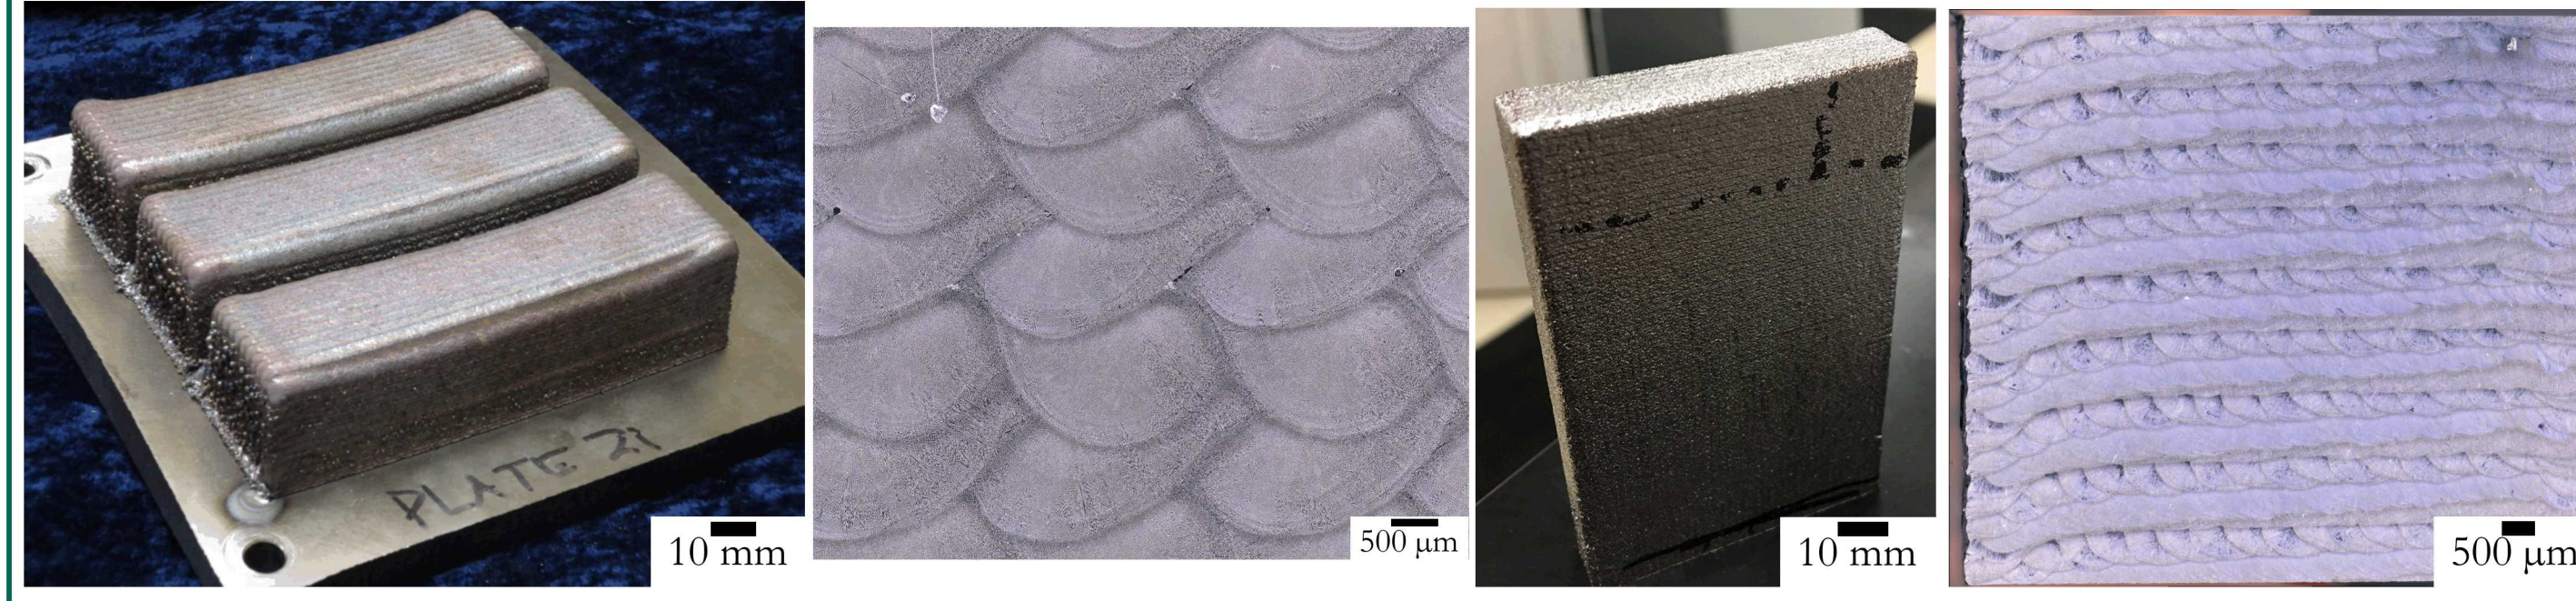

Composition (wt%)	Cr	Ni	Mn	Si	Mo	Cu	N	P	C	S	O	PREN
Starting powder	19.1	10.4	1.6	0.50	0.04	0.03	0.089	0.006	0.015	0.006	0.017	20.8
LPLENS	18.62	9.86	1.48	0.59	0.004	0.01	0.044	0.01	0.011	0.005	0.018	19.3
HPLENS	19.22	10.06	1.45	0.57	0.042	0.034	0.087	0.008	0.012	0.004	0.031	20.8
Wrought 304L	18.43	8.26	1.76	0.25	0.31	0.56	0.073	0.03	0.024	<0.001	0.009	20.6


## Microstructural characterization

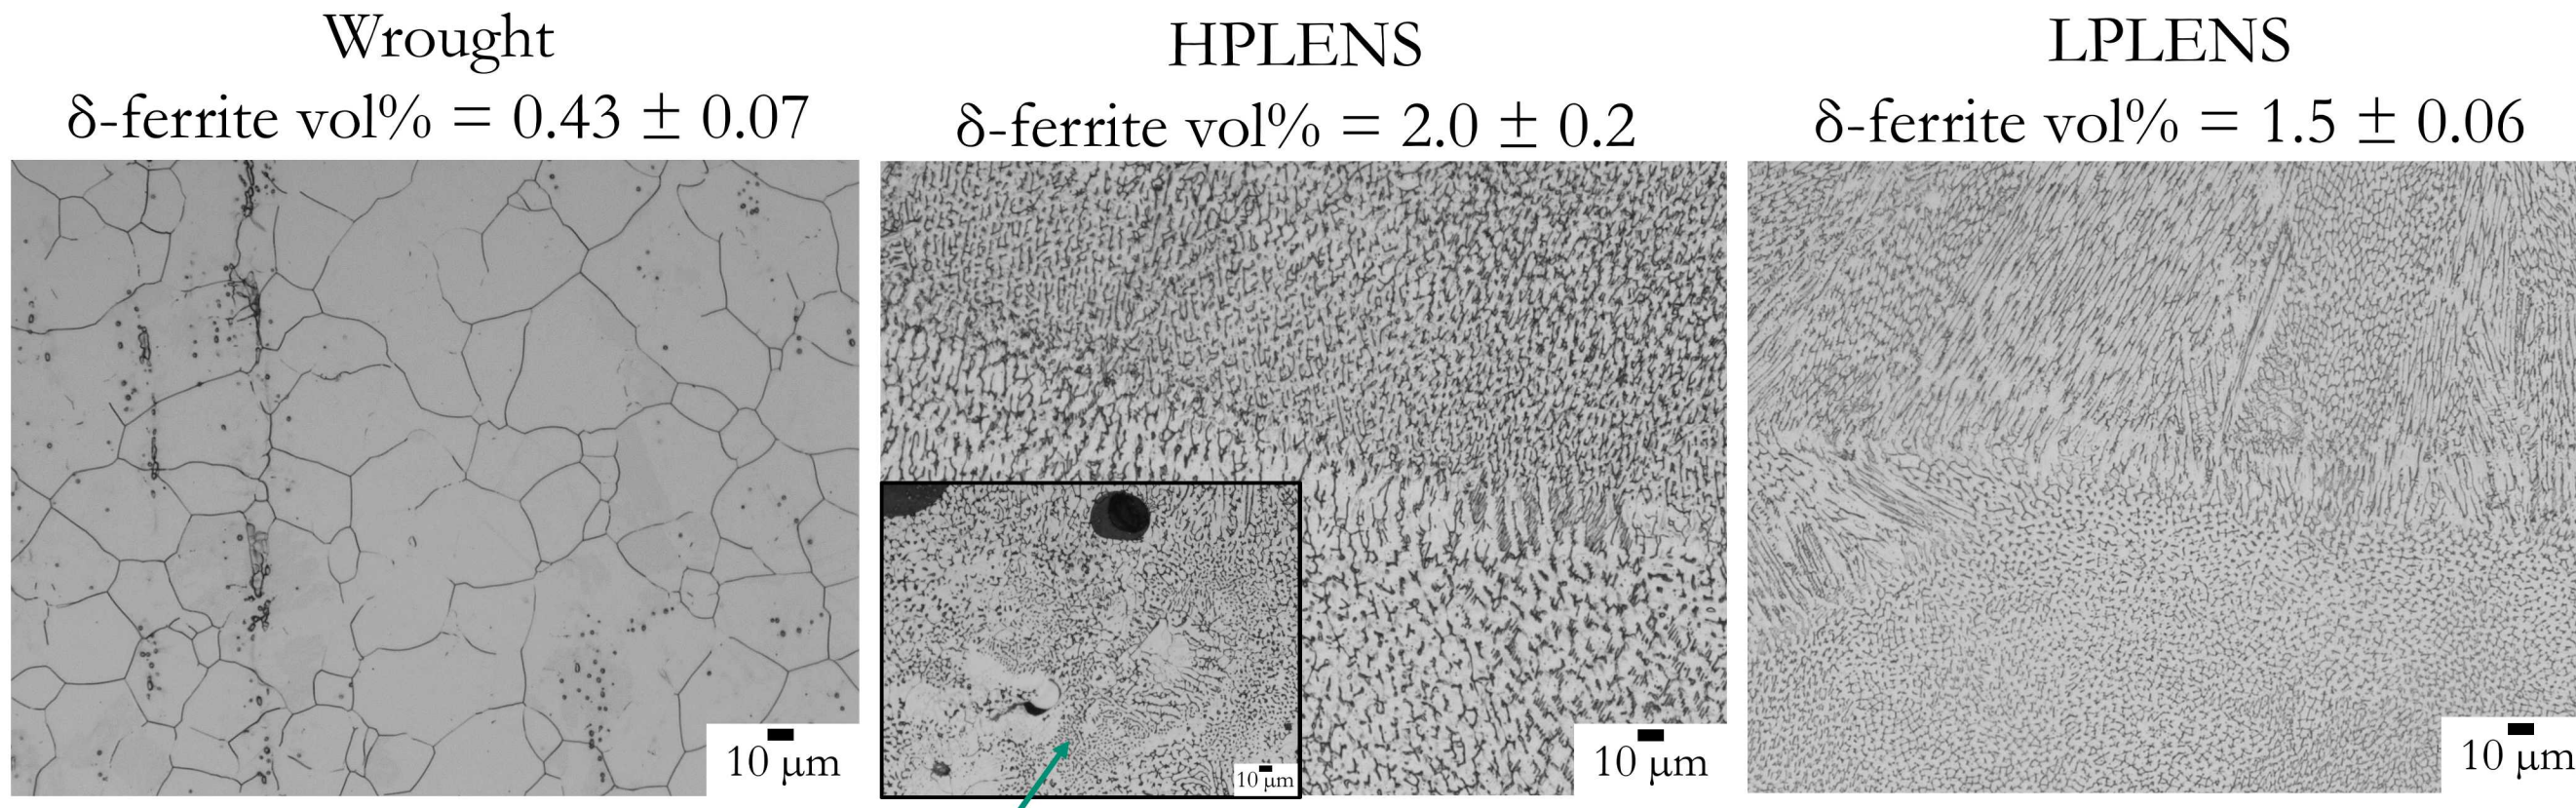


Microstructure near fusion pores

Typical morphology of pores

WDS elemental maps

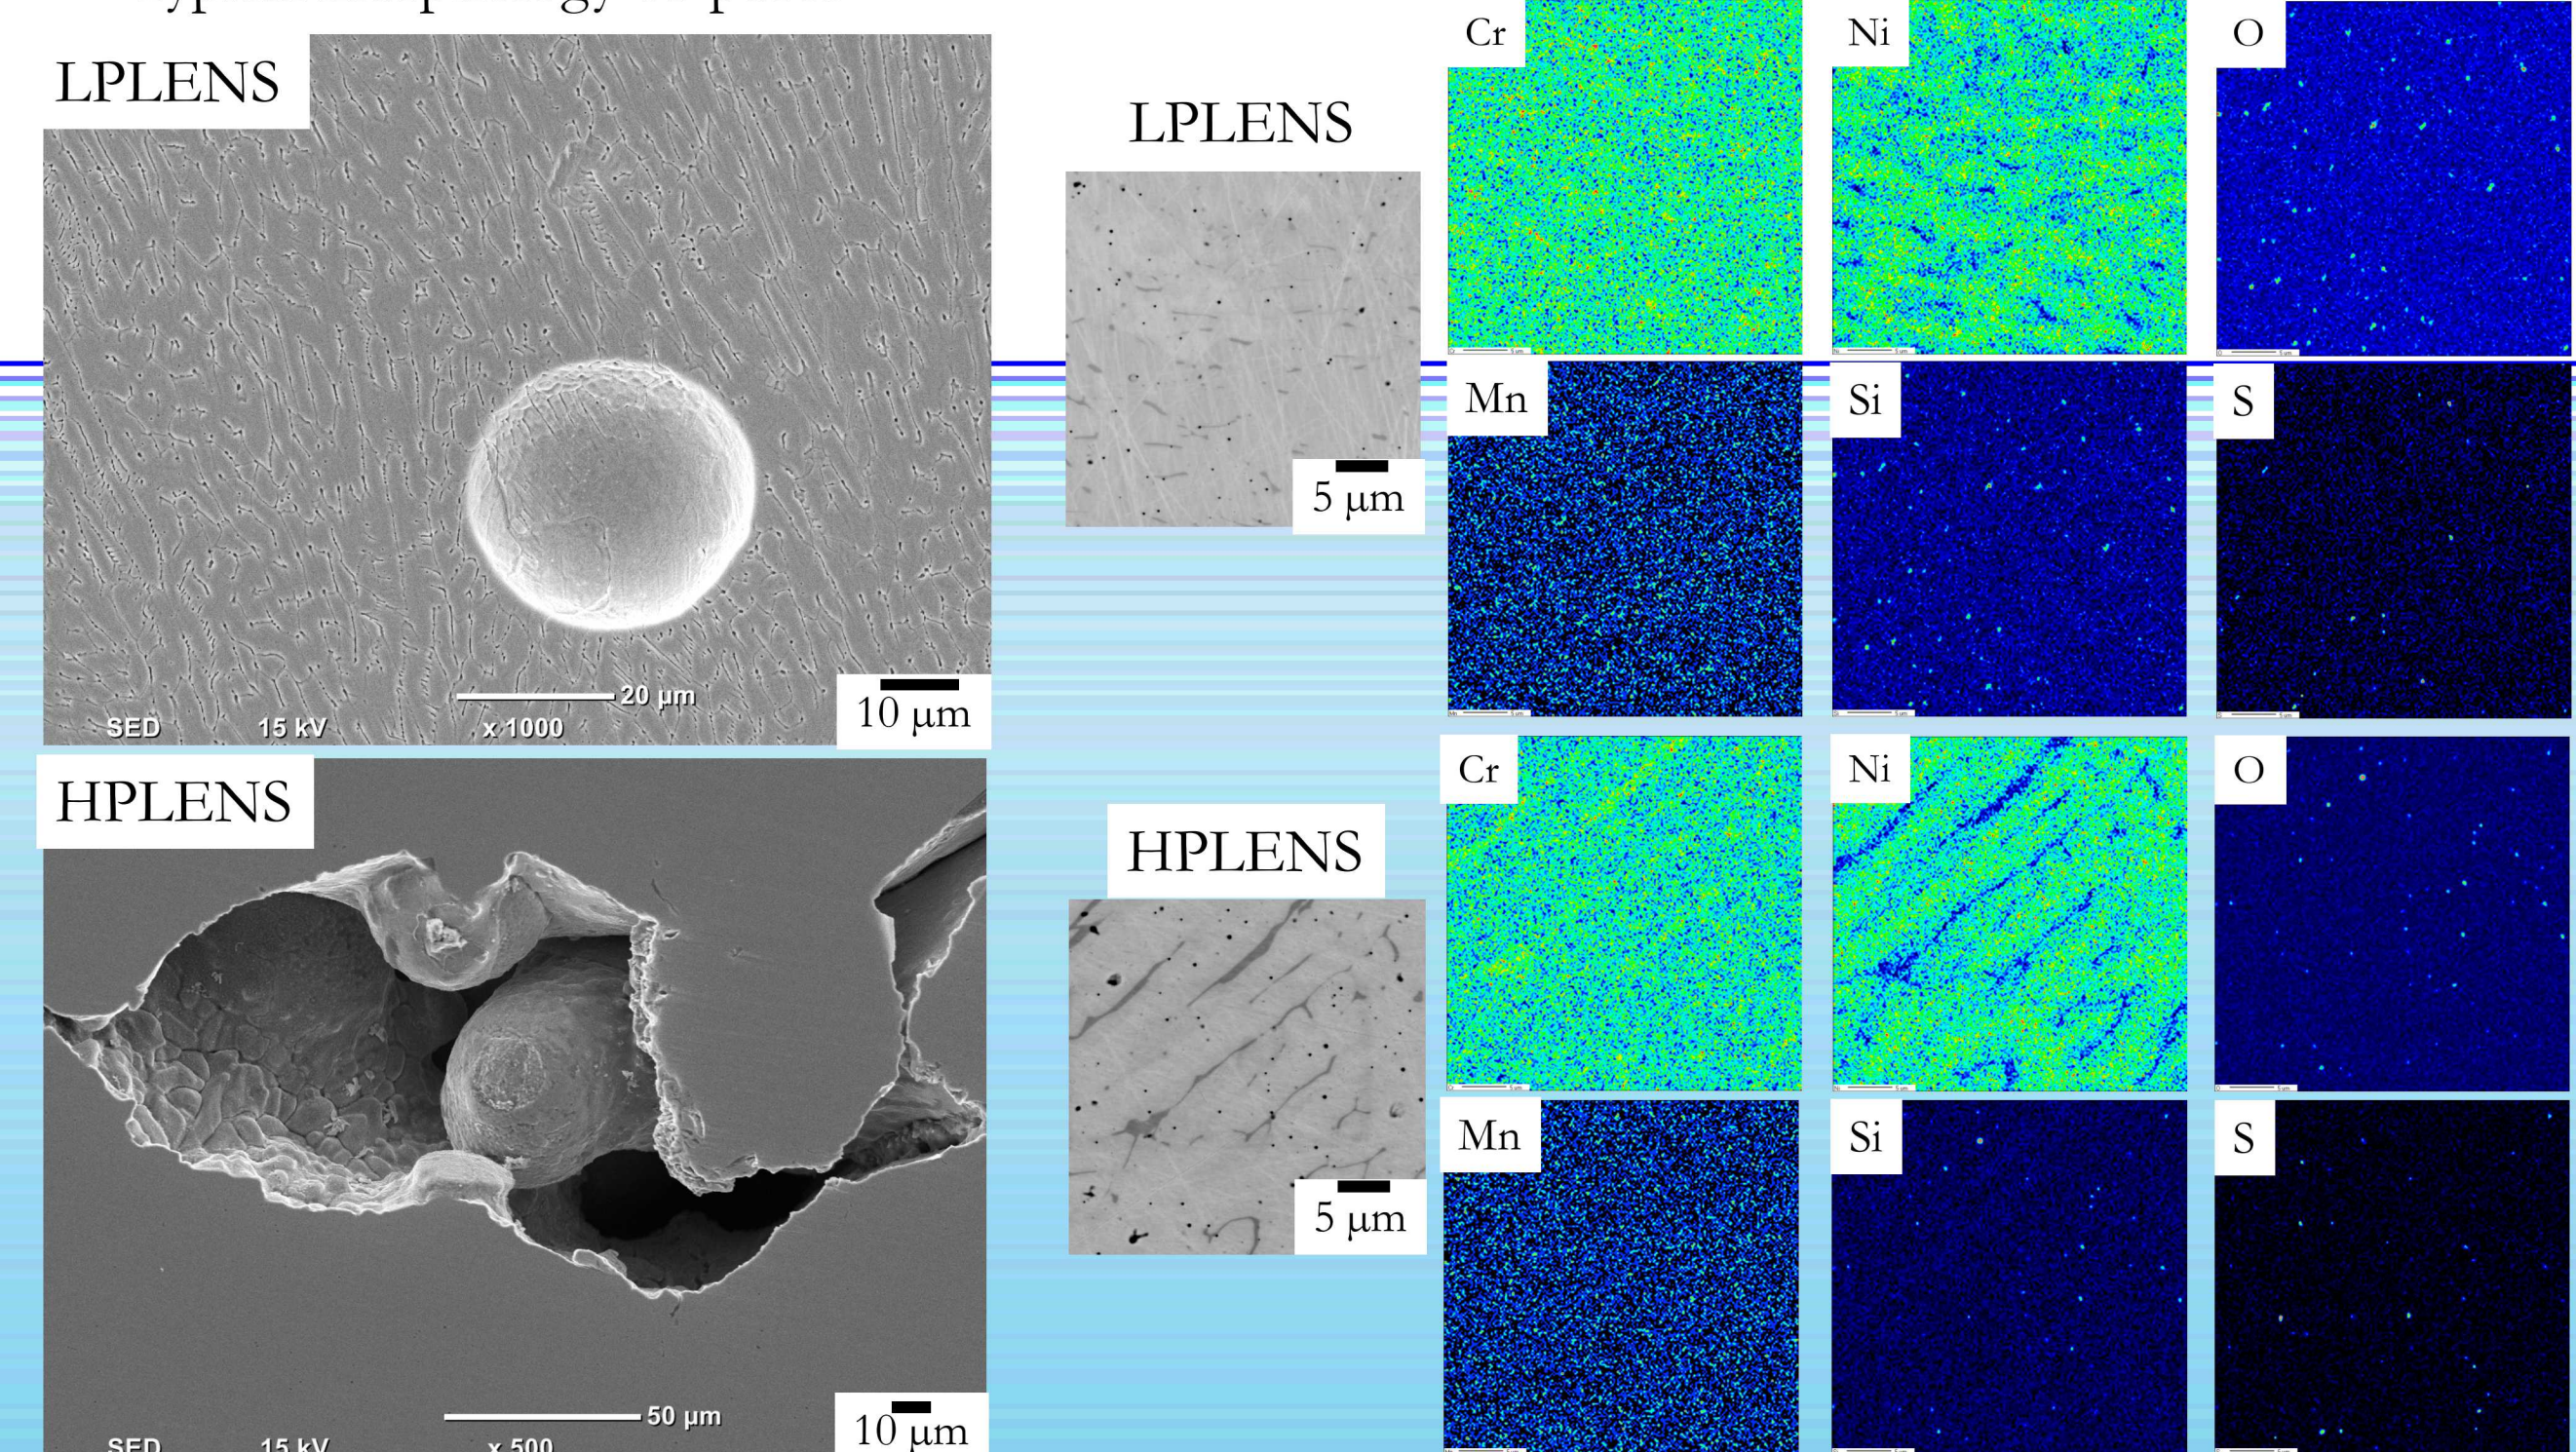


## Cyclic potentiodynamic polarization (CPP) measurements in quiescent 0.6 M NaCl solution – scan rate = 1 mV/sec.

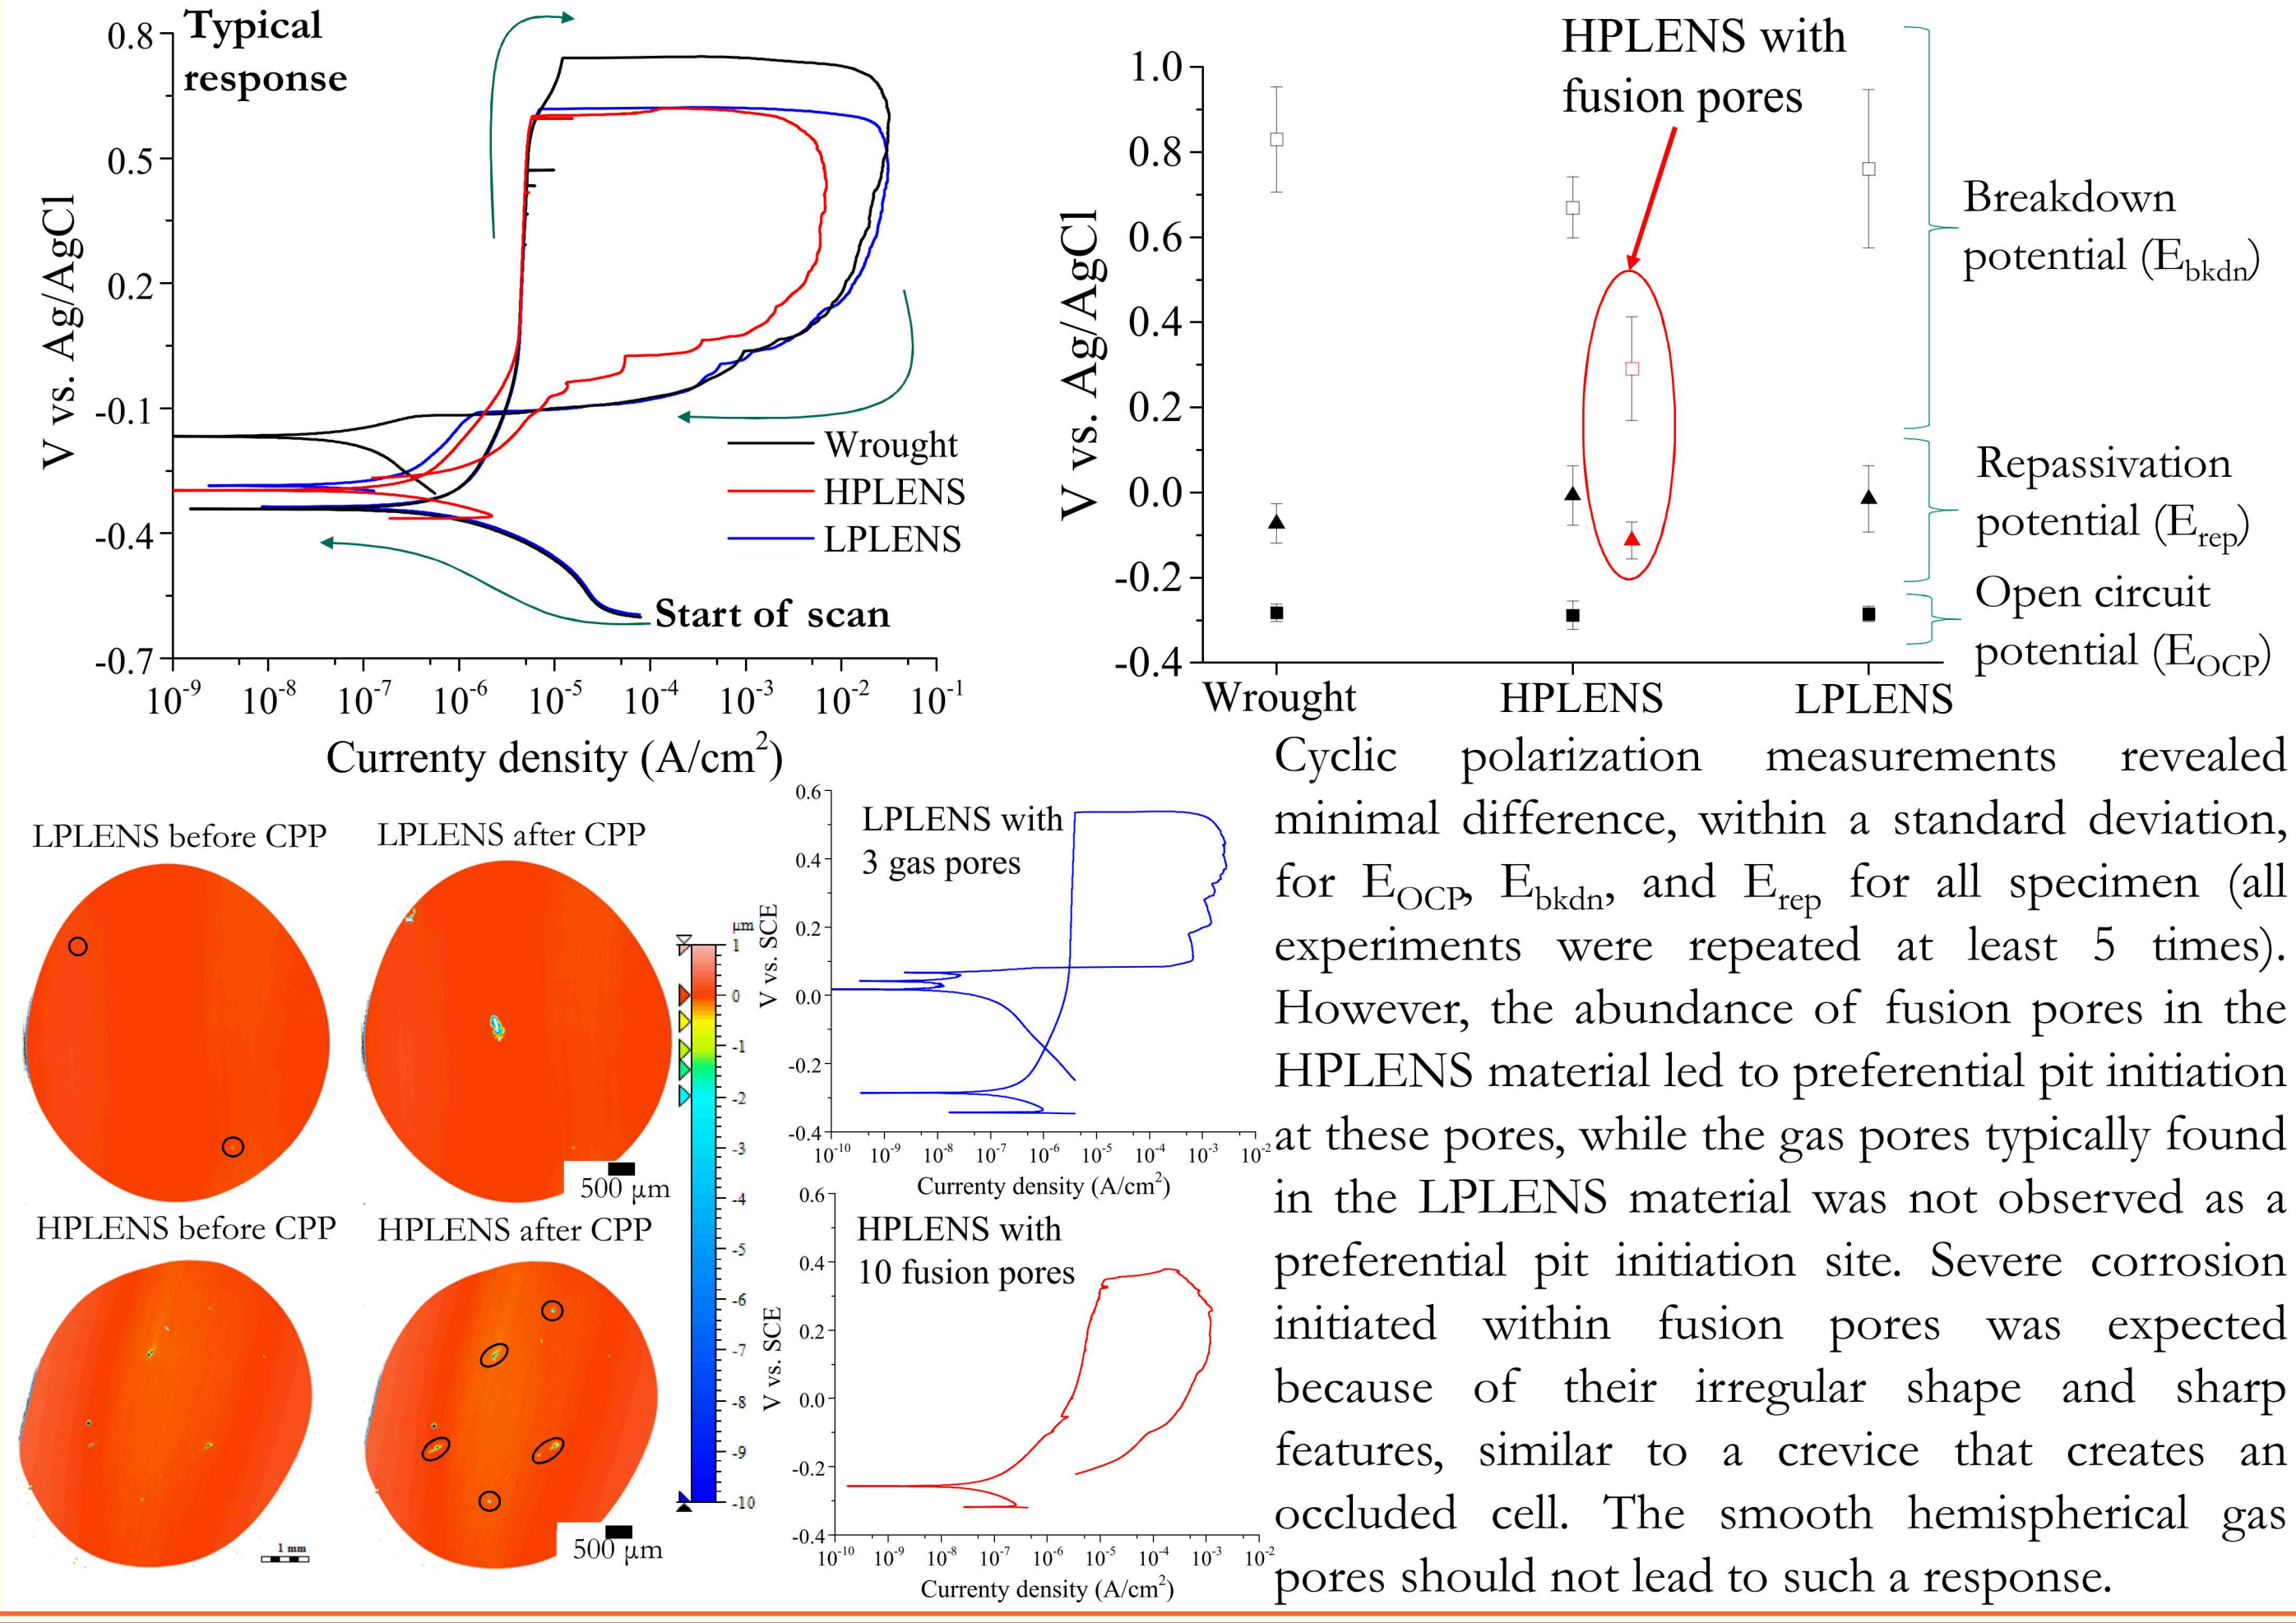

Cyclic polarization measurements revealed minimal difference, within a standard deviation, for  $E_{OCp}$ ,  $E_{bkdn}$ , and  $E_{rep}$  for all specimen (all experiments were repeated at least 5 times). However, the abundance of fusion pores in the HPLENS material led to preferential pit initiation at these pores, while the gas pores typically found in the LPLENS material was not observed as a preferential pit initiation site. Severe corrosion initiated within fusion pores was expected because of their irregular shape and sharp features, similar to a crevice that creates an occluded cell. The smooth hemispherical gas pores should not lead to such a response.


## Pit initiation using potentiostatic control at 0.60 V vs. Ag/AgCl

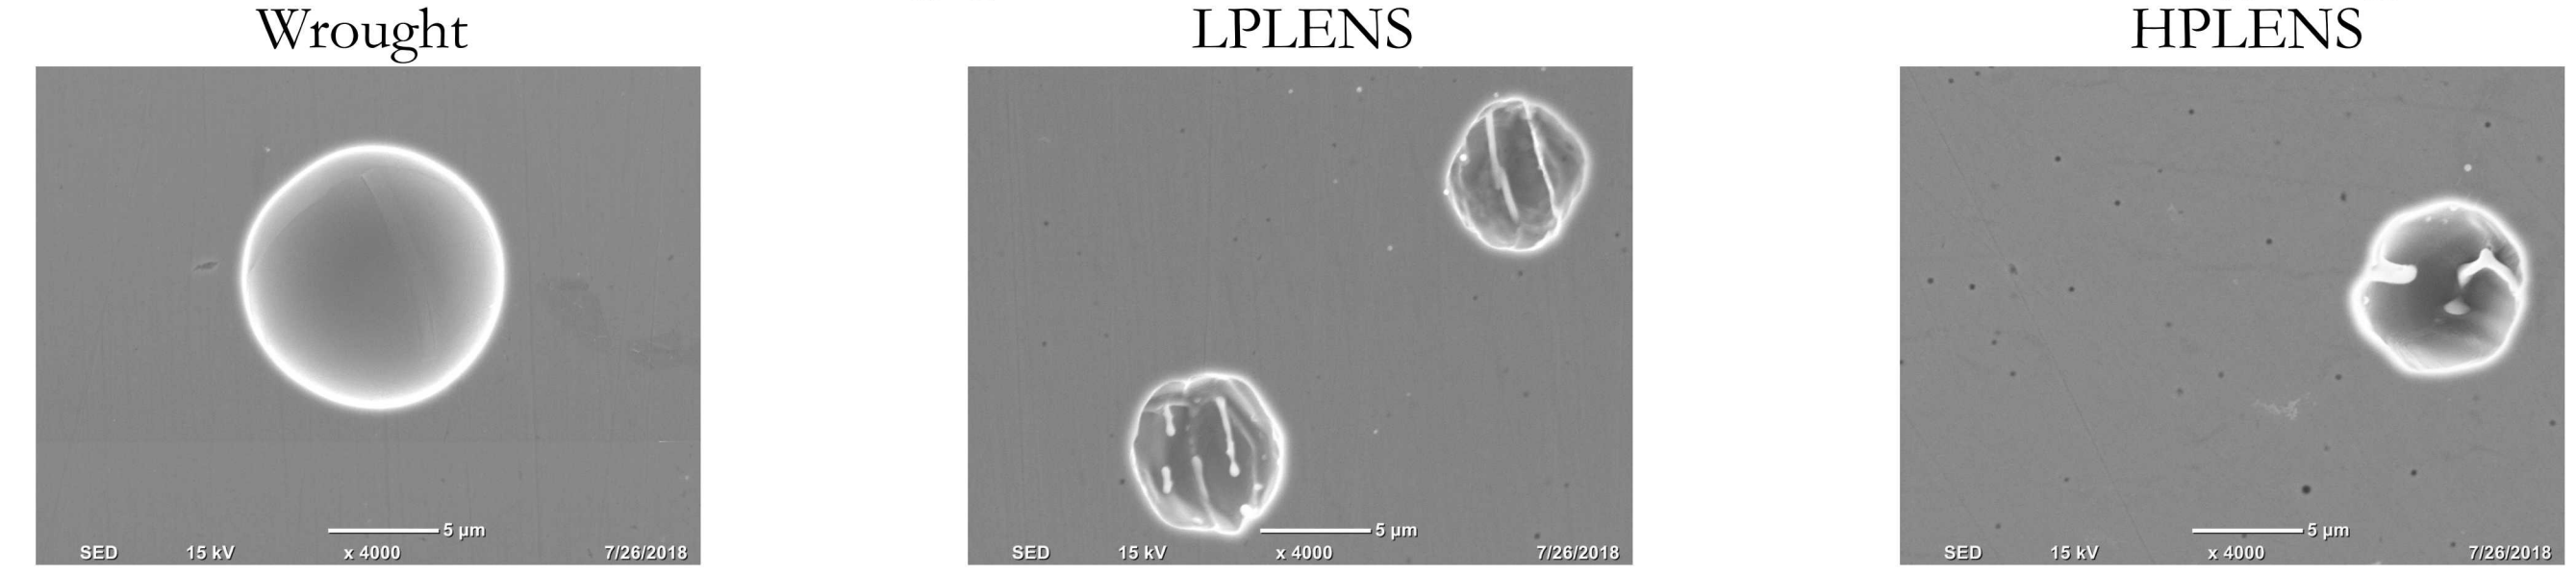

Initiation of pits under potentiostatic control did not show any clear preferred initiation sites, however the pit morphology was noticeably different when comparing wrought to LENS material. At early stages of pitting the wrought material showed very smooth, hemispherical pits which appeared to see little influence from different crystallographic oriented grains. The LENS material consistently observed a rougher and more irregular hemispherical shaped pit in addition to the presence of delta ferrite that was minimally corroded due to the higher Cr content in this phase.

## Double loop electrochemical potentiokinetic reactivation (DLEPR)

measurements in quiescent 0.5 M H<sub>2</sub>SO<sub>4</sub> + 0.005 M KSCN.

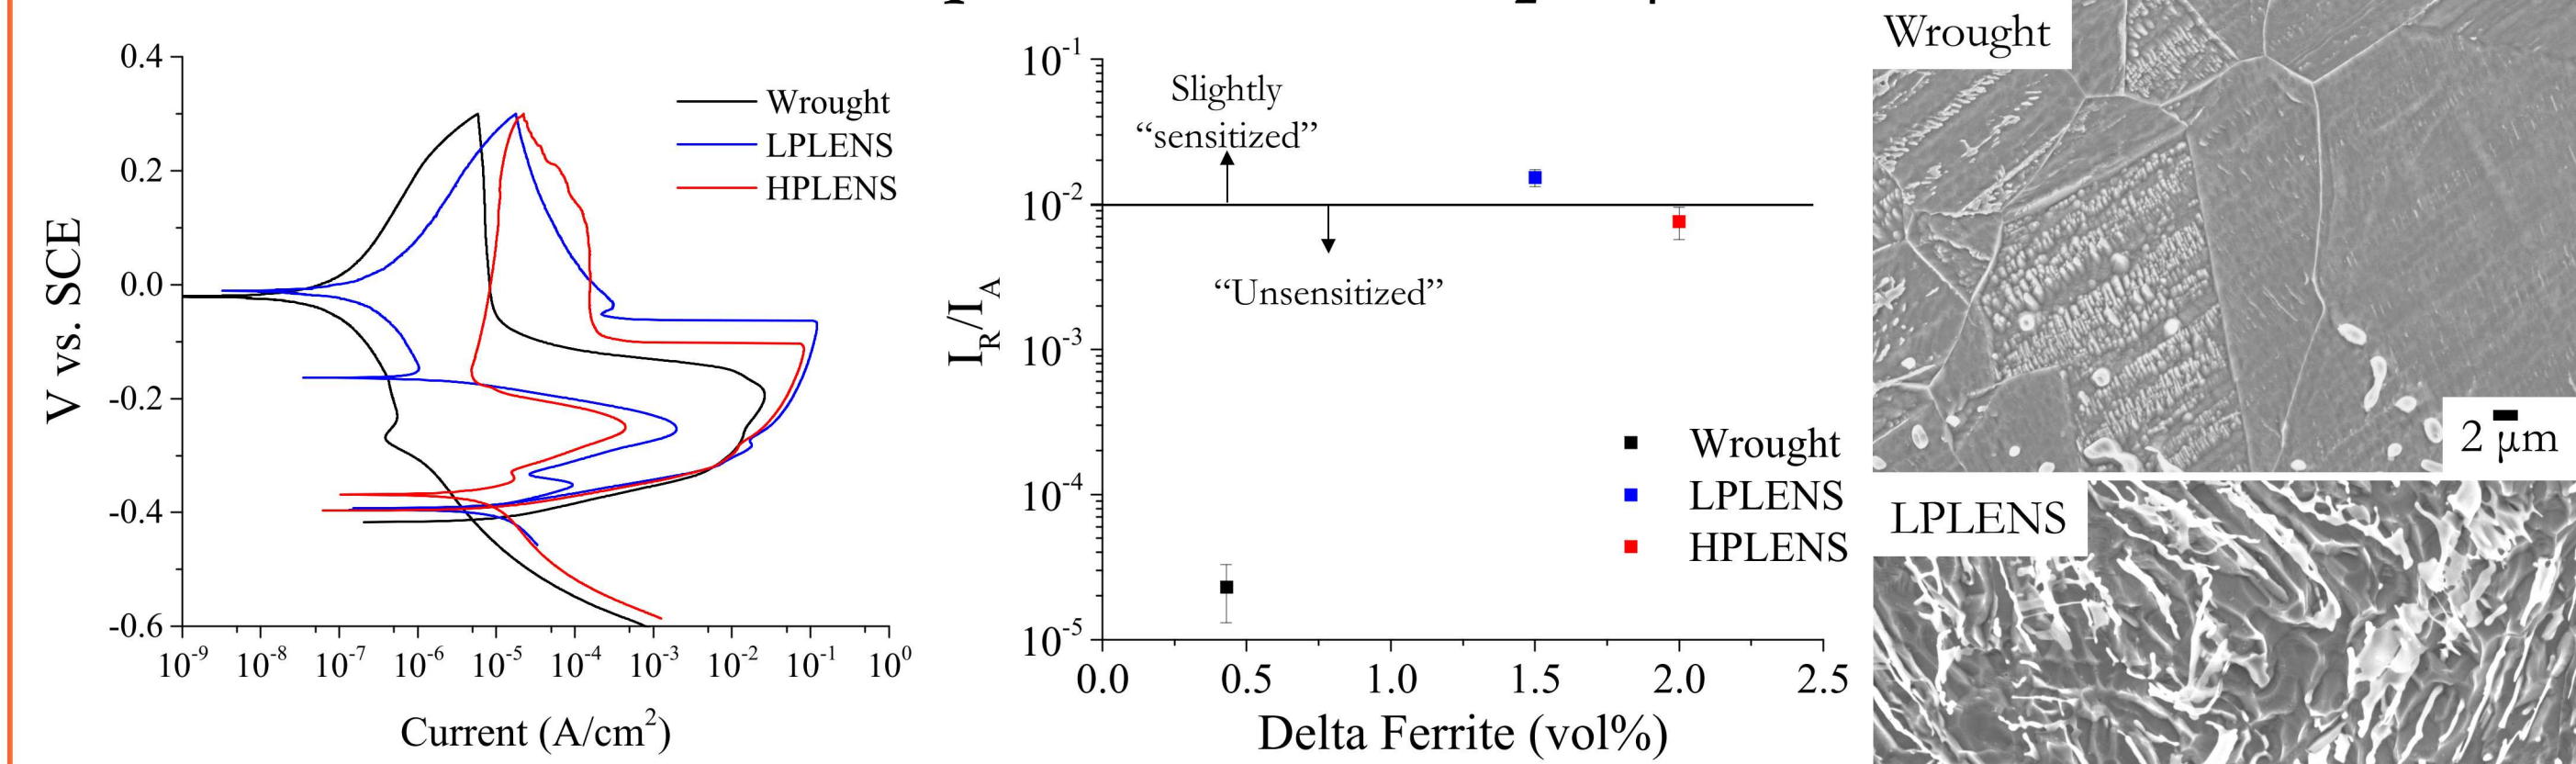

Quantification of chemical segregation for each specimen was performed by DLEPR, revealing a substantial reactivation current for both LENS materials, behaving similarly to sensitized stainless steel. A majority of the local corrosion attack occurring in the austenite located adjacent to  $\delta$ -ferrite for the LENS material. The large Cr content in the  $\delta$ -ferrite observed in the LENS material led to a more protective passive corrosion product compared to austenite, leading to the preferred corrosion of the austenite.

## Conclusions

The microstructure and corrosion response of 304L stainless steel manufactured using two LENS processes was investigated. The cyclic potentiodynamic polarization measurements revealed the breakdown and repassivation potentials for LP and HP LENS were comparable to wrought 304L. The abundance of fusion pores present in the HPLENS material often led to premature breakdown while the gas pores in the LPLENS had much less impact on pit initiation. The DLEPR experiments verified the presence of  $\delta$ -ferrite can lead to local dissolution of the austenite phase, however this effect did not appear to correlate to an increased susceptibility to pit initiation or metastable pitting. Fusion pores were evidently observed to be the controlling factor in pit initiation for these materials, with their mechanism for increased corrosion activity similar to that for crevice corrosion.

## Acknowledgements

The author would like to acknowledge Christina Profazi and Celedonio Jaramillo for metallographic sample preparation and Richard Grant for microprobe WDS mapping. Also John Carpenter from LANL for a discussion about the LENS process.