

PNNL-32706

Alkaline Modified Solid Oxide Catalysts for Condensation Reactions between Biomolecules Enter

March 2022

Suh-Jane Lee
Casper O. Brady
Kuan-Ting Lin

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor Battelle Memorial Institute, nor any of their employees, makes **any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights.** Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or Battelle Memorial Institute. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

PACIFIC NORTHWEST NATIONAL LABORATORY
operated by
BATTELLE
for the
UNITED STATES DEPARTMENT OF ENERGY
under Contract DE-AC05-76RL01830

Printed in the United States of America

Available to DOE and DOE contractors from the
Office of Scientific and Technical Information,
P.O. Box 62, Oak Ridge, TN 37831-0062;
ph: (865) 576-8401
fax: (865) 576-5728
email: reports@adonis.osti.gov

Available to the public from the National Technical Information Service
5301 Shawnee Rd., Alexandria, VA 22312
ph: (800) 553-NTIS (6847)
email: orders@ntis.gov <<https://www.ntis.gov/about>>
Online ordering: <http://www.ntis.gov>

Alkaline Modified Solid Oxide Catalysts for Condensation Reactions between Biomolecules Enter

March 2022

Suh-Jane Lee
Casper O. Brady
Kuan-Ting Lin

Prepared for
the U.S. Department of Energy
under Contract DE-AC05-76RL01830

Pacific Northwest National Laboratory
Richland, Washington 99354

Abstract

The coupling of oxygenates derived from biomass is critical to the production of sustainable commodity chemicals. However, most current industrial oxygenate condensation processes rely on highly corrosive homogenous basic catalysts. To find greener alternatives, several condensation reactions were screened using a variety of alkaline-doped MgO and MgO-Al₂O₃ heterogenous catalysts. These include i) the self-condensation of hexanedione to methylcyclopentenone, ii) the self-condensation of methyl ethyl ketone to form C8 or C12 ketones, and iii) the coupling of dimethyl succinate and benzaldehyde. We demonstrate substantial yields for several condensation reactions that typically require homogenous base catalysts.

Summary

A range of basic catalysts were prepared by modifying MgO and hydrotalcite derived MgO-Al₂O₃ with potassium, strontium, and cesium. Several of these catalysts were shown to be capable of catalyzing the self-condensation reactions of hexanedione and methyl-ethyl ketone and cross condensation of dimethyl succinate and benzaldehyde. The different pKa values of the tested reactants (hexanedione \leq MEK $<$ dimethyl succinate) lead to marked differences in the activity of the catalysts for each coupling reaction. For instance, while the self-condensation of MEK occurs readily on non-modified hydrotalcite derived catalysts (base strength sufficient to deprotonate pKa:18–35) the condensation of dimethyl succinate and benzaldehyde occurs only in the presence of stronger base catalysts (base strength sufficient to deprotonate pKa \geq 35). However, reactant pKa values alone are clearly not sufficient predictors of the required solid base site strength necessary for reaction. The self-condensation of hexanedione seems to rely on catalytic sites intrinsic to the rehydrated hydrotalcite catalyst which we cannot fully characterize with the techniques employed in this study. As leaching of introduced alkali cations by water produced during condensation has been observed in similar work [24], future work is required to better understand if the catalysts employed in this work will be fully recyclable in practice.

Acknowledgments

This research was supported by the Energy and Environmental Directorate (EED) Mission Seed, under the Laboratory Directed Research and Development (LDRD) Program at Pacific Northwest National Laboratory (PNNL). PNNL is a multi-program national laboratory operated for the U.S. Department of Energy (DOE) by Battelle Memorial Institute under Contract No. DE-AC05-76RL01830.

Acronyms and Abbreviations

C-C Coupling: Carbon-Carbon Coupling reaction

Hydrotalcite: $Mg_6Al_2(CO_3)(OH)_{16} \cdot H_2O$

LDH: Layered double hydroxide

TPD: Temperature programmed desorption

*H*_: Basicity

HD: 2,5 Hexanedione

MCP: Methyl Cyclopentenone

MEK: Mehtyl Ethyl Ketone

MCPBA: 3-methoxycarbonyl-4-phenylbut-3-enoic acid

Contents

Figures

1. Condensation reaction used in this study
2. CO₂ TPD spectra of the prepared catalysts
3. Correlations of MCPBA yield in Reaction C w/ the concentration of different types of basic sites as quantified by CO₂ TPD

Tables

1. Basicity screening by Hammett indicator
2. Basicity screening by TPD
3. Product yield of methylcyclopentenone from hexanedione at 200 °C
4. Product yield of MEK self-condensation at 120 °C and 200 psig
5. Product yield of the condensation of dimethyl succinate and benzaldehyde


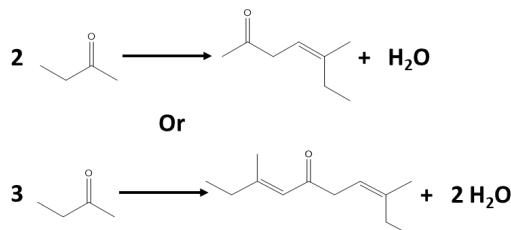
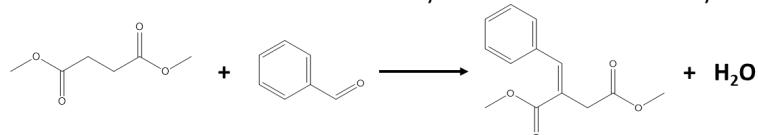
1.0 Introduction

Studies have shown that biomass-based fuels and chemicals have lower health and environmental risks compared to traditional fossil carbon sources [1, 2]. Biofuels have been growing steadily as a possible source of carbon-neutral sustainable energy that can reduce greenhouse gases and air pollutants. However, practical use of biomass to make biofuels and bioproducts requires efficient conversion processes and catalysts.

Carbon–carbon coupling reactions between oxygenates, particularly aldol condensations and other coupling reactions involving carbonyls, are a key step in the conversion of biomass to useful fuels and chemicals [3]. However, many base-catalyzed condensation reactions of ketones and esters require the use of prohibitively corrosive homogenous catalysts like alkali hydroxides (NaOH/KOH) and metal alkoxides (CH₃ONa) [4]. The use of these strong base catalysts also results in the production of substantial amounts of waste and imposes significant recycling costs [4]. Thus, better conversion technologies are urgently needed to replace homogenous base catalysts with cost effective heterogenous catalyst systems. While solid acid catalysts see extensive use in the refining industry, solid base catalysts, by comparison, are relatively uncommon in industrial processes [5].

This study focuses on condensation reactions leading to coupled ketones and esters derived from biomass using solid base catalysts. A carbonyl condensation reaction takes place between two carbonyl partners, one of which must possess an alpha-hydrogen atom. The first step in the reaction involves the removal of an α -proton by a base. The typical pKa value of a ketone is 20–24 and an ester is ≥ 25 [6]. Therefore, a suitable solid base catalyst must have the appropriate strength to facilitate deprotonation of the reactant under investigation.

We screen condensation reactions between ketones and/or esters with a variety of pKa values. Three reactions (shown in Figure 1): the self-condensation of hexanedione to methylcyclopentenone (Reaction A), the self-condensation of methyl ethyl ketone to form C8 or C12 ketones (Reaction B), and the coupling of dimethyl succinate and benzaldehyde (Reaction C) are chosen for screening as each of these compounds may be produced from biomass resources. Hexadione has been identified as an important intermediate in the production of methylcyclopentenone, a desirable next generation gasoline blend stock, from 2,5-dimethylfuran (DMF) [7]. Methyl ethyl ketone (MEK) may be produced from biomass resources via combined fermentation and catalytic processing [8]. Bio-based succinic acid is one of the twelve most promising bio-based building blocks named by DOE for future biorefineries[9] and offers sustainable options for a wide range of applications in the food, cosmetics, pharmaceutical and chemical industries [10].

Reaction A: Self-condensation of hexanedione to methylcyclopentenone**Reaction B:** Self-condensation of Methyl Ethyl Ketone**Reaction C:** Cross-condensation of dimethyl succinate and benzaldehyde**Figure 1:** Condensation reactions used in this study.

To screen a variety of catalytic systems for these reactions we focus on modifying two known heterogenous catalysts: magnesium oxide (MgO) and hydrotalcite derived MgO-Al₂O₃. The use of MgO as a base catalyst has been studied extensively for the reactions of organic carbonates, such as the Wittig reaction [11], Claisen-Schmidt condensation [12], and asymmetric Henry and Michael reactions [13]. The base strength of MgO can be altered by pre-treatment temperature and increased by doping with alkali and alkaline-earth metals [14, 15]. Hydrotalcite-derived mixed metal oxide catalysts are an emerging class of solid base catalysts.

Hydrotalcite is a layered double hydroxide (LDH) consisting of Mg and Al. Upon thermal treatment the layered structure of hydrotalcite dehydrates to form a mixture of amorphous MgO and Al₂O₃ with unique catalytic properties [16]. These amorphous oxides also possess a “memory-effect” by which re-introduced water will cause a restructuring of the material, reforming the original LDH phase [16, 17]. Hydrotalcite, or hydrotalcite derived oxides, have been widely reported to be active for several base-catalyzed reactions, including Michael addition [18] and several condensation reactions [19, 20]. Several parameters have been shown to impact the nature of the catalytic sites of hydrotalcite derived catalysts, including the Mg/Al ratio [21, 22], calcination temperature [23], and the introduction of alkali cations [24].

In this work we screen representative biomass-derived oxygenate coupling reactions over a variety of catalysts; specifically typical solid base catalysts (MgO and hydrotalcite derived MgO-Al₂O₃) modified with alkaline species (Cs, Sr, K). We demonstrate substantial yields of coupling products (>20%) for at least one screened catalyst in each reaction. Via characterization of the base sites of these catalyst via titration with Hammett indicators and CO₂ TPD we make preliminary steps towards understanding the catalytic site requirements of each reaction.

2.0 Experimental

2.1 Materials & Chemicals

Magnesium oxide (MgO) powder (1-5micron) was purchased from Atlantic Equipment Engineers. Hydrotalcite, Mg₆Al₂(CO₃)₁₆·4H₂O powder was purchased from Sigma-Aldrich. The molar Mg/Al ratio of this materials is between 4.0 and 5.0. The alkali metal and alkali earth metals used for doping were purchased as salts - NaNO₃, KNO₃, CsNO₃ and Sr(NO₃)₂ from Sigma-Aldrich. The indicators—phenolphthalein, 4-nitroaniline, 2,4-dinitroaniline and diphenylmethane—were purchased from TCI America.

2.2 Catalyst preparation

Solid base catalysts were prepared via wetness impregnation of nitrate salts on MgO powder (1-5 μ) and hydrotalcite powder. Each support was calcined in air at 550 °C for 5 hours prior to impregnation. The alkaline salts, NaNO₃, KNO₃, CsNO₃, and Sr(NO₃)₂, were dissolved in deionized water and introduced to the solid catalyst by wetness impregnation. The wet catalysts were dried at room temperature for 2 hours and then at 100 °C for 4 hours before calcination at 600 °C for 3 hours under N₂. The catalysts were transferred and stored in a glove box. Rehydration of hydrotalcite catalysts was performed by treating the calcined catalyst at room temperature in a nitrogen flow saturated with water vapor for 2 hours prior to dry N₂ for 4 hours.

2.3 Measurement of catalyst basicity

Two methods were used to characterize the basic properties of the synthesized catalysts. Hammett indicators were used to titrate basic sites according to literature protocols [25]. A 200 mg catalyst sample was added to a 0.5mL solution of indicator diluted in toluene under nitrogen. The color of the solution was observed after 2 hours.

Temperature programmed desorption (TPD) of CO₂ was used to characterize the basicity of catalysts. The experiments were performed on an Automated Catalyst Characterization System (AutoChem II) from Micromeritics. 50 mg of a powder sample was heated to 500 °C under N₂ for 1 hour. After cooling the sample to room temperature, it was exposed to a 20 mL min⁻¹ flow of CO₂ for 1 hour and then purged with N₂ for 1 hour to remove physical absorbed CO₂. A TPD was then performed using a N₂ flow of 20 mL min⁻¹ by heating from room temperature to 850 °C at a heating rate of 4 °C min⁻¹. CO₂ desorption was tracked via an online mass spectrometer (Pfeiffer Thermostar GSD 301).

2.4 Measurement of catalytic activity

All reactions were carried out with neat reactant. 10 wt% of catalyst was added to the substrate for each experiment. All reactions were conducted under nitrogen. The catalyst was first loaded into a Schlenk flask in the glove box. The substrate was then cannulated into the flask under N₂. The reaction mixture was heated to reflux at 200 °C for Reaction A and 120 °C for Reaction C. Both reactions A and C were allowed to proceed for 12 h. The reaction of methyl ethyl ketone (Reaction B) was performed in a high-pressure batch reactor under 200 psig of N₂ at 120 °C for 4 h. In all cases the catalyst was removed by filtration after the reaction mixture was cooled to room temperature. The products were identified and quantified via gas chromatography (GC-MS

and GC-FID; Agilent 7890). In each tested reaction no significant byproducts are observed via GC and reasonably high (>90%) carbon balances are achieved. Thus, we report only coupling product yields for each screened catalyst and reaction.

3.0 Results and Discussion

3.1 Catalyst Characterization

The base strength of the prepared catalysts was determined using the Hammett indicators phenolphthalein, 4-nitroaniline, 2,4-dinitroaniline and diphenylmethane. The results shown in Table 1 reveal that the H- value (as defined by Paul and Long [25]) of non-modified hydrotalcite (HT-MgO-Al₂O₃) is ≥ 18.4 and < 35 whereas the H- of non-modified MgO is in the range 9.8–13.0. Generally, the basicity of hydrotalcite based catalysts is stronger than that of MgO based catalysts. The K, Sr, and Cs modified hydrotalcite possess basic sites with pKa values greater than 35, meaning these catalysts are superbases. Superbases exhibit basicity (H-) greater than 26, where H- corresponds to the pKa value of the indicator [4].

Table 1: Basicity screening by Hammett indicators:

pKa	MgO	K/MgO	Sr/MgO	HT-MgO-Al ₂ O ₃	Sr/ HT-MgO-Al ₂ O ₃	K/ HT-MgO-Al ₂ O ₃	Cs/ HT-MgO-Al ₂ O ₃
Phenolphthalein	9.8	+	+	+	+	+	+
4-nitroaniline	13.0	-	-	-	+	+	+
2,4-dinitroaniline	18.5	-	-	-	+	+	+
diphenylmethane	35.0	-	-	-	-	+	+

The base properties of these catalysts were also examined by CO₂-temperature programmed desorption (TPD) (Figure 2). For ease of discussion 3 arbitrary temperature regions (25–350 °C, 350–750 °C, and 750–850 °C) are used to define weak, medium, and strong basic sites respectively.

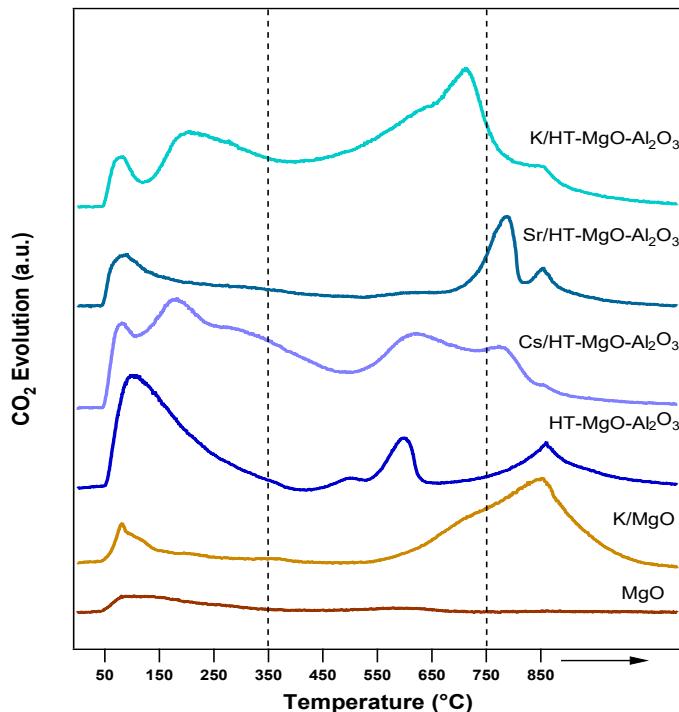


Figure 2: CO₂ TPD spectra of the prepared catalysts

MgO possesses little to no basic sites compared to the other tested catalysts, however this may simple be due to the relatively low surface area of our tested MgO. Alkali modification introduces a substantial number of strong base sites to the MgO catalyst (K/MgO), in line with previous literature [15]. HT-MgO-Al₂O₃ has a broad variety of base sites but is characterized by predominantly weakly basic sites. Interestingly, the changes in catalyst basicity upon alkaline modification of the hydrotalcite catalyst with a variety of modifiers (Cs, Sr, K) is highly dependent on the modifier used. While all alkaline species introduce some medium and strong basic sites the proportion and specific temperature region of these sites vary dramatically.

Table 2: Basicity screening by TPD:

Catalyst	Catalyst Basic Site Density (μmol/g)			
	Weak (R.T. – 350 °C)	Medium (350 – 750 °C)	Strong (750 – 850 °C)	Total
K/HT-MgO-Al ₂ O ₃	254	490	118	863
Sr/HT-MgO-Al ₂ O ₃	133	94	117	344
Cs/HT-MgO-Al ₂ O ₃	392	339	102	833
HT-MgO-Al ₂ O ₃	270	79	110	459
K/MgO	64	90	205	359
MgO	50	18	6	74

3.2 Catalyst Activity Testing

3.2.1 Reaction A: Self-condensation of 2,5 hexanedione to methylcyclopentenone

The reaction mechanism for condensation of hexanedione (HD) to methyl cyclopentenone (MCP) is well-established and is generally thought to require both a base to initiate the nucleophile and an acid for dehydration. Homogenous base catalysts have been shown to be able to catalyze this reaction at moderate yields [26]. More recent work has also demonstrated that mixed metal oxide solid base catalysts are also active for this reaction and have been shown to achieve quite high yields [7].

Reactivity testing of the self-condensation of HD to MCP using several catalysts (Table 3) shows that several solid base catalysts can facilitate this reaction. Rehydrated hydrotalcite demonstrates the highest yield of MCP (41.6%) while alkali modified MgO catalysts (K-MgO and Sr-MgO) exhibit middling yields (10-20%). The high product yield with rehydrated hydrotalcite could be attributed to an increase in the available mild Brønsted base sites by reconstruction of its hydroxyl interlayer, which has been demonstrated in the literature [27]. Unfortunately, given that the advanced catalyst characterization that is necessary to discern these specific sites is outside the scope of this work, we cannot comment on whether similar sites may be present on K-MgO and Sr-MgO. This result does indicate, however, that base site strength alone is not a sufficient indicator for catalytic performance in this reaction, as alkali modified catalysts with

strong base character deliver poor results compared to the rehydrated hydrotalcite-derived catalyst.

Table 3: Product yield of methylcyclopentenone from hexanedione at 200 °C

Catalyst	% Yield of MCP
HT-MgO-Al ₂ O ₃	1.5
HT-MgO-Al ₂ O ₃ Rehydrated	41.6
Sr-MgO-Al ₂ O ₃	4.7
K-MgO	10.2
Sr-MgO	19.3

3.2.2 Reaction B: Self -condensation of Methyl Ethyl Ketone (MEK)

The condensation of MEK using base catalysts results in primary dimer (C8 ketones) and secondary trimer products (C12 ketone). Reactivity testing of several solid base catalysts reveal several counterintuitive trends in this reaction (Table 4). The yield of MEK coupling products is nearly identical in the case of all tested hydrotalcite derived catalysts (HT-MgO-Al₂O₃, HT-MgO-Al₂O₃ rehydrated and K-HT-MgO-Al₂O₃). Many studies focused on condensation reactions over hydrotalcite catalysts observe higher rates over rehydrated catalysts [28-30]. Rehydrated hydrotalcite catalysts have been shown to possess weaker base sites than calcined hydrotalcite catalysts [29], however they are generally believed to exhibit better catalytic activity due to the formation of Brønsted base sites by water introduction [27]. One potential explanation of the negligible difference between calcined and rehydrated hydrotalcite for MEK condensation is that stronger Lewis base sites intrinsic to the hydrotalcite catalyst are more catalytically relevant than the Brønsted sites formed by rehydration. This is consistent with the slight increase in condensation yield over K-HT-MgO-Al₂O₃, as K introduction does increase the strong base site density of the hydrotalcite catalyst.

Table 4: Product yield of MEK self-condensation at 120 °C and 200 psig

Catalyst	% Yield of MEK dimers and trimers
HT-MgO-Al ₂ O ₃	20.7
HT-MgO-Al ₂ O ₃ Rehydrated	20.3
K-HT-MgO-Al ₂ O ₃	24.6
K-MgO	0.43

3.2.3 Reaction C: Cross-condensation of dimethyl succinate and benzaldehyde

Dimethyl succinate reacts with benzaldehyde to give a Stobbe condensation product of 3-methoxycarbonyl-4phenylbut-3-enoic acid (MCPBA). The condensation of dimethyl succinate and benzaldehyde has been shown to proceed in the presence of strong homogenous base catalysts like potassium tert-butoxide [31] and lithium methoxide [32]. The results of reactivity testing are summarized in Table 5. The K modified hydrotalcite based catalyst (K-HT-MgO-

Al₂O₃) achieves the highest yield of MCPBA at 38% compared with other tested catalysts. While all tested catalysts exhibit some activity for this reaction, all tested alkali doped hydrotalcite derived catalysts generally possess substantially higher activity. As these catalysts are the only screened catalysts to be titrated by diphenylmethane, this reaction appears to require a high pKa .

Table 5: Product yield of the condensation of dimethyl succinate and benzaldehyde

Catalyst	% Yield of MCPBA
HT-MgO-Al ₂ O ₃	2.8
HT-MgO-Al ₂ O ₃ Rehydrated	3.4
K-HT-MgO-Al ₂ O ₃	38.4
Sr-HT-MgO-Al ₂ O ₃	13.3
Cs-HT-MgO-Al ₂ O ₃	30.2
MgO	2.1
K-MgO	6.6

It is also notable that while the catalysts studied here can facilitate condensation between dimethyl succinate and benzaldehyde, none demonstrate measurable activity for the self-condensation of dimethyl succinate under the tested reaction conditions. This can be explained by the ability of the strongly basic sites on alkaline treated hydrotalcite-based catalysts to activate dimethyl succinate as a nucleophile but not complete the corresponding electrophile addition. Similar reactions have been shown to proceed when catalyzed by NaOMe forming an organic Na⁺ salt product [33]. Thus, we postulate that self-condensation of dimethyl succinates requires a homogenous cation containing catalyst to stabilize the final product. Scheme 1 shows the proposed reaction product stabilized by Na⁺.



Scheme 1: Dimethyl succinated self-condensation and product stabilization by Na cations

A broad range of yields for the products obtained in Reaction C for the tested catalysts are observed (Table 5). Given the wide variety of weak, medium and strongly basic sites measured by CO₂ TPD (Table 2) for the tested catalysts, qualitative correlations to gain insight into which sites are catalytically relevant are shown in Figure 3.

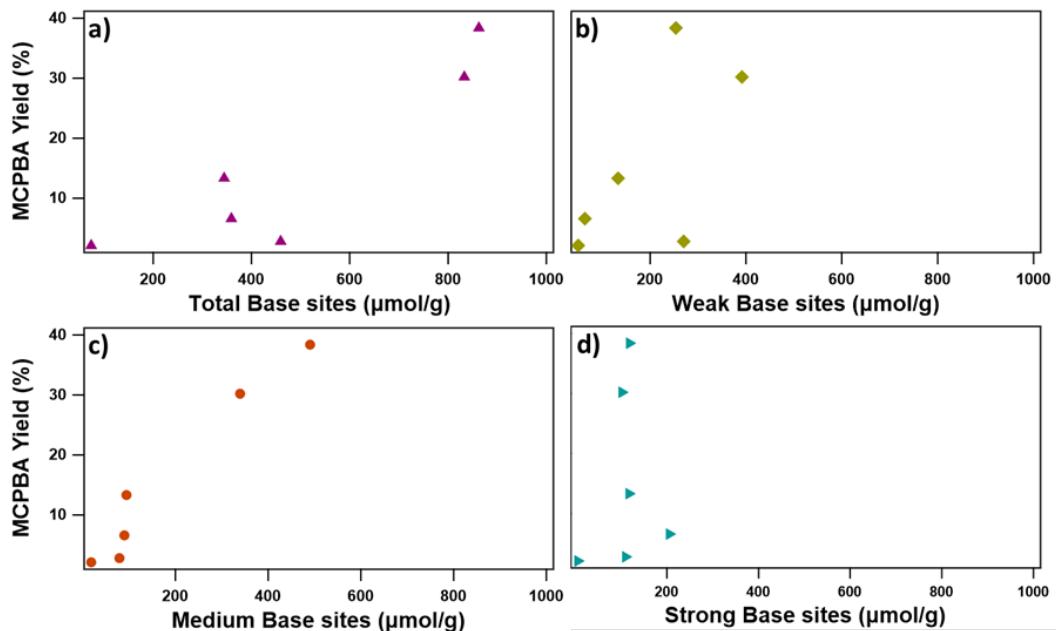


Figure 3: Correlations of MCPBA yield in Reaction C with the concentration of different types of basic sites as quantified by CO_2 TPD.

The yield of MCPBA varying with the total site density (Figure 3.a), weak site density (Figure 3.b), medium site density (Figure 3.c), and strong site density (Figure 3.d) are plotted. While no discernable correlation between the total (Figure 3.a), weak (Figure 3.b) or strong sites (Figure 3.d) appears to exist, a relatively monotonic trend is observed between the yield of MCPBA and the density of medium strength base sites (Figure 3.c). This implies that base sites that desorb CO_2 between 350 and 750 $^{\circ}\text{C}$ are more catalytically relevant in this reaction than very weak or very strong sites.

4.0 Conclusions

A range of basic catalysts were prepared by modifying MgO and hydrotalcite derived MgO-Al₂O₃ with potassium, strontium, and cesium. Several of these catalysts were shown to be capable of catalyzing the self-condensation reactions of hexanedione and methyl-ethyl ketone and cross condensation of dimethyl succinate and benzaldehyde. The different pKa values of the tested reactants (hexanedione \leq MEK $<$ dimethyl succinate) lead to marked differences in the activity of the catalysts for each coupling reaction. For instance, while the self-condensation of MEK occurs readily on non-modified hydrotalcite derived catalysts (base strength sufficient to deprotonate pKa:18–35) the condensation of dimethyl succinate and benzaldehyde occurs only in the presence of stronger base catalysts (base strength sufficient to deprotonate pKa \geq 35). However, reactant pKa values alone are clearly not sufficient predictors of the required solid base site strength necessary for reaction. The self-condensation of hexanedione seems to rely on catalytic sites intrinsic to the rehydrated hydrotalcite catalyst which we cannot fully characterize with the techniques employed in this study. As leaching of introduced alkali cations by water produced during condensation has been observed in similar work [24], future work is required to better understand if the catalysts employed in this work will be fully recyclable in practice.

5.0 References

- [1] B. Antizar-Ladislao, J.L. Turrian-Gomez, Second-generation biofuels and local bioenergy systems, *Biofuel. Bioprod. Bior.*, 2 (2008) 455-469.
- [2] J.D. Wolt, Advancing environmental risk assessment for transgenic biofeedstock crops, *Biotechnol. Biofuels*, 2 (2009) 1-13.
- [3] D.A. Simonetti, J.A. Dumesic, Catalytic strategies for changing the energy content and achieving C-C coupling in biomass-derived oxygenated hydrocarbons, *ChemSusChem*, 1 (2008) 725-733.
- [4] G. Kelly, F. King, M. Kett, Waste elimination in condensation reactions of industrial importance, *Green Chem.*, 4 (2002) 392-399.
- [5] K. Tanabe, W.F. Hölderich, Industrial application of solid acid–base catalysts, *Appl. Catal. A-Gen.*, 181 (1999) 399-434.
- [6] J. March, *Advanced Organic Chemistry: Reaction, Mechanisms, And Structure*, 4th Edition ed., Wiley-Interscience: New York 1997.
- [7] E.R. Sacia, M.H. Deaner, A.T. Bell, Synthesis of biomass-derived methylcyclopentane as a gasoline additive via aldol condensation/hydrodeoxygenation of 2, 5-hexanedione, *Green Chem.*, 17 (2015) 2393-2397.
- [8] A. Multer, N. McGraw, K. Hohn, P. Vadlani, Production of methyl ethyl ketone from biomass using a hybrid biochemical/catalytic approach, *Ind. Eng. Chem. Res.*, 52 (2013) 56-60.
- [9] J.J. Bozell, G.R. Petersen, Technology development for the production of biobased products from biorefinery carbohydrates—the US Department of Energy’s “Top 10” revisited, *Green Chem.*, 12 (2010) 539-554.
- [10] C. Delhomme, D. Weuster-Botz, F. Kühn, Succinic acid from renewable resources as a C 4 building-block chemical—a review of the catalytic possibilities in aqueous media, *Green Chem.*, 11 (2009) 13-26.
- [11] V.R. Chintareddy, M.L. Kantam, Recent developments on catalytic applications of nano-crystalline magnesium oxide, *Catal. Surv. Asia.*, 15 (2011) 89-110.
- [12] A.B. Patil, B.M. Bhanage, Novel and green approach for the nanocrystalline magnesium oxide synthesis and its catalytic performance in Claisen–Schmidt condensation, *Catal. Commun.*, 36 (2013) 79-83.
- [13] B.M. Choudary, K.V. Ranganath, U. Pal, M.L. Kantam, B. Sreedhar, Nanocrystalline MgO for asymmetric Henry and Michael reactions, *J. Am. Chem. Soc.*, 127 (2005) 13167-13171.
- [14] A.A. Pilarska, Ł. Kłapiszewski, T. Jasionowski, Recent development in the synthesis, modification and application of Mg (OH) 2 and MgO: A review, *Powder Technol.*, 319 (2017) 373-407.

[15] P. Thomasson, O. Tyagi, H. Knözinger, Characterisation of the basicity of modified MgO-catalysts, *Appl. Catal. A-Gen.*, 181 (1999) 181-188.

[16] F. Cavani, F. Trifiro, A. Vaccari, Hydrotalcite-type anionic clays: Preparation, properties and applications, *Catal. Today*, 11 (1991) 173-301.

[17] N. Puttaswamy, P.V. Kamath, Reversible thermal behaviour of layered double hydroxides: a thermogravimetric study, *J. Mater. Chem.*, 7 (1997) 1941-1945.

[18] B.M. Choudary, M.L. Kantam, C.R.V. Reddy, K.K. Rao, F. Figueras, The first example of Michael addition catalysed by modified Mg-Al hydrotalcite, *J. Mol. Catal. A-Chem.*, 146 (1999) 279-284.

[19] M. Lakshmi Kantam, B. M Choudary, C. Venkat Reddy, K. Koteswara Rao, Aldol and Knoevenagel condensations catalysed by modified Mg-Al hydrotalcite: a solid base as catalyst useful in synthetic organic chemistry, *Chem. Commun.*, (1998) 1033-1034.

[20] A. Guida, M.H. Lhouty, D. Tichit, F. Figueras, P. Geneste, Hydrotalcites as base catalysts. Kinetics of Claisen-Schmidt condensation, intramolecular condensation of acetonylacetone and synthesis of chalcone, *Appl. Catal. A-Gen.*, 164 (1997) 251-264.

[21] D. Stojić, F. Hosoglu, S. Bennici, A. Travert, M. Capron, F. Dumeignil, J.-L. Couturier, J.-L. Dubois, A. Auroux, Methanol and ethanol reactivity in the presence of hydrotalcites with Mg/Al ratios varying from 2 to 7, *Catal. Commun.*, 89 (2017) 14-18.

[22] J.I. Di Cosimo, C. Apesteguia, M. Ginés, E. Iglesia, Structural requirements and reaction pathways in condensation reactions of alcohols on MgyAlO_x catalysts, *J. Catal.*, 190 (2000) 261-275.

[23] Y. Liu, E. Lotero, J.G. Goodwin Jr, X. Mo, Transesterification of poultry fat with methanol using Mg-Al hydrotalcite derived catalysts, *Appl. Catal. A-Gen.*, 331 (2007) 138-148.

[24] S. Abelló, F. Medina, D. Tichit, J. Pérez-Ramírez, X. Rodríguez, J. Sueiras, P. Salagre, Y. Cesteros, Study of alkaline-doping agents on the performance of reconstructed Mg-Al hydrotalcites in aldol condensations, *Appl. Catal. A-Gen.*, 281 (2005) 191-198.

[25] M. Paul, F. Long, H₀ and related indicator acidity function, *Chem. Rev.*, 57 (1957) 1-45.

[26] J. An, L. Bagnell, T. Cablewski, C.R. Strauss, R.W. Trainor, Applications of high-temperature aqueous media for synthetic organic reactions, *J. Org. Chem.*, 62 (1997) 2505-2511.

[27] F. Winter, X. Xia, B.P. Hereijgers, J.H. Bitter, A.J. van Dillen, M. Muhler, K.P. de Jong, On the nature and accessibility of the brønsted-base sites in activated hydrotalcite catalysts, *J. Phys. Chem. B.*, 110 (2006) 9211-9218.

[28] S. Abelló, F. Medina, D. Tichit, J. Perez-Ramirez, J.C. Groen, J.E. Sueiras, P. Salagre, Y. Cesteros, Aldol condensations over reconstructed Mg-Al hydrotalcites: structure-activity relationships related to the rehydration method, *Chem-Eur. J.*, 11 (2005) 728-739.

[29] K.K. Rao, M. Gravelle, J.S. Valente, F. Figueras, Activation of Mg–Al hydrotalcite catalysts for aldol condensation reactions, *J. Catal.*, 173 (1998) 115-121.

[30] J. Roelofs, A.J. van Dillen, K. De Jong, Base-catalyzed condensation of citral and acetone at low temperature using modified hydrotalcite catalysts, *Catal. Today*, 60 (2000) 297-303.

[31] H. Malik, F.P. Rutjes, B. Zwanenburg, A new efficient synthesis of GR24 and dimethyl A-ring analogues, germinating agents for seeds of the parasitic weeds *Striga* and *Orobanche* spp, *Tetrahedron*, 66 (2010) 7198-7203.

[32] V. Bilenko, H. Jiao, A. Spannenberg, C. Fischer, H. Reinke, J. Kösters, I. Komarov, A. Börner, A New Target for Highly Stereoselective Katsuki–Sharpless Epoxidation–One-Pot Synthesis of C2-Symmetric 2, 2'-Bioxiranes, *Eur. J. Org. Chem.*, (2007).

[33] S. Zheng, S. Xu, J. Zhou, R. Shen, Y. Ji, M. Shen, W. Li, Insight into the Claisen condensation of methyl acetate and dimethyl carbonate to dimethyl malonate, *New J. Chem.*, 42 (2018) 6689-6694.

Pacific Northwest National Laboratory

902 Battelle Boulevard
P.O. Box 999
Richland, WA 99354
1-888-375-PNNL (7665)

www.pnnl.gov