

# Materials Horizons

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: Y. Li, Y. Cho, J. Cai, C. Kim, X. Zheng, W. Wu, A. Musgrove, Y. Su, R. L. Sacci, Z. Chen, J. Nanda and G. Yang, *Mater. Horiz.*, 2024, DOI: 10.1039/D4MH01211A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Our investigation delves into the realm of calendar aging in sulfide all-solid-state batteries, specifically targeting NMC811 cathodes—a critically important yet largely unexplored area. A central and surprising finding from our research is that sulfide catholytes, typically considered less oxidatively stable than their halide counterparts, exhibit superior performance when used with lithium niobate-coated NMC811 cathodes. We thoroughly examine the interactions between high-nickel NMC811 cathodes and various catholytes, including  $\text{Li}_6\text{PS}_5\text{Cl}$  (LPSCl),  $\text{Li}_3\text{InCl}_6\text{-Li}_6\text{PS}_5\text{Cl}$  (LIC-LPSCl), and  $\text{Li}_3\text{YCl}_6\text{-Li}_6\text{PS}_5\text{Cl}$  (LYC-LPSCl), under simulated prolonged operational conditions. Among these, LPSCl demonstrates the most promising capacity retention, suggesting its potential to significantly enhance the longevity of sulfide-based solid-state batteries. Conversely, the LIC-LPSCl mixture shows considerable degradation due to chemical mismatches, adversely affecting cathode performance. We have introduced a robust electrochemical calendar aging testing protocol that provides a rapid and effective method for evaluating the long-term stability of cathode materials under realistic usage scenarios. These findings not only fill a crucial gap in existing literature but also introduce a conceptual advance by emphasizing the importance of catholyte selection in mitigating interface degradation and boosting the durability of sulfide all-solid-state batteries. This paradigm-shifting insight paves the way for future advancements in battery technology.

## ARTICLE

## Effects of Catholyte Aging on High-Nickel NMC Cathodes in Sulfide All-Solid-State Batteries

Yuanshun Li<sup>a,b</sup>, Yukio Cho<sup>c</sup>, Jiyu Cai<sup>d</sup>, Chanh Kim<sup>a</sup>, Xueli Zheng<sup>c</sup>, Wenda Wu<sup>a</sup>, Amanda Musgrove<sup>a</sup>, Yifeng Su<sup>e</sup>, Robert Sacci<sup>a</sup>, Zonghai Chen<sup>d</sup>, Jagjit Nanda<sup>\*c</sup> and Guang Yang<sup>\*a</sup>Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Sulfide solid-state electrolytes (SSEs) in all-solid-state batteries (SSBs) are recognized for their high ionic conductivity and inherent safety. The  $\text{LiNi}_{0.8}\text{Mn}_{0.1}\text{Co}_{0.1}\text{O}_2$  (NMC811) cathode offers a high thermodynamic potential of approximately 3.8 V vs Li/Li<sup>+</sup> and a theoretical specific capacity of 200 mAh/g. However, the practical utilization of NMC811 in sulfide SSBs faces significant interfacial challenges. The oxidation instability of sulfide solid electrolytes against NMC811 and the formation of the cathode electrolyte interphase (CEI) during cycling lead to degradation and reduced cell performance. Volumetric changes in NMC during lithiation and de-lithiation can also cause detachment from sulfide electrolytes or internal particle cracking. Despite extensive galvanostatic cycling studies to address the issues, the calendar life of sulfide SSBs remains poorly understood. Here, we systematically studied the effects of four different catholytes on the calendar aging of  $\text{LiNbO}_3$  (LNO)-coated NMC811, including  $\text{Li}_6\text{PS}_5\text{Cl}$  (LPSCI),  $\text{Li}_3\text{InCl}_6\text{-Li}_6\text{PS}_5\text{Cl}$  (LIC-LPSCI),  $\text{Li}_3\text{YCl}_6\text{-Li}_6\text{PS}_5\text{Cl}$  (LYC-LPSCI), and  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$  (LGPS). Our results indicate that LPSCI provides optimal capacity retention when stored at high state-of-charge (SOC) at room temperature, but the LIC-LPSCI cathode shows significant capacity degradation and chemical incompatibility. We also established an effective electrochemical calendar aging testing protocol to simulate daily usage, enabling quick inference of calendar life for SSB. This new testing approach accelerates materials selection strategies for high-Nickel NMC composite cathodes in sulfide SSBs.

## Introduction

Sulfide-based all-solid-state batteries (SSBs) present a highly promising alternative to lithium-ion batteries due to their comparable ionic conductivity and intrinsic safety in the operation of solid electrolytes. The development of Nickel-rich  $\text{LiNi}_x\text{Mn}_{1-x-y}\text{Co}_y\text{O}_2$  (NMC,  $x \geq 0.8$ ,  $y \leq 0.1$ ) cathodes, such as NMC811, is critical to meeting high voltage and specific capacity requirements. NMC811 possesses a high thermodynamic potential of approximately 3.8 V vs Li/Li<sup>+</sup>. Additionally, NMC811 delivers a theoretical specific capacity of 200 mAh/g, outperforming  $\text{LiFePO}_4$  at 170 mAh/g. Therefore, accelerating the development of NMC cathodes in sulfide SSBs is of great interest for urgent and broad energy storage applications.

The practical utilization of the NMC811 composite cathode in sulfide SSBs faces several critical interfacial challenges<sup>1</sup>. A major challenge is the oxidation instability of sulfide SSE against

NMC cathodes. Over cycling, the formation of the cathode electrolyte interphase (CEI) in the NMC composite cathode can lead to electrochemical and chemical degradation, resulting in a disconnected lithium-ion charge pathway and reduced cell performance<sup>2</sup>. Additionally, the volumetric change of NMC during lithiation and de-lithiation can cause either detachment from sulfide electrolytes or internal particle cracking, leading to a loss of active sites for capacity delivery<sup>3</sup>. Thus, considerable efforts have been devoted to increasing the capacity retention of sulfide SSBs by creating a stable CEI in the composite cathode. Two major strategies have been adopted and reported in the literature. The first one involves cathode surface coating, including using wet chemistry<sup>4</sup> with  $\text{LiNbO}_3$  (LNO) or atomic layer deposition (ALD) with different oxide chemistries<sup>5</sup>. The second method is known as the bilayer design<sup>6</sup>, which engages halide electrolytes, such as  $\text{Li}_3\text{InCl}_6$  (LIC) or  $\text{Li}_3\text{YCl}_6$  (LYC), as a catholyte while retaining majority composition of sulfide SSEs as separators. This idea stems from the halide's broader electrochemical window, which improves the oxidation stability of the CEI. Numerous reports indicate that such bilayer sulfide SSBs can significantly improve capacity retention<sup>7-10</sup>.

Although galvanostatic cycling studies have been extensively performed on most sulfide SSBs to infer their performance and reliability, the calendar life of sulfide SSBs remains underexplored. Calendar life estimates a battery's lifespan from the point of manufacture, which depends solely on storage conditions and state of charge (SOC). Dubarry et al.

\*E-mails: yangg@ornl.gov (Guang Yang); jnanda@slac.stanford.edu

<sup>a</sup> Chemical Sciences Division, Oak Ridge National Laboratory, Tennessee, 37831, Oak Ridge, United States<sup>b</sup> Department of Chemical and Biomolecular Engineering, University of Tennessee Knoxville, TN, 37996, Knoxville, United States<sup>c</sup> Applied Energy Division, SLAC National Laboratory, CA, 94025, Menlo Park, United States<sup>d</sup> Chemical Sciences and Engineering Division, Argonne National Laboratory, IL, 60439, Lemont, USA<sup>e</sup> Materials Science and Technology Division, Oak Ridge National Laboratory, TN, 37831, Oak Ridge, USA

initially developed calendar aging to study aging mechanisms in commercial Li-ion batteries<sup>11</sup>. They observed that the NMC cathode exhibits a significant degradation rate at 40 to 60°C, whereas nickel-cobalt aluminum oxide (NCA) shows minimal change within the same temperature range. Similarly, it is crucial to measure calendar life for next-generation batteries beyond lithium-ion technology. Xiao et al. emphasized that calendar life testing is mandatory for solid-state batteries to monitor minor interphase impedance growth rates<sup>12</sup>. This test reveals potential negative effects of SSEs decomposition in response to high cathode loading and low SE loading in state-of-the-art designs. In a recent study, Kim et al. conducted a calendar aging test on NMC811-LiC|LIC/LPSCI|LiIn cells with different SOC aging protocols at 25°C and 70°C<sup>13</sup>. They demonstrated that this bilayer solid electrolyte with LIC as the catholyte protects NMC from significant capacity degradation when aged at high SOC for 7 days at 70°C, compared to the high-capacity degradation observed at low SOC. However, very few calendar aging test protocols have been developed to study the aging mechanisms of sulfide SSBs. Similarly, there is a lack of systematic electrochemical experimental designs to standardize calendar aging tests and explore the effects of catholytes on the calendar life of NMC cathodes.

Herein, we adapted a calendar aging protocol developed for Li-Si batteries to explore sulfide SSBs<sup>14</sup>. We systematically studied the effects of four different catholytes on the calendar aging of the composite LNO-coated NMC811, including  $\text{Li}_6\text{PS}_5\text{Cl}$  (LPSCI),  $\text{Li}_3\text{InCl}_6$ - $\text{Li}_6\text{PS}_5\text{Cl}$  (LIC-LPSCI),  $\text{Li}_3\text{YCl}_6$ - $\text{Li}_6\text{PS}_5\text{Cl}$  (LYC-LPSCI), and  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$  (LGPS). We demonstrated that LPSCI presents optimal capacity retention after aging when stored at high SOC at room temperature. The LIC-LPSCI cathode exhibits significant capacity degradation and chemical incompatibility, as confirmed by Raman imaging armed with unsupervised learning algorithm, and sulfur K-edge XAS. Additionally, a robust electrochemical calendar aging testing protocol was developed to mimic daily use in mobile devices, enabling rapid estimation of the sulfide solid-state battery's calendar life over a short period (less than 10 days). The electrochemical calendar aging tests herein presents a pivotal advancement in accelerating materials selection strategies for the development of high-Nickel NMC composite cathodes in sulfide SSBs.

## Results and discussion

To understand how catholytes impact the calendar life of NMC particles, an illustration of the aging protocol is presented in Fig 1a. Originally, the calendar life aging protocol was developed for studying silicon's calendar life against liquid electrolyte in Si|NMC<sup>14</sup>. Briefly, the cell starts with three formation cycles at 0.1 C from 1.98 V to 3.678V against  $\text{Li}_x\text{In}$  alloy. Then, it is held at 3.678 V for 180 hours to calendar age the NMC composite cathode. Following that, one diagnostic cycle is executed at 0.1 C. Holding a battery at a full SOC simulates a practical condition when energy storage devices are

routinely operated. For example, batteries in electric vehicles or phones are often 'overcharged,' with no minimum control applied to unplug a 100% SOC battery. It is believed that maintaining a high potential and overcharging a battery would accelerate side reactions at the electrode/electrolyte interphases, which are typically irreversible. This issue is even more critical in the cathode electrolyte interphase (CEI) of sulfide solid-state batteries. Four different catholytes were examined for their stability against LNO-NMC811 during calendar aging testing, including LPSCI, LGPS, LIC-LPSCI, and LYC-LPSCI. LPSCI was employed as a baseline catholyte. LGPS was reported to have the highest ionic conductivity in sulfide SSE. LIC-LPSCI and LYC-LPSCI are two synergized halides and sulfide SSEs, represent advanced strategies that have been shown to effectively stabilize the CEI<sup>9, 15</sup>.

The irreversible capacity loss after calendar aging is quantified through two means. One method involves comparing the discharge capacity from the last formation cycle (before aging) to that of the diagnostic cycle (after aging). This comparison directly reflects the effectiveness of different catholytes degradation against NMC. Fig 1b reveals that LPSCI-cathode reserves the highest discharge capacity after calendar aging at 122.97 mAh/g with a high 73.1% capacity retention. Similarly, LYC-LPSCI presents 106.34 mAh/g (discharge capacity after aging) with 68.1% capacity retention. The LGPS-cathode presents a slightly lower capacity at 72.22 mAh/g and 53.3%. In contrast, the LIC-LPSCI cathode depicts significant degradation with only 25.8% capacity retention and 32.48 mAh/g. This indicates that curing the LIC-LPSCI cathode cell at high potential for one week resulted in severe irreversible capacity degradation, potentially attributed to catholyte decompositions. This LIC-LPSCI calendar life degradation effects on cathode spread same influence on NMC622 as evidenced in Fig S1. We have observed that for several years, researchers have been actively debating whether a bilayer LIC-LPSCI is necessary, or if LIC alone should replace LPSCI as a catholyte to safeguard the NMC cathode. Ye et al. reported that LIC serves as a catholyte, and using LPSCI as a solid electrolyte enhances pellet type SSB performance in both discharging capacity and capacity retention<sup>16</sup>. In contrast, Carolin et al. reported chemical incompatibility between LIC and LPSCI, which does not benefit the overall electrochemical performance when introducing LIC as a catholyte<sup>17</sup>. The aging test underscores that storing cells at a high state of charge (SOC) with LIC-LPSCI blended catholytes is not recommended. The potential mechanisms behind this recommendation are further elucidated in subsequent characterizations.

The second calendar aging quantification method involved monitoring the residual current during high voltage holding, as shown in Fig 1c. It is assumed that the cell is fully charged and only side reaction due to SSE oxidative decomposition occurs at 3.678 V approaching the end of the 180 hours holding period. In the first 20 hours of voltage holding, the current drops significantly, which corresponds to compensating for the 'unfinished' de-lithiation process in the cathode. Furthermore,

the residual current stabilizes and reaches a plateau during continuous high voltage holding. At the end of voltage holding, the zoom-in profile was revealed to further investigate the steady-state residual current, which is assigned to the side-reaction rate. The orange noisy curve referred to the residual current between LPSCI and NMC811, registering at 1400 nA, depicts that the LPSCI-cathode undergoes the severest side reaction compared with other catholytes. Blending LIC or LYC with LPSCI yields almost identical residual current responses at approximately 170 nA. This suggests that blending LIC or LYC with LPSCI could stabilize the interphases of  $\text{Li}_x\text{In}$ |NMC and reduce the residual current. Additionally, the LGPS-cathode presents the lowest value of 80 nA. A possible explanation is that LGPS can mitigate the interfacial side reaction by lower its parasitic electron transfer across the interphase. During voltage holding process, the vacancy of lithium ion in NMC reaches maximum. Thus, LGPS with its Ge substituted stable structure and low Young's modulus exhibits better stability against NMC with minimal lithium existing in the CEI. However, obviously, the findings from the second method are not consistent with the first method. Specifically, the LPSCI exhibits the best aging capacity retention, but it produces the highest residual current during aging. Several possible factors can contribute to this discrepancy: 1) The  $\text{Li}_x\text{In}$  alloy has a fluctuating voltage response during the lithiation process, causing the holding voltage to be inaccurate as the upper cutoff voltage; 2) Different catholytes can form different CEIs, affecting their stability in response to high voltage. This underscores the limitations of the second method, highlighting areas that require further refinement.


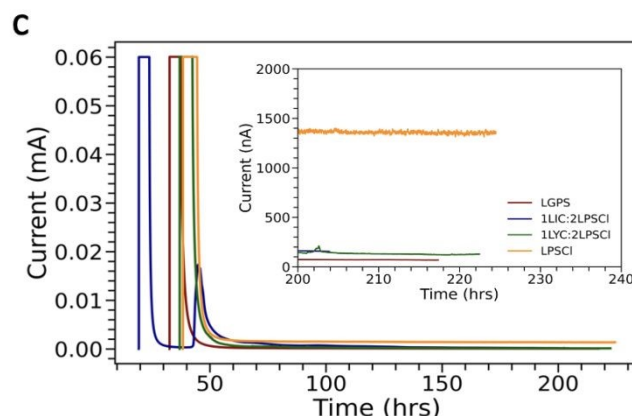


Figure 1: Calendar life protocols and outcomes for  $\text{Li}_x\text{In}$ |LPSCI|LNO-NMC811 SSB in different catholytes. a) an illustration of calendar aging protocol by voltage holding<sup>14, 18</sup> with direct modification applied to adjust for studying catholytes effects on calendar life of high Nickel NMC cathode in sulfide solid state battery. b) Results comparing discharge capacities before and after calendar aging. c) The leakage current as a function of time with nanoampere accuracy in 180 hours holding at 3.678V (v.s.  $\text{Li}_x\text{In}$  or 4.3 V vs.  $\text{Li/Li}^+$ ), with the specific zoom-in at the end of 20 hours of aging to distinguish the leakage current values among different catholytes.

When reaching the voltage plateau during lithiation,  $\text{Li}_x\text{In}$  alloy resides at 0.62 V vs.  $\text{Li/Li}^+$ , lower than the reduction decomposition of the sulfide SSE. To delineate the sulfide SSE reduction decomposition at the anode surface during voltage holding, the  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  (LTO) was further chosen as the counter electrode to evaluate the leakage current of specific study of catholytes aging effects. In addition, LTO has a flat voltage plateau above 1.5 V vs.  $\text{Li/Li}^+$ , minimizing the reduction decomposition of the SSE at anode surface. In this case, the leakage current is more representative to the oxidation parasitic reactions, after the electrode reaches to its equilibrium state. LTO|LPSCI|NMC full cell with two representative catholytes (LPSCI, LIC-LPSCI) was tested in the same calendar protocol above with adjusting the cut-off voltage to 2.75 V exclusively because LTO has a potential at 1.55 V vs.  $\text{Li/Li}^+$ . The difference of leakage currents between two catholytes looks obvious in Fig 2, suggesting much higher rate of parasitic reactions using LIC-LPSCI catholyte. This is aligned with most significant capacity degradation observed in LIC-LPSCI previously after aging. Thus, we demonstrate the LTO anode as effective counter electrode in measuring leakage current accounting for the cathode side oxidation parasitic reaction in a sulfide all-solid-state cell. However, additional research is required to develop a quantitative model that accurately predicts the state of health of solid-state batteries (SSBs) based on their calendar aging behavior.

Further, we also noticed some ripples occurred particularly in LIC-LPSCI (Fig.2). The abruptly increased leakage current is very likely due to sudden increase of interface contact between cathode and catholyte to facilitate parasitic reactions, or due to the transitionally accelerated side reactions. Considering the mechanical nature of more rigid LIC than LPSCI, the catholyte

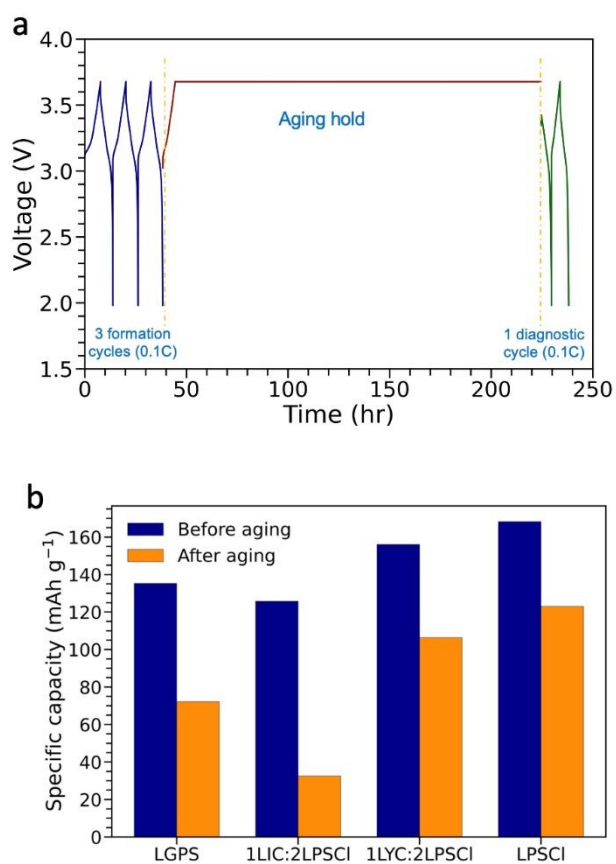

using LIC-LPSCI potentially suffer worse contact with NMC under same cell stack pressure. On the other hand, LPSCI current response also depicts at least two different reactions. The first reaction before 50 hours is suspected to be the slow relaxation of concentration gradient in the NMC, while it is typically completed within first few hours in the liquid cells as evidenced in many previous reports<sup>19, 20</sup>. However, SSBs suffer poor and less covered interface contact at cathode compared with liquid electrolyte lithium-ion battery. Thus, SSBs, owing to their sluggish ion transport, typically require longer time to reach the equilibrium during the voltage holding. Additionally, the later reaction after 50 hours is referred to parasitic reaction, and some ripples were also detected. These can be explained by the new formations of side products during parasitic reaction, contributing to dramatically changing the volume. This induces fluctuation of interfacial contact during the voltage holding, randomly facilitating parasitic reaction.

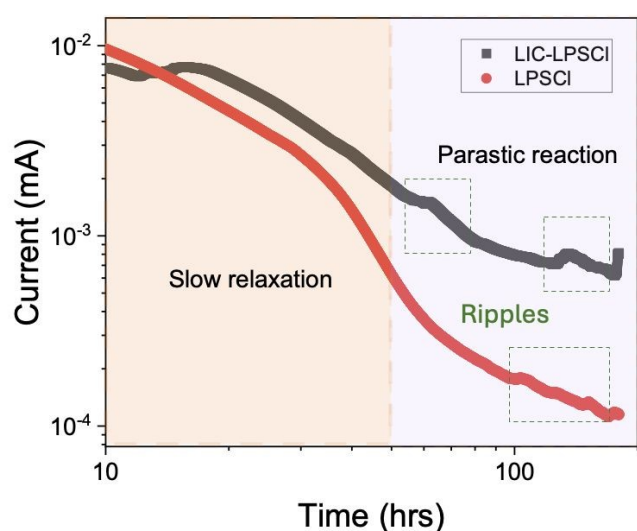


Figure 2: The leakage current response of LTO|LPSCI|NMC811 full cell over 180 hour of voltage holding (A light orange dashed line delineates major distinct electrochemical reactions, hypothesized to occur due to different leakage current responses). Two reactions are assumed during the voltage holding process: 1. Slow relaxation of NMC to reach equilibrium; 2. Parasitic reaction. Notable fluctuations are highlighted within green dashed boxes, indicating the additional relaxation reaction for probably more interfacial contact of electrode materials.

To further elucidate how interfacial resistance changes during calendar aging testing, in-situ electrochemical impedance spectroscopy (EIS) was applied to measure the impedance in three states: pristine, before aging, and after aging. Similar EIS evolution trends were observed for four catholytes shown in Figures 2a-d. Briefly, starting with the pristine state, the EIS exhibits a semi-circle followed by a straight tail. The resistance value at the junction between the semi-circle and the long tail directly reflects the bulk resistance,  $R_1$ . As shown in the four plots, after three formation cycles, the bulk resistance of the cell decreases due to the consolidation of solid electrolytes over cycling. After high voltage holding, it is

believed that interphases are formed, contributing to the second semi-circle present in the Nyquist plot. By comparing the three states, we aim to identify which step is limiting in different catholytes.

LPSCI cathodes exhibit the best performance with the lowest interfacial resistance post-aging, while LIC-LPSCI cathodes show the highest resistance and electrochemical instability at all stages, indicating chemical incompatibility explored further with advanced spectroscopy. Figs 2a and 2d depict that LPSCI- and LGPS-cathodes present similar initial bulk resistance, registered at 300 Ohms, superior to the LIC-LPSCI-cathode's 350 Ohms (shown in Fig 2b) but less effective than the LYC-LPSCI-cathode, which registers at 250 Ohms (Fig 2c). After three formation cycles, the LPSCI-, LGPS-, and LYC-LPSCI-cathodes demonstrate reduced bulk resistances of 100 Ohms, contracting with only a modest reduction to 300 Ohms for the LIC-LPSCI cathode. Upon aging, the LPSCI cathode significantly outperforms all other catholytes, maintaining an interfacial resistance of approximately 300 Ohms.

Notably, the interfacial resistance of the LIC-LPSCI cathode is about 300% greater than that of LPSCI, 250% more than LYC-LPSCI, and 200% higher than LGPS. Additionally, the post-aging phase reveals the LGPS cathode exhibits a higher interfacial resistance compared to the LPSCI cathode, despite presenting a lower leakage current, suggesting distinct interfacial side reaction pathways or mechanisms compared to LPSCI. Further, our findings confirm the electrochemical disfavor of the LIC-LPSCI cathode at all stages of the calendar aging test, corroborating earlier observations of significant capacity degradation. This is supported by previous reports of chemical incompatibility between LIC and LPSCI<sup>17, 21</sup>, prompting further investigation into this issue through Raman mapping and XAS (Ni K-edge and sulfur K-edge) analyses.

To explore the chemical and structural changes of CEI of post-aging electrodes, Raman spectroscopy was employed for mapping and analyzed using K-means clustering. Four post-aging samples were meticulously stripped with an insulating ceramic knife to expose the cathode in a plane view as shown in Fig S2. Figures 4a, 4d, 4g, and 4j present five distinct clusters, representing possible compositional variations in the cathode. The Raman shift ranges from 350 to 550  $\text{cm}^{-1}$ , indicating the P-S stretching. Notably, a peak at 422  $\text{cm}^{-1}$  indicative of a classical  $\text{PS}_4^{3-}$  was observed across all cathodes but varied locally due to environmental effects. Furthermore, the signal of the peak was normalized to the highest intensity to enhance the differentiation of the concentration of the 'new peak'. To examine the potential new substances or chemicals manifesting as new Raman peaks, we performed single Raman spectral analysis for the pristine cathode with different catholytes as a reference, as depicted in Fig S3. Our findings reveal that blending LIC or LYC with LPSCI does not yield new peaks other than  $\text{PS}_4^{3-}$ . However, as illustrated in Fig 4d depicts, a peak at 460.8  $\text{cm}^{-1}$  emerges on the LIC-LPSCI-cathode after aging, suggesting the formation of a new side product in the CEI. This

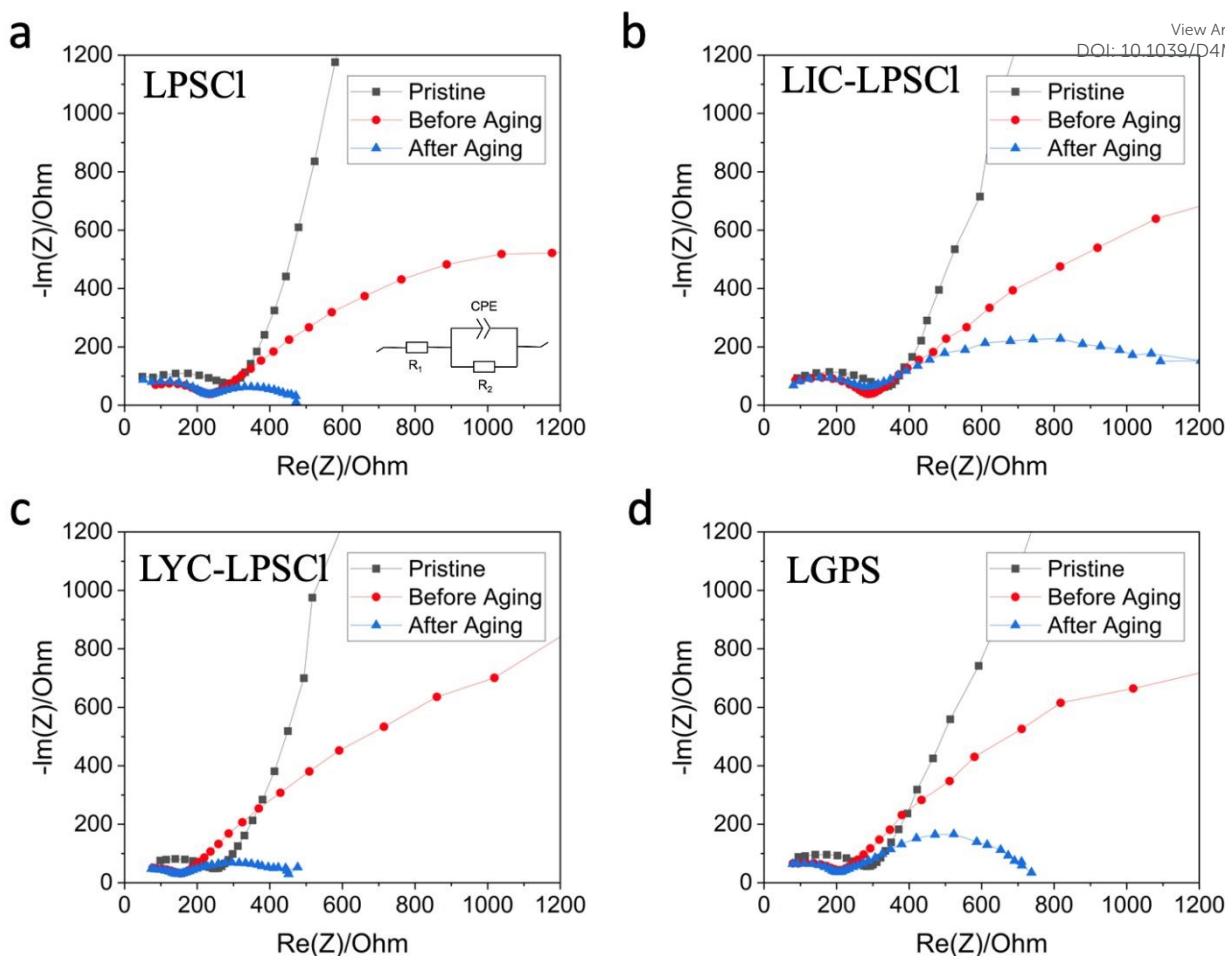


Figure 3: EIS Nyquist plot for four different catholytes of a) LPSCI, b) LIC-LPSCI, c) LYC-LPSCI, d) LGPS. The inset of a) includes the equivalent circuit model, with  $R_1$  representing bulk SSE resistance,  $R_2$  representing interfacial resistance, and CPE presenting the constant phase element.

peak is attributed to the S-S bond in molten/polymerized elemental sulfur<sup>22, 23</sup>. This observation underscores the chemical incompatibility between LIC and LPSCI, particularly when the cell is stored at a high SOC. Additionally, Figs 4b, 4e, 4h, and 4k reveal markedly heterogeneous CEIs, highlighting the complexity of reactions occurring within the cathodes. Moreover, the composition of each colored cluster was statistically analyzed in Figs 4c-f, enabling further quantification of clusters rich in LPSCI-rich or sulfur. For example, in the LIC-LPSCI-cathode, Clusters 2, 3, and 5 account for sulfur-rich regions, and their total percentage is over 50%, indicating significant degradation and sulfur enrichment within half of the CEI.

To explore the chemical and structural changes of CEI of post-aging electrodes, Raman spectroscopy was employed for mapping and analyzed using K-means clustering. Four post-aging samples were meticulously stripped with an insulating ceramic knife to expose the cathode in a plane view as shown in Fig S1. Figures 4a, 4d, 4g, and 4j present five distinct clusters, representing possible compositional variations in the cathode. The Raman shift ranges from 350 to 550  $\text{cm}^{-1}$ , indicating the P-S stretching. Notably, a peak at 422  $\text{cm}^{-1}$  indicative of a classical  $\text{PS}_4^{3-}$  was observed across all cathodes but varied locally due to

environmental effects. Furthermore, the signal of the peak was normalized to the highest intensity to enhance the differentiation of the concentration of the 'new peak'. To examine the potential new substances or chemicals manifesting as new Raman peaks, we performed single Raman spectral analysis for the pristine cathode with different catholytes as a reference, as depicted in Fig S2. Our findings reveal that blending LIC or LYC with LPSCI does not yield new peaks other than  $\text{PS}_4^{3-}$ . However, as illustrated in Fig 4d depicts, a peak at 460.8  $\text{cm}^{-1}$  emerges on the LIC-LPSCI-cathode after aging, suggesting the formation of a new side product in the CEI. This peak is attributed to the S-S bond in molten/polymerized elemental sulfur<sup>22, 23</sup>. This observation underscores the chemical incompatibility between LIC and LPSCI, particularly when the cell is stored at a high SOC. Additionally, Figs 4b, 4e, 4h, and 4k reveal markedly heterogeneous CEIs, highlighting the complexity of reactions occurring within the cathodes. Moreover, the composition of each colored cluster was statistically analyzed in Figs 4c-f, enabling further quantification of clusters rich in LPSCI-rich or sulfur. For example, in the LIC-LPSCI-cathode, Clusters 2, 3, and 5 account for sulfur-rich regions, and their total percentage is over 50%, indicating

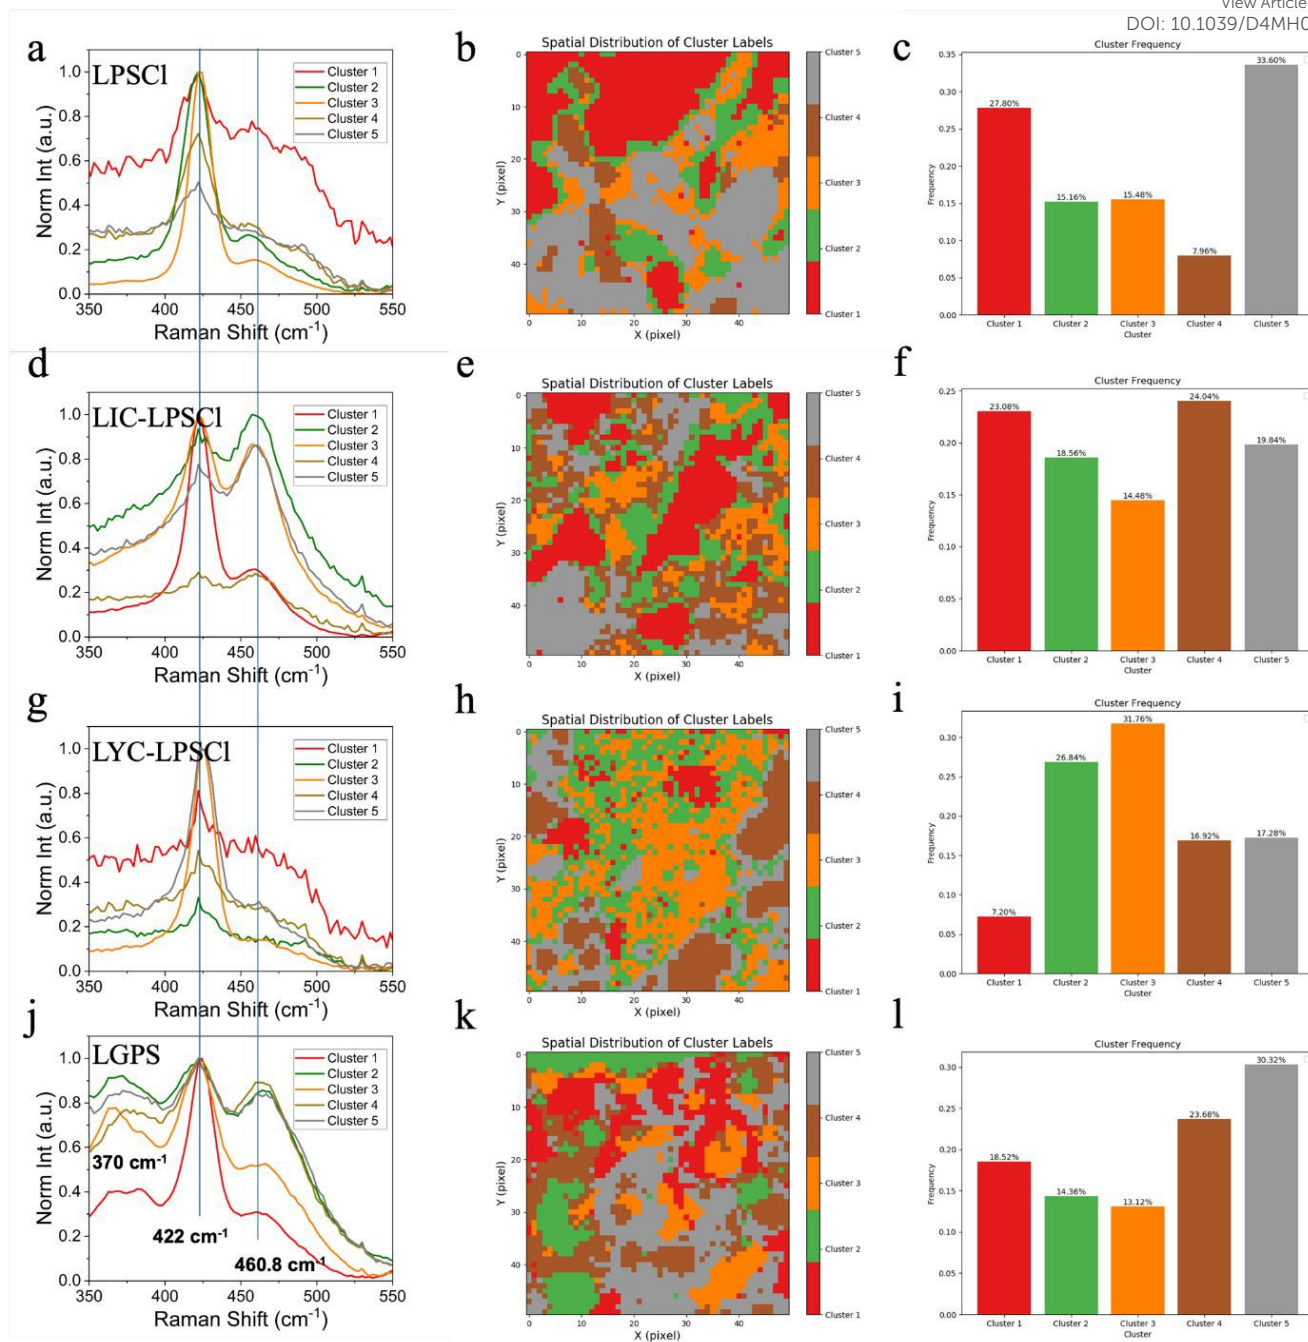


Figure 4: Comprehensive Raman spectral analysis through K-means clustering and spatial clustering distribution of different cathodes. Panels (a, d, g, j) display normalized Raman spectra for LPSCI, LIC-LPSCI, LYC-LPSCI, and LGPS cathodes, respectively, indicating distinct peaks corresponding to varied clusters. Panels (b, e, h, k) depict the spatial distribution of cluster labels within the cathodes, analyzed using machine learning with K-means clustering. Panels (c, f, i, l) present the frequency of each cluster, showcasing the predominance or rarity of specific Raman features across the cathode types.

significant degradation and sulfur enrichment within half of the CEI.

To determine the electrochemical stability of nickel in composite NMC811 cathode with different catholytes after 180 hours voltage holding, we performed Ni K-edge XANES and EXAFS on post calendar aging samples. In Shown in Fig 5a, the spectral shape of four aged samples with different catholytes exhibits remarkable similarity to the reference pristine LPSCI-

NMC spectrum. This similarity suggests the absence of macroscopic decomposition or phase changes in the NMC during high voltage holding. The first derivative of the XANES spectra enables a clear comparison of the nickel oxidation states across all the samples. Notably, the LIC-LPSCI-cathode (at 8343.8 eV) exhibits an oxidation state around 1 eV higher than other cathode counterparts (from 8342.4 to 8342.7 eV). This higher oxidation state suggests a greater degree of irreversible changes in the nickel of the LIC-LPSCI-cathode after calendar



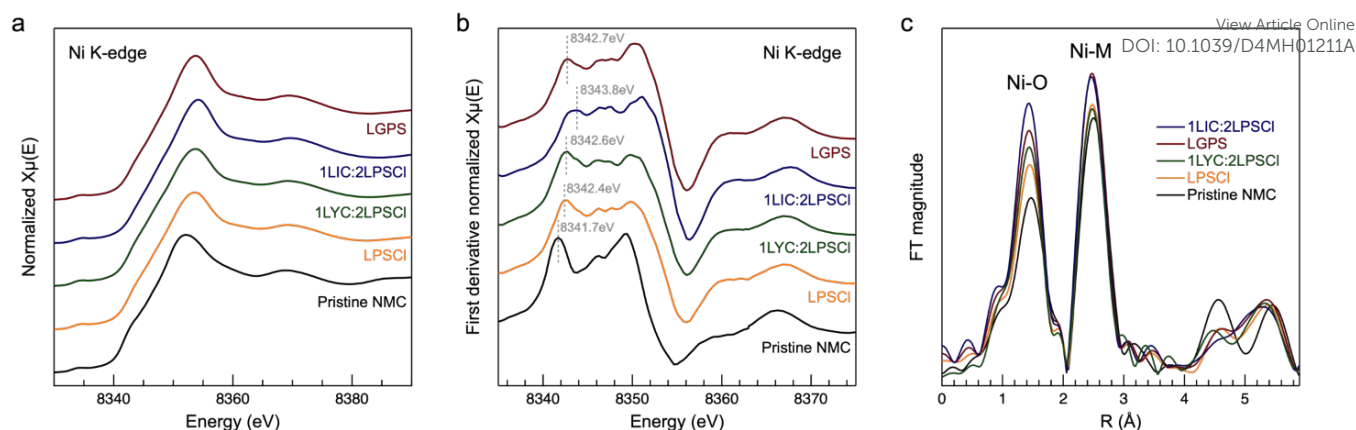


Figure 5: a) Normalized XANES spectra at Ni K-edge for pristine LPSCI- NMC811, aged cathode samples with different catholytes among LPSCI, LGPS, LYC-LPSCI, LIC-LPSCI (note that Ni XAS were collected from peeled off current collector, from the residue NMC on it and also all cathodes are in discharged condition); b) First derivative of XANES spectrum at Ni K-edge highlights oxidation difference among all catholytes; c) FT-EXAFS spectra in R space at Ni K-edge exhibits moderate changes in Ni local structure.

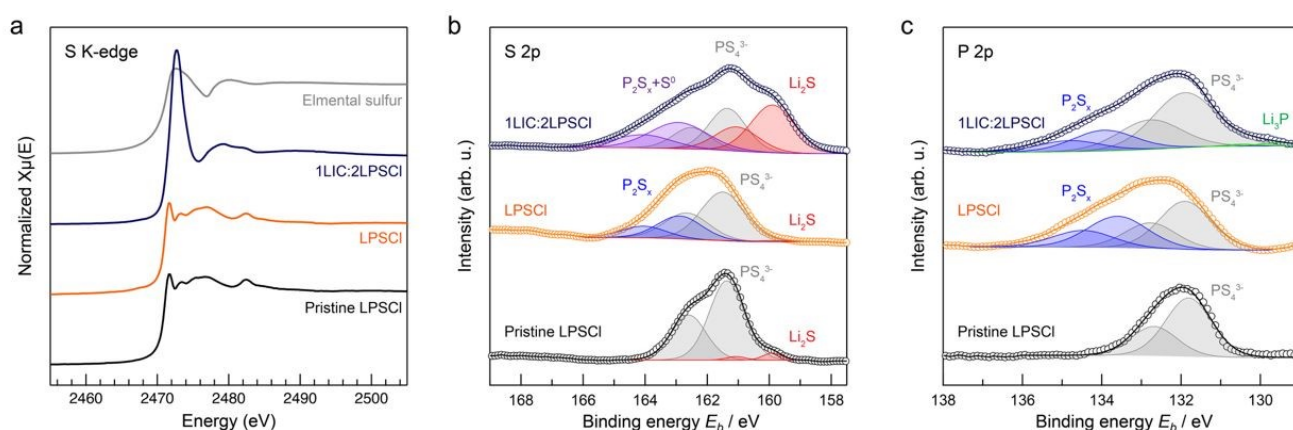


Figure 6: a) Normalized XANES spectra at S K-edge for pristine LPSCI- NMC811, aged NMC811 with LPSCI and LIC-LPSCI catholytes, and elemental sulfur as a control. (note that S XAS were collected from the cycled cell); XPS spectra of b) the S 2p, and c) the P 2p orbitals for pristine LPSCI, aged LPSCI catholyte and LIC-LPSCI catholyte, illustrating the decomposition pathway of LIC-LPSCI.

aging, consistent with the notably lower capacity retention observed in the electrochemical exploration. Despite all cathodes being maintained in a discharged state at completion, an imbalance in lithium levels relative to the pristine state persists. Consequently, in the Ni oxidation state in aged samples is elevated compared to the pristine NMC (8341.7 eV). Fourier-transformed EXAFS analysis of Ni-K edge across all cathodes reveals a consistent first peak at around 1.5 Å, corresponding to Ni–O first shell coordination, and a second peak at around 2.5 Å is ascribed to Ni–M (M = Ni, Mn and Co) scatterings. Comparisons with the pristine reference (shown in Fig. 5c) disclose no significant changes in bond distances, suggesting the stability of the NMC phase during high voltage holding<sup>24, 25</sup>.

To support the findings from Ni K-edge, we further performed XRD for both LPSCI and LIC-LPSCI samples before and after calendar aging, as seen in Fig S4-5. Pristine LPSCI vs aged LPSCI were analyzed as a control to aid in identification of NMC811 peaks for the cathode before vs after calendar aging. NMC811 peaks were confirmed via Mo to Cu 2θ conversion and compared to a previously reported diffractogram (ICSD #8362,

peak assignment for NMC811 summary can be accessed in Table S1)<sup>26</sup>. 0.1° peak shifts are observed for both LPSCI and NMC811 after cycling which suggests lithiation into the layered structure, causing slight lattice expansion. Additionally, a notable decrease in intensity is observed for all peaks corresponding to NMC 811 after aging. For peaks at higher 2θ values, such as the NMC 811 peak corresponding to (105) at 21.8° (Fig S6), the peak is absent after cycling. This overall decrease in peak intensity corresponds to a decrease in crystallinity over the course of calendar aging. Similar observations have been previously reported in literature<sup>27</sup>.

To illuminate the interfacial side reaction mechanisms between catholytes and the NMC811 cathode, we conducted sulfur K-edge XAS analyses on aged LPSCI and LIC-LPSCI aged samples. Notably, LIC-LPSCI sample presents a distinctively different sulfur chemistry compared to other LPSCI samples (Fig. 6a). This indicates that most of the sulfur in the LIC-LPSCI sample is oxidized to the level of elemental sulfur. This

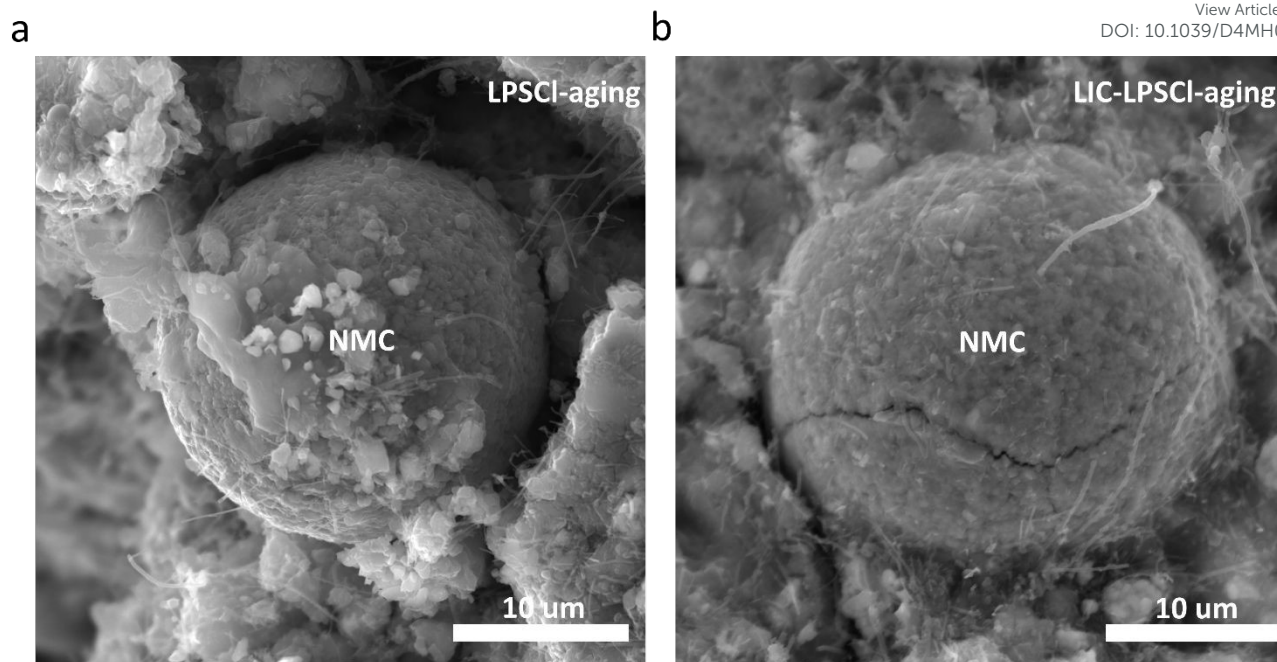


Figure 7. SEM micrographs displaying the morphological changes in cathodes after aging in various catholyte environments. (a) NMC particles aged in LPSCI; (b) NMC particles aged in LIC-LPSCI, exhibiting internal cracking.

observation corroborates our Raman mapping results, which identified sulfur as the primary side product in aged LIC-LPSCI samples, contributing to the limited capacity retention following the high voltage holding. Furthermore, XPS spectra for S 2p and P 2p orbitals in these samples indicate that the sulfur and phosphorus species of LPSCI degraded to  $P_2S_5$ , similar to what has been reported in literature<sup>28–30</sup> (fitting parameters can be found in Table S2–S3). The LIC-LPSCI catholyte undergoes significant decomposition to sulfur,  $Li_2S$ , and  $Li_3P$  (Fig. 6b and 6c). This degradation is likely driven by LIC's catalytic effect during high voltage holding, leading to irreversible decomposition and substantial cathode volume changes. These changes result in the NMC losing contact and being locked in a high oxidation state.

Our findings suggest that the poor capacity retention in LIC-LPSCI over calendar aging is due to the formation of parasitic products, such as elemental sulfur, and species containing higher irreversible oxidation state of nickel. However, it remains uncertain whether this substantial capacity degradation is solely attributed to chemical and structural change of CEI. To further investigate this, we performed scanning electron microscopy with energy-dispersive X-ray spectroscopy (SEM-EDX) to investigate the morphological change in NMC particles within LPSCI and LIC-LPSCI.

Notably, Fig 7b reveals that the LIC-LPSCI cathode presents internal cracks of NMC and voids between the NMC particle and LIC-LPSCI electrolyte after aging, which likely contribute to capacity degradation due to internal cracking of particles and loss of contact with catholyte and VGCF. In contrast, the LPSCI cathode demonstrates that the NMC particle remains intact with minimal internal microcracking (Fig 7a). To further justify


the different mechanical behaviors of the CEI when using different catholytes, we also included lower magnification SEM images of aged LPSCI-cathode and LIC-LPSCI-cathode in Fig S7 (a–b). We found that LPSCI cathode presents a more homogeneous material distribution compared to the LIC-LPSCI cathode, indicating less volume change and detachment in LPSCI-cathode during high voltage holding. Previous EIS measurement (Figs 3a and b) also underscores a significant difference in interfacial resistance between LPSCI cathode and LIC-LPSCI cathode after aging. This suggests that the impedance growth in the LIC-LPSCI cathode interphase is likely attributed to the formation of the elemental sulfur. The insulative S formation, together with the physical contact loss impedes lithium-ion transport between the NMC811 and the catholyte. These observations provide additional evidence that catholyte effects significantly influence the chemical and structural integrity of the cathode, as well as its mechanical stability.

Scheme 1 was presented below to highlight the key different chemical compositions on CEI after aging between LPSCI and LIC-LPSCI samples. The catholytes play a vital role in its calendar aging performance on the NMC. Highly oxidized elemental sulfur was detected as the major side product in the interphase. Higher oxidative state of Ni was also detected in aged LIC-LPSCI-cathode in comparison to LPSCI-cathode. It has been reported that highly oxidized or fully charged  $Ni^{4+}$  tends to react with electrolyte and facilitates parasitic reaction<sup>27</sup>.

To enhance NMC811 aging performance, two main strategies were explored: (1) using single crystal NMC and (2) optimizing charge/discharge conditions. Our preliminary results (Fig S8 (a–b)) show that both approaches—using single crystal NMC811 and reducing the c-rate during the formation cycle—effectively improve aging performance, as indicated by higher

capacity retention and lower leakage current. Further investigation into their mechanisms is planned for future studies.

dried using a rotovap at 80 °C before drying at 150 °C overnight. The sample was hand ground then pelletized and heated to 500 °C (heating rate 5 °C min<sup>-1</sup>) for 5 h under argon flow (30 mL min<sup>-1</sup>). Both samples showed less than 5% by wt. LiCl.

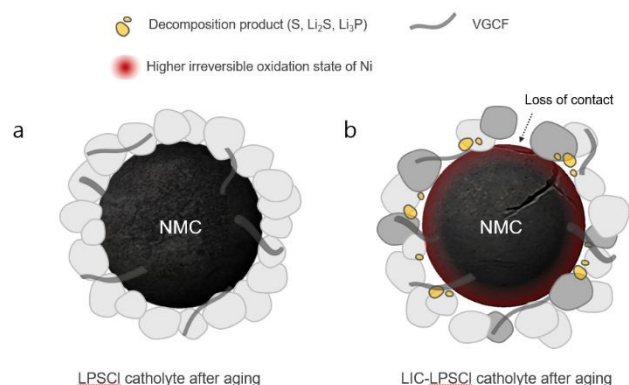

Scheme 1: An illustration to elucidate the difference in CEI and interface evolution of NMC811 after calendar aging process.

## Experimental

### LPSCI solid electrolyte thin film fabrication

The protocol of fabrication of LPSCI thin film was developed by our group and its step-by-step details can be accessed in<sup>31</sup>. binder solution was firstly prepared by mixing 1270kg/mol Poly(isobutylene) (PIB) (Scientific Polymer Products, Inc., New York, U.S), toluene, and two stirring bar. The stock binder solution is controlled in 7.4 w.t.% PIB. The LPSCI slurry was prepared by mixing as-obtained LPSCI (3-5 μm; NEI Corp., New Jersey, U.S.), stock binder solution, toluene with a ratio of solvent to solid ratio with 1: 1 in a glass vial. Then, three zirconia milling media were added into the vial and rolling overnight in a flat roller machine. The slurry was carefully distributed in a pre-dried meta film, following by 8 mil (200 μm) doctor blade casting. Well-casted LPSCI was dried in the large anti-chamber overnight. The LPSCI thin film was obtained by calendaring deposited and dried LPSCI between two mylar films to detach LPSCI. The thickness of calendar machine was fixed at 304 μm, and multiple calendaring process is needed to desired thickness of thin film and free-standing film was obtained. All calendar process is under room temperature (cold pressing).

### LIC and LYC synthesis

Li<sub>3</sub>InCl<sub>6</sub> was synthesized by first fully dissolving LiCl and InCl<sub>3</sub> (>99.99%, Sigma-Aldrich) in a 3:1 molar ratio in DI water. The solution was sonicated to deaerate then the bulk water was removed using a rotovap at 40 °C. The flask was quickly transferred to an Argon filled glovebox to limit continued exposure to moisture. We ground the precipitate by hand with mortar and pestle and dried the powder at 80 °C in vacuum overnight. Li<sub>3</sub>YCl<sub>6</sub> was synthesized similarly but with the addition of 3 molar equivalence of ammonium chloride added to the aqueous solution. Again, the solution was sonicated, then

### Composite electrode preparation

The composite NMC cathode was prepared by mixing LiNbO<sub>3</sub>-coated NMC811 active material acquired from NEI Corp. with manufactured standard specification of D<sub>50</sub> ~ 12 μm in Fig S9 (the thickness of LiNbO<sub>3</sub> coating was unveiled using TEM and is roughly 15 nm, as shown in Fig S10), various catholytes (LPSCI, LIC-LPSCI, LYC-LPSCI, and LGPS), and vapor grown carbon fiber (VGCF) in a weight ratio of 60:35:5 inside an argon-filled glovebox. Zirconia milling media was added to the mixture in a weight ratio of 5:1 relative to the composite mass. The sealed mixture was then dry-milled using a Turbula mixer for one hour. The composite LTO anode was prepared by mixing Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> active material, LPSCI, and VGCF in a weight ratio of 60:30:10 in an Ar-filled glovebox. Zirconia milling media was added to the mixture in a weight ratio of 5:1 relative to the composite mass. The sealed mixture was then dry-milled using a SPEX mixer for 5 mins.

### Battery assembly and electrochemical testing

Cell tests were conducted at room temperature using PEEK cells with a diameter of 6 mm. Two electrolyte sheets, each 6 mm in diameter, were placed in a mold and pressed at 20 bar to form the LPSCI layer. Subsequently, the cathode composite was spread on one surface, followed by placing carbon-coated Al foil as the current collector. This assembly was cold pressed at 60 bar for 3 minutes. Subsequently, a 5 mm diameter indium foil (150x150 TF, Custom Thermoelectric) and a 6 mm diameter copper foil were added on the opposite side of electrolyte layer. The stack was then secured by tightening to achieve a stack pressure of 50 MPa roughly.

The galvanostatic tests were conducted between 1.98 V and 3.678 V vs Li<sub>x</sub>In to examine the characteristics of different catholytes. The electrochemical impedance spectra (EIS) were obtained under open circuit conditions with an amplitude of 20 mV from 1 MHz to 100 MHz. Electrochemical evaluations and current leakage monitoring during the charged state were performed using Biologic EC-Lab software. All fabrication processes and electrochemical evaluations were carried out within an argon-filled glovebox.

### Raman mapping

Raman mapping was performed using a Horiba XploRA confocal Raman system. This system is equipped with a 405 nm UV laser, and the laser power was meticulously controlled to be below 500 μW to prevent sample damage. The mapping was conducted at 50x magnification, maintaining a spot size of 1 μm to ensure spatial resolution. Data were collected using a diffraction grating with 2400 grooves per mm. The mapping covered an area of 50 by 50 points, resulting in a total analysis of 2500 points. All Raman analysis results were processed and analyzed using the Horiba LabSpec 6 imaging and spectroscopy tool.



**SEM-EDX**

Materials were characterized using a TESCAN model MIRA3 scanning electron microscopy (SEM) equipped with an EDAX Octane Elect Super Silicon Drift Detector. We operated at 20 kV for microstructure characterization and X-ray-based chemistry analysis. We used the secondary electron (SE) mode to obtain microstructure images, and for analyzing chemical compositions, we utilized energy dispersive spectroscopy (EDS).

**TEM**

The TEM imaging was performed using a JEOL JEM-2100F equipped with a Schottky field emission gun operated at 200 kV.

**XAS**

Ni K-edge XANES and EXAFS spectra are collected using fluorescence mode at the beamline 4-1 of Stanford Synchrotron Radiation Light source (SSRL). Metallic nickel foil was used as reference and a Si (220) crystal was used as a monochromator. S K-edge XANES spectra are collected using fluorescence mode at the beamline 4-3 of SSRL. Si(111) double crystal monochromator was used with the cutoff energy of the upstream bare silicon mirror set below 6 keV to reject harmonics. To minimize atmospheric attenuation of the X-rays, the experiment was maintained in an atmosphere of helium gas. All data was analyzed using Athena.

**XPS**

XPS was performed using a PHI Versaprobe 3 with an Al K $\alpha$  source radiation of 1486.6 eV. Spot size was set to 200  $\mu$ m and pass energy was set to 55 eV. CasaXPS software was employed to fit the XPS core level spectra, with peak calibration being performed with respect to the C 1s peak (284.8 eV).

**XRD**

XRD was performed using a Rigaku SmartLab diffractometer with a Mo K- $\alpha$  x-ray source (0.71 Å). All samples were prepared using a sealed air-tight sample holder under inert atmosphere to preserve the samples during data collection. Diffractograms were collected from 5° to 40° at a scan rate of 0.7 °/min. Diffractograms of LPSCI before and after cycling were collected to aid in NMC 811 peak identification. A Mo to Cu 2 $\theta$  conversion was done for all NMC 811 peaks to compare to ICSD #8362 for phase confirmation.

**Conclusion**

In this study, we systematically explored the impact of various catholytes on the calendar aging of NMC811 in sulfide SSBs, highlighting the crucial role of catholyte composition in determining the electrochemical performance and durability of high-nickel NMC cathodes. Our comprehensive electrochemical evaluations, combined with advanced spectroscopic and imaging analyses, reveal that while LPSCI catholyte offers superior capacity retention and stability, the LIC-LPSCI blend

exhibits significant degradation, emphasizing the detrimental effects of catholyte incompatibility on cell longevity.

The data convincingly demonstrate that blending LIC with LPSCI accelerates interfacial side reactions and capacity degradation during calendar aging, underscoring the need for careful selection and optimization of catholyte materials in the design of SSBs. The profound impact of LIC-LPSCI on the electrochemical stability of NMC811, particularly in terms of irreversible nickel oxidation and the formation of parasitic sulfur species, calls for a reevaluation of current strategies employing mixed catholyte systems. Given the pressing demand for reliable and durable energy storage solutions, our findings stress the importance of further research into catholyte compositions that can enhance the interfacial stability and extend the operational life of sulfide SSBs. We note future studies should focus on the development of novel catholyte materials that can withstand high operational voltages and resist chemical decomposition, potentially through the incorporation of new halide and sulfide formulations or innovative coating technologies. Ultimately, the insights gained from this work not only contribute to a deeper understanding of the degradation mechanisms in high-nickel cathode materials but also pave the way for the next generation of all-solid-state battery technologies. By advancing our knowledge of catholyte-cathode interactions and their implications on battery performance, we move closer to achieving the high-capacity, long-life batteries needed for future energy storage applications.

**Conflicts of interest**

There are no conflicts to declare.

**Data availability**

A data availability statement (DAS) is required to be submitted alongside all articles. Please read our [full guidance on data availability statements](#) for more details and examples of suitable statements you can use.

**Acknowledgement**

This research was conducted at Oak Ridge National Laboratory, managed by UT Battelle, LLC, for the U.S. Department of Energy (DOE) and is sponsored by the Office of Energy Efficiency and Renewable Energy (EERE) in the Vehicle Technologies Office (VTO) through the Advanced Battery Materials Research (BMR) Program, managed by Drs. Simon Thompson and Tien Duong. This manuscript has been authored by UT-Battelle, LLC under Contract No. DE-AC05-00OR22725 with the U.S. Department of



Energy. SEM and EDX research were conducted as part of a user project at the Center for Nanophase Materials Sciences (CNMS), which is a US Department of Energy, Office of Science User Facility at Oak Ridge National Laboratory.

XPS was performed at the Stanford Nano Shared Facilities (SNSF), supported by the National Science Foundation under award ECCS-2026822. Use of the Stanford Synchrotron Radiation Lightsource at SLAC National Accelerator Laboratory is supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences under Contract No. DE-AC02-76SF00515. Y.C. was supported by the Japan Society for the Promotion of Science (JSPS) overseas research fellowship and the Stanford Energy Postdoctoral Fellowship and the Precourt Institute for Energy.

## References

1. Brahmabhatt, T.; Yang, G.; Self, E.; Nanda, J., Cathode–Sulfide Solid Electrolyte Interfacial Instability: Challenges and Solutions. *Frontiers in energy research* **2020**, *8*.
2. Byeon, Y.-W.; Kim, H. Review on Interface and Interphase Issues in Sulfide Solid-State Electrolytes for All-Solid-State Li-Metal Batteries *Electrochem* [Online], 2021, p. 452-471.
3. Shi, T.; Zhang, Y.-Q.; Tu, Q.; Wang, Y.; Scott, M. C.; Ceder, G., Characterization of mechanical degradation in an all-solid-state battery cathode. *Journal of Materials Chemistry A* **2020**, *8* (34), 17399-17404.
4. Li, X.; Jin, L.; Song, D.; Zhang, H.; Shi, X.; Wang, Z.; Zhang, L.; Zhu, L., LiNbO<sub>3</sub>-coated LiNi<sub>0.8</sub>Co<sub>0.1</sub>Mn<sub>0.1</sub>O<sub>2</sub> cathode with high discharge capacity and rate performance for all-solid-state lithium battery. *J. Energy Chem.* **2020**, *40*, 39-45.
5. Cai, X.; Wang, Z.; Xing, Y.; Zheng, C.; Yan, P.; Bao, W.; Xie, T.; Hu, Y.; Deng, Y.; Zhang, Y.; Wu, Y.; Yang, S.; Zheng, F.; Zhang, H.; Wang, Z.-J.; Xie, J., Promotion of the Nucleation of Ultrafine Ni-Rich Layered Oxide Primary Particles by an Atomic Layer-Deposited Thin Film for Enhanced Mechanical Stability. *Nano Letters* **2023**, *23* (12), 5770-5778.
6. Kim, Y.; Juarez-Yescas, C.; Liao, D. W.; Jangid, M. K.; Joshi, P.; Yang, H.; Zahiri, B.; Braun, P. V.; Dasgupta, N. P., Thin Free-Standing Sulfide/Halide Bilayer Electrolytes for Solid-State Batteries Using Slurry Processing and Lamination. *ACS Energy Letters* **2024**, *9* (4), 1353-1360.
7. Zhang, H.; Yu, Z.; Cheng, J.; Chen, H.; Huang, X.; Tian, B., Halide/sulfide composite solid-state electrolyte for Li-anode based all-solid-state batteries. *Chinese Chemical Letters* **2023**, *34* (11), 108228.
8. Han, Y.; Jung, S.; Kwak, H.; Jun, S.; Kwak, H.; Lee, J. H.; Hong, S.-T.; Jung, Y. S., Single- or Poly-Crystalline Ni-Rich Layered Cathode, Sulfide or Halide Solid Electrolyte: Which Will be the Winners for All-Solid-State Batteries? *Advanced Energy Materials* **2021**, *11*.
9. Lee, Y.; Jeong, J.; Lee, H. J.; Kim, M.; Han, D.; Kim, H.; Yuk, J. M.; Nam, K.-W.; Chung, K. Y.; Jung, H.-G., Lithium argyrodite sulfide electrolytes with high ionic conductivity and air stability for all-solid-state Li-ion batteries. *ACS Energy Letters* **2021**, *7* (1), 171-179.
10. Wang, J.; Zhao, S.; Zhang, A.; Zhuo, H.; Zhang, G.; Han, F.; Zhang, Y.; Tang, L.; Yang, R.; Wang, L., High lithium-ion conductivity, halide-coated, Ni-rich NCM improves cycling stability in sulfide all-solid-state batteries. *ACS Applied Energy Materials* **2023**, *6* (7), 3671-3681.
11. Dubarry, M.; Qin, N.; Brooker, P., Calendar aging of commercial Li-ion cells of different chemistries – A review. *Current Opinion in Electrochemistry* **2018**, *9*, 106-113.
12. Xiao, Y.; Wang, Y.; Bo, S.-H.; Kim, J. C.; Miara, L. J.; Ceder, G., Understanding interface stability in solid-state batteries. *Nature Reviews Materials* **2020**, *5* (2), 105-126.
13. Kim, W.; Noh, J.; Lee, S.; Yoon, K.; Han, S.; Yu, S.; Ko, K.-H.; Kang, K., Aging Property of Halide Solid Electrolyte at the Cathode Interface. *Advanced Materials* **2023**, *35* (32), 2301631.
14. McBrayer, J. D.; Rodrigues, M.-T. F.; Schulze, M. C.; Abraham, D. P.; Apblett, C. A.; Bloom, I.; Carroll, G. M.; Colclasure, A. M.; Fang, C.; Harrison, K. L.; Liu, G.; Minter, S. D.; Neale, N. R.; Veith, G. M.; Johnson, C. S.; Vaughey, J. T.; Burrell, A. K.; Cunningham, B., Calendar aging of silicon-containing batteries. *Nature Energy* **2021**, *6* (9), 866-872.
15. Yun, J.; Shin, H. R.; Hoang, T. D.; Kim, S.; Choi, J. H.; Kim, B.; Jung, H.; Moon, J.; Lee, J.-W., Deciphering the critical degradation factors of solid composite electrodes with halide electrolytes: interfacial reaction versus ionic transport. *Energy Storage Materials* **2023**, *59*, 102787.
16. Ye, Q.; Li, X.; Zhang, W.; Xia, Y.; He, X.; Huang, H.; Gan, Y.; Xia, X.; Zhang, J., Slurry-coated LiNi<sub>0.8</sub>Co<sub>0.1</sub>Mn<sub>0.1</sub>O<sub>2</sub>-Li<sub>3</sub>InCl<sub>6</sub> composite cathode with enhanced interfacial stability for sulfide-based all-solid-state batteries. *ACS Applied Materials & Interfaces* **2023**, *15* (15), 18878-18888.
17. Rosenbach, C.; Walther, F.; Ruhl, J.; Hartmann, M.; Hendriks, T. A.; Ohno, S.; Janek, J.; Zeier, W. G., Visualizing the chemical incompatibility of halide and sulfide-based electrolytes in solid-state batteries. *Advanced Energy Materials* **2023**, *13* (6), 2203673.
18. Schulze, M. C.; Rodrigues, M.-T. F.; McBrayer, J. D.; Abraham, D. P.; Apblett, C. A.; Bloom, I.; Chen, Z.; Colclasure, A. M.; Dunlop, A. R.; Fang, C.; Harrison, K. L.; Liu, G.; Minter, S. D.; Neale, N. R.; Robertson, D.; Tornheim, A. P.; Trask, S. E.; Veith, G. M.; Verma, A.; Yang, Z.; Johnson, C., Critical Evaluation of Potentiostatic Holds as Accelerated Predictors of Capacity Fade during Calendar Aging. *Journal of The Electrochemical Society* **2022**, *169* (5), 050531.
19. Cai, J.; Zhou, X.; Li, T.; Nguyen, H. T.; Veith, G. M.; Qin, Y.; Lu, W.; Trask, S. E.; Fonseca Rodrigues, M.-T.; Liu, Y.; Xu, W.; Schulze, M. C.; Burrell, A. K.; Chen, Z., Critical Contribution of Imbalanced Charge Loss to Performance Deterioration of Si-Based Lithium-Ion Cells during Calendar Aging. *ACS Applied Materials & Interfaces* **2023**, *15* (41), 48085-48095.
20. Cai, J.; Yang, Z.; Zhou, X.; Wang, B.; Suzana, A.; Bai, J.; Liao, C.; Liu, Y.; Chen, Y.; Song, S.; Zhang, X.; Wang, L.; He, X.; Meng, X.; Karami, N.; Ali Shaik Sulaiman, B.; Chernova, N. A.; Upreti, S.; Prevel, B.; Wang, F.; Chen, Z., Unveiling the parasitic-reaction-driven surface reconstruction in Ni-rich cathode and the electrochemical role of Li<sub>2</sub>CO<sub>3</sub>. *J. Energy Chem.* **2023**, *85*, 126-136.
21. Samanta, S.; Bera, S.; Biswas, R. K.; Mondal, S.; Mandal, L.; Banerjee, A., Ionocovalency of the Central Metal Halide Bond-Dependent Chemical Compatibility of Halide Solid Electrolytes with Li<sub>6</sub>PS<sub>5</sub>Cl. *ACS Energy Letters* **2024**, 3683-3693.
22. Andrikopoulos, K.; Kalampounias, A.; Falagara, O.; Yannopoulos, S., The glassy and supercooled state of elemental sulfur: Vibrational

modes, structure metastability, and polymer content. *The Journal of chemical physics* **2013**, *139*, 124501.

23. Nims, C.; Cron, B.; Wetherington, M.; Macalady, J.; Cosmidis, J., Low frequency Raman Spectroscopy for micron-scale and in vivo characterization of elemental sulfur in microbial samples. *Sci Rep* **2019**, *9* (1), 7971.

24. Ates, M. N.; Mukerjee, S.; Abraham, K. M., A high rate Li-rich layered MNC cathode material for lithium-ion batteries. *RSC Advances* **2015**, *5* (35), 27375-27386.

25. Fang, L.; Chen, M.; Nam, K.-W.; Kang, Y.-M., Redox Evolution of Li-Rich Layered Cathode Materials. *Batteries* **2022**, *8* (10), 132.

26. Stival, U. A.; Gallo, I. B. C.; Gonin, C. F. N.; Reis, S. L.; Grosso, R. L.; Kosciuk, J. B.; Franchetti, M. G. S.; Leão, B.; Oliveira, F. E. R.; Souza, A.; Freitas, H. R.; Monteiro, R. S.; Parreira, L. S.; Berton, M. A. C., Experimental challenges for electrochemical evaluation of cathodes in lithium-ion battery half-cells. *Journal of Energy Storage* **2023**, *72*, 108706.

27. Li, T.; Yuan, X.-Z.; Zhang, L.; Song, D.; Shi, K.; Bock, C., Degradation Mechanisms and Mitigation Strategies of Nickel-Rich NMC-Based Lithium-Ion Batteries. *Electrochemical Energy Reviews* **2020**, *3* (1), 43-80.

28. Tan, D. H. S.; Wu, E. A.; Nguyen, H.; Chen, Z.; Marple, M. A. T.; Doux, J.-M.; Wang, X.; Yang, H.; Banerjee, A.; Meng, Y. S., Elucidating Reversible Electrochemical Redox of Li<sub>6</sub>PS<sub>5</sub>Cl Solid Electrolyte. *ACS Energy Letters* **2019**, *4* (10), 2418-2427.

29. Wang, L.; Sun, X.; Ma, J.; Chen, B.; Li, C.; Li, J.; Chang, L.; Yu, X.; Chan, T.-S.; Hu, Z.; Noked, M.; Cui, G., Bidirectionally Compatible Buffering Layer Enables Highly Stable and Conductive Interface for 4.5 V Sulfide-Based All-Solid-State Lithium Batteries. *Advanced Energy Materials* **2021**, *11* (32), 2100881.

30. Hood, Z. D.; Mane, A. U.; Sundar, A.; Tepavcevic, S.; Zapol, P.; Eze, U. D.; Adhikari, S. P.; Lee, E.; Sterbinsky, G. E.; Elam, J. W.; Connell, J. G., Multifunctional Coatings on Sulfide-Based Solid Electrolyte Powders with Enhanced Processability, Stability, and Performance for Solid-State Batteries. *Advanced Materials* **2023**, *35* (21), 2300673.

31. Mills, A.; Kalnaus, S.; Tsai, W.-Y.; Su, Y.-F.; Williams, E.; Zheng, X.; Vaidyanathan, S.; Hallinan Jr, D. T.; Nanda, J.; Yang, G., Elucidating Polymer Binder Entanglement in Freestanding Sulfide Solid-State Electrolyte Membranes. *ACS Energy Letters* **2024**, *9*, 2677-2684.

View Article Online  
DOI: 10.1039/D4MH01211A

[View Article Online](#)  
DOI: 10.1039/D4MH01211A

## Data Availability

The data supporting this article have been included as part of the Supplementary Information.