

# LEGIBILITY NOTICE

A major purpose of the Technical Information Center is to provide the broadest dissemination possible of information contained in DOE's Research and Development Reports to business, industry, the academic community, and federal, state and local governments.

Although a small portion of this report is not reproducible, it is being made available to expedite the availability of information on the research discussed herein.

LA-UR--89-3331

DE90 002440

**TITLE: RF SUPERCONDUCTIVITY RESEARCH AND DEVELOPMENT  
AT LOS ALAMOS NATIONAL LABORATORY**

**AUTHOR(S)** D. W. Cooke, MP-14; E. R. Gray, AT-1; R. J. Houlton, AT-1;  
G. P. Lawrence, AT-DO; J. A. McGill, MP-10; E. Meyer, AT-2;  
C. Morris, MP-10; B. Rusnak, AT-1; and T. P. Starke, DRA-DIO

**SUBMITTED TO** The 4th Workshop on RF Superconductivity  
Tsukuba, Japan  
August 14-18, 1989

**DISCLAIMER**

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

By acceptance of this article, the publisher recognizes that the U.S. Government retains a non-exclusive, royalty-free license to publish or reproduce the published form of this contribution, or to allow others to do so, for U.S. Government purposes.

The Los Alamos National Laboratory requests that the publisher identify this article as work performed under the auspices of the U.S. Department of Energy.

**MASTER**

**Los Alamos**

Los Alamos National Laboratory  
Los Alamos, New Mexico 87545

The 4th Workshop on RF Superconductivity  
Tsukuba, Japan  
August 14 - 18, 1989

RF SUPERCONDUCTIVITY RESEARCH AND DEVELOPMENT  
AT LOS ALAMOS NATIONAL LABORATORY

D. W. Cooke, E. R. Gray, R. J. Houlton, G. P. Lawrence, J. A. McGill,  
E. Meyer, C. Morris, B. Rusnak, and T. P. Starke

Los Alamos National Laboratory  
Los Alamos, New Mexico 87545

Los Alamos National Laboratory is engaged in two distinct areas of rf superconductivity research and development. One program is devoted to studying the rf properties of high-temperature superconductors (HTS) and assessing their potential for accelerator-cavity applications. Our best results to date have come from  $\text{YBa}_2\text{Cu}_3\text{O}_7$  films ( $0.8 \mu\text{m}$ ) electron-beam deposited onto  $\text{LaGaO}_3$  substrates. A typical surface resistance value is  $0.2 \pm 0.1 \text{ m}\Omega$  measured at 22 GHz and 4 K, which is only a factor of 2 - 4 higher than Nb.

A second area of rf superconductivity R&D at Los Alamos involves fabricating and testing conventional Nb superconducting rf cavities. Facilities are being constructed for polishing, cleaning, and testing both small (3 GHz) and large (805-MHz) Nb cavities. Much of our effort is being devoted to understanding the proper techniques for welding, cleaning, and handling Nb cavities, to ensure good high-field performance.

Nb cavity applications are foreseen in upgrades to LAMPF, compact free-electron lasers, and high-current cw proton linacs. A single 402.5-MHz Nb cavity (in a beam cryostat) is presently being acquired from industry to provide a momentum compactor for the low-energy pion beam at LAMPF.

## HTS Research

Applications involving high-temperature superconductors (HTS) generally fall into two categories; those that require low values of surface resistance ( $R_s$ ) in negligible surface magnetic fields ( $H_{rf}$ ), and those that require low values of  $R_s$  in moderate to strong fields. Radiofrequency (rf) accelerating cavities demand the latter criterion. The possibility of fabricating HTS cavities that exhibit high Q-values in strong rf fields (~ few hundred oersteds) at temperatures greater than LHe (4 K) has motivated many researchers to investigate the electrodynamic properties of these unique materials.<sup>1-3</sup>

We have employed several cavity types to investigate  $R_s$  of HTS materials. A 3-GHz Nb cavity (TM<sub>010</sub> fundamental mode) operating at 4 K has been used to measure  $R_s$  of bulk ceramic specimens. For polycrystalline  $\text{YBa}_2\text{Cu}_3\text{O}_7$  (YBCO) we have attained  $R_s$  values near 0.1 mΩ at 4 K (3 GHz), which is two orders of magnitude higher than Nb. Much lower values have been obtained from oriented thin films.<sup>4</sup> Utilizing 22-GHz Cu and Nb cavities (TE<sub>011</sub> fundamental mode), we have measured  $R_s$  of several YBCO films (typically 0.8 μm thickness) which were electron-beam deposited onto 1" LaGaO<sub>3</sub> substrates. Typical  $R_s$  values obtained at 22 GHz and 4 K are 0.8±0.1 mΩ, with the best value being 0.2±0.1 mΩ.

The surface resistances of both 1" and 1.5" Tl-Ba-Ca-Cu-O (TBCCO) polycrystalline films that have been magnetron-sputtered onto yttria-stabilized zirconia (YSZ) have also been measured. In addition to the 22-GHz Cu cavity (1" films), we have also used an 18-GHz Cu cavity (1.5" films) for these measurements. A typical  $R_s$

value for a 1" TBCCO film measured at 12 K and 22 GHz is  $5 \pm 2$  m $\Omega$ ; this value increases to  $\sim 50$  m $\Omega$  at 77 K. As shown in Fig. 1, the value at 4 K is only slightly lower than Cu. The 1.5" TBCCO films are characterized by  $R_s$  values that are approximately equal to Cu at 4 K. By orienting the crystalline axes of these films we expect to achieve lower  $R_s$  values.

For rf cavity applications it is necessary to achieve low values of  $R_s$  in the presence of moderately high surface magnetic fields. A typical accelerating electric field of 5 MV/m corresponds to  $H_{rf} \sim 300 - 500$  Oe.  $R_s$  vs.  $H_{rf}$  measurements on single crystals, laser-ablation produced films, and grain-aligned bulk ceramics indicate that  $R_s$  becomes very large for  $H_{rf} > 90$  Oe.<sup>5</sup> These measurements were made by placing the samples on a sapphire pedestal inside an evacuated cavity. This arrangement does not allow the rf-generated heat to be readily dissipated, and, consequently, the value of  $H_{rf}$  where  $R_s$  rapidly increases may not be the intrinsic value. Similar measurements on long cylindrical rods of YBCO immersed in LN<sub>2</sub> or LHe show that field values of  $\sim 640$  Oe can be achieved without destroying superconductivity.<sup>6</sup> Preliminary measurements of  $R_s$  vs.  $H_H$  on our YBCO films indicate that  $R_s$  approaches its normal-state value for  $H_H > 20$  Oe. Further measurements on YBCO and TBCCO films are awaiting construction and testing of an 18-GHz Nb cavity.

### Conventional Superconductor Research

A second area of rf superconductivity research and development at Los Alamos involves fabricating and testing conventional Nb rf cavities. Facilities are being constructed for

polishing, cleaning, and testing both small (3-GHz) and large (805-MHz) Nb cavities. Progress to date includes installation of a clean room and a clean-water system, design of a chemical-polishing system, installation of test cryostats, and fabrication of four 3-GHz cavities, which are presently undergoing initial high-field testing. Preliminary results for the first cavity showed that an electric field of  $8 \pm 1$  MV/m could be achieved in the cavity before it suffered a superconducting quench, presumably due to surface defects. The significance of this result lies not in the value of electric field attained (which is above the industry standard value of 5 MV/m), but in the fact that this represents the first superconducting Nb cavity which was fabricated, cleaned, and tested at Los Alamos National Laboratory, and thus represents our entry into this high-technology arena.

Two 805-MHz Nb cavities have been formed and e-beam welded and are awaiting chemical cleaning; these are shown in Fig. 2. Cavities of this particular frequency are of interest because they represent the operating frequency of the Los Alamos Meson Physics Facility (LAMPF) accelerator. Future upgrades to this facility would probably involve installation of superconducting cavities, and consequently we would like to have the on-site capability to fabricate and test such devices. Presently, however, much of our experimental effort is devoted to understanding the proper techniques for welding, cleaning, and handling Nb cavities to ensure good high-field performance.

## Applications

Niobium cavity applications are foreseen in upgrades to LAMPF, compact free-electron lasers, and high-current cw proton linacs. A single 402.5 MHz Nb cavity (in a beam cryostat) is presently being acquired from industry to provide a momentum compactor for the low-energy pion beam at LAMPF. The basic idea of this application is to take the pion beam at the achromatic focus of the LAMPF low-energy pion (LEP) channel and inject it into the superconducting cavity at zero degrees phase angle so that it does not undergo any net acceleration. Particles at the early part of the pion bunch are decelerated while those arriving at a later time are accelerated. Because there is a correlation between time and energy, the net result of this "SCRUNCHER" (superconducting rf unit for changing energy resolution) is to compress the energy spread of the pion beam as shown in Fig. 3. This yields a factor of five improvement in the beam flux per MeV of energy. Currently the energy spread is controlled by a set of jaws which accept only a small momentum bite. Installation of the SCRUNCHER cavity will allow us to take the full acceptance of the channel ( $\pm 2\%$  in momentum) and compress it to  $\pm 0.4\%$ .


The SCRUNCHER is being built by INTERATOM using standard technology, except that it will be pipe-cooled rather than bath cooled. It will be tested at INTERATOM and, assuming that it meets technical specifications, will be delivered to LAMPF where it will be installed at LEP.

## REFERENCES

1. N. Klein, G. Müller, H. Piel, B. Roas, L. Schultz, U. Klein, and M. Peiniger, *Appl. Phys. Lett.* **54**, 757 (1989).
2. D. L. Rubin, K. Green, J. Gruschus, J. Kirchgessner, D. Moffat, H. Padamsee, J. Sears, Q. S. Shu, L. F. Schnemann, and J. V. Waszczak, *Phys. Rev. B* **38**, 6538 (1988).
3. D-H. Wu, W. L. Kennedy, C. Zahopoulos, and S. Sridhar, *Appl. Phys. Lett.* **55**, 696 (1989).
4. D. W. Cooke, E. R. Gray, R. J. Houlton, B. Rusnak, E. A. Meyer, J. G. Beery, D. R. Brown, F. H. Garzon, I. D. Raistrick, A. D. Rollett, and R. Bolmaro, *Appl. Phys. Lett.* **55**, 914 (1989).
5. H. Padamsee, J. Kirchgessner, D. Moffat, D. L. Rubin, Q. S. Shu, A. Inam, X. D. Wu, L. Nazar, M. S. Hegde, and T. Venkatesan, CLNS 89/929, Cornell University, Ithaca, NY, 1989.
6. J. R. Delayen and C. L. Bohn, *Phys. Rev. B*, to be published.

## FIGURE CAPTIONS

- Fig. 1. Surface resistance of TBCCO and YBCO. 1" and 1.5" samples are measured at 22 and 18 GHz, respectively. Cu and Nb are shown for reference.
- Fig. 2. 805-MHz Nb cavities fabricated at Los Alamos.
- Fig. 3. Schematic illustration of pion beam compression as anticipated from installation of a superconducting 402.5-MHz Nb cavity at the LAMPF low-energy pion channel.

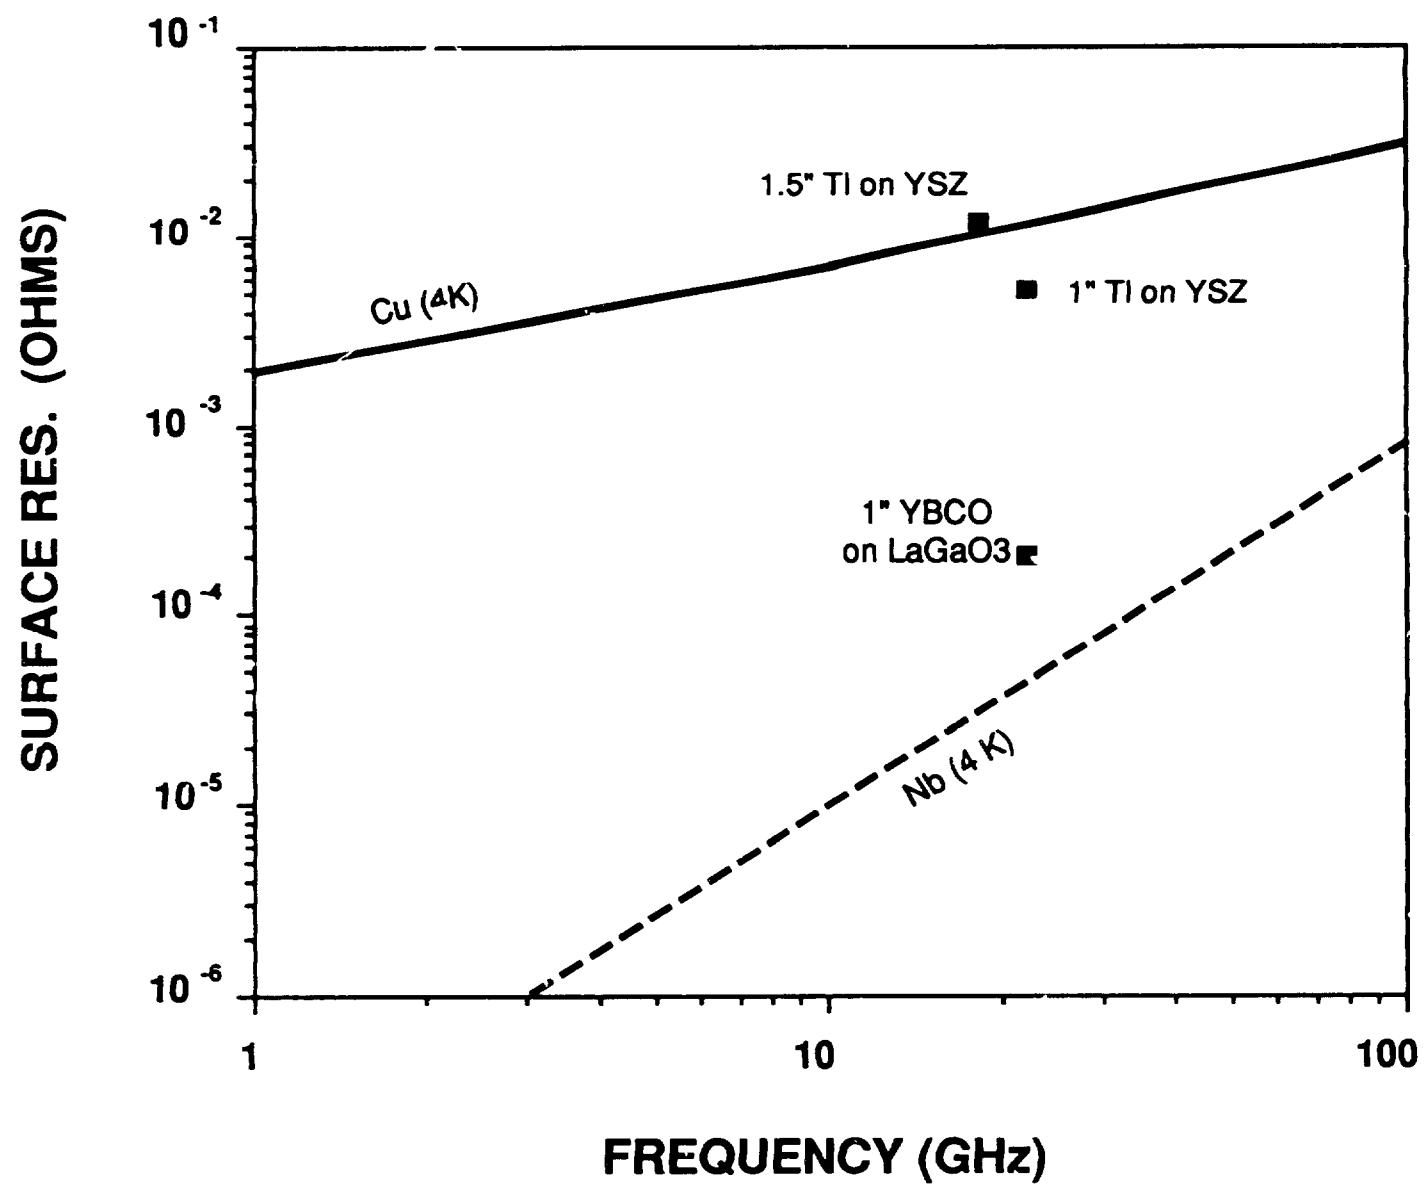

LOS ALAMOS NATIONAL LABORATORY  
805 MHz NIOBIUM  
SUPERCONDUCTING CAVITY  
AT-1 / MST-6 / WX-3

JULY 1989



COOKE & GRAY  
FIG. 2

# ENERGY COMPRESSION OF A BEAM

