

✓

Chemical Engineering Division  
Argonne National Laboratory  
9700 S. Cass Avenue  
Argonne, Illinois 60439

MASTER

DISCLAIMER

This book was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

Experiments on Cold Trap Regeneration by NaH Decomposition

by

C. C. McPheeters, S. B. Skladzien and D. J. Rau

The submitted manuscript has been authored  
by a contractor of the U. S. Government  
under contract No. W-31-109-ENG-38.  
Accordingly, the U. S. Government retains a  
nonexclusive, royalty-free license to publish  
or reproduce the published form of this  
contribution, or allow others to do so, for  
U. S. Government purposes.

October 1979

eb  
DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

## **DISCLAIMER**

**This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.**

---

## **DISCLAIMER**

**Portions of this document may be illegible in electronic image products. Images are produced from the best available original document.**

TABLE OF CONTENTS

	<u>Page</u>
ABSTRACT . . . . .	1
I. INTRODUCTION . . . . .	1
II. PRINCIPALS OF HYDROGEN EVOLUTION FROM NaH IN Na . . . . .	3
III. EXPERIMENTAL APPARATUS . . . . .	7
IV. RESULTS AND DISCUSSION . . . . .	10
V. CONCLUSIONS AND FUTURE DIRECTIONS . . . . .	16
REFERENCES . . . . .	18

## LIST OF FIGURES

<u>No.</u>	<u>Title</u>	<u>Page</u>
1.	Temperature required to nucleate bubbles of various sizes under vacuum and atmospheric pressure . . . . .	5
2.	Test apparatus for removing hydrogen from simulated cold traps (SCT) . . . . .	8
3.	Contact print of pretest neutron radiograph of SCT number 2. . . . .	11
4.	Contact print of post-test neutron radiograph of SCT number 2. . . . .	12
5.	Hydrogen evolution observed during tests 2a and 2b with SCT number 2. . . . .	13
6.	Hydrogen evolution rates observed in all tests . .	15

## LIST OF TABLES

<u>No.</u>	<u>Title</u>	<u>Page</u>
1.	Summary of Cold Trap Unloading Experiment Parameters . . . . .	9
2.	Summary of Cold Trap Unloading Test Results . . .	14

EXPERIMENTS ON COLD TRAP REGENERATION BY NaH DECOMPOSITION

by

C. C. McPheevers, S. B. Skladzien and D. J. Raue

ABSTRACT

Cold trap regeneration may be very important in future LMFBRs because of the expected high hydrogen source from the steam generators. This hydrogen precipitates as NaH in the cold trap and may fill the trap within one year of operation. Several methods of cold trap regeneration were considered, but the simplest and least expensive appears to be decomposition of NaH under vacuum at elevated temperatures.

Experiments were done to assess the feasibility of this method for cold trap regeneration. Small-scale simulated cold traps (SCT) were loaded with NaH and NaH plus Na<sub>2</sub>O, and were heated both under vacuum and under a sweep gas at 100 kPa. The evolved hydrogen was converted to water by a CuO bed and collected in a weighing tube.

The experimental results indicate that significant hydrogen evolution rates occur  $\sim$ 100 K lower in temperature under vacuum (600 K) than under 100 kPa pressure (700 K). The results also indicate that the hydrogen evolution rate is reduced (at 600 K) more than one order of magnitude (to  $\sim$ .15  $\mu$ g/s) by the addition of  $\sim$ 50% Na<sub>2</sub>O.

I. INTRODUCTION

Operation of liquid sodium systems such as the LMFBR heat transfer systems requires continuous removal of impurities such as oxygen and hydrogen from the sodium. Cold trapping is the most widely used method for this purification. Cold traps are usually operated until they become filled with impurity deposits to the extent that a flow blockage occurs. At that point, the cold trap is removed from the system and replaced with a new one. The choked cold trap is usually stored indefinitely or cleaned up with steam or alcohol for refurbishing and reuse. The practice of replacing choked cold traps may be acceptable in cases where the useful lifetime of the trap is five to ten years; however, if the expected time to plugging were on the order of one to two years, the replacement operation would be too expensive and time-consuming.

Measurements of diffusion of hydrogen from water-side corrosion of steam generator tubes through the tube wall to the sodium side<sup>1</sup> indicate

that the hydrogen source rate may be sufficient to fill the cold trap with NaH within one year of full-power operation. This short cold trap lifetime is expected only in the intermediate heat transport system (IHTS) while the expected lifetime of the primary heat transport system (PHTS) cold traps is much longer because the impurity sources are much smaller.

Since the primary impurity of concern in the IHTS is hydrogen, thermal decomposition of NaH should be well suited for regeneration of the IHTS cold traps. This method consists of draining some of the sodium from the cold trap to provide a cover gas space, heating the trap to 670 K (400°C) under vacuum, collecting sodium vapors in a high-efficiency vapor trap, converting the evolved hydrogen to water and collecting the water for disposal as tritiated water. Of course, impurities other than NaH, such as Na<sub>2</sub>O, will remain in the cold trap. After many regeneration cycles, these stable impurities may have accumulated sufficiently to require replacement of the cold trap; however, extending the cold trap lifetime from one year to, perhaps, five to ten years justifies use of the NaH decomposition method.

Several methods of cold trap regeneration other than thermal decomposition of NaH have been attempted with varying degrees of success. These methods include replacement of the mesh section, steam or alcohol cleaning, dissolution of impurities with hot sodium, and reaction of Na<sub>2</sub>O and NaH to form NaOH to be drained from the trap. These methods are discussed in the following paragraphs to place them in perspective; however, they are not discussed in detail because the primary objective of this paper is to present the results of recent studies of the NaH decomposition method.

The method of replacing the mesh-packed section has been used as a means of renewing cold traps.<sup>2,3</sup> This method requires isolating the cold trap from the main system, draining the sodium, opening the trap, removing the loaded mesh section, cleaning impurity deposits from internal surfaces, replacing the mesh section with a clean unit and resealing the trap. The method is simple and direct; however, it suffers from the disadvantages of having to use a special configuration to allow opening the trap and removing the mesh section, the need for special sodium handling equipment, the problem of handling and disposal of tritium and other radionuclides, and possible problems in removing the mesh sections due to impurity deposits in close-tolerance regions.

The method of using steam or alcohol to clean choked cold traps has been used with success.<sup>4,5</sup> The methods require removal of the trap from the sodium system, draining the sodium, injecting the steam or alcohol into the trap to dissolve the impurity deposit, drying the trap and replacing it on the system. While this method has been used successfully, it suffers from the requirement of cutting the system piping to remove the trap. A method for performing the regeneration *in situ* is much more desirable.

Dissolution of impurities from a choked cold trap with hot sodium ( $\sim 670$  K) is attractive because of its simplicity and the ability to process the trap *in-situ*. The process involves pumping hot sodium through the trap and cooling the sodium to precipitate the impurities in a less expensive vessel that may be processed at a more leisurely pace. While this method has obvious advantages, the waste management problems associated with handling the radioactive sodium waste are more difficult than those involved in handling gaseous tritium or tritiated water.

The Na-NaOH vertical section of the Na-Na<sub>2</sub>O-NaOH-NaH system<sup>6</sup> shows a region of two immiscible liquids, Na( $\ell$ ) and NaOH( $\ell$ ), above 685 K (412°C). The concept of heating a cold trap above 685 K to allow Na<sub>2</sub>O and NaH to react and form liquid NaOH was explored by McKee<sup>7</sup>. In this method, the liquid NaOH could be drained directly from the trap for disposal. While the method is very attractive for its simplicity and direct approach, the corrosion problems associated with the molten NaOH must be examined more closely before it can be used on a reactor system.

Compared with the other methods discussed above, the NaH decomposition method has the advantages of simplicity, true *in-situ* operation, rapid regeneration, and an easily disposable waste product (either tritiated water or a tritiated metal hydride).

## II. PRINCIPALS OF HYDROGEN EVOLUTION FROM NaH IN Na

The NaH decomposition method of cold trap regeneration may be operated either under vacuum or with an inert sweep gas. In either of these cases, the sodium must be, at least partially, drained from the trap to provide a gas space through which to flow the inert gas or to allow a vacuum space above the sodium. This gas space may be created by pressurizing one side of the trap (either inlet or outlet) to force sodium out the opposite side and into the main sodium system. In the sweep-gas case, the gas is pumped through the trap to sweep out the hydrogen as the temperature is raised to  $\sim 700$  K (450°C). In the vacuum case, the gas space is evacuated while the temperature is raised to  $\sim 670$  K (400°C).

Hydrogen may be evolved from the trap in either case by two mechanisms: 1) diffusion of hydrogen from the NaH to the sodium/gas interface either in a quiet sodium pool or aided by thermal convection, and 2) formation of hydrogen bubbles on the NaH surface that disengage and rise to the sodium/gas interface. The diffusion mechanism is obviously much slower in a quiet pool than when aided by thermal convection. In either case, the diffusion mechanism should be slower than the bubble formation mechanism. The diffusion mechanism would be expected to predominate at lower temperatures where the hydrogen pressure over NaH is insufficient to nucleate bubbles.

The rate of hydrogen transfer from the NaH deposit to the liquid surface by diffusion may be expressed by

$$\phi = DA \frac{dC}{dh} \quad (1)$$

where  $\phi$  = the hydrogen flux,  $\mu\text{g/s}$

$D$  = the hydrogen diffusivity in sodium,  $\text{m}^2/\text{s}$

$A$  = the cross sectional area perpendicular to the diffusion path,  $\text{m}^2$ , and

$dC/dh$  = the hydrogen concentration gradient along the diffusion path,  $\mu\text{g}/\text{m}^3\text{-m}$ .

The hydrogen concentration is assumed to be at saturation at the SCT temperature adjacent to the NaH deposit and essentially zero at the liquid/gas or liquid/vacuum interface. The diffusivity of hydrogen in sodium is not known; however, it may be estimated as  $\sim 10^{-7} \text{m}^2/\text{s}$  at 670 K as a maximum. The solubility of hydrogen in sodium was measured by Vissers, *et al.*,<sup>8</sup> and is expressed by

$$\log C(\text{g}/\text{m}^3) = 5.998 - \frac{2880}{T(\text{K})} \quad (2)$$

Using equations 1 and 2, and the estimate of hydrogen diffusivity in sodium, the maximum hydrogen flux that could be achieved at 670 K without thermal convection is  $\sim 0.14 \mu\text{g/s}$  (for the geometry used in the tests described below). This hydrogen flux would be increased by thermal convection; however, these experiments were conducted in isothermal vessels so that significant thermal convection would not be expected. Hydrogen fluxes much greater than  $0.14 \mu\text{g/s}$  could be achieved by nucleation and growth of hydrogen bubbles on the NaH deposit. The pressure required to nucleate a bubble in a homogeneous liquid is given by

$$\Delta P_c = \frac{2\sigma}{r_c} \quad (1)$$

where  $\Delta P_c$  = the pressure differential across the liquid-gas interface of a bubble of critical size,\* kPa,

$\sigma$  = the liquid surface tension, N/m,

and  $r_c$  = the radius of a bubble of critical size, mm.

Bubbles that nucleate on a solid-liquid interface require a lower pressure differential which may be expressed by

$$\Delta P_c = \sigma \left( \frac{1}{r_c} + \frac{1}{r_c} \right) \quad (2)$$

\*A bubble smaller than the critical size is thermodynamically unstable relative to the gas in solution while a bubble larger than the critical size is stable in the same solution.

where  $r_c$  and  $r'$  are the principle radii of curvature of the bubble surface. In cases where the solid is poorly wetted by the liquid, the bubble-solid contact angle is large and the bubble is significantly distorted from a spherical shape. This distortion results in a significant difference in the radii of curvature. Conversely, when the solid is very well wetted by the liquid, the contact angle approaches zero, and the bubble shape approximates a sphere. Contact angles have not been measured for hydrogen bubbles in sodium in contact with sodium hydride; however, sodium is expected to wet sodium hydride very well, so the bubble shape should be approximately spherical. Since a spherical bubble requires the greatest pressure to sustain, assumption of a spherical shape is the most conservative case.

The hydrogen pressure required to form a bubble of critical size is equal to the sum of the sodium hydraulic pressure and the pressure differential across the bubble wall. The sodium hydraulic pressure arises from the gas pressure over the sodium,  $P_g$ , plus the head due to the sodium depth,  $P_h$ . The hydrogen pressure in the bubble is then expressed by

$$P_H = P_g + P_h + \Delta P_c \quad (3)$$

For sodium at 670 K, equation 3 may be written

$$P_H (\text{kPa}) = P_g (\text{kPa}) + .00825 h + 0.334/r_c \quad (4)$$

where  $h$  is the sodium depth, mm, and  $r_c$  is the critical bubble radius, mm.

The equilibrium hydrogen pressure over NaH has been measured by several investigators, and the most reliable seems to be Banus, *et al.*,<sup>9</sup> who determined the relationship

$$\log P(\text{kPa}) = 9.61 - \frac{5070}{T(\text{K})} \quad (5)$$

The temperature required to produce hydrogen bubbles in sodium due to decomposition of NaH may be calculated as a function of critical radius by combining equations 4 and 5 to obtain

$$T(\text{K}) = 5070/[9.61 - \log(P_g + .00825h + 0.334/r_c)] \quad (6)$$

Figure 1 is a plot of the bubble nucleation temperature *vs.* the critical radius for two cases: 1) an inert gas pressure of 100 kPa over the sodium and 2) vacuum over the sodium. Equation 6 and figure 1 show two important features, *i.e.*, the sodium depth is relatively unimportant up to approximately 1 m, and if the critical bubble radius is less than  $\sim 2 \mu\text{m}$ , the bubble nucleation temperature should be approximately the same under vacuum as it is at 100 kPa pressure. For critical bubble radii greater than  $2 \mu\text{m}$ , bubble nucleation should occur much

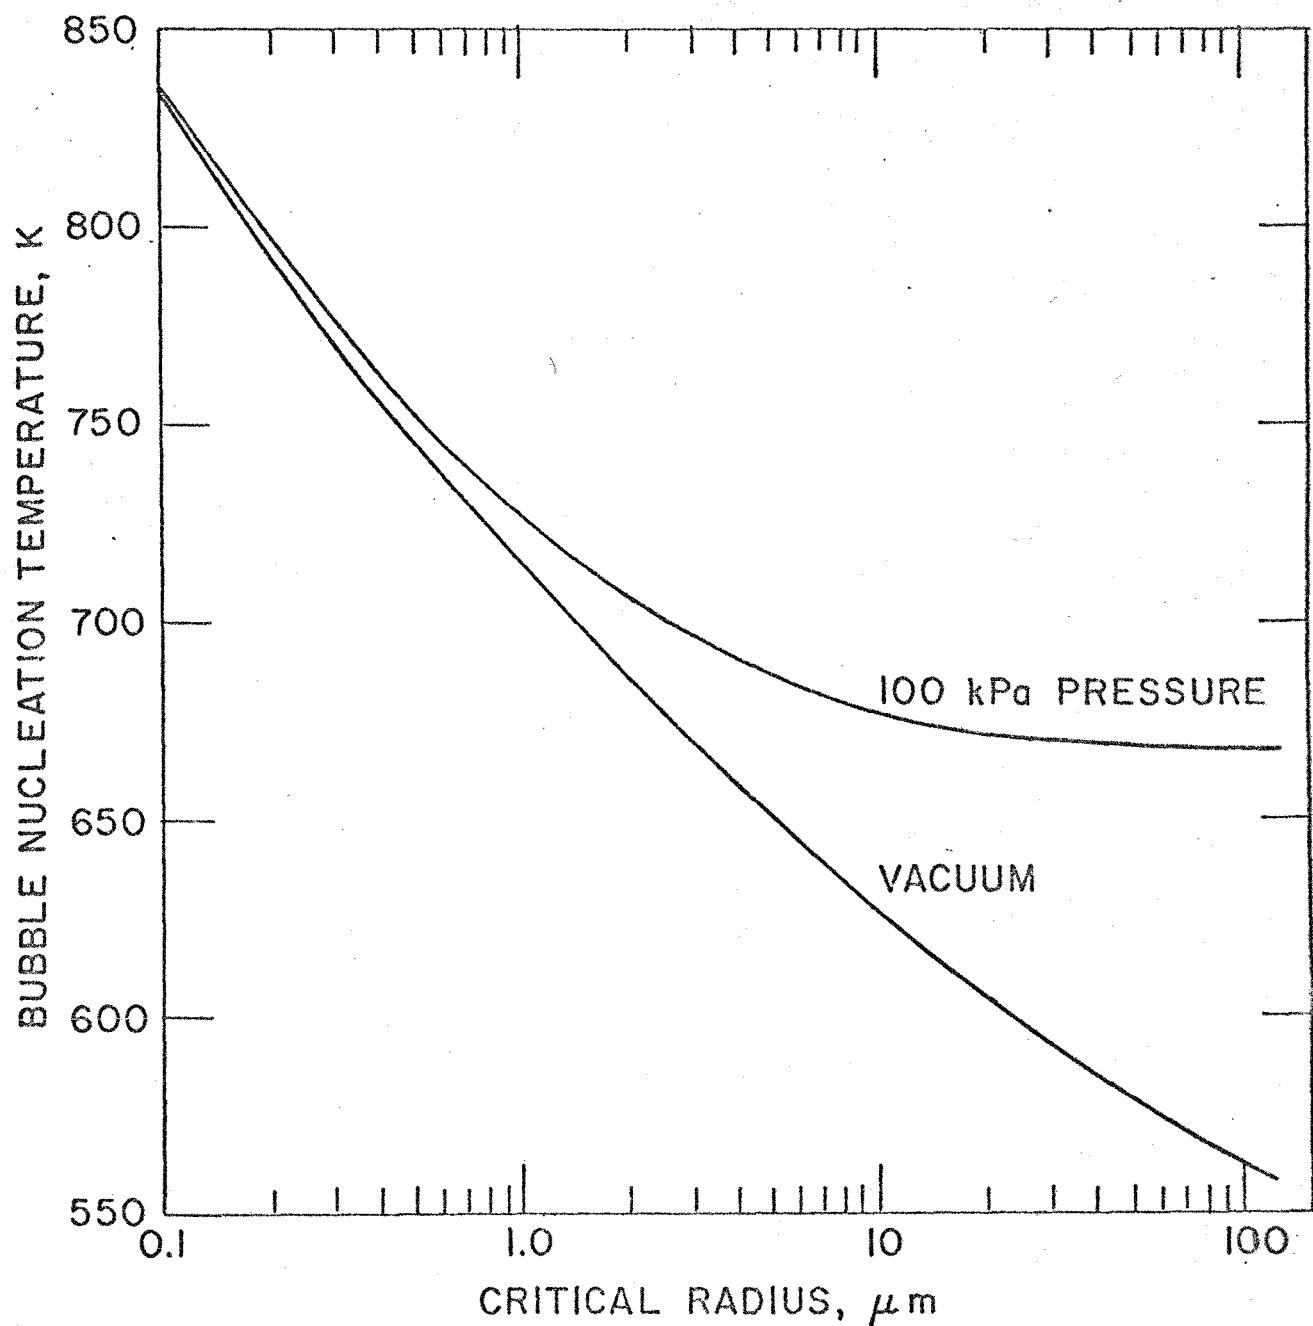


Figure 1. Temperature required to nucleate bubbles of various sizes under vacuum and atmospheric pressure.

more readily under vacuum than under a 100 kPa cover gas. The critical radius of hydrogen bubbles in sodium has not, to our knowledge, been measured.

Once the bubble has reached the critical size, its rate of growth is limited only by the rate at which hydrogen becomes available by decomposition of the NaH. The kinetics of NaH decomposition was measured by Naud<sup>10</sup> in the temperature range of 550 to 585 K. Naud determined that the NaH decomposition reaction is first-order and follows the relationship

$$-\frac{dC}{dt} = kC \quad (7)$$

where C is the amount of NaH present in grams, t is the time in seconds and k is the rate constant in reciprocal seconds. If Naud's data may be extrapolated to 670 K, the rate constant is  $.0019 \text{ s}^{-1}$ , and (assuming 5 g NaH for these experiments) the limiting initial rate of hydrogen evolution that could be expected in these experiments is 400  $\mu\text{g/s}$ . This rate could only be achieved under ideal conditions with no rate-inhibiting factors such as competing reactions, solution/dissolution steps, or diffusion barriers.

### III. EXPERIMENTAL APPARATUS

The apparatus used to perform the experiments is shown schematically in figure 2. In the sweep-gas mode of operation, the inert gas flows through a flowmeter into the simulated cold trap (SCT) which is a sealed stainless steel vessel 40 mm dia. and 125 mm high. NaH was placed in the bottom of the SCT and covered with stainless steel wire mesh typical of that used as cold trap packing. Sodium was poured into the SCT to fill it to the top of the wire mesh. The initial sodium depth was  $\sim 50$  mm in all of the tests.

The inert gas flows from the SCT, carrying a burden of sodium vapor and hydrogen, into the reflux condenser. The condenser is 40 mm dia. and 575 mm high. The upper 400 mm is filled with wire mesh packing and the lower 175 mm is intended for collecting the condensed sodium. The vapor-laden gas enters at  $\sim 725$  K at the approximate mid-point of the condenser. A temperature gradient is maintained so that the top and bottom ends are  $\sim 400$  K. As the gas flows upward, it is cooled, the sodium condenses and flows down through the mesh packing. The downward-flowing sodium aids the condensation of the incoming vapor. No doubt, some of the condensed sodium reevaporates in the hot zone; however, it eventually reaches the cool lower end where it is retained for the duration of the test.

Gas leaving the condenser is cooled to room temperature and enters a final vapor trap for removal of residual sodium aerosol. This vapor trap provides a quiet volume for aerosol settling and the gas exits through a porous stainless steel filter of  $\sim 10 \mu\text{m}$  pore size.

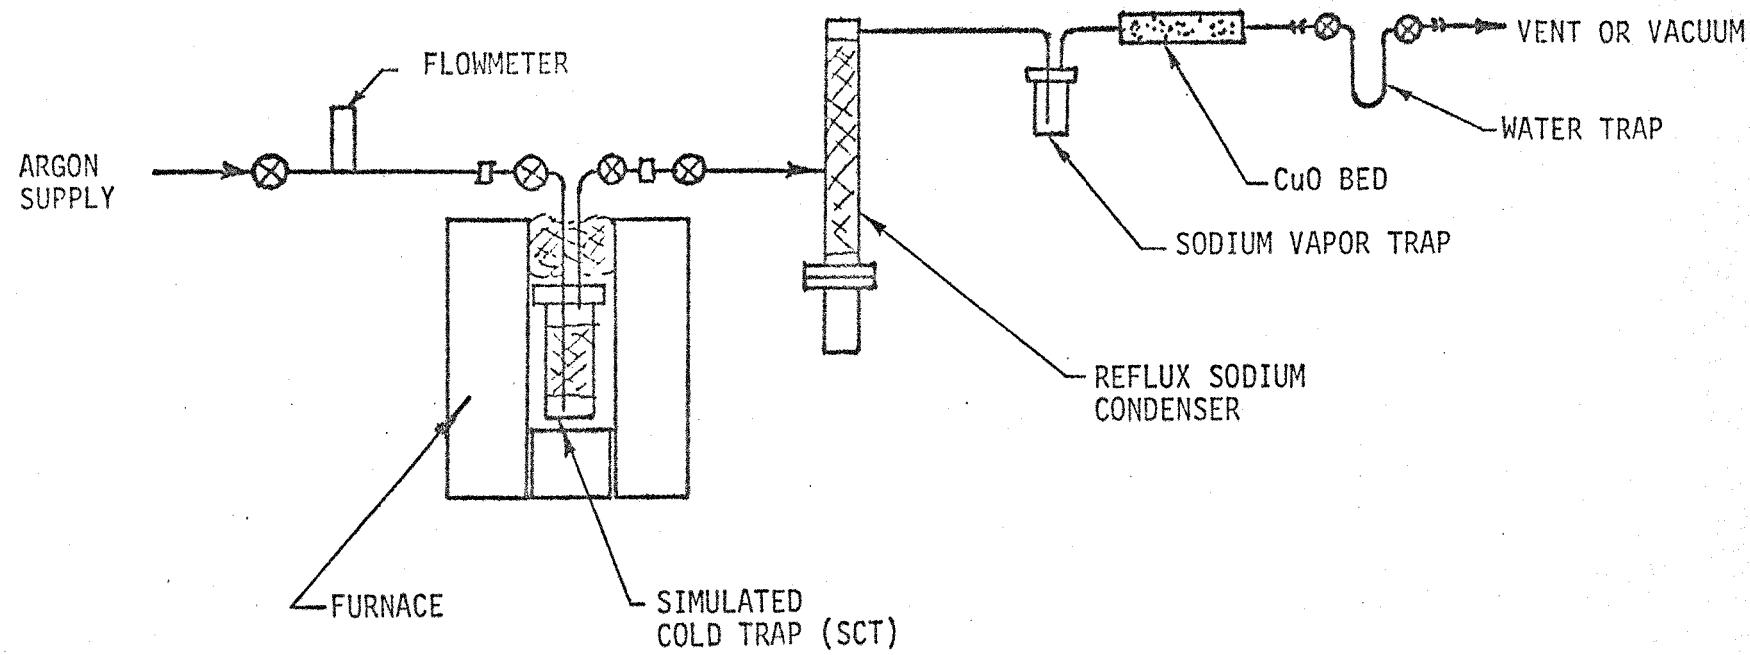


Figure 2. Test apparatus for removing hydrogen from simulated cold traps (SCT).

The gas flows from the vapor trap to a CuO bed which is maintained at 775 K to convert the hydrogen to water. The water vapor is collected in a trap filled with Molecular Sieve 5A adsorbent, and the quantity of water is determined by weight gain of the trap. While only one trap is shown in figure 2, two traps were actually used in parallel so that one trap could be weighed while the other continued to collect water.

When the system is operated under vacuum, the valve at the inlet to the SCT is closed and all other features of the system remain the same. The Molecular Sieve trap was found to retain adsorbed water under vacuum even at room temperature with very low water loadings. Therefore, the traps were operated at room temperature during these tests. Hydrogen recoveries ranging from ~70% in one experiment to >97% were observed.

Corrosion tabs were placed in the SCT for three of the tests. They were cut from cold-rolled type 304 stainless steel sheet and were 12 mm x 25 mm x 0.2 mm thick. The flat surfaces were left as received and the edges were filed smooth. The tabs were ultrasonically cleaned in acetone, rinsed in alcohol and dried before being placed in the SCT near the NaH on the bottom.

The parameters of the experiments performed in this series are summarized in Table I.

Table I.

Summary of Cold Trap Unloading Experiment Parameters

Test No.	SCT Temp. (K)	Test Time (ks)	Compounds in SCT (g)	Ar Flow or Vac. (mm <sup>3</sup> /s)
1	718	18.0	NaH(6.16)	14
2a	693	10.8	NaH(5.56)	14
2b	710	18.0		14
3a	523	79.2	NaH(3.81)	Vac.
3b	598	202		Vac.
4a	543	26.3	{Na <sub>2</sub> O(3.14)}	Vac.
4b	568	93.6	{NaH(2.08)}	Vac.
4c	588	59.8		Vac.
4d	603	86.0		Vac.

The procedure for performing these tests was to (in an inert-gas glove box) load the NaH into the SCT along with the corrosion tab, insert the wire mesh and pour liquid sodium over the mesh to a height sufficient to cover the mesh. The SCT was then sealed with a Varian bakeable vacuum flange using a nickel gasket. The SCT inlet and outlet valves were closed, and the SCT was transported to the test laboratory and connected to the test apparatus. The valves were then opened and argon flow was initiated while the components were at room temperature. The CuO bed, the sodium condenser and, finally, the SCT were heated to operating temperature to initiate the experiment. The SCT operating temperatures listed in Table I were maintained for the listed test times, and, at regular intervals during the test, the water-collection tubes were weighed to monitor the hydrogen evolution.

Neutron radiographs of the SCT were taken before and after the tests to qualitatively determine the effect of the unloading procedure. Since thermal neutrons are preferentially absorbed by hydrogen, any hydrogen-bearing compounds (such as NaH) are easily detected in an all-stainless-steel system as light, relatively unexposed areas on the film. Figures 3 and 4 are contact prints of neutron radiographs of the SCT used in test number 2. In the contact print, the NaH appears as a dark area in the bottom of the SCT. Figure 3 is the pretest radiograph and figure 4 is the post test radiograph. Note that the NaH deposit obscures the corrosion tab in figure 3 and that, in figure 4, the NaH appears to be completely eliminated. (The weight gain of the water traps also confirms complete unloading of the NaH in test number 2). These radiographs also indicate that the sodium appears to be completely removed from the SCT by the test procedure. The sodium appears as a lightly shaded region in figure 3 up to a height just below the inlet and outlet tubes. This region is not shaded in Figure 4 indicating that the sodium has been removed. Post test examination confirmed this sodium removal.

Accumulation of water in the traps occurred at different rates during each test depending upon the test conditions. Figure 5 shows the results of two tests using the same SCT loading. The first test involved heating the SCT to 690 K which resulted in a slow release of hydrogen while the second test was run at 710 K at which temperature, the hydrogen was released rapidly. The results of these tests and the others are discussed in the following sections.

#### IV. RESULTS AND DISCUSSION

The hydrogen evolution rates and the percent recovery of hydrogen from the SCT are summarized in Table II for each of the tests of this series. Tests number 2, 3 and 4 were done in several steps using the same impurity loading in a single SCT. The results of tests 2a and 2b are shown in figure 5 above, and tests 3a, 3b, 4a, 4b, 4c and 4d were done in a similar manner. The temperature was raised in each test in the sequence and the hydrogen evolution rate was measured at each temperature.

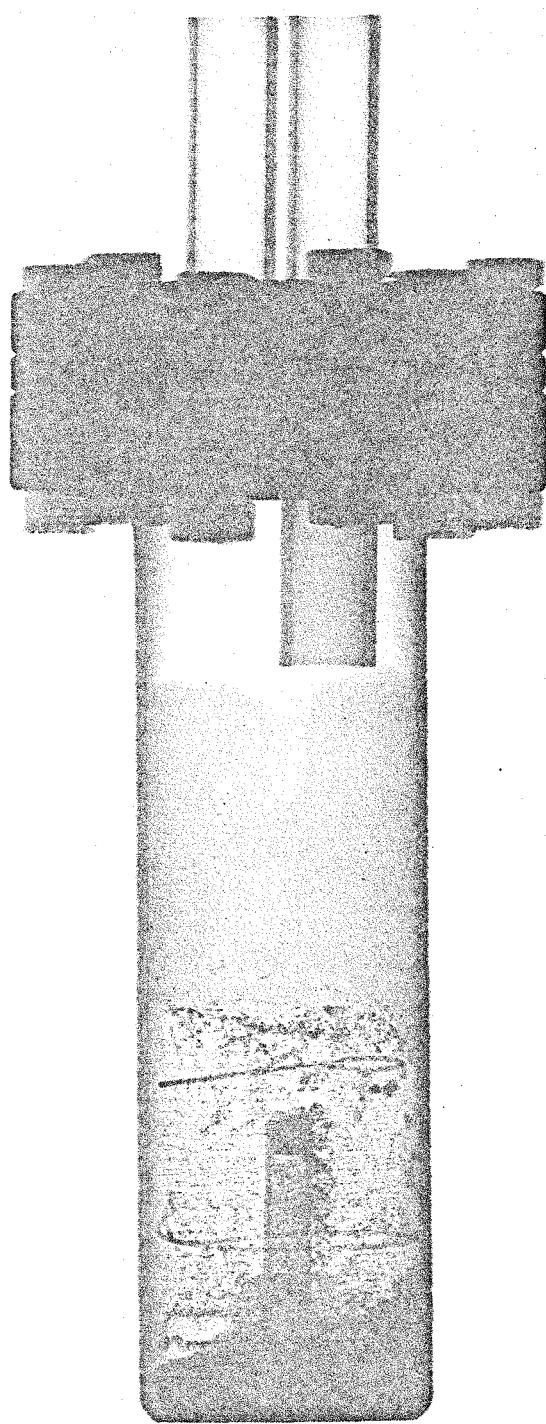
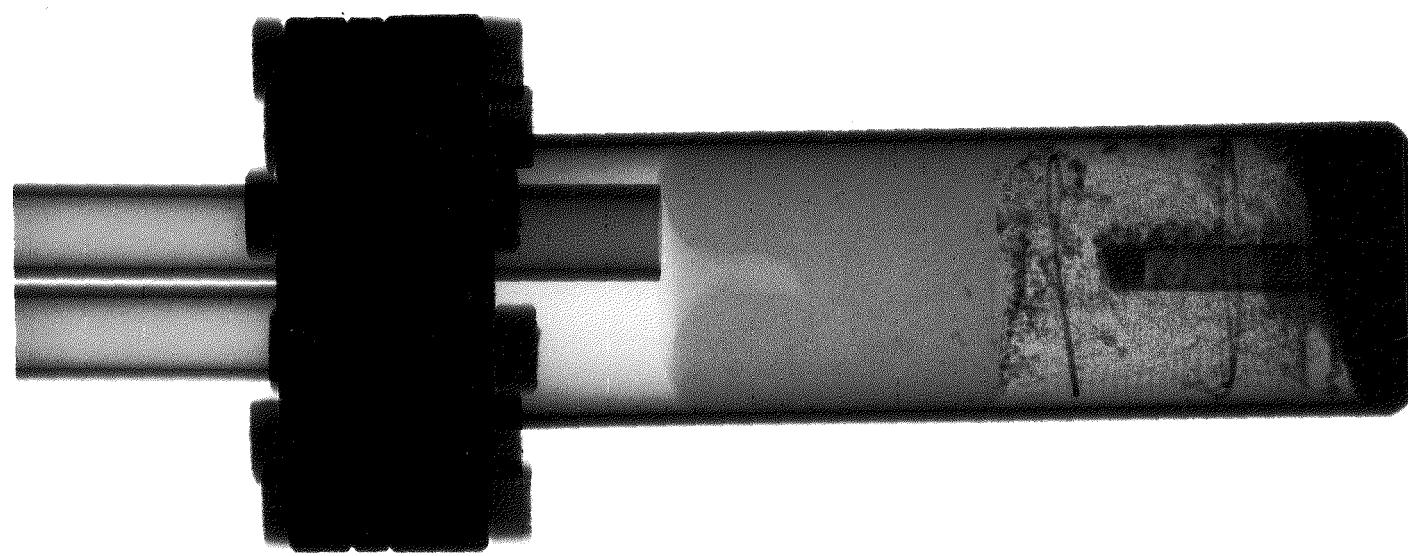


Figure 3. Contact print of pretest neutron radiograph of  
SCT number 2.



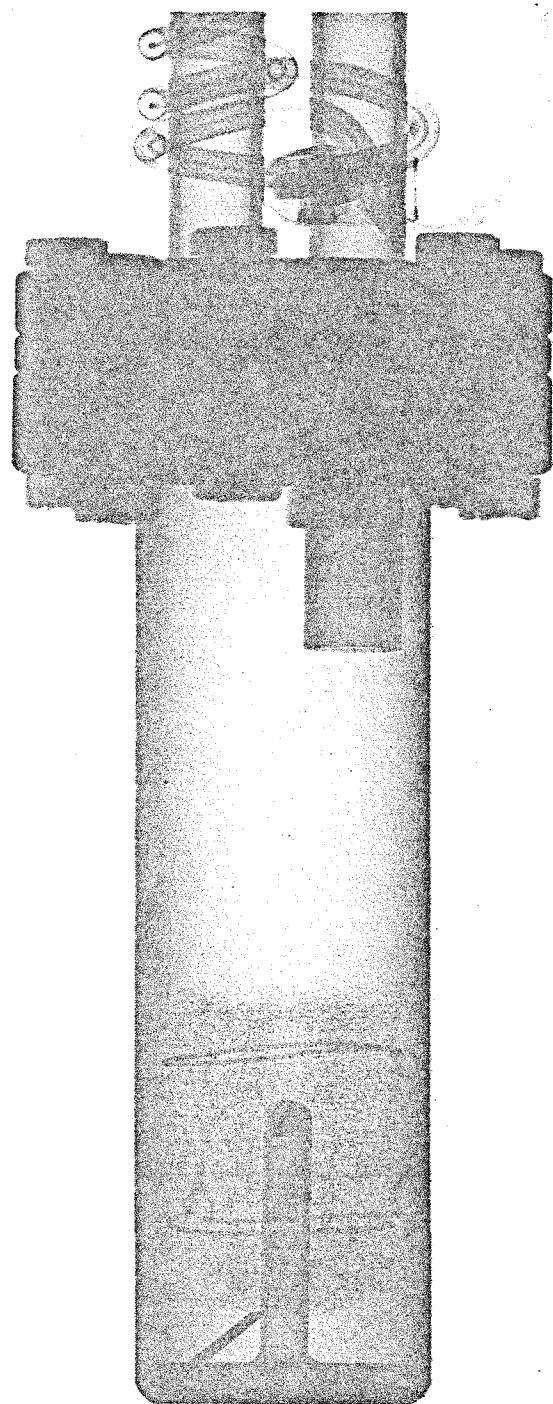
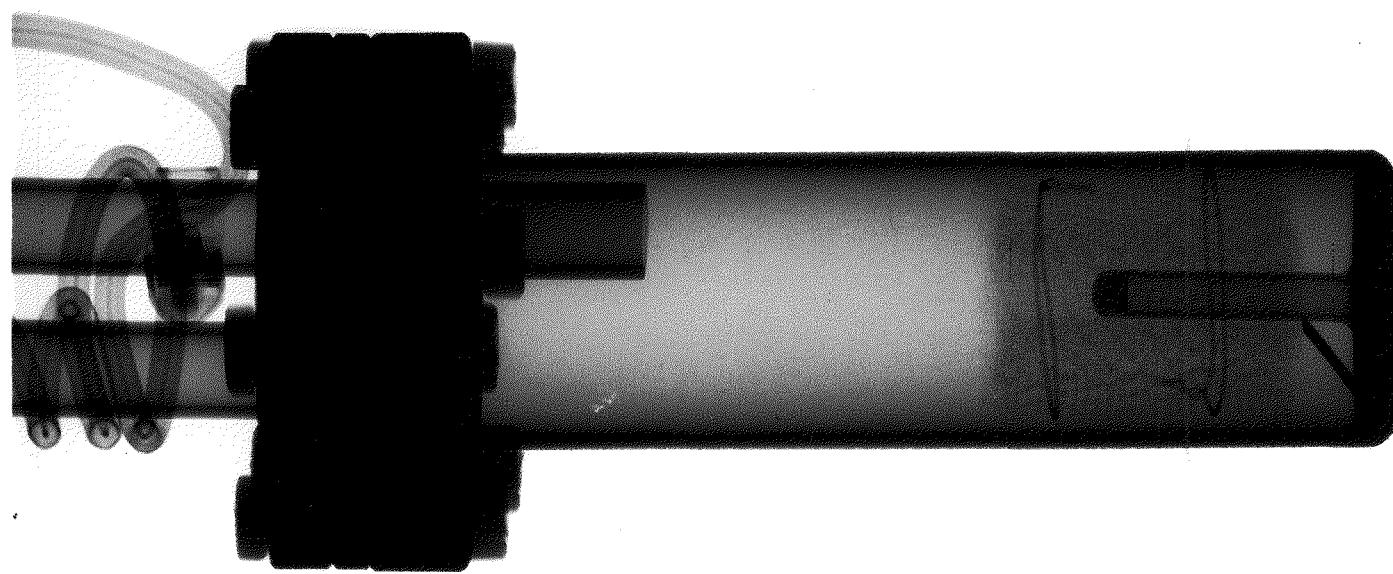


Figure 4. Contact print of post-test neutron radiograph of SCT number 2.



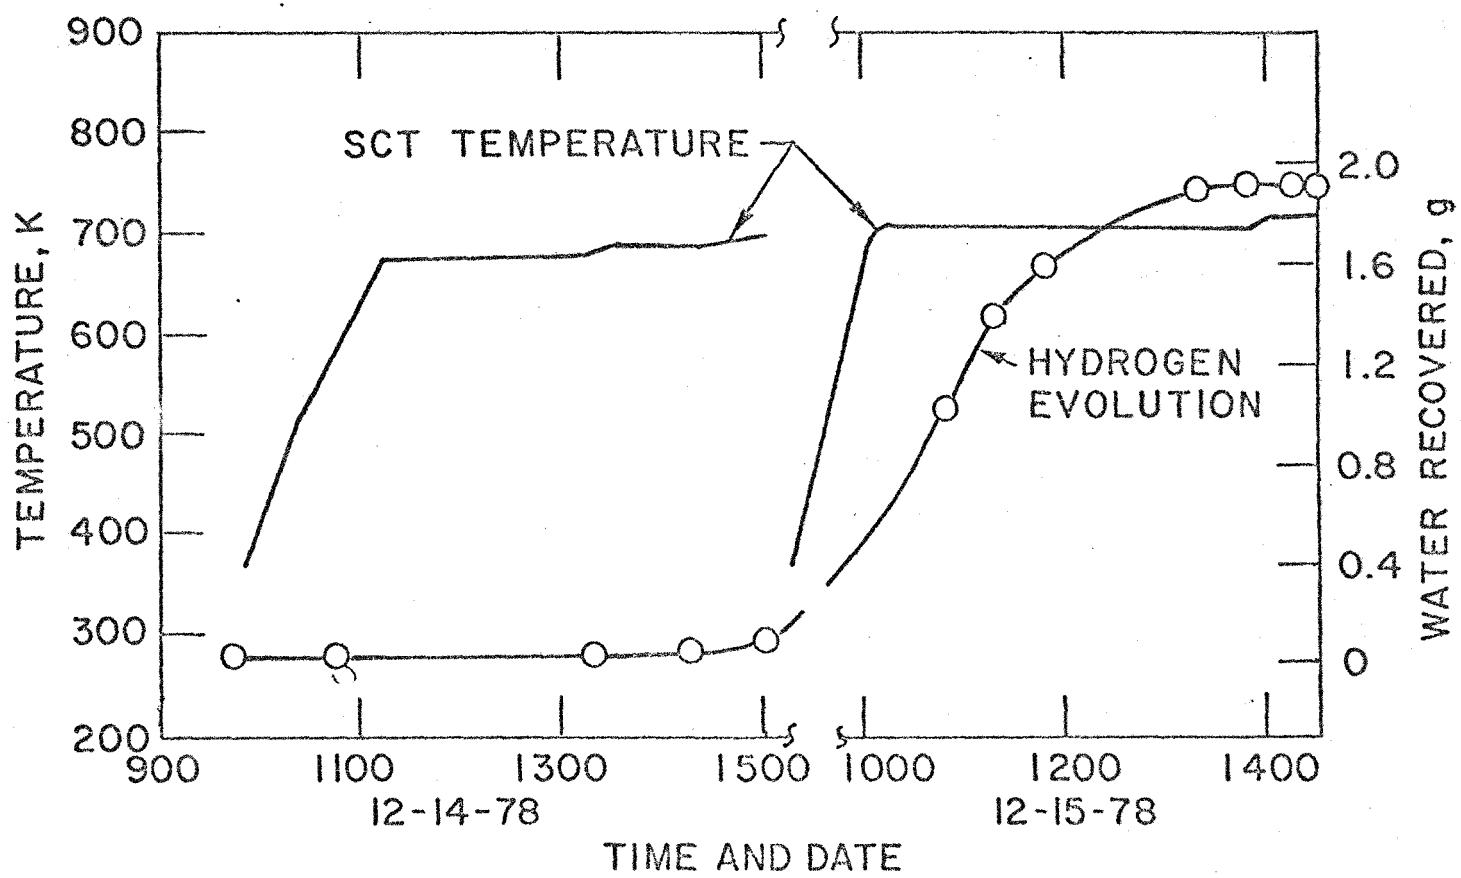


Figure 5. Hydrogen evolution observed during tests 2a and 2b with SCT number 2.

Table II  
Summary of Cold Trap Unloading Test Results

Test No.	Test Temp (K)	Test Pressure (kPa)	Hydrogen Loaded (as NaH) (mg H)	Hydrogen Recovery (%)	Hydrogen Evolution Rate ( $\mu\text{g/s}$ )
1	718	100	257	95.4	56.9
2a	693	100	232		.833
2b	710	100	232	90.3	17.8
3a	523	0	159		.142
3b	598	0	159	72.1	2.47
4a	543	0	87		.042
4b	568	0	87		.044
4c	588	0	87		.089
4d	603	0	87	97.3	.142

The results presented in Table II may be divided into three groups: tests 1, 2a and 2b which were run at atmospheric pressure, tests 3a and 3b in which NaH was decomposed under vacuum, and tests 4a through 4d in which NaH in the presence of Na<sub>2</sub>O was decomposed under vacuum. The hydrogen evolution rates for these three groups are plotted *vs.* temperature in figure 6. Although straight lines are drawn through these data points, the amount of information available is insufficient to determine the nature of the relationships. However, several observations can be made from these results. A significantly higher temperature is needed to evolve hydrogen at atmospheric pressure than under vacuum. This observation is consistent with the theory that the primary mechanism for rapid hydrogen evolution is by bubble nucleation, growth and release. Hydrogen evolution at 3  $\mu\text{g/s}$  is arbitrarily considered "rapid" in these tests because it is  $\sim 20$  times the rate calculated for simple diffusion. The temperature difference between hydrogen evolution at 3  $\mu\text{g/s}$  under atmospheric pressure and the same rate under vacuum was found to be 100 K. This temperature difference corresponds (in figure 1) to a critical bubble radius of between 50 and 100  $\mu\text{m}$ . Although the bubble nucleation temperatures shown in figure 1 (670 and 570 K for a 75  $\mu\text{m}$  critical radius and atmospheric pressure and vacuum, respectively) do not agree exactly with the observed temperatures shown in figure 6 (700 and 600 K for a hydrogen evolution rate of 3  $\mu\text{g/s}$ ), the agreement is better than would be expected for this simple analysis.

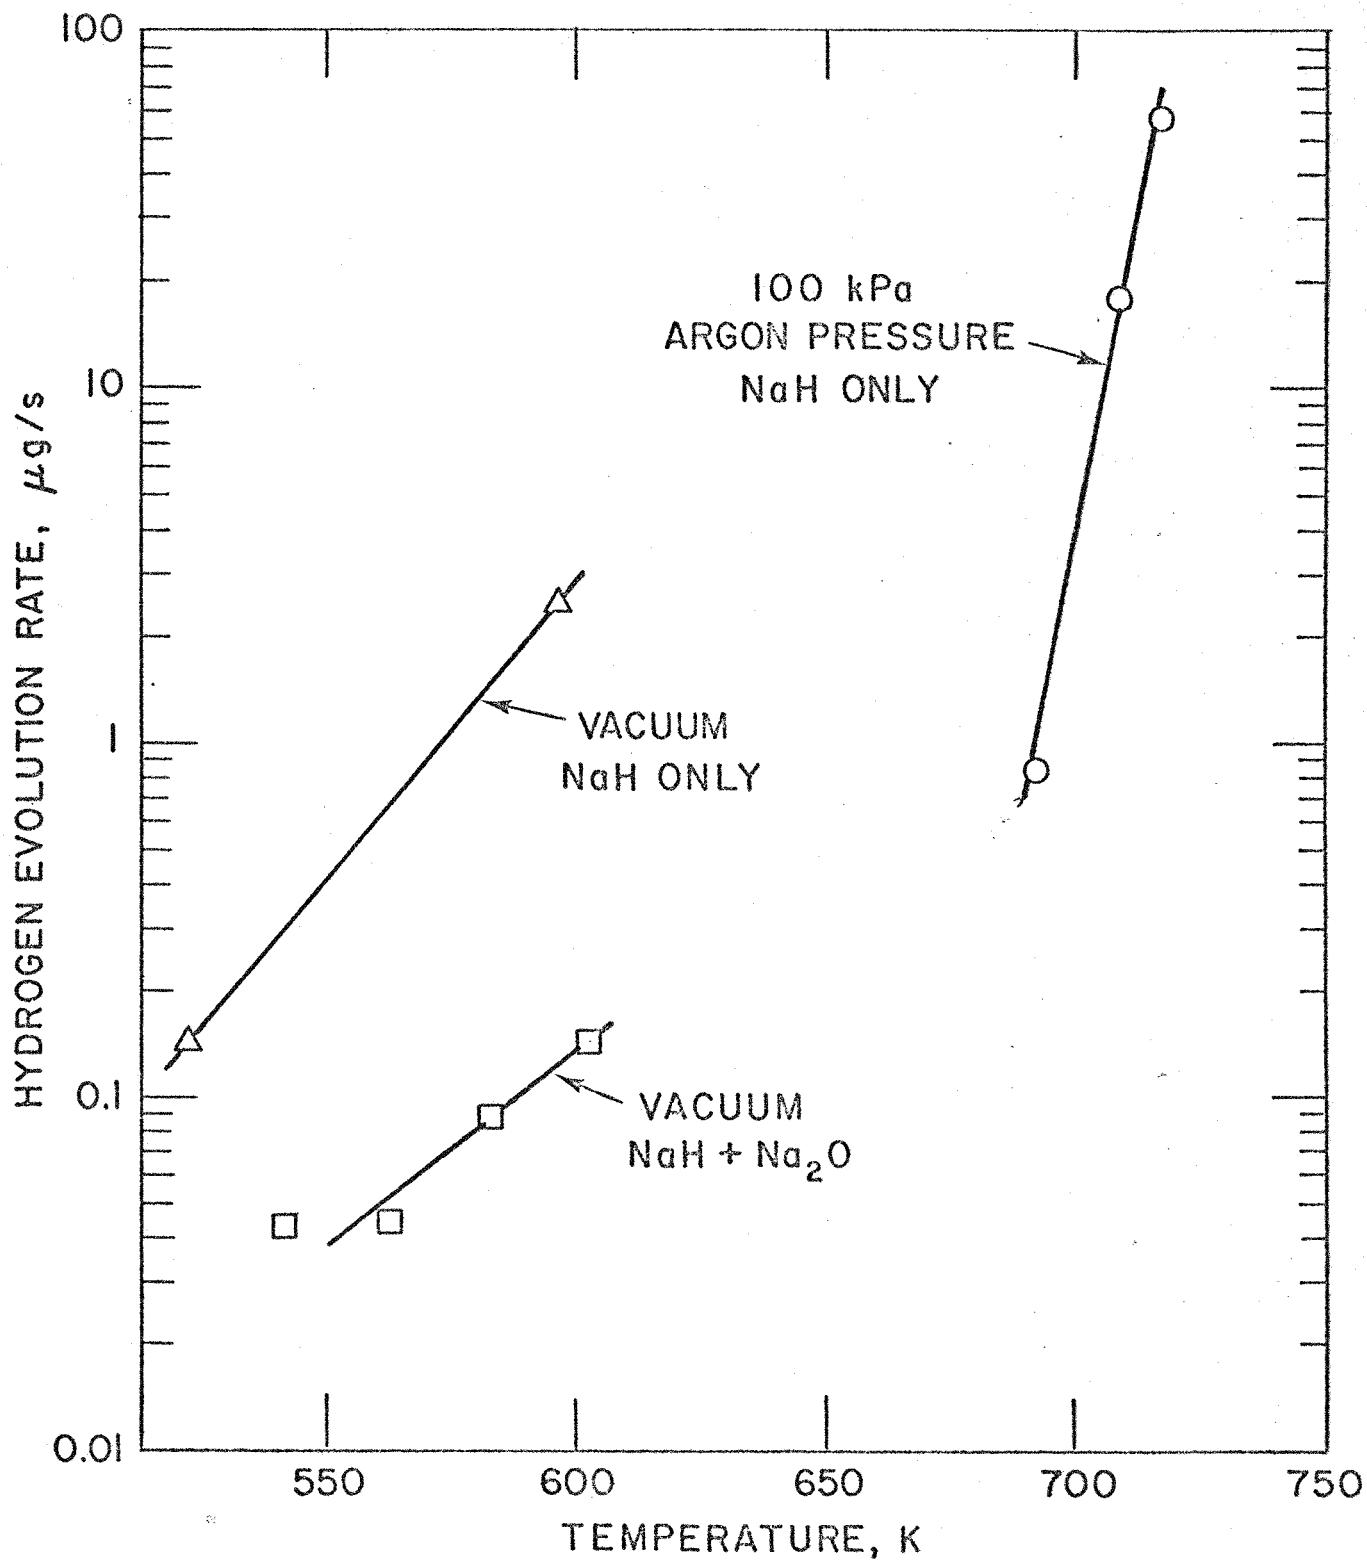


Figure 6. Hydrogen evolution rates observed in all tests.

Another important observation is that the presence of  $\text{Na}_2\text{O}$  appears to inhibit the hydrogen evolution rate by as much as one order of magnitude. This reduction of evolution rate is probably due to interaction of the hydrogen and oxygen species either in solution, or at interfaces between phases. The data obtained in this study are insufficient to determine the mechanisms of this interaction, and more work is needed in this area. This interaction could have a significant impact on the time required to regenerate cold traps that have large quantities of  $\text{Na}_2\text{O}$ . However, IHTS cold traps should contain relatively little  $\text{Na}_2\text{O}$ , so the regeneration rate should be acceptable in the IHTS case.

Corrosion tabs were present in the bottom of SCT's 2, 3 and 4. Post-test examination of these tabs showed very little visible effect of exposure to the test environment. The post-test appearance was very slightly duller than the initial appearance; however, weight losses were not detectable beyond the normal handling, cleaning and weighing errors.

Little significance should be given to the relatively low hydrogen recovery achieved from SCT number 3. The emphasis of the test was on determination of the maximum rate of hydrogen evolution rather than on total hydrogen recovery. The test terminated before all the hydrogen had been evolved.

## V. CONCLUSIONS AND FUTURE DIRECTIONS

Although this work was preliminary in nature, several significant conclusions may be drawn from the results:

- 1) Thermal decomposition of  $\text{NaH}$  is an effective method for removal of  $\text{NaH}$  from sodium in a configuration similar to a cold trap.
- 2) Effective decomposition of  $\text{NaH}$  can be achieved either at one atmosphere pressure using a sweep gas or under vacuum.
- 3) The hydrogen evolution rate becomes significant ( $>3 \mu\text{g/s}$  in these tests) at temperatures  $\sim 100$  K lower for the vacuum method than for the sweep-gas method.
- 4) The presence of  $\text{Na}_2\text{O}$  significantly reduces the hydrogen evolution rate from  $\text{NaH}$ .
- 5) The  $\text{NaH}$  decomposition method should be suitable for regenerating IHTS cold traps because the deposit should be primarily  $\text{NaH}$  with little  $\text{Na}_2\text{O}$ .

The NaH decomposition method for cold trap regeneration - particularly under vacuum -- appears attractive for regeneration of IHTS cold traps. Additional studies are being conducted to more completely establish the relationships between temperature, pressure and hydrogen flux; to establish the effect of Na<sub>2</sub>O on the hydrogen flux; to determine the impact of tritium on the equipment design and operating requirements; and to test the NaH decomposition method on a circulating sodium system.

#### REFERENCES

1. P. Roy and D. N. Rogers, "Hydrogen Burden from the Steam Side Corrosion in Sodium-Heated Steam Generators," *Nucl. Tech.* 39, 213, (July, 1978).
2. D. J. Hebditch and B. J. Gliddon, "Impurity Crystallisation in Liquid Sodium Systems," *Int. Conf. on Liquid Metal Tech. in Energy Production*, CONF-760503-P2, 643, Champion, PA, (May 3-6, 1976).
3. G. Billuris, "Experimental Investigations of the Removal of Sodium Oxide from Liquid Sodium," *Atomic Energy Commission Report GEAP-3328*, (January, 1960).
4. Personal Communication, W. H. Olson, EBR-II Project, Argonne National Laboratory, Idaho, USA (August, 1977).
5. W. Haubold, C. Ch. Smit and K. Ch. Stade, "Status of Sodium Removal and component Decontamination in the SNR Program," *Int. Working Group on Fast Reactors, Specialist Meeting on Sodium Removal and Decontamination*, pp 1-7, Richland, Washington, USA, (February, 1978).
6. K. M. Myles and F. A. Cafasso, "The Reciprocal Ternary System Na-NaOH-Na<sub>2</sub>O-NaH," *J. Nucl. Mat'*1, 67, 249, (1977).
7. J. M. McKee, "Unloading Sodium Cold Traps -- Concept Exploration," *Trans. Am. Nucl. Soc.*, New Orleans, LA. (June 8-13, 1975).
8. D. R. Vissers, J. T. Holmes, L. G. Bartholme and P. A. Nelson, "A Hydrogen-Activity Meter for Liquid Sodium and its Application to Hydrogen Solubility Measurements," *Nucl. Tech.*, 21, 235 (March 1974).
9. M. O. Banus, J. J. McSharry and E. A. Sullivan, "The Sodium-Sodium Hydride-Hydrogen System at 500-600°C, *J. Amer. Chem. Soc.*, 77, 2007, (1955).
10. G. Naud, "Contribution to the Study of Hydrogenated and Oxygenated Impurities in Liquid Sodium," *UKAEA TRG Information Series 552(c)*, (1966).