

DOE/ER/45268--19

DE92 008518

$\text{CeCu}_4\text{Al}$  and  $\text{CeCu}_2\text{Zn}_2\text{Al}$  - Very Heavy Fermion  
Systems in High Magnetic Fields

B. Andraka, J. S. Kim, and G. R. Stewart<sup>+</sup>

Department of Physics, University of Florida

Gainesville, FL 32611

Z. Fisk

FAX 0 4 3032

Los Alamos National Laboratory

Los Alamos, NM 87545

Abstract

$\text{CeCu}_4\text{Al}$  and  $\text{CeCu}_2\text{Zn}_2\text{Al}$  are heavy fermion systems with extremely enhanced C/T (specific heat divided by temperature) values of 2.3 and 1.8 J/K<sup>2</sup> respectively as T → 0 K. The field dependence of the low temperature specific heat is also extreme; 11 T reduces C of  $\text{CeCu}_4\text{Al}$  by more than a factor of five, 12.5 T suppresses C of  $\text{CeCu}_2\text{Zn}_2\text{Al}$  about seven times. Magnetic field caused changes of the specific heat of  $\text{CeCu}_4\text{Al}$  are consistent with a single ion Kondo model. Magnetic correlations are at least partially responsible for the enhanced low temperature specific heat of  $\text{CeCu}_2\text{Zn}_2\text{Al}$ .

**DISCLAIMER**

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

The proximity of heavy fermion and magnetic ground states has been recognized for some time already.<sup>1,2</sup> Many heavy fermion systems order antiferromagnetically at low temperatures of the order of 1 K. In some systems, e.g.  $\text{UPt}_3$ ,  $\text{CeCu}_2\text{Si}_2$  or  $\text{CeAl}_3$ , magnetic order has very little effect on the low temperature thermodynamic properties<sup>3</sup> like specific heat (C). The linear, low temperature coefficient of the specific heat,  $\gamma$ , (called also the Sommerfeld coefficient) can be truly electronic in nature (as proved by the large discontinuities in the specific heats of  $\text{UPt}_3$  and  $\text{CeCu}_2\text{Si}_2$  at their superconducting transition temperatures) and reaches spectacular values of order  $1000 \text{ mJ/K}^2 \text{ mol}$ . The ordered moments associated with these itinerant heavy quasi-particles are extremely small; a value of the order of  $0.02 \mu_B$  has recently been reported<sup>4</sup> for  $\text{UPt}_3$ .

Another group of systems, e.g.  $\text{CeAl}_2$ ,  $\text{CeCu}_2$ ,  $\text{CeB}_6$ ,  $\text{CePdIn}$ , order magnetically, with large local moments of the order of  $1 \mu_B$  before the heavy fermion ground state is fully established.<sup>5</sup> In this case, the enhanced high temperature coefficient  $\gamma$  (at temperatures much larger than the ordering temperature), of the order of  $100 \text{ mJ/K}^2 \text{ mol}$ , is reduced by the ordering to much lower values as  $T \rightarrow 0 \text{ K}$ .

There is, however, a group of systems sometimes called "false heavy fermions"<sup>6</sup> that, although they do not undergo magnetic ordering down to the lowest temperatures have large, low temperature specific heats clearly not due to heavy electrons but rather associated with magnetic entropy or crystal field effects. Examples are  $\text{CeCu}_{6.5}\text{Al}_{6.5}$ <sup>6</sup> and  $\text{CePd}_3\text{B}_{0.3}$ <sup>7</sup> in which disorder on non-Ce sites causes a variation in the RKKY interactions between Ce ions that prevent magnetic ordering. Instead, spin glass behavior with low freezing temperatures is observed.

One could also speculate on intermediate cases when the low temperature enhancement of the specific heat arises from a combination of the formation of a heavy fermion state and an onset of a magnetic phase transition as has been suggested for  $\text{CeCuIn}_2$ <sup>8</sup> and it might be the case for  $\text{CeCu}_4\text{Ga}$ .<sup>9</sup>

$\text{CeCu}_4\text{Ga}$  has recently become a subject of very intense studies due to its extremely large C/T values, of the order of  $2 \text{ J/K}^2 \text{ mol}$  at  $T \rightarrow 0 \text{ K}$ . The nature of this enhancement (magnetic vs. heavy fermions) still remains a subject of controversy.<sup>9, 10, 11</sup>

Two more isostructural systems have lately been synthesized:<sup>12</sup> ( $\text{CeCu}_4\text{Al}$  and  $\text{CeCu}_2\text{Zn}_2\text{Al}$ ) that do not order magnetically down to 150 mK which have C/T values approaching  $2.3 \text{ J/K}^2 \text{ mol}$  in the 0.3 to 0.4 K temperature range. At still lower temperatures this value is reduced to about 2 and  $1.7 \text{ J/K}^2 \text{ mol}$  for  $\text{CeCu}_4\text{Al}$  and  $\text{CeCu}_2\text{Zn}_2\text{Al}$ , respectively. Such shallow maxima have been observed for other heavy fermion systems (e.g.  $\text{CeCu}_2\text{Si}_2$  and  $\text{CeAl}_3$ ) and are usually attributed to the formation of a coherent heavy fermion state.<sup>13</sup> According to both theoretical<sup>14</sup> and experimental studies<sup>13</sup> these maxima shift to lower temperatures when magnetic field is applied and vanish for sufficiently large fields (2 T for  $\text{CeAl}_3$  and 8 T for  $\text{CeCu}_2\text{Si}_2$ ).

Both  $\text{CeCu}_4\text{Al}$  and  $\text{CeCu}_2\text{Zn}_2\text{Al}$  as well as the above-mentioned  $\text{CeCu}_4\text{Ga}$  are derivatives of  $\text{CeCu}_5$  that undergoes two magnetic phase transitions<sup>15</sup> at 3.6 and 3.8 K, indicating probably a very delicate and complicated magnetic ground state. Hexagonal  $\text{CeCu}_5$  contains two inequivalent Cu sites, twofold and threefold sites; doping on the Ce sites with either Al, Zn or Ga leads to the destruction of the magnetic order in a very abrupt way<sup>12, 15, 16</sup> and a great enhancement of low temperature C/T.

In order to further elucidate the nature of this enhancement we have performed specific heat measurements on  $\text{CeCu}_4\text{Al}$  and  $\text{CeCu}_2\text{Zn}_2\text{Al}$  in magnetic fields to 12.5 T and temperatures down to 0.35 K. Our zero field data (Fig. 1) for  $\text{CeCu}_4\text{Al}$  agree well with already published results;<sup>12</sup> we observe a maximum in C/T of  $2320 \text{ J/K}^2 \text{ mol}$  between 0.35 and 0.45 K. On the other hand, our lowest temperature (0.35 K) value of C/T for  $\text{CeCu}_2\text{Zn}_2\text{Al}$  (Fig. 3) is near  $1.8 \text{ J/K}^2 \text{ mol}$ , i.e. about 20% lower than the previously reported value. The above mentioned values of C/T together with our lowest temperature (1.8 K) magnetic susceptibilities, 100 memu/mol for  $\text{CeCu}_4\text{Al}$  and 50 memu/mol for  $\text{CeCu}_2\text{Zn}_2\text{Al}$ , have been used to calculate the so-called Wilson ratio

$$R \left[ R \propto \frac{\chi}{\mu_{\text{eff}}^2 \gamma} \right],$$

a popular parameter quantifying heavy fermion systems.<sup>1</sup> We assume that the Ce ions are in stable trivalent configuration with an effective moment  $\mu_{\text{eff}} = 2.54 \mu_B$ , giving Wilson ratios of 1.5 and 0.9 for  $\text{CeCu}_4\text{Al}$  and  $\text{CeCu}_2\text{Zn}_2\text{Al}$  respectively.

Both values are comparable to those of  $\text{UCd}_{11}$ <sup>1</sup> ( $R \sim 0.9$ ),  $\text{NpBe}_{13}$  ( $R \sim 1.8$ ) and  $\text{CeAl}_3$  ( $R \sim 0.7$ ), those compounds regarded as heavy fermions exhibiting band magnetism at low temperatures.<sup>17</sup>

The dramatic effects of magnetic field on the low temperature specific heat of  $\text{CeCu}_4\text{Al}$  are presented in Fig. 1. In the temperature range of the measurement, 0.35 to 1.2 K,  $C/T$  monotonically decreases with the increasing field. 11 T reduces  $C/T$  at the lowest temperature to about  $0.45 \text{ J/K}^2 \text{ mol}$ , i.e. by a factor larger than 5 from the zero field value. Similar strong sensitivity to the magnetic field has been observed only for the isostructural compound  $\text{CeCu}_4\text{Ga}$ ,<sup>10</sup> where a magnetic field of 6.7 T suppresses  $C/T$  at 100 mK from about  $1.8 \text{ J/K}^2 \text{ mol}$  to  $0.74 \text{ J/K}^2 \text{ mol}$ . For comparison 11 T field reduces  $C/T$  ( $T \rightarrow 0$ ) of  $\text{CeCu}_6$ <sup>18</sup> by a factor of 2.

The strong magnetic field dependence of the specific heat of  $\text{CeCu}_4\text{Al}$  is of no surprise considering the very large  $\gamma$  and thus very small effective band width of a few K. What is somewhat unexpected though is the fact that  $C/T$  for  $H = 11$  T is proportional to  $T^2$  in the whole temperature range of the measurement. Such a temperature dependence is characteristic of normal metals or antiferromagnets at temperatures well below the Néel temperature. In order to further explore this point, additional measurements over larger temperature range and in higher magnetic fields are planned. It is also difficult to speculate at this point on the origin of the low temperature maximum in  $C/T$ . It is not clear from our data if the low temperature structure is removed by an application of the magnetic field or is being smeared out and moved to higher temperatures.

A simple analysis of the field depression of the Sommerfeld coefficient  $\gamma$  is offered by a single ion Kondo model.<sup>10, 19</sup> In this model, the low temperature value of the specific heat is determined solely by the width  $\Gamma_0$  of the Kondo resonance band ( $\Gamma_0 \propto T_K$ ). Magnetic field  $H$  broadens the Kondo resonance band ( $\Gamma$ ) and decreases  $\gamma$  in the following way:

$$\Gamma^2 = \Gamma_0^2 + (\mu H)^2$$

$$\gamma = \frac{\pi k_B R}{3 \Gamma} = \frac{\pi k_B R}{3} \frac{1}{\sqrt{\Gamma_0^2 + (\mu H)^2}}; \quad (1)$$

where  $\mu$  is an effective magnetic moment. It has been shown that the above relationship is well satisfied by the dilute Ce Kondo system  $\text{Ce}_{0.1} \text{La}_{0.9} \text{Cu}_6$ <sup>19</sup> for magnetic fields as high as 5 T and the concentrated Ce system  $\text{CeCu}_4 \text{Ga}$  up to at least 6.7 T.<sup>10</sup>

In Fig. 2,  $\gamma$ , taken as  $C/T$  at 0.35 K, is plotted vs. magnetic field  $H$ . The solid line is a fit to eqn. 1. This simple formula describes rather well the magnetic field dependence of  $\gamma$ . The best fit has been obtained with the following parameters:

$T_K = \Gamma_0/k_B = 3.68 \text{ K}$ ,  $\mu = 2.17 \mu_B$ . For comparison, such an analysis for  $\text{CeCu}_4 \text{Ga}$  yields  $T_K = 4.4 \text{ K}$  and  $\mu = 2.58 \mu_B$ .

Let us turn to the field response of the specific heat of  $\text{CeCu}_2 \text{Zn}_2 \text{Al}$ , shown in Fig. 3. The lowest temperature specific heat depression is comparable to that of  $\text{CeCu}_4 \text{Al}$ . A 12.5 T field reduces  $C/T$  at 0.35 K by more than seven times. A maximum in  $C/T$  at  $T \sim 1 \text{ K}$  appears for  $H = 9 \text{ T}$  below which  $C/T$  falls rapidly with the decrease of temperature. The maximum is shifted to  $T \sim 2.5 \text{ K}$  by 12.5 T field. This behavior is consistent with the low temperature specific heat of  $\text{CeCu}_2 \text{Zn}_2 \text{Al}$  being due, in some part at least, to magnetic correlations. Magnetic field raises the temperature below which these magnetic correlations freeze out. The nearby compound in the phase diagram  $\text{CeZn}_3 \text{Cu}_2$  is antiferromagnetic with  $T_N = 6 \text{ K}$ .<sup>20</sup> An analysis similar to that of  $\text{CeCu}_4 \text{Al}$  (presented in

Fig. 2) fails completely for  $\text{CeCu}_2\text{Zn}_2\text{Al}$ . Thus, the magnetic field dependence of C/T at  $T = 0.35$  K cannot be described by the single ion Kondo model.

On the other hand, there are some experimental observations that are difficult to rectify with the magnetic model of the specific heat enhancement. No apparent phase transition nor spin glass freezing has been detected in zero field down to temperatures as low as 150 mK.<sup>12</sup> The low temperature magnetic susceptibility is comparable to that of  $\text{CeCu}_6$  and  $\text{CeAl}_3$  and is twice smaller than that of  $\text{CeCu}_4\text{Al}$ . The Wilson ratio R is fairly small, much smaller than R of  $\text{CeCu}_4\text{Al}$ .

In summary, low temperature specific heats of both compounds are very sensitive to magnetic fields. Despite very similar zero field temperature dependence their field dependences are quite different. Our results indicate strong magnetic correlations in  $\text{CeCu}_2\text{Zn}_2\text{Al}$ . However, specific heat data alone cannot be conclusive. Other measurements are required to explain the origin of the spectacular low temperature enhancement of the specific heat of  $\text{CeCu}_2\text{Zn}_2\text{Al}$  and  $\text{CeCu}_4\text{Al}$ , as well as of other  $\text{CeCu}_5$  derivatives.

Acknowledgements: Work at the University of Florida supported by the U. S. Department of Energy Grant number DE-FG05-86ER45268. Work at Los Alamos supported by the U. S. Department of Energy.

<sup>+</sup> Also at Universität Augsburg, Augsburg, Germany.

References

1. G. R. Stewart, Rev. Mod. Phys. 56, 755 (1984).
2. R. Selim, T. Mihalisin, Sol. St. Commun. 59, 785 (1986).
3. N. Grewe and F. Steglich, to be published.
4. G. Aepli, E. Bucher, A. I. Goldman, G. Shirane, C. Broholm, and J. K. Kjems, J. Magn. Magn. Mat. 76 & 77, 385 (1988).
5. C. D. Bredl, J. Magn. Magn. Mat. 63 & 64, 355 (1987).
6. U. Rauchschwalbe, U. Gottwick, U. Ahlheim, H. M. Mayer, and F. Steglich, J. Less-Common Metals 111, 265 (1985).
7. S. K. Dhar, K. A. Gschneider, Jr., C. D. Bredl, and F. Steglich, Phys. Rev. B39, 2439 (1989).
8. S. Takagi, T. Kimura, N. Sato, T. Satoh, and T. Kosuya, J. Phys. Soc. Japan 57, 1562 (1988).
9. K. A. Gschneidner, Jr., J. Tang, S. K. Dhar, and A. Goldman, Physica B163, 507 (1990).
10. J. Kohlmann, E. Bauer, and K. Winzer, J. Magn. Magn. Mat. 82, 169 (1989).
11. S. K. Dhar and K. A. Gschneider, Jr., J. Magn. Magn. Mat. 79, 151 (1989).
12. Z. Fisk, J. D. Thompson, and H. R. Ott, J. Magn. Magn. Mat. 76 & 77, 637 (1988).
13. C. D. Bredl, S. Horn, F. Steglich, B. Lüthi, and R. M. Martin, Phys. Rev. Lett. 52, 1982 (1984).
14. C. Lacroix, J. Magn. Magn. Mat. 63 & 64, 239 (1987).
15. J. O. Willis, R. H. Aiken, Z. Fisk, E. Zirngiebl, J. D. Thompson, H. R. Ott, and B. Batlogg, in Proceedings on the International Conference on Valence Fluctuations, Bangalore, India (Plenum, NY, 1987), p. 57.
16. E. Bauer, N. Pillmayr, E. Gratz, D. Gignoux, D. Schitt, K. Winzer, and J. Kohlmann, J. Magn. Magn. Mat. 71, 311 (1988).

17. S. Barth, H. R. Ott, F. N. Gygax, B. Hitti, E. Lippelt, A. Schenck, C. Baines, Bivanden Brandt, T. Konter, and S. Mango, Phys. Rev. Lett. 59, 2991 (1987).
18. G. R. Stewart, Z. Fisk, and M. S. Wire, Phys. Rev. B30, 482 (1984).
19. K. Satoh, T. Fujito, Y. Maeno, Y. Onuki, and T. Komatsubara, J. Magn. Magn. Mat. 76 & 77, 128 (1988).
20. J. O. Willis, R. H. Aikin, Z. Fisk, E. Zirngiebl, J. D. Thompson, H. R. Ott, and B. Batlogg, in: Theoretical and Experimental Aspects of Valence Fluctuations and Heavy Fermions, eds. L. C. Gupta and S. K. Malik (Plenum, New York, 1987), p. 57.

Figure Captions

Figure 1. Specific heat divided by temperature vs. temperature squared for  $\text{CeCu}_4\text{Al}$  between 0.35 and 1.1 K in 0, 4, 8, and 11 T.

Figure 2. Specific heat divided by temperature at 0.35 vs. magnetic field for  $\text{CeCu}_4\text{Al}$ . The solid line represents the best fit to eqn. 1.

Figure 3. Specific heat divided by temperature vs. temperature for  $\text{CeCu}_2\text{An}_2\text{Al}$  between 0.35 and 4 K in 0, 5, 9, and 12.5 T.

Fig. 1.  
CeCu<sub>4</sub>Al

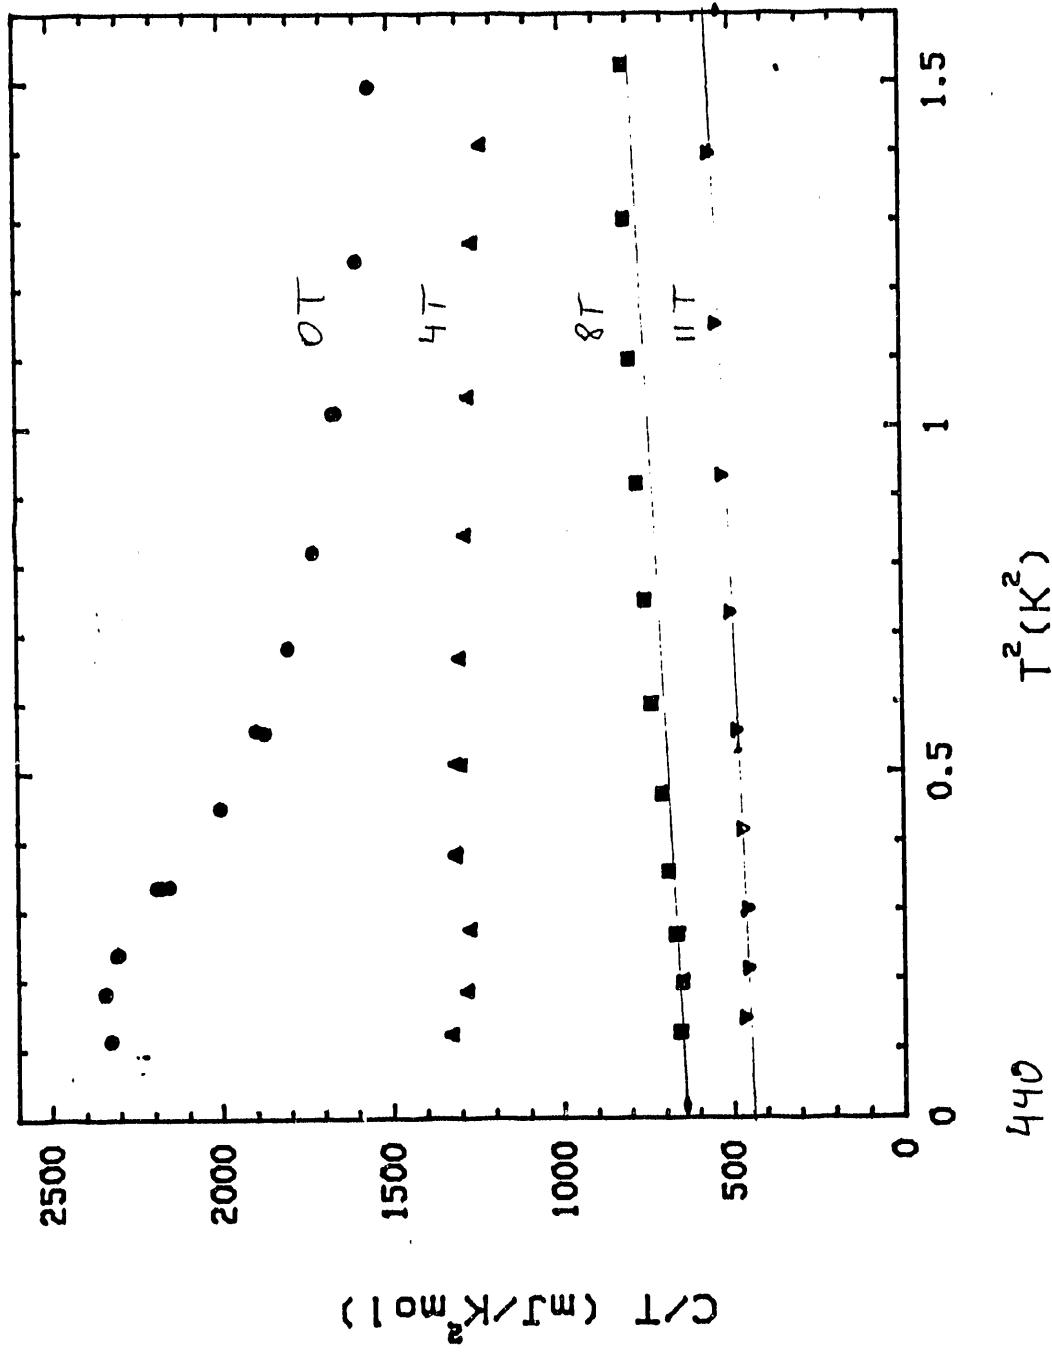


Fig. 2


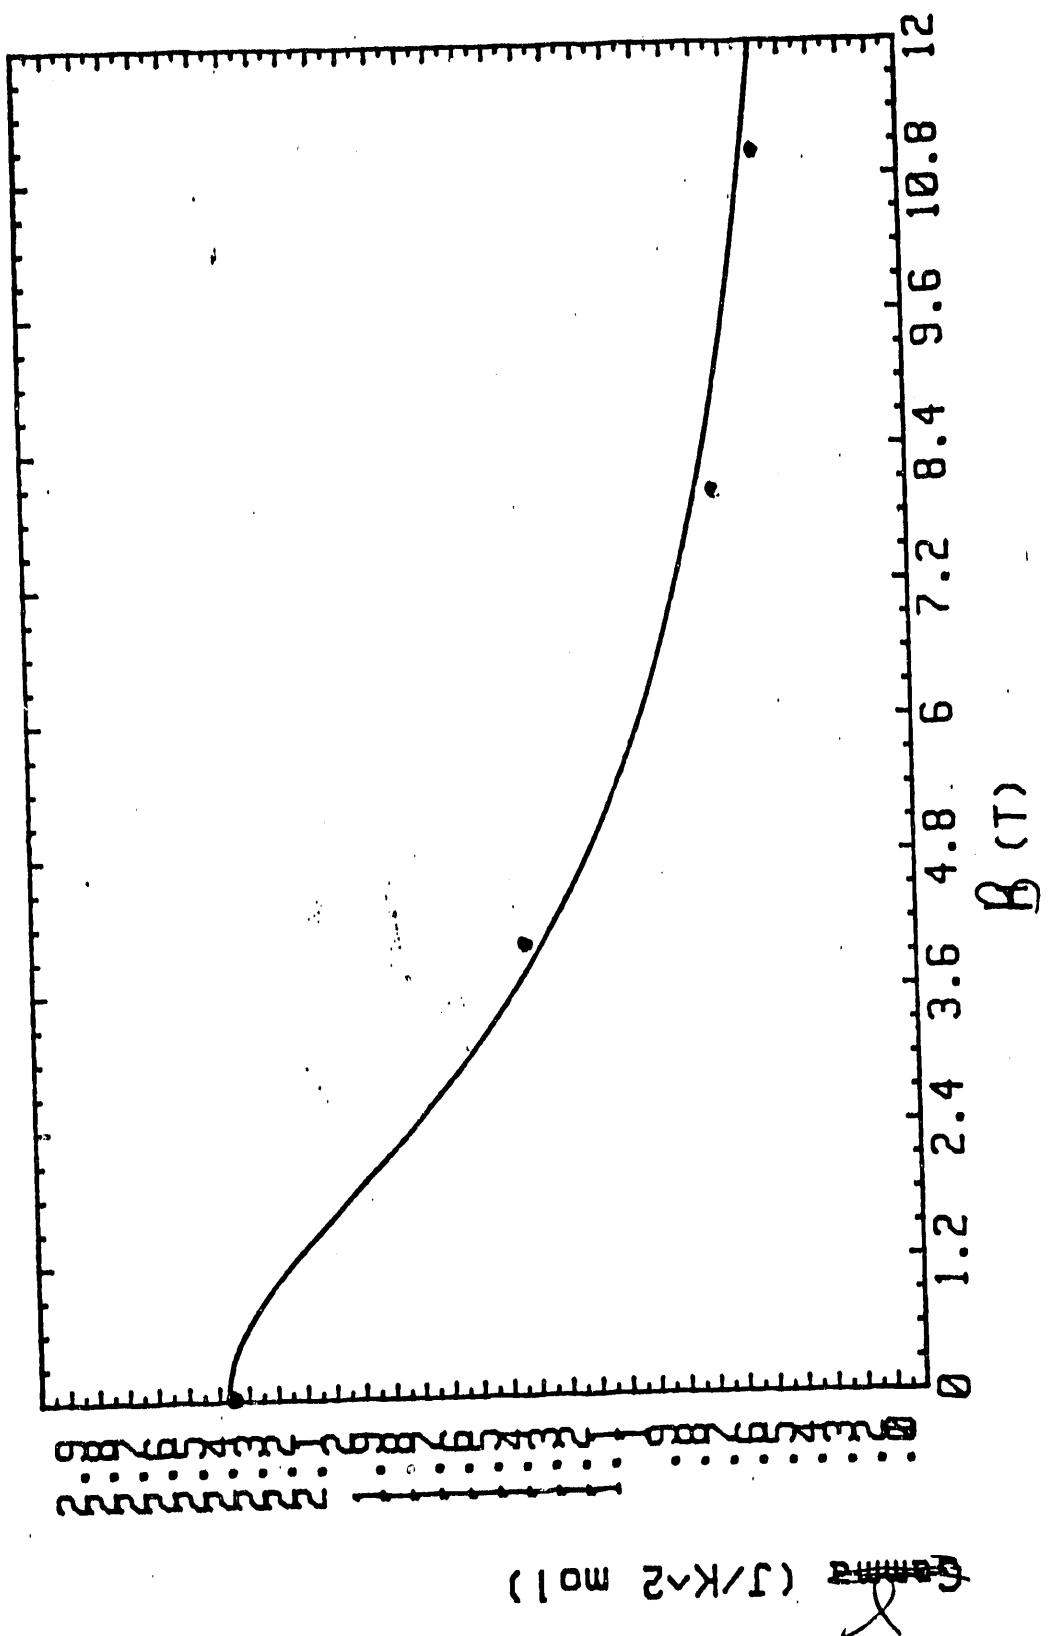


Fig. 3.

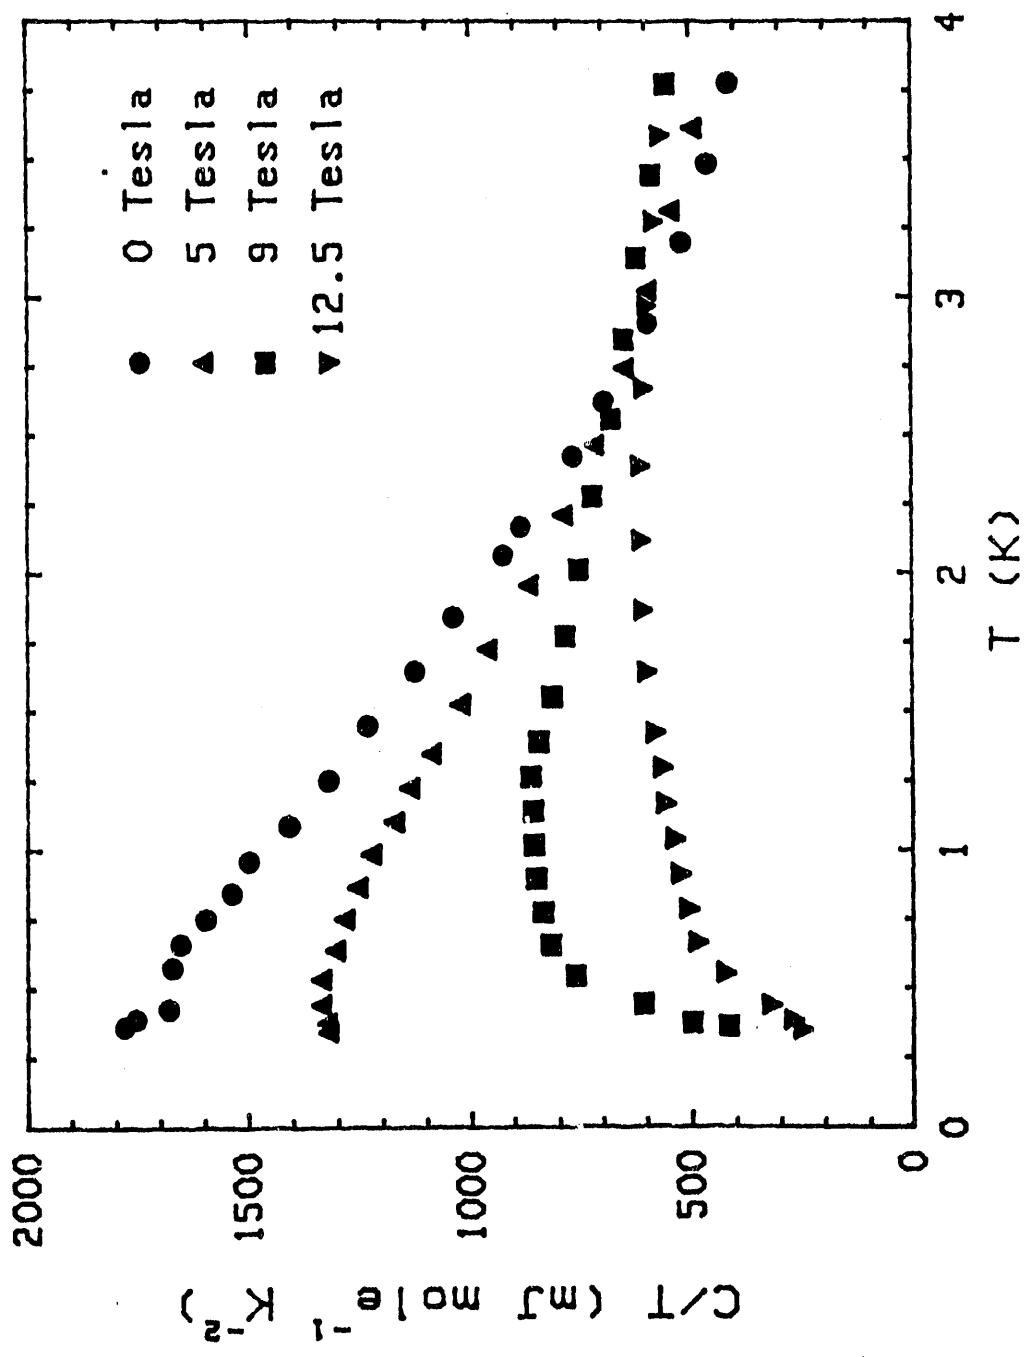

END

DATE  
FILMED  
4/6/92

2

