

Mechanical States in Wound Heterogeneous Tapes by the Finite Element Method*

R. K. Thomas
 Sandia National Laboratories
 Albuquerque, New Mexico 87185

SAND--90-3129C
 DE91 009255

Received by USI

MAR 22 1991

Abstract

The problem of predicting the mechanical stress and deformation states in wound tapes that result from the winding process is addressed by application of the finite element method. The generally heterogeneous tape construction is approximated by continuum finite elements each of which represents many tape plies. Material behavior within the finite element continuum is assumed to be orthotropic elastic. The actual winding process, in which stressed plies are added to an already stressed but partially wound tape, is simulated by sequentially activating layers of finite elements which have initial stress equal to the average winding stress. This model has been implemented in the three-dimensional code JAC3D. Numerical results are presented for the case of a regular two-dimensional circular geometry, for which analytical solutions have been reported in the literature. The favorable comparison between finite element results and analytical results for this example problem validate the finite element approach.

Introduction

Orthotropic, heterogeneous rolls are fabricated by simultaneously center winding plies of different materials around a common mandrel, or core. Figure 1 shows a capacitor being wound with two plies of aluminum conductor and four plies of mylar dielectric constituting a single wrap. In this construction a common winding tension is applied to all plies as the mandrel turns, so that the stress state in the interior of the partially wound capacitor is continuously altered as new wraps are added. Knowledge of the stress states in completed tapes is necessary to assess reliability of the winding process. For example, insufficient radial compression can result in ply separation, and loss of circumferential tension can result in local ply instabilities such as buckling. Additionally, the stress state in the completed tape can be altered in a deleterious manner by electric and magnetic fields, gravity, and thermal gradients imposed during operation of the winding.

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

*This work performed at Sandia National Laboratories supported by the U. S. Department of Energy under contract number DE-AC04-76DP00789.

MASTER


EB

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

DISCLAIMER

Portions of this document may be illegible in electronic image products. Images are produced from the best available original document.

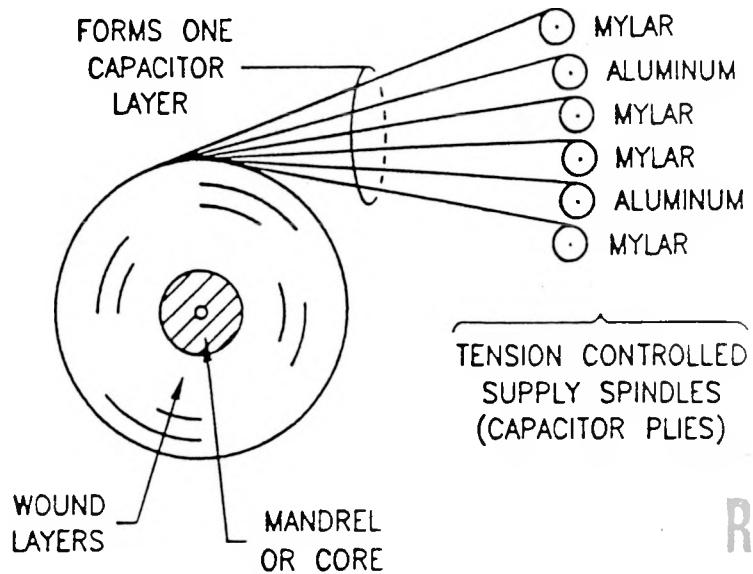

Received by OSTI

MAR 22 1991

Figure 1. Tape Winding Process for Six-Ply Construction

Determination of the mechanical states in wound tapes belongs to the general class of accreting body problems discussed by Brown and Goodman [1]. These problems are characterized by the continual addition of stressed material to an already stressed and deformed body. Typical problems include the case of a gravitating sphere which grows to a stable size by acquiring material uniformly through accretion, and a concrete dam which is built up in successive layers. Solutions to accreting body problems are nonlinear in the sense that they are path dependent. In the wound tape problem the final stress state will not be the same if all wraps with initial tension are added simultaneously. Compatibility arguments prevent the individual wraps from fitting together because the final circumferential length of each wrap is not known before it is added to the partially wound tape.

Analytical expressions for the stress states in homogeneous wound tapes have been reported by Harland [2], Altmann [3], and others. Viscoelastic material behavior was considered by Tramposch [4], and heterogeneous ply constructions were reported on by Reuter [5]. Generally these theories have been limited to the geometric and constitutive equations of linear, two-dimensional elasticity. Willett and Poesch [6] introduced the finite difference method as a tool to solve winding problems for nonlinear materials, but only for the case of cylindrical symmetry.

In this paper the finite element method is presented as a method to extend the predictive capability to problems of complex geometry and nonlinear materials. It is also desirable to have the capability to predict winding stresses in noncircular coils, to analyze asymmetric thermal and gravitational loadings, and to study the general problem of interlayer friction on slippage instabilities. The finite element method offers the potential to solve these problems. This paper presents the general methodology for finite element analysis of the tape winding process, and reports comparisons of predicted stresses for a capacitor with cylindrical symmetry with analytic solutions reported in the literature.

The Finite Element Approach

Application of the finite element method rests upon the assumption that the discontinuous displacements across individual plies within a representative elementary volume can be approximated by average displacements within a replacement continuum. In practice this means that the characteristic length of the finite element must be large compared to the thickness of the individual plies. Once this assumption is made, the gross behavior of the heterogeneous mixture of plies can then be modelled with a single material constitutive relation. The concept of representative elementary volumes has been previously applied with success to modelling jointed rock media [7].

The finite element method applied to the tape winding problem is illustrated in Figure 2. The mandrel and the final wound geometry are meshed, with the coil winding being discretized into finite element layers. The extent of the discretization, or layering, depends upon the

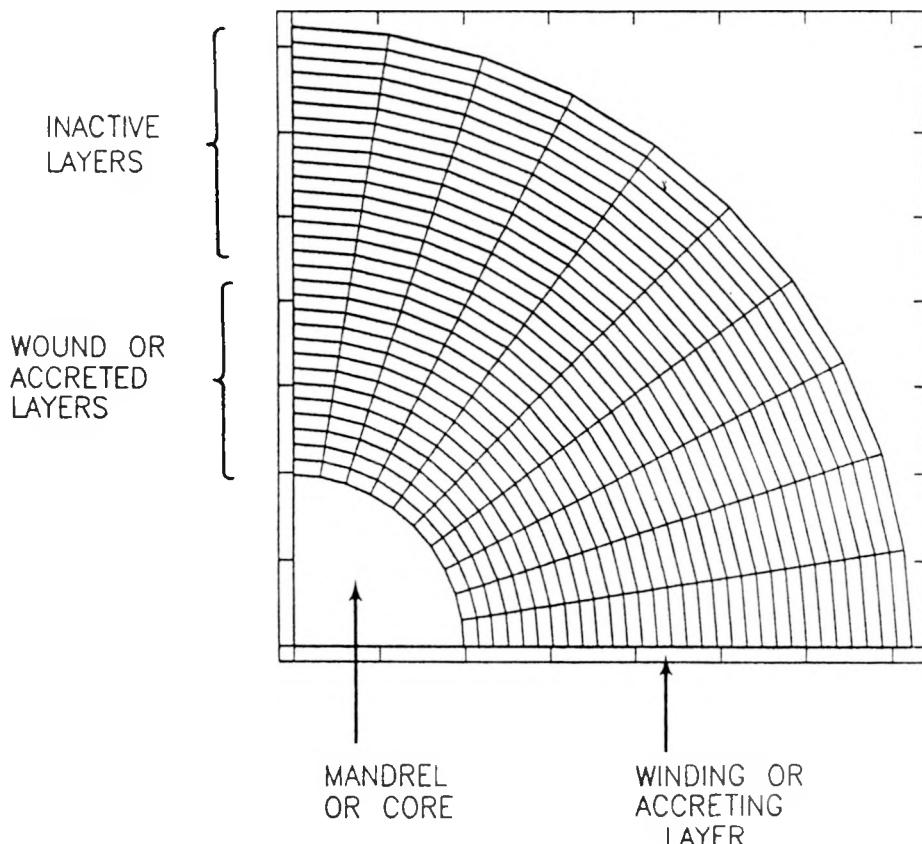


Figure 2. Finite Element Approach to Tape Winding

desired resolution of the mechanical states. Each layer contains many plies, and has initial circumferential stress equal to the winding stress, i.e., the winding tension per unit area of winding cross section. At the beginning of the calculation, all finite element layers are inactive in the sense that their nodal generalized coordinates are omitted from the solution process. With each load step, an additional layer is added, or accreted, to simulate the winding process. The accreting layer is activated and all layers outside of the accreting layer remain inactive. Numerical solutions to the stress and deformation states are obtained for the partially wound tape at each step in the winding process. When the outer, or final, layer is accreted, the resulting stress and deformation state is that for the completely wound tape.

Orthotropic Material Model

An orthotropic, elastic material law is employed to model the behavior of a finite element composed of many heterogeneous plies. In three-dimensional cylindrical coordinates, these standard relations are,

$$\begin{aligned}
 e_{rr} &= \frac{\sigma_{rr}}{E_{rr}} - \frac{\nu_{\theta r} \sigma_{\theta\theta}}{E_{\theta\theta}} - \frac{\nu_{zr} \sigma_{zz}}{E_{zz}} \\
 e_{\theta\theta} &= -\frac{\nu_{r\theta} \sigma_{rr}}{E_{rr}} + \frac{\sigma_{\theta\theta}}{E_{\theta\theta}} - \frac{\nu_{z\theta} \sigma_{zz}}{E_{zz}} \\
 e_{zz} &= -\frac{\nu_{rz} \sigma_{rr}}{E_{rr}} - \frac{\nu_{\theta z} \sigma_{\theta\theta}}{E_{\theta\theta}} + \frac{\sigma_{zz}}{E_{zz}} \\
 \gamma_{r\theta} &= \frac{\tau_{r\theta}}{G_{r\theta}} \\
 \gamma_{\theta z} &= \frac{\tau_{\theta z}}{G_{\theta z}} \\
 \gamma_{zr} &= \frac{\tau_{zr}}{G_{zr}}
 \end{aligned} \tag{1}$$

Example: Cylindrically Symmetric Capacitor

As an example of the finite element approach to tape winding processes, consider the problem of a cylindrically symmetric capacitor. Analytical solutions for this example have been reported by Reuter [5]. Each capacitor winding is composed of four plies of mylar dielectric and two plies of aluminum conductor, as illustrated in Figure 1. This six-ply construction is wound onto a Lexan mandrel. Material and geometric properties for the mylar plies are,

$$\begin{aligned}
 E_{rr} &= 1.72 \times 10^2 \text{ MPa} \\
 E_{\theta\theta} &= 4.41 \times 10^3 \text{ MPa} \\
 \nu_{r\theta} &= 0.017 \\
 t &= 1.02 \times 10^{-2} \text{ mm}
 \end{aligned} \tag{2}$$

for the aluminum plies,

$$\begin{aligned}
 E_{rr} &= 6.89 \times 10^4 \text{ MPa} \\
 E_{\theta\theta} &= 6.89 \times 10^4 \text{ MPa} \\
 \nu_{r\theta} &= 0.33 \\
 t &= 5.59 \times 10^{-3} \text{ mm}
 \end{aligned} \tag{3}$$

and for the lexan mandrel,

$$\begin{aligned}
 E_{rr} &= 6.89 \times 10^3 \text{ MPa} \\
 E_{\theta\theta} &= 6.89 \times 10^3 \text{ MPa} \\
 \nu_{r\theta} &= 0.40 \\
 R &= 3.96 \text{ mm}
 \end{aligned} \tag{4}$$

where t is the thickness of an individual ply, and R is the radius of the solid mandrel. This design of capacitor has 50.8 mm wide ply materials, 2.4 N of tension which is constant throughout the winding process, and 200 windings. This results in a total of 1200 plies in the completely wound capacitor.

Equivalent, orthotropic material properties for the six-ply construction were derived by Reuter. These are,

$$\begin{aligned}\bar{E}_{rr} &= 2.20 \times 10^2 \text{ MPa} \\ \bar{E}_{\theta\theta} &= 1.83 \times 10^4 \text{ MPa} \\ \bar{\nu}_{r\theta} &= 0.085\end{aligned}\quad (5)$$

The finite element calculations were performed with the three-dimensional code JAC3D [8]. The two-dimensional geometry was modelled in the three-dimensional code by applying appropriate symmetry conditions. The completed capacitor windings were divided into 30 concentric finite element layers, which are shown in Figure 2. Each finite element layer therefore modelled the behavior of 40 plies.

Radial and circumferential stresses are compared with Reuter's analytical solutions in Figures 3 and 4, respectively. Analytical solutions have been obtained for cases in which the completed capacitor winding has been divided into 10, 20 and 200 layers. The analytical solution for 200 layers is the correct, or convergent, solution for this example because 200 turns of the mandrel was required to produce the completed geometry. It can be seen that the the finite

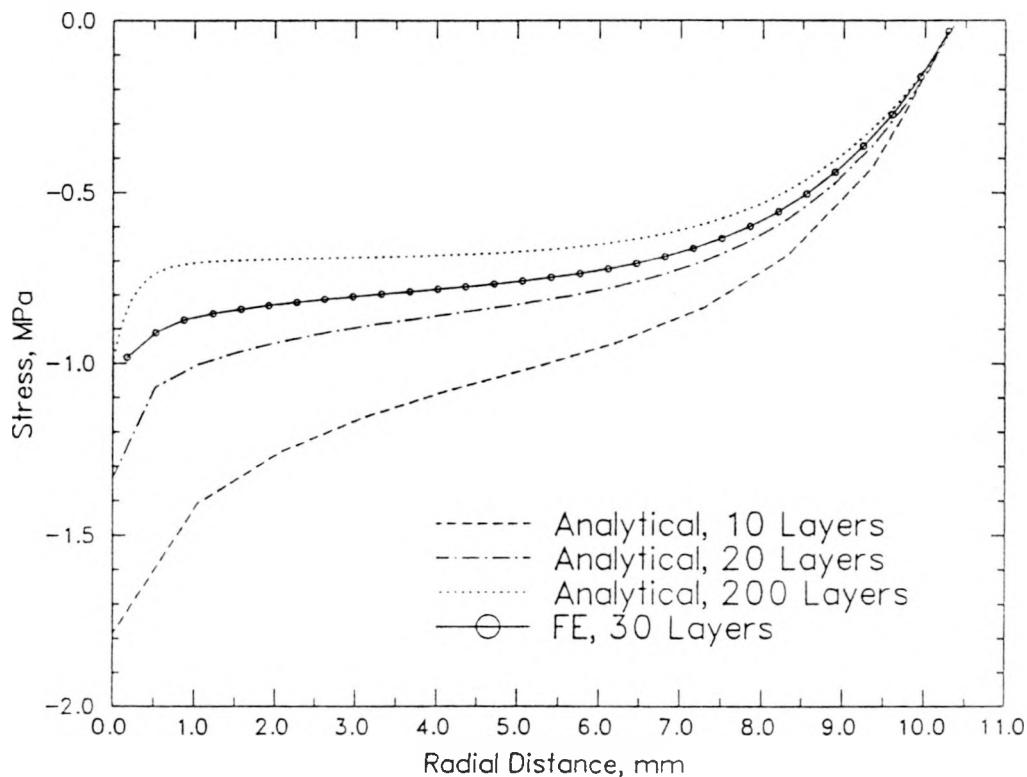


Figure 3. Radial Stresses in Capacitor Winding

element stresses, obtained for 30 layers, fall between the analytically computed stresses obtained for 20 and 200 layers. However, more resolution is needed to model the circumferential stresses in those windings adjacent to the mandrel. Mechanical states at these locations are primarily governed by the initial windings, and only minimally altered by subsequent windings. The nonlinear distribution of stresses in partially wound tapes is similar to those in the completed tape. The finite element model used for this example has difficulty modelling the nonlinear distributions in the first few windings because of the assumption of linear displacement fields within the continuum elements. This problem exists down to the level of a single winding.

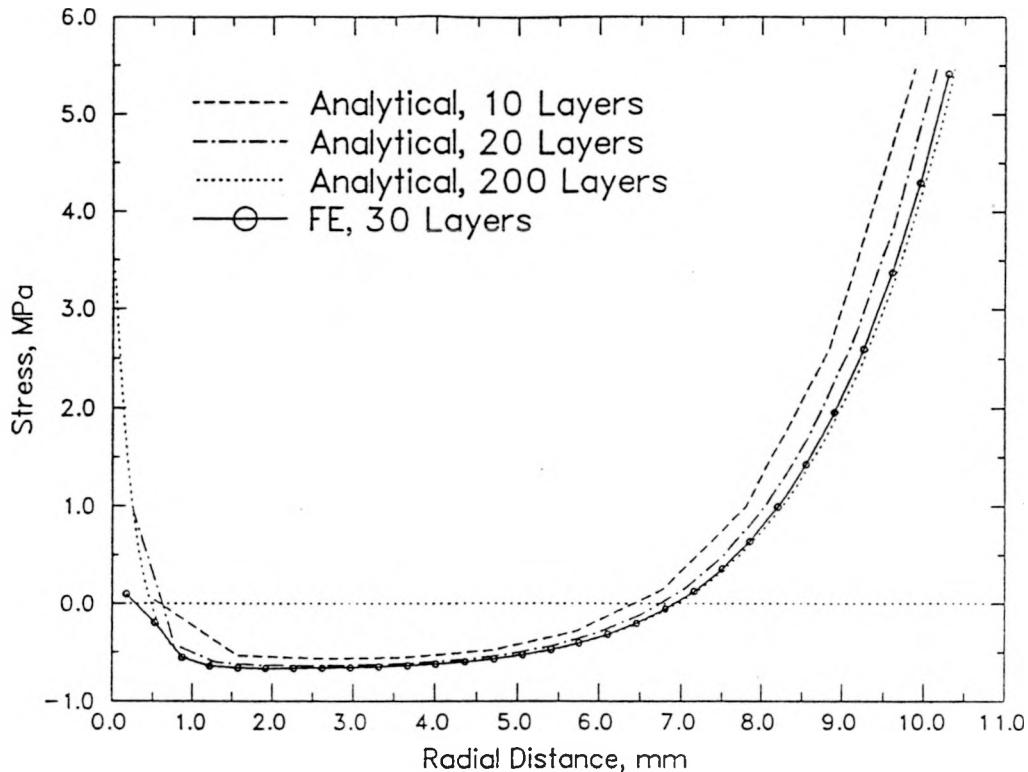


Figure 4. Circumferential Stresses in Capacitor Winding

More study is needed to arrive at appropriate discretization of these initial windings, and the effect of the discretization on mechanical states in the completed tape.

Conclusions and Future Work

It has been shown that the finite element method can be applied to computing process winding stresses in heterogeneous tape constructions. More work is needed to assess the layering resolution required to predict circumferential stresses in windings adjacent to the mandrel.

The finite element method is a potentially valuable tool for studying noncircular tapes, and the effects of asymmetric temperature and gravitational loadings. Neither of these problems can be attacked by the two-dimensional analytical formulations.

Inter-ply friction can potentially be modelled by incorporating a Mohr-Coulomb failure criteria in the orthotropic material constitutive model. By this method, initiation of slip resulting from asymmetric loading, for example, may be addressed. Post-slip behavior would be difficult to model because large geometric deformations are not easily or accurately established through constitutive relationships.

The extension of the finite element method to slip problems is not straightforward if the slip instability results from the spiral winding. Continuum finite element modelling of spiral windings may not be possible because of the extremely large number of elements which would be needed to model the entire coil. Slip instabilities which initiate at a point would be difficult to model within the continuum assumption of representative elementary volumes. Conceptually, spiral windings can be modelled by orthotropic, truss-like elements which are linked together and maintain compatibility during the winding process. The feasibility of this approach will be investigated in our future work.

References

- [1] C. B. Brown and L. E. Goodman, *Gravitational Stresses in Accreted Bodies*, Proc Royal Society of London, series A, vol 276, pp 571-576 (1963).
- [2] W. G. Harland, *Stress Distribution and Winding Faults in Reels of Plastic Film*, Polymer Engineering and Science, pp 58-62 (1967).
- [3] H. C. Altmann, *Formulas for Computing the Stresses in Center-Wound Rolls*, Tappia, vol 51, no 4, pp 176-179 (1968).
- [4] H. Tramposch, *Relaxation of Internal Forces in a Wound Reel of Magnetic Tape*, Jour Appl Mech, pp 865-873 (1965).
- [5] R. C. Reuter, Jr., *Mechanical and Thermomechanical Stress States in Wound, Composite Rolls*, Proc Fifth Japan - U.S. Conf on Composite Materials, Tokyo, Japan, June 24-27 (1990).
- [6] M. S. Willett and W. L. Poesch, *Determining the Stress Distributions in Wound Reels of Magnetic Tape Using a Nonlinear Finite-Difference Approach*, Jour Appl Mech, pp 365-371 (1988).
- [7] R. K. Thomas, *A Continuum Description for Jointed Media*, SAND81-2615, Sandia National Laboratories (1982).
- [8] J. H. Biffle, *JAC3D - A Three-Dimensional Finite Element Computer Program for the Nonlinear Quasi-Static Response of Solids with the Conjugate Gradient Method*, SAND87-1305, Sandia National Laboratories (1987).