

CONF-901125-17

UCRL-JC--103724

DE91 006707

... CSTI

JAN 28 1991

A Photoemission Investigation of Compound
Semiconductor Monodisperse Clusters

J. G. Tobin
V. L. Colvin
A. P. Alivisatos

This paper was prepared for submittal to
J. Vac. Sci. Tech. A
and 1990 Symposium of the Am. Vac. Soc.
Toronto, Canada
October 1990

December 7, 1990

Lawrence
Livermore
National
Laboratory

This is a preprint of a paper intended for publication in a journal or proceedings. Since changes may be made before publication, this preprint is made available with the understanding that it will not be cited or reproduced without the permission of the author.

MASTER
d/s
DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

DISCLAIMER

This document was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor the University of California nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial products, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or the University of California, and shall not be used for advertising or product endorsement purposes.

MODIFIED BY
JCT, 6/06/90

~~TD~~

OCT 23 1990

Abstract # : 321
Program # : EM-TUM3
Put on JVST manuscript
18-oct-90

A PHOTOEMISSION INVESTIGATION OF COMPOUND SEMICONDUCTOR MONODISPERSE CLUSTERS. J. G. Tobin, Lawrence Livermore National Laboratory, L-268, Livermore, CA 94551; V. L. Colvin and A. P. Alivisatos, University of California, Berkeley, CA 94720.

Abstract

We have used synchrotron radiation photoemission to probe the valence and core level electronic structure of compound-semiconductor monodisperse clusters (nanocrystals). These clusters exhibited a 10% or less variation relative to the mean diameter and were attached to the metal substrates via alkane chains. Direct evidence of gap broadening due to size variation in CdS clusters was observed. The novel utilization of alkane chain attachment is the key to eliminating the otherwise debilitating problem of sample charging, as occurs with powders. The quality of sample preparation was confirmed by other methods such as transmission electron microscopy, Raman scattering and x-ray diffraction. This work provides a direct link between photoemission studies of epitaxial ultra-thin films of compound semiconductors, the photone-spectroscopy measurements of cluster powders and the existing theories of quantum confinement in reduced dimensionality structures.

For submission to the J. Vac. Sci. Tech. A., in conjunction with the 1990 Symposium of the Am. Vac. Soc. in Toronto, Canada, October 1990.

ACCT 5685-36

Introduction:

Understanding the relationship between structures and properties on an atomic scale remains a crucial goal in the study of reduced dimensionality systems. One avenue of attack upon these important questions is the study of the size dependence of the electronic structure in compound semiconductor nanocrystals. In these monodisperse (single-size) clusters, the finite size (diameters of 2 to 20 nm, 10^2 to 10^5 atoms) and crystallinity can combine to create effects such as novel variations of their optical properties and catalytic capabilities. The thrust of the experiments described here is to probe the occupied valence electronic structure with synchrotron radiation photoemission, using a unique wet chemical method for growth and attachment of the nanocrystals to the metallic substrates.

NOTE
Clusters

Cluster Synthesis:

One of our goals is to prepare semiconductor clusters in the condensed phase with very narrow size distributions.¹ Clusters of CdS in the 20 to 200 Å size regime with diameter distributions of 3% are routinely synthesized in our laboratory. The chemical preparations rely on the fact that, in the very early stages of crystal growth in solution, small crystallites are formed which all grow in parallel, distributed uniformly in size. By terminating the crystal growth at this stage one is able to capture the crystallites. This is normally done by reacting the crystallites with an organic terminating moiety. This organic group "caps" the cluster surface, preventing the clusters from aggregating or growing further. By appropriately choosing the organic group on the surface one can adjust the solubility of the clusters. Thus the clusters can be dissolved in polar or nonpolar solvents, or they can be dispersed in a polymer film; in addition, all solvent can be removed and one obtains a powder of coalesced clusters (these can

subsequently be redissolved;) finally, the organic group can be bifunctional, so that the other end can be used to attach the clusters to a variety of substrates. We have developed a method to attach the clusters to Au and Al surfaces using short chain alkanes as bridges. This is shown schematically in figure 1.

Cluster Characterization:

Once the clusters are made they are characterized by the following methods¹:

1. Transmission Electron Microscopy is performed at the National Center for Electron Microscopy at LBL. These experiments allow us to determine particle size and shape. From the electron diffraction pattern one can determine the crystallinity of the samples.
2. X-ray powder diffraction is used to determine the crystallinity of the samples. The width of the X-ray diffraction lines are consistent with the finite size of the clusters, and indicate that the material is highly crystalline.
3. Resonance Raman scattering is used to measure the vibrational spectra.
4. Optical absorption is measured to study quantum size effects.
5. X-ray fluorescence is used for elemental analysis.
6. In-house X-ray photoelectron spectroscopy (XPS).

Synchrotron Radiation Photoemission

The occupied electronic structure of the clusters was probed with photoemission,² using synchrotron radiation from the 4 meter NIM beamline on the 1GeV ring, Aladdin, at the University of Wisconsin Synchrotron Radiation Center. An example of our data is shown in figure 2. The novel use of the alkane chain attachment of the cluster to the metal substrate is essential for the avoidance of sample charging. As described above, the quality of the sample

preparation was confirmed by several other methods and the distribution of cluster diameters is 10% or less of the mean diameter.

One of the most interesting properties of the clusters is the strong dependence of the valence band maximum on size. The crystallites we make are smaller than the bulk semiconductor exciton diameter, and consequently show quantum size effects. We have observed these effects in photoemission spectra which were obtained for CdS clusters ranging in size from 32 to 70 Å diameter.³ The clearest result to emerge from these experiments is that the valence band collapses in the smaller clusters. That is, the valence band maximum moves to smaller binding energies as the nanocrystals increase in size. This shift is due to both a quantum confinement in the initial state and size-dependent final state charge solvation, as described in Ref. 3.

In the future, we expect that at sufficiently high resolution we should be able to observe a discrete series of states in the valence bands of the smallest clusters. Additionally, we recently have begun work using GaAs clusters⁴ and have collected preliminary photoemission data of the GaAs clusters at the Stanford Synchrotron Radiation Laboratory.⁵

Acknowledgements:

A. P. Alivisatos and V. L. Colvin appreciate the support of the NSF through contract DMR-9057186. Work performed under the auspices of the U.S. Department of Energy by the Lawrence Livermore National Laboratory under contract No. W-7405-ENG-48.

References:

1. V. L. Colvin, A. N. Goldstein and A. P. Alivisatos, to be submitted to J. Am. Chem. Soc., 1990.
2. B. J. Knapp, J. C. Hansen, M. K. Wagner, W. D. Clendening and J. G. Tobin, Phys. Rev. B40, 2814 (1989).
3. V. L. Colvin, A. P. Alivisatos and J. G. Tobin, submitted to Phys. Rev. Lett., 1990.
4. M. A. Olshavsky, A. N. Goldstein and A. P. Alivisatos, submitted to J. Amer. Chem. Soc., 1990.
5. J. G. Tobin, V. L. Colvin, A. P. Alivisatos, R. Daley and S. Chaudhury, 1990 Users Meeting of the Stanford Synchrotron Radiation Laboratory.

Figure Captions:

Figure 1. Schematic representation of the attachment of the CdS clusters to the aluminum substrate via alkane chains.

Figure 2. Photoemission spectra of 34Å radius CdS clusters on an aluminum substrate. The photon energies are shown on the side. The binding energy is relative to the Fermi energy, established via gold evaporation. Note the Cd 4d core level peak at a binding energy of about 12 eV. The valence band maximum edge can be seen at a binding energy of about 4 eV. Backgrounds have been subtracted from these spectra.

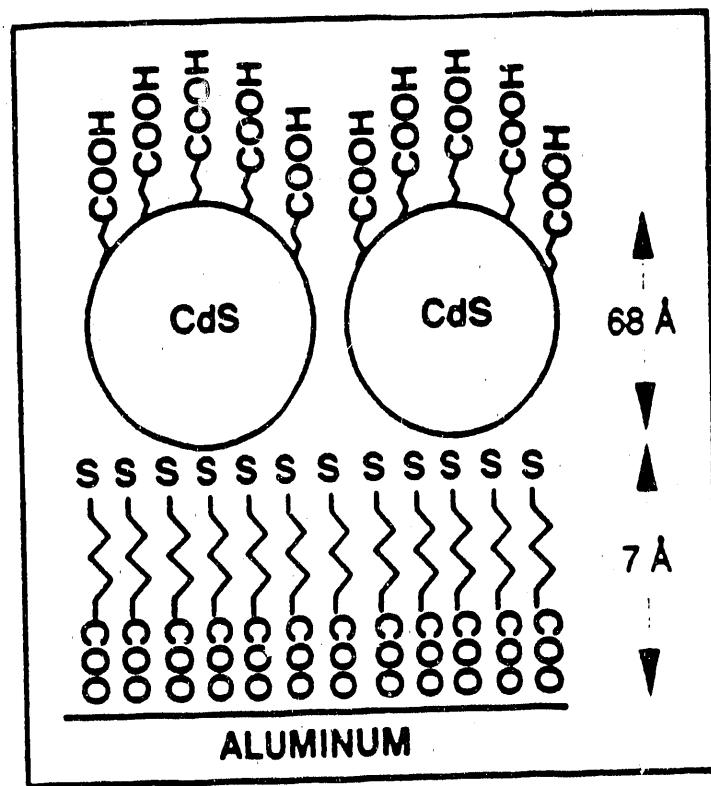


Figure 1.

34 \AA RADIUS CdS ON ALUMINUM

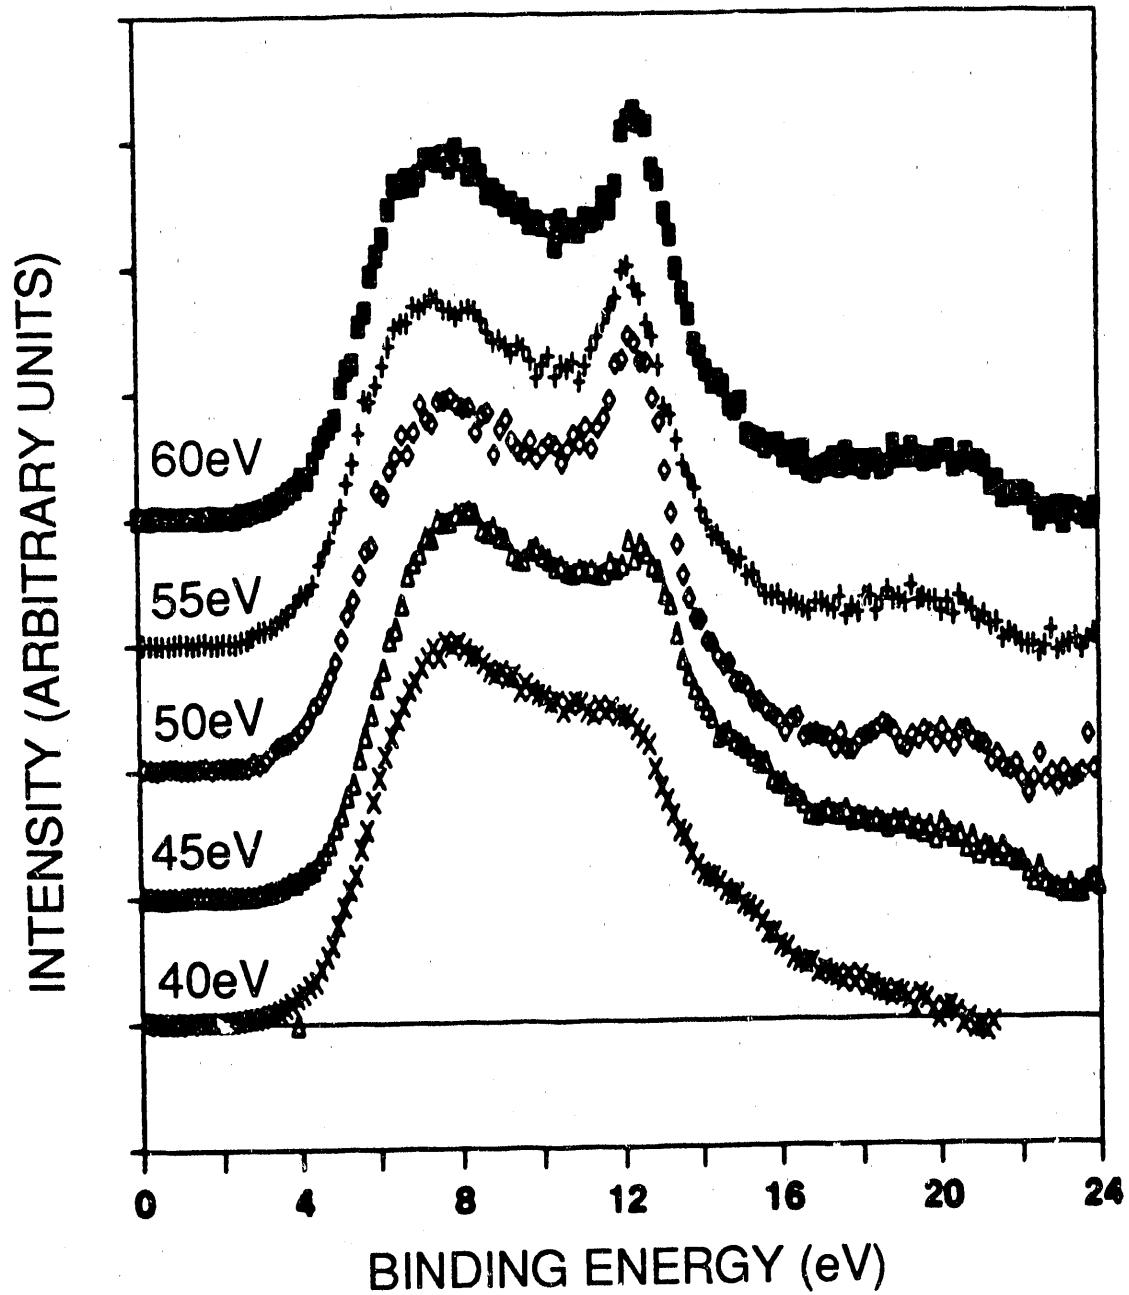


Figure 2.

END

DATE FILMED

02/26/91

