

**"Inelastic Neutron Studies of the Low Energy Phonon Excitations in the  
RENi<sub>2</sub>B<sub>2</sub>C Superconductors (RE=Lu,Y,Ho,Er)" CONF-970814--**

M. Bullock<sup>a</sup>, C. Stassis<sup>a</sup>, J. Zarestky<sup>a</sup>, A. Goldman<sup>a</sup>, P. Canfield<sup>a</sup>, G. Shirane<sup>b</sup>  
and S. Shapiro<sup>b</sup>

<sup>a</sup>Ames Laboratory and Department of Physics, Iowa State University, Ames, IA 50011

<sup>b</sup>Brookhaven National Laboratory, Upton, NY 11973

**Abstract**

We studied the low-energy phonon excitations for wavevectors close to the Fermi surface nesting vector  $\bar{\xi}_m \equiv 0.55 \bar{a}$ . We find that above  $T_c$  the frequencies of the  $\Delta_4[\zeta 00]$  lowest-lying optical and acoustic phonon modes decrease with decreasing temperature, for  $\bar{\xi}$  close to  $\bar{\xi}_m$ , and there is a shift of intensity from the upper to the lower mode, an effect characteristic of coupled modes. From approximately 120K down to temperatures in the vicinity of  $T_c$ , only a single unresolved peak is observed. Below  $T_c$  the phonon spectra of the Y and Lu compounds change dramatically: it consists of a sharp peak at approximately 4.5 meV with a weak shoulder at the higher energy side. No such sharp peak was observed below  $T_c$  in the Ho and Er compounds.

**Key words:** Phonon anomalies; Superconductivity

**MASTER**

Please, address all correspondence to:

Prof. C. Stassis  
Ames Laboratory and Department of Physics  
A523 Physics  
Iowa State University  
Ames, IA 50011  
TEL: (515) 294-4224  
FAX: (515) 294-0689  
E-MAIL: stassis@ameslab.gov

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

DTIC QUALITY INSPECTED 3

19980330 032

Many of the body-centered tetragonal  $RENi_2B_2C$  compounds are superconductors with relatively high superconducting transition temperatures ( $T_c = 16.5, 15.5, 10.5$ , and  $8.5$  for the Lu, Y, Er, and Ho compounds) and in some cases ( $RE = Tm, Ho, Er$ , and  $Dy$ ) superconductivity co-exists with magnetic order.<sup>[1]</sup> Of particular interest, for the present study, is that the frequencies of the lowest lying phonon modes near the nesting vector  $\bar{\xi}_m$  decrease with decreasing temperature,<sup>[2,3]</sup> and a dramatic change in the phonon spectra of both Y<sup>[3]</sup> and Lu<sup>[4]</sup> compounds was observed below  $T_c$ . In this report we present a brief summary of the results obtained in a systematic study of the low-lying phonon excitations of the Lu, Y, Ho, and Er compounds.

The branches of interest are the acoustic and lowest lying optical branch in the  $[\bar{\xi}00]$  direction, both belonging to the  $\Delta_4$  representation. The dispersion of these branches at room temperature, for the Y compound, is shown in Fig. 1. The phonon energies for the Lu, Ho, and Er are, of course, lower than in the Y compound. At room temperature two peaks are observed for  $\xi$  up to approximately 0.45, but these peaks are not easily resolved for  $\xi$  in the vicinity of 0.5 (See Fig. 2).

As the temperature decreases, the energies of the modes in the vicinity of  $\bar{\xi}_m$  decrease and there is transfer of intensity from the optic to the acoustic mode. For temperatures lower than approximately 120K, the two modes cannot be resolved and only a broad feature is observed. This is illustrated for the Lu compound in Figure 2. In the Y compound, it was necessary to perform measurements at temperatures higher than room temperature in order to see clearly this mode interaction. As in the case of ferroelectric materials, the temperature dependence of the anticrossing behavior of the modes observed in the present experiments can be formulated as a problem of mode coupling via anharmonic forces<sup>[5]</sup>.

At temperatures below approximately 120K, and down to the vicinity of  $T_c$ , the  $\Delta_4$  optical and acoustic modes close to  $\bar{\xi}_m$  cannot be resolved and only a relatively broad

## **DISCLAIMER**

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, make any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

feature is observed (see third panel of Fig. 2 and insert in the first panel of Fig. 3). Below  $T_c$  the phonon spectra for the Lu and Y change dramatically. They consist of a sharp peak at approximately 4.5 meV with a weak shoulder at the higher energy side. The width and position of this sharp peak remain practically unchanged below  $T_c$ , its intensity decreases with increasing temperature, and it is practically indistinguishable from the background at temperatures close to  $T_c$  (see insert in the second panel of Fig. 3). From a study of the energies of the sharp peak and the broad shoulder as a function of  $\xi$  and  $\zeta$  (along the  $[00\zeta]$  direction), we concluded <sup>[5]</sup> that the sharp peak must be associated with the acoustic mode and the barely visible shoulder with the optical mode. No such sharp peak was observed in the Ho (see panel 3 of Fig. 3) and Er compounds at low temperatures. It should be pointed out, however, that the detailed study of the low lying phonon excitations in these magnetic superconductors is hindered by the presence of peaks corresponding to crystal electric field (CEF) levels (at approximately 10 meV in Ho and 5 meV in Er).

The experimental results show that the dramatic change in the phonon spectra of the Lu and Y compounds below  $T_c$  must be related to the abrupt change in the polarizability of the superconducting electrons at  $\omega = 2\Delta$ . Actually, recent calculations<sup>[6,7]</sup> yield phonon spectra almost identical to those observed in the present experiments. It should be pointed out, however, that in both approaches the theoretically predicted BCS temperature dependence of the sharp peak does not agree very well with the present experimental results.

This work is supported in part by Contract No. DE-AC02-76CH00016, Division of Materials Sciences, U.S. Department of Energy.

### References

1. For a brief review see: C. Stassis and A. Goldman, *J. Alloys and Comp.* (in press) and references therein.
2. P. Dervenagas, J. Zarestky, C. Stassis, A.I. Goldman, P.C. Canfield, B.K. Cho, *Phys Rev. B* **53**, 8506 (1996).
3. K. Kawano, H. Yoshizawa, H. Takeya, and K. Kadownki, *Phys. Rev. Lett.* **77**, C.V. Tomy, and D. McK. Paul, *Phys. Rev. Lett.* **28**, 935 (1997).
4. C. Stassis, M. Bullock, J. Zarestky, P. Canfield, A. Goldman, G. Shirane, S.M. Shapiro, *Phys. Rev. B* (Rapid Communications) **55**, 8678 (1977).
5. M. Bullock et al. (to be published) and references therein.
6. P.B. Allen, V.N. Kostur, N. Takesue and G. Shirane, *Phys. Rev. Lett* (in print), and references therein.
7. H.-Y. Kee and C.M. Varma (preprint).

### Figure Captions

Fig. 1 Room temperature phonon dispersion of the  $\Delta_4$  acoustic (A) and optic (O) branches of  $\text{YNi}_2\text{B}_2\text{C}$ . For  $\zeta > \xi_m$  the intensity of the optical modes is very weak and this is indicated by a dotted line. The lines are used as a guide to the eye.

Fig. 2 Temperature dependence of the phonon spectra in the vicinity of  $\xi_m$  in the Lu compound, the lines are used as a guide to the eye.

Fig. 3 Phonon profiles obtained below  $T_c$  for the Y, Lu and Ho compounds. Upper insert: typical phonon profile in the vicinity of  $T_c$ . Lower insert: temperature dependence of the intensity of the sharp peak (see text).

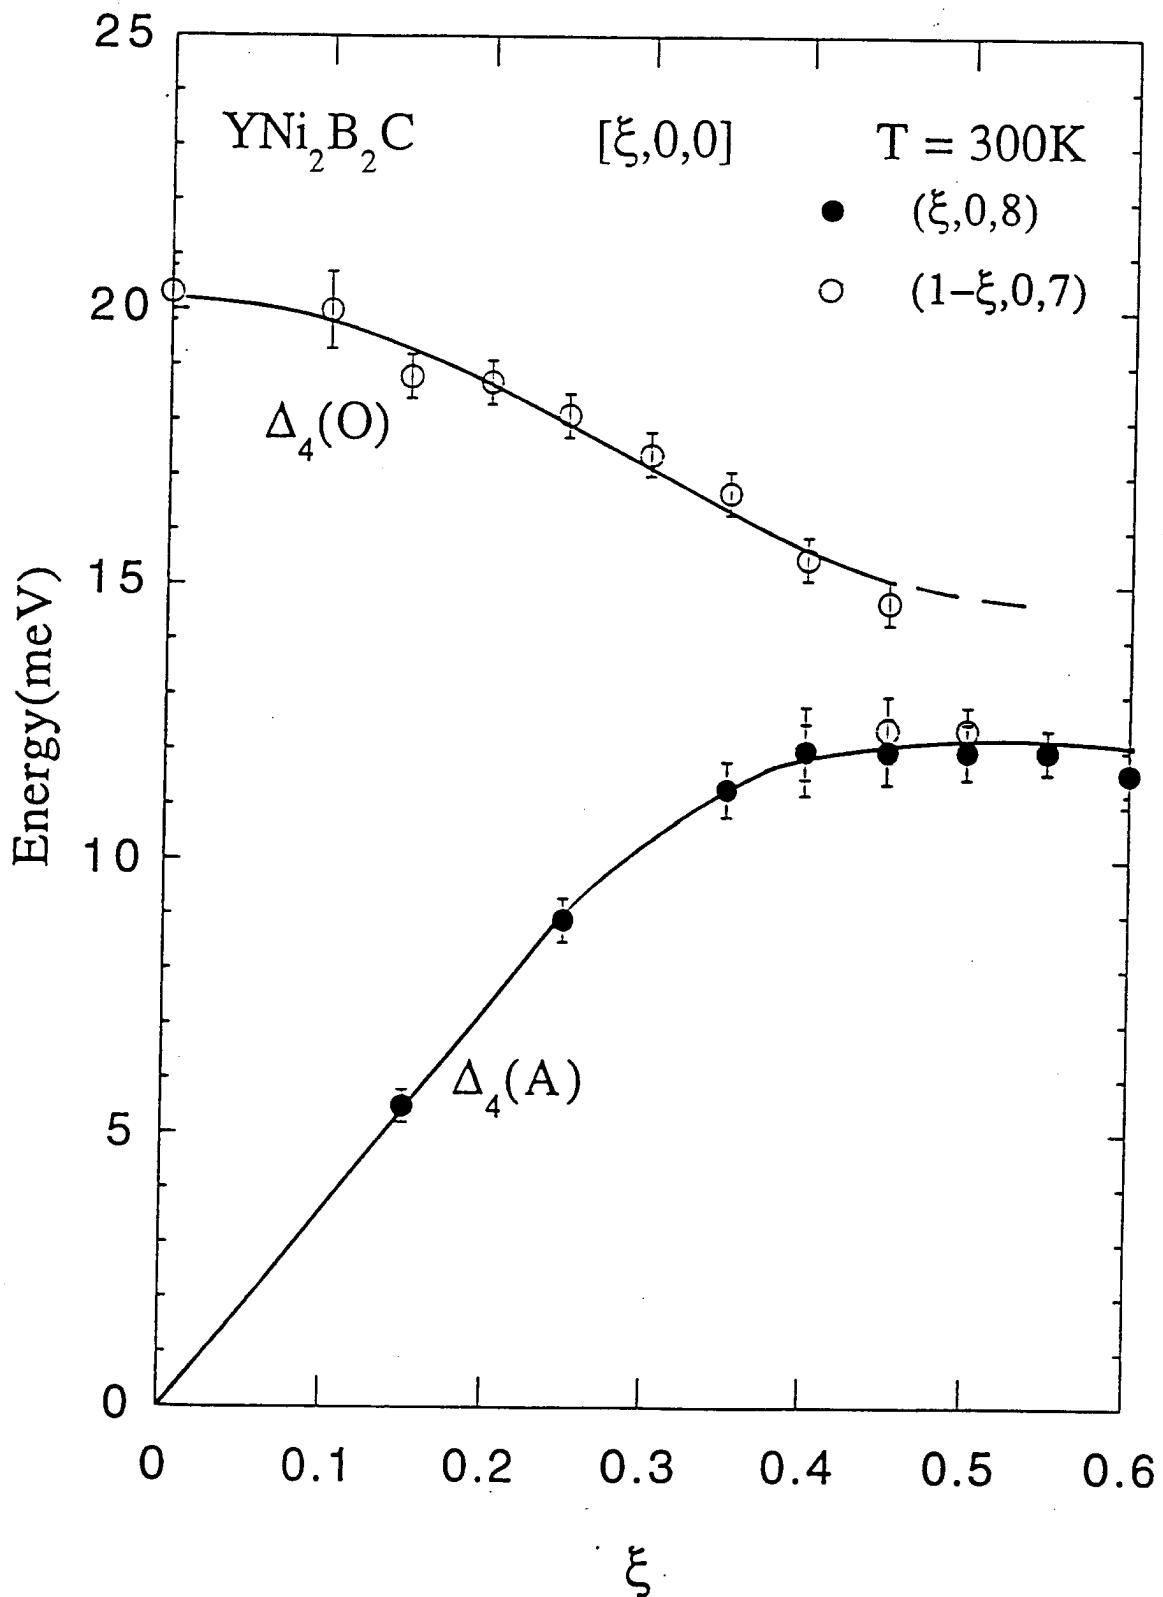


Fig. 1

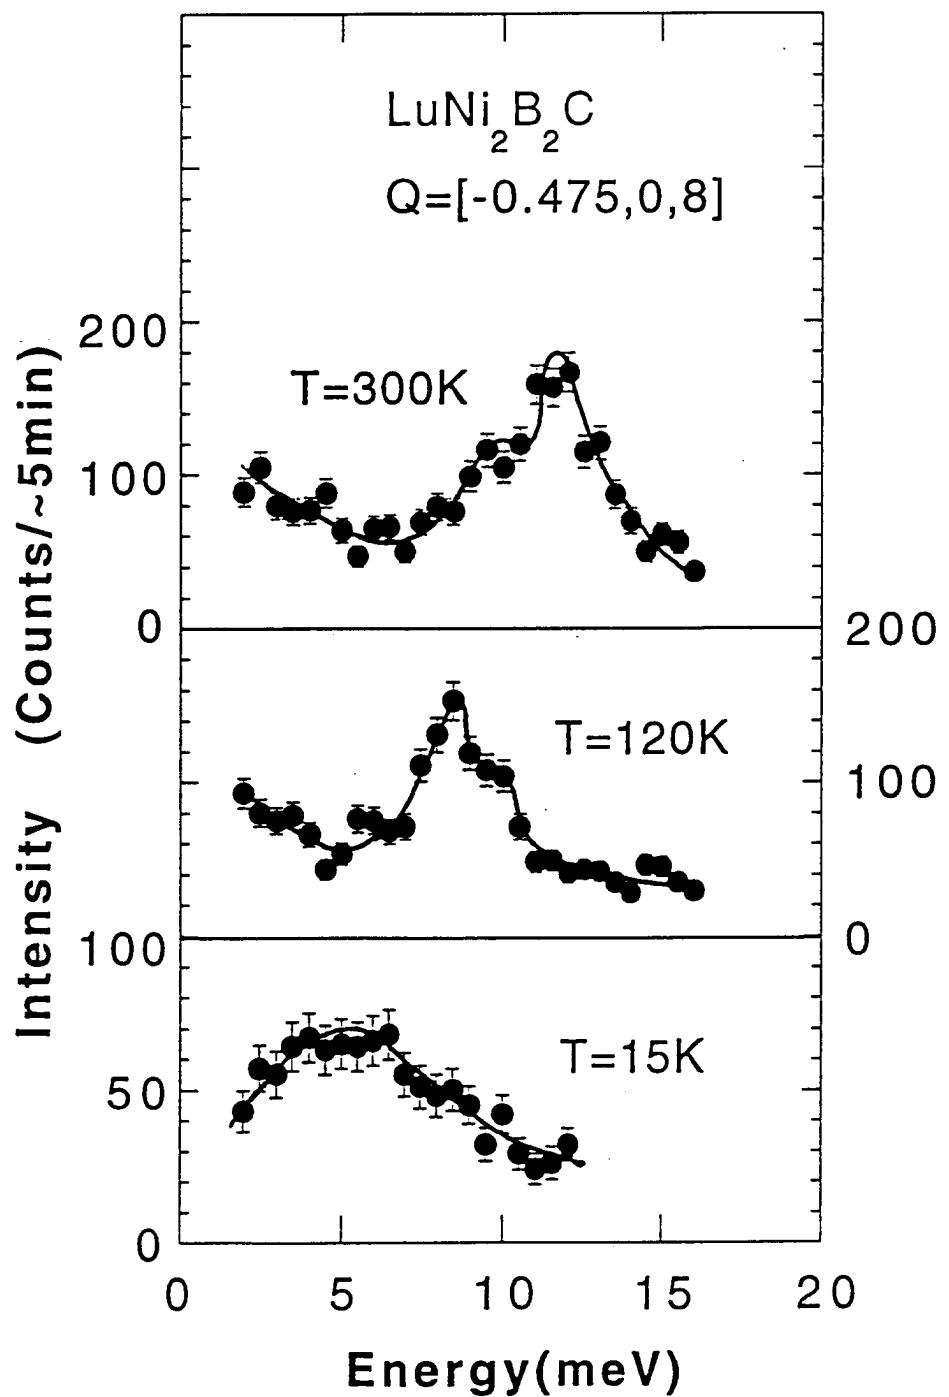


Fig. 2


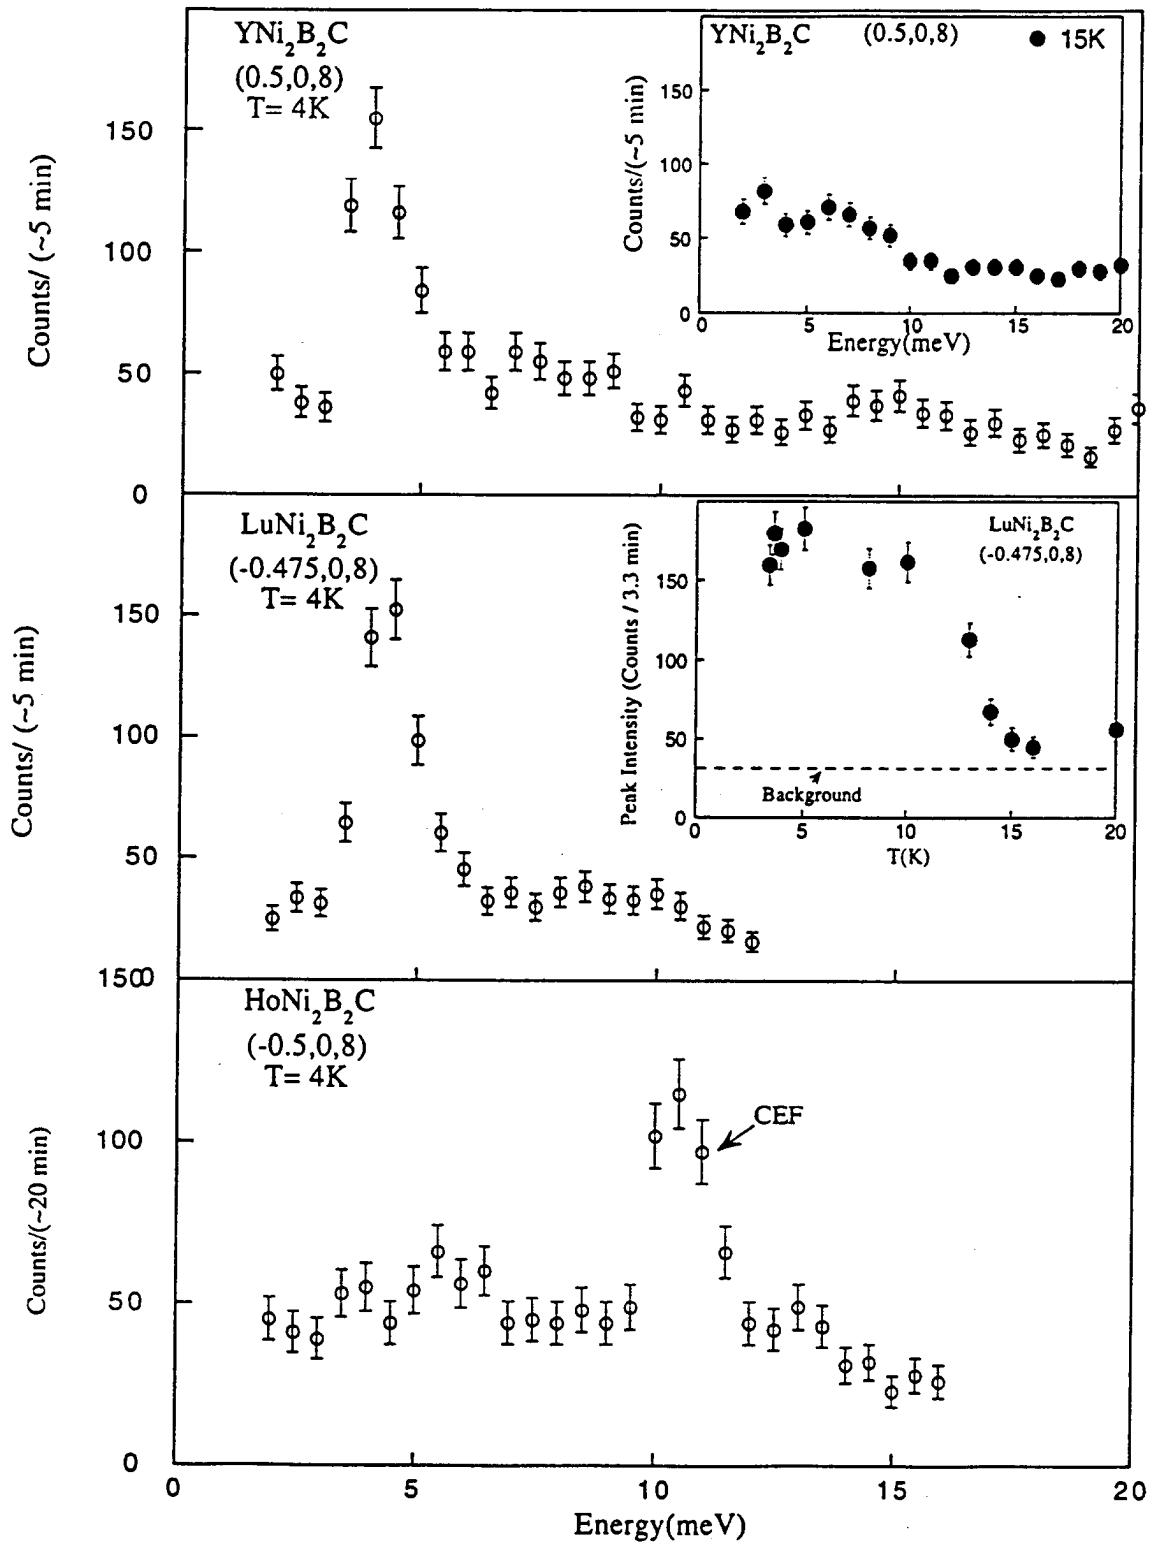


Fig. 3




AMES LABORATORY  
Interoffice Communication

DATE: July 18, 1997

MEMO TO: P. Canfield  
A. Goldman  
S. Shapiro  
G. Shirane  
J. Zarestky

Please, find enclosed a copy of contributed paper submitted for ICNS' 97 at Toronto. It was a very difficult task to write it because of the space limitations.\* Actually, we may have to eliminate one of the figures. However, please let me know if you have any comments and I will try to incorporate them in the final version of the paper.

Best regards,



Costas

\* 400 words reserved for title and abstract and 150 words per figure; 1600 words for the entire paper.



Report Number (14) BNL --64633  
CONF-970814

Publ. Date (11) 199708  
Sponsor Code (18) DOE/ER, XF  
UC Category (19) UC-410, DOE/ER

**DOE**