

CONF-900402

CONF-900402--4

DE90 005663

ACTIVATION OF METHANE BY TRANSITION  
METAL-SUBSTITUTED ALUMINOPHOSPHATE MOLECULAR SIEVES\*

V. A. Maroni, K. A. Willms, Hiephoa Nguyen, and L. E. Iton

Argonne National Laboratory  
9700 South Cass Avenue  
Argonne, Illinois 60439

December 1989

To be published in the  
Preprints of the Fuel Chemistry Division of the ACS  
for the American Chemical Society Meeting  
Boston, MA  
April 22-27, 1990

**DISCLAIMER**

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

\*This work was supported by the U.S. Department of Energy, Office of Basic Energy Sciences, Division of Advanced Projects, under contract W-31-109-ENG-38.

**MASTER**  
DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

## **DISCLAIMER**

**This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency Thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.**

## **DISCLAIMER**

**Portions of this document may be illegible in electronic image products. Images are produced from the best available original document.**

# ACTIVATION OF METHANE BY TRANSITION METAL-SUBSTITUTED ALUMINOPHOSPHATE MOLECULAR SIEVES

V. A. Maroni, K. A. Willms, Hiephoa Nguyen, and L. E. Iton  
Argonne National Laboratory  
9700 South Cass Avenue  
Argonne, Illinois 60439.

Keywords: methane activation, molecular sieve, catalysis

## ABSTRACT

Recent experiments in our laboratory have demonstrated that aluminophosphate molecular sieves substituted with cobalt and cobalt/silicon combinations and having the  $\text{AlPO}_4$ -34 or  $\text{AlPO}_4$ -5 structure activate methane starting at  $\sim 350^\circ\text{C}$ . Between 400 and  $500^\circ\text{C}$  the rate of methane conversion increases steadily with typical conversion efficiencies at  $500^\circ\text{C}$  ranging from 15 to 60%. The cobalt and silicon substituted  $\text{AlPO}_4$ -34 structure (CoAPS0-34) produces ethylene, ethane, propylene, and propane in varying proportions, depending on reaction conditions. The cobalt-substituted  $\text{AlPO}_4$ -5 (CoAPS0-5) produces propylene in very high yield, with ethane, ethylene, and propane also seen. Analogous aluminophosphate molecular sieves substituted with magnesium or silicon, but containing no transition metal (e.g., SAPO-34, MAPO-5), do not activate methane under the conditions described above. The activation mechanism is based on reduction of the cobalt(III) form of the molecular sieve to the cobalt(II) form with accompanying oxidative dehydrogenation of the methane. Reoxidation of the cobalt(II) form to the cobalt(III) form can be done either chemically (e.g., using  $\text{O}_2$ ) or electrochemically.

## INTRODUCTION

In a recently published paper (1) we reported the finding that when Co(II) is substituted for Al(III) in the framework of certain aluminophosphate ( $\text{AlPO}_4$ ) molecular sieves and the resulting Co(II)-containing  $\text{AlPO}_4$  (CoAPO) is calcined in oxygen, the Co(II) is oxidized to Co(III). Further work with these Co(III)APOs showed that they possess strong oxidizing capability, and, for example, can convert methanol to formaldehyde (at  $25^\circ\text{C}$ ),  $\text{NO}$  to  $\text{NO}^+$  (at  $25^\circ\text{C}$ ), and  $\text{H}_2$  to  $2\text{H}^+$  (at  $>300^\circ\text{C}$ ). These results inspired the thought that Co(III)APOs might actually oxidize methane and in the process convert the activated species directly to light hydrocarbons by virtue of their known Bronsted acid catalyzed homologation capacity (2,3) and the product selectivity constraints imposed by their pore dimensions. Recent experiments in our laboratory (summarized below) have demonstrated that this is in fact the case.

## EXPERIMENTAL

The synthesis methods used to prepare the aluminophosphate molecular sieve materials employed in this work have been discussed elsewhere (1). Reactions of methane on these molecular sieve materials and on several other metal oxides known to activate methane (e.g.,  $\text{Sm}_2\text{O}_3$ ) were carried out in a quartz tube reactor having an 8 mm inside diameter. The catalyst sample ( $\sim 1$  gram) was supported on a quartz fritted disk fused into the midsection of the quartz tube. The tube was mounted in an electrically heated furnace (with the sample in the middle of the heated zone) and attached to the gas handling system. The gases used in the experiments [99.999% He, 10%  $\text{CH}_4$  in Ar ( $\text{C}_2+$  hydrocarbons/ $\text{CH}_4 \approx 0.002$ ), and "zero" air, all supplied by Matheson Gas Products] were introduced at the bottom of the

reaction tube. A quartz-sheathed thermocouple was positioned inside the reaction tube just above the bed of catalyst material. Electrochemical activation was accomplished by inserting two coiled sections of platinum wire that were flattened to conform to the side wall of the reaction tube and then mounted in the tube so that they faced each other with a spacing of ~3 mm.

In a typical experiment with a molecular sieve material, the sieve sample was calcined in "zero" air at 550°C in the reaction tube to burn off any remaining template ions (for a fresh sample) or carbonaceous residues (for a used sample). This calcining restored the cobalt-containing molecular sieves to the Co(III) form as described previously (1). After calcining, the reaction tube was brought to the desired temperature and purged of residual oxygen with flowing helium, then ~10 cc (STP) of the 10% CH<sub>4</sub> in Ar mixture was introduced at a rate of ~0.5 cc/min. The reaction products, unreacted CH<sub>4</sub>, and Ar coming out the top of the reaction tube were collected in a liquid nitrogen cooled loop. The loop was then isolated from the reaction tube and warmed up to room temperature; after which a gas sample was withdrawn through a septum port on the side of the loop (using a gas syringe) and injected into a gas chromatograph (GC) equipped with a flame ionization detector (FID). In some experiments injections were also made into a GC equipped with a thermal conductivity detector (TCD) to determine the amounts of H<sub>2</sub>O, CO, and CO<sub>2</sub> that were produced relative to the amount of CH<sub>4</sub> reacted.

Electrochemical activation studies were performed using a constant voltage power supply. Potentials in the range from 3 to 10 V dc were applied across the two platinum wire electrodes (described above). Gas handling procedures employed in the presence of an applied potential were the same as those used on air calcined molecular sieve samples, except that the sieve sample was fully reduced (deactivated) with CH<sub>4</sub> between the calcining and helium purging steps. The voltage was applied during purging and maintained throughout the CH<sub>4</sub> introduction step.

## RESULTS

Methane activation experiments were performed on the following aluminophosphate molecular sieve materials: CoAPS0-34 (P:Co:Si = 12:1:1.8), CoAPO-5 (P:Co = 24:1), MAPO-5 (P:Mg = 12:1), and SAPO-34 (P:Si = 6.7:1). The onset temperature for activation of CH<sub>4</sub> by the cobalt-containing AlPO<sub>4</sub> (i.e., where a few percent of C<sub>2+</sub> products are observed relative to the CH<sub>4</sub>) occurs in the 350 to 400°C range. At 500°C the reaction proceeds more rapidly, and single pass conversions of CH<sub>4</sub> to C<sub>2+</sub> hydrocarbons ranging from 15 to 30% have been observed. In single pass experiments without electrochemical stimulation, ~1 cc (STP) of methane deactivates almost all of the active sites in ~1 gram of the CoAPS0-34 or CoAPO-5, and recalcination with O<sub>2</sub> is required to reactivate the sieve material. Many air calcinings have been run on some samples of CoAPS0-34 without evidence of significant permanent loss of activity, but in most other cases we have observed steady decreases in activity with extended use. In the presence of applied dc potentials in the 3 to 10 V range, it is possible to activate the reduced form of the cobalt-containing molecular sieves [(HCo(II)APS0-34 and HCo(II)APO-5)] and achieve significant (> 15%) methane conversion to C<sub>2+</sub> hydrocarbons in a single pass at 500°C. However, even electrochemically activated samples tend to exhibit reduced activity with extended use.

Identical experiments were performed on the silicon-substituted AlPO<sub>4</sub>-34 (SAPO-34) and magnesium-substituted AlPO<sub>4</sub>-5 (MAPO-5), wherein air calcination and electrochemical stimulation were employed in the same manner as was used with the CoAPS0-34 and CoAPO-5. None of these experiments gave any evidence of methane activation to C<sub>2+</sub> hydrocarbons. A test of air-calcined Sm<sub>2</sub>O<sub>3</sub>, a known methane

activation catalyst at  $>700^{\circ}\text{C}$  (4), failed to produce any  $\text{C}_{2+}$  products in our apparatus for temperatures up to  $580^{\circ}\text{C}$ , using methane only as a reactant (no oxygen co-feed).


A summary of typical results from the experiments described above is given in Table I. Reproductions of FID gas chromatograms for the products of methane activation over an air calcined sample of CoAPS0-34, an electrochemically stimulated sample of CoAPS0-34, and an electrochemically stimulated sample of CoAPO-5 are shown in Figs. 1, 2a, and 2b, respectively. TCD gas chromatograms run on products from experiments where high yields of  $\text{C}_{2+}$  hydrocarbon were obtained typically showed relatively low levels of  $\text{CO}_2$  (a few percent at most) and hardly any  $\text{CO}$ . If care was not taken to remove oxygen (as  $\text{O}_2$ ) from the reaction environment prior to introduction of the methane, higher levels of  $\text{CO}_2$  and lower levels of  $\text{C}_{2+}$  hydrocarbons were normally observed, i.e., the yields of  $\text{C}_{2+}$  hydrocarbons and  $\text{CO}_x$  have tended to be inversely related to one another in the types of experiments described above.

Finally, we wish to note that electrochemical stimulation experiments done on samples of Co(II)-exchanged SAPO-34 (P:Co  $\leq 12$ ) and Co(II)-exchanged Y zeolite (Si:Co  $\sim 5$ ) at  $500^{\circ}\text{C}$  (using the same conditions as for the CoAPS0-34 and CoAPO-5 experiments) produced smaller (but nonetheless measurable) yields of the same products observed for CoAPS0-34 (see Table I). In the case of single pass experiments with Co(II)-exchanged Y zeolite, evidence of a few percent conversion of methane to  $\text{C}_{2+}$  hydrocarbons at  $500^{\circ}\text{C}$  was also seen for a sieve sample that was air calcined at  $550^{\circ}\text{C}$  prior to methane exposure.

## DISCUSSION

The results presented in the preceding section give clear evidence that cobalt-substituted aluminophosphate molecular sieves have the capability to catalyze the coupling of methane to  $\text{C}_{2+}$  hydrocarbons at temperatures  $< 500^{\circ}\text{C}$ . The single pass yields which have exceeded 30% at  $500^{\circ}\text{C}$ , the high selectivity to  $\text{C}_{2+}$  hydrocarbons, the encouraging observation that molecular oxygen is not essential to the activation process, and the absence of large quantities of  $\text{CO}_x$  in the product stream represent a significant advance in the state-of-the-art for methane coupling using inorganic catalyst materials. The further finding that the cobalt-substituted molecular sieve can be maintained in the active state by an electric field allows for the development of continuous methane homologation processes using, e.g., packed or fluidized electrochemical bed reactors.

Data from comparative experiments -- CoAPS0-34 vs SAPO-34 and CoAPO-5 vs MAPO-5 -- show that cobalt is essential to the activation process. Prior work (1) indicates that the active state of the cobalt is tetrahedrally-coordinated Co(III) bound in framework metal atom positions of the molecular sieve. The overall reaction mechanism is believed to include the following steps:



The formation of  $\text{C}_3$  hydrocarbons could occur from reaction of methyl radicals ( $\text{CH}_3\bullet$ ) with ethylene or from Bronsted acid catalyzed reactions involving

ethylene. All of the above reactions are believed to take place within the molecular sieve framework which selectively constrains the size and shape of the transition state species and the products.

Although we assume that the framework-bound cobalt is the active agent in this catalysis, there was evidence that air calcined and electrochemically stimulated beds of Co(II)-exchanged SAPO-34 and Co(II)-exchanged Y zeolite also produced detectable quantities of  $C_{2+}$  hydrocarbons when exposed to methane at 500°C. This apparent catalytic activity of Co(II)-exchanged molecular sieves, which was actually predicted recently in the modeling work of Aparicio and Dumesic (5), is believed to occur by a mechanism that is separate from, but possibly related to, the one given above for framework-bound Co(II)/Co(III) in AlPO<sub>4</sub> molecular sieve structures.

The effectiveness of electrochemical stimulation as a redox activator was not unexpected in this work. There is increasing evidence (6) that molecular sieve materials are good ionic conductors at elevated temperature and have great potential for use in gas phase electrocatalysis applications. Also, Creasy and Shaw (7) recently demonstrated the electrocatalytic activity of CoAPS0-34 micro-electrodes in the presence of methane using cyclic voltammetry.

There are a number of aspects of the research findings described above that call for further, more detailed study. Other transition metals, such as manganese and iron, can be substituted into the framework of AlPO<sub>4</sub> molecular sieves (2,3) and these might also exhibit methane coupling activity. The fact that a variety of pore sizes and framework architectures are possible with AlPO<sub>4</sub> molecular sieves (2,3) should be exploited to determine the relationship between sieving properties and activity/selectivity. The optimum amount of transition metal substitution, the role (beneficial or otherwise) of non-redox type acid site creators (e.g., Si, Mg, Zn) in the framework, and the optimum balance between redox and non-redox framework metal atoms requires exploration. Factors such as framework demetalization, over-dehydrogenation (leading to soot formation), the need for oxygen potential control (to avoid destabilization of the framework structure), and the role of impurities (e.g., H<sub>2</sub>O) in the activation and ionic conduction processes all need to be elucidated. Foremost among the concerns stemming from our research to date are the causes of the gradual loss of catalytic activity observed for the CoAPS0-34 and CoAPO-5 sieve materials, and the implicit need for a methodology to identify/produce more stable, resilient transition metal-substituted AlPO<sub>4</sub> structures.

#### ACKNOWLEDGEMENT

This work was supported by the U. S. Department of Energy, Office of Basic Energy Sciences, Division of Advanced Projects, under contract W-31-109-ENG-38.

#### REFERENCES

- (1) L. E. Iton, I. Choi, J. A. Desjardins, and V. A. Maroni, *Zeolites* 9, 535 (1989).
- (2) R. J. Pellet, P. K. Coughlin, E. S. Shamshoum, and J. A. Rabo, in Perspectives in Molecular Sieve Science, W. H. Flank and T. E. Whyte, Jr., Eds., American Chemical Society Symposium Series No. 368 (1988) p.85.
- (3) E. M. Flanigen, R. L. Patton, and S. T. Wilson, in Studies in Surface Science and Catalysis, Vol. 37, P. J. Gobet, W. J. Mortier, E. F. Vansant, and G. Schulz-Ekloff, Eds. (Elsevier Publishers, Amsterdam, 1988) p. 189.

- (4) K. Otsuka, K. Jinno, and A. Morikawa, J. Catal. 100, 353 (1986).
- (5) L. M. Aparicio and J.-A. Dumesic, J. Molec. Catal. 49, 205 (1989).
- (6) K. E. Creasy, Electrochemical Society Extended Abstracts Vol. 89-2, 972 (1989).
- (7) K. E. Creasy and B. R. Shaw, Department of Chemistry, University of Connecticut (work in progress).

Table I. Examples of Product Distributions from Typical<sup>a</sup>  
Methane Activation Experiments at 500°C

Molecular Sieve	Activation Method	Number of Passes	Product Distribution (Mole %)				
			CH <sub>4</sub>	C <sub>2</sub> H <sub>6</sub>	C <sub>2</sub> H <sub>4</sub>	C <sub>3</sub> H <sub>5</sub>	C <sub>3</sub> H <sub>6</sub>
CoAPSO-34	Air calcine	Single	65	15	12	1	7
	Electrochem.	Single	91	5	1	2	1
	Electrochem.	Multiple <sup>b</sup>	85	4	3	4	4
SAP0-34	Air Calcine	Single	99	nil	nil	nil	nil
	Electrochem.	Single	99	nil	nil	nil	nil
CoAPO-5	Air Calcine	Single	54	1	5	1	39
	Air Calcine	Multiple <sup>b</sup>	21	1	10	1	67
	Electrochem.	Single	58	2	4	4	32
MAPO-5	Air Calcine	Single	99	nil	nil	nil	nil
	Electrochem.	Single	99	nil	nil	nil	nil
Co(II)-EX <sup>c</sup> SAP0-34	Electrochem.	Single	98 <sup>d</sup>	0.5	0.4	0.3	0.3
Co(II)-EX <sup>c</sup> Y Zeolite	Electrochem.	Single	98	1	1	1	1
	Electrochem.	Multiple <sup>b</sup>	94	1	1	1	1

- (a) The data presented in this table were derived from averages of several of the better results obtained with each material.
- (b) In multiple pass experiments the unreacted methane and products from the first pass are recycled through the bed four or five additional times.
- (c) Indicates Co(II) exchanged molecular sieve material.
- (d) A fifth undetermined low molecular weight product was observed with Co(II)-exchanged SAP0-34. It was not acetylene, cyclopropane, or CO. ▼

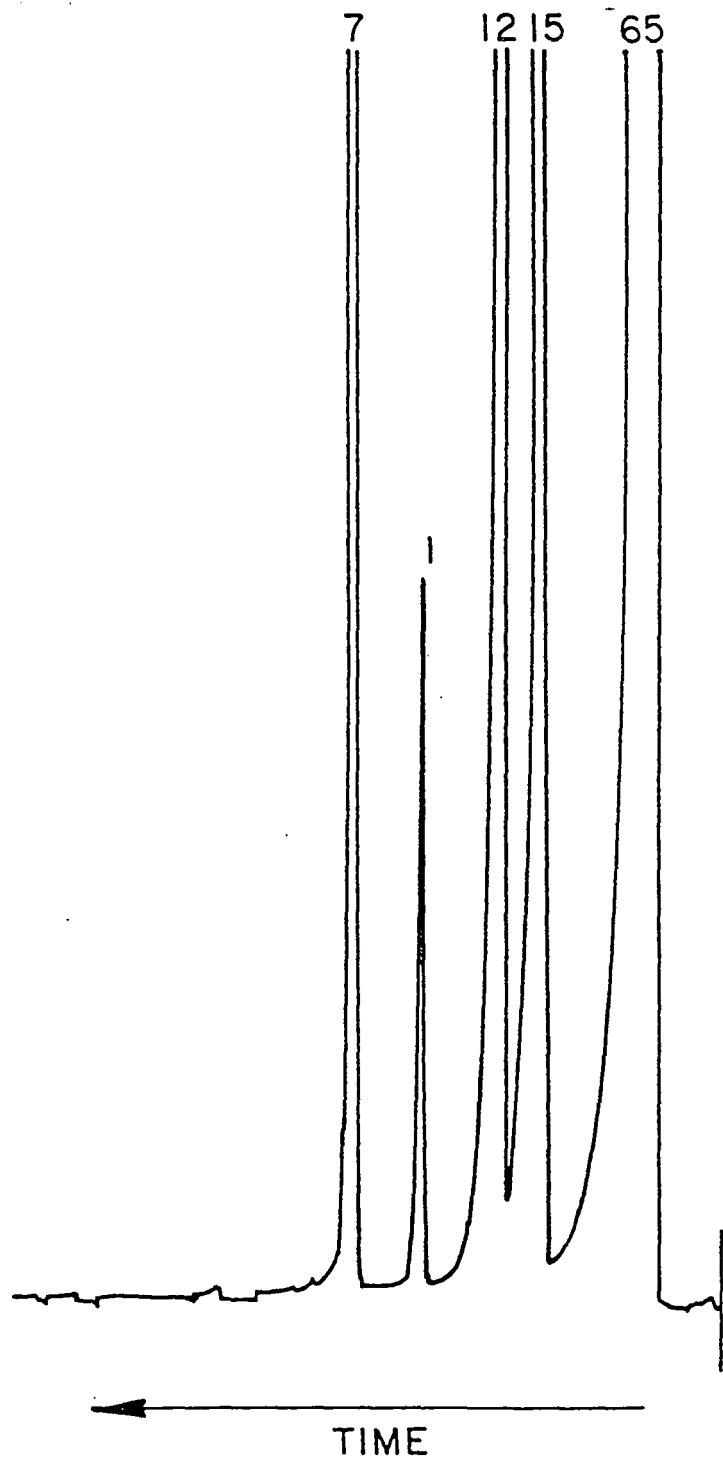


Figure 1. Gas chromatogram of the products from a typical single pass reaction of methane over air calcined CoAPS0-34 at 500°C. The numbers above each peak give the approximate mole percentages of each gas; i.e., 65% = CH<sub>4</sub>, 15% = C<sub>2</sub>H<sub>6</sub>, 12% = C<sub>2</sub>H<sub>4</sub>, 1% = C<sub>3</sub>H<sub>8</sub>, and 7% = C<sub>3</sub>H<sub>6</sub>.

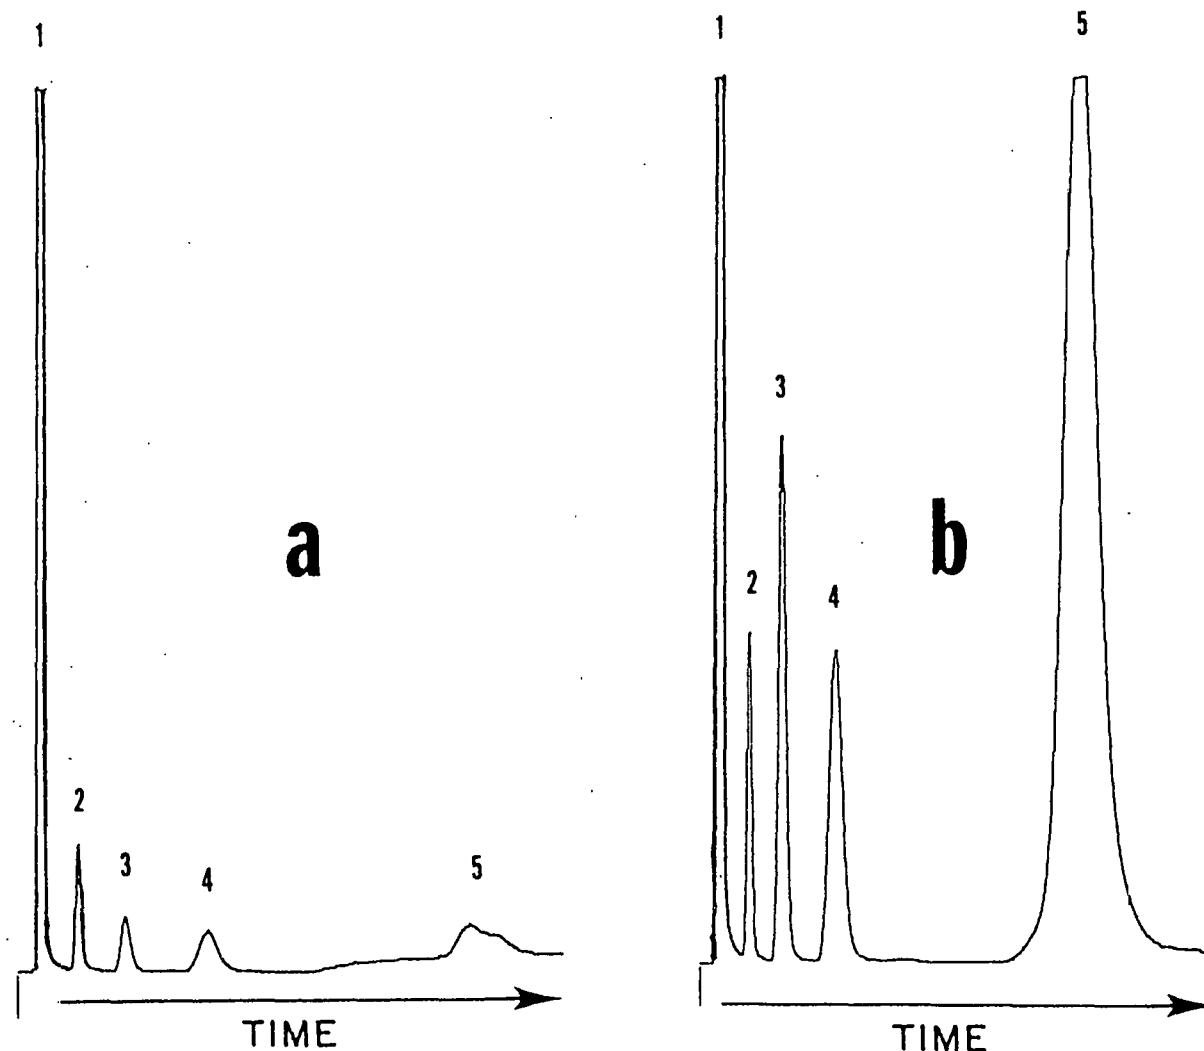


Figure 2. Results of single pass reactions of methane over electrochemically stimulated (10 V) CoAPS0-34 (insert a) and CoAPO-5 (insert b) at 500°C. Peaks 1 through 5 are  $\text{CH}_4$ ,  $\text{C}_2\text{H}_6$ ,  $\text{C}_2\text{H}_4$ ,  $\text{C}_3\text{H}_8$ , and  $\text{C}_3\text{H}_6$ , respectively.