

LM-01K083  
September 12, 2001

---

---

# **Factors Affecting the Hydrogen Environment Assisted Cracking Resistance of an Al-Zn-Mg-(Cu) Alloy**

George A. Young, John R. Scully

---

---

## **NOTICE**

This report was prepared as an account of work sponsored by the United States Government. Neither the United States, nor the United States Department of Energy, nor any of their employees, nor any of their contractors, subcontractors, or their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness or usefulness of any information, apparatus, product or process disclosed, or represents that its use would not infringe privately owned rights.

---

## Factors Affecting the Hydrogen Environment Assisted Cracking Resistance of an Al-Zn-Mg-(Cu) Alloy

George A. Young<sup>†</sup> and John R. Scully  
Center for Electrochemical Science and Engineering  
Department of Materials Science  
University of Virginia  
Charlottesville, VA 22903-2442

<sup>†</sup>Present Address: Lockheed Martin Corporation  
P.O. Box 1072, Schenectady, NY 12301-1072

It is well established that Al-Zn-Mg-(Cu) aluminum alloys are susceptible to hydrogen environment assisted cracking (HEAC) when exposed to aqueous environments. In Al-Zn-Mg-Cu alloys, overaged tempers are commonly used to increase HEAC resistance at the expense of strength. Overaging has little benefit in low copper alloys. However, the mechanism or mechanisms by which overaging imparts HEAC resistance is poorly understood. The present research investigated hydrogen uptake, diffusion, and crack growth rate in 90% relative humidity (RH) air for both a commercial copper bearing Al-Zn-Mg-Cu alloy (AA 7050) and a low copper variant of this alloy in order to better understand the factors which affect HEAC resistance. Experimental methods used to evaluate hydrogen concentrations local to a surface and near a crack tip include nuclear reaction analysis (NRA), focused ion beam, secondary ion mass spectroscopy (FIB/SIMS) and thermal desorption spectroscopy (TDS).

When freshly bared coupons of AA 7050 are exposed to 90°C, 90% RH air, hydrogen ingress follows inverse-logarithmic-type kinetics and is equivalent for underaged (HEAC susceptible) and overaged (HEAC resistant) tempers. However, when the native oxide is allowed to form (24 hrs in 25°C, 40% RH lab air) prior to exposure to 90°C, 90% RH air, underaged alloy shows significantly greater hydrogen ingress than the overaged alloy. Humid air is a very aggressive environment producing local (~1μm) hydrogen concentrations in excess of 10,000 wt. ppm at 90°C. In the copper bearing alloy, overaging also effects the apparent diffusivity of hydrogen. As AA 7050 is aged from underaged → peak aged → overaged, the activation energy for hydrogen diffusion increases and the apparent diffusivity for hydrogen decreases. In the low copper alloy, overaging has little effect on hydrogen diffusion. Comparison of the apparent activation energies for hydrogen diffusion and for  $K$  independent (stage II) crack growth rate in 90% RH air between 25 and 90°C indicates that hydrogen transport kinetics are responsible for the decreased crack growth rate of overaged AA 7050 relative to the peak aged temper.

## Experimental Procedure

### Materials and Heat Treatments


The AA 7050 and the low copper variant of AA 7050 were supplied by the Aluminum Company of America (Alcoa) in final heat-treated form. The chemical composition of each material is given in Table 1. The AA 7050 material was heat-treated from a commercially produced 6" thick plate. The low copper material was from a 2" thick plate produced at the Alcoa Technical Center. Samples were taken from the T/4 plane of the 6" AA 7050 plate and the T/2 plane of the 2" thick low copper material. The heat treatments used are summarized in Table 2. The precipitation sequence in AA 7050 is *Supersaturated Solid Solution*  $\rightarrow$  G.P. Zones  $\rightarrow$   $\eta'$   $\rightarrow$   $\eta$  where  $\eta'$  is a metastable precipitate and  $\eta$  is the equilibrium phase ( $MgZn_2$ ) [1-4].

**Table 1.** Chemical composition of the alloys used in this study (weight percent).

Alloy	Zn	Mg	Cu	Zr	Si	Fe	Al	Mg/Zn ratio
AA 7050 (spec.)	5.7-6.7	1.9-2.6	2.0-2.6	.08-.15	0.12	0.15	Bal.	0.28-0.45
AA 7050 (meas.)	6.09	2.14	2.19	0.11	0.05	0.09	Bal.	0.35
Low Cu 7050 (meas.)	6.87	2.65	0.06	0.10	0.04	0.10	Bal.	0.38

**Table 2.** Temper designations and heat treatments.

Temper	Heat Treatment
Underaged (UA)	467°C / 2 hrs + Water Quench + 2% Stretch + 118°C / 4 hrs
Peak Aged (PA)	7050-Underaged + 118°C / 20 hrs + 154°C / 12 hrs
Overaged (OA)	7050-Underaged + 163°C / 27 hrs

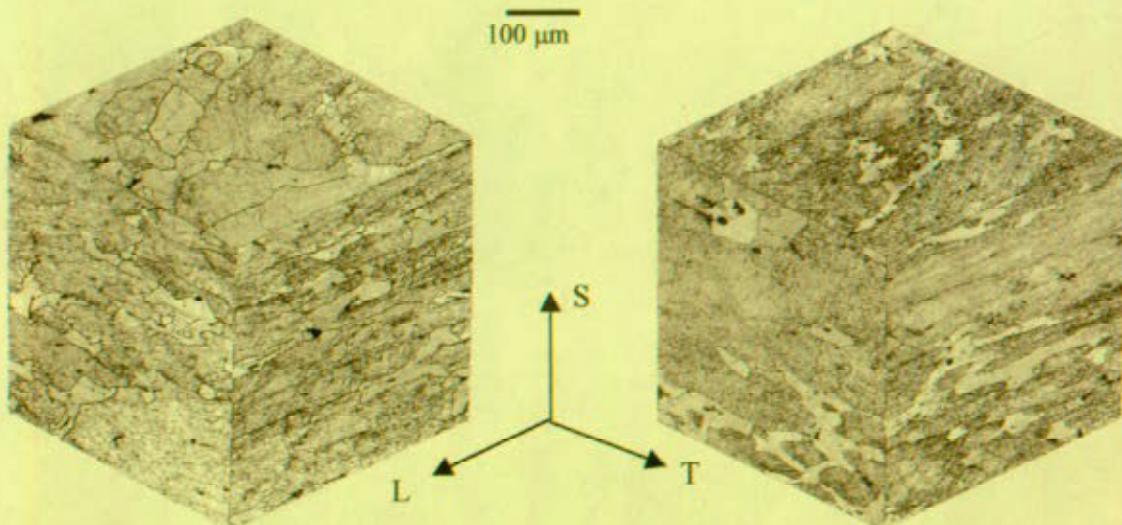

**Figure 1.** Orthogonal metallographic views of the AA 7050 (left) and low copper material (right) showing the pancake shaped grain structure. Keller's + Graff and Sargent's etchants.

The microstructure of AA 7050 and the low copper variant are shown in Figure 1. The microstructure contained a combination of recrystallized and unrecrystallized grains. Typical dimensions of the pancake shaped, unrecrystallized grains are approximately 1000  $\mu\text{m}$  (L) x 250  $\mu\text{m}$  (T) x 75  $\mu\text{m}$  (S). Note the similar grain structure and degree of recrystallization for the AA 7050 and the low copper material. Note that *the peak aged thermal treatment actually produced a slightly overaged microstructure in the low copper alloy*. However, to facilitate the discussion, the term “peak aged” will be used to describe both the AA 7050 and the low copper alloy that was processed at the 154°C, 12 hour thermal treatment.

### **Environmental Exposure to Humid Air**

Hydrogen charging of the samples used in this study was performed via exposure to 90% RH at temperatures between 25 and 90°C. Temperature and humidity were electronically controlled in an electronically controlled, environmentally sealed cabinet. The source of water vapor was distilled deionized water, while the source of air was laboratory air with low levels of NO<sub>x</sub> and SO<sub>x</sub>. Details of the crack growth rate testing have been presented previously [5, 6].

### **Hydrogen Uptake**

#### *Nuclear Reaction Analysis (NRA)*

Nuclear reaction analysis for hydrogen concentration measurements was performed via the  $^{15}\text{N}(\text{p}, \alpha\gamma)^{12}\text{C}$  resonance reaction. The NRA tests were performed in a vacuum chamber with a total pressure of  $<1.3 \times 10^{-3}$  Pa, with beam acceleration in excess of 6.385 MeV. The spot size of the beam was approximately 3 mm in diameter. Depth profiling between 0-1  $\mu\text{m}$  was achieved by varying the energy of the  $^{15}\text{N}$  beam at a constant fluence. NRA was performed on both unstressed coupons (~2.5 cm x 2.5 cm x 1 cm) and on samples sectioned from the fracture surfaces of crack growth rate tests.

#### *Secondary Ion Mass Spectroscopy (SIMS)*


The SIMS depth profiles used a liquid gallium sputtering source focused to 10 x 10  $\mu\text{m}$  at a current of 1000 pA. Depth profiling was performed in each of these regions from approximately 0-1 micron into the surface. Sputtering depth was determined via known sputtering rates for aluminum. The hydrogen signal (mass/charge=1) was monitored with a quadrupole mass spectrometer. Three distinct areas of fracture surfaces from crack growth rate tests were investigated, the precrack, the near crack tip HEAC region (~5 mm from the crack tip on a single grain facet) and the fast fracture region. These areas were chosen to correspond to the position of NRA depth profiles as shown schematically in Figure 2. Note that for both NRA and SIMS, hydrogen charged samples were stored in liquid nitrogen for long term storage (> 3 days) or dry ice for short term storage.

### **Hydrogen Diffusion and Trapping**

#### *Material and Hydrogen Charging*

The specimens used for diffusion and trapping studies were 0.16 cm diameter x 2.5 cm long rods machined from the T/4 position of the AA 7050 plate and the T/2 position of the low copper alloy. Hydrogen was charged into the samples via exposure to hot moist

air 40°C, 90% RH for approximately 7 days. The exposure time ensured a uniform hydrogen concentration through the samples ( $C_{Center} \geq 90\% C_{Surface}$ ) assuming that the effective diffusivity through the alloy was  $\geq 1 \times 10^{-12} \text{ m}^2/\text{s}$  at 40°C. After hydrogen charging and prior to testing, the sample surfaces were lightly ground with 600 grit abrasive paper, rinsed in acetone, and ultrasonically cleaned in high purity methanol. The time between removal from the charging environment and test initiation was less than ten minutes for isothermal tests and less than 20 minutes for the thermally ramped tests.

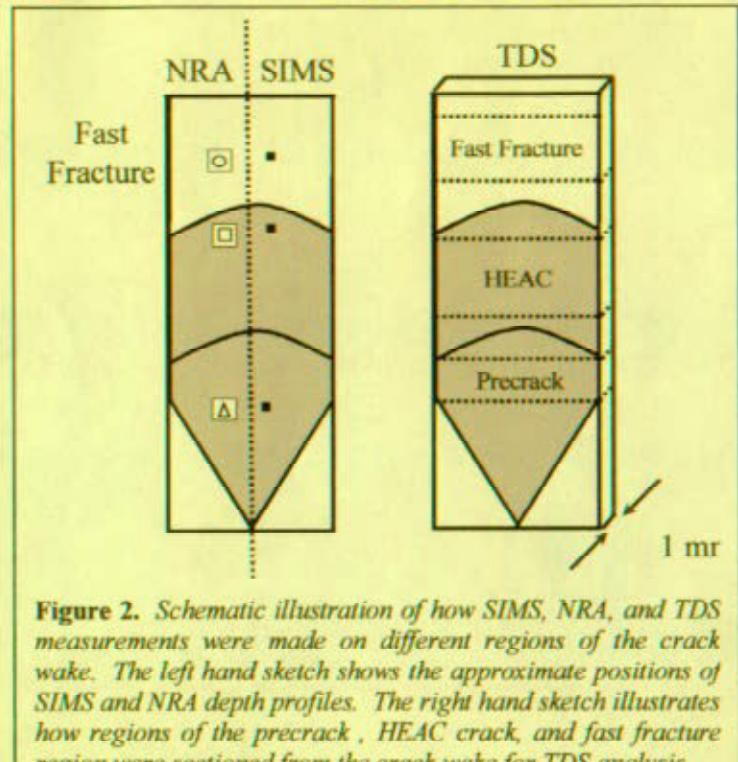

**Figure 2.** Schematic illustration of how SIMS, NRA, and TDS measurements were made on different regions of the crack wake. The left hand sketch shows the approximate positions of SIMS and NRA depth profiles. The right hand sketch illustrates how regions of the precrack, HEAC crack, and fast fracture region were sectioned from the crack wake for TDS analysis.

### Thermal Desorption Spectroscopy

The thermal desorption spectroscopy (TDS) system used in these experiments has been described previously [6-9]. The TDS was used to determine the diffusivity of hydrogen via Equation 1 where  $D$  is the diffusivity,  $m$  is the initial slope of the hydrogen pressure decay transient,  $l$  is the length of the sample,  $\beta_1$  is the root of the Bessel function  $J_0(\beta_n) = 0$ , and  $d$  is the diameter of the sample. Note that the slope,  $(\log dP/dt)$  is a flux so the units of  $m$  are  $1/\text{s}$  and  $l$  and  $d$  are lengths yielding  $D$  in  $\text{length}^2/\text{s}$  (i.e.,  $\text{m}^2/\text{s}$ ). Details of the procedure to calculate the diffusivity are given elsewhere [7, 10-12].

$$D = \frac{2.3 \text{ m}}{\left(\frac{\pi}{l}\right)^2 + \left(\frac{2\beta_1}{d}\right)^2} \quad (1)$$

Constant heating rate tests were performed in a similar manner to the isothermal tests with one notable difference. After lowering the specimen into the furnace, the sample was isolated from the low vacuum side of the TDS system and the total background pressure was allowed to stabilize to less than  $1.3 \times 10^{-6} \text{ Pa}$  (with a hydrogen partial pressure of  $< 1.3 \times 10^{-7} \text{ Pa}$ ) before the temperature ramp was initiated. In all cases, this background pressure was achieved in less than 5 minutes to help ensure minimal outgassing of the specimen prior to the desorption test.


## Results

### Hydrogen Uptake in Unstressed Coupons

The hydrogen concentration profiles in unstressed coupons of underaged and overaged AA 7050 that were exposed to 90°C, 90% RH air are shown in Figure 3. In Figure 3, the top graph is for coupons that had the native oxide on the exposed face while the bottom graph is for coupons which had the native oxide mechanically ground off with 600 grit, silicon carbide abrasive paper immediately prior to exposure to 90°C, 90% RH air. Note that the presence of the native oxide does not appear to hinder hydrogen ingress in the underaged alloy, but it does appear to prevent significant hydrogen uptake in the overaged alloy.

### Hydrogen Concentrations Near Stress Corrosion Cracks

Both NRA and SIMS concentration depth profiles for an overaged AA 7050 sample are shown in Figure 4. Three different regions of crack wake were examined with each technique; the precrack region (exposed to humid air for the longest time), the hydrogen environment assisted cracking (HEAC) region, and the fast fracture region which was only exposed to relatively dry (~20% RH) laboratory air. Note that the NRA and SIMS spectra show similar concentration vs. depth profiles for each region investigated.

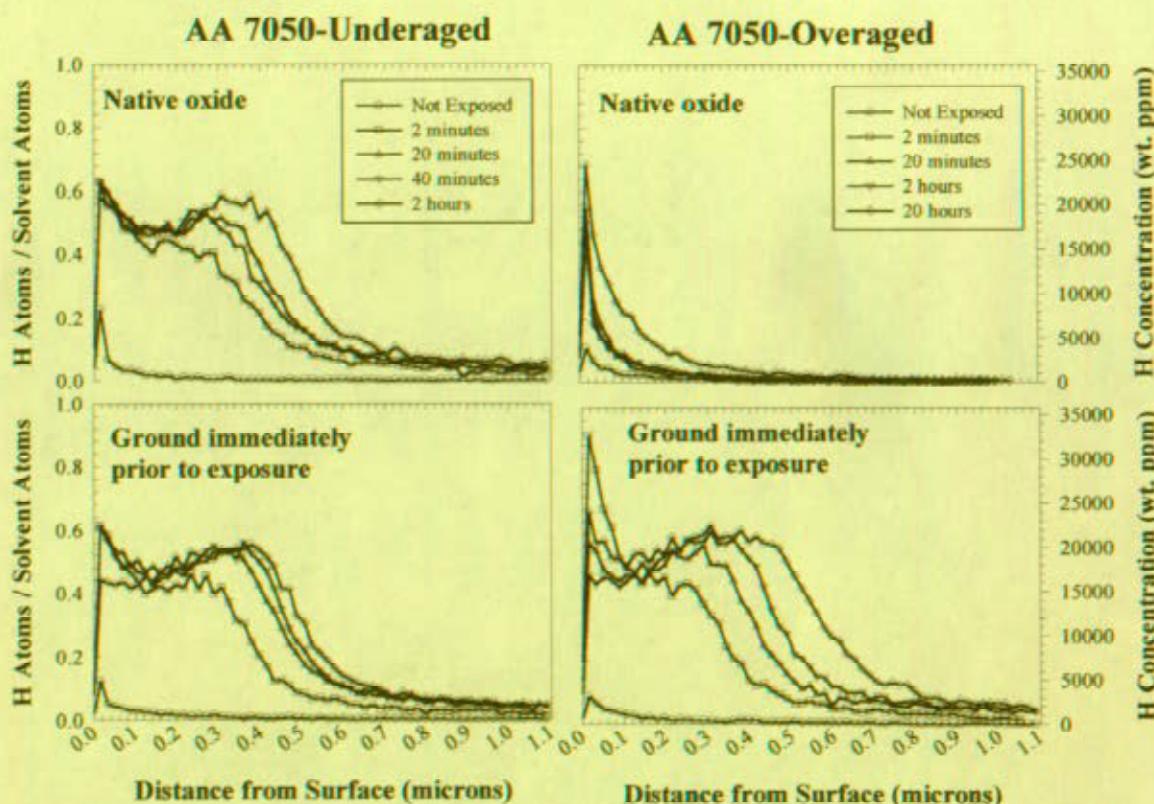

**Figure 3.** Comparison of the hydrogen concentration profiles from unstressed coupons of underaged and overaged AA 7050 with and without the native oxide. The samples were exposed to 90°C, 90% RH air.

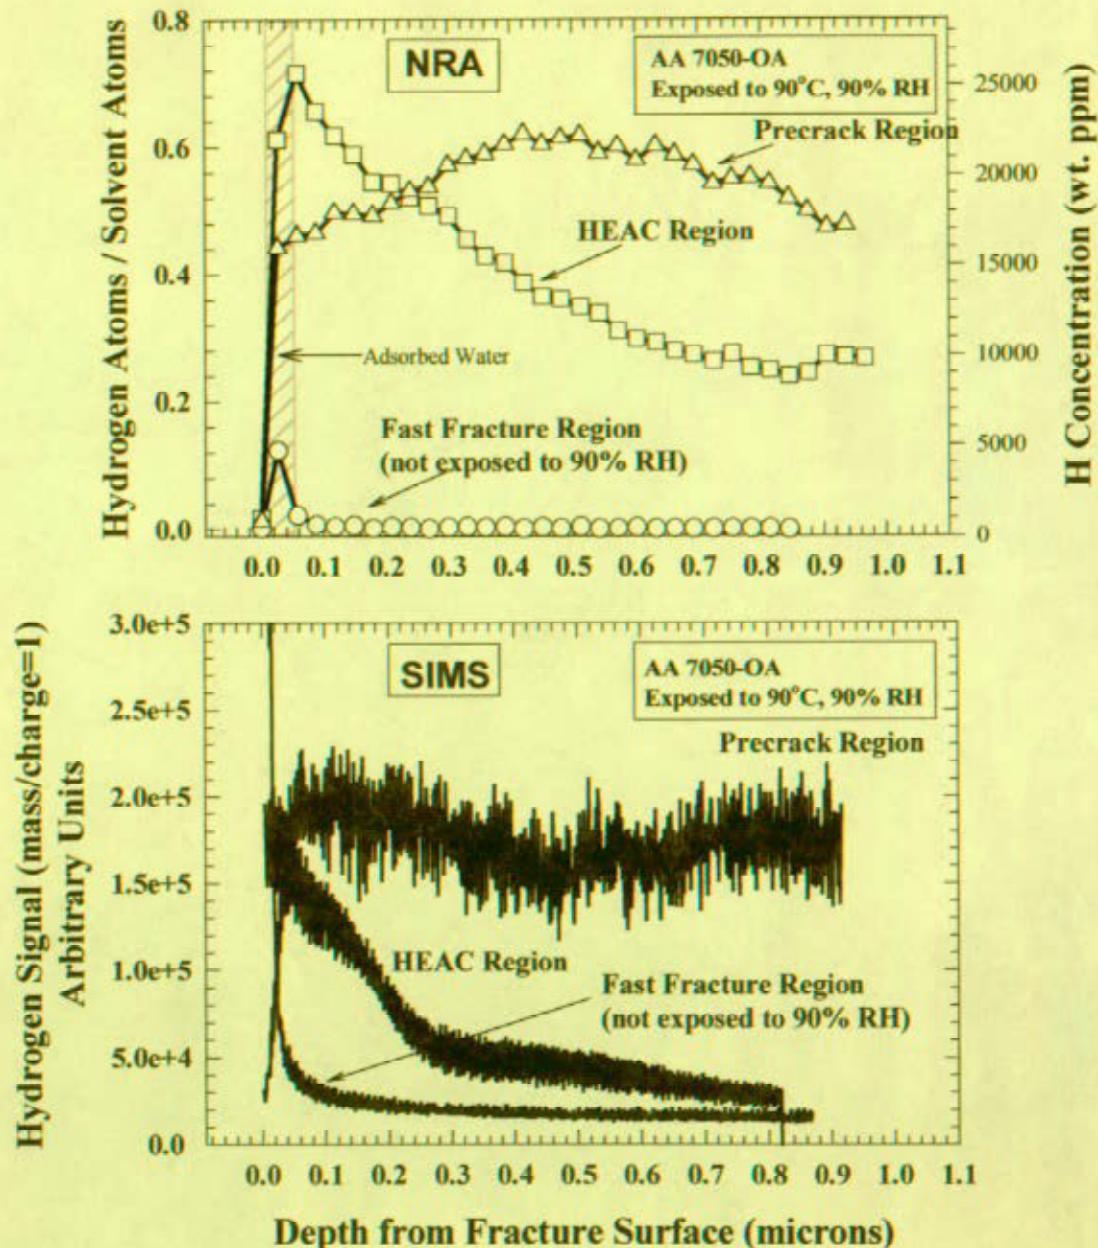


Figure 4. Comparison of NRA (top) and SIMS (bottom) spectra from crack wakes.

#### Hydrogen Diffusion Measurements

Results of the hydrogen diffusion measurements for AA 705 and low copper alloy are summarized in Table 3 and shown graphically in Figure 5. Note that previously published data for high purity aluminum are also shown for comparison [7]. Note the similarity in activation energy (given by the slope of the lines) for all tempers except the overaged AA 7050.

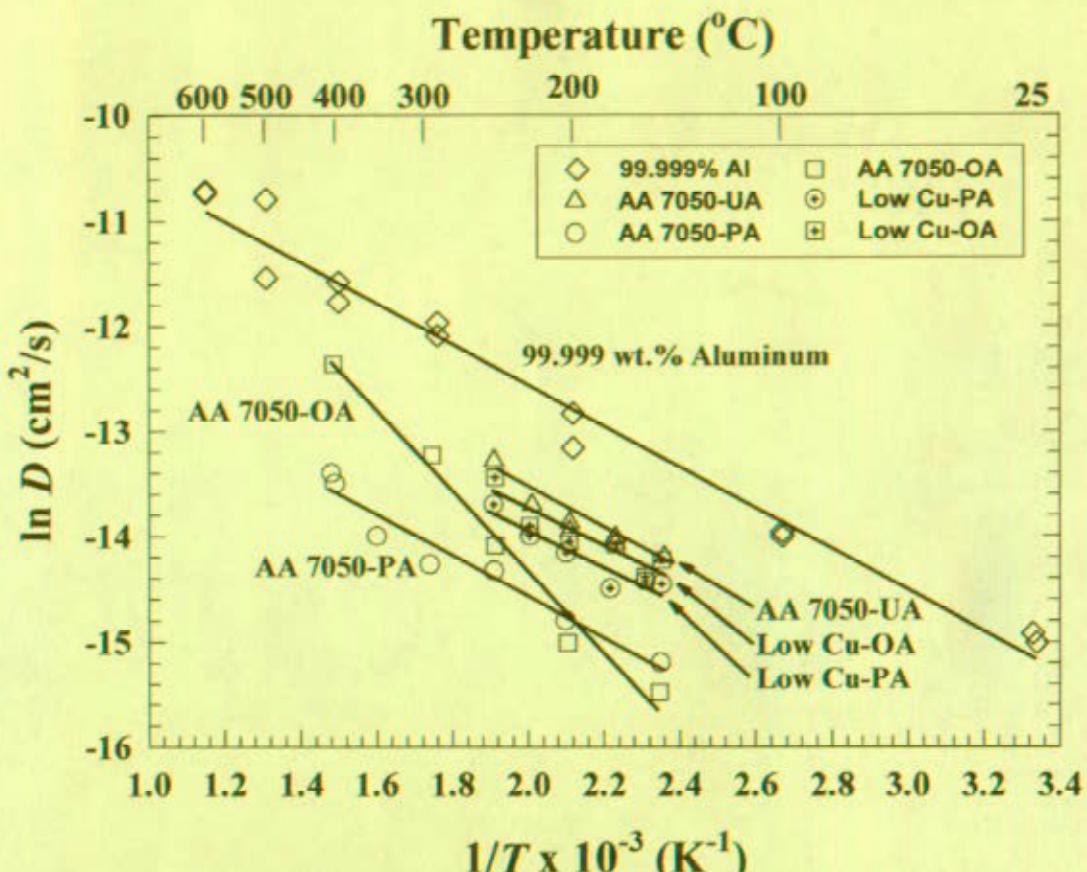



Figure 5. Summary of hydrogen diffusion data for AA 7050 and the low copper variant of the alloy.

Table 3. Hydrogen Diffusion Measurements from Isothermal Desorption Experiments.


Material	$D_0$ (m <sup>2</sup> /s)	95% Confidence (m <sup>2</sup> /s)	$Q_{Lattice} \pm 95\%$ (kJ/mol)	T Range Studied (°C)	$D_{Lattice}$ at 25°C (m <sup>2</sup> /s)
99.999 wt.% Al	$1.80 \times 10^{-8}$	$1.19-2.57 \times 10^{-8}$	$16.2 \pm 1.5$	25-600	$2.60 \times 10^{-11}$
AA 7050-UA	$5.49 \times 10^{-9}$	$0.15-2.0 \times 10^{-8}$	$15.8 \pm 5.0$	150-250	$9.33 \times 10^{-12}$
AA 7050-PA	$2.24 \times 10^{-9}$	$0.89-5.64 \times 10^{-9}$	$16.1 \pm 4.2$	150-400	$3.37 \times 10^{-12}$
AA7050-OA	$1.70 \times 10^{-7}$	$0.37-7.88 \times 10^{-7}$	$32.7 \pm 6.7$	150-400	$3.15 \times 10^{-13}$
Low Cu-PA	$2.65 \times 10^{-9}$	$1.39-5.05 \times 10^{-9}$	$14.2 \pm 2.5$	150-250	$8.59 \times 10^{-12}$
Low Cu-OA	$3.24 \times 10^{-9}$	$1.41-7.43 \times 10^{-9}$	$14.2 \pm 3.2$	150-250	$1.05 \times 10^{-11}$

#### Thermal Desorption Spectroscopy

Thermal desorption spectra from peak aged and overaged AA 7050 are compared in Figure 6. Additionally, hardness data from similarly heated (and subsequently fast quenched) samples are shown to illustrate the instability of the microstructure during the desorption experiments. In Figure 7, the relative hydrogen concentration from different regions of a crack growth rate test are compared. Note the elevated hydrogen concentrations in the precrack and the HEAC regions.

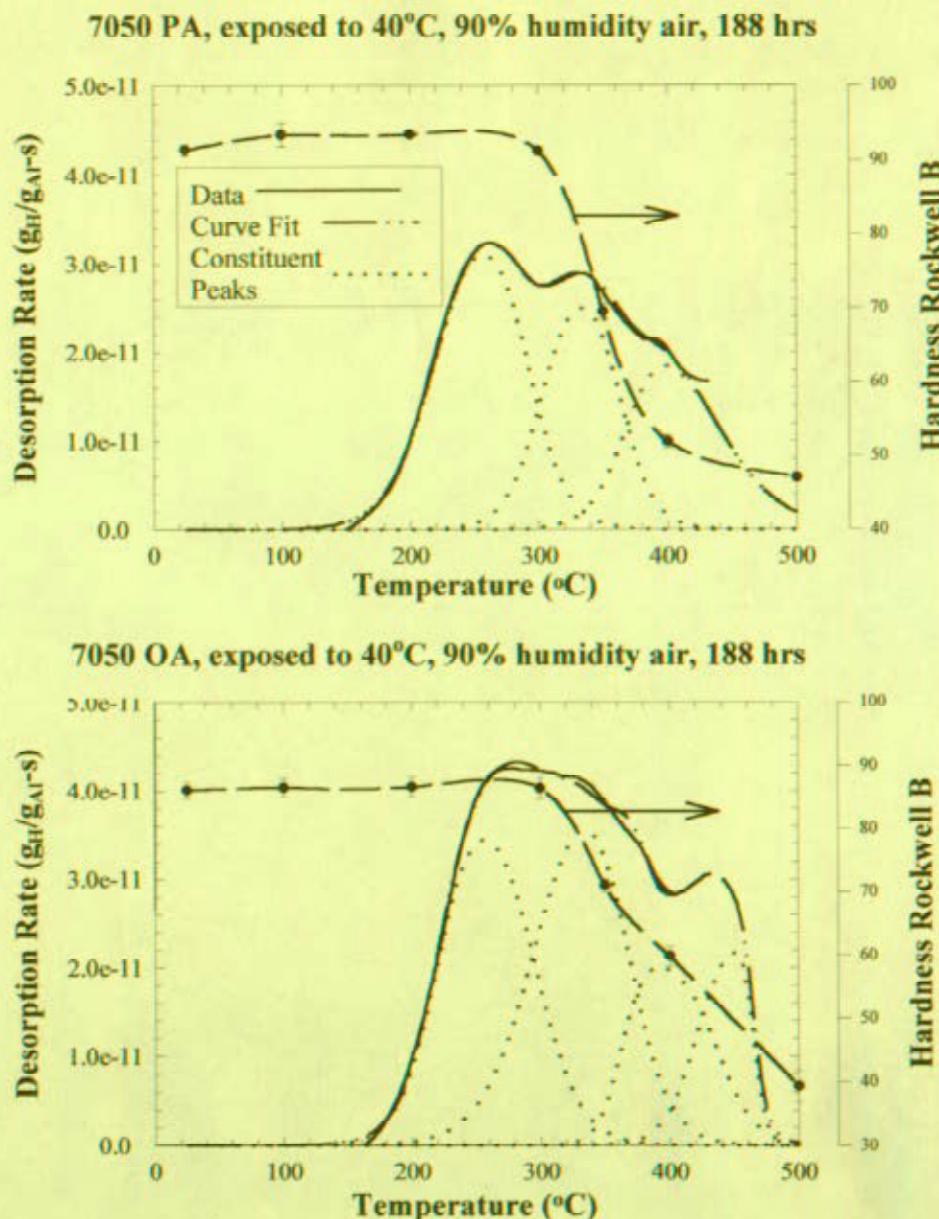

**Figure 6.** Thermal desorption spectra from peak aged (top) and overaged (bottom) AA 7050. The dashed lines show how the macroscopic hardness changes as the alloy is heated at a rate of 10°C/minute. These results illustrate the thermal instability of the microstructure during the TDS heating cycle.

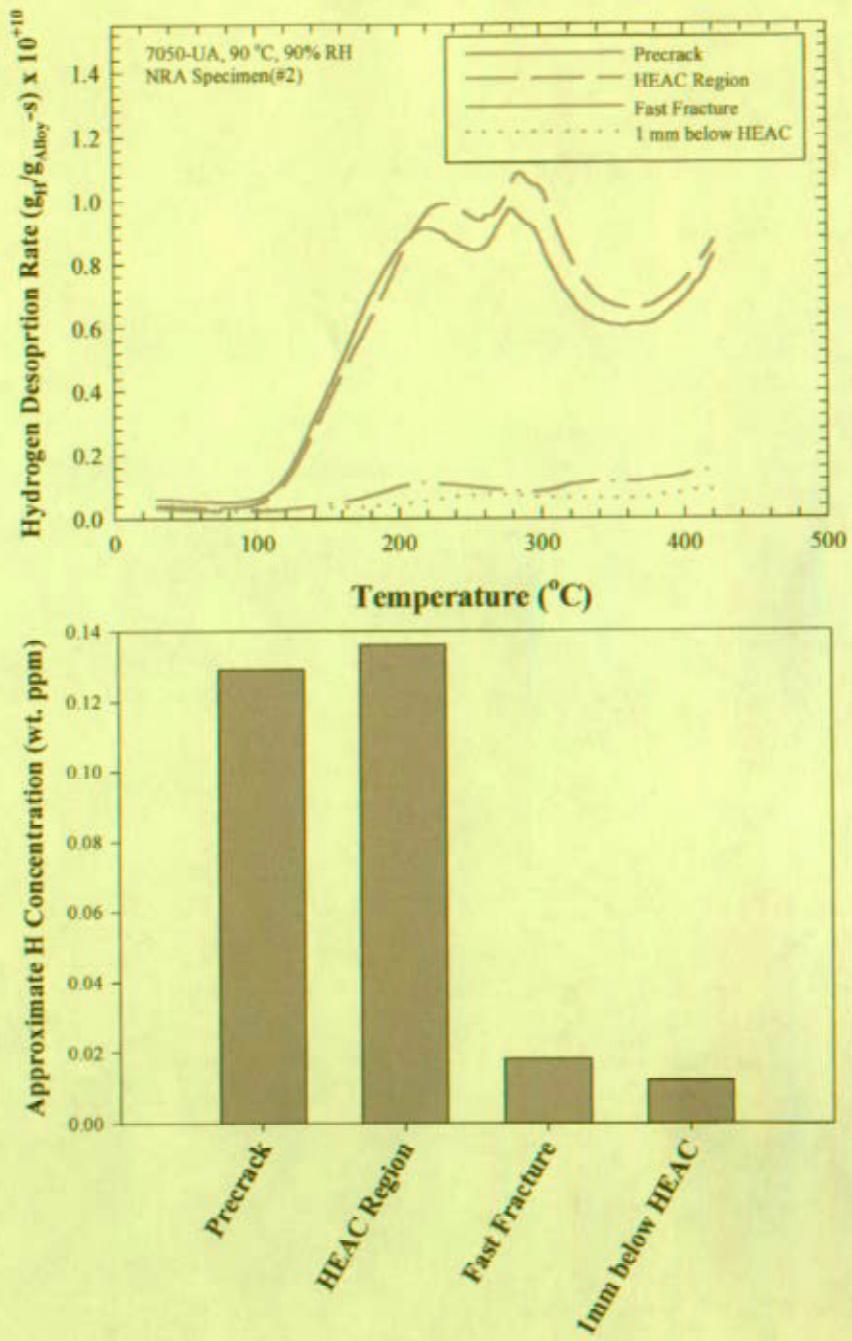

**Figure 7.** Thermal desorption spectra from crack wakes of AA 7050-UA. Note that the precrack and HEAC regions contain significantly higher hydrogen concentrations than the fast fracture region or a sample taken 1mm below the HEAC region.

## Discussion

### Unstressed Coupons Exposed to 90°C, 90% RH – Effect of the Native Oxide

As shown in Figure 3, hydrogen uptake occurs readily on the freshly abraded surfaces of both AA 7050-UA and AA 7050-OA. However, there appears to be a distinct difference in uptake when the native oxides of the underaged and overaged alloys are exposed to 90°C, 90% RH air. In the underaged condition, uptake occurred readily and penetration distances were very similar to the ground surface as shown in Figure 3. However, in AA 7050 OA, the native oxide delayed hydrogen uptake and the concentration profile after 20 hours exposure was less than the ground surface after 2 minutes exposure.

These results suggest that the nature of the passive film may change with temper. This idea has also been suggested by Puiggali *et al.* [13]. These researchers investigated the native oxide of AA 7010 (Al-6.12Zn-2.33Mg-1.60Cu) which is compositionally similar to AA 7050 (Al-6.09Zn-2.14Mg-2.19Cu). Puiggali *et al.* found that the surface film consisted of two sub-layers an inner  $\text{Al}_2\text{O}_3$  and outer  $\text{MgO}$  layer. Moreover, the chemical composition was related to the temper, *i.e.*, the Mg content of the surface layer decreased and the Al content increased as the alloy was heat treated from an underaged temper to the –T7451 overaged temper. These findings are consistent with the notion that  $\text{MgO}$  is not protective and water may react readily with Mg and Al to produce high fugacity hydrogen, while  $\text{Al}_2\text{O}_3$  offers some protection before it hydrates and water can react with aluminum metal [14].

The magnitude of the hydrogen concentration produced near the surface exposed to 90°C, 90% RH is also notable. The NRA technique measured peak concentrations ~20,000-25,000 wt. ppm (~60-70 atomic%), consistent with a high hydrogen fugacity generated by the oxidation of aluminum. The fugacity required to produce 25,000 wt. ppm via Sievert's law ( $<10^{25}$  atm) [6] is many orders of magnitude below the theoretical hydrogen fugacity of hydrogen produced when aluminum is oxidized to form  $\text{Al}_2\text{O}_3$  ( $\sim 10^{62}$  atm) [5].

### Kinetics of Hydrogen Uptake

Integration of the hydrogen concentration vs. distance plots shown in Figure 3 illustrate the kinetics of hydrogen ingress. These data are shown in Figure 8. Note that data for both the underaged and overaged tempers fall on the same curve and that hydrogen absorption follows logarithmic-type kinetics. The hydrogen ingress rate then (given by the derivative of this curve) follow inverse-logarithmic-type kinetics. The kinetics imply that hydrogen ingress is not diffusion controlled but rather

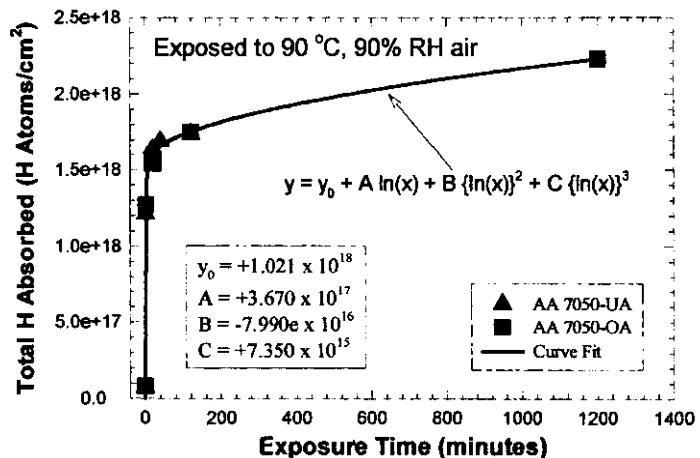


Figure 8. Hydrogen absorption kinetics from freshly bared AA 7050 exposed to 90°C, 90% RH air. Note that the underaged and overaged data fall on the same curve fit.

---

hydrogen production via oxidation likely limits the ingress rate.

### **Hydrogen Diffusion in Aluminum Alloys**

There are conflicting data for hydrogen diffusion in both aluminum [7] and in aluminum alloys. Available data for hydrogen diffusion in aluminum alloys are summarized in Table 4. Although hydrogen diffusion data in aluminum alloys is limited, the present work can likely be compared to data on AA 7075-T6 (i.e. peak aged) because of their similar composition and microstructure.

The present work predicts a room temperature hydrogen diffusivity in AA 7050 PA to be  $\sim 3 \times 10^{-12} \text{ m}^2/\text{sec}$ . The apparent diffusivity in AA 7050-PA is  $\sim 7X$  slower than that predicted for AA 7075-T6 by Braun [15] and  $\sim 17X$  faster than the diffusivity predicted by Gest and Troiano [16]. However, analysis of the experimental techniques of both Gest and Braun suggest that the Gest data may underpredict the diffusivity while the Braun data may overpredict it.

Gest and Troiano investigated hydrogen diffusion in AA 7075-T6 (i.e., peak aged) via galvanostatic permeation and reported a diffusivity of  $D=2 \times 10^{-13} \text{ m}^2/\text{s}$  at room temperature [16, 17]. However, Gest also showed that their permeation fluxes were independent of foil thickness, indicating that the results are not diffusion controlled and that surface reactions may bias their data toward lower apparent diffusivities [16, 17].

Braun *et al.* have also studied the diffusion of hydrogen in AA 7075-T6 via electrochemical permeation at 20°C and concluded that the diffusivity is approximately 100 times faster (i.e.,  $2.3\text{-}6.0 \times 10^{-11} \text{ m}^2/\text{s}$ ) than the data of Gest and Troiano [15]. However, Braun *et al.* also fail to show that their permeation experiments are volume diffusion controlled and they note that localized corrosion of the permeation foils (pitting) occurred, despite the use of Pd-Ag coatings and a corrosion inhibitor ( $\text{NaNO}_3$ ) in their electrolyte [15]. Either pitting or fast-path diffusion may have biased their diffusivities toward higher values of apparent diffusivity.

The diffusivity of hydrogen in other alloy systems is also controversial. Aluminum-lithium binary alloys have been studied by both Anyalebechi [12] and Nakashima *et al.* [18]. As shown in Table 4, the data of these researchers are in disagreement with large differences in the reported activation energies for hydrogen diffusion (18 versus 62.7 kJ/mol for similar alloys). Note that the data of Onuchukwu on AA 1060 are likely erroneous since the surface conditions at the charging side of their permeation foils were non-uniform and the currents measured on the exit side of their foils were not dominated by the oxidation of hydrogen [19].

**Table 4.** Summary of literature data for the apparent diffusivity of hydrogen in solid aluminum alloys.

Material	Temperature Range (°C)	Experimental Technique	$D_\theta$ (m <sup>2</sup> /s)	$Q$ (kJ/mol)	Diffusivity At 20°C (m <sup>2</sup> /s)	Reference
1060	20	Permeation	---	---	$2.4 \times 10^{-10}$	[19]
AA 7075-T6	20	Galvanostatic Permeation	---	---	$2 \times 10^{-13}$	[16]
2024-T3	20	Potentiostatic Permeation	---	---	$4 \times 10^{-11}$	
7075-T6	20	Galvanostatic Permeation	---	---	$2.3 \times 10^{-11}$	
7076-T6	20	Potentiostatic Permeation	---	---	$2.5 \times 10^{-11}$	[15]
7075-T6	20	Current Pulse	---	---	$6 \times 10^{-11}$	
7050-T3 (UA)	150-250		$5.49 \times 10^{-9}$	$15.8 \pm 5.0$	$9.33 \times 10^{-12}$	
7050-T6 (PA)	150-400		$2.24 \times 10^{-9}$	$16.1 \pm 4.2$	$3.37 \times 10^{-12}$	
7050-T74 (OA)	150-400	Isothermal Desorption	$1.70 \times 10^{-7}$	$32.7 \pm 6.7$	$3.15 \times 10^{-13}$	Present Work
Low Cu "PA"	150-250		$2.65 \times 10^{-9}$	$14.2 \pm 2.5$	$8.59 \times 10^{-12}$	
Low Cu OA	150-25-		$3.24 \times 10^{-9}$	$14.2 \pm 3.2$	$1.05 \times 10^{-11}$	
Al + 0.02 Li	186-252		$8.5 \times 10^{-9}$	$43.9 \pm 14.8$	$1.3 \times 10^{-16}$ *	
Al+0.26 Li	276-381	Tritium concentration profile analysis	$9.3 \times 10^{-9}$	$48.5 \pm 15.0$	$2.1 \times 10^{-17}$	[18]
Al+1.12 Li	381-480		$5.3 \times 10^{-9}$	$62.7 \pm 13.8$	$3.5 \times 10^{-20}$	
Al + 1 wt.% Li	250-600		$2.34 \times 10^{-8}$	18.98	$9.67 \times 10^{-12}$ *	
Al + 2 wt.% Li	325-600	Isothermal Desorption	$1.83 \times 10^{-8}$	18.12	$1.08 \times 10^{-11}$	[12]
Al + 3wt.% Li	325-600		$6.66 \times 10^{-8}$	29.32	$3.94 \times 10^{-13}$	

\* indicates a value extrapolated from high temperature data

### Hydrogen Trapping in Aluminum Alloys


The effect of solute atoms on hydrogen diffusion was investigated by Leger and Piercy who used internal friction experiments to quantify hydrogen trapping at copper and magnesium solute atoms in Al-Cu and Al-Mg binary alloys [20]. Their research indicates that these elements were relatively weak traps with binding energies of <4.8 and <5.8 kJ/mol for copper and magnesium, respectively. Other microstructural defects such as precipitates and dislocations may also act as hydrogen trap states. Saitoh, Iijima, and co-workers have used tritium microautoradiography to investigate hydrogen trapping in high purity aluminum, Al-4 Cu mass%, Al-1 Mg<sub>2</sub>Si mass%, and an Al-6wt%Zn-2wt%Mg alloy [21, 22]. This technique has spatial resolution better than 0.1 μm.

The microautoradiography work suggests that, in general, microstructural features with tensile elastic stress fields act as hydrogen traps while features with compressive elastic stress fields act as hydrogen repellers [21, 22]. Guinier-Preston (GP) zones with compressive stress fields (the Al-Mg<sub>2</sub>Si and the Al-Zn-Mg alloys) repel hydrogen while GP-zones with a tensile stress field (the Al-Cu alloy) act as hydrogen traps [21, 22]. In each of these alloys, trapping was observed at dislocations introduced by cold work and at interfacial dislocations associated with tensile elastic stress fields (the θ/matrix interface in the Al-Cu alloy and the η'/matrix interface in the Al-Zn-Mg alloy). Additionally, no evidence of hydrogen trapping was found at either η' precipitates or grain boundaries in the Al-Zn-Mg alloy [22].

### Implications to Hydrogen Environment Assisted Crack Growth

In copper bearing 7XXX series alloys, it is well established that overaging produces an increased resistance to crack growth in both liquid and gaseous water environments [5, 23-27]. Without copper additions greater than ~1 wt. % [27], overaging has little effect on crack growth kinetics. The findings of the present study can help explain these observations.

As shown in Figure 3, the native oxide on overaged AA 7050 retards hydrogen ingress (likely because the thicker  $\text{Al}_2\text{O}_3$  oxide is more stable and prevents hydrogen production as discussed previously) for significantly longer times (little uptake after 20 hours) relative to the underaged temper (significant uptake after 2 minutes). The increased resistance of AA 7050 OA to hydrogen ingress likely delays SCC initiation and increases SCC incubation<sup>1</sup> times. When freshly bared metal is present to produce corrosion generated hydrogen, Figures 3 and 8 show little difference in the hydrogen uptake rates. In this case, analogous to SCC from a precrack with freshly bared metal [5], the increased resistance of the overaged temper is likely from the decrease in the apparent diffusivity of hydrogen. Note that Figure 5 predicts that this benefit only occurs at temperatures  $<200^\circ\text{C}$ . Additional support for the role of diffusion limiting crack growth kinetics comes from a comparison of the apparent activation energies for crack growth and hydrogen diffusion. For AA 7050, overaging produces a change in activation energy for crack growth in 90% RH air and for hydrogen diffusion of approximately 16 kJ/mol [5] as shown in Figure 9.

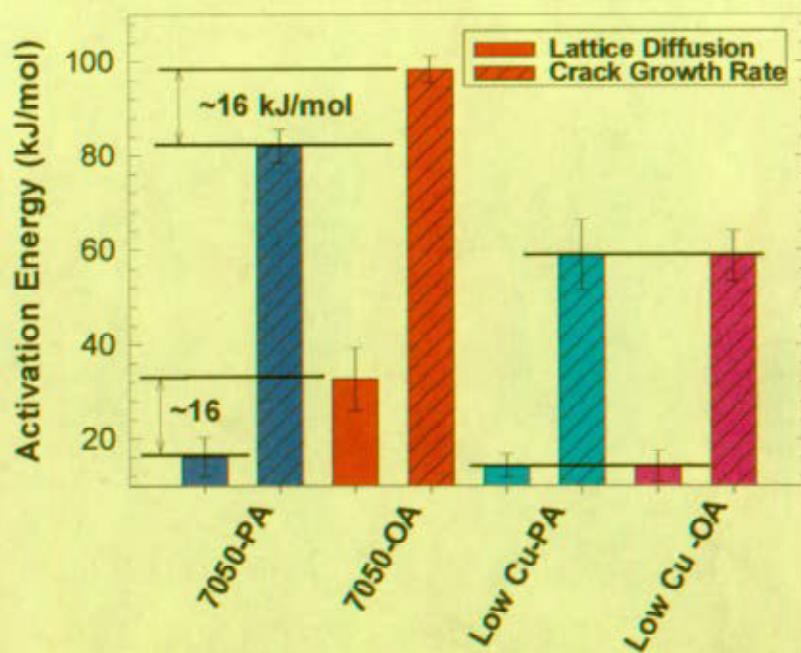

**Figure 9.** Comparison of the change in the apparent activation energy for stage II crack growth and for hydrogen diffusion. Note that the change for diffusion and crack growth is approximately equal (~16 kJ/mol) for the copper bearing AA 7050 while little change is observed for the low copper alloy.

<sup>1</sup> Here, SCC incubation is defined as the time required to initiate crack growth from a fatigue precracked (but oxide covered) specimen.

## Conclusions

- Exposure of bare AA 7050 to 90°C, 90% RH air produces near-surface concentrations of hydrogen on the order of 20,000 wt. ppm (~50 atomic %) within 1  $\mu\text{m}$  of the surface. These concentrations were observed in both crack wake samples and in unstressed coupons.
- When exposed to 90°C, 90% RH air, hydrogen uptake is not impeded by the native oxide of underaged AA 7050 but it is hindered by the native oxide of the overaged temper.
- In copper bearing AA 7050, the overaged temper displayed an activation energy for hydrogen diffusion ~2x greater than that of peak aged or underaged heat treatments (~33 kJ/mol vs. 16 kJ/mol). In the low copper alloy, overaging has little effect on either the activation energy or apparent diffusivity of hydrogen.
- Since near surface hydrogen concentrations and concentration profiles (~0-1  $\mu\text{m}$ ) are similar in crack wake samples from AA 7050-UA and AA 7050-OA, the enhanced cracking resistance of the overaged temper is, in part, due to the decreased diffusivity of hydrogen through the AA 7050-OA.

## References

1. Lorimer, G.W., *Precipitation in Aluminum Alloys*, in Precipitation Processes in Solids, K.C. Russell and H.I. Aaronson, editors, TMS-AIME, Niagara Falls, NY, p. 87-119, 1976.
2. Bigot, A., *et al.*, "Tomographic Atom Probe Study of Age Hardening Precipitation in Industrial AlZnMgCu (7050) Alloy", *Materials Science Forum*, Vol. 217-222, p. 695-700, 1996.
3. Cziraki, A., B. Fogarassy, and I. Gerocs, *Solid State Reactions in Al-Zn-Mg-Cu Alloys*, in Light Materials for Transportation Systems, N.J. Kim, editor, TMS, Kyongju, Korea, p. 391-405, 1993.
4. Staley, J.T., "Aging Kinetics of Aluminum Alloy 7050", *Met. Trans.*, Vol. 5, p. 929-932, 1974.
5. Young, G.A. and J.R. Scully, "The Effects of Test Temperature, Temper, and Alloyed Copper on the Hydrogen-Controlled Crack Growth Rate of an Al-Zn-Mg-(Cu) Alloy", *Met. Trans. A*, Vol. submitted for publication 2001.
6. Young, G.A., *Hydrogen Environment Assisted Cracking of an Al-Zn-Mg-(Cu) Alloy*, Ph.D., University of Virginia, Charlottesville, 1999.
7. Young, G.A. and J.R. Scully, "The Diffusion and Trapping of Hydrogen in High Purity Aluminum", *Submitted to Acta Mat.*, 1998.
8. Smith, S.W. and J.R. Scully, *Hydrogen Trapping and its Correlation to the Hydrogen Embrittlement Susceptibility of Al-Li-Cu-Zr Alloys*, in Hydrogen Effects in Metals, A.W. Thompson and N.R. Moody, editors, TMS, Moran, Wyoming, 1994.
9. Smith, S.W., *Hydrogen Interactions and Their Correlation to the Hydrogen Embrittlement Susceptibility of Al-Li-Cu-Zr Alloys*, Ph.D., University of Virginia, Charlottesville, 1995.

---

10. Hill, M.L. and E.W. Johnson, "The Diffusivity of Hydrogen in Nickel", *Acta Met.*, Vol. 3, p. 566-571, 1955.
11. Outlaw, R.A., D.T. Petersen, and F.A. Schmidt, "Diffusion of Hydrogen in Large Grain Aluminum", *Scripta Met.*, Vol. 16, p. 287-292, 1982.
12. Anyalebechi, P.N., "Hydrogen Diffusion in Al-Li Alloys", *Met. Trans. B*, Vol. 21B, p. 649-655, 1990.
13. Puiggali, M. and e. al., "Effect of Microstructure on Stress Corrosion Cracking of an Al-Zn-Mg-Cu Alloy", *Corr. Sci.*, Vol. 40(4/5), p. 805-819, 1998.
14. Wefers, K. and C. Misra, *Oxides and Hydroxides of Aluminum*, Report , Alcoa Laboratories, Alcoa Center, 1987.
15. Braun, R., H.-J. Schluter, H. Zuchner, and H. Buhl, *Hydrogen Permeation Measurements in Aluminum Alloy Foils*, in Hydrogen Transport and Cracking in Metals, A. Turnbull, editor, The Institute of Materials, Teddington, UK, p. 280-288, 1994.
16. Gest, R.J. and A.R. Troiano, *Hydrogen Embrittlement and Stress Corrosion Cracking in Aluminum Alloys*, in L'Hydrogene dans les Metaux, Editions Science et Industrie, Paris, p. 427-432, 1972.
17. Gest, R.J. and A.R. Troiano, "Stress Corrosion and Hydrogen Embrittlement in an Aluminum Alloy", *Corrosion*, Vol. 30(8), p. 274-279, 1974.
18. Nakashima, M., M. Saeki, Y. Aratono, and E. Tachikawa, "Diffusivity of Tritium in Li-Al Alloys", *J. Nucl. Mats*, Vol. 116(141-146), p. 141-146, 1983.
19. Onuchukwu, A.I. and S. Trasatti, "Hydrogen Permeation into Aluminum alloy 1060 as a Result of Corrosion in Alkaline Medium. Basic Features of the Process", *Electrochimica Acta*, Vol. 33(10), p. 1425-1430, 1988.
20. Leger, M. and G.R. Piercy, "Internal Friction in Hydrogen-Charged Aluminium Alloys", *Phil. Mag. A*, Vol. 43(2), p. 337-385, 1981.
21. Saitoh, H., Y. Iijima, and K. Hirano, "Behavior of Hydrogen in Pure Aluminium, Al-4mass% Cu and Al-1mass% Mg<sub>2</sub>Si Alloys Studied by Tritium Electron Microautoradiography", *Journal of Materials Science*, Vol. 29, p. 5739-5743, 1994.
22. Iijima, Y., *et al.*, "Hydrogen Trapping and Repelling in an Al-6wt%Zn-2wt%Mg Alloy", *J. Mat. Sci.*, Vol. 27 (21), p. 5735-5738, 1992.
23. Hyatt, M.V. and M.O. Speidel, *Stress-Corrosion Cracking of High-Strength Aluminum Alloys*, Report No. D6-24840, Boeing, Seattle, WA, 1970.
24. Speidel, M.O., "Stress Corrosion Cracking of Aluminum Alloys", *Met. Trans. A*, Vol. 6A, p. 631-651, 1975.
25. Scamans, G.M., "Stress Corrosion Cracking of Aluminium Alloys by Hydrogen Embrittlement", *Aluminium*, Vol. 58, p. 332-334, 1982.
26. Holroyd, N.J.H., A.K. Vasudevan, and L. Christodoulou, *Stress Corrosion of High-Strength Aluminum Alloys*, in Aluminum Alloys-Contemporary Research and Applications, A.K. Vasudevan and R.D. Doherty, editors, Academic Press, New York, p. 463-483, 1989.
27. Sarkar, B., M. Marek, and E.A. Starke, "The Effect of Copper Content and Heat Treatment on the Stress Corrosion Characteristics of Al-6zn-2Mg-X Cu Alloys", *Met. Trans. A*, Vol. 12A, p. 1939-1943, 1981.